

Cite this: *Mater. Adv.*, 2022,
3, 1539

Tailoring co-doping of cobalt and nitrogen in a fullerene-based carbon composite and its effect on the supercapacitive performance†

Bohong Jiang,^{‡,a} Guangpu Zhang,^{‡,b} Qin Tang,^c Fancang Meng,^a Dechun Zhou,^a Wenli Zhao,^a Wei Jiang^{id}*^b and Qingmin Ji^{id}*^a

Fullerene-based carbons have attracted great attention in applications of energy storage and conversion due to their unique properties and tunable architectures. However, fullerene's poor long-range conductivity limits their application performance for supercapacitors. Therefore, developing active fullerene-based carbons with high capacitances is expected. In this work, mesoporous carbon composites with various doping amounts of cobalt (Co) and nitrogen (N) were fabricated via manipulation of fullerene self-assembly with a cobalt tetramethoxy phenylporphyrin (CoTMPP) and pyrolysis. The confined state of CoTMPPs within the fullerene superstructures facilitates the fixation of Co and N during the carbonation and leads to a highly homogeneous distribution state within fullerene-based carbon composites. When used as electrodes for supercapacitors, the doped carbon composite showed significantly improved electrochemical performance. The specific capacitance could be nearly ten times higher than that of the fullerene carbons without doping and they have excellent cyclic stability. The work presents new insight into controllable functional doping of carbon materials. It may also further promote the development of fullerene superstructures for advanced electrochemical applications.

Received 9th October 2021,
Accepted 5th December 2021

DOI: 10.1039/d1ma00937k

rsc.li/materials-advances

Introduction

Unlike other kinds of carbon materials, fullerene could be used as building blocks to assemble into multi-dimensional superstructures with various morphologies and transform into stable mesoporous carbon materials after thermal treatments.^{1–6} Due to their unique properties and tunable architectures at the molecular level, these fullerene-based carbons have attracted great attention for application in solar cells, energy storage and conversion.^{7–9} However, when used as electrode materials for supercapacitors, the specific capacitance of the fullerene-based carbons was still relatively low. Therefore, the search for an

active fullerene-based supercapacitor with improved performance is still needed.

Doping heteroatoms in the structure is one of the best solutions to overcome the shortcomings of fullerene's poor long-range conductivity.^{10–12} It may also improve the structural features of the fullerene superstructures for electrochemical applications.^{13,14} Almost all the species, metals or non-metals could be doped in fullerenes. Particularly, metal doping may effectively improve the electronic properties of fullerene-derived carbons.^{15–17} The doped metals could form a binary electron acceptor–donor system and provide more active sites in the structures.¹⁸

Various strategies have been applied for the metal doping of fullerene superstructures. For example, Peng *et al.* fabricated three-dimensional cross-type Fe-doped fullerene structures by self-assembly of ferrocene-modified fullerene and achieved enhanced electrochemical performance.¹⁹ Saianand *et al.* introduced copper into fullerene superstructures by a hard template and used them as effective catalysts for the oxygen reduction reaction (ORR).²⁰ We also successfully prepared fullerene carbon materials with enhanced supercapacitive properties by regulating the self-assembled structures of ferrocene-modified fullerenes in our previous work.²¹ However, these studies still cannot control the doping ratio of metals. The relationship between the metal doping content and application performance of fullerene-derived carbons is thus unclear.

^a Herbert Gleiter Institute for Nanoscience, School of Materials Science and Engineering, Nanjing University of Science & Technology, 200 Xiaolingwei, Nanjing, 210094, China. E-mail: jiqingmin@njjust.edu.cn

^b National Special Superfine Powder Engineering Technology Research Center, Nanjing University of Science and Technology, 200 Xiaolingwei, Nanjing, 210094, China. E-mail: superfine_jw@126.com

^c School of Chemistry and Chemical Engineering, Yancheng Institute of Technology, No. 1 Mid. Xiwang Avenue, Yancheng, China

† Electronic supplementary information (ESI) available: SEM and TEM images, FTIR spectra, Raman spectra, XPS spectra, nitrogen isotherms and CV curves of fullerene superstructures and related fullerene-based carbons. See DOI: 10.1039/d1ma00937k

‡ B. J and G. Z contributed equally to this work.



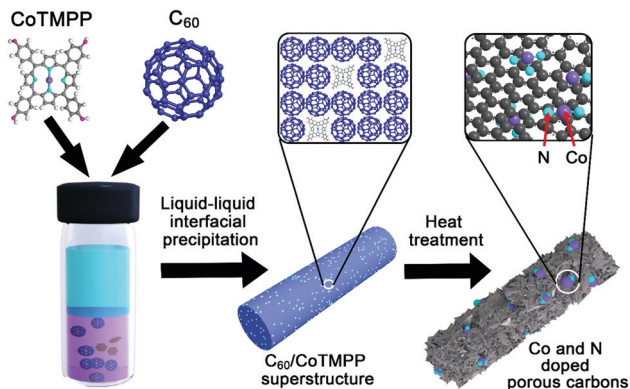


Fig. 1 Scheme for the preparation of Co and N doped carbon composites by manipulating C₆₀ assembly with CoTMPP and pyrolysis.

Herein, we fabricated cobalt (Co) and nitrogen (N) doped mesoporous carbon composites based on the liquid-liquid interfacial precipitation (LLIP) process of C₆₀ fullerenes with a cobalt tetramethoxy phenylporphyrin (CoTMPP) and pyrolysis. By manipulating the mixing ratios of C₆₀ and CoTMPP, we obtained various porous carbon materials with controllable doping amounts of Co and N (totally 0.30–1.52%) (Fig. 1). Co, a transition metal, has excellent energy storage capability for supercapacitors. But unfavorable aggregation may easily occur during the doping process or their usage.²² The confined state of CoTMPP within C₆₀ crystalline structures could prevent Co agglomeration in the carbon structure and successfully dope functional Co and N simultaneously. With the homogenous distribution of Co and N, the resultant mesoporous carbon composites exhibit excellent energy storage performance, the specific capacitance value of which could be about ten times higher than that of the fullerene carbons without doping and also well maintained 99.5% specific capacitance at least after 5000 cycles.

Experimental part

The assembly process of fullerene superstructures

C₆₀s are dissolved in toluene (about 2.5 mg mL⁻¹) by sonication for 1 hour. The undissolved C₆₀s in the toluene solution are removed by filtration. The self-assembly of fullerenes is based on the liquid-liquid interfacial precipitation (LLIP) process. For details, 4 ml C₆₀ solution is placed in a glass bottle (15 mL), and 8 mL IPA is slowly added on the top of the solution to form an interface. The mixture solution is left undisturbed for 5 minutes and then stored at room temperature for 12 hours after shaking. The sediment from the process is collected by centrifugation. In the C₆₀CoTMPP assembly process, C₆₀ and CoTMPP with different mixing ratios (5:1, 10:1, 20:1) are dissolved in toluene by sonication, and then similar procedures mentioned above are followed. The C₆₀CoTMPP crystals obtained from mixing ratios of 5:1, 10:1, and 20:1 are named C₆₀CoTMPP-0.2, C₆₀CoTMPP-0.1 and C₆₀CoTMPP-0.05, respectively.

Formation of mesoporous carbons from fullerene superstructures

The collected precipitate from the LLIP process is dried under vacuum. The dry samples are then heated to 900 °C with a heating speed of 10 °C min⁻¹ and kept for 2 hours at 900 °C in a tubular pyrolysis furnace under a constant nitrogen flow (120 cm³ min⁻¹). The carbonized C₆₀CoTMPP crystals from C₆₀CoTMPP-0.2, C₆₀CoTMPP-0.1 and C₆₀CoTMPP-0.05 are named C₆₀CoTMPP-0.2_900, C₆₀CoTMPP-0.1_900 and C₆₀CoTMPP-0.05_900, respectively.

Electrochemical measurements

The electrochemical performance is measured in a three-electrode system in 1 M H₂SO₄ aqueous electrolyte. A glassy carbon electrode is used as the working electrode, with a Ag/AgCl electrode as the reference electrode and Pt wire as the counter electrode. For the preparation of the working electrode, one drop of the IPA-water suspension of the porous carbon samples (5 μL, 5 mg mL⁻¹) is spread on the surface of the glassy carbon electrode and dry at room temperature. 2.5 μL Nafion solution (0.05%) is dropped on the glassy carbon electrode before the measurement. The specific capacitance (C_s) is calculated from the cyclic voltammograms (CV) the galvanostatic charge/discharge (CD) curves according to the following equations:

$$C_s(\text{weight}) = Q/(2\Delta E \cdot v \cdot m)$$

$$\text{or } C_s(\text{area}) = Q/(2\Delta E \cdot v \cdot A)$$

$$C_s = I/(m \cdot \Delta E / \Delta t)$$

in which Q is the area encircled by CV, I is the voltammetric current or the constant current for charge-discharge, ΔE is the potential range, v is the scan rate, A is the surface area of the active material, m is the mass of the active material, and Δt is the discharge time, respectively.

Characterization

Field emission scanning electron microscopy (FE-SEM) is performed at 15 kV on a FEI Quanta 250FEG. Transmission electron microscopy (TEM) is performed by using a Tecnai G220 at 200 kV. Nitrogen sorption measurements are conducted on powder samples at 77 K using an Autosorb-1 surface area and pore size analyzer (Gemini VII 2390). X-Ray diffraction (XRD) patterns are measured using a Bruker-AXS D8 Advance diffractometer. Raman spectra are recorded on a Raman scattering spectrometer (Renishaw-invia) using excitation radiation at 514 nm from an Ar⁺ ion laser and at a power of 10 mW. Fourier transform infrared (FTIR) spectra are obtained using a FTIR spectrometer Nicolet S10 (Thermo Fisher). The Co contents in the carbon samples are determined by inductively coupled plasma optical emission spectroscopy (ICP-OES) using Agilent 5110.



Results and discussion

Fullerene superstructures from the mixture of C₆₀ and CoTMPP

According to the solubility of C₆₀ in solvents, C₆₀s may self-assemble into crystalline superstructures at the interface of good and bad solvents.²³ Therefore, various solvent types could affect the packing of C₆₀s and lead to different morphologies of C₆₀ superstructures. As the driving force of the fullerene assembly is mainly based on π - π interactions, other π -molecules may easily intercalate into the C₆₀s superstructures from the co-assembly.⁸ In the system with CoTMPP, a metalloporphyrin molecule, as its metal ion center could coordinate with carbon atoms in fullerene,^{24,25} it may thus further promote the insertion into C₆₀ superstructures.

In this work, we use toluene (PhMe)-isopropyl alcohol (IPA) as the solvent system to carry out the self-assembly of C₆₀s based on the LLIP process. Without mixing CoTMPP, the assembly of C₆₀s at the toluene-IPA interface leads to the formation of nanorods. As shown in Fig. S1 (ESI[†]), the nanorods are \sim 400 nm in diameter, \sim 10 μ m in length and possess smooth surfaces. The co-assembly with CoTMPP alters the packing of C₆₀s and leads to the formation of C₆₀CoTMPPs with completely different morphologies (Fig. 2 and Table S1, ESI[†]). C₆₀CoTMPP-0.2 shows rod morphology with polyprism structures (Fig. 2a). Its length is \sim 2.5 μ m and its diameter is \sim 1 μ m. C₆₀CoTMPP-0.1 seems to possess microparticles with lamellar structures (about \sim 1.9 μ m in diameter) and a rough surface (Fig. 2b). While for C₆₀CoTMPP-0.05 with the lowest mixing amount, similar rod morphology like the nanorods from pure C₆₀s is obtained (Fig. 2c), but it shows shorter lengths (\sim 2.3 μ m) and larger diameters (\sim 1.2 μ m). We suggest that the influence of the CoTMPP amount on the morphologies

of C₆₀CoTMPP superstructures should be caused by the strong packing inclination between CoTMPPs. CoTMPPs can form flaky crystals in the solvent mixture of PhMe-IPA (Fig. S2, ESI[†]). This aggregation inclination of CoTMPPs may change their insertion state within C₆₀s and might also interfere with the packing of C₆₀s during the co-assembly process. It thus leads to distinct structural features of the C₆₀CoTMPP superstructures. It should be mentioned that even higher content of CoTMPP is possible to assemble with C₆₀s. For example, crystalline nanosheets of C₆₀/CoTMPP can be formed at a mixing ratio of 1 : 1. However, the C₆₀/CoTMPP hybrid structure with mixing ratios higher than 5 : 1 may cause serious fusion of Co components and destroy the morphology during the following heat treatment. As the resultant blocks can hardly be used for further applications, we thus focus on the C₆₀/CoTMPP superstructures with the mixing ratio lower than 5 : 1.

The elemental mapping analyses indicate the homogenous distributions of Co, N, and C elements across the microstructures for all C₆₀CoTMPP superstructures (Fig. S3, ESI[†]). HR-TEM observations prove the changes of C₆₀s packing after the intercalation of CoTMPPs (Fig. 2g-i). The nanorods from bare C₆₀s (C₆₀-rod) show regular lattices of 1.21 nm and 0.927 nm, which correspond to the (110) and (101) planes (Fig. S4, ESI[†]). The lattice spacing of C₆₀CoTMPP superstructures is inclined to shrink with the increase of the CoTMPP amount. As shown in Fig. 2g, C₆₀CoTMPP-0.2 shows a lattice spacing of 1.16 nm for the (110) plane, while the spacing of C₆₀CoTMPP-0.1 and C₆₀CoTMPP-0.05 turns to be 0.863 nm and 0.882 nm for the (101) plane, respectively.

The detailed crystalline structures of C₆₀CoTMPPs are analyzed by the X-ray diffraction (XRD) technique (Fig. 3). Similar to C₆₀ nanorods without CoTMPP, the XRD patterns of C₆₀CoTMPPs also show the characteristic peaks of the HCP phase. However, with the presence of CoTMPP, a new diffraction peak at 6.2°, which should arise from the packing of CoTMPPs, appeared. The diffraction peak for the (110) plane (around 7.4°) also shifts to a little higher degree for C₆₀CoTMPPs, which is consistent with the TEM observations. The intercalation of CoTMPPs within C₆₀s might strengthen the interactions between molecules and lead to the spacing shrinkage of C₆₀s.

To understand the molecular interactions between C₆₀ and CoTMPP, FTIR spectra of pure C₆₀ rods, CoTMPP, and C₆₀CoTMPPs were measured (Fig. S5, ESI[†]). The peaks around 550 cm⁻¹, 1185 cm⁻¹ and 1430 cm⁻¹ for C₆₀ nanorods and C₆₀CoTMPPs can be attributed to the ring stretching and deformation vibrations of C₆₀s.²⁶ The characteristic peaks of CoTMPP at 750-900 cm⁻¹ (ρ -substituted phenyl groups and N-H bending), 1510 cm⁻¹ (C-C bonds in the pyrrole ring), 1254 cm⁻¹ (C-N stretching vibration), and 1000 cm⁻¹ (breathing modes of the pyrrole ring) are found to shift to lower wave-numbers for C₆₀CoTMPPs.²⁷ This implies the interactions between the porphyrin moieties and C₆₀s in the C₆₀CoTMPPs.

Mesoporous carbon from C₆₀/CoTMPP crystals

As solvent molecules exist within the fullerene superstructures from the LLIP assembly process, carbonization of fullerene

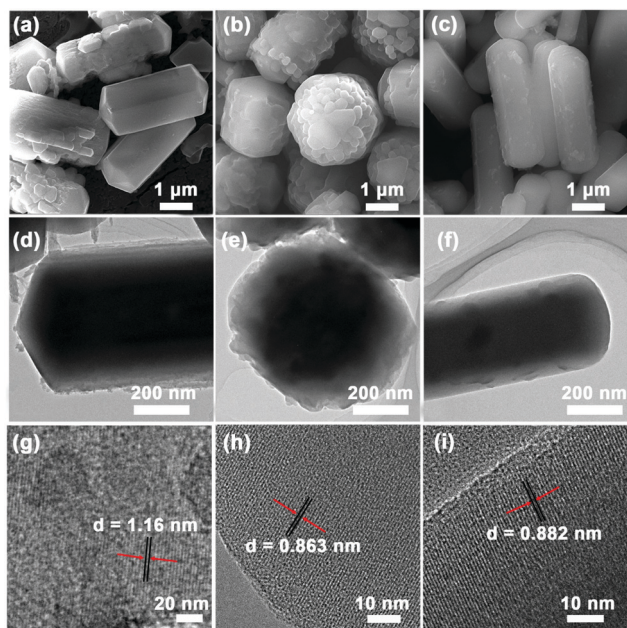


Fig. 2 SEM and TEM images of (a, d and g) C₆₀CoTMPP-0.2; (b, e and h) C₆₀CoTMPP-0.1; and (c, f and i) C₆₀CoTMPP-0.05.



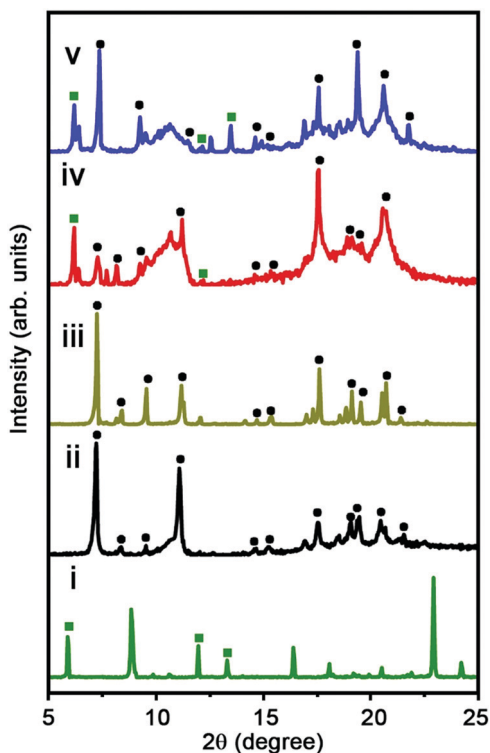


Fig. 3 XRD patterns of C_{60} CoTMPP structures. (i) C_{60} CoTMPP-0.2, (ii) C_{60} CoTMPP-0.1, (iii) C_{60} CoTMPP-0.05, (iv) C_{60} -rods, and (v) CoTMPPs.

superstructures may induce the formation of meso- or micropores in the carbon structures, which is beneficial for their applications for energy storage. In this work, C_{60} CoTMPP crystals were carbonized through heat treatment at 900 °C under N_2 flow.

The Raman spectra of the resultant C_{60} CoTMPP_900s exhibit two strong bands around 1360 and 1580 cm^{-1} , corresponding to the D band from defect-containing or disordered graphitic carbon and the G band from the in-plane vibration of sp^2 carbons (Fig. 4a). The typical peaks from C_{60} (two A_g bands and six H_g bands), which are observed in Raman spectra of C_{60} CoTMPPs, disappeared (Fig. S6, ESI†). This indicates the successful structural transformation to carbon materials after the heat treatment (Fig. 4a). The intensity ratios of the D band and G band (I_D/I_G) for C_{60} _900 (without CoTMPP), C_{60} CoTMPP-0.05_900, C_{60} CoTMPP-0.1_900 and C_{60} CoTMPP-0.2_900 are 0.76, 1.09, 0.92 and 1.18. This result suggests that the intercalation of CoTMPPs in the fullerene superstructures may induce the formation of more defects in the carbon structures. But the orders of I_D/I_G for C_{60} CoTMPP_900s are not exactly the same as the CoTMPP amount in C_{60} CoTMPPs. This implies that the intercalation state of CoTMPP might also influence the transforming structures of carbons. In C_{60} CoTMPP_900s, the A_{1g} vibration mode (690 cm^{-1}) of Co components appears and its intensity is increased with the additional CoTMPP amount in C_{60} CoTMPPs.^{28,29} This suggests the consistence of the Co doping amount of C_{60} CoTMPP_900s with the intercalated CoTMPPs in C_{60} CoTMPPs.

The XRD patterns of C_{60} CoTMPP_900s also indicate that the characteristic diffraction peaks of C_{60} CoTMPP disappeared

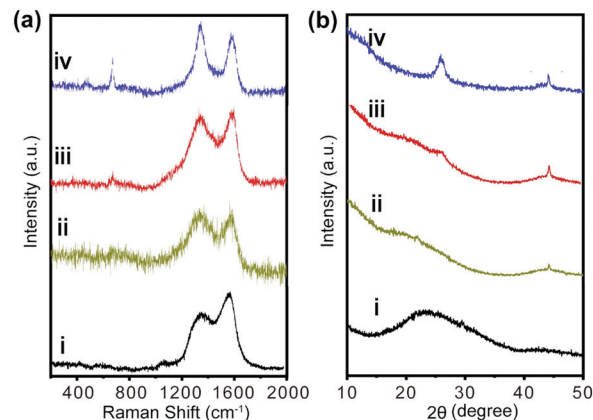


Fig. 4 (a) Raman spectra and (b) XRD patterns of C_{60} _900s and C_{60} CoTMPP_900s. (i) C_{60} _900s (ii) C_{60} CoTMPP-0.05_900, (iii) C_{60} CoTMPP-0.1_900, and (iv) C_{60} CoTMPP-0.2_900.

after carbonation (Fig. 4b). Unlike the carbonized C_{60} _900 (without doping) with only a wide peak in the range of 20–30°, two additional diffraction peaks appeared at 25.8° and 44.2° for C_{60} CoTMPP_900s. The diffraction at 25.8° is ascribed to the (002) plane of graphite,³⁰ which suggests that the existence of CoTMPP might promote the stacking of graphene sheets during the structural transformation of fullerenes into carbons. While the diffraction at 44.2° should arise from the planes of cobalt nitride and cobalt oxide,^{31,32} which can be attributed to the (111) plane of CoN_4 (JCPDS No. 41-0943) and the (400) plane of Co_3O_4 (JCPDS No. 42-1467) (Fig. S7, ESI†). Its peak intensity is shown to increase with the mixing amount of CoTMPP in C_{60} CoTMPPs, indicating again varied doping amounts of Co and N in C_{60} CoTMPP_900s.

The TEM observations directly indicate the formation of the porous matrix of C_{60} CoTMPP_900s from the dense crystalline nature of C_{60} CoTMPPs (Fig. S8, ESI† and Fig. 5). Compared with various C_{60} CoTMPP_900s, we can find that C_{60} CoTMPP-0.1_900 has a much looser networked structure, which means more pore spaces and larger exposure surfaces for active sites. The elemental mapping analyses based on TEM prove the existence of Co, N, and C elements (Fig. 5). This also reveals the maintenance of the dispersion state of Co and N after the high-temperature heat treatment. With different doping amounts, C_{60} CoTMPP_900s possess varied Co distribution states in the structure (Fig. S8, ESI†). C_{60} CoTMPP-0.01_900 shows tiny nanoparticles of Co components with relatively scattered distributions. We can also observe tiny nanoparticles in the structure of C_{60} CoTMPP-0.1_900, but it has much more dense distributions. While for C_{60} CoTMPP-0.2_900, nanoparticles can be hardly found, and metal components seem to aggregate as blocks in the structure.

To understand the molecular transformation during the pyrolysis, we use thermogravimetric analysis (TGA) to gain information (Fig. S9, ESI†). The thermograms of C_{60} CoTMPPs show a small weight loss of 5–8% below 150 °C, which should be attributed to the removal of solvent molecules within the superstructures. The weak mass loss that occurred between 450



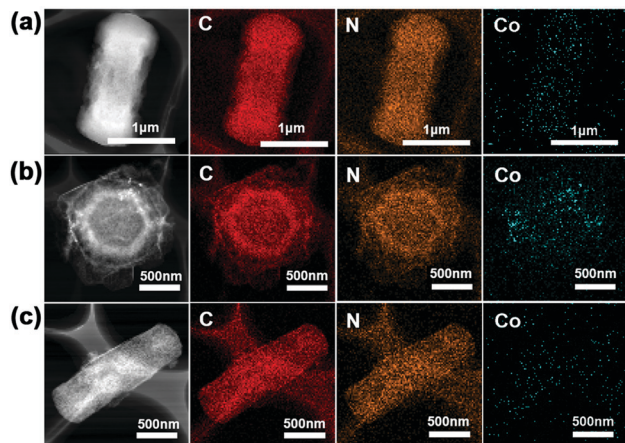


Fig. 5 STEM images and the corresponding elemental mapping images of $C_{60}CoTMPP_{900s}$. (a) $C_{60}CoTMPP-0.2_{900}$, (b) $C_{60}CoTMPP-0.1_{900}$, and (c) $C_{60}CoTMPP-0.05_{900}$.

and 600 °C is related to the gradual decomposition of CoTMPP. A significant mass loss at a temperature higher than 700 °C is observed, which should be associated with molecular changes from $C_{60}s$. $C_{60}s$ are transferred into carbon networks or decomposed by the oxygen within the structures. Comparing the weight loss ratios of $C_{60}CoTMPPs$ and C_{60} -rod, we can find that the presence of CoTMPPs in the C_{60} superstructures may effectively restrain the decomposition of $C_{60}s$ during the pyrolysis. The oxygen within the structure might prefer to combine with Co. This leads to the formation of more oxidized Co and lower decomposition of $C_{60}s$ for $C_{60}CoTMPPs$ with a large mixing amount of CoTMPP.

The chemical states of Co and N in $C_{60}CoTMPP_{900s}$ are further analyzed based on XPS measurement (Fig. 6 and Fig. S10, ESI†). Fig. 6a shows the Co 2p spectrum in the binding energy range from 770 to 810 eV by the Gaussian method. It contains split spin-orbit $2p_{3/2}$ (778–785 eV) and $2p_{1/2}$ (793–798 eV) regions. The spectrum is fitted into two states, whose peaks at 779 and 795 eV should belong to Co^{3+} (Co–O); peaks at 782 and 797 eV are attributed to Co^{2+} (Co– N_x) with satellite peaks at 786 and 805 eV.^{33,34} The N 1s spectra are deconvoluted into five peaks, which can be assigned to primary pyridine N (398.5 eV), metal N (399.2 eV), pyrrole N (400.2 eV), graphite N (401.5 eV), and oxidized N (404.5 eV) (Fig. 6b).^{35,36} The C 1s

spectrum shows the existence of a C=N bond (285.8 eV) with C=C (284.4 eV) and a C–O bond (289.2 eV) (Fig. 6c).³⁷ These results indicate that the doped Co and N atoms may form Co–N and Co–O in the carbon network of the fullerene-derived carbons.

According to the relative area of each component peak in XPS spectra, the proportions of different Co states in $C_{60}CoTMPP_{900s}$ are compared (Table S2, ESI†). The Co–N:Co–O ratio is 1.52 ($C_{60}CoTMPP-0.05_{900}$), 3.66 ($C_{60}CoTMPP-0.1_{900}$), and 0.5 ($C_{60}CoTMPP-0.2_{900}$), respectively. These results indicate that the formation of Co–N becomes greatly restrained in the carbonization of $C_{60}CoTMPPs$ when a large amount of CoTMPP is involved. Since CoTMPP in large amounts tends to aggregate themselves during the co-assembly with $C_{60}s$, the densely packed state of CoTMPPs in the superstructure and the oxygen in CoTMPPs may promote the oxidation of Co during carbonization and lead to the formation of less Co–N. ICP measurement was further employed to confirm the Co content in $C_{60}CoTMPP_{900s}$ (Table S3, ESI†). The result indicates that the mass fraction of the Co element is 1.52% for $C_{60}CoTMPP-0.2_{900}$, 0.71% for $C_{60}CoTMPP-0.1_{900}$, and 0.30% for $C_{60}CoTMPP-0.05_{900}$, respectively. In comparison of Co ratios in $C_{60}CoTMPP$ (before carbonation), which are 1.26% ($C_{60}CoTMPP-0.2$), 0.57% ($C_{60}CoTMPP-0.1$) and 0.26% ($C_{60}CoTMPP-0.05$), there is almost no loss of doped Co during the heating process. Compared with the theoretical content of Co in $C_{60}CoTMPP$ (Table S3, ESI†), there are also no big differences. These results demonstrate that we could precisely control the doping amount of Co in the fullerene carbon materials through this assembly process.

The doping influence on the porous structures of $C_{60}CoTMPP_{900s}$ is analyzed based on nitrogen adsorption/desorption isotherms (Fig. S11, ESI†). Brunauer–Emmett–Teller (BET) and Barrett–Joyner–Halenda (BJH) methods are adapted to calculate the specific surface area and pore size distributions (Table S4, ESI†). The isotherms of $C_{60}CoTMPP_{900s}$ are shown to be of type IV with a H3 hysteresis loop. This indicates the existence of mesopores and a small part of micropores in $C_{60}CoTMPP_{900s}$. $C_{60}CoTMPP-0.1_{900}$ has the highest BET surface area of about 496 m² g^{−1}, while those of $C_{60}CoTMPP-0.2_{900}$ and $C_{60}CoTMPP-0.05_{900}$ are 365 m² g^{−1} and 446 m² g^{−1}, respectively. As the intercalation of CoTMPP in $C_{60}s$ may bring more packing disorders in the structure, it might facilitate the

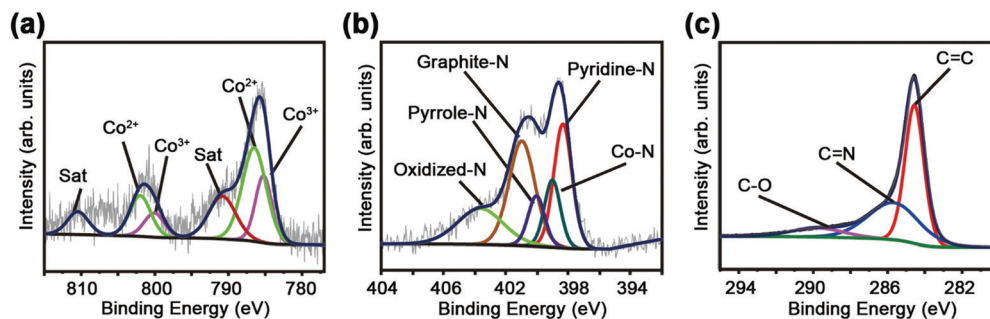


Fig. 6 XPS spectra of $C_{60}CoTMPP-0.1_{900}$. (a) Co 2p spectrum, (b) N 1s spectrum, and (c) C 1s spectrum.



production of more pores from the decomposition during the heat treatment. This thus leads to a higher surface area of $C_{60}CoTMPP_{900s}$ than the porous carbon from pure $C_{60}s$ (C_{60_900}), the surface area of which is $285\text{ m}^2\text{ g}^{-1}$ (Fig. S12, ESI[†]). However, when more CoTMPPs are involved, the presence of more CoTMPP aggregates and their effect on promoting the stacking of graphene sheets may diminish part of pores in the carbon structures, resulting in lower surface areas and also narrower distribution of pore size for $C_{60}CoTMPP-0.2_900$.

Electrochemical performances of $C_{60}/CoTMPP_{900s}$

The porous carbons derived from $C_{60}CoTMPP_{900s}$ are applied as electrode materials for supercapacitors. Their electrochemical supercapacitive properties are measured based on cyclic voltammetry (CV) and galvanostatic charge-discharge cycles (GCD) by using a three-electrode configuration in 1 M H_2SO_4 aqueous electrolyte. $C_{60}CoTMPP_{900s}$ are deposited at the surface of the glassy carbon electrode. SEM observation of the $C_{60}CoTMPP_{900}$ layers indicates their uniform coverage states on the electrode surface with porous nature accessible for electrolytes (Fig. S13, ESI[†]). The CV curves of $C_{60}CoTMPP_{900s}$ at 10 mV s^{-1} over the range of 0–0.8 V are shown in Fig. 7a. All samples display a rectangular-like shape curve, which proves that $C_{60}CoTMPP_{900s}$ could act like a typical double-layer capacitor. In contrast to the low specific capacitance of C_{60_900} without doping (32.5 F g^{-1} at 10 mV s^{-1} and 46.9 F g^{-1} at 1 A g^{-1}) (Fig. S14, ESI[†]), $C_{60}CoTMPP_{900s}$ with Co and N doping all show enhanced capacitive property of fullerene-based carbons. $C_{60}CoTMPP-0.1_900$ possesses the highest specific capacitance of 296 F g^{-1} or 0.1 F cm^{-2} . $C_{60}CoTMPP-0.05_900$ and $C_{60}CoTMPP-0.2_900$ have a specific capacitance of 168 F g^{-1} (0.06 F cm^{-2}) and 55 F g^{-1} (0.02 F cm^{-2}), respectively. That is to say, the capacitance order of $C_{60}CoTMPP_{900s}$ is

$C_{60}CoTMPP-0.1_900 > C_{60}CoTMPP-0.2_900 > C_{60}CoTMPP-0.05_900$. This order is consistent with that of the surface area of $C_{60}CoTMPP_{900s}$ and Co–N content in the carbons. This means that both structural and chemical factors may affect the performance. The surface area of the electrode is demonstrated as one major factor for supercapacitor performance.³⁸ It is related to the ion diffusion ability in the carbon electrode and the formation of an ion-electron double layer. The double-layer capacitance is known to be directly proportional to the surface area.³⁹ But for this system, the capacitance difference of $C_{60}CoTMPP_{900s}$ is much larger than that of their BET surface areas. This implies that the doping state of Co–N should bring great influence on their effective surface area for ion diffusion and conversion, which leads to a large difference in the electrochemical performance. However, the distinct effects from the porous structure and doping state cannot be evaluated separately. The assembly structures of fullerenes are sensitive to the assembly conditions. Small changes in the type and volume of solvents or additives may alter the structural features of the fullerene superstructures.^{23,40} Therefore, the intercalation of functional molecules within the $C_{60}s$ superstructures will inevitably change the assembled morphologies. The advantage of tunable architectures for fullerene assemblies always accompanies the functions.

The GCD curves of $C_{60}CoTMPP_{900s}$ are all triangular shapes, which also indicates a typical double-layer capacitor of the samples. The longer discharge time of $C_{60}CoTMPP-0.1_900$ means a higher specific capacitance of 416.31 F g^{-1} at 1 A g^{-1} (Fig. 7b). Compared with other reported fullerene-derived carbon materials (Table S5, ESI[†]), the performance of $C_{60}CoTMPP-0.1_900$ could exceed those of most of the reported fullerene carbon materials.

To further investigate the mechanism of charge storage for supercapacitors, electrochemical impedance spectroscopy (EIS) is performed. The Nyquist plots of $C_{60}CoTMPP_{900s}$ reveal good capacitive behaviors (Fig. 7c), which possess a semicircle in the high-frequency area and inclined linear plot at low frequencies. The width of the semicircle at high frequencies can determine charge transfer resistance (R_{ct}), which is associated with the charge transfer across the electrode–electrolyte interface. $C_{60}CoTMPP-0.1_900$ displays the shortest diameter of the semicircle, which means the lowest R_{ct} . This indicates more effective charge transfer and better capacitive contribution in $C_{60}CoTMPP-0.1_900$. The slope inclination in the low-frequency area is related to internal resistance (R_s). As $C_{60}CoTMPP-0.1_900$ exhibits the highest inclination degree, a higher electrical conductivity of $C_{60}CoTMPP-0.1_900$ is suggested. The calculated R_{ct} values for $C_{60}CoTMPP-0.05_900$, $C_{60}CoTMPP-0.1_900$, and $C_{60}CoTMPP-0.2_900$ are 11.2, 5.6, and $45.4\ \Omega$, and the R_s values are 6.2, 4.6, and $8.2\ \Omega$, respectively. $C_{60}CoTMPP-0.2_900$ shows the highest R_{ct} and R_s values, which suggests that besides the Co doping amount, the doping state and structural features may also have a large influence on the electron transfer in the carbon composites.

From the above results, it is observed that the content of Co–N in the carbon composites plays the main role in

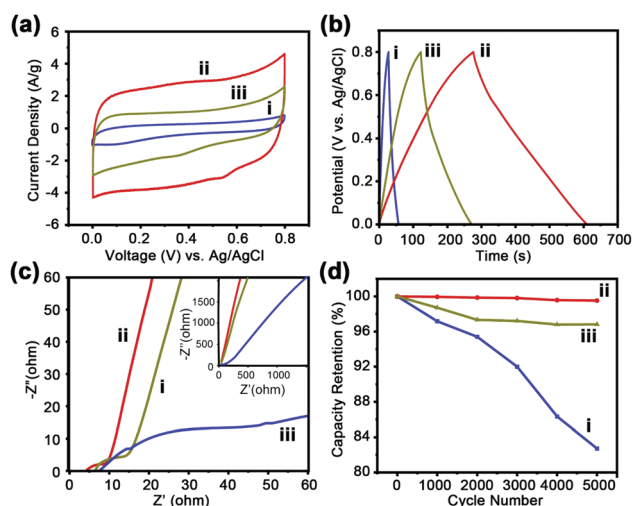


Fig. 7 (a) CV curves of $C_{60}CoTMPP_{900s}$ at a scan rate of 10 mV s^{-1} ; (b) CD curves of $C_{60}CoTMPP_{900s}$ at a current density of 1 A g^{-1} ; (c) Nyquist plots of $C_{60}CoTMPP_{900s}$; and (d) cycling stability test of $C_{60}CoTMPP_{900s}$. (i) $C_{60}CoTMPP-0.2_900$, (ii) $C_{60}CoTMPP-0.1_900$, and (iii) $C_{60}CoTMPP-0.05_900$.



improving the electrochemical performance. C₆₀CoTMPP-0.1_900 possesses unique morphology and highest content of Co–N, and thus exhibits better capacitance than C₆₀CoTMPP-0.05_900 and C₆₀CoTMPP-0.2_900. Although C₆₀CoTMPP-0.2_900 has the highest Co doping amount, more doped Co in the carbon structure exists as the Co–O state with the least content of Co–N, which brings an adverse effect on the conductivity of the carbon composite. The doping influence on the structural features also affects the electrochemical performance. The doping ratio of CoTMPP for C₆₀CoTMPP-0.1 completely changes the inclination of forming the rod morphology. The homogeneous distribution of CoTMPP in C₆₀CoTMPP-0.1 also facilitates the formation of Co–N and the transformation of more porous structures during the carbonation process. With less doping of CoTMPP, the assembled structure largely maintains the features of the C₆₀ superstructures without doping and shows limited influence on the formation of pores during the carbonation. While for C₆₀CoTMPP-0.2 with large doping of CoTMPP, CoTMPPs are dispersed in the superstructure as molecular aggregates and may more easily induce the formation of Co–O and dense packing of graphite carbons during the heat treatment. These factors make C₆₀CoTMPP-0.2_900 exhibit the worst performance. It should be noted that besides the doping content in C₆₀CoTMPP_900s, the existence of graphitic carbons is also important for electrochemical performance. Based on the TGA result, C₆₀s will not begin carbon transformation at a temperature lower than 700 °C. This means that no graphitic carbons formed for the carbonized C₆₀CoTMPPs by 700 °C. The resultant carbons also show poor electrochemical performance (Fig. S15, ESI[†]), in which C₆₀CoTMPP-0.1_700 only has a specific capacitance of 35 F g⁻¹, similar to fullerene-carbons without doping.

Considering the best electrochemical performance of C₆₀CoTMPP-0.1, we further evaluate its electrochemical stability. Fig. S16 (ESI[†]) shows the CV curves of C₆₀CoTMPP-0.1_900 at different scan rates from 10 to 100 mV s⁻¹. All curves at different scan rates display quasi-rectangular shape, indicating the good maintenance of double-layer capacitor behavior as well as good rate capability. The capacitance retention is also excellent, which is shown to keep >99% of the initial capacitance after 5000 GCD cycles (Fig. 7d). In contrast, C₆₀CoTMPP-0.05_900 could maintain about 97% of the capacitance, but C₆₀CoTMPP-0.2_900 shows a big decrease with the cycles. The worse electrochemical stability for C₆₀CoTMPP-0.2_900 should be due to the existence of more Co–O in the carbon composite, since cobalt oxides have disadvantages of poor electrical conductivity, easy polarization, and volumetric expansion during the charge and discharge processes.^{41,42} Therefore, this result further proves that the control of the CoTMPP intercalation state in C₆₀ structures is essential to both the porous feature and the doping states of Co in the carbon composites.

Conclusions

In summary, we successfully manipulated the intercalation of CoTMPP in the C₆₀ self-assembled structure through the LLIP

process and fabricated C₆₀ composite crystals with various microscopic morphologies. After carbonization, the CoTMPP confined in the C₆₀ crystals transformed into active Co–N in the carbon structures. The content of Co–N is shown to be not only directly related to the mixing ratio of CoTMPP in C₆₀ crystals but also the distribution state in the superstructures. The presence of Co–N in the porous carbon composites improves the electrochemical properties greatly. The resultant carbon composite showed an enhanced specific capacitance of 416.31 F g⁻¹ at 1 A g⁻¹, which is almost ten times higher than that of the C₆₀ carbons without doping, and could almost show no activity loss after at least 5000 cycles. This work brings new insight into controllable functional doping of carbon materials by fullerene interfacial self-assembly. This may also further promote the development of fullerene superstructures for advanced electrochemical applications.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work has been financially supported by Instrument & Equipment Open Funding of Nanjing University of Science and Technology, by the National Natural Science Foundation of China No. 21875108 and by the Fundamental Research Funds for the Central Universities (No. 30921013106).

Notes and references

- M. R. Benzigar, S. Joseph, H. Ilbeygi, D. H. Park, S. Sarkar, G. Chandra, S. Umopathy, S. Srinivasan, S. N. Talapaneni and A. Vinu, *Angew. Chem., Int. Ed.*, 2020, **57**, 569–573.
- T. Xu, W. Shen, W. Huang and X. Lu, *Mater. Today Nano*, 2020, **11**, 100081.
- L. K. Shrestha, Q. Ji, T. Mori, K. Miyazawa, Y. Yamauchi, J. P. Hill and K. Ariga, *Chem. – Asian. J.*, 2013, **8**, 1662–1679.
- F. Lu, E. A. Neal and T. Nakanishi, *Acc. Chem. Res.*, 2019, **52**, 1834–1843.
- R. G. Shrestha, L. K. Shrestha, M. Abe and K. Ariga, *J. Nanosci. Nanotechnol.*, 2015, **15**, 2394–2399.
- Q. Tang, P. Bairy, R. G. Shrestha, J. P. Hill, K. Ariga, H. Zeng, Q. Ji and L. K. Shrestha, *ACS Appl. Mater. Interfaces*, 2017, **9**, 44458–44465.
- Q. Tang, S. Maji, B. Jiang, J. Sun, W. Zhao, J. P. Hill, K. Ariga, H. Fuchs, Q. Ji and L. K. Shrestha, *ACS Nano*, 2019, **13**, 14005–14012.
- Q. Tang, S. Zhang, X. Liu, M. Sumita, S. Ishihara, H. Fuchs, Q. Ji, L. K. Shrestha and K. Ariga, *Phys. Chem. Chem. Phys.*, 2017, **19**, 29099–29105.
- T. Anusha, K. S. Bhavani, J. S. Kumar and P. K. Brahman, *Diamond Relat. Mater.*, 2020, **104**, 107761.
- P. Bairy, T. Tsuruoka, S. Acharya, Q. Ji, J. P. Hill, K. Ariga, Y. Yamauchi and L. K. Shrestha, *Mater. Horiz.*, 2018, **5**, 285–290.



- 11 L. K. Shrestha, R. G. Shrestha, Y. Yamauchi, J. P. Hill, T. Nishimura, K. Miyazawa, T. Kawai, S. Okada, K. Wakabayashi and K. Ariga, *Angew. Chem., Int. Ed.*, 2015, **127**, 965–969.
- 12 P. Bairi, R. G. Shrestha, J. P. Hill, T. Nishimura, K. Ariga and L. K. Shrestha, *J. Mater. Chem. A*, 2016, **4**, 13899–13906.
- 13 T. Wakahara, P. D'Angelo, K. Miyazawa, Y. Nemoto, O. Ito, N. Tanigaki, D. D. Bradley and T. D. Anthopoulos, *J. Am. Chem. Soc.*, 2012, **134**, 7204–7206.
- 14 T. Wakahara, M. Sathish, K. Miyazawa, C. Hu, Y. Tateyama, Y. Nemoto, T. Sasaki and O. Ito, *J. Am. Chem. Soc.*, 2009, **131**, 9940–9944.
- 15 S. Saha, P. Samanta, N. C. Murmu and T. Kuila, *J. Energy Storage*, 2018, **17**, 181–202.
- 16 Z. Yu, L. Tetard, L. Zhai and J. Thomas, *Energy Environ. Sci.*, 2015, **8**, 702–730.
- 17 M. A. Lebedeva, T. W. Chamberlain and A. N. Khlobystov, *Chem. Rev.*, 2015, **115**, 11301–11351.
- 18 A. L. Balch and K. Winkler, *Coord. Chem. Rev.*, 2021, **438**, 213623.
- 19 Z. Peng, Y. Hu, J. Wang, S. Liu, C. Li, Q. Jiang, J. Lu, X. Zeng, P. Peng and F. F. Li, *Adv. Energy Mater.*, 2019, **9**, 1802928.
- 20 G. Saianand, A. I. Gopalan, J. C. Lee, C. Sathish, K. Gopalakrishnan, G. E. Unni, D. Shanbhag, V. D. Dasireddy, J. Yi and S. Xi, *Small*, 2020, **16**, 1903937.
- 21 B. Jiang, Q. Tang, W. Zhao, J. Sun, R. An, T. Niu, H. Fuchs and Q. Ji, *CrystEngComm*, 2020, **22**, 6287–6294.
- 22 S. J. Uke, V. P. Akhare, D. R. Bambole, A. B. Bodade and G. N. Chaudhari, *Front. Mater.*, 2017, **4**, 21.
- 23 J. Minato and K. Miyazawa, *Carbon*, 2005, **43**, 2837–2841.
- 24 D. V. Konarev, S. S. Khasanov and R. N. Lyubovskaya, *Coord. Chem. Rev.*, 2014, **262**, 16–36.
- 25 D. M. Guldi, *Chem. Soc. Rev.*, 2002, **31**, 22–36.
- 26 G. Andrievsky, V. Klochkov, A. Bordyuh and G. Dovbeshko, *Chem. Phys. Lett.*, 2002, **364**, 8–17.
- 27 G. Zuo, X. Lu, Z. Xue, B. Lv, Y. Wang and J. Kang, *Synth. React. Inorg. Met.-Org. Chem.*, 2006, **36**, 589–594.
- 28 S. Bhattacharyya, B. Konkena, K. Jayaramulu, W. Schuhmann and T. K. Maji, *J. Mater. Chem. A*, 2017, **5**, 13573–13580.
- 29 C. Liu, G. Bai, X. Tong, Y. Wang, B. Lv, N. Yang and X.-Y. Guo, *Electrochem. Commun.*, 2019, **98**, 87–91.
- 30 L. Fu, Y. Chen, S. Zhao, Z. Liu and R. Zhu, *RSC Adv.*, 2016, **6**, 19482–19491.
- 31 J. Sheng, L. Wang, L. Deng, M. Zhang, H. He, K. Zeng, F. Tang and Y.-N. Liu, *ACS Appl. Mater. Interfaces*, 2018, **10**, 7191–7200.
- 32 Y. Wu, Q. Shi, Y. Li, Z. Lai, H. Yu, H. Wang and F. Peng, *J. Mater. Chem. A*, 2015, **3**, 1142–1151.
- 33 S.-H. Cho, K. R. Yoon, K. Shin, J.-W. Jung, C. Kim, J. Y. Cheong, D.-Y. Youn, S. W. Song, G. Henkelman and I.-D. Kim, *Chem. Mater.*, 2018, **30**, 5941–5950.
- 34 K. Niu, B. Yang, J. Cui, J. Jin, X. Fu, Q. Zhao and J. Zhang, *J. Power Sources*, 2013, **243**, 65–71.
- 35 J. M. Ziegelbauer, T. S. Olson, S. Pylypenko, F. Alamgir, C. Jaye, P. Atanassov and S. Mukerjee, *J. Phys. Chem. C*, 2008, **112**, 8839–8849.
- 36 Y. Jiang, Y. Lu, X. Wang, Y. Bao, W. Chen and L. Niu, *Nanoscale*, 2014, **6**, 15066–15072.
- 37 S. S. Park, S.-W. Chu, C. Xue, D. Zhao and C.-S. Ha, *J. Mater. Chem.*, 2011, **21**, 10801–10807.
- 38 E. J. Lee, L. Lee, M. A. Abbas and J. H. Bang, *Phys. Chem. Chem. Phys.*, 2017, **19**, 21140–21151.
- 39 E. Taer, A. Agustino, R. Farma, R. Taslim, Awitdrus, M. Paiszal, A. Ira, S. D. Yardi, Y. P. Sari, H. Yusra, S. Nurjanah, S. D. Hartati, Z. Aini and R. N. Setiadi, *J. Phys.: Conf. Ser.*, 2018, **1116**, 032040.
- 40 K. Ariga and L. K. Shrestha, *Mater. Adv.*, 2021, **2**, 582–597.
- 41 S. Wang, L. Li, Y. Shao, L. Zhang, Y. Li, Y. Wu and X. Hao, *Adv. Mater.*, 2019, **31**, 1806088.
- 42 D. Qiu, X. Ma, J. Zhang, B. Zhao and Z. Lin, *Chem. Phys. Lett.*, 2018, **710**, 188–192.

