

Cite this: *Mater. Adv.*, 2022,  
3, 4899

# Non-ammonolysis synthesis and characterisation of environmentally benign yellow pigments based on calcium–tantalum perovskite oxynitrides†

Takuya Sakata,<sup>ab</sup> Sohta Urushidani,<sup>a</sup> Naoki Tarutani,<sup>ib</sup> Kiyofumi Katagiri,<sup>ib</sup> Kei Inumaru,<sup>ib</sup> Kyohei Koyama,<sup>c</sup> Nozomu Iwata<sup>c</sup> and Yuji Masubuchi<sup>ib</sup>

Calcium–tantalum-based perovskite oxynitrides were synthesised as candidates for environmentally benign inorganic yellow pigments. The compounds were prepared via a urea-nitriding method, which does not involve a harmful ammonolysis process. Rapid single-phase synthesis was achieved under the optimum conditions, and only removable by-products were generated. Although the colours and bandgap energies of the obtained calcium–tantalum oxynitrides, CaTa(O,N)<sub>3</sub>, fell short of those of CaTaO<sub>2</sub>N synthesised by ammonolysis, they were made comparable by doping with La<sup>3+</sup>. Among the samples synthesised in this study, the most brilliant yellow hue was achieved with Ca<sub>0.8</sub>La<sub>0.2</sub>Ta(O,N)<sub>3</sub>, which has lightness (*L*\*) and yellowness (*b*\*) values comparable to those of conventional inorganic yellow pigments. In this synthetic method, harmful substances are eliminated both from the products and the synthesis process. In addition, the short heat-treatment duration enables the products to be obtained as fine powders suitable for pigment applications. Calcium–tantalum-based perovskite oxynitrides prepared by the strategy developed in this study have potential applications as environmentally benign yellow pigments.

Received 1st April 2022,  
Accepted 9th May 2022

DOI: 10.1039/d2ma00378c

rsc.li/materials-advances

## Introduction

Our world contains a variety of colours. Colour has psychological and aesthetic importance in daily life.<sup>1,2</sup> Inorganic pigments have been used in a wide variety of applications such as ceramics, glasses, plastics, inks and others.<sup>3</sup> However, inorganic pigments are not used only because of their colouristic properties. In a wide range of applications, their superior thermal and chemical stabilities, and resistance to climatic conditions give inorganic pigments advantages over their organic counterparts.<sup>3</sup> Though various colours exist in inorganic pigment, yellow is in particularly high demand because of its high visibility and use in many applications, *e.g.*, traffic signs, road markers, construction and others.<sup>4–6</sup> Chromium

yellow (PbCrO<sub>4</sub>),<sup>7</sup> cadmium yellow (CdS·ZnS),<sup>8</sup> and nickel–antimony–titanium yellow (NiO·Sb<sub>2</sub>O<sub>3</sub>·TiO<sub>2</sub>)<sup>9</sup> have been popularly employed as inorganic yellow pigments for such applications. However, there is growing concern that the toxic elements (Pb, Cr, Cd and Sb) in these pigments critically affect human health as well as the environment.<sup>10–13</sup> Recently, the Institute for Health Metrics and Evaluation estimated that in 2019, Pb exposure accounted for 0.90 million deaths and 21.7 million years lost of healthy life (disability-adjusted life years) worldwide owing to long-term health effects.<sup>14</sup> This situation has led to governmental authorities strictly limiting the use of inorganic yellow pigments that contain hazardous elements. The development of alternatives that are applicable as environmentally-friendly yellow pigments is therefore strongly desired, and considerable efforts have been devoted to developing such alternative materials.<sup>15–24</sup> For example, praseodymium yellow (ZrSiO<sub>4</sub>:Pr)<sup>21,22</sup> and bismuth vanadate (BiVO<sub>4</sub>)<sup>23,24</sup> have been developed as metal-oxide-based yellow pigments. However, the preparation of ZrSiO<sub>4</sub>:Pr is time consuming and its particles are poorly dispersible, which limits its use in paints and inks. Among several potential candidates, metal oxynitrides are also drawing much attentions as alternatives because they exhibit brilliant colours but do not contain toxic elements.<sup>25,26</sup> Jansen and Letschert developed pigments based on CaTaO<sub>2</sub>N–LaTaON<sub>2</sub> solid solutions, which are able to

<sup>a</sup> Graduate School of Advanced Science and Engineering, Hiroshima University, 1-4-1 Kagamiyama, Higashi-Hiroshima 739-8527, Japan.  
E-mail: kktgr@hiroshima-u.ac.jp

<sup>b</sup> Western Region Industrial Research Center, Hiroshima Prefectural Technology Research Institute, 2-10-1 Aga-Minami, Kure 737-0004, Japan

<sup>c</sup> Graduate School of Chemical Sciences and Engineering, Hokkaido University, N13W8, Kita-ku, Sapporo 060-8628, Japan

<sup>d</sup> Division of Applied Chemistry, Faculty of Engineering, Hokkaido University, N13 W8, Kita-ku, Sapporo 060-8628, Japan

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d2ma00378c>



substitute conventional inorganic yellow-red pigments.<sup>25</sup> Kim also reported that the preparation of  $\text{CaTaO}_2\text{N}$  exhibited a chromatic colour of yellow, close to that of the commercial cadmium yellow pigment.<sup>26</sup> However, there are several obstacles in the preparation of metal oxynitrides, and these need to be resolved. Ammonolysis, which involves the use of harmful  $\text{NH}_3$  gas for long time at high temperature, is usually required for synthesis of metal oxynitride.<sup>27–29</sup> The single-phase synthesis of  $\text{CaTaO}_2\text{N}$  by ammonolysis usually requires heat treatment at temperatures above 1000 °C for several days.<sup>30</sup> Even though the final products are environmentally benign, their use is unfavourable if materials that affect the environment and/or human health are used in their preparation. Prolonged heat treatment at high temperatures is also undesirable because it consumes a large amount of energy. There is also a cost issue because of the continuous flow of expensive  $\text{NH}_3$  gas for a long period of time. In addition, the products grow into large crystalline grains, which are unsuitable for applications as pigments where a fine morphology is desired. In the context of these circumstances, several approaches for eliminating the use of toxic  $\text{NH}_3$  gas by using solid nitriding agents for metal oxynitride synthesis have been proposed.<sup>31–38</sup> We recently developed a urea-nitriding method for synthesizing metal oxynitrides, namely  $\text{GaN}:\text{ZnO}$  and  $\text{LaTiO}_2\text{N}$ , and the nitriding mechanisms were elucidated.<sup>39,40</sup> The shorter heat-treatment duration compared with those in processes that involve ammonolysis achieved a reduction in energy consumption and enabled the formation of finer sample powders. More recently, the strontium–tantalum oxynitride,  $\text{SrTaO}_2\text{N}$ , and its solid solutions with  $\text{Sr}_{1.4}\text{Ta}_{0.6}\text{O}_{2.9}$  have also been prepared by the urea-nitriding method using  $\text{SrCO}_3$  and  $\text{Ta}_2\text{O}_5$  gel as precursors.<sup>41</sup> The oxygen and nitrogen contents in the solid solutions can be controlled by changing the quantity of urea in the precursor mixture. The solid solutions exhibited various chromatic colours, suggesting their potential applications as secure inorganic pigments. However, tantalum-based oxynitrides that exhibit a brilliant yellow colour comparable to those of  $\text{PbCrO}_4$ ,  $\text{CdS}$  and  $\text{ZrSiO}_4:\text{Pr}$  have not been obtained.

The main aims of the current work were the ammonolysis-free synthesis and characterisation of the calcium–tantalum perovskite oxynitride,  $\text{CaTa}(\text{O},\text{N})_3$ , which has potential applications as an environmentally benign yellow pigment. There have been several reports on the synthesis of  $\text{CaTa}(\text{O},\text{N})_3$  through a non-ammonolysis process, *e.g.*, calcination of  $\text{CaCO}_3$  and  $\text{TaON}$ ,<sup>31</sup> and nitridation of  $\text{Ca}_2\text{Ta}_2\text{O}_7$  with  $\text{C}_3\text{N}_4$ .<sup>36</sup> However, because of the presence of raw material residues and the generation of by-products, single-phase synthesis of calcium–tantalum perovskite oxynitrides has not been achieved. In addition, a detailed colour evaluation of the products was not carried out in either of these reports. In this paper, we determined the precursor composition needed to obtain  $\text{CaTa}(\text{O},\text{N})_3$  in a single phase by using two different Ca sources, *i.e.*, calcium carbonate ( $\text{CaCO}_3$ ) and calcium hydroxide ( $\text{Ca}(\text{OH})_2$ ). The optical absorption properties of metal oxynitrides depend on their band structures. When both  $\text{O}^{2-}$  and  $\text{N}^{3-}$  ions occupy the anion sites of the perovskite structure, the O 2p and N 2p states are

hybridised, and the bandgap energies of the metal oxynitrides are lower than those of the corresponding metal oxides.<sup>28,29,42</sup> The ratio of O to N therefore critically affects the metal oxynitride colour. For example, in the case of  $\text{CaTaO}_2\text{N}$ , the synthesised products often lack N, and the molar ratio of oxygen to nitrogen is not always 2 : 1.<sup>43</sup> This is why the chemical formula of the calcium–tantalum perovskite oxynitride is represented by  $\text{CaTa}(\text{O},\text{N})_3$  in this paper. In addition to the colour coordinates, the bandgap energies and the O/N ratios of the obtained products were therefore evaluated in detail. To achieve the synthesis of calcium–tantalum-based oxynitrides with colours equivalent to those of commercially available inorganic yellow pigments such as  $\text{BiVO}_4$  and  $\text{ZrSiO}_4:\text{Pr}$ , partial substitution of  $\text{La}^{3+}$  at  $\text{Ca}^{2+}$  sites of  $\text{CaTa}(\text{O},\text{N})_3$  for adjustment of the bandgap energy, *i.e.*, the O/N ratio, was also investigated.

## Experimental procedure

Details of the materials employed in this study are provided in the ESI.† As calcium sources,  $\text{CaCO}_3$  and  $\text{Ca}(\text{OH})_2$  were selected for the preparation of  $\text{CaTa}(\text{O},\text{N})_3$  on the basis of cost, safety, and ease of handling. For the preparation of La-doped  $\text{CaTa}(\text{O},\text{N})_3$ , lanthanum hydroxide ( $\text{La}(\text{OH})_3$ ) was used as the lanthanum source. Tantalum oxide ( $\text{Ta}_2\text{O}_5$ ) gel, which was synthesised *via* the sol–gel method, was used as the tantalum source for preparation of calcium–tantalum-based oxynitrides. Tantalum(v) ethoxide ( $\text{Ta}(\text{OC}_2\text{H}_5)_5$ ; 1 mmol) was added to ethanol (EtOH) (1 mL). Then, deionised (DI) water (5 mL) was added to the EtOH solution and the mixture was stirred vigorously to achieve hydrolysis and polycondensation of  $\text{Ta}(\text{OC}_2\text{H}_5)_5$ . The mixture was centrifuged and the  $\text{Ta}_2\text{O}_5$  gel was obtained by drying the separated product overnight in an oven at 50 °C. The  $\text{Ta}_2\text{O}_5$  gel, Ca source ( $\text{CaCO}_3$  or  $\text{Ca}(\text{OH})_2$ ) and urea ( $\text{CO}(\text{NH}_2)_2$ ) were put in an agate mortar and were mixed well with a pestle for 10 min under dry conditions. The molar ratio of Ca (in the Ca source)/Ta (in the  $\text{Ta}_2\text{O}_5$  gel)/urea in the precursor mixture was varied to obtain perovskite oxynitrides without any impurity phases. The synthesis of  $\text{CaTa}(\text{O},\text{N})_3$  was carried out in a horizontal quartz furnace tube under a flow of  $\text{N}_2$  gas (purity 99.99%) at 0.3 L  $\text{min}^{-1}$ . An alumina boat loaded with the precursor mixture was placed at the centre of the furnace. The heating rate was 15 °C  $\text{min}^{-1}$ . The temperature of heat-treatment was 950 °C. The heat-treatment duration was fixed at 2 h.

X-Ray diffraction (XRD) measurement, scanning electron microscopy (SEM), ultraviolet-visible (UV-vis) spectroscopy, Fourier-transform infrared (FT-IR) spectroscopy, chromatic property determination, oxygen/nitrogen combustion analysis and X-ray fluorescence (XRF) spectroscopy were used to characterise the obtained products. Details of the apparatus and methods used in this study are described in the ESI.†

## Results and discussion

In the previous report on the preparation of  $\text{SrTaO}_2\text{N}$  from a  $\text{Ta}_2\text{O}_5$  gel and urea, a single-phase synthesis was achieved by using  $\text{SrCO}_3$  as the Sr source.<sup>41</sup> In this study, we thus first



examined the use of  $\text{CaCO}_3$  as the Ca source in the preparation of  $\text{CaTa}(\text{O},\text{N})_3$ . Information obtained by characterisation of products synthesised with various molar ratios of urea can be used to identify the optimum conditions for the formation of perovskite oxynitrides.<sup>41</sup> We therefore varied the urea content relative to those of  $\text{CaCO}_3$  and the  $\text{Ta}_2\text{O}_5$  gel in the precursor mixture. The Ca and Ta molar ratio ( $x:y$ ) in the precursor was fixed at 1:1 and the molar ratio of urea ( $z$ ) was changed from 3 to 5. The XRD patterns of the products prepared from  $\text{CaCO}_3$ ,  $\text{Ta}_2\text{O}_5$ , and urea ( $x:y:z = 1:1:3$ ,  $1:1:4$  and  $1:1:5$ ) are shown in Fig. 1. Photographs of the products are provided in the ESI† (Fig. S1). At the lowest urea content ( $x:y:z = 1:1:3$ ), diffraction peaks assignable to the perovskite phase appeared, but other phases, such as  $\text{Ca}_2\text{Ta}_2\text{O}_7$ ,  $\text{Ta}_3\text{N}_5$  and  $\text{TaON}$ , were also detected. As shown in Fig. S1a (ESI†), the colour of this product was pale beige, far from the yellow colour of  $\text{CaTaO}_2\text{N}$ . In the cases of higher amounts of urea ( $x:y:z = 1:1:4$  and  $1:1:5$ ), sharp and strong diffraction peaks corresponding to the perovskite phase were observed. The positions of these peaks correspond well to those of  $\text{CaTaO}_2\text{N}$  (orthorhombic perovskite, space group:  $Pnma$ ).<sup>44</sup> Small amounts of tantalum nitrides ( $\text{Ta}_3\text{N}_5$  and  $\text{TaN}$ ) were detected as impurities. The grey colour of the product obtained with  $x:y:z = 1:1:5$  (Fig. S1c, ESI†) was probably caused by the presence of  $\text{TaN}$ . These results indicate that  $z = 4$  or higher is appropriate for obtaining  $\text{CaTaO}_2\text{N}$  as the main product. However, post-treatment to remove the tantalum nitride by-products that dull the colour tone of the products is difficult. To suppress the generation of tantalum nitrides, we investigated the synthesis of  $\text{CaTa}(\text{O},\text{N})_3$  at various ratios of Ca to Ta. The calcium-based by-products can potentially be removed by post-treatment, therefore the molar ratio of Ca to Ta was increased. The Ta and urea molar ratio ( $y:z$ ) in the

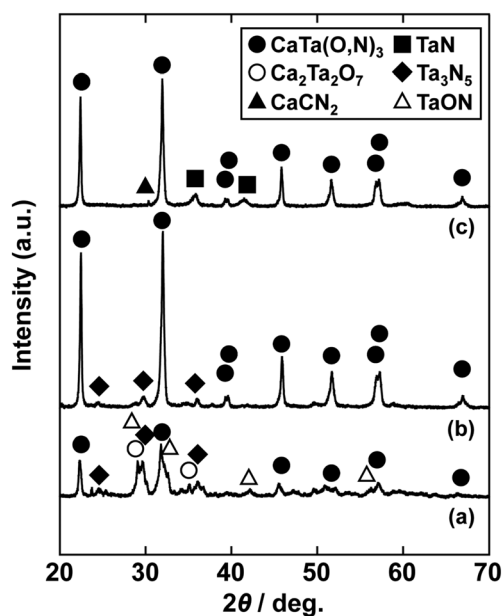


Fig. 1 XRD patterns of products prepared from  $\text{CaCO}_3$ ,  $\text{Ta}_2\text{O}_5$  gel and urea after heat-treatment at  $950\text{ }^\circ\text{C}$  for 2 h. Molar ratios of Ca/Ta/urea in precursors were (a) 1:1:3, (b) 1:1:4 and (c) 1:1:5.

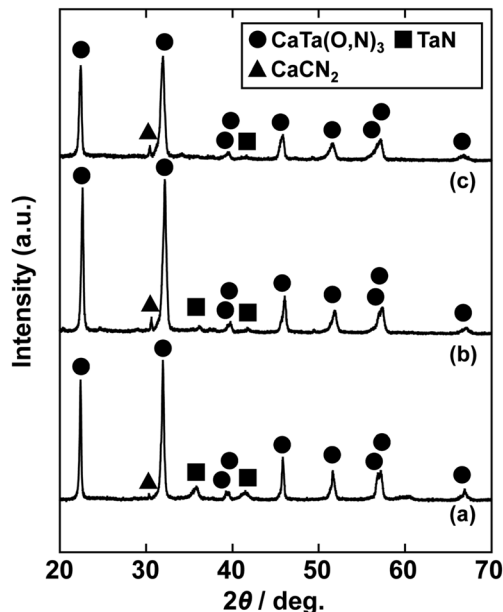


Fig. 2 XRD patterns of products prepared from  $\text{CaCO}_3$ ,  $\text{Ta}_2\text{O}_5$  gel and urea after heat treatment at  $950\text{ }^\circ\text{C}$  for 2 h. Molar ratios of Ca/Ta/urea in precursors were (a) 1:1:5, (b) 1.5:1:5 and (c) 2:1:5.

precursor mixture was fixed at 1:5 and the molar ratio of Ca ( $x$ ) was changed from 1 to 2. The XRD patterns of the products prepared from  $\text{CaCO}_3$ ,  $\text{Ta}_2\text{O}_5$  and urea ( $x:y:z = 1:1:5$ ,  $1.5:1:5$  and  $2:1:5$ ) are shown in Fig. 2. Photographs of the products are shown in the ESI† (Fig. S2). When the amount of  $\text{CaCO}_3$  was increased by a factor of 1.5 (Fig. 2(b)), the main product was  $\text{CaTa}(\text{O},\text{N})_3$ , and  $\text{CaCN}_2$  was generated as a new by-product. It should be noted that the generation of  $\text{CaCN}_2$  was not observed under any conditions in a previous study of the preparation of  $\text{CaTa}(\text{O},\text{N})_3$  by using  $\text{C}_3\text{N}_4$ .<sup>36</sup> Both are methods for the preparation of oxynitrides by using solid nitriding agents, but the nitridation processes with  $\text{C}_3\text{N}_4$  and urea presumably differ. The colour of this product was pale yellow (Fig. S2b, ESI†). This indicates that the formation of  $\text{TaN}$  was suppressed, but weak  $\text{TaN}$  peaks were still present in the XRD pattern. However, when the amount of  $\text{CaCO}_3$  was doubled, the diffraction peaks of  $\text{TaN}$  almost disappeared (Fig. 2(c)). This shows that increasing the amount of  $\text{CaCO}_3$  effectively suppressed the formation of  $\text{TaN}$  in the product.  $\text{CaCN}_2$  decomposes to  $\text{NH}_3$  and  $\text{CaCO}_3$  when reacted with water, and  $\text{CaCO}_3$  is soluble in acidic solutions. The  $\text{CaCN}_2$  by-product can therefore be removed by treatment with water and hydrochloric acid ( $\text{HCl aq.}$ ) The FT-IR spectra and XRD patterns of samples prepared from  $\text{CaCO}_3$ ,  $\text{Ta}_2\text{O}_5$  and urea before and after washing with DI water and  $\text{HCl aq.}$  are provided in Fig. S3 and S4, respectively, in the ESI.† As depicted in Fig. S3, ESI† the peak attributed to the stretching vibration of carbodiimide ( $\text{N}=\text{C}=\text{N}$ ) in  $\text{CaCN}_2$  appeared at approximately  $2000\text{--}2200\text{ cm}^{-1}$  in the FT-IR spectrum of the product before washing,<sup>45</sup> but this peak was not present in the spectrum of the product after washing. In the XRD pattern of the products after washing (Fig. S4, ESI†), the peaks assignable to  $\text{CaCN}_2$  disappeared and only peaks corresponding to  $\text{CaTa}(\text{O},\text{N})_3$  were



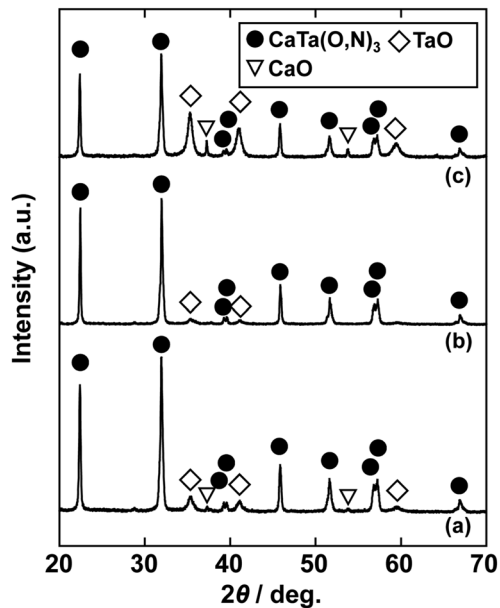


Fig. 3 XRD patterns of products prepared from  $\text{Ca(OH)}_2$ ,  $\text{Ta}_2\text{O}_5$  gel and urea after heat treatment at  $950^\circ\text{C}$  for 2 h. Molar ratios of Ca/Ta/urea in precursors were (a) 1:1:3, (b) 1:1:4 and (c) 1:1:5.

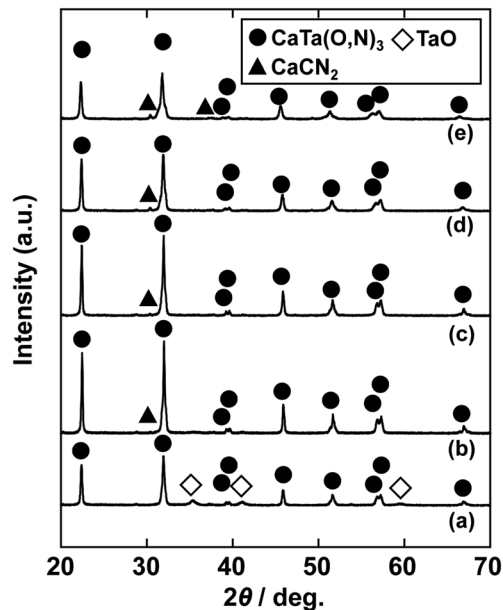


Fig. 4 XRD patterns of products prepared from  $\text{Ca(OH)}_2$ ,  $\text{Ta}_2\text{O}_5$  gel and urea after heat treatment at  $950^\circ\text{C}$  for 2 h. Molar ratios of Ca/Ta/urea in precursors were (a) 1:1:3, (b) 1.15:1:3, (c) 1.3:1:3, (d) 1.5:1:3 and (e) 2:1:3.

observed. These results show that  $\text{CaTa(O,N)}_3$  could be obtained almost as a single phase by sequential washing with DI water and HCl aq. Next,  $\text{Ca(OH)}_2$  was examined as a Ca source for the preparation of  $\text{CaTa(O,N)}_3$ . Similarly to the case for  $\text{CaCO}_3$ , the effects of varying the amount of urea relative to those of  $\text{Ca(OH)}_2$  and  $\text{Ta}_2\text{O}_5$  gel in the precursor mixture were investigated. The Ca and Ta molar ratio ( $x:y$ ) in the precursor mixture was fixed at 1:1 and the urea molar ratio ( $z$ ) was varied from 3 to 5. Fig. 3 depicts the XRD patterns of the products prepared from  $\text{Ca(OH)}_2$ ,  $\text{Ta}_2\text{O}_5$  and urea ( $x:y:z = 1:1:3$ ,  $1:1:4$  and  $1:1:5$ ). Photographs of the products are provided in the ESI† (Fig. S5). For all precursor compositions, a perovskite phase, which corresponded to  $\text{CaTa(O,N)}_3$ , was formed as the main phase of the obtained products. The generated by-products differed from those generated with the products prepared by using  $\text{CaCO}_3$  as the Ca source. In the case of  $\text{CaCO}_3$ , tantalum nitrides, *i.e.*,  $\text{TaN}$  and  $\text{Ta}_3\text{N}_5$ , were formed as by-products, but in the case of  $\text{Ca(OH)}_2$ , the by-products were metal oxides, *i.e.*, TaO and CaO. In addition, the lowest urea amount,  $z = 3$ , was enough to achieve nitridation to  $\text{CaTa(O,N)}_3$  when  $\text{Ca(OH)}_2$  was used as the Ca source, but  $z = 5$  was required when  $\text{CaCO}_3$  was used. As in the case of  $\text{CaCO}_3$ , the effect of increasing the molar ratio of Ca to Ta was investigated. The Ta to urea molar ratio ( $y:z$ ) in the precursor mixture was fixed at 1:3 and the Ca molar ratio ( $x$ ) was varied from 1 to 2. Fig. 4 shows XRD patterns of the products prepared from  $\text{Ca(OH)}_2$ ,  $\text{Ta}_2\text{O}_5$  and urea ( $x:y:z = 1:1:3$ ,  $1.15:1:3$ ,  $1.3:1:3$ ,  $1.5:1:3$  and  $2:1:3$ ). Photographs of the products are given in the ESI† (Fig. S6). When the Ca ratio ( $x$ ) was 1.15 or higher, the impurity phases of TaO and CaO disappeared or became negligible. Similarly to the case for  $\text{CaCO}_3$ ,  $\text{CaCN}_2$  was formed as a by-product when the ratio of Ca in the precursor was increased. As

shown in Fig. S6, ESI† the colour of the sample was grey when the Ca ratio,  $x$ , was 1, but the blackness decreased with increasing value of  $x$ , and the colour of the sample with  $x = 1.5$  was bright yellow. However, the yellowish colour faded and the sample became whitish beige at  $x = 2$ . In the XRD pattern of this sample, all the peaks attributed to  $\text{CaTa(O,N)}_3$  broadened, which suggests decreased crystallinity. Molar ratios of Ca/Ta/urea = 1.5:1:3 are therefore considered to be the optimum composition. The  $\text{CaCN}_2$  by-product can be removed by washing with DI water and HCl aq., as described above, therefore  $\text{CaTa(O,N)}_3$  can be obtained as a single phase by washing. The high-temperature reaction time needed to synthesise  $\text{CaTaO}_2\text{N}$  by ammonolysis of  $\text{Ca}_2\text{Ta}_2\text{O}_7$  is longer than those needed to synthesise other tantalum-based perovskite oxynitrides, *e.g.*,  $\text{BaTaO}_2\text{N}$ .<sup>30</sup> For example, it has been reported that  $\text{Ca}_2\text{Ta}_2\text{O}_7$  remains after heat treatment under a flow of  $\text{NH}_3$  at  $1100^\circ\text{C}$  for 240 h. Sun *et al.* achieved the synthesis of  $\text{CaTaO}_2\text{N}$  from the reaction of  $\text{CaCO}_3$  and TaON by heat treatment for 3 h, but  $\text{Ca}_2\text{Ta}_2\text{O}_7$  remained, and  $\text{Ta}_4\text{N}_5$  and TaON were formed as impurities.<sup>31</sup> Masubuchi and co-workers recently reported an ammonia-free synthesis of  $\text{CaTa(O,N)}_3$  *via* the reaction of  $\text{Ca}_2\text{Ta}_2\text{O}_7$  and  $\text{C}_3\text{N}_4$ .<sup>36</sup> The heat-treatment time was decreased to 6 h, but a certain amount of  $\text{Ca}_2\text{Ta}_2\text{O}_7$  remained and a single-phase  $\text{CaTa(O,N)}_3$  was not obtained. In contrast, in the present method, optimisation of the precursor composition suppresses formation of by-products that are difficult to remove, and only soluble  $\text{CaCN}_2$  is produced as a by-product. It is therefore possible to obtain a single phase of  $\text{CaTaO}_2\text{N}$  with a short calcination time and by using a simple washing process. XRD pattern of the products prepared from either  $\text{CaCO}_3$  or  $\text{Ca(OH)}_2$  after washing with DI water and HCl aq. are given in the ESI†



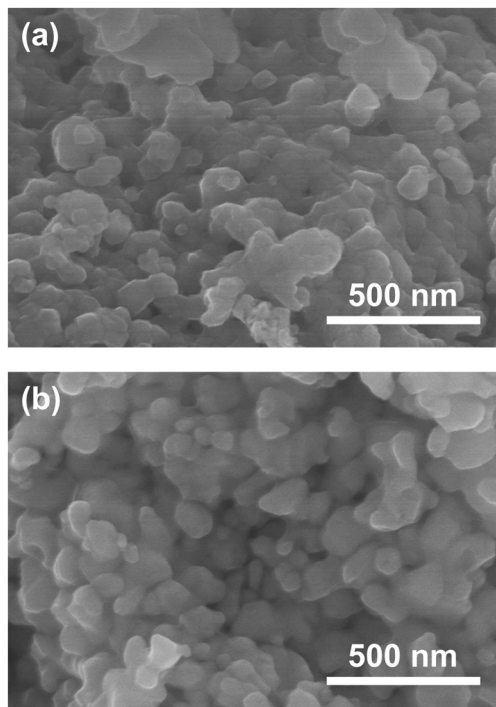


Fig. 5 SEM images of  $\text{CaTa}(\text{O},\text{N})_3$  prepared from Ca source (a)  $\text{CaCO}_3$ , (b)  $\text{Ca}(\text{OH})_2$ ,  $\text{Ta}_2\text{O}_5$  gel and urea after heat treatment at  $950\text{ }^\circ\text{C}$  for 2 h. Molar ratios of Ca/Ta/urea in precursors were (a) 2 : 1 : 5 and (b) 1.5 : 1 : 3.

(Fig. S7). The morphologies of  $\text{CaTa}(\text{O},\text{N})_3$  were observed using SEM (Fig. 5). The average particle sizes of the products were *ca.* 100 nm, which is smaller than those reported in the literature for  $\text{CaTaO}_2\text{N}$  prepared by ammonolysis. In addition, the crystalline sizes of the corresponding products, which were estimated from the XRD data by using the Scherrer equation, were 31 nm (Ca source:  $\text{CaCO}_3$ ) and 28 nm [Ca source:  $\text{Ca}(\text{OH})_2$ ]. This suggests that crystal growth of  $\text{CaTa}(\text{O},\text{N})_3$  during the urea-nitriding process was effectively suppressed. The grain and crystalline sizes are smaller because of the lower temperature and shorter heat-treatment duration in the urea-nitriding process.

The optical properties of the  $\text{CaTa}(\text{O},\text{N})_3$  samples prepared from both  $\text{CaCO}_3$  and  $\text{Ca}(\text{OH})_2$  were evaluated. Photographs and UV-vis diffuse reflectance spectra (DRS) of the products prepared from  $\text{CaCO}_3$  and  $\text{Ca}(\text{OH})_2$  are shown in Fig. 6 and 7, respectively. All the samples were washed with DI water, and then with HCl aq. It has been reported that the sample crystallinity affects the absorption-edge steepness of the DRS.<sup>46</sup> The absorption-edge profiles of the products obtained using  $\text{Ca}(\text{OH})_2$  were much steeper than those of the products prepared from  $\text{CaCO}_3$ . This is primarily because of the higher crystallinity of the products obtained from  $\text{Ca}(\text{OH})_2$ . The peaks in the XRD patterns of the products prepared using  $\text{Ca}(\text{OH})_2$  were also much sharper than those in the XRD patterns of the products prepared using  $\text{CaCO}_3$  (Fig. S7, ESI<sup>†</sup>). These results suggest that  $\text{CaTa}(\text{O},\text{N})_3$  prepared from  $\text{Ca}(\text{OH})_2$  has a higher crystallinity than that prepared from  $\text{CaCO}_3$ . The thermal decomposition temperature of  $\text{CaCO}_3$  is  $825\text{ }^\circ\text{C}$ , which means

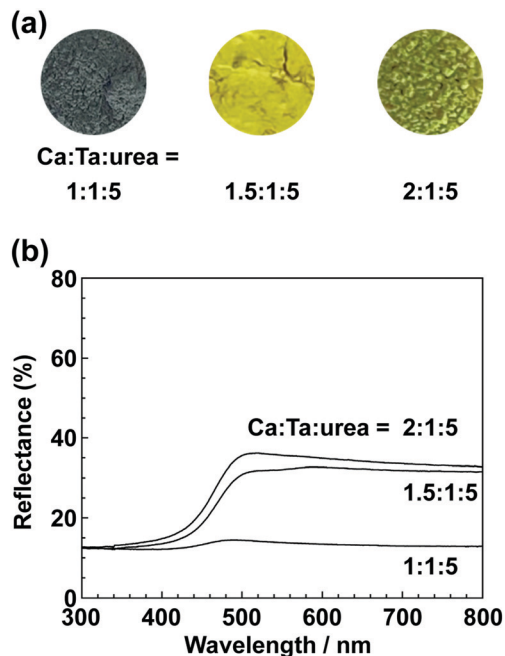


Fig. 6 (a) Photographs and (b) UV-vis DRS of  $\text{CaTa}(\text{O},\text{N})_3$  prepared from  $\text{CaCO}_3$ ,  $\text{Ta}_2\text{O}_5$  gel, and urea after heat treatment at  $950\text{ }^\circ\text{C}$  for 2 h. Molar ratios of Ca/Ta/urea in precursors were 1 : 1 : 5, 1.5 : 1 : 5 and 2 : 1 : 5.

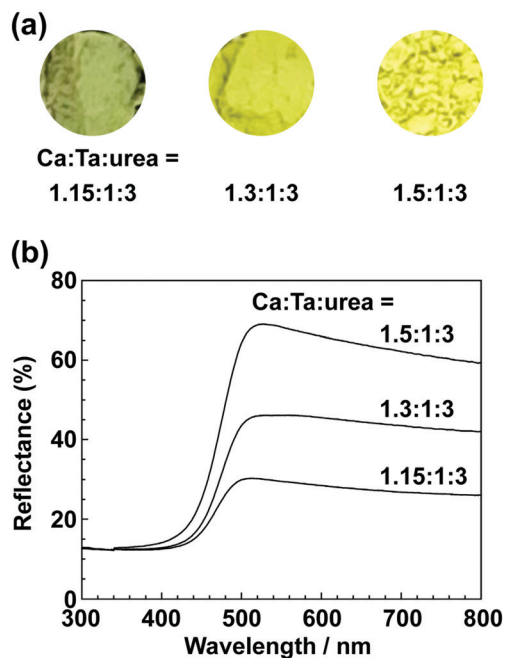


Fig. 7 (a) Photographs and (b) UV-vis DRS of  $\text{CaTa}(\text{O},\text{N})_3$  prepared from  $\text{Ca}(\text{OH})_2$ ,  $\text{Ta}_2\text{O}_5$  gel, and urea after heat treatment at  $950\text{ }^\circ\text{C}$  for 2 h. Molar ratios of Ca/Ta/urea in precursors were 1.15 : 1 : 3, 1.3 : 1 : 3 and 1.5 : 1 : 3.

that  $\text{CaCO}_3$  is stable even at high calcination temperatures. The thermal decomposition temperature of  $\text{Ca}(\text{OH})_2$  is  $580\text{ }^\circ\text{C}$ , which is much lower than that of  $\text{CaCO}_3$ . The reaction of  $\text{Ca}(\text{OH})_2$  with urea and its derivatives therefore starts at a lower



temperature during calcination in the synthesis of  $\text{CaTa}(\text{O},\text{N})_3$ . The difference between the thermal decomposition temperatures of  $\text{CaCO}_3$  and  $\text{Ca}(\text{OH})_2$  is therefore an important factor in the difference between the crystallinities of  $\text{CaTa}(\text{O},\text{N})_3$  obtained from these Ca sources.

All the spectra exhibited strong absorption of blue light at wavelengths below 500 nm; blue is a complementary colour to yellow. This absorption originates from electronic transitions between the valence band formed by hybridisation of O 2p/N 2p orbitals and the conduction band consisting of the 5d orbital of Ta.<sup>29,30</sup> Regardless of the Ca source, an increase in the proportion of Ca in the precursor resulted in an increase in the maximum reflectance intensity of the products in the long-wavelength range 500–800 nm. As mentioned above, the product prepared using  $\text{CaCO}_3$  at a lower Ca ratio was contaminated with TaN, and this caused a grey colour. However, even for the products in which formation of TaN as a by-product was sufficiently suppressed, their reflectance was lower and their colour was a duller yellow than those reported in the literature. This is presumably because of reduction of  $\text{Ta}^{5+}$  in  $\text{CaTa}(\text{O},\text{N})_3$  to  $\text{Ta}^{4+}$  by urea, which also acts as a reducing agent.<sup>40,41</sup> In other words, the dull colour arose from a tantalum species, which was reduced during the urea-nitriding process. The Commission Internationale de l'Éclairage (CIE)  $L^*a^*b^*Ch^\circ$  colour coordinate parameters of  $\text{CaTa}(\text{O},\text{N})_3$  prepared using  $\text{CaCO}_3$  (Ca:Ta:urea = 2:1:5) and  $\text{Ca}(\text{OH})_2$  (Ca:Ta:urea = 1.5:1:3) are summarised in Table 1. The bandgap energy ( $E_g$ ) values, which were estimated from UV-vis DRS, are also given in Table 1. The hue angles ( $h^\circ$ ) of the products were 104° and 110°, which implies that the colours were in the boundary region between yellow and green. Although the redness ( $a^*$ ) value was comparable to those of conventional yellow pigments (−7.90 for cadmium yellow and −3.28 for  $\text{ZrSiO}_4\text{:Pr}$ ), the lightness ( $L^*$ ), yellowness ( $b^*$ ) and chroma ( $C$ ) values of  $\text{CaTa}(\text{O},\text{N})_3$  prepared from  $\text{CaCO}_3$  were considerably lower than those of  $\text{CaTaO}_2\text{N}$  prepared by ammonolysis.<sup>26</sup> In the case of the product prepared from  $\text{Ca}(\text{OH})_2$ , the  $L^*$  value was close to that of  $\text{CaTaO}_2\text{N}$  prepared by ammonolysis, but the  $b^*$  and  $C$  values were still low. The estimated bandgap energies for the products prepared from  $\text{CaCO}_3$  and  $\text{Ca}(\text{OH})_2$  (2.57 and 2.59 eV, respectively) were larger than the reported value for  $\text{CaTaO}_2\text{N}$  prepared *via* ammonolysis (2.47 eV).<sup>47</sup> It is well known that the O/N ratio strongly affects the band structures of oxynitrides, *i.e.*, a lower nitrogen content leads to widening of the bandgap compared with those of oxynitrides with an ideal O/N ratio.<sup>25,47</sup> The

**Table 2** Oxygen and nitrogen contents (determined by combustion method) of  $\text{CaTa}(\text{O},\text{N})_3$  prepared from Ca source ( $\text{CaCO}_3$  or  $\text{Ca}(\text{OH})_2$ ),  $\text{Ta}_2\text{O}_5$  gel and urea after heat treatment at 950 °C for 2 h

Ca source	Molar ratios of Ca/Ta/urea in the precursors	O/N molar ratio in products (O + N = 3)	
		O	N
$\text{CaCO}_3$	2:1:5	2.54	0.46
$\text{Ca}(\text{OH})_2$	1.5:1:3	2.32	0.68

$\text{CaTa}(\text{O},\text{N})_3$  samples prepared using  $\text{CaCO}_3$  and  $\text{Ca}(\text{OH})_2$  were analysed by the O/N combustion method. The data in Table 2 show that the nitrogen contents of oxynitrides prepared by the urea-nitriding method were consistently lower than that of  $\text{CaTaO}_2\text{N}$  obtained through ammonolysis.

To achieve a colour equivalent to the ideal for  $\text{CaTaO}_2\text{N}$ , the lack of nitrogen in the perovskite structure needs to be compensated for. As mentioned above, increasing the amount of urea, *i.e.*, the nitrogen source in the precursor, is undesirable because it leads to increased formation of tantalum nitride by-products such as TaN. However, it is possible to control the O and N contents by changing the A site cation in the metal oxynitrides,  $\text{AB}(\text{O},\text{N})_3$ , in which  $\text{Ta}^{5+}$  occupies the B site.<sup>25,47</sup> For example, when divalent cations such as  $\text{Ca}^{2+}$  are used, the O:N molar ratio is ideally 2:1, as in  $\text{CaTaO}_2\text{N}$ , but when trivalent cations such as  $\text{La}^{3+}$  are used, the O:N molar ratio is 1:2 and the N content is greater, as in  $\text{LaTaO}_2\text{N}$ . In other words, it can be speculated that if a certain portion of the  $\text{Ca}^{2+}$  in  $\text{CaTaO}_2\text{N}$  is substituted by  $\text{La}^{3+}$ , the N ratio can be increased while maintaining the perovskite structure. Fig. 8 displays XRD patterns of the products obtained from La-doped calcium–tantalum oxynitrides, *i.e.*,  $\text{Ca}_{1-x}\text{La}_x\text{Ta}(\text{O},\text{N})_3$ , with various La contents ( $x = 0.00, 0.05, 0.10, 0.15$  and  $0.20$ ). The molar ratios of (Ca + La)/Ta/urea were 1.5:1:3. All the products crystallised with an almost single-phase perovskite structure without any impurity phases. This suggests that solid solutions of  $\text{CaTa}(\text{O},\text{N})_3$  and  $\text{LaTa}(\text{O},\text{N})_3$  are formed in the examined Ca/La composition range. When the doping amount of  $\text{La}^{3+}$  was further increased ( $x > 0.20$ ),  $\text{LaN}$  and  $\text{Ca}_2\text{LaTaO}_6$  were generated as impurity phases (Fig. S8 in the ESI†). In addition, the yellowness ( $b^*$ ) value of the products decreased in the colour evaluation. Therefore, a detailed investigation of  $\text{Ca}_{1-x}\text{La}_x\text{Ta}(\text{O},\text{N})_3$  in the range  $0 \leq x \leq 0.2$  was performed. Fig. 8 shows that all the diffraction peaks consecutively shifted towards lower angles with increasing  $\text{La}^{3+}$  uptake. This indicates

**Table 1** CIE  $L^*a^*b^*Ch^\circ$  colour coordinates and bandgap energies ( $E_g$ ) of  $\text{CaTa}(\text{O},\text{N})_3$  prepared from Ca source ( $\text{CaCO}_3$  or  $\text{Ca}(\text{OH})_2$ ),  $\text{Ta}_2\text{O}_5$  gel and urea after heat treatment at 950 °C for 2 h

Ca source	Molar ratios of Ca/Ta/urea in the precursors	Colour coordinates					$E_g/\text{eV}$
		$L^*$	$a^*$	$b^*$	$C$	$h^\circ$	
$\text{CaCO}_3$	2:1:5	57.0	−5.89	+24.1	24.9	104	2.57
$\text{Ca}(\text{OH})_2$	1.5:1:3	82.3	−15.4	+41.8	44.5	110	2.59
Reference data for $\text{CaTaO}_2\text{N}$ prepared by ammonolysis <sup>26</sup>		75.5	−5.23 <sup>#</sup>	+61.7 <sup>#</sup>	62.0	94.8	—

<sup>#</sup> The values of  $a^*$  and  $b^*$  for  $\text{CaTaO}_2\text{N}$  prepared by ammonolysis were extracted from the positions in the plots in a figure in the literature by using ImageJ software.



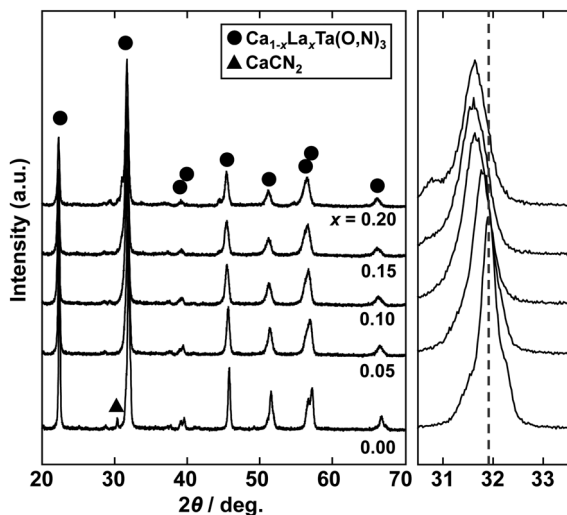


Fig. 8 XRD patterns of  $\text{Ca}_{1-x}\text{La}_x\text{Ta}(\text{O},\text{N})_3$  ( $x = 0.00, 0.05, 0.10, 0.15$  and  $0.20$ ) prepared from  $\text{Ca}(\text{OH})_2$ ,  $\text{La}(\text{OH})_3$ ,  $\text{Ta}_2\text{O}_5$  gel and urea after heat treatment at  $950\text{ }^\circ\text{C}$  for 2 h. Enlargements of main reflections at approximately  $32^\circ$  are shown on the right; dashed line provides a guide for the eye.

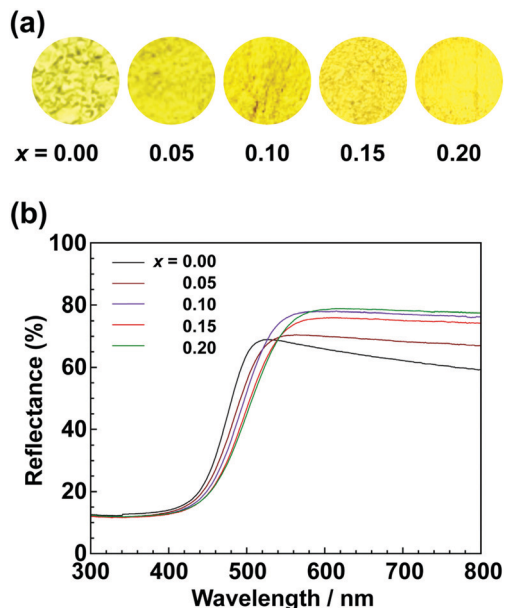


Fig. 9 (a) Photographs and (b) UV-vis DRS of  $\text{Ca}_{1-x}\text{La}_x\text{Ta}(\text{O},\text{N})_3$  ( $x = 0.00, 0.05, 0.10, 0.15$  and  $0.20$ ) obtained from  $\text{Ca}(\text{OH})_2$ ,  $\text{La}(\text{OH})_3$ ,  $\text{Ta}_2\text{O}_5$  gel and urea after calcination at  $950\text{ }^\circ\text{C}$  for 2 h.

continuous expansion of the  $\text{AB}(\text{O},\text{N})_3$  unit cell on substitution of  $\text{Ca}^{2+}$  with  $\text{La}^{3+}$ . The lattice parameters and volumes of the products are listed in Table S1 in the ESI.† The lattice parameters and volumes increased with increasing doping with  $\text{La}^{3+}$  ions at the A sites. This reveals that smaller  $\text{Ca}^{2+}$  ions (ionic radius:  $0.134\text{ nm}$ )<sup>48</sup> in  $\text{CaTa}(\text{O},\text{N})_3$  were replaced with larger  $\text{La}^{3+}$  ions (ionic radius:  $0.136\text{ nm}$ ).<sup>48</sup> Photographs and UV-vis DRS of  $\text{Ca}_{1-x}\text{La}_x\text{Ta}(\text{O},\text{N})_3$  ( $x = 0.00, 0.05, 0.10, 0.15$  and  $0.20$ ) are depicted in Fig. 9. The products were washed sequentially with DI water and HCl aq. to remove the  $\text{CaCN}_2$  by-product. All the products exhibited a bright yellow colour, as shown in Fig. 9(a). Higher reflectances were observed on the longer-wavelength side of the DRS even with increasing  $\text{La}^{3+}$  ion concentration. This suggests that substitution of  $\text{Ca}^{2+}$  ions with  $\text{La}^{3+}$  ions did not induce the reduction of  $\text{Ta}^{5+}$  ions during the urea-nitriding process. The spectroscopic curves shifted towards the longer-wavelength side with increasing  $\text{La}^{3+}$  ion concentration. The CIE  $L^*a^*b^*Ch^\circ$  colour coordinate parameters and bandgap energies of  $\text{Ca}_{1-x}\text{La}_x\text{Ta}(\text{O},\text{N})_3$  ( $x = 0.00, 0.05, 0.10, 0.15$  and  $0.20$ ) are given in Table 3. The hue angle parameters were located in the yellow region ( $70^\circ < h^\circ < 105^\circ$ ), therefore all the products were yellow. The yellowness ( $b^*$ ) value increased in the positive direction, from  $+41.8$  to  $+65.3$ , with increasing doping amount of  $\text{La}^{3+}$  from 0 to 0.2. The colour saturation parameter ( $C$ ) also increased with increasing  $b^*$  value. Among the  $\text{Ca}_{1-x}\text{La}_x\text{Ta}(\text{O},\text{N})_3$  samples prepared in this study,  $\text{Ca}_{0.8}\text{La}_{0.2}\text{Ta}(\text{O},\text{N})_3$  had the highest  $b^*$  and  $C$  values. This indicates that this oxynitride exhibited the most brilliant yellow colour. The estimated bandgap energy ( $E_g$ ) of  $\text{Ca}_{0.8}\text{La}_{0.2}\text{Ta}(\text{O},\text{N})_3$  was  $2.48\text{ eV}$ , which is smaller than that of  $\text{CaTa}(\text{O},\text{N})_3$  ( $E_g = 2.56\text{ eV}$ ; described above) and comparable to that of  $\text{CaTaO}_2\text{N}$  synthesised by ammonolysis ( $E_g = 2.47\text{ eV}$ ).<sup>47</sup> The elemental contents of  $\text{Ca}_{0.8}\text{La}_{0.2}\text{Ta}(\text{O},\text{N})_3$  were determined by O/N

Table 3 CIE  $L^*a^*b^*Ch^\circ$  colour coordinates and bandgap energies ( $E_g$ ) of  $\text{Ca}_{1-x}\text{La}_x\text{Ta}(\text{O},\text{N})_3$  ( $x = 0.00, 0.05, 0.10, 0.15$  and  $0.20$ ) prepared from  $\text{Ca}(\text{OH})_2$ ,  $\text{La}(\text{OH})_3$ ,  $\text{Ta}_2\text{O}_5$  gel and urea after heat treatment at  $950\text{ }^\circ\text{C}$  for 2 h


$x$ in $\text{Ca}_{1-x}\text{La}_x\text{Ta}(\text{O},\text{N})_3$	Colour coordinates					$E_g/\text{eV}$
	$L^*$	$a^*$	$b^*$	$C$	$h^\circ$	
0.00	82.3	-15.4	+41.8	44.5	110	2.59
0.05	90.0	-13.8	+55.9	57.5	104	2.56
0.10	91.1	-10.9	+62.1	63.0	100	2.53
0.15	88.2	-7.88	+62.8	63.3	97	2.50
0.20	88.8	-5.51	+65.3	65.5	95	2.48

combustion analysis and XRF spectroscopy. The O:N ratio obtained by combustion analysis was  $2.28:0.72$  and that obtained by XRF spectroscopy was  $2.11:0.89$ . These values are closer to an O/N ratio of 2:1 than is that of  $\text{CaTa}(\text{O},\text{N})_3$  (Table 4). These results reveal that the partial substitution of  $\text{Ca}^{2+}$  sites by  $\text{La}^{3+}$  compensates for the deficiency of  $\text{N}^{3-}$  at the anion sites of a Ca-Ta-based perovskite oxynitride. This results in a bandgap energy and chromaticity that resemble those of  $\text{CaTaO}_2\text{N}$  with an ideal O/N ratio. The distortion of Ta-O-N-Ta bonds is also a critical factor in the electronic structures of Ta-based perovskite oxynitrides because hybridisations between the 5d orbital of Ta and the 2p orbitals of O and N contribute significantly to the conduction and valence bands.<sup>47,49</sup> The substitution of  $\text{Ca}^{2+}$  with  $\text{La}^{3+}$  induces changes in the Ta-O/N-Ta bond angles and this may contribute to the variations in the bandgap energies of  $\text{Ca}_{1-x}\text{La}_x\text{Ta}(\text{O},\text{N})_3$ . The colour coordinate data for  $\text{CaTa}(\text{O},\text{N})_3$  and  $\text{Ca}_{0.8}\text{La}_{0.2}\text{Ta}(\text{O},\text{N})_3$  prepared in this study were compared with those reported in the literature for  $\text{CaTaO}_2\text{N}$  synthesised by ammonolysis<sup>26</sup> and conventional



**Table 4** Oxygen and nitrogen contents of  $\text{Ca}_{1-x}\text{La}_x\text{Ta}(\text{O},\text{N})_3$  ( $x = 0.00$  and  $0.20$ ) prepared from  $\text{Ca}(\text{OH})_2$ ,  $\text{La}(\text{OH})_3$ ,  $\text{Ta}_2\text{O}_5$  gel and urea after heat treatment at  $950^\circ\text{C}$  for 2 h

Sample	O/N molar ratio in the product analysed by combustion method (O + N = 3)		O/N molar ratio in the product analysed by XRF spectroscopy (O + N = 3)	
	O	N	O	N
$\text{CaLaTa}(\text{O},\text{N})_3$	2.32	0.68	2.18	0.82
$\text{Ca}_{0.8}\text{La}_{0.2}\text{Ta}(\text{O},\text{N})_3$	2.28	0.72	2.11	0.89

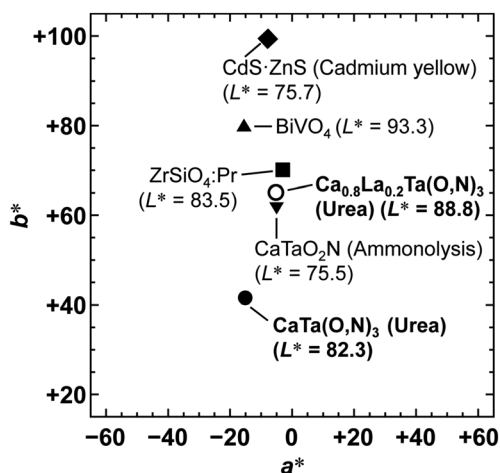

**Fig. 10** CIE  $L^*a^*b^*$  colour coordinate plots for  $\text{Ca}_{1-x}\text{La}_x\text{Ta}(\text{O},\text{N})_3$  ( $x = 0, 0.2$ ) prepared by urea-nitriding method in this study. Data for  $\text{CaTaO}_2\text{N}$  prepared via the ammonolysis method<sup>26</sup> and commercially available yellow pigments ( $\text{CdS-ZnS}$  (cadmium yellow),<sup>25</sup>  $\text{BiVO}_4$ <sup>20</sup> and  $\text{ZrSiO}_4:\text{Pr}^{20}$ ) are also displayed for comparison.

yellow pigments such as cadmium yellow,<sup>25</sup>  $\text{BiVO}_4$ <sup>20</sup> and  $\text{ZrSiO}_4:\text{Pr}^{20}$  (Fig. 10). Although the yellowness ( $b^*$ ) value for  $\text{CaTa}(\text{O},\text{N})_3$  prepared by using urea fell short of those for  $\text{CaTaO}_2\text{N}$  prepared by ammonolysis and conventional yellow pigments, that for  $\text{Ca}_{1-x}\text{La}_x\text{Ta}(\text{O},\text{N})_3$  was almost comparable to those of  $\text{CaTaO}_2\text{N}$  obtained by ammonolysis and  $\text{ZrSiO}_4:\text{Pr}$ . The lightness ( $L^*$ ) value of  $\text{Ca}_{1-x}\text{La}_x\text{Ta}(\text{O},\text{N})_3$  was higher than those of  $\text{CaTaO}_2\text{N}$  and cadmium yellow. SEM was used to observe the morphology of  $\text{Ca}_{0.8}\text{La}_{0.2}\text{Ta}(\text{O},\text{N})_3$  (Fig. S9 in the ESI†). Similarly to that of  $\text{CaTa}(\text{O},\text{N})_3$  (Fig. 5), the particle size was *ca.* 100 nm. The crystalline size of  $\text{Ca}_{0.8}\text{La}_{0.2}\text{Ta}(\text{O},\text{N})_3$  estimated from the XRD pattern by using the Scherrer equation was 28 nm. These small grain and crystalline sizes are suitable for pigment applications. These results therefore show that  $\text{Ca}_{1-x}\text{La}_x\text{Ta}(\text{O},\text{N})_3$  samples prepared via the urea-nitriding method have good potential as environmentally benign alternatives to conventional inorganic yellow pigments that contain harmful elements.

## Conclusions

Calcium-tantalum-based perovskite oxynitrides were successfully synthesised without use of an ammonolysis process. As a

Ca source,  $\text{Ca}(\text{OH})_2$  was more suitable than  $\text{CaCO}_3$  because the  $\text{CaTa}(\text{O},\text{N})_3$  product had a bright yellow colour and the formation of by-products that are difficult to remove was suppressed. Increasing the amount of the Ca source in the precursor suppressed the formation of tantalum nitride by-products. Because the  $\text{CaCN}_2$  by-product and excess Ca components remaining after nitridation could be removed by sequential washing with DI water and  $\text{HCl}$  aq.,  $\text{CaTa}(\text{O},\text{N})_3$  was obtained as a single phase. The  $\text{CaTa}(\text{O},\text{N})_3$  obtained by this method was not completely nitrided and did not give ideal  $\text{CaTaO}_2\text{N}$ . The proportion of  $\text{N}^{3-}$  at the anion sites of the perovskite structure was adjusted by increasing the total cation charge by partial substitution of  $\text{Ca}^{2+}$  with  $\text{La}^{3+}$ . The bandgap energy of  $\text{Ca}_{0.8}\text{La}_{0.2}\text{Ta}(\text{O},\text{N})_3$  was comparable to that of  $\text{CaTaO}_2\text{N}$  prepared by ammonolysis and its colour parameters were comparable to those of commercially available inorganic yellow pigments. In this approach, hazardous components are eliminated both from the preparation process and the final products. The urea-nitriding method enables shortening of the high-temperature reaction time. This is advantageous in terms of reduced energy consumption. In addition, because of the shortened reaction time, the sample particles are finer. This is an important advantage in pigment applications. We therefore believe that this developed approach to the preparation of oxynitride pigments will help the inorganic pigment industry to achieve sustainable development goals.

## Author contributions

T. Sakata: investigation, writing – original draft; S. Urushidani: investigation; N. Tarutani: investigation, methodology, writing – review & editing; K. Katagiri: conceptualization, funding acquisition, methodology, supervision, writing – review & editing; K. Inumaru: supervision; K. Koyama: investigation; N. Iwata: investigation; Y. Masubuchi: resources.

## Conflicts of interest

The authors declare no conflicts of interest.

## Acknowledgements

This work was supported by JSPS KAKENHI (Grant No. JP16H06439, JP18K19132, JP18H01709, JP19H04699, and JP20H02439). We thank Edanz (<https://jp.edanz.com/ac>) for editing a draft of this manuscript.

## References

- 1 K. Nassau, *The Physics and Chemistry of Color: The Fifteen Causes of Color*, John Wiley & Sons, Inc., New York, NY, USA, 2nd edn, 2001.
- 2 R. G. Kuehni, *Color: An Introduction to Practice and Principles*, John Wiley & Sons, Inc., Hoboken, NJ, USA, 2nd edn, 2005.





- 3 E. B. Faulkner and R. J. Schwartz, *High Performance Pigments*, Wiley-VCH, Weinheim, 2nd edn, 2009.
- 4 R. A. Eppler and E. R. Douglas, *Ceram. Eng. Sci. Proc.*, 1994, **15**, 281–288.
- 5 J. A. Badenes, M. Llusar, M. A. Tena, J. Calbo and G. Monrós, *J. Eur. Ceram. Soc.*, 2002, **22**, 1981–1990.
- 6 A. Mahmoodi, Z. Jiryaei, A. Dadras, M. Khorasani and X. Shi, *J. Cleaner Prod.*, 2021, **319**, 128733.
- 7 A. Amat, C. Milianni and S. Fantacci, *RSC Adv.*, 2016, **6**, 36336–36344.
- 8 A. Cesaratto, C. D'Andrea, A. Nevin, G. Valentini, F. Tassone, R. Alberti, T. Frizzi and D. Comelli, *Anal. Methods*, 2014, **6**, 130–138.
- 9 G. Zeng, J. Yang, R. Hong, Z. Li, Y. Chen, F. Li, Q. Wu, L. Liu and X. Jiang, *Ceram. Int.*, 2018, **44**, 8788–8794.
- 10 S. H. Gilani and M. Marano, *Environ. Res.*, 1979, **19**, 427–431.
- 11 L. Järup and A. Åkesson, *Toxicol. Appl. Pharmacol.*, 2009, **238**, 201–208.
- 12 C. J. Boreiko and T. G. Rossman, *Toxicol. Appl. Pharmacol.*, 2020, **403**, 115156.
- 13 A. L. Wani, A. Ara and J. A. Usmani, *Interdiscip. Toxicol.*, 2015, **8**, 55–64.
- 14 World Health Organization, Lead poisoning, <https://www.who.int/news-room/fact-sheets/detail/lead-poisoning-and-health> (accessed March 2022).
- 15 V. S. Vishnu, S. Jose and M. L. Reddy, *J. Am. Ceram. Soc.*, 2011, **94**, 997–1001.
- 16 T. Masui, T. Honda, Wendusu and N. Imanaka, *Dyes Pigm.*, 2013, **99**, 636–641.
- 17 S. P. Radhika, K. J. Sreeram and B. U. Nair, *ACS Sustainable Chem. Eng.*, 2014, **2**, 1251–1256.
- 18 S. Chen, M. Cai and X. Ma, *J. Alloys Compd.*, 2016, **689**, 36–40.
- 19 Wendusu, T. Honda, T. Masui and N. Imanaka, *RSC Adv.*, 2013, **3**, 24941–24945.
- 20 K. Minagawa, Y. Nishiguchi, R. Oka and T. Masui, *ACS Omega*, 2021, **6**, 3411–3417.
- 21 J. A. Badenes, J. B. Vicent, M. Llusar, M. A. Tena and G. Monr, *J. Mater. Sci.*, 2002, **37**, 1413–1420.
- 22 G. D. Nero, G. Cappelletti, S. Ardizzone, P. Fermo and S. Gilardoni, *J. Eur. Ceram. Soc.*, 2004, **24**, 3603–3611.
- 23 R. Nayak, A. Suryanarayana and S. B. Rao, *J. Sci. Ind. Res.*, 2000, **59**, 833–837.
- 24 X. Zhang, T. Chen, Y. Xu, W. Jiang, J. Liu and Z. Xie, *J. Sol-Gel Sci. Technol.*, 2019, **91**, 127–137.
- 25 M. Jansen and H. P. Letschert, *Nature*, 2000, **404**, 980–982.
- 26 Y.-I. Kim, *Ceram. Int.*, 2014, **40**, 5275–5281.
- 27 P. Maillard, F. Tessier, E. Orhan, F. Cheviré and R. Marchand, *Chem. Mater.*, 2005, **17**, 152–156.
- 28 A. Fuertes, *J. Mater. Chem.*, 2012, **22**, 3293–3299.
- 29 F. Tessier, P. Maillard, F. Cheviré, K. Domen and S. Kikkawa, *J. Ceram. Soc. Jpn.*, 2009, **117**, 1–5.
- 30 Y.-I. Kim, P. M. Woodward, K. Z. Baba-Kishi and C. W. Tai, *Chem. Mater.*, 2004, **16**, 1267–1276.
- 31 S.-K. Sun, Y. Masubuchi, T. Motohashi and S. Kikkawa, *J. Eur. Ceram. Soc.*, 2015, **35**, 3289–3294.
- 32 J. Odahara, A. Miura, N. C. Rosero-Navarro and K. Tadanaga, *Inorg. Chem.*, 2018, **57**, 24–27.
- 33 S.-L. Chen, W.-M. Guo, S.-K. Sun, Y. Masubuchi, M. Lv, H.-T. Lin and C.-Y. Wang, *Ceram. Int.*, 2018, **44**, 4504–4507.
- 34 A. Hosono, Y. Masubuchi, S. Yasui, M. Takesada, T. Endo, M. Higuchi, M. Itoh and S. Kikkawa, *Inorg. Chem.*, 2019, **58**, 16752–16760.
- 35 Y. Masubuchi, M. Tadaki and S. Kikkawa, *Chem. Lett.*, 2018, **47**, 31–33.
- 36 Q. Yang, Y. Masubuchi and M. Higuchi, *Ceram. Int.*, 2020, **46**, 13941–13944.
- 37 A. Gomathi, S. Reshma and C. N.-R. Rao, *J. Solid State Chem.*, 2009, **182**, 72–76.
- 38 Q. Gao, C. Giordano and M. Antonietti, *Small*, 2011, **7**, 3334–3340.
- 39 K. Katagiri, Y. Hayashi, R. Yoshiyuki, K. Inumaru, T. Uchiyama, N. Nagata, Y. Uchimoto, A. Miyoshi and K. Maeda, *Inorg. Chem.*, 2018, **57**, 13953–13962.
- 40 R. Okada, K. Katagiri, Y. Masubuchi and K. Inumaru, *Eur. J. Inorg. Chem.*, 2019, 1257–1264.
- 41 T. Sakata, R. Yoshiyuki, R. Okada, S. Urushidani, N. Tarutani, K. Katagiri, K. Inumaru, K. Koyama and Y. Masubuchi, *Inorg. Chem.*, 2021, **60**, 4852–4859.
- 42 R. J. Xie and H. T. Hintzen, *J. Am. Ceram. Soc.*, 2013, **96**, 665–687.
- 43 F. Oehler, R. Naumann, R. Köferstein, D. Hesse and S. G. Ebbinghaus, *Mater. Res. Bull.*, 2016, **73**, 276–283.
- 44 E. Günther, R. Hagenmayer and M. Jansen, *Z. Anorg. Allg. Chem.*, 2000, **626**, 1519–1525.
- 45 U. Berger and W. Schnick, *J. Alloys Compd.*, 1994, **206**, 179–184.
- 46 F. Cheviré, F. Tessier and R. Marchand, *Eur. J. Inorg. Chem.*, 2006, 1223–1230.
- 47 Y. Wang, Y. Kang, H. Zhu, G. Liu, J. T.-S. Irvine and X. Xu, *Adv. Sci.*, 2021, **8**, 2003343.
- 48 R. D. Shannon, *Acta Crystallogr., Sect. A: Found. Adv.*, 1976, **32**, 751–767.
- 49 S. Balaz, S. H. Porter, P. M. Woodward and L. J. Brillson, *Chem. Mater.*, 2013, **25**, 3337–3343.

