


Cite this: *RSC Adv.*, 2022, 12, 2729

Received 10th November 2021
Accepted 3rd January 2022

DOI: 10.1039/d1ra08236a

rsc.li/rsc-advances

In situ construction of a Te/CsPbBr₃ heterojunction for self-powered photodetector

Jie Zhang^{ab} and Jiaojiao Liu^{ID}*^{ab}

In this study, CsPbBr₃ particles were prepared by a simple solvent evaporation method in ambient environment; the p–n heterojunction formed by CsPbBr₃ particles on the surface of a single long Te wire was used to construct a high-performance Te/CsPbBr₃ photodetector. Compared with CsPbBr₃ PDs, the Te/CsPbBr₃ photodetector showed improved photocurrent, and exhibited characteristics of excellent self-powered performance, broad-spectrum response (UV-visible), and ultra-fast response speed ($t_{\text{rise}} = 0.09$ ms). In addition, under zero bias and upon 540 nm light irradiation, the device had good responsivity (0.35 mA W^{-1}), high photosensitivity (up to 100 on/off ratio), and a detectivity of 1.42×10^{10} Jones. This study provides insight into the possibility of manufacturing high-performance self-powered photodetectors through a simple *in situ* construction of heterojunctions.

1. Introduction

Photodetectors (PDs) can convert optical signals into electrical signals by the photoelectric effect. By analyzing the electrical signals, it is easy to derive the optical signal information and detect optical radiation. PDs have applications in environmental monitoring, environmental sensors, spectrum analysis, communications, imaging, *etc.*^{1–5} In general, PDs need an external power supply to work, but self-powered PDs take advantage of the photovoltaic effect of the p–n junction, heterojunction, or Schottky junction, and can work under zero bias.⁶ Self-powered PDs are energy-saving, safe, and stable, and have great application potential.^{7–9} Therefore, particularly in the face of the global energy crisis, the electronic equipment industry is urgently pursuing this self-powered feature. This study focuses on the manufacture of self-powered PDs through the construction of heterojunctions.

Tellurium (Te) is a common p-type semiconductor with a band gap of 0.35 eV.¹⁰ Due to anisotropy during the growth of Te crystals, they can form one-dimensional nanostructures. One-dimensional Te crystals are called Te nanowires, and the synthesis process is simple, fast, and high-yielding. In addition, Te nanowires also have excellent photoelectric properties. Te nanowires have applications in gas sensing, nonlinear optical response devices, optoelectronic devices, thermoelectric devices, piezoelectric devices, photonic crystals, field-effect devices, and infrared acousto-optic deflectors, *etc.*^{11,12} Considering Te nanowires have a high specific surface area, clear charge transfer pathway, and good surface adhesion, it is

a promising candidate for constructing high-performance self-powered PDs with high photosensitivity, high responsiveness, and excellent performance.¹³ Te wire is very suitable for constructing heterojunction photodetectors, and its composite device may have excellent self-powered performance.

The organic–inorganic hybrid perovskite has received considerable attention recently due to its excellent photoelectric properties. These include an adjustable direct band gap, high electron mobility, long electron holes, simple processing technology, easy integration with various semiconductor materials.^{14,15} However, the instability, humidity, and high temperature of organic lead halide perovskites and its composites under continuous irradiation have severely hindered its long-term application in commercial development.¹⁶ CsPbBr₃ is a kind of organic–inorganic perovskite with good stability and good light detection performance. The PDs based on perovskite crystals have been widely used, with characteristics of high detectivity and fast response speed.^{17,18} Due to the high electron mobility and low exciton binding energy of CsPbBr₃, considerable research has been conducted on its photoelectric properties.¹⁹ In addition, CsPbBr₃ particle has high stability, excellent optical properties, and can be combined with other materials for optoelectronic components.²⁰ Fang *et al.* reported that millimeter-sized CsPbBr₃ was prepared by a simple solution evaporation method to form p-CuI/n-CsPbBr₃ heterojunctions. The resulting device exhibited good rectification characteristics and excellent self-powering performance upon 540 nm light illumination.²¹ Fang *et al.* also reported that a controllable combination of CsPbBr₃ and SnO₂ of different sizes was formed by chemical deposition, and the formed optoelectronic device achieved a dual spectral response. Upon 320, 520 nm light illumination, both showed good self-powered characteristics.²² However, when PDs about Te and CsPbBr₃

^aCollege of Electronic and Information Engineering, Changshu Institute of Technology, Changshu 215500, China. E-mail: zj2016@cslg.edu.cn; liujiaojiao@cslg.edu.cn

^bSuzhou Key Laboratory of Advanced Lighting and Display Technologies, China



composite are unreported, we can use a simple method to construct Te/CsPbBr₃ heterojunction and study its performance.

In this study, CsPbBr₃ particles were prepared by a simple solvent evaporation method in ambient environment, and the p–n heterojunction formed by CsPbBr₃ particles on the surface of a single long Te wire was used to construct a high-performance Te/CsPbBr₃ photodetector. The as-fabricated p-Te/n-CsPbBr₃ heterojunction device worked stably as a self-powered UV PD with broad-spectrum response (UV-visible), and exhibited excellent self-powered characteristics under 540 nm light irradiation, such as high photocurrent (near 1 nA, good responsivity (0.35 mA W^{−1})), high photosensitivity (up to 100 on/off ratio), detectivity of 1.42×10^{10} Jones per W and fast response speed ($t_{\text{rise}} = 0.09$ ms). This work introduces a simple method for constructing heterojunction devices *in situ* and provides insights into manufacturing high-performance self-powered PDs.

2. Experimental section

2.1 CVD method to prepare Te wire

Te powder was placed in the middle of the horizontal tube furnace, the horizontal tube furnace was vacuumed to less than 1 mTorr, and filled with a carrier gas for cleaning. After repeating twice, the carrier gas was passed and a mechanical pump was used to maintain the pressure in the furnace tube at 10–15 torr. The cleaned Te substrate was then placed downwind from the evaporation source, in the middle of the horizontal tube furnace and at a distance of 25 cm to 28 cm from the middle of the furnace body, and the horizontal tube furnace heated. The temperature of the evaporation source in the tube was increased to 480 °C, and this temperature was maintained for 90–150 min. During the reaction, carrier gas was passed. After the reaction finished, the carrier gas was passed continually for natural cooling.

2.2 Preparation of the Te/CsPbBr₃ heterojunction

All the chemicals were purchased from Aladdin and used directly without further processing. The Te wire prepared by CVD was placed on a clean glass substrate, and the 0.45 M PbBr₂ (99.999%) dimethylformamide (DMF) precursor solution was dropped around the Te wire onto the glass substrate (Fig. 1a). As DMF evaporated, a series of PbBr₂ milliwires (MWs) were formed on the Te surface. 0.45 M CsBr (99.9%) methanol solution was immersed in half of the Te–PbBr₂ (MWs) to form CsPbBr₃ particles on the Te wire surface. It was heated for 30 min under ambient conditions to form a Te/CsPbBr₃ heterojunction (Fig. 1a). The Te/CsPbBr₃ heterojunction was cleaned with isopropanol before use. Two small pieces of indium paste were coated on the surface of the composite as electrodes to construct Te/CsPbBr₃. Electrode diameter and length were about 0.2×0.05 cm and the effective area was about 0.001 cm².

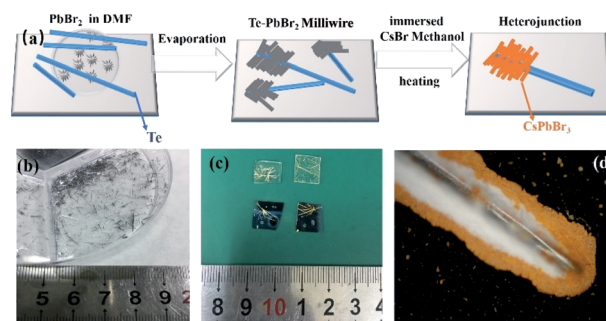


Fig. 1 (a) Schematic of the preparation process of the Te/CsPbBr₃ heterojunction. The photographs of the as-prepared Te wire and the Te/CsPbBr₃ heterojunction (b) and (c). (d) Optical microscope image of the Te/CsPbBr₃ heterojunction.

2.3 Characterization

A field-emission scanning electron microscope (FE-SEM, Zeiss Sigma) was used to characterize sample morphologies. X-ray diffraction (XRD) patterns were collected on a Bruker D8-A25 diffractometer using Cu K α radiation ($\lambda = 1.5405$ Å) in the 2θ range from 10° to 70°. X-ray photoelectron spectroscopy (XPS, PerkinElmer PHI 5000C ESCA system equipped with a hemispherical electron energy analyzer) was utilized experimentally to investigate the composition and chemical state of the samples. The binding energy for the C 1s peak at 285 eV was used as the reference for calibration. The photoelectric performance was characterized by a program-controlled semiconductor characterization system (Keithley 4200, USA). Time-resolved responses of the device were measured with a YAG:Nd laser in the pulse duration range of 3–5 ns (Continuum Electro-Optics, MINILITE II, 355 nm), an oscilloscope (Tektronix MSO/DPO5000), and a 1 G Ω resistor. The light intensity was measured with a NOVA II power meter (OPHIR Photonics). All measurements were performed at room temperature.

3. Results and discussion

A schematic of the process of forming a heterojunction is shown in Fig. 1a. It can be seen that Te wires are crystals with metal glossy and only a few millimeters long (Fig. 1b). The surface of the Te wire was covered by CsPbBr₃ particles, which caused the color of the Te wires to change to yellow and formed a Te/CsPbBr₃ composite material. Fig. 1c is a photo of the heterojunction used in the experiment. Fig. 1d is an optical microscope photo of the end of the Te wire covered with CsPbBr₃ particles. It was observed that pure CsPbBr₃ particles aggregate on the Te surface, and the long Te wire can easily be assembled into different heterostructures. As the preparation process of the Te/CsPbBr₃ heterojunction is simple, it has potential applications in the field of basic research.

X-ray diffraction (XRD) patterns were used to determine the crystalline properties of single Te wires and CsPbBr₃ particles. The Te wires were synthesized by the chemical vapor deposition method. CsPbBr₃ particles were obtained by a simple solvent



evaporation method. The detailed preparation process is discussed in the experimental part. As shown in Fig. 2a, the strong and sharp diffraction peak of a single Te wire at 27.5° proves the high crystal quality, which corresponds to the (101) crystal plane of hexagonal Te with lattice parameters of $a = b = 4.458 \text{ \AA}$ and $c = 5.927 \text{ \AA}$ (JCPDF no. 36-1452). The as-prepared high-quality Te wires are a promising candidate to be integrated with other semiconductor materials in various device structures. Fig. 2b exhibits the diffraction peaks of the CsPbBr₃ particles, which match well with monoclinic cesium lead bromide with lattice parameters of $a = 9.843 \text{ \AA}$, $b = 4.127 \text{ \AA}$, and $c = 6.874 \text{ \AA}$ (JCPDF no. 54-0751), and confirm the crystallinity and purity of the as-obtained sample. The main diffraction peaks of CsPbBr₃ particles located at 2θ of 15.05° , 21.68° , 23.84° , 30.79° , 37.41° , 42.97° are attributed to the (001), (010), (110), (002), (102), (020) crystal facets, respectively, of the CsPbBr₃ particles. The obvious peak at 2θ of 30.8° corresponds to the (002) crystal plane of CsPbBr₃, indicating that the crystal exposed surface is the (002) plane. The diffraction peaks at 12.7° and 18.2° are derived from PbBr₂ MWs (these two peaks are not marked in Fig. 2b). We used a two-step method to prepare CrPbBr₃ particles. A part of the

PbBr₂ crystals generated in the first step was not completely converted into CrPbBr₃ particles, indicating the presence of PbBr₂ impurity peaks. These characteristics indicate that Te wires and CsPbBr₃ particles have good crystallinity. To investigate the composition and electronic states of the as-prepared CsPbBr₃ crystals, X-ray photoelectron spectroscopy (XPS) measurements were performed using element C for calibration. Fig. 2c shows the XPS spectrum of the CsPbBr₃ sample. Fig. 2d–f presents the spectra of elements in the CsPbBr₃ sample and Fig. 2d shows that the binding energy spectrum (XPS) of 725.4 eV corresponds to Cs 3d_{5/2}. The two nearby binding energy peaks at 139.5 eV and 144.4 eV were attributed to Pb 4f_{7/2} and Pb 4f_{5/2}, respectively, revealing the existence of Pb²⁺ in CsPbBr₃ samples (Fig. 2e). The binding energy peaks located at 69.9 eV can be attributed to the spin-orbit splitting photoelectron of Br 3d_{5/2} (Fig. 2f). The results further proved the coexistence of the elements Cs, Pb, and Br. The Te wires and CsPbBr₃ crystals obtained by collecting all these features have good crystallinity.

To explore the potential of PD, and study its photoelectric performance and self-powered properties, CsPbBr₃ particles were used to integrate onto the surface of Te wire to form a Te/

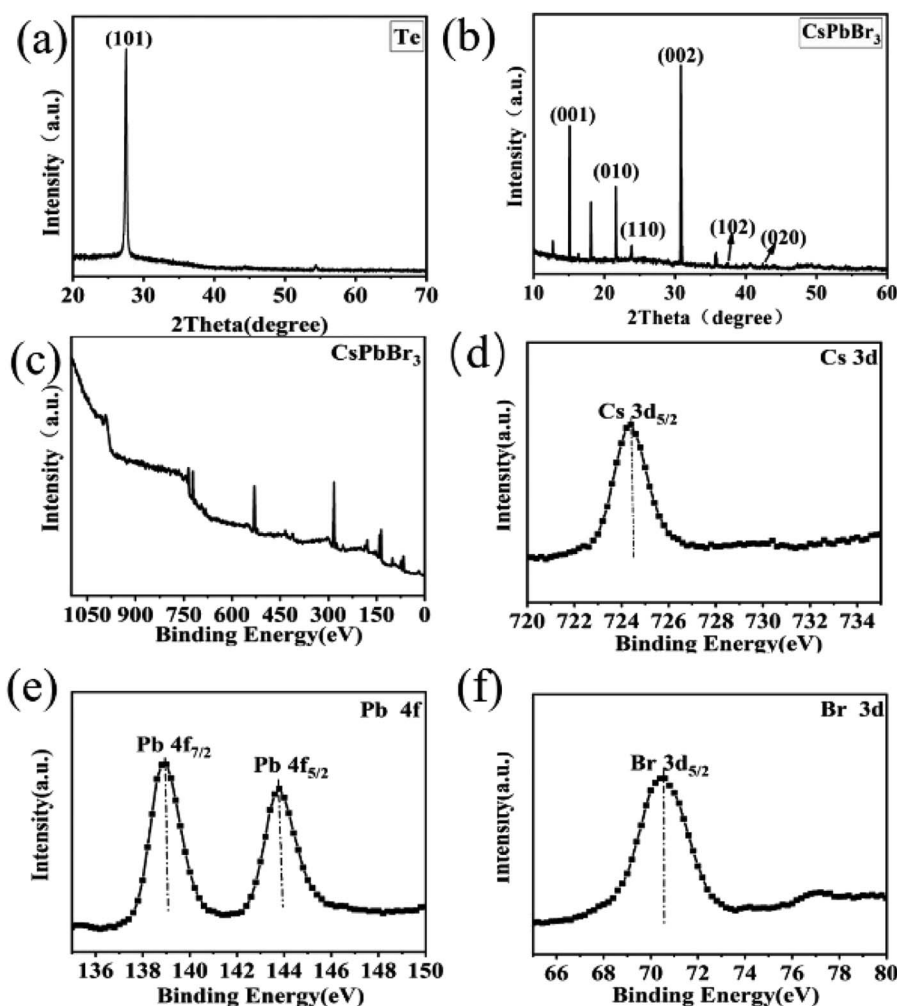


Fig. 2 XRD patterns (a) Te wire (b) CsPbBr₃ particles, XPS spectra (c) CsPbBr₃ (d) Cs 3d (e) Pb 4f (f) Br 3d.



CsPbBr₃ composite. The schematic of the Te/CsPbBr₃ PD is shown in Fig. 3a. Fig. 3b shows the current–voltage (*I*–*V*) curve of a single Te/CsPbBr₃ heterojunction under dark and upon 500, 400, and 300 nm light illumination under the bias of 3 V. Te/CsPbBr₃ PDs exhibited different photocurrent and dark currents, indicating that it had acquired photoelectric characteristics. Under the illumination of 500 nm at 3 V, the photocurrent of the Te/CsPbBr₃ device could reach 28 nA, which was about 223 times that in dark. Under 0 V and 500 nm light illumination, the relatively high photocurrent of 3.7 nA indicates that the hybrid device can be used as a self-powered PD to detect light without additional energy consumption. The effect of self-powered devices is mainly based on the photovoltaic effect of p-Te and n-CsPbBr₃ heterojunction. The photocurrent of the Te/CsPbBr₃ device is two orders of magnitude larger than the dark current, which indicates that the device has good photo-response characteristics under illumination.

For comparison, the *I*–*V* curves of the pure CsPbBr₃ particle device and the Te device are shown in Fig. 3c and d. The pure CsPbBr₃ device has a photoelectric response, and the Te device has no photoelectric characteristics, but the photocurrent and dark current values are not much different, and the dark current is very small at 0 V. This shows that neither the CsPbBr₃ device nor the Te device can produce self-powered behavior. Te is a p-type semiconductor material with high hole mobility and carrier concentration, which is generally used as a hole transport layer.²³ CsPbBr₃ particles is an n-type semiconductor with high carrier mobility, which can balance the electron–hole diffusion length in the range of visible light.^{24,25} This means that the self-powered behavior of the Te/CsPbBr₃ device originates

from the p–n junction formed by p-Te and n-CsPbBr₃. The Te/CsPbBr₃ composite device has a better photoelectric and self-powered performance than the CsPbBr₃ device. The Te device can also be used as PDs, but the on-off ratio is so small that our equipment cannot measure it.

To further detect the response characteristics of Te/CsPbBr₃ PD, we checked current–time (*I*–*t*) for different bias voltages (3 V, 0.5 V, and –0.5 V) under 500, 400, and 300 nm light (Fig. 4). For comparison, we tested the *I*–*t* curve of the CsPbBr₃ device under 500 nm light and Te/CsPbBr₃ PDs under 500, 400, 300 nm light at 3 V, as shown in Fig. 4a. For the CsPbBr₃ device, the output current rose from nearly zero to 60 pA when the ultra-violet light was switched on, and attenuated to 3 pA when the light was switched off. When the light (500, 400, and 300 nm) is turned on at 3 V, the photocurrent reached 12 nA, 8 nA, and 4 nA, the dark current was 0.1 nA, and the maximum on/off ratio was 120. We note that when compared with the CsPbBr₃ device, Te/CsPbBr₃ PDs have better photosensitivity and the photocurrent is relatively smoother when starting and stopping the illumination, indicating that the photocurrent of the PDs is less sensitive to the capacitive current. Different biases (–0.5 V and 0.5 V) were applied according to their open-circuit voltages (Fig. 3b), as shown in Fig. 4b. Interestingly, the photocurrent and dark current of Te/CsPbBr₃ PD at 0.5 V were higher than –0.5 V, and the on/off ratio of the device was higher too. This may have been caused by the photovoltaic effect, and the ratio of light to dark current shown in Fig. 3b. The open-circuit voltage of the device was about 0.5 V, which has a similar dark current but a higher photocurrent and on/off ratio than at –0.5 V. The *I*–*t* curve shows that the on/off switch is repeatable

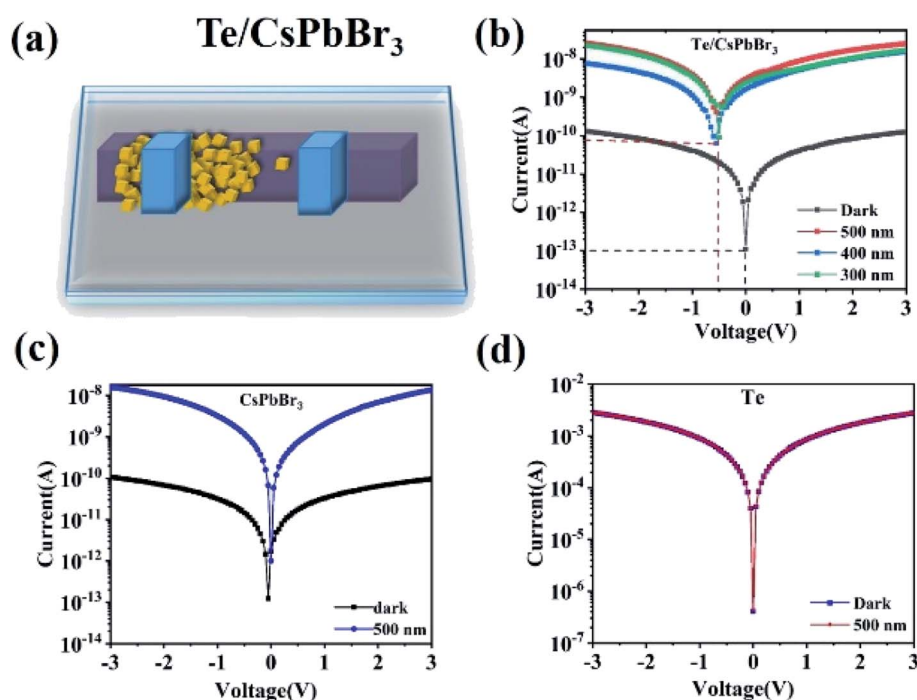


Fig. 3 (a) Schematic of the Te/CsPbBr₃ PD; Typical *I*–*V* curves for different device under dark and illumination of 500 nm; (b) the Te/CsPbBr₃ PD (c) CsPbBr₃ particles (d) Te wire.



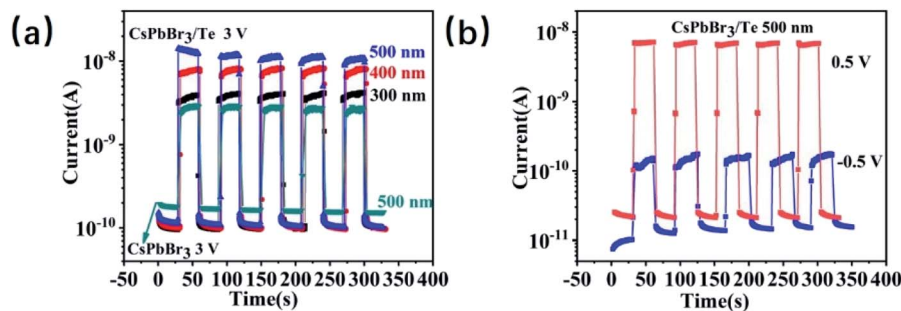


Fig. 4 (a) $I-t$ curves of the CsPbBr₃ device and Te/CsPbBr₃ PDs upon different light illumination under 3 V (b) the Te/CsPbBr₃ (0.5 V and -0.5 V) PDs upon 500 nm light illumination.

and stable under a negative bias and that there is no obvious photocurrent decay cycle. Te/CsPbBr₃ PDs under positive and negative biases have photoelectric properties similar to conventional UV PDs.²⁶

The Te/CsPbBr₃ PDs exhibited an obvious photoresponse at the bias of 0 V upon different light illumination, indicating that the device can be used as a self-powered PD. Fig. 5a shows the time-dependent current ($I-t$) tests under 500, 400, and 300 nm light at 0 V. Reliability and rapid response to light illumination are essential for high-performance PDs. The repeatability and the speed of response to light are two important factors to measure the performance of PDs. The device showed high stability and repeatability in multiple switching cycles under 500, 400, and 300 nm light, with no obvious attenuation in each cycle. When the light was switched on and off without an external power source, the photocurrent of the device rapidly increased to a steady-state, and then rapidly decreased. This indicates that the built-in electric field near the heterojunction caused the electron-hole pair to quickly separate. In the absence of an external bias, the photosensitivity of the device (I_{ph}/I_d) under 500, 400, and 300 nm illumination was

respectively 100, 70, 50. The maximum photocurrent could reach 1 nA under 0 V upon 500 nm light. In addition, the photocurrent remained stable during continuous illumination, indicating that the device can operate efficiently and stably without an external power supply. To better illustrate the time-resolved characteristics of the device, a rapid response measurement system was applied. The pulse response of the device is shown in Fig. 5c and d. In the application of this system, a pulsed YAG:Nd laser was used as the light source, and an oscilloscope recorded the voltage variation of series resistance with time. When the pulsed laser irradiated PDs, the concentration of photogenerated carriers increased and the resistance decreased, leading to the rise in the partial pressure on the resistance. At a bias of 0 V, the optical response of the device was very fast, and the oscilloscope captured the photo-voltaic voltage change on the device after local illumination. Fig. 5b shows a laser pulse of 0 V in response. The ten cycles of Te/CsPbBr₃ PD impulse response confirm the stability and repeatability of the device. The very sharp current peak was generated under periodic pulse radiation, indicating extremely fast incident laser pulses and highly stable light response. Response time is a parameter that describes how fast the PDs respond to incident radiation. It is expressed by the rise time constant t_{rise} (the rise time corresponds to the growth process of photogenerated carriers, expressed by the time required for the peak photocurrent to increase from 10% to 90%) and the decay time constant t_{decay} (the decay time corresponds to the decay process of photogenerated carriers, expressed by the time required for the peak photocurrent to drop from 90% to 10%). For Te/CsPbBr₃ PDs, the rise/decay time is estimated to be 0.09 ms/0.59 ms (Fig. 5c), which shows that it has ultra-fast response speed as a self-powered device. The rise time can reach the sub-millisecond level, and to the best of our knowledge, this is the faster response time of Te-based PDs. It has been reported in the literature that the rise and decay time of CsPbBr₃/ZnO PDs are 0.88 ms and 1.53 ms, respectively.²⁷ This result shows that the Te/CsPbBr₃ device has a faster response speed than the CsPbBr₃-based device prepared by the solution method.^{28,29}

Based on the Te wire, the heterojunction device formed by CsPbBr₃ particles clearly shows an ultra-fast response speed. Spectral responsivity (R_s) is another key factor for evaluating the

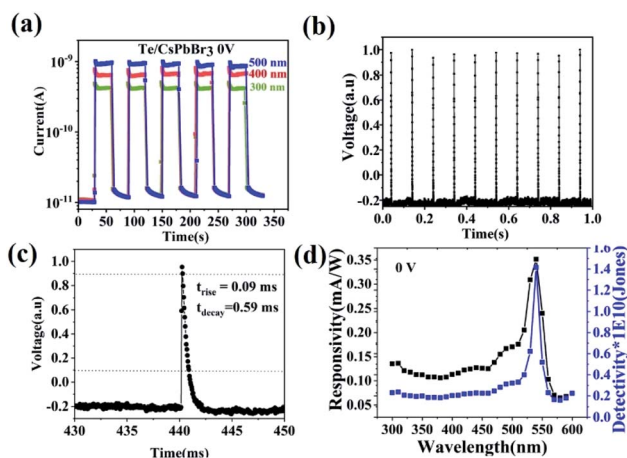


Fig. 5 (a) $I-t$ curves of the Te/CsPbBr₃ PDs upon 500, 400, 300 nm illumination under biases of 0 V; (b) photoresponse of Te/CsPbBr₃ PDs under 355 nm pulse laser radiation at zero bias; (c) single period of pulse response; (d) responsivity and detectivity of the Te/CsPbBr₃ PDs at 0 V bias.



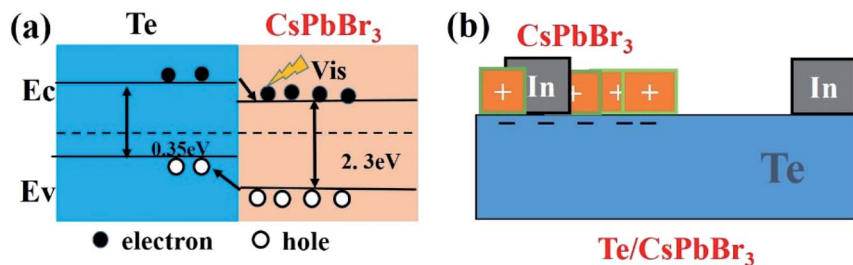


Fig. 6 (a) Schematic energy-band diagrams of the Te/CsPbBr₃ PDs; (b) simplified schematic of the Te/CsPbBr₃ structure.

characteristics of PDs, which was calculated according to the following formula:

$$R_{\lambda} = \frac{I_{ph} - I_d}{P_{in}} = \frac{I_{ph} - I_d}{P_{\lambda} S} \quad (1)$$

where I_{ph} is the photocurrent, I_d is the dark current, P_{λ} is the optical power, E_{λ} is the optical power intensity, and S is the effective lighting area. Next, the R_{λ} of Te/CsPbBr₃ PDs from 300 nm to 600 nm under 0 V was calculated, as shown in Fig. 5d. The peak of responsivity appeared at 550 nm with a value of 0.35 mA W⁻¹, which is equivalent to a self-powered PD based on CsPbBr₃. Detectivity (D^*) refers to the ability of the detector to detect weak signals from environmental noise and is also an important indicator of PD performance. Since the main source of environmental noise is dark current, D^* is expressed as:^{30,31}

$$D^* = \frac{R_{\lambda}}{\left(\frac{2eI_d}{S}\right)^{\frac{1}{2}}} \quad (2)$$

where e is the electron charge and S is the effective lighting area. The detectivity of the Te/CsPbBr₃ device from 300 nm to 600 nm under 0 V was calculated, as shown in Fig. 5d. In this study, the device demonstrated photoresponse in the UV-to-visible region. The D^* of Te/CsPbBr₃ PDs was as high as 1.42×10^{10} Jones (0 V) at a wavelength of 540 nm. Due to its high UV sensitivity and low dark current, Te/CsPbBr₃ PDs are comparable to other self-powered UV PDs.

To understand the self-powered mechanism of Te/CsPbBr₃ PDs, Fig. 6a shows a schematic of the built-in electric field and energy level formed at the interface of p-Te and n-CsPbBr₃. The simplified structure diagram of Te/CsPbBr₃ PD is shown in Fig. 6b. The self-powered characteristics of the device are mainly due to the heterojunction formed at the interface between the p-type Te wire and the n-type CsPbBr₃ particles.^{31,32} The CsPbBr₃ particles were deposited on the surface of the Te wire, and the device exhibited a type-II heterojunction.^{32,33} The band gaps of Te and CsPbBr₃ were 0.35 eV and 2.3 eV, respectively.^{34,35} Under light irradiation, the photogenerated electrons and holes were rapidly separated by the built-in field of the depleted layer. The photo-generated holes in the CsPbBr₃ particles were transferred to the valence band of the Te semiconductor, and the electrons in the conduction band of the Te semiconductor drifted into CsPbBr₃, thereby forming a photo-voltage and a stable photocurrent at the interface.^{36,37} This device can be regarded as a Te/CsPbBr₃ p-n heterojunction

photodiode. Due to the excellent intrinsic physical properties of Te and CsPbBr₃, the Te/CsPbBr₃ heterojunction has a high photocurrent, fast response speed, and a high on/off ratio at 0 V. Due to the narrow Te band gap, the device can respond to ultraviolet and visible light. Therefore, the Te wire is the main carrier transport channel and provides the driving force for the built-in electric field.

4. Conclusion

The long Te wire was synthesized by chemical vapor deposition, where CsPbBr₃ particles were formed on the Te wire surface and then heated to form the p-n heterojunction. CsPbBr₃ particles were then deposited onto the surface of the Te wires and a built-in field formed between Te and CsPbBr₃. This made the device self-powered and exhibits characteristics of broad-spectrum response (UV-visible) and ultra-fast response speed ($t_{rise} = 0.09$ ms). The open-circuit voltage of Te/CsPbBr₃ PD was 0.5 V, which confirms the strong built-in electric field. In addition, under 0 V bias and upon 540 nm light irradiation, the devices had good responsivity (0.35 mA W⁻¹), high photosensitivity (up to 100 on/off ratio), and detectivity of 1.42×10^{10} Jones per W. This study provides a simple and effective method for the *in situ* preparation of heterojunctions. All these promising characteristics show that the composite Te/CsPbBr₃ device has a wide range of application prospects in the field of optoelectronic devices.

Conflicts of interest

The authors declare no conflict of interest.

Acknowledgements

This work was financially supported by the National Natural Science Foundation of China (Grant No. 11904034) and Natural Science Foundation of Jiangsu Province of China (Grant No. BK20191025). Zhang Jie acknowledged the support of the National Natural Science Foundation of China (Grant No. 61704012).

References

- 1 G. Pelayo, A. Armin, P. Meredith and E. H. Sargent, *Nat. Rev. Mater.*, 2017, **2**, 16100.



- 2 M. Cao, W. Zhao, R. Li, H. Gong, Y. Zhang, H. Xu and J. R. Lu, *ACS Appl. Mater. Interfaces*, 2018, **10**, 24937–24946.
- 3 X. Y. Zhao, L. X. Huang, Y. K. Wang, X. L. Zhu, L. Li, G. X. Li and W. H. Sun, *RSC Adv.*, 2020, **10**, 32976–32983.
- 4 Z. B. He, J. X. Guo, S. D. Li, Z. C. Lei, L. Lin, Y. Z. Ke, W. J. Jie, T. X. Gong, Y. Lin, T. D. Cheng, W. Huang and X. S. Zhang, *Adv. Mater. Interfaces*, 2020, **7**, 2070050.
- 5 D. Periyangounder, T. C. Wei, T. Y. Li, C. H. Lin, T. P. Goncalves, *et al.*, *Adv. Mater.*, 2020, **32**, 1904634.
- 6 F. Teng, K. Hu, W. X. Ouyang and X. S. Fang, *Adv. Mater.*, 2018, **30**, 1706262.
- 7 B. S. Ouyang, K. W. Zhang and Y. Yang, *Adv. Mater. Technol.*, 2017, **2**, 1700208.
- 8 Y. Zhang and W. D. Song, *J. Mater. Chem. C*, 2021, **9**, 4799–4807.
- 9 Y. Zhang, W. L. Liu, Y. S. Liu, C. H. Wag, G. D. Zhu and W. D. Song, *J. Mater. Chem. C*, 2021, **9**, 15654–15661.
- 10 J. W. Liu, F. Chen, M. Zhang, H. Qi, C. L. Zhang and S. H. Yu, *Langmuir*, 2010, **26**, 11372–11377.
- 11 J. Yuan, H. Schmalz, Y. Xu, N. Miyajima, M. Drechsler, M. W. Möller, F. Schacher and A. H. E. Müller, *Adv. Mater.*, 2010, **20**, 947–952.
- 12 G. She, W. Shi, X. Zhang, T. Wong, Y. Cai and N. Wang, *Cryst. Growth Des.*, 2013, **9**, 663–666.
- 13 Q. P. Zhang, M. M. Tavakoli, L. L. Gu, D. Q. Zhang, L. Tang, Y. Gao, J. Guo, Y. J. Lin, S. F. Leung, S. Poddar, Y. Fu and Z. Y. Fan, *Nat. Commun.*, 2019, **10**, 727.
- 14 V. V. Belykh, D. R. Yakovlev, M. M. Glazov, P. S. Grigoryev, M. Hussain, J. Rautert, D. N. Dirin, M. V. Kovalenko and M. Bayer, *Nat. Commun.*, 2019, **10**, 673.
- 15 C. H. Lin, B. Cheng, T. Y. Li, J. R. D. Retamal, T. C. Wei, H. C. Fu, X. S. Fang and J. H. He, *ACS Nano*, 2019, **13**, 1168–1176.
- 16 F. Chen, C. X. Xu, Q. Y. Xu, Y. Z. Zhu, F. F. Qin, W. Zhang, Z. Zhu, W. Liu and Z. L. Shi, *ACS Appl. Mater. Interfaces*, 2018, **10**, 25763–25769.
- 17 L. Dou, Y. M. Yang, J. B. You, Z. R. Hong, W. H. Chang, L. Gang and Y. Yang, *Nat. Commun.*, 2014, **5**, 5404.
- 18 Q. Q. Lin, A. Armin, D. M. Lyons, P. L. Burn and P. Meredith, *Adv. Mater.*, 2015, **27**, 2060–2064.
- 19 N. Yantara, S. Bhaumik, F. Yan, D. Sabba, H. A. Dewi, N. Mathews, P. P. Boix, H. V. Demir and S. Mhaisalkar, *J. Phys. Chem. Lett.*, 2015, **6**, 4360–4364.
- 20 L. Protesescu, S. Yakunin, M. I. Bodnarchuk, F. Krieg, R. Caputo, C. H. Hendon, R. X. Yang, A. Walsh and M. V. Kovalenko, *Nano Lett.*, 2015, **15**, 3692–3696.
- 21 Y. Zhang, S. Y. Li, W. Yang, M. K. Joshi and X. S. Fang, *J. Phys. Chem. Lett.*, 2019, **10**, 2400–2407.
- 22 Y. Zhang, W. X. Xu, X. J. Xu, J. Cai, W. Yang and X. S. Fang, *J. Phys. Chem. Lett.*, 2019, **10**, 836–841.
- 23 U. K. Gautam and C. N. R. Rao, *J. Mater. Chem.*, 2004, **14**, 2530–2535.
- 24 J. Ding, S. Du, Z. Zuo, Y. Zhao, H. Cui and X. Zhan, *J. Phys. Chem. C*, 2017, **121**, 4917–4923.
- 25 M. Shoaib, X. Zhang, X. Wang, H. Zhou, T. Xu, X. Wang, X. Hu, H. Liu, X. Fan, W. Zheng, *et al.*, *J. Am. Chem. Soc.*, 2017, **139**, 15592–15595.
- 26 Y. Zhang, W. X. Xu, X. J. Xu, W. Yang, S. Y. Li, J. X. Chen and X. S. Fang, *Nanoscale Horiz.*, 2019, **4**, 452–456.
- 27 Y. L. Shen, C. Wei, L. B. Ma, S. L. Wang, X. Wang, X. B. Xu and H. B. Zeng, *J. Mater. Chem. C*, 2018, **6**, 12164–12169.
- 28 H. J. Zhang, X. Liu, J. P. Dong, H. Yu, C. Zhou, B. B. Zhang, Y. D. Xu and W. Q. Jie, *Cryst. Growth Des.*, 2017, **17**, 6426–6431.
- 29 Z. Yang, Q. Xu, X. D. Wang, J. F. Lu, H. Wang, F. T. Li, L. Zhang, G. F. Hu and C. F. Pan, *Adv. Mater.*, 2018, **30**, 1802110.
- 30 B. Zhao, F. Wang, H. Y. Chen, Y. P. Wang, M. M. Jiang, X. S. Fang and D. X. Zhao, *Nano Lett.*, 2015, **15**, 3988–3993.
- 31 S. Liang, Y. Fang, H. Wei, Y. Yuan and J. Huang, *Adv. Mater.*, 2016, **28**, 2043–2048.
- 32 W. X. Ouyang, F. Teng and X. S. Fang, *Adv. Funct. Mater.*, 2018, **28**, 1707178.
- 33 W. X. Ouyang, F. Teng, J. H. He and X. S. Fang, *Adv. Funct. Mater.*, 2019, **29**, 1807672.
- 34 H. H. Li, P. Zhang, C. L. Liang, J. Yang, M. Zhou, X. H. Lu and G. A. Hope, *Cryst. Res. Technol.*, 2012, **47**, 1069–1074.
- 35 X. Y. Liu, X. H. Tan, Z. Y. Liu, X. N. Zhang, T. L. Shi and G. L. Liao, *J. Mater. Chem. C*, 2020, **8**, 14409–14422.
- 36 N. Gao and X. S. Fang, *Chem. Rev.*, 2015, **115**, 8294–8343.
- 37 A. Alarawi, V. Ramalingam, H. C. Fu, P. Varadhan, R. S. Yang and J. H. He, *Opt. Express*, 2019, **27**, A352–A362.

