



Cite this: *RSC Adv.*, 2022, 12, 5080

# Photocatalytic turnover of CO<sub>2</sub> under visible light by [Re(CO)<sub>3</sub>(1-(1,10) phenanthroline-5-(4-nitro-naphthalimide))Cl] in tandem with the sacrificial donor BIH<sup>†</sup>

Alyssa Spear,<sup>a</sup> Robson L. Schuarca,<sup>b</sup> Jesse Q. Bond,<sup>b</sup> Timothy M. Korter,<sup>a</sup> Jon Zubietta<sup>\*a</sup> and Robert P. Doyle<sup>\*a</sup>

Optimized photocatalytic conversion of CO<sub>2</sub> requires new potent catalysts that can absorb visible light. The photocatalytic reduction of CO<sub>2</sub> using rhenium(i) has been demonstrated but suffers from low turnover. Herein, we describe a [Re(CO)<sub>3</sub>(1-(1,10)phenanthroline-5-(4-nitro-naphthalimide))Cl] photocatalyst, which when combined with the sacrificial donor 1,3-dimethyl-2-phenyl-2,3-dihydro-1*H*-benzo[d]imidazole, results in selective production of formic acid and a high turnover number of 533 and turnover frequency of 356 h<sup>-1</sup>. Single-crystal X-ray diffraction and DFT studies are also discussed.

Received 11th November 2021  
Accepted 4th February 2022

DOI: 10.1039/d1ra08261b

rsc.li/rsc-advances

## 1. Introduction

Increasing levels of atmospheric and anthropogenic CO<sub>2</sub> require the development of new technologies and strategies in the pursuit of sustainable energy and climate preservation.<sup>1–3</sup> Homogenous mononuclear rhenium(i) complexes have been explored as reductive catalysts for the conversion of CO<sub>2</sub> to fuels and feedstocks, primarily CO.<sup>4,5</sup> While this subset of catalysts has been tuned for high turnover numbers (TN, [CO<sub>2</sub> reduction product]/[catalyst]), notably as high as 350,<sup>6</sup> rarely is selective CO<sub>2</sub> to formic acid conversion reported. Formate and formic acid are attractive products due to ease of transportation and storage, and high energy densities, and as favourable candidates for hydrogen storage.<sup>7–9</sup> Any reports of CO<sub>2</sub> to formate reduction by mononuclear rhenium(i) complexes are typically in trace amounts and hence there is an unmet need to tune such complexes towards formate/formic acid selectivity if they are to provide a viable option for CO<sub>2</sub> conversion to more diverse products, especially under visible light.

Previously, we have reported on the synthesis, characterization, electrochemistry, and catalytic activity of a [Re(CO)<sub>3</sub>(1-(1,10)-phenanthroline-5-(4-nitro-naphthalimide)Cl] complex (1). 1 consists of a rhenium(i) tricarbonyl core with

a naphthalimide based photosensitizing ligand, (1,10)-phenanthroline-5-(4-nitro-naphthalimide) (5-PAN), for the visible light photoreduction of CO<sub>2</sub> to formate (Fig. 1).<sup>10</sup> A sacrificial electron donor, triethylamine (TEA), was required for photocatalysis.<sup>7</sup> The catalytic activity of 1 increased with a concomitant increase in TEA, and no CO<sub>2</sub> conversion was obtained in the absence of light (450–460 nm). Catalytic saturation was reached at 0.87 mmol of HCOO<sup>-</sup>, corresponding to a TN ([HCOO<sup>-</sup>]/[1]) of 48.<sup>10</sup>

In the present research, we aim to discern a mechanism for the system and improve the photocatalytic ability of 1. We synthesized the bromide analogue, [Re(CO)<sub>3</sub>(1-(1,10)-

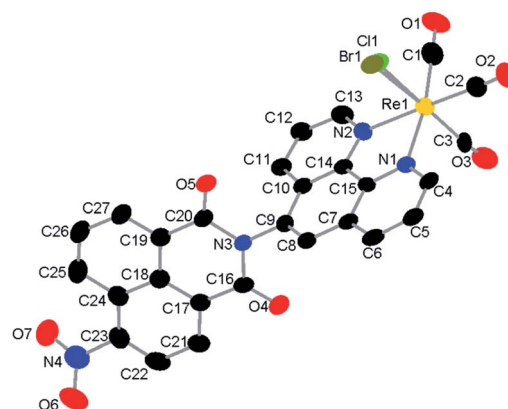


Fig. 1 Single-crystal X-ray diffraction structure of a mixture of 1 and 2. H-atoms and toluene solvent molecule are omitted for clarity. The halido ligand site is modelled as a disorder of Br : Cl, 0.80 : 0.20. Structure deposited as CCDC # 2086581.

<sup>a</sup>Department of Chemistry, Syracuse University, Syracuse, NY 13244, USA. E-mail: jazubiet@syr.edu; rpdoyle@syr.edu

<sup>b</sup>Department of Biomedical and Chemical Engineering, Syracuse University, Syracuse, NY 13244, USA

<sup>†</sup> Electronic supplementary information (ESI) available: Details of the X-ray determinations, bond lengths and angles. CCDC 2086581. For ESI and crystallographic data in CIF or other electronic format see DOI: 10.1039/d1ra08261b



phenanthroline-5-(4-nitro-naphthalimide)Br] (**2**), to evaluate the effect of the halide. Moreover, we obtained crystals of combined **1** and **2** which allowed X-ray diffraction studies and subsequent DFT calculations reported herein. To further drive CO<sub>2</sub> reduction, we replaced TEA with a 2-electron proton donor in the form of 1,3-dimethyl-2-phenyl-2,3-dihydro-1*H*-benzo[*d*]imidazole (BIH), which has been shown to significantly quench the excited state of rhenium(i) photocatalysts thereby yielding better turnover.<sup>11,12</sup> Consequently, we have combined BIH with **1** and **2** in the presence of blue light (450–460 nm) to produce formate in high selectivity over CO.

## 2. Experimental

### 2.1. Materials and methods

CDCl<sub>3</sub>, CD<sub>3</sub>OD, deuterated DMSO, Re(CO)<sub>5</sub>(X) (X = Cl, Br), 2-phenylbenzimidazole, iodomethane, sodium borohydride, sulfuric acid, and diethyl ether were purchased through Sigma Aldrich (Milwaukee, WI, USA). Sodium hydroxide was purchased through Fisher Scientific (Agawam, MA, USA). Methanol (MeOH), ethanol, and dichloromethane (DCM) were purchased through Sigma Aldrich (Milwaukee, WI, USA) and dried over 4 Å molecular sieves (Sigma-Aldrich) in-house to remove water. Barium carbonate (<sup>13</sup>C, 98%+) was purchased from Cambridge Isotope Laboratories, Inc (Tewksbury, MA, USA). 1 M H<sub>2</sub>SO<sub>4</sub> was prepared in-house. A 12 W LED blue light (450–460 nm) was purchased from Abi, USA (Vernon, CA, USA).

<sup>1</sup>H/<sup>13</sup>C NMR were conducted on a Bruker Avance III HD 400 MHz instrument and calibrated to the residual CDCl<sub>3</sub> signal at 7.24 ppm, D1 = 5s for <sup>13</sup>C NMR. FT-IR was carried out on a Nicolet Infrared Spectrophotometer utilizing potassium bromide (KBr) disks. Crystals of [Re(CO)<sub>3</sub>(1-(1,10)phenanthroline-5-(4-nitro-naphthalimide))X] (X = Cl or Br) suitable for single crystal X-ray diffraction studies were only obtained by combining **1** and **2** (1 : 4 by mass) in MeOH/DCM (1 : 9 v/v) and gently layering toluene on top, then sealing the glass vial with a cap and parafilm. Gas chromatography (GC) was conducted on an HP-6890 instrument with a ShinCarbon packed column (Restek, PA, USA), a Flame Ionization Detector (FID), and a methanizer. The FID was calibrated with the standards 1% CO in helium, 1% CO<sub>2</sub> in helium, and 0.5% CH<sub>4</sub> in helium (Airgas). All injections were done with a calibrated 1 mL syringe (Agilent). Ion chromatography was conducted by Intertek Pharmaceuticals (Whitehouse, NJ, USA).

### 2.2. Synthetic procedures

**1** was prepared as previously reported.<sup>10</sup> **2** and BIH were prepared as described below. Re(CO)<sub>5</sub>Br was refluxed in water for 24 h to produce [Re(CO)<sub>5</sub>(H<sub>2</sub>O)<sub>3</sub>Br].<sup>13</sup> The ligand **5-PAN** was prepared as previously reported.<sup>10</sup> [Re(CO)<sub>3</sub>(H<sub>2</sub>O)<sub>3</sub>Br] (0.26 mmol, 105 mg) and **5-PAN** (0.26 mmol, 110 mg) were combined in 30 mL MeOH/DCM (1 : 9 v/v), put under argon, and stirred for 1.5 hours. The solution volume was reduced to half *in vacuo* and diethyl ether was added to precipitate the product. The mixture was centrifuged, and the ether decanted.

The yellow solid noted was collected and dried under vacuum overnight giving 68% yield based on rhenium.

The synthesis of BIH was modified from literature procedures.<sup>14,15</sup> 2-Phenylbenzimidazole (3 g) was mixed with methyl iodide (8 g) in 15 mL of anhydrous MeOH containing NaOH (0.64 g) in a pressure tube. The tube was purged with argon then sealed and heated at 110 °C with stirring for 3 days. After cooling to room temperature, crystals formed. The crude intermediate was filtered and washed with MeOH and dried *in vacuo*. The intermediate was dissolved in 80 mL of anhydrous MeOH and NaBH<sub>4</sub> (1.5 g) was slowly added and stirred for 1 hour under argon. The solvent was then evaporated, and the product was recrystallized in hot ethanol/water 5 : 1 to give white crystals of BIH in 75% yield.

### 2.3. Density functional theory

The electronic structure of the metal complex was simulated with Gaussian 16 Rev C.01 using the B3LYP density functional and the def2-TZVP basis set (all-electron basis functions for atoms except Re, which utilized an effective-core potential). The starting geometry of the complex was taken from the experimental crystallographic structure and the structure was then fully geometry optimized. Solvent effects were included in all calculations using the Polarizable Continuum Model (nonequilibrium for the excited states) with DCM as the specified solvent. Vertical electronic transitions were calculated with time-dependent DFT based on the Tamm-Dancoff approximation (TDA) and included 100 states (singlets and triplets) to explore the possible transitions.

### 2.4. Typical photocatalysis experiments

The following is a typical experiment using **1**. In each sample tested, 0–110.3 equivalences of BIH (0–2 mmol), were premixed in MeOH/DCM (1 : 9 v/v) for 10 min, after which, 13.5 mg (0.018 mmol) of **1** was added. All samples were kept at a 5 mL total reaction volume, irradiated with blue light positioned 1 inch from the reaction vessel and at a 21° angle of incident light. The solution was bubbled with <sup>13</sup>CO<sub>2</sub> evolved *in situ* with 0.500 g Ba<sup>13</sup>CO<sub>3</sub> and 1 M H<sub>2</sub>SO<sub>4</sub> drip for a reaction time of 1.5 hours. For each trial, the drip rate was set such that the Schlenk flask containing Ba<sup>13</sup>CO<sub>3</sub> was full at the end of 1.5 hours and the H<sub>2</sub>SO<sub>4</sub> was well in excess. All catalytic experiments were conducted at least in triplicate under blue light irradiation.

At the end of each trial, liquid products were quantified *via* <sup>13</sup>C NMR. 400 µL of the reaction solution and 250 µL of CDCl<sub>3</sub> were added to an NMR tube and wrapped in aluminium foil until it was ready to be loaded into the NMR. The carbon peaks for BIH and its oxidative product, BI<sup>+</sup>, at ~33 ppm were integrated and set to 1. The H<sup>13</sup>COO<sup>−</sup> peak at ~160 ppm was integrated and quantified with a calibration curve (S12†).

For the detection of gaseous products, **1** and BIH were dissolved in MeOH/DCM (1 : 9 v/v) in a vial with a stir bar and septum cap. The vial was purged with CO<sub>2</sub> for 20 min, then irradiated with blue light for 30 min. A headspace sample was taken with a 1 mL airtight syringe and analysed by GC.

### 3. Results and discussion

#### 3.1. Crystal structure

We sought to obtain a solid-state structure of the catalytic species to facilitate DFT studies. Single-crystal X-ray diffraction analysis revealed that the catalyst crystallizes in the triclinic space group  $P\bar{1}$  with two molecules in the unit cell, one catalyst and one toluene solvate molecule (S8†). Diffraction quality crystals were only obtained from a mix of **1** and **2**; thus, the six-coordinate, octahedral rhenium center includes a disordered halido ligand comprised of Br : Cl, 0.80 : 0.20. The CO ligands are facially coordinated, and the ligand, **5-PAN**, is coordinated to the rhenium center in a bidentate fashion at N1 and N2 (Fig. 1). Detailed description of the structure is included in ESI†.

#### 3.2. Density functional theory

The full geometry optimization yielded a final structure that was in good agreement with the X-ray diffraction results described herein for **1**.

The TDA simulation yielded a predicted a UV/VIS spectrum that matched very well with the experimental data<sup>7</sup> (S9†), indicating the high quality of the calculated orbital energies and participating states. Of particular interest to the photocatalytic behaviour are the four transitions with non-zero oscillator strength in the 400 to 500 nm region. These singlet transitions are detailed in Table 1 and the strongest transition, HOMO–1 → LUMO+1, is visualised in Fig. 2. Other transitions are visualised in the ESI (S10)†.

#### 3.3. Homogenous photocatalysis

Previously reported<sup>10</sup> cyclic voltammetry of **1** indicated sufficient potentials of –0.95 V and –1.18 V for the two-electron reduction of CO<sub>2</sub> to formate (–0.53 V).<sup>4</sup> Thus, **1** was evaluated for catalytic reduction of CO<sub>2</sub> in the presence and absence of blue light (450–460 nm) utilizing <sup>13</sup>C NMR tracking of H<sup>13</sup>COO<sup>–</sup> (typical <sup>13</sup>C NMR included in S11†).

It should be noted that at higher concentrations of BIH (≥1 mmol), the limit of solubility in MeOH/DCM (1 : 9 v/v) in the presence of catalyst was reached, requiring that the BIH be dissolved in the solvent system prior to addition of the catalyst. Without this order of dissolution, the catalytic production of H<sup>13</sup>COO<sup>–</sup> at concentrations of BIH ≥ 1 mmol, was highly

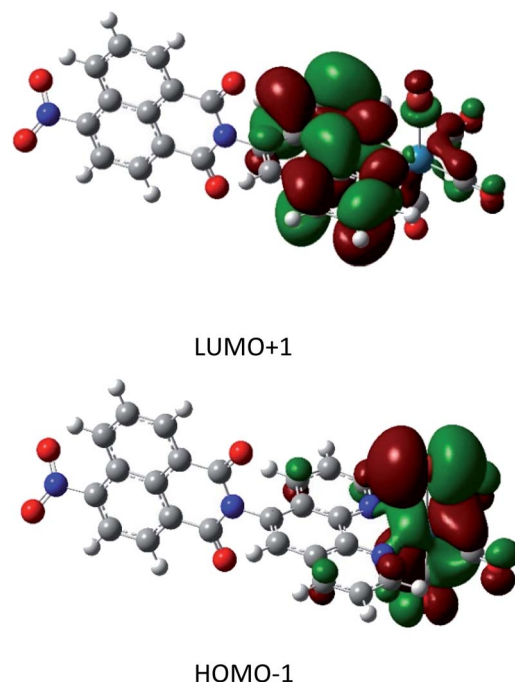


Fig. 2 Orbital density plots for HOMO–1 → LUMO+1. The trend in these excitations is a migration of electron density from the rhenium atom to the ligand.

variable (S12†) as undissolved BIH would be misrepresented in the calibration curve (S13†).

The production of H<sup>13</sup>COO<sup>–</sup> correlates with the addition of excess BIH and blue light in an exponential trend with  $R^2 = 0.9932$  (Fig. 3). A plateau at 9.48 mmol indicated the maximum H<sup>13</sup>COO<sup>–</sup> produced and catalytic saturation. The maximum TN achieved was 533, and turnover frequency (TOF = TN/reaction time) 356 h<sup>–1</sup> at ~110 equivalences of BIH, where the concentration of **1** was 3.62 mM in 5 mL of MeOH/DCM (1 : 9 v/v). **2** was also tested for photocatalytic activity and showed no functional difference from that of **1**, which is in contradiction to some literature reports which have seen halide degradation kinetics differences.<sup>16,17</sup> No formate was detected in the absence of catalyst, BIH, or <sup>13</sup>CO<sub>2</sub> and a negligible amount was detected in the absence of irradiation. The calculated TN of 533 not only surpasses our previously reported **1**/TEA system tenfold but introduces a standard for selective turnover of CO<sub>2</sub> to formate via a mononuclear rhenium(i) catalyst.

Table 1 Singlet transitions of **1**

Excitation wavelength (nm)	Oscillator strength (f)	Main participating orbitals and percentage contributions
470.63	0.0016	HOMO → LUMO+1 (99%)
446.59	0.0680	HOMO–1 → LUMO+1 (90%) HOMO → LUMO+2 (8%)
426.62	0.0345	HOMO–1 → LUMO+1 (8%) HOMO → LUMO+2 (90%)
416.46	0.0172	HOMO–1 → LUMO+2 (98%)



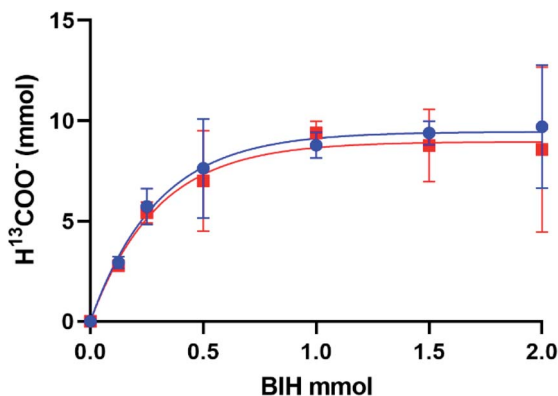


Fig. 3 A plot of  $\text{H}^{13}\text{COO}^-$  (mmol) vs. BIH (mmol) upon blue light (450–460 nm) irradiation of **1** (blue circles,  $R^2 = 0.9932$ ) and **2** (red squares,  $R^2 = 0.9864$ ).  $\text{H}^{13}\text{COO}^-$  increased with an exponential curve fit and reached a plateau at  $y = 9.45$  and  $8.96$  mmol  $\text{H}^{13}\text{COO}^-$ , respectively.

The production of  $\text{HCO}_3^-$  has also been reported appearing on  $^{13}\text{C}$  NMR at  $\sim 158$  ppm.<sup>18</sup> Ion chromatography was therefore conducted and confirmed the identity of formic acid, and lack of carbonate ( $\text{S14}^\dagger$ ). Gaseous products of photocatalysis were also analysed by GC. Trace quantities of CO were detected at a maximum production of 820 nmol CO corresponding to a TN of 0.04 and a TOF of  $0.09 \text{ h}^{-1}$  ( $\text{S15}^\dagger$ ).

### 3.4. Solvent effects

The solvent system MeOH/DCM (1 : 9 v/v) was chosen because it best solubilized all of the reaction components, however MeOH has been reported to enhance the catalytic activity of rhenium diimine complexes by increasing the current in electrolysis experiments.<sup>19</sup> To reveal the effect of MeOH in photocatalysis, experiments were done in the presence of deuterated methanol (along with DMF at typical 1 : 9 v/v ratio used before). When DCM was used as the lone solvent, no formate was produced as evidenced by the loss of the  $\sim 160$  ppm peak in the  $^{13}\text{C}$  NMR and the subsequent emergence of a weak peak at  $\sim 156$  ppm with an integration of 0.6. When MeOH was replaced with  $\text{CD}_3\text{OD}$  ( $\text{CD}_3\text{OD}/\text{DCM}$  1 : 9 v/v), the  $\sim 160$  ppm peak was reduced to an integration of 0.9 ( $\text{S16}^\dagger$ ).

In DMF alone, a common solvent used in rhenium photocatalysis, the formate peak was also not seen in the  $^{13}\text{C}$  NMR and a peak at  $\sim 156$  ppm was seen with an integration of 7.6. It should be noted that the aldehyde carbon of DMF has a peak at 161 ppm, therefore a formate peak could be occluded. Nonetheless, the absence of MeOH resulted in the loss of the signature formate peak at 160 ppm and subsequent appearance of a peak slightly upfield at 156 ppm with greatly diminished integration. When experiments were conducted in MeOH/DCM with no  $\text{CO}_2$ , no carbon signal was observed above 150 ppm, thus the source of the carbon is indeed  $\text{CO}_2$  with no degradation of MeOH itself. MeOH is likely necessary for catalysis as a major proton source.

### 3.5. Photocatalytic mechanism

A variety of factors including solvent, sacrificial donor, and halide ligand can affect the catalytic activity of rhenium diimine

complexes. TLC analysis of the reaction mixture before and after irradiation showed no obvious degradation of the catalyst while BI+ did separate from BIH ( $\text{S17}^\dagger$ ), which was also indicated by NMR. With the addition of BIH, compared to TEA, TN was dramatically increased possibly due to the increase in reductive power and efficient formation of the one-electron reduced catalytic species.<sup>20</sup> When TEMPO was added in equimolar concentrations to BIH, the integration of formate increased, suggesting TEMPO acting as a hydride donor. These observations allude to a hydride mechanism.

A possible mechanism is described (Fig. 4). After reductive quenching of the photoexcited catalyst by BIH, the halide dissociates, and the active catalyst is produced. Literature descriptions of formate generation then propose the formation of a metal hydride intermediate.<sup>4,21–23</sup> Insertion of  $\text{CO}_2$  into the M–H bond then produces the intermediate. This process is in competition with  $\text{H}_2$  generation, which cannot be detected as  $\text{H}_2$  is used as a co-feed gas for the methanizer during GC analysis.

In control experiments in the absence of light, formate was still detected, reaching a maximum amount of 3.20 mmol ( $R^2 = 0.9037$ ) corresponding to a TN of 176 at 110 equivalents of BIH to **1**. To explain the cause of this activity, we noted a literature report of BIH forming a radical cation in the presence of atmospheric  $\text{O}_2$  without irradiation.<sup>24</sup> Under blue light irradiation, BIH alone, in MeOH/DCM (1 : 9 v/v), was able to reduce  $\text{CO}_2$  to formate with a low turnover of 5.7 ( $\text{TN} = [\text{formate}]/[\text{BIH}]$ ). Given the sizable difference in TN from 5.7 to 533, we conclude that any BIH-only mechanism is overridden in the presence of **1** by the hydride mechanism.

The hydride mechanism shown in Fig. 4 only accounts for one BIH per catalytic cycle, whereas the TN is 533 with 110 equivalences of BIH. This suggests multiple mechanisms or components are contributing to the formation of formate herein. Notably, the role of methanol is underappreciated in the proposed mechanism and may account for the enhanced TN.

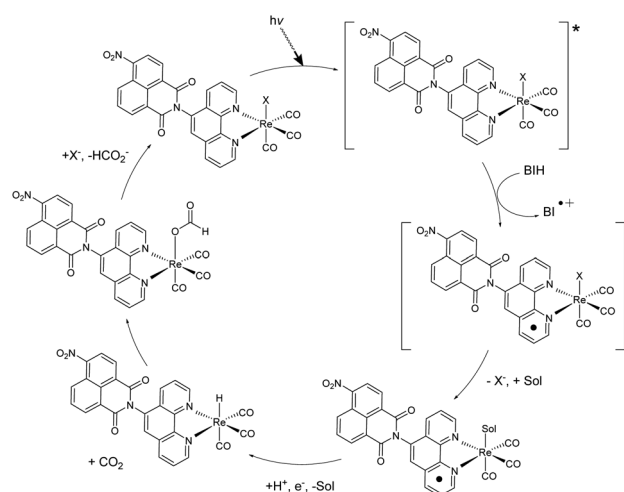


Fig. 4 Proposed hydride mechanism of  $\text{CO}_2$  reduction to formate via **1** or **2**.  $\text{X} = \text{Cl}$  or  $\text{Br}$ ,  $\text{Sol} = \text{DCM}$  or  $\text{MeOH}$ .





## 4. Conclusion

We have reported an extraordinarily improved photocatalytic TN and TOF of a rhenium(i) naphthalimide complex in the presence of the sacrificial electron and proton donor, BIH. The crystal structure of  $[\text{Re}(\text{CO})_3(1-(1,10)\text{phenanthroline-5-(4-nitro-naphthalimide)}) \text{X}]$  (X = Cl or Br) was also reported, indicating facial coordination of three CO ligands, coordination of a halide in the solid state, and bidentate coordination of the naphthalimide-based photosensitizing ligand. The generated  $\text{H}^{13}\text{COO}^-$  increased with excess BIH until a plateau was reached at 9.45 mmol of  $\text{H}^{13}\text{COOH}$ . The corresponding TN at 110 equivalents of BIH to **1** is 533, a tenfold improvement to catalysis using **1** with the sacrificial donor TEA<sup>10</sup> and marked selectivity over CO production, which was observed in nanomole quantities. MeOH/DCM was not only used for its ability to solvate the catalyst, but to optimize the production of  $\text{H}^{13}\text{COO}^-$ ; DCM or DMF lead to diminished  $\text{H}^{13}\text{COO}^-$  signal. While the addition of MeOH improved catalytic activity, the source of the carbon was  $\text{CO}_2$ . To date, this TN is the only reported value for a rhenium(i) mononuclear homogeneous photocatalyst for the selective photoreduction of  $\text{CO}_2$  to formate.

**1** is an exciting complex to apply towards  $\text{CO}_2$  reduction as the field is developing new methods of synthesizing valuable chemicals while maintaining sustainable and mild conditions. Notably, at similar reduction potentials to those reported for **1**,<sup>10</sup> electrosynthesis of methylamine from  $\text{CO}_2$  and  $\text{NO}_3^-$  was recently reported<sup>25</sup> and will be explored with **1**/BIH. Further mechanistic studies are needed to elaborate on the complex mechanism at play, especially the role of MeOH. The complex itself is an interesting avenue for future investigation in terms of development through derivatization of the bidentate naphthalimide ligand and optimization of the solvent system to better harness the quenching capabilities of BIH.

## Conflicts of interest

There are no conflicts to declare.

## Notes and references

- 1 D. Archer, *J. Geophys. Res.*, 2005, **110**, C09S05.
- 2 E. T. Sundquist, *Quat. Sci. Rev.*, 1991, **10**, 283–296.
- 3 G. Shaffer, S. M. Olsen and J. O. P. Pedersen, *Nat. Geosci.*, 2009, **2**, 105–109.
- 4 A. J. Morris, G. J. Meyer and E. Fujita, *Acc. Chem. Res.*, 2009, **42**, 1983–1994.
- 5 H. Takeda and O. Ishitani, *Coord. Chem. Rev.*, 2010, **254**, 346–354.
- 6 L. Q. Qiu, K. H. Chen, Z. W. Yang and L. N. He, *Green Chem.*, 2020, **22**, 8614–8622.
- 7 D. Mellmann, P. Sponholz, H. Junge and M. Beller, *Chem. Soc. Rev.*, 2016, **45**, 3954–3988.
- 8 J. Eppinger and K. W. Huang, *ACS Energy Lett.*, 2017, **2**, 188–195.
- 9 L. Wang, S. Nitopi, A. B. Wong, J. L. Snider, A. C. Nielander, C. G. Morales-Guio, M. Orazov, D. C. Higgins, C. Hahn and T. F. Jaramillo, *Nat. Catal.*, 2019, **2**(8), 702–708.
- 10 D. R. Case, A. Spear, A. F. Henwood, M. Nanao, S. Dampf, T. M. Korter, T. Gunnlaugsson, J. Zubieta and R. P. Doyle, *Dalton Trans.*, 2021, **50**, 3479–3486.
- 11 Y. Tamaki, K. Koike, T. Morimoto and O. Ishitani, *J. Catal.*, 2013, **304**, 22–28.
- 12 P. Lang, M. Pfrunder, G. Quach, B. Braun-Cula, E. G. Moore and M. Schwalbe, *Chem.–Eur. J.*, 2019, **25**, 4509–4519.
- 13 N. Lazarova, S. James, J. Babich and J. Zubieta, *Inorg. Chem. Commun.*, 2004, **7**, 1023–1026.
- 14 I. S. H. Lee, E. H. Jeoung and M. M. Kreevoy, *J. Am. Chem. Soc.*, 1997, **119**, 2722–2728.
- 15 A. Rosas-Hernández, C. Steinlechner, H. Junge and M. Beller, *Green Chem.*, 2017, **19**, 2356–2360.
- 16 J. Hawecker, J. Lehn and R. Ziessel, *Helv. Chim. Acta*, 1986, **69**, 1990.
- 17 J. Hawecker, J.-M. Lehn and R. Ziessel, *Chem. Commun.*, 1983, 536–538.
- 18 Y. Tamaki, K. Koike, T. Morimoto, Y. Yamazaki and O. Ishitani, *Inorg. Chem.*, 2013, **52**, 11902–11909.
- 19 L. Rotundo, E. Azzi, A. Deagostino, C. Garino, L. Nencini, E. Priola, P. Quagliotto, R. Rocca, R. Gobetto and C. Nervi, *Front. Chem.*, 2019, **7**, 417.
- 20 L. Rotundo, D. C. Grills, R. Gobetto, E. Priola, C. Nervi, D. E. Polyansky and E. Fujita, *ChemPhotoChem*, 2021, **5**, 526–537.
- 21 N. D. Loewen, T. V. Neelakantan and L. A. Berben, *Acc. Chem. Res.*, 2017, **50**, 2362–2370.
- 22 D. B. Cluff, A. Arnold, J. C. Fettinger and L. A. Berben, *Organometallics*, 2018, **38**, 1230–1235.
- 23 D. W. Cunningham and J. Y. Yang, *Chem. Commun.*, 2020, **56**, 12965–12968.
- 24 E. Hasegawa, S. Nakamura, K. Oomori, T. Tanaka, H. Iwamoto and K. Wakamatsu, *J. Org. Chem.*, 2021, **86**, 47.
- 25 Y. Wu, Z. Jiang, Z. Lin, Y. Liang and H. Wang, *Nat. Sustain.*, 2021, **4**, 725–730.

