


 Cite this: *RSC Adv.*, 2022, 12, 31093

# Rare-earth-incorporated ternary $\text{Ce}_x\text{Cd}_{1-x}\text{S}$ quantum dot-sensitized solar cells

 Eva Natalia Chiristina,<sup>a</sup> Siti Utari Rahayu,<sup>ab</sup> Auttasit Tubtimtae,<sup>c</sup> Jen-Bin Shi<sup>d</sup> and Ming-Way Lee<sup>id</sup>\*<sup>a</sup>

This work presents a new absorber material – rare-earth-doped ternary  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  quantum dots (QDs) – for solar cells.  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  QDs were synthesized by partially replacing the cation Cd in the binary sulfide CdS with Ce using a two-step solution processing process. First, Ce–S QDs were grown on a mesoporous  $\text{TiO}_2$  electrode. Second, Cd–S QDs were grown on top of the Ce–S QDs. Post annealing transformed the Ce–S/Cd–S double layers into the ternary  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  structure. The synthesized  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  QDs have the same hexagonal structure as the host CdS, with an average particle size of 11.8 nm. X-ray diffraction reveals a slight lattice expansion in  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  relative to CdS. The band gap  $E_g$  of  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  exhibits a monotonic decrease from 2.40 to 2.24 eV with increasing Ce content  $x$  from 0 to 0.20, indicating an  $E_g$  tunable by controlling the dopant content.  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  QDSCs were fabricated with a polysulfide electrolyte and CuS counter electrode. The best  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  cell yields a  $J_{sc}$  of 8.16  $\text{mA cm}^{-2}$ , a  $V_{oc}$  of 0.73 V, a fill factor of 62.5%, and an efficiency of 3.72% under 1 sun. The efficiency increases to 4.24% under the reduced light intensity of 0.25 sun. The efficiency of the  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  cell is 25% higher than that of the host CdS cell. The improved performance is attributed to the broader absorption range resulting from Ce doping. These results suggest the potential of using Ce as a dopant in CdS to tune the  $E_g$  and improve the photovoltaic performance.

 Received 19th September 2022  
 Accepted 24th October 2022

DOI: 10.1039/d2ra05905c

[rsc.li/rsc-advances](http://rsc.li/rsc-advances)

## 1 Introduction

The increasing demand for energy and the limited availability of fossil fuels encourage scientists and researchers worldwide to develop cost-effective renewable energy devices, one of them being photovoltaic cells. Amongst many types of photovoltaic cells, quantum dot-sensitized solar cells (QDSCs) are promising photovoltaic cells. A QDSC contains three components: a photoanode, an electrolyte, and a counter electrode. The photoanode consists of a mesoporous  $\text{TiO}_2$  matrix coated with a layer of semiconductor in the form of quantum dots (QDs) as the light absorber. There are several advantages of employing QDs as the absorber, such as high extinction coefficient,<sup>1</sup> tunable bandgap,<sup>2</sup> efficient multiple exciton generation (MEG),<sup>3</sup> and increased stability toward heat, moisture, and light.<sup>4</sup> Besides, QDs can be obtained *via* the solution processing method, making QDSCs a low-cost alternative to Si-based photovoltaic cells. Furthermore, the MEG in QDSC could allow the power

conversion efficiency (PCE) to go beyond the Shockley–Queisser limit. Yet, some challenges must be inspected to reach the maximum theoretical PCE above 40%.<sup>5</sup>

An important criterion for a good semiconductor absorber material is that its bandgap should be near 1.4 eV to produce the maximal output of the Shockley–Queisser limit.<sup>6</sup> However, there are a limited number of semiconductors in nature with the ideal Shockley–Queisser gap. It would be desirable to tune the bandgap artificially to be closer to the ideal bandgap. Currently, metal sulfides are the most widely studied semiconductor materials for QDSCs. There are three ways to tune the bandgap of a metal sulfide by controlling the composition of (a) cation alloy, (b) anion alloy, and (c) cation–anion alloy. The incorporation of Sn into  $\text{Sb}_2\text{S}_3$  leads to a tunable optical range of 300–800 nm in cation alloyed semiconductor  $\text{Sn}_x\text{Sb}_{2-y}\text{S}_3$ .<sup>7</sup> The absorption range of the cation alloyed semiconductor  $\text{Zn}_x\text{Cd}_{1-x}\text{S}$  is tunable from 474 to 391 nm by controlling the composition ratios of the two cation elements Zn and Cd.<sup>8</sup>

CdS has been one of the most widely studied materials for solar cells among all metal sulfides. For example, the incorporation of CdS QDs in a blend of P3HT and PCBM for hybrid bulk heterojunction polymer solar cells increased the efficiency from 2.95% to 4.41%.<sup>9</sup> An advantage of CdS is the  $V_{oc}$  ~0.6–0.7 V, a relatively high photovoltage for a QDSC. This high  $V_{oc}$  is because of the relatively large band gap of 2.4 eV. However, the large  $E_g$  also yields a narrow absorption band of 300–500 nm,

<sup>a</sup>Department of Physics and Institute of Nanoscience, National Chung Hsing University, Taichung, 402, Taiwan. E-mail: mwl@phys.nchu.edu.tw

<sup>b</sup>Program of Study in Physics, Universitas Sumatera Utara, Medan 20155, Sumatera Utara, Indonesia

<sup>c</sup>Department of Physics, Faculty of Liberal Arts and Science, Kasetsart University Kamphaeng Saen Campus, Nakhon Pathom 73140, Thailand

<sup>d</sup>Department of Electronic Engineering, Feng Chia University, Taichung, 40724, Taiwan


leading to inefficient light absorption and low solar cell efficiency. The problem of the narrow absorption band can be improved by using one of the band tuning strategies discussed above. Herein, the composition control of cation alloying is adopted by incorporating a second metal into CdS to obtain a tunable band gap in CdS.

The use of rare-earth metals as solar absorbers in QDSCs has been less explored. Recently, Gd doping into CdS has been reported to lower the band gap and produces an enhanced efficiency.<sup>10</sup> The result suggests the potential of using other rare earth metals to improve QDSCs. Based on the empirical results, the band gap of a semiconductor is roughly inversely proportional to the lattice constant: a semiconductor with a small lattice constant would have a larger band gap.<sup>11</sup> The ionic radius of  $\text{Ce}^{3+}$  (102 pm) is larger than that (95 pm) of  $\text{Cd}^{2+}$ . Therefore, substituting  $\text{Cd}^{2+}$  with  $\text{Ce}^{3+}$  would increase the lattice constant and produce a reduced band gap, increasing the light absorption range.

In this study, a fraction of the cation  $\text{Cd}^{2+}$  in the binary CdS is replaced by  $\text{Ce}^{3+}$ , forming ternary  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  quantum dots.  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  liquid-junction quantum dot-sensitized solar cells (QDSCs) were fabricated using the synthesized QDs. The photovoltaic performance under different successive ionic layer adsorption and reaction (SILAR) cycles and sun intensities are examined. The effects of Ce incorporation were investigated using XRD and XPS measurements. In addition, the transition of the band gap with Ce content toward a longer wavelength was studied *via* UV-Vis and external quantum efficiency (EQE) measurements. There is a slight increase in the optical absorption range of  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  compared to pure CdS. The short-circuit current density, open-circuit voltage, and fill factor all increase after Ce doping, leading to an ~24% increase in the power conversion efficiency (PCE). To our best knowledge, this is the first work on  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  QDSCs. The results show the clear benefit of Ce incorporation to CdS in improving the performance of CdS QDSCs.

## 2 Experimental section

Fig. 1(a) shows a schematic diagram of a  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  QDSC, containing three major components: a photoanode, an electrolyte, and a counter electrode. Details of preparation for each component are described as follows.

### 2.1. Preparation of $\text{TiO}_2$ electrodes

The  $\text{TiO}_2$  electrode consisted of a three-layer structure: a blocking layer<sup>12</sup> (thickness: ~50–70 nm), a mesoporous  $\text{TiO}_2$  layer (mp- $\text{TiO}_2$ , thickness: 10–12  $\mu\text{m}$ , particle size ~30 nm), and a  $\text{TiO}_2$  scattering layer<sup>13</sup> (thickness: ~5  $\mu\text{m}$ , particle size ~300–400 nm). FTO glass was first cleaned using acetone, methanol, and DI water sequentially for 3 min each with an ultrasonic cleaner. Then, 50  $\mu\text{l}$  of the prepared 0.247 M titanium(IV) isopropoxide (TTIP) solution was spin-coated on top of the FTO glass (area ~1.5 cm  $\times$  1.2 cm), followed by heating on a hot plate at 190  $^\circ\text{C}$  for 5 min. Next, the mp- $\text{TiO}_2$  layer sample was prepared by pasting commercial  $\text{TiO}_2$  paste (DSL 30NR-T, GreatCell Solar) using the doctor blade method, then heated at 125  $^\circ\text{C}$  for 10 min. After cooling down, the sample was coated

with a  $\text{TiO}_2$  scattering layer, 0.5 cm in diameter, by applying the same doctor blade method. The prepared  $\text{TiO}_2$  electrode was finally annealed at 500  $^\circ\text{C}$  for 90 min.<sup>14</sup> The active area of a fabricated  $\text{TiO}_2$  electrode is a circle with a diameter of 0.3 cm. The function of each layer is as follows: the  $\text{TiO}_2$  blocking layer prevents the photoelectrons in the FTO glass substrate from being in direct contact with holes in the electrolyte; the mesoporous  $\text{TiO}_2$  layer serves as the three-dimensional frame for QD deposition as well as electron conduction layer; the  $\text{TiO}_2$  scattering layer increases the light-harvesting capacity by collecting the scattered light with the layer.

### 2.2. Synthesis of $\text{Ce}_x\text{Cd}_{1-x}\text{S}$ QDs

Ce-incorporated CdS QDs were grown onto an mp- $\text{TiO}_2$  electrode using a two-stage successive ionic layer adsorption and reaction (SILAR) method as described in several earlier reports.<sup>15–17</sup> First, a layer of Ce–S QDs was grown on the  $\text{TiO}_2$  electrode. Second, a layer of Cd–S QDs was grown on top of the Ce–S QDs. A post-annealing process transforms the Ce–S/Cd–S structure into the ternary  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  phase. A Ce–S SILAR cycle consisted of dipping a  $\text{TiO}_2$  electrode into a 0.1 M  $\text{Ce}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}$  ethanol solution for 60 s, followed by rinsing with ethanol and drying on a hot plate at 40  $^\circ\text{C}$ . Then, the sample was immersed in a 0.1 M  $\text{Na}_2\text{S} \cdot 9\text{H}_2\text{O}$  methanol/DI water (1 : 1, v/v) solution for 150 s and subsequently rinsed with methanol and dried on a hot plate at 40  $^\circ\text{C}$ . Finally, the substrate was immersed again in the  $\text{Ce}^{3+}$  solution for 1 min. This two-step immersing process formed one SILAR cycle for Ce–S seeds. The process was repeated  $n$  times ( $n = 1$  to 4) to obtain the desired amount of Ce–S material on the  $\text{TiO}_2$  electrode. For the Cd–S SILAR deposition, the Ce–S-coated  $\text{TiO}_2$  electrode was dipped into a 0.1 M  $\text{Cd}(\text{CH}_3\text{COO})_2 \cdot 2\text{H}_2\text{O}$  ethanol/DI water (1 : 1, v/v) solution for 120 s, followed by rinsing with ethanol and drying at 40  $^\circ\text{C}$ . Next, it was immersed in a 0.1 M  $\text{Na}_2\text{S} \cdot 9\text{H}_2\text{O}$  methanol/DI water (1 : 1, v/v) solution for 150 s, then rinsed with methanol and dried at 40  $^\circ\text{C}$ . This two-dipping process formed one SILAR cycle for Cd–S seeds. As reported in the literature, the optimal number of SILAR cycles for CdS had been determined to be seven;<sup>18</sup> hence, the number of CdS SILAR cycles was fixed at six herein to make room to accommodate the incorporated Ce in this work. Lastly, the double-layer Ce–S/Cd–S seeds were annealed at 250  $^\circ\text{C}$  for 10 min, forming ternary  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  QDs. The sample that went through  $n$  cycles of Ce–S seeds and six cycles of Cd–S seeds is denoted as  $\text{CeS}(n)/\text{CdS}(6)$  herein.

The synthesized  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  QDs were coated with a ZnS film layer to reduce carrier recombination using the SILAR method. The prepared sample was first immersed in a  $\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$  ethanol solution for 60 s, then rinsed with ethanol and dried at 40  $^\circ\text{C}$ . It was then dipped in the  $\text{Na}_2\text{S} \cdot 9\text{H}_2\text{O}$  methanol/DI water (1 : 1, v/v) solution for 60 s, rinsed with methanol, and dried at 40  $^\circ\text{C}$ . This two-step process was repeated for two cycles to obtain the ZnS passivation layer.

### 2.3. Solar cell fabrication

The  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  sensitized solar cells were fabricated by assembling the prepared  $\text{TiO}_2$  electrode with a CuS counter electrode



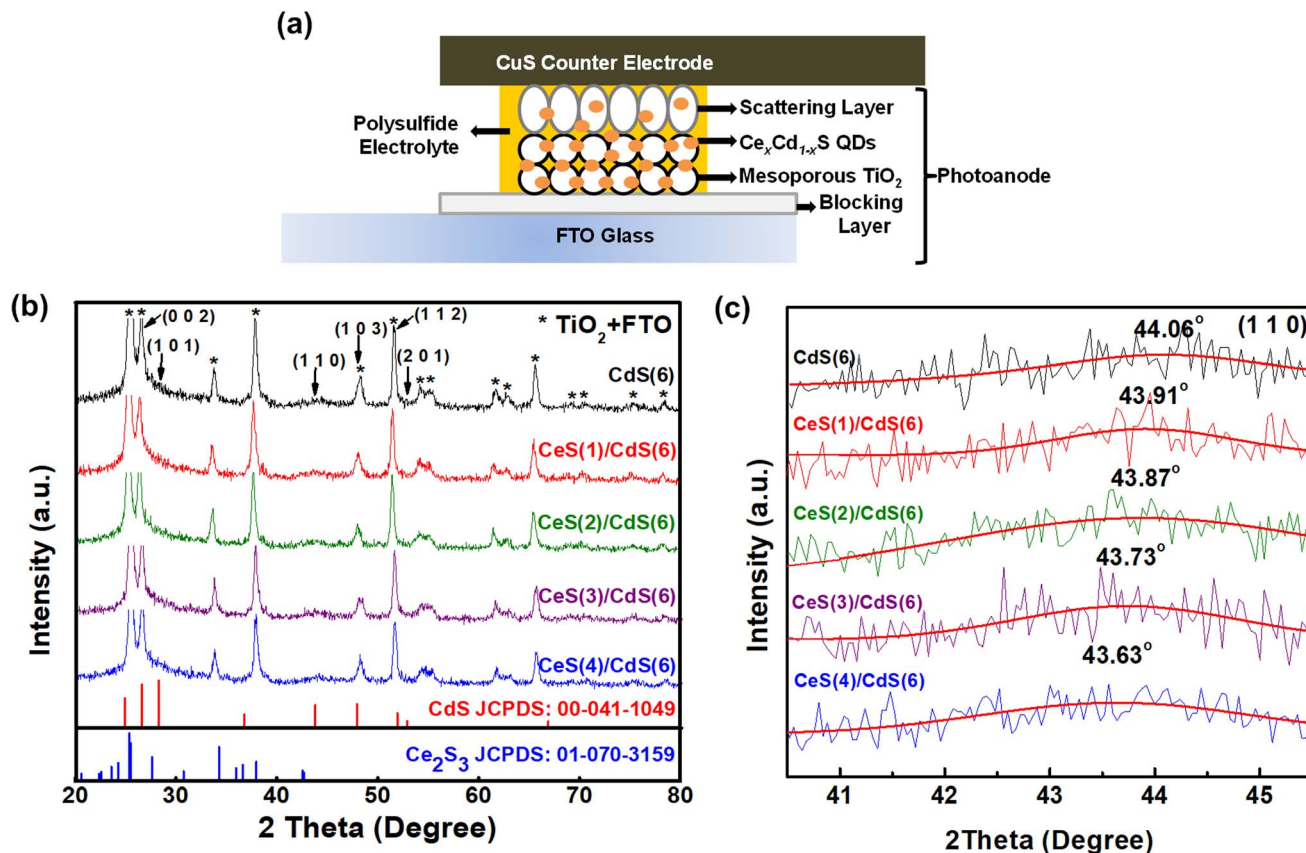


Fig. 1 (a) A schematic diagram of a  $Ce_xCd_{1-x}S$  QDSC, (b) XRD patterns of CdS and four  $Ce_xCd_{1-x}S$  samples prepared on a mesoporous  $TiO_2$ /FTO glass substrate with different SILAR cycles, and (c) enlarged XRD (1 1 0) peaks of five samples with various Ce–S SILAR cycles.

using a parafilm spacer (thickness  $\sim 190 \mu m$ ). The CuS counter electrode was fabricated through the chemical bath deposition (CBD) method. In brief, three pieces of pre-cleaned FTO glass were placed horizontally in a 40 ml aqueous solution (consisting of 1.564 g of  $CuSO_4 \cdot 5H_2O$ , 3.968 g of  $Na_2S_2O_3$ , and 0.969 g of  $CH_4N_2O$ ) at  $55^\circ C$  for 70 min.<sup>19</sup> The polysulfide electrolyte, consisting of 1 M  $Na_2S$ , 2 M S, and 0.2 M KCl in methanol/water (7 : 3 by volume), was injected into the space between the  $TiO_2$  electrode and the CuS counter electrode before  $I-V$  measurements.

#### 2.4. Material characterization

The structural and morphological characteristics of the synthesized QDs were studied using an X-ray diffractometer (XRD, Bruker D8) and a transmission electron microscope (TEM, JEOL JEM-2010). X-ray photoelectron spectroscopy (XPS) was measured using a ULVAC-PHI 5000 with Ar-heated treatment. Optical spectra were measured using a Hitachi U-2800A UV-Vis spectrophotometer.  $I-V$  measurements were conducted using a Keithley 2400 source meter with  $100 mW cm^{-2}$  light illumination from a 150 W Xe lamp. A metal mask defined the cell's active area to be a circle of 3 mm in diameter. External quantum efficiency (EQE) spectra were collected using an Acton monochromator with a 250 W tungsten halogen lamp (without

white-light biasing). A batch of three to six samples was measured for each experiment to ensure data consistency.

## 3 Results and discussion

### 3.1. X-ray diffraction

The structural property of Ce-incorporated CdS quantum dots (QDs) under different SILAR cycles was analyzed by XRD. Fig. 1(b) displays the XRD patterns of pure CdS and four  $Ce_xCd_{1-x}S$  samples. The pure CdS QDs exhibit the hexagonal structure with the reference JCPDS number 00-041-1049. The CdS pattern can be indexed to the Miller indices (002), (101), (110), (103), (112), and (201). Many prominent peaks due to the  $TiO_2$  matrix or FTO glass are also observed in the spectrum. These background peaks are much more intense than CdS because the amount of  $TiO_2$  and FTO material in the photoanode is much larger than that of the CdS QDs. For comparison, the XRD peaks of the two starting materials – CdS and  $Ce_2S_3$  – are shown at the bottom panel. The  $Ce_xCd_{1-x}S$  QDs maintain the hexagonal structure of CdS with no impurity phase arising from Ce, CeS, or  $Ce_2S_3$ ; similar results were obtained from other reports using different growth techniques.<sup>20–22</sup> Many  $Ce_xCd_{1-x}S$  peaks overlap strongly with the background  $TiO_2$  peaks and are difficult to discern. Only the (110) index around the angle of  $44^\circ$  is well separated from the background peaks. Fig. 1(c) shows the







**Table 1** XPS analysis of the atomic percentage of CdS and  $Ce_xCd_{1-x}S$  QDs with different SILAR cycles

Sample	Ce (%)	Cd (%)	S (%)	Ce : Cd ratio	Ce content (x)
CeS(0)/CdS(6)	0	62.5	37.5	—	0
CeS(1)/CdS(6)	2.6	65.7	31.7	1 : 25	0.04
CeS(2)/CdS(6)	3.6	60.0	36.4	1 : 17	0.05
CeS(3)/CdS(6)	5.8	60.0	34.2	1 : 10	0.10
CeS(4)/CdS(6)	10.7	57.1	32.2	1 : 5	0.20


### 3.3. Transmission electron microscopy

Fig. 3(a) displays a TEM picture of a bare  $TiO_2$  film. The  $TiO_2$  particles are in a long rectangular shape with an average size of 30 nm. Fig. 3(b) depicts a TEM picture of  $Ce_{0.04}Cd_{0.96}S$  QDs coated over the pores of mesoporous  $TiO_2$ . The  $Ce_{0.04}Cd_{0.96}S$  QDs, indicated by red arrows in the figure, are approximately round in shape and are randomly dispersed over the surface of  $TiO_2$  nanoparticles. The particle sizes of  $Ce_{0.04}Cd_{0.96}S$  QDs are 6–17 nm, with an average particle size of 11.8 nm (Fig. 3(c)), while the  $d$ -spacing (inset) of 0.203 nm is in good agreement

with the database of host CdS (JCPDS number 00-041-1049). The selected area electron diffraction (SAED) pattern of  $Ce_{0.04}Cd_{0.96}S$  QDs (Fig. 3(d)) matches the hexagonal structure of CdS nanocrystals with the Miller indices marked in the figure. The  $Ce_{0.04}Cd_{0.96}S$  QDs have the same crystallographic structure as the host material CdS. This result agrees with the XRD patterns of  $Ce_xCd_{1-x}S$  shown in Fig. 1(b).

### 3.4. Optical spectra

Fig. 4 displays the optical absorption spectra of  $Ce_xCd_{1-x}S$  QDs. The transmission spectra  $T(\lambda)$  were taken by rationing the light intensity transmitted through a  $T(\lambda)$   $Ce_xCd_{1-x}S$  sample to that of a mesoporous  $TiO_2$  background (Fig. 4(a)). The transmission decreases with increasing Ce-S SILAR cycles, implying increasing light absorption due to the increasing amount of Ce incorporation. Fig. 4(b) displays the absorbance spectra  $A(\lambda) = -\log_{10} T(\lambda)$ . The absorbance  $A$  also increases with increasing the Ce-S SILAR cycle, which again indicates that the incorporation of Ce increases the light absorption capacity of the sample. Fig. 4(c) shows the Tauc plots  $(Ah\nu)^2$  vs.  $h\nu$  for the five samples, where  $h$  is the Planck constant and  $\nu$  is the photon frequency. The optical band gap  $E_{g,op}$  was determined by taking

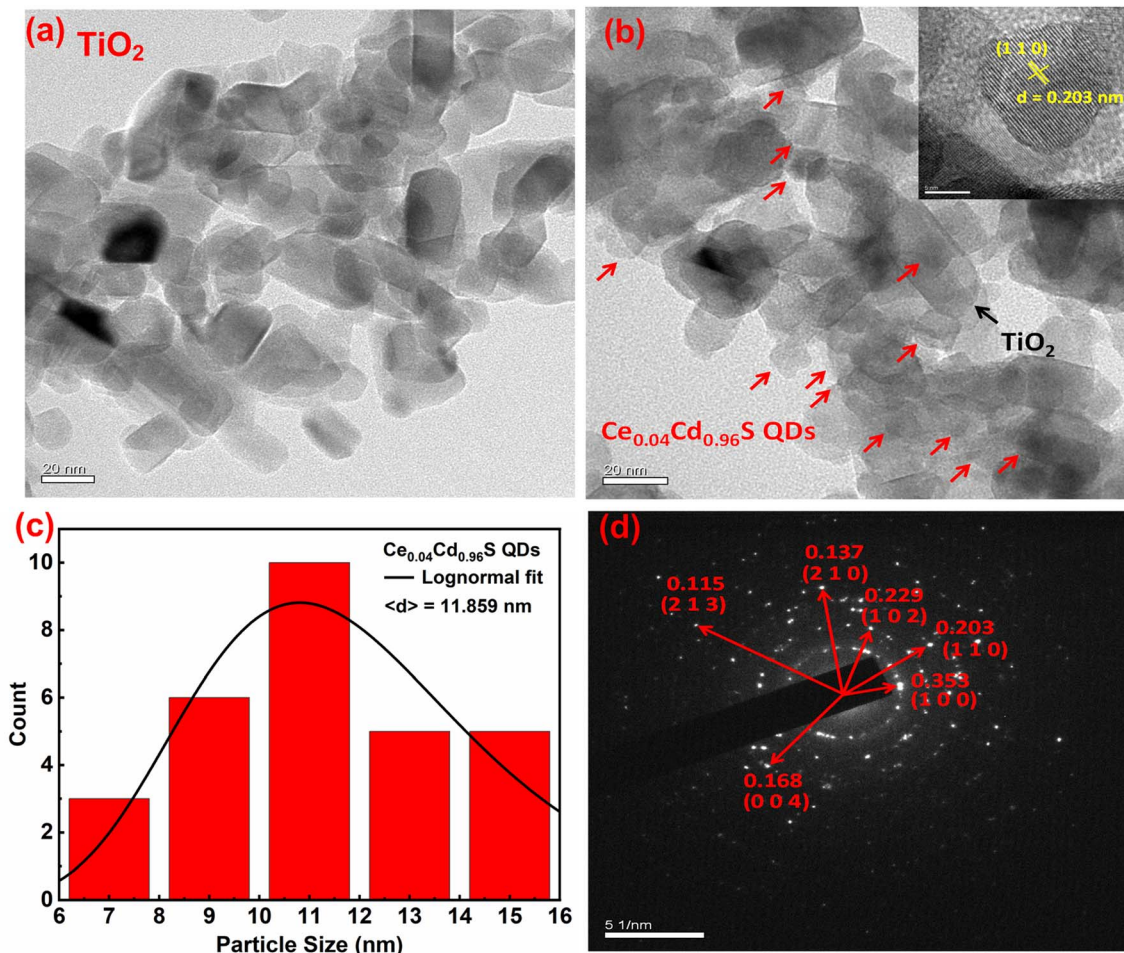

**Fig. 3** TEM images of (a) a bare mp- $TiO_2$ , (b)  $Ce_{0.04}Cd_{0.96}S$  QDs on mp- $TiO_2$  (inset picture shows the lattice fringe of  $Ce_{0.04}Cd_{0.96}S$  QDs), (c) distribution of particle size of  $Ce_{0.04}Cd_{0.96}S$  QDs, and (d) selective area diffraction (SAED) of  $Ce_{0.04}Cd_{0.96}S$  QDs.



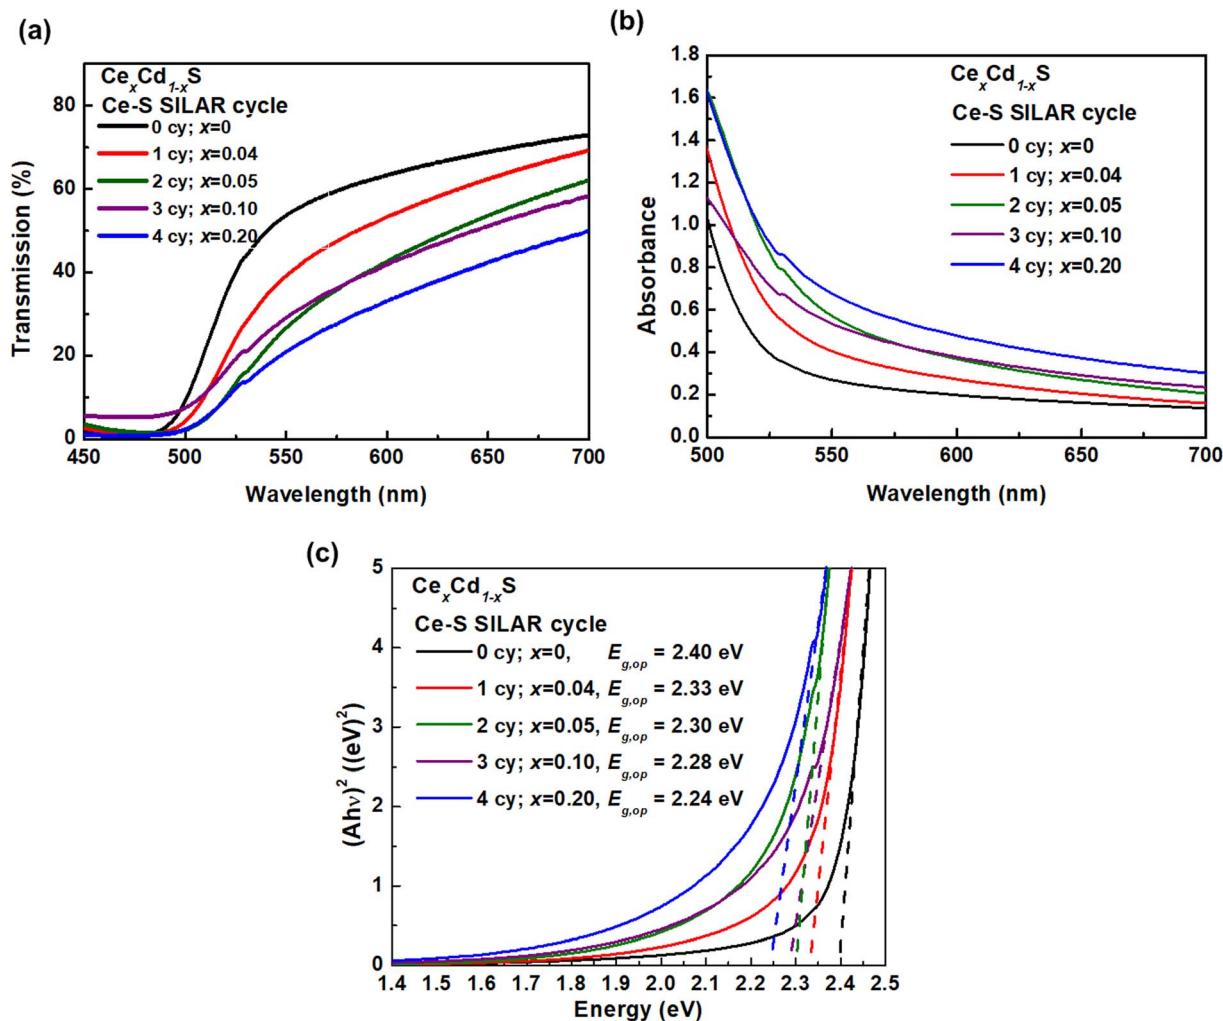


Fig. 4 Optical spectra: (a) transmission, (b) absorbance, and (c) Tauc plots  $(Ah\nu)^2$  vs.  $h\nu$  of  $Ce_xCd_{1-x}S$  with various Ce content.

the  $x$ -intercept of an extrapolated Tauc plot. The  $E_{g,op}$  exhibits a monotonic decrease with increasing number of Ce-S SILAR cycles: 2.40 (CdS), 2.33 (CeS(1)/CdS(6)), 2.30 (CeS(2)/CdS(6)), 2.28 (CeS(3)/CdS(6)) and 2.24 eV (CeS(4)/CdS(6)). The substitution of  $Cd^{2+}(0.95 \text{ \AA})$  by the larger  $Ce^{3+}(1.14 \text{ \AA})$  leads to a lattice expansion, which results in a reduced  $E_g$ . Increasing SILAR cycles produces larger crystalline size, which also leads to a lower  $E_g$ . The  $E_{g,op}$  of the pure CdS sample is 2.40 eV, consistent with earlier reports.<sup>27–29</sup> The sample CeS(1)/CdS(6) with the best photovoltaic performance (discussed below) has an  $E_{g,op}$  of 2.33 eV. This result is consistent with the report by Zhan *et al.* that the best Ce-doped CdS solar cell on  $TiO_2$  nanorods has an  $E_{g,op}$  of 2.35 eV.<sup>21</sup>

### 3.5. Photovoltaic performance

Fig. 5(a) displays the  $I$ - $V$  curves of six  $Ce_xCd_{1-x}S$  QDSCs with various numbers of Ce-S SILAR cycles. Table 2 lists the photovoltaic parameters, including the short-circuit current density ( $J_{sc}$ ), open-circuit voltage ( $V_{oc}$ ), fill factor (FF), and efficiency. The pure, undoped CdS solar cells (sample no. 1) have an efficiency

of 2.98%, with a  $J_{sc}$  of  $7.64 \text{ mA cm}^{-2}$ , a  $V_{oc}$  of 0.66 V, and an FF of 59.0%. The incorporation of Ce into Cd-S (sample no. 2, CeS(1)/CdS(6)) improves the  $J_{sc}$  to  $8.28 \text{ mA cm}^{-2}$ , the  $V_{oc}$  to 0.70 V, and FF of 61.7%, yielding an efficiency of 3.56% (an 18.8% increase over that of CdS). To further improve the performance, the best cell (sample no. 2) was coated with a ZnS passivation layer. The ZnS treatment improves the efficiency to 3.71% (sample no. 6), a modest improvement over that (3.56%) of the untreated cell. The enhanced performance of  $Ce_xCd_{1-x}S$  samples is attributed to the broader absorption range, as revealed in the optical results shown in Fig. 4. However, a further increase in the Ce content does not improve the performance. The efficiency decreases from 3.37 to 1.28% as the SILAR cycle increases from 2 to 4 (sample no. 3–5). This is explained by the excess amount of material loading in the matrix of a mesoporous  $TiO_2$  could impede the electrolyte flow inside the cell, hampering the redox reaction.

The synthesized  $Ce_xCd_{1-x}S$  QDs were coated with a ZnS film layer to reduce carrier recombination using the SILAR method. As shown in the schematic diagram of Fig. 5(c), the high conduction band level of ZnS blocks the photoelectrons in the





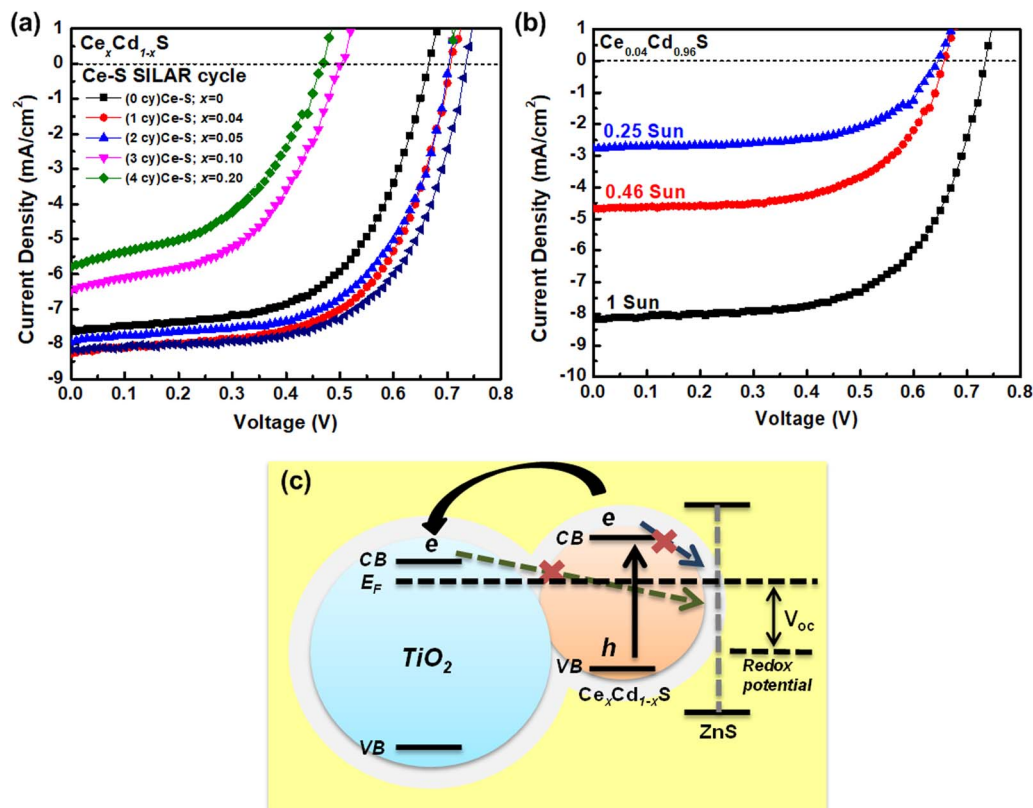


Fig. 5  $I$ - $V$  curves of  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  QDSCs with (a) different SILAR cycles and ZnS passivation treatment and (b) different sun intensities, and (c) the schematic diagram of electron transfer from  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  into  $\text{TiO}_2$ .

conduction band of  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  QDs from recombination with holes in the electrolyte.

The photovoltaic performance of SILAR-prepared QDSCs can be enhanced by measuring  $I$ - $V$  curves under reduced sun intensities. Fig. 5(b) displays the  $I$ - $V$  curves under three reduced sun intensities: 1, 0.46, and 0.25 sun. Table 3 lists the photovoltaic parameters. As shown, lowering sun intensity generates improved photovoltaic efficiency, except for  $V_{oc}$ . The efficiency increases from 3.72% (1 sun) to 4.24% (0.25 sun), a 14% enhancement. The improved photovoltaic performance of the cells can be understood from the fact that the use of SILAR to grow quantum dots in the mesoporous  $\text{TiO}_2$  results in

nanoparticles with many surface defects, which act as recombination centers for the electron-hole pairs;<sup>33</sup> therefore, by lowering the sun intensity (fewer photons), the number of photocarriers is reduced, leading to reduced carrier recombination and improved photovoltaic performance. This result indicates that  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  QDSCs work more efficiently under low light.

### 3.6. External quantum efficiency (EQE)

Fig. 6 displays the EQE spectra for the pure CdS and  $\text{Ce}_{0.04}\text{Cd}_{0.96}\text{S}$  QDSCs. The  $\text{Ce}_{0.04}\text{Cd}_{0.96}\text{S}$  cell exhibits a broader spectral range (350–630 nm) than that (350–610 nm) of CdS. The

Table 2 Photovoltaic performance of  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  QDSCs and the comparison with other similar systems


No	Sample	$J_{sc}$ ( $\text{mA cm}^{-2}$ )	$V_{oc}$ (V)	Fill factor (%)	Efficiency (%)
1	CdS <sup>a</sup>	7.64 ± 0.30	0.66 ± 0.01	59.0 ± 0.57	2.98 ± 0.02
2	$\text{Ce}_{0.04}\text{Cd}_{0.96}\text{S}^a$	8.28 ± 0.63	0.70 ± 0.00	61.7 ± 6.58	3.56 ± 0.11
3	$\text{Ce}_{0.05}\text{Cd}_{0.95}\text{S}^a$	7.94 ± 0.74	0.65 ± 0.00	65.3 ± 3.14	3.37 ± 0.15
4	$\text{Ce}_{0.10}\text{Cd}_{0.90}\text{S}^a$	6.48 ± 0.52	0.50 ± 0.04	51.2 ± 1.30	1.66 ± 0.05
5	$\text{Ce}_{0.20}\text{Cd}_{0.80}\text{S}^a$	5.80 ± 0.13	0.47 ± 0.01	47.5 ± 0.61	1.28 ± 0.03
6	$\text{Ce}_{0.04}\text{Cd}_{0.96}\text{S}/\text{ZnS}^a$	8.39 ± 0.33	0.72 ± 0.01	61.4 ± 1.49	3.71 ± 0.01
7	$\text{Ce}_{0.04}\text{Cd}_{0.96}\text{S}/\text{ZnS}^b$	8.16	0.73	62.5	3.72
8	Mn-doped CdS <sup>30</sup>	8.90	0.58	49.0	2.53
9	Ni-doped CdS <sup>31</sup>	8.91	0.64	54.3	3.11
10	Cu-doped CdS <sup>32</sup>	9.40	0.64	50.1	3.00

<sup>a</sup> Average value from three cells in parallel. <sup>b</sup> Champion cell.



**Table 3** Photovoltaic performance of  $\text{Ce}_{0.04}\text{Cd}_{0.96}\text{S}$  QDSCs under different sun intensities

Light intensity	$J_{\text{sc}}$ ( $\text{mA cm}^{-2}$ )	$V_{\text{oc}}$ (V)	Fill factor (%)	Efficiency (%)
1 sun	8.16	0.73	62.5	3.72
0.46 sun	4.67	0.65	60.7	4.00
0.25 sun	2.77	0.64	59.9	4.24

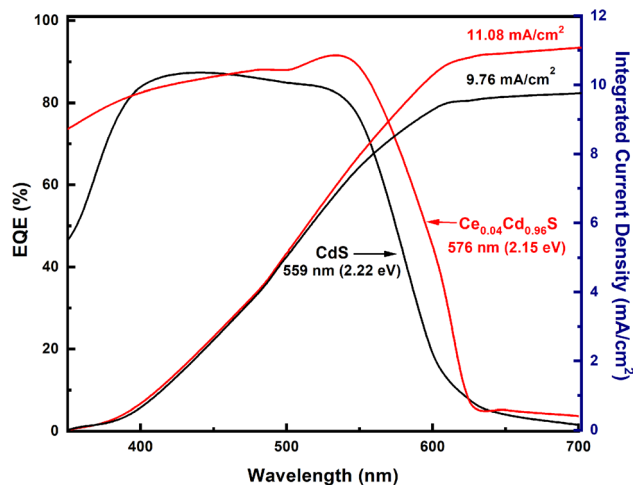

**Fig. 6** EQE spectra of  $\text{Ce}_{0.04}\text{Cd}_{0.96}\text{S}$  and CdS QDSCs and their EQE-integrated photocurrents.

band gap energy,  $E_{\text{g,pv}}$ , can be deduced from the absorption onset of an EQE spectrum.<sup>34</sup> The onset of the two EQE curves yields  $E_{\text{g,pv}} = 2.15$  eV for  $\text{Ce}_{0.04}\text{Cd}_{0.96}\text{S}$  and 2.22 eV for CdS (Fig. 6). The incorporation of Ce into CdS leads to a decreased bandgap, resulting in a broader light absorption range and enhanced solar cell efficiency. The EQE values are 80–90% over the spectral range of 350–550 nm. These EQE values are relatively high for a solar cell, indicating the good quality of the samples in this work.

The integrated current density ( $J_{\text{sc}}$ ) of a solar cell can be calculated from an EQE spectrum using (1)

$$J_{\text{sc}} = e \int \text{EQE}(\lambda) \Phi(\lambda) d\lambda \quad (1)$$

where  $\Phi(\lambda)$  is the incident photon flux and  $e$  is the elementary charge. The integrated  $J_{\text{sc}}$  is  $11.08 \text{ mA cm}^{-2}$  for the  $\text{Ce}_{0.04}\text{Cd}_{0.96}\text{S}$  solar cell and  $9.76 \text{ mA cm}^{-2}$  for CdS solar cell. The  $\text{Ce}_{0.04}\text{Cd}_{0.96}\text{S}$  cell generates 13.5% more current than the CdS cell. The improved  $J_{\text{sc}}$  in  $\text{Ce}_{0.04}\text{Cd}_{0.96}\text{S}$  is consistent with  $J_{\text{sc}}$  obtained from  $I$ - $V$  measurements shown in Fig. 5.

## 4 Conclusions

We demonstrated the fabrication of  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  QDSSCs prepared on a mp-TiO<sub>2</sub> electrode. The incorporation of Ce into CdS QDs broadens the optical absorbance range from 500 nm to 550 nm, resulting in an  $E_{\text{g,op}}$  of 2.24–2.33 eV, which is 7%

broader than that of CdS. As a result, the best  $\text{Ce}_x\text{Cd}_{1-x}\text{S}$  liquid-junction QDSCs, with  $x = 0.04$ , had an efficiency of 3.72% and a high  $V_{\text{oc}}$  of 0.73 V, representing about 25% improvement over the CdS QDSCs (2.98%). The EQE-integrated  $J_{\text{sc}}$  equals to  $11.08 \text{ mA cm}^{-2}$ , 13% higher than  $9.76 \text{ mA cm}^{-2}$  for CdS solar cell. These results suggest that Ce could be used as a dopant to tune the optical properties and improve the photovoltaic performance of CdS.

## Author contributions

Eva Natalia Christina: methodology, validation, formal analysis, investigation. Siti Utari Rahayu: investigation, formal analysis, writing – original draft. Auttasit Tubtimtae: formal analysis. Jen-Bin Shi: formal analysis. Ming-Way Lee: term, conceptualization, methodology, resources, formal analysis, investigation, writing – review & editing, supervision.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The authors are grateful for the financial support from the Ministry of Science and Technology (MOST) in Taiwan under grant no. MOST 111-2112-M-005-017.

## Notes and references

- W. W. Yu, L. Qu, W. Guo and X. Peng, *Chem. Mater.*, 2003, **15**, 2854–2860.
- S. K. Haram, A. Kshirsagar, Y. D. Gujarathi, P. P. Ingole, O. A. Nene, G. B. Markad and S. P. Nanavati, *J. Phys. Chem. C*, 2011, **115**(14), 6243–6249.
- V. I. Klimov, *Appl. Phys. Lett.*, 2006, **89**(12), 123118.
- Z. Pan, H. Rao, I. Mora-Seró, J. Bisquert and X. Zhong, *Chem. Soc. Rev.*, 2018, **47**, 7659–7702.
- M. C. Hanna and A. J. Nozik, *J. Appl. Phys.*, 2006, **100**(7), 074510.
- W. Shockley and H. J. Queisser, *J. Appl. Phys.*, 1961, **32**(3), 510–519.
- H. Samosir, P. Boon-On, Y. E. Lin, L. P. Chen, D. J. Singh, J. B. Shi and M. W. Lee, *J. Phys. Chem. C*, 2019, **123**(9), 5209–5215.
- X. Zhong, Y. Feng, W. Knoll and M. Han, *J. Am. Chem. Soc.*, 2003, **125**(44), 13559–13563.
- M. Imran, M. Ikram, A. Shahzadi, S. Dilpazir, H. Khan, I. Shahzadi, S. A. Yousaf, S. Ali, J. Geng and Y. Huang, *RSC Adv.*, 2018, **8**(32), 18051.
- A. Reza Amani-Ghadim, E. Mohammad-Gholipour-Rezaei, F. Bayat, S. Agbolaghi and F. Khodam, *Sol. Energy*, 2022, **231**, 402–413.
- R. Dalven, *Phys. Rev. B*, 1973, **8**, 6033.
- A. Sangiorgi, R. Bondoni, N. Sangiorgi, A. Sanson and B. Ballarin, *Ceram. Int.*, 2014, **40**(7), 10727–10735.





- 13 S. Hore, C. Vetter, R. Kern, H. Smit and A. Hinsch, *Sol. Energy Mater. Sol. Cells*, 2006, **90**(9), 1176–1188.
- 14 P. Wang, S. M. Zakeeruddin, P. Comte, R. Charvet, R. Humphry-Baker and M. Grätzel, *J. Phys. Chem. B*, 2003, **107**(51), 14336–14341.
- 15 M. W. Lee, in *AIP Conference Proceeding*, 2020, vol. 2221.
- 16 S. U. Rahayu and M. W. Lee, in *AIP Conference Proceedings*, 2020.
- 17 K. Sebayang, S. U. Rahayu, M. W. Lee, S. Gea, H. Ginting and A. Warman, *Rasayan J. Chem.*, 2021, **14**(1), 88–93.
- 18 P. Boon-on, S. W. Lien, T. R. Chang, J. Bin Shi and M. W. Lee, *Prog. Photovoltaics*, 2020, **28**(4), 328–341.
- 19 W. Zheng and S. Zhang, *Inorg. Chem. Commun.*, 2020, **122**, 108294.
- 20 L. Saravanan, A. Pandurangan and R. Jayavel, *Mater. Lett.*, 2012, **66**(1), 343–345.
- 21 F. Zhan, W. Liu, H. Li, Y. Yang and M. Wang, *Appl. Surf. Sci.*, 2018, **455**, 476–483.
- 22 A. Ekinici, S. Horoz and Ö. Şahin, *Chalcogenide Lett.*, 2020, **17**(6), 263–268.
- 23 E. Bêche, P. Charvin, D. Perarnau, S. Abanades and G. Flamant, *Surf. Interface Anal.*, 2008, **40**(3–4), 264–267.
- 24 R. Fiorenza, C. Crisafulli, G. G. Condorelli, F. Lupo and S. Scirè, *Catal. Lett.*, 2015, **145**(9), 1691–1702.
- 25 D. Barreca, A. Gasparotto, C. Maragno and E. Tondello, *Surf. Sci. Spectra*, 2002, **9**(1), 46–53.
- 26 C. Liu, H. Tang, J. Li, W. Li, Y. Yang, Y. Li and Q. Chen, *RSC Adv.*, 2015, **5**, 35506–35512.
- 27 Y. Tachibana, H. Y. Akiyama, Y. Ohtsuka, T. Torimoto and S. Kuwabata, *Chem. Lett.*, 2007, **36**, 88–89.
- 28 X. Qi, G. She, Y. Liu, L. Mu and W. Shi, *Chem. Commun.*, 2012, **48**(2), 242–244.
- 29 M. F. Rahman, J. Hossain, A. Kuddus, S. Tabassum, M. H. K. Rubel, H. Shirai and A. B. M. Ismail, *Appl. Phys. A: Mater. Sci. Process.*, 2020, **126**(2), 1–11.
- 30 P. K. Santra and P. V. Kamat, *J. Am. Chem. Soc.*, 2012, **134**(5), 2508–2511.
- 31 C. V. V. M. Gopi, M. Venkata-Haritha, H. Seo, S. Singh, S. K. Kim, M. Shiratani and H. J. Kim, *Dalton Trans.*, 2016, **45**(20), 8447–8457.
- 32 M. P. A. Muthalif, Y. S. Lee, C. D. Sunesh, H. J. Kim and Y. Choe, *Appl. Surf. Sci.*, 2017, **396**, 582–589.
- 33 M. Tachiya and K. Seki, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 2010, **82**(8), 085201.
- 34 O. Almora, C. I. Cabrera, J. Garcia-Cerrillo, T. Kirchartz, U. Rau and C. J. Brabec, *Adv. Energy Mater.*, 2021, **11**(16), 2100022.

