


Chemical Science

Volume 13
Number 33
7 September 2022
Pages 9455–9792

rsc.li/chemical-science

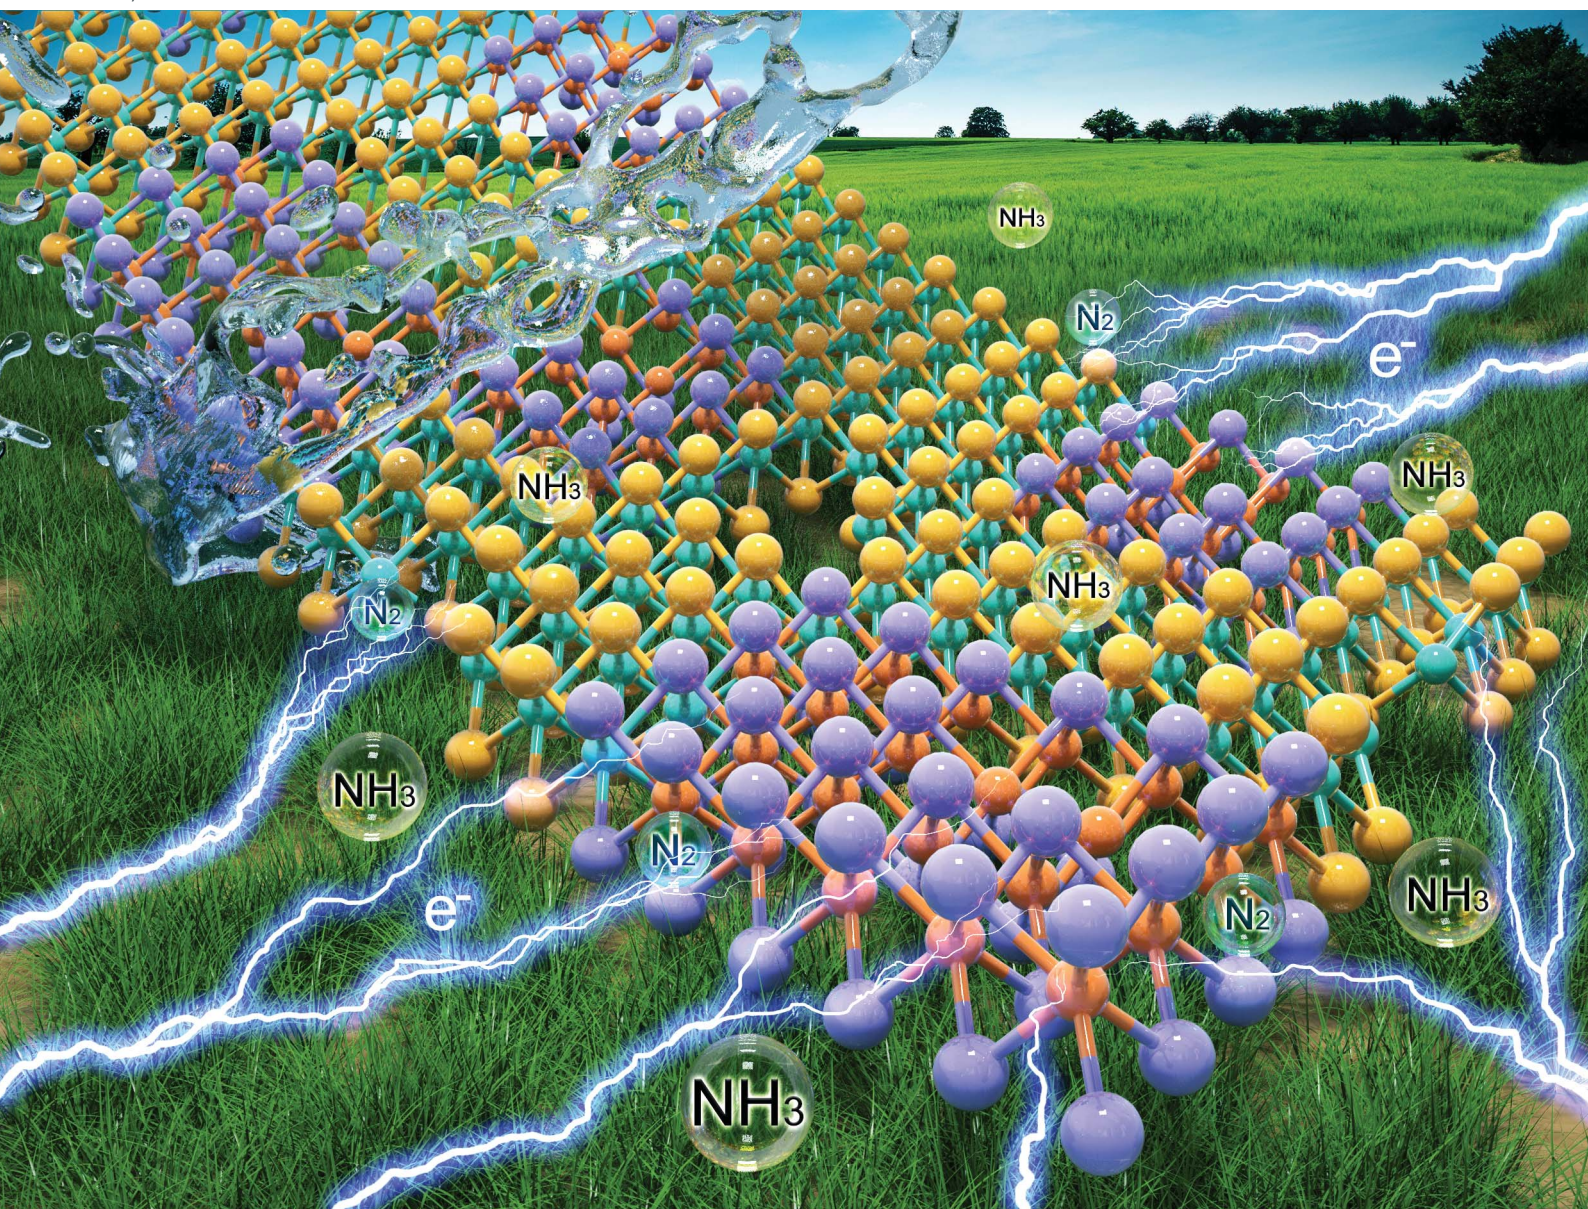

ISSN 2041-6539

EDGE ARTICLE

Bin Song, Yingwen Cheng, Ke Lu *et al.*
Activation of MoS₂ monolayer electrocatalysts *via*
reduction and phase control in molten sodium for
selective hydrogenation of nitrogen to ammonia

Cite this: *Chem. Sci.*, 2022, 13, 9498

All publication charges for this article have been paid for by the Royal Society of Chemistry

Activation of MoS₂ monolayer electrocatalysts *via* reduction and phase control in molten sodium for selective hydrogenation of nitrogen to ammonia†

Hong Zhang,^{ab} Bin Song,^{*c} Weiwei Zhang,^d Yingwen Cheng,^{*e} Qianwang Chen^{ab} and Ke Lu^{*ab}

Electrochemical nitrogen fixation under ambient conditions is promising for sustainable ammonia production but is hampered by high reaction barrier and strong competition from hydrogen evolution, leading to low specificity and faradaic efficiency with existing catalysts. Here we describe the activation of MoS₂ in molten sodium that leads to simultaneous formation of a sulfur vacancy-rich heterostructured 1T/2H-MoS_x monolayer *via* reduction and phase transformation. The resultant catalyst exhibits intrinsic activities for electrocatalytic N₂-to-NH₃ conversion, delivering a faradaic efficiency of 20.5% and an average NH₃ rate of 93.2 μg h⁻¹ mg_{cat}⁻¹. The interfacial heterojunctions with sulfur vacancies function synergistically to increase electron localization for locking up nitrogen and suppressing proton recombination. The 1T phase facilitates H–OH dissociation, with S serving as H-shuttling sites and to stabilize H_{ad}^{*}. The H_{ad}^{*} subsequently couple with nearby N₂ and NH_x intermediates bound at Mo sites, thus greatly promoting the activity of the catalyst. First-principles calculations revealed that the heterojunction with sulfur vacancies effectively lowered the energy barrier in the potential-determining step for nitrogen reduction, and, in combination with operando spectroscopic analysis, validated the associative electrochemical nitrogen reduction pathway. This work provides new insights on manipulating chalcogenide vacancies and phase junctions for preparing monolayered MoS₂ with unique catalytic properties.

Received 7th July 2022

Accepted 24th July 2022

DOI: 10.1039/d2sc03804h

rsc.li/chemical-science

1. Introduction

Ammonia, a vital chemical feedstock with high energy density (*e.g.*, 3 kWh kg⁻¹, 4.3 kWh h⁻¹), is of great importance to the agricultural industry and clean energy exploration. Commercial industrial NH₃ synthesis is dominated by the Haber–Bosch process with harsh synthetic conditions, which consumes 1–2% of global energy production and results in carbon dioxide emissions.^{1,2} This can be potentially replaced by direct electrochemical nitrogen fixation to ammonia using renewable

electricity as an attractive ‘carbon-neutral’ alternative strategy.^{3,4} However, current heterogeneous electrocatalysts have very limited activity to activate nitrogen molecules due to their chemical inertness (dissociation energy of the N≡N triple bond: 940.95 kJ mol⁻¹). As a result, electrocatalytic nitrogen conversion typically operates *via* high overpotentials and under potentials that are well below the hydrogen evolution reaction (HER). Unfortunately, the HER typically exhibits fast kinetics in aqueous solutions and the selectivity towards NH₃ is still far from being competitive with that of the Haber–Bosch process. In addition, ambient ammonia contamination during catalysis is significant and inevitable, thus leading to it also being difficult to detect ammonia generated by the nitrogen reduction reaction (NRR) accurately. So, the effect of ambient ammonia contamination also needs to be identified in as much detail as possible.^{5,6} Further advances on novel catalyst design and fundamental understanding regarding the multi-step transfer of electrons and protons during nitrogen hydrogenation are required to overcome the limitations of existing nitrogen reduction electrocatalysts such as slow kinetics and high energy barrier.^{7–10}

Transition metal dichalcogenides with tunable electronic properties have attracted wide attention and have been extensively exploited in electrocatalysis.^{11–14} Of them, inspired by

^aInstitutes of Physical Science and Information Technology, School of Materials Science and Engineering, Key Laboratory of Structure and Functional Regulation of Hybrid Materials of Ministry of Education, Anhui University, Hefei, Anhui 230601, China. E-mail: luke@ahu.edu.cn

^bHefei National Laboratory for Physical Sciences at the Microscale, University of Science and Technology of China, Hefei, Anhui 230026, China

^cInstitute of Functional Nano & Soft Materials (FUNSOM), Soochow University, Suzhou, Jiangsu 215123, China. E-mail: bsong@suda.edu.cn

^dSchool of Chemistry and Chemical Engineering, Qufu Normal University, Qufu, Shandong, 273165, China

^eDepartment of Chemistry and Biochemistry, Northern Illinois University, DeKalb, IL 60115, USA. E-mail: ycheng@niu.edu

† Electronic supplementary information (ESI) available. See <https://doi.org/10.1039/d2sc03804h>



natural metalloenzymes, such as Mo-dependent nitrogenase, MoS₂ exhibits very similar constituent elements and is viewed as a very promising nitrogen functionalization catalyst.^{15–19} In this regard, the low-coordinated Mo atoms at the edge sites are generally accepted as the nitrogen reduction catalytic centers for activating N₂ molecules. The abundant saturated coordinative atoms in the base planes, on the other hand, are inactive and the overall catalytic efficiency is severely slowed by a deficiency of active sites on the basal plane.²⁰ To this end, defect, phase and strain engineering have been explored to boost the intrinsic activity of MoS₂ catalysts.^{21–24} However, their poor conductivity and inert basal planes result in NH₃ yield rates that are generally less than 50 μg h⁻¹ mg_{cat}⁻¹, such as 13.09 μg h⁻¹ mg_{cat}⁻¹ for MoS₂ nanosheets and 29.28 μg h⁻¹ mg_{cat}⁻¹ for defect-rich 2H-MoS₂ nanoflowers.²⁵ By far, 2H-MoS₂ is the most studied material, but its trigonal prismatic Mo coordination leads to fully occupied d_{z²} and empty d_{xy}, d_{x²-y²} orbitals, making them intrinsically less active. On the other hand, the metastable 1T phase MoS₂ has octahedral Mo coordination that splits the 4d² orbitals of Mo⁴⁺ into e_g and t_{2g} orbitals and could be more attractive as partially occupied t_{2g} orbitals provide mechanisms to overlap with N₂ and form strong σ bonds and transfer electrons to the anti-bonding molecular orbital of N₂ for lowering the barrier associated with initial activation.^{25,26} In addition, the Mo–Mo distance, potentially adjustable *via* doping or crystal defects, could be further employed to modulate Mo–N interaction for nitrogen conversion. Multi-functional heterojunctions that strengthen nitrogen adsorption and promote its activation while suppressing hydrogen evolution represent a promising direction for catalyst design.²⁶ Notably, various research endeavors have been devoted to the phase engineering of MoS₂, especially focusing on the transformation from the 2H to 1T phase (such as the *n*-butyllithium intercalation approach) for realizing metallic features with strong hydrophilicity. Besides this, defect engineering is also an effective strategy to improve the activity of MoS₂ base planes. The formation of sulfur vacancies can become interstitials by lodging in nearby locations, which will greatly promote the charge distributions of monolayer MoS₂ base planes.^{24–26} However, facile effective experimental strategies by which to synthesize MoS₂-based catalysts with a tunable 1T/2H phase and sulfur vacancies have not yet been identified.

Herein, we report a facile chemical conversion technique to transform bulk MoS₂ *via* an amalgamated MoS₂-Na method to 1T/2H-MoS_x with engineered sulfur vacancies that exhibits high intrinsic activity. The strong chemical interactions between metallic Na and MoS₂ sites under molten Na states generate ~10% sulfur vacancies and the conversion of stabilized 1T phases, realizing the activation of the basal plane. The final heterostructured 1T/2H-MoS_{1.79} monolayer exhibits intrinsic selectivity and yields excellent nitrogen fixation performance, with an average ammonia formation rate of 93.2 μg h⁻¹ mg_{cat}⁻¹ at -0.4 V *versus* the reversible hydrogen electrode (RHE) and a faradaic efficiency of 20.5% with remarkable long-term operation stability over 30 h. Specifically, it was identified that the undercoordinated Mo regions and the intimate 1T/2H interfacial heterojunctions with sulfur vacancies can lock up nitrogen

at localized hotspots, and phase transformation promotes H–OH dissociation in mild electrolyte, whereas S sites serve as a H-provider and are conducive to H_{ad}^{*} stabilization, thus both processes work synergistically to lower the nitrogen reduction energy barrier in the potential-determining step and assist selective N₂ transformation, further supported by density functional theory (DFT) calculations.

2. Results and discussion

Fig. 1a illustrates our molten-Na-assisted intercalation and subsequent chemical conversion approach for generating abundant 1T/2H interfacial heterojunctions with sulfur vacancies (SVs) starting from bulk MoS₂ (MoS₂-H). Briefly, bulk MoS₂ powder (Fig. S1†) was infiltrated with molten Na metal and then calcined under an Ar atmosphere (optimized at 120 °C). During the blending process, the difference between the electron affinity of MoS₂ (4.45) and the ionization potential of Na (5.12 eV) results the intercalation of Na into MoS₂ interlayers (MoS₂ accepts electrons due to high electron affinity) to realize reduction and phase control, producing an exfoliated nanosheet morphology.^{27–29} In addition, the intercalated Na atoms generate Na–S bonds, and the large electronegativity difference between the Na and S atoms facilitates the transfer of electrons and induces the formation of SVs and a 1T phase (Table S1†).³⁰ Therefore, junction type MoS_x-H/T monolayers could be synthesized through a highly-scalable molten-Na-assisted approach.

To confirm the phase transformation of the exfoliated MoS_x-H/T nanoplatelets, the morphology and lattice properties were investigated by high resolution transmission electron microscopy (HRTEM). Fig. 1b–d show the microscopy images and energy-dispersive X-ray spectroscopy (EDS) mapping of the MoS_{1.79}-H/T prepared under the optimal synthesis conditions of 120 °C and 10 min. The Mo and S are homogeneously distributed on the basal plane of the MoS_x nanosheets. Fig. 1e presents the junction where the 1T- and 2H-phases meet. The characteristic crystalline lattice structures of the 1T- and 2H-phases were clarified from the zoomed-in images (red and blue frames) and the atomic arrangement profiles. The 1T-phase region shows characteristic Mo–S octahedral coordination, corresponding to the (100) plane of MoS₂ with two sulfur atoms between neighboring molybdenum atoms (Mo–S–S–Mo), whereas the 2H-phase region exhibits typical Mo–S trigonalprismatic coordination (Mo–S–Mo) (red line).^{31,32} The monolayer nanosheet nature of MoS_x-H/T was verified, with a height of 1.05 nm in the atomic force microscopy (AFM) image (Fig. 1f). In addition, the HRTEM image in Fig. 1g highlights the 1T- and 2H-phase heterojunctions within the basal plane of MoS_x-H/T. Moreover, aberration-corrected scanning transmission electron microscopy (AC-STEM) was carried out to disclose the atomic configurations of MoS_x-H/T. Prominent defect sites were observed in MoS_x-H/T, as highlighted by the red arrows in Fig. 1h. This evidence indicates that the SVs were clearly generated after the molten-Na treatment.^{12,17,21}

Due to the formation of SVs, the atomic ratio of MoS_x-H/T (*x* = 1.59–2) with different molten-Na-assisted intercalation



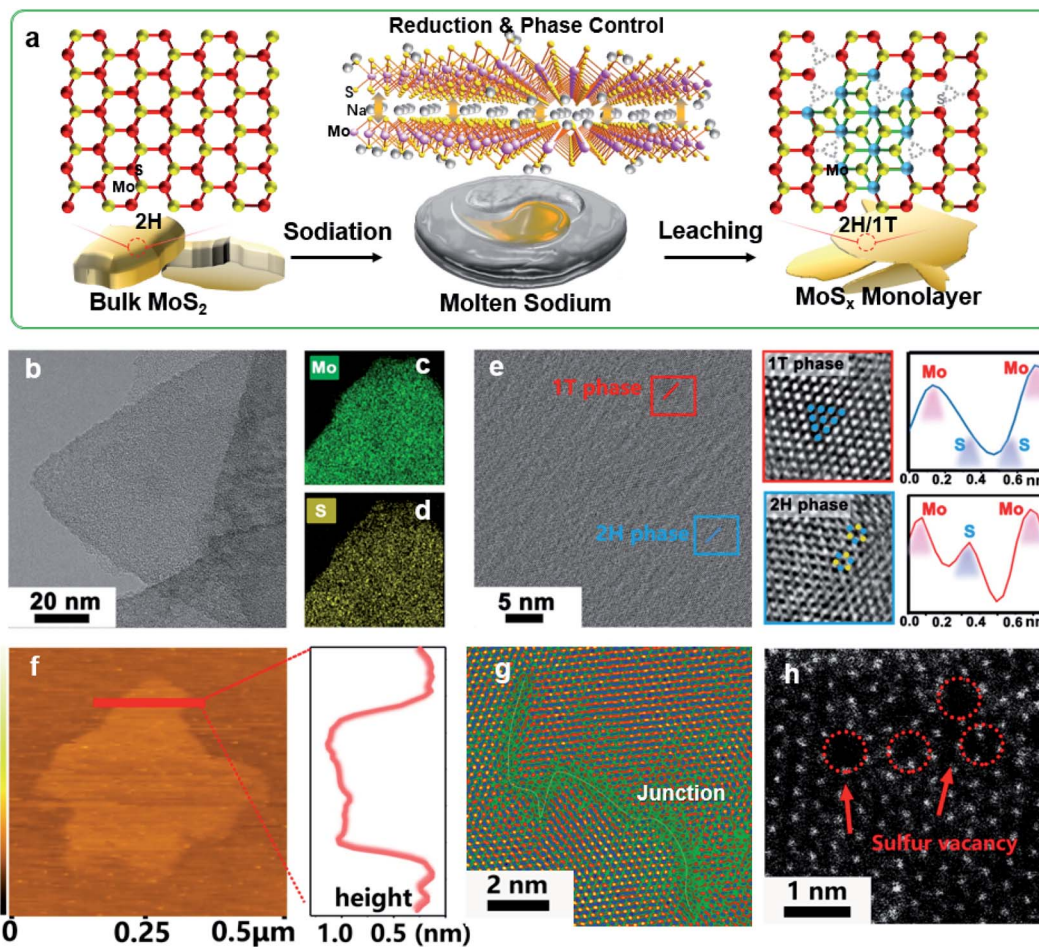


Fig. 1 Schematic illustration of the catalyst synthesis and representative electron microscopy morphology. (a) Schematic illustration of the preparation of $\text{MoS}_x\text{-H/T}$. (b) TEM and the corresponding (c, d) EDS mapping analysis of $\text{MoS}_x\text{-H/T}$ sample, confirming the homogeneous distributions of Mo and S. (e) TEM and HRTEM images of $\text{MoS}_{1.79}\text{-H/T}$, showing the hybrid 1T-phase and 2H-phase domains. Zoomed-in images of the 1T (red frame) and 2H (blue frame) phase regions in (e), showing the octahedral (1T) and trigonal-prismatic (2H) coordinated lattice structure with corresponding atomic profiles, respectively. (f) Tapping-mode AFM image and the corresponding line scan of the $\text{MoS}_x\text{-H/T}$ film. (g) HRTEM image of $\text{MoS}_{1.79}\text{-H/T}$ with pseudo color labelling. (h) Atomic-resolution HAADF-STEM images of $\text{MoS}_x\text{-H/T}$ with vacancies.

reaction times was quantified by inductively coupled plasma atomic emission spectroscopy (see Table S1†). The molten-Na-assisted intercalation and subsequent chemical conversion and its effect on the MoS_x phase were further verified by X-ray diffraction (XRD) analysis. Fig. 2a presents the XRD peaks of Na-intercalated MoS_2 . The (002) plane of pristine MoS_2 can be observed at $\sim 14^\circ$, which gradually widened (the full width at half maximum was significantly increased from 0.2° to 1.1°) during Na intercalation and hence suggests increased MoS_2 interlayer spacing after Na intercalation. Meanwhile, the diffraction signals of the (002) plane were blueshifted (from 14.1° to 13.2°) for $\text{MoS}_x\text{-H/T}$ relative to $\text{MoS}_2\text{-H}$, indicating the effective intercalation and phase transformation from 2H to 1T in MoS_x .^{32,33} The phase control and molten-Na-assisted generation of SVs were investigated by conducting X-ray photoelectron spectroscopy (XPS) measurements on the as-prepared $\text{MoS}_x\text{-H/T}$ (Fig. 2b). Mo $3d_{5/2}$ and $3d_{3/2}$ peaks can be observed at ~ 229.8 and ~ 232.9 eV, respectively, in the spectra of 2H- MoS_2 (red areas), whereas for 1T- MoS_2 (green areas), these two peaks appear at ~ 229.0 and ~ 232.1 eV (Fig. 2b), respectively. A similar

downshift in the binding energies of the 1T phase were identified from the S $2p_{3/2}$ and S $2p_{1/2}$ signals (Fig. 2c), which arise at ~ 163.0 and ~ 164.1 eV in the spectra of the 2H phase, and at ~ 162.1 and ~ 163.4 eV for the 1T phase, respectively. These downshifts in the 1T phase are attributable to the change in the Fermi level induced by electron filling in the Mo d orbitals.^{32–34} Remarkably, the signals from the 1T phase (green areas) gradually dominate the main composition with an increase in the reaction time from 0 to 30 min, which confirms that the molten-Na-assisted process effectively transformed from 2H to 1T. Furthermore, in the XPS results, the phase compositions of the 1T phase were calculated from 0 to 72%, indicating that the proposed molten-Na-assisted intercalation approach successfully controls the 2H and 1T phases (Fig. 2d). As shown in Fig. 2e, after molten-Na-assisted intercalation treatment, $\text{MoS}_x\text{-H/T}$ shows different vibration modes in its Raman spectra. For 2H- MoS_2 (black line) two characteristic Raman peaks at 383 cm^{-1} (E_{2g}^1 mode, in-plane stretching) and 401 cm^{-1} (A_{1g} mode, out-of-plane vibration) arise from S–Mo–S. In addition, during the molten-Na-assisted intercalation treatment, the



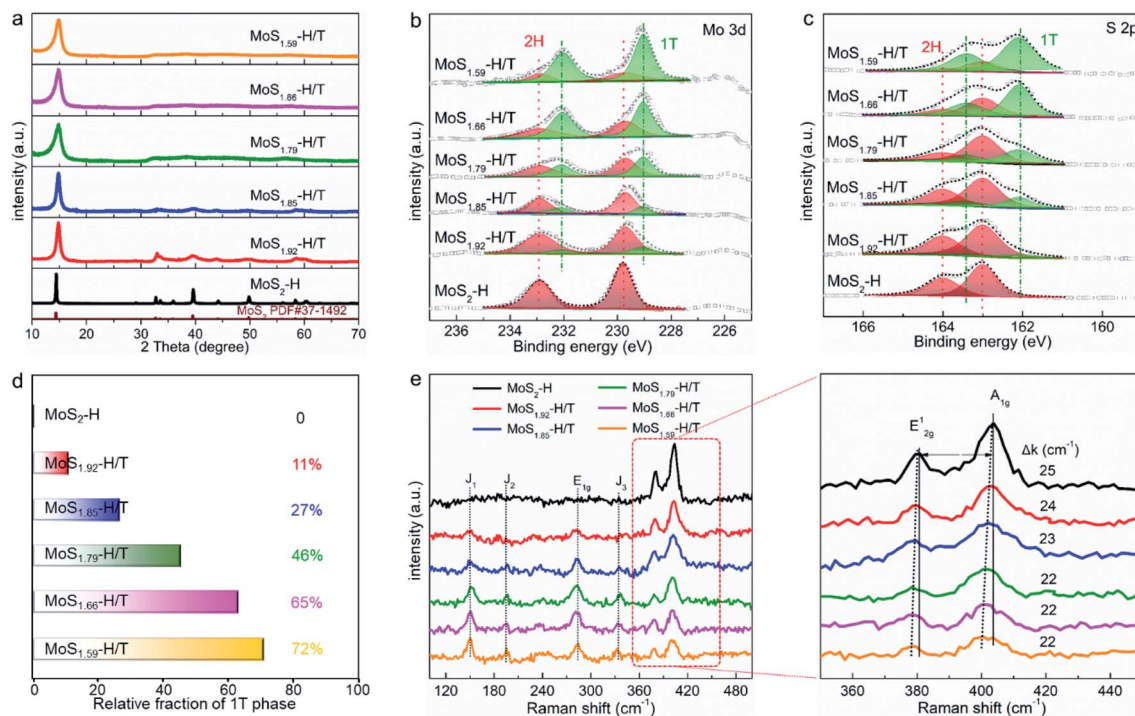


Fig. 2 Physical characterization of MoS₂ samples before and after molten-Na-assisted intercalation. (a) Selected XRD spectra of pristine and treated MoS₂ samples. The clearly widened and blue shifted 2θ peaks indicate that the Na intercalation expands the interlayer spacing of 2H- and 1T-MoS₂. Comparison of the high-resolution (b) Mo 3d and (c) S 2p XPS spectra of the different MoS_x samples. (d) Relative fractions of the 1T phase in the original and treated MoS₂ samples. (e) Raman spectra of the different MoS_x samples as noted.

intensities of the E_{2g}¹ and A_{1g} modes decrease dramatically, meanwhile, the new Raman peaks at 280 cm⁻¹ (E_{1g} mode, attributable to the octahedral coordination of Mo), 152 cm⁻¹ (J₁ mode), 201 cm⁻¹ (J₂ mode) and 337 cm⁻¹ (J₃ mode) indicate the formation of the 1T phase. In particular, the amplification of the Raman peaks at 383 cm⁻¹ (E_{2g}¹ mode) and 401 cm⁻¹ (A_{1g} mode), and the gaps (Δk) between the two Raman peaks of A_{1g} to E_{2g}¹ progressively decrease from 25 to 22, further demonstrating that the Na intercalation process weakens the interactions between neighboring MoS₂ layers along with the exfoliation of the monolayers.^{32,35}

Electron spin resonance (ESR) was utilized to quantify the paramagnetic signals of MoS_x-H/T and the formation of SVs (Fig. 3a), in which the ~337 mT (*g* = 2.009) intensity reveals the concentration of unsaturated sites with unpaired electrons.²⁵ Notably, the pristine 2H-MoS₂ demonstrates a relatively low signal intensity, which can be attributed to the inherent in-plane and edge SVs. Remarkably, the MoS_x-H/T exhibits approximately 10 times higher signal intensity than pristine 2H-MoS₂, corroborating the formation of abundant SVs, which also demonstrates that the SV concentration correlates well with the 1T phase. Temperature-programmed desorption (TPD) of nitrogen was used to investigate the N₂ adsorption properties (Fig. 3b). Pristine 2H-MoS₂ exhibits a Brunauer–Emmett–Teller (BET) specific surface area of 33.2 m² g⁻¹ (Fig. S2†) and inferior N₂ physisorption and chemisorption. In particular, strong correlation between physisorption/chemisorption and SV density was observed. All of the MoS_x-H/T groups display

enhanced chemisorption and physisorption capability with increased BET surface areas from 85.1 to 174.2 m² g⁻¹ due to their high SV concentration in the hybrid 2H/1T heterojunction system. Thus, the density of interfacial heterojunctions plays a vital role in strengthening the chemisorption. Among them, MoS_{1.79}-H/T exhibits the highest chemisorption capacity, thus the heterojunction and SVs can act as strong active sites to “lock up” the nitrogen reactant for subsequent triple-bond dissociation. In addition, the Fourier-transform infrared (FTIR) spectra exhibits an obvious blueshift for the resonance peak from adsorbed nitrogen species from 2365 to 2358 cm⁻¹ after Na-assisted intercalation (Fig. 3c), suggesting the elongation of the N≡N triple bond length when adsorbed on the MoS_x-H/T catalyst.³⁶ Therefore, we conclude that the abundant localized electron induced by heterojunction and SVs in MoS_x-H/T could better activate the N≡N triple bond to accelerate the catalysis.

Fig. 3d and e compare the hydrogen evolution reaction (HER) activities and kinetics of the pristine MoS₂ and MoS_x-H/T. As expected, pristine MoS₂ is a poor HER catalyst with an onset potential of ~-0.5 V vs. RHE and a high Tafel slope of 190 mV dec⁻¹ due to its non-defective basal planes featuring few active sites.^{31–35} The MoS_x-H/T catalysts, on the other hand, exhibited enhanced HER activities, and in particular, MoS_{1.59}-H/T exhibits the best performance (with an onset overpotential of ~-0.3 V vs. RHE and a Tafel slope of 93 mV dec⁻¹), highlighting the advantages of the 1T phase. Meanwhile, the electrochemically active surface areas (ECSA, Fig. S3†) of MoS_x-H/T were analysed and compared to reveal the electrochemical properties



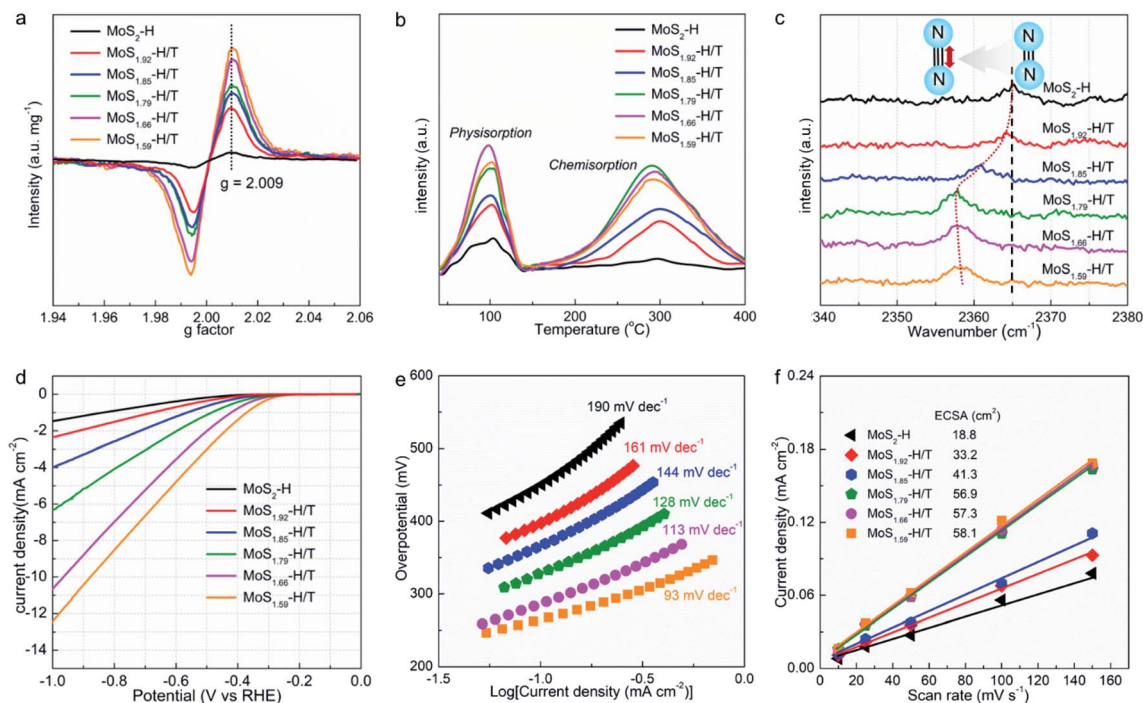


Fig. 3 Structural and primary electrochemical characterization of the different catalysts. (a) ESR spectra. (b) N_2 TPD curves of the different MoS_x samples as noted. (c) FTIR spectra of N_2 adsorption on the different MoS_x samples. (d) LSV curves and (e) the corresponding Tafel slopes of the different MoS_x in Ar-saturated electrolyte. (f) Comparison of the electrochemical surface areas of the different MoS_x samples.

of the different electrocatalysts. $MoS_{1.59}$ -H/T exhibited the highest ECSA value (58.1 cm^2), suggesting that it contains abundant active sites, owing to its higher 1T-phase content, providing a favorable platform for electrocatalytic activity. $MoS_{1.59}$ -H/T displays the lowest charge transfer resistance, which should be attributed to its high metallic 1T phase content (Fig. S4†). In addition, we can see from Fig. 3f that the monolayer catalyst shows a very similar ECSA value and that the 1T/2H interfacial junctions could have a positive effect on promoting both the NRR and HER kinetics.^{17,20,26}

The resultant MoS_x -H/T catalysts were deposited on carbon paper working electrodes and employed for the NRR in a three-compartment cell under ambient conditions (Fig. S5†). The NRR performance was evaluated by quantifying the generated NH_3 via the indophenol blue method (Fig. S6†), and the possible formation of byproduct (N_2H_4) was also quantified using the Watt and Chrisp method.³⁷ Fig. 4a shows the faradaic efficiencies (FEs) of the different MoS_x -H/T catalysts at various potentials, of which $MoS_{1.79}$ -H/T exhibits the highest average NH_3 yield rate and FE of $93.2 \mu\text{g h}^{-1} \text{ mg}_{\text{cat}}^{-1}$ and 20.5% at -0.4 V vs. RHE , respectively, much higher than that of pristine 2H- MoS_2 (FE: 0.5%) and the other MoS_2 -H/T catalysts (FEs from 3.2 to 11.5%), implying that the 1T phases and SVs mainly promote the electrocatalytic NRR performance. It is worth mentioning that, due to the competing HER, the FEs of the catalysts significantly decreased when the applied potential was lower than -0.5 V . Moreover, as illustrated in Fig. 4b, the linear sweep voltammograms (LSVs) show a gas-dependent response for the $MoS_{1.79}$ -H/T catalyst (the electrolyte was purged with N_2 or Ar for 30 min before measurements). Compared to the Ar

measurements, the N_2 LSVs displayed evidently higher cathodic currents, especially after -0.26 V vs. RHE , indicating the catalytic reduction of N_2 . In addition, the $MoS_{1.59}$ -H/T catalyst exhibits a relatively poor HER activity under an Ar atmosphere (with a Tafel slope of 128 mV dec^{-1}) and could be beneficial for efficient N_2 reduction. In comparison, a decreased Tafel slope of 114 mV dec^{-1} was achieved in a N_2 saturated environment, indicating that the N_2 electrochemical processes accelerate the interfacial H_{ad}^* generation and/or removal. Considering the competitive relationship between the HER and NRR, the difference in the Tafel slopes under Ar and N_2 diminished when the applied potential was lower than -0.77 V , indicating dominant $*H$ adsorption and suppressed $*N_2$ adsorption under high overpotentials. It should be noted that at the highest potential, more protons occupied the active sites and dominate proton reduction, seriously impeding the yield of the NRR. Further, the ammonia yields were 4.96, 26.2, 93.2, 84.9, and 36.7 $\mu\text{g h}^{-1} \text{ mg}_{\text{cat}}^{-1}$, with FEs of 9.7%, 17.6%, 20.5%, 8.1%, and 2.2% at -0.20 , -0.30 , -0.40 , -0.50 , and -0.60 V vs. RHE (Fig. 4d, S7–S8,† average experimental values), respectively. In addition, none of the N_2H_4 by-products were observed in the cycled electrolyte (Fig. S9†), thus further confirming the high selectivity of the monolayer catalyst. The highest NH_3 yield rate and FE reached $93.2 \mu\text{g h}^{-1} \text{ mg}_{\text{cat}}^{-1}$ and 20.5% at -0.4 V vs. RHE , respectively. The normalized LSV results (Fig. S10†) again confirmed the synergistic function of the 1T phase and SVs for facilitating nitrogen activation and conversion, especially in comparison with the pristine MoS_2 . The $MoS_{1.79}$ -H/T monolayer catalyst possesses the most catalytic active sites for the NRR. And the highest activity of $MoS_{1.79}$ -H/T catalyst under our



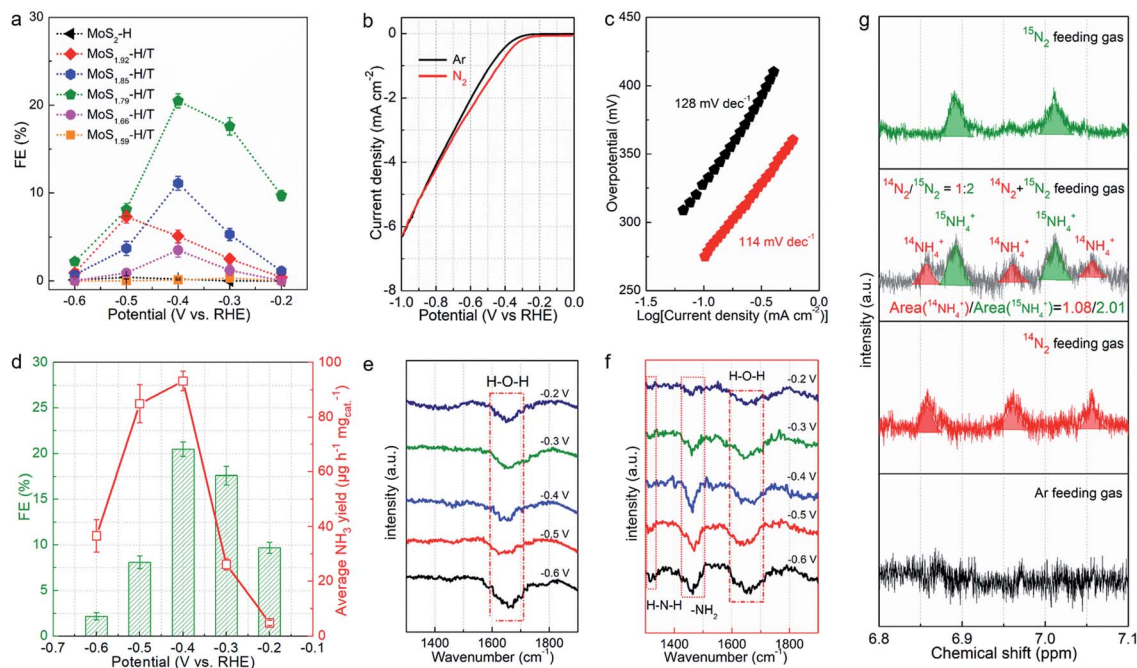


Fig. 4 Ambient electrochemical NRR activity of the MoS₂-based monolayer catalyst. (a) Average FEs of the different MoS_x samples at different applied potentials. (b) LSV curves of MoS_{1.79}-H/T in Ar- and N₂-saturated electrolyte at a scan rate of 10 mV s⁻¹, and (c) the corresponding Tafel slopes of the MoS_{1.79}-H/T electrode. (d) Average NH₃ yields and FEs of MoS_{1.79}-H/T at different applied potentials. (e, f) FTIR spectra from -0.2 to -0.6 V vs. RHE for MoS_{1.79}-H/T using Ar or N₂ as the feed gas. (g) ¹⁵N isotopic labeling experiment. The integrated peak areas associated with ¹⁴NH₄⁺ and ¹⁵NH₄⁺ are proportional to the initial ratio of the ¹⁴N₂/¹⁵N₂ feed gas.

testing conditions, when normalized to the electroactive surface area, was 0.491 μg h⁻¹·cm_{ECSA}⁻². Importantly, the catalyst exhibited an appreciable FE of 0.43% at an almost thermodynamic equilibrium potential of 0 V vs. RHE, indicating highly active catalysts in comparison with previously reported work.

Fig. 4e and f exhibit the FTIR spectra of MoS_{1.59}-H/T in Ar- and N₂-saturated 0.1 M Na₂SO₄ solution at room temperature and -0.2 to -0.6 V vs. RHE. Different from the spectra under Ar, the spectra under N₂ have additional peaks at 1317 and 1461 cm⁻¹ corresponding to H-N-H and -NH₂ vibrations. These results show that -NH_x intermediates were indeed generated on MoS_{1.59}-H/T during the NRR. An isotopic ¹⁵N labeling experiment was conducted to confirm the origin of the nitrogen resources (Fig. 4g). With ¹⁴N and an Ar feed gas, the obtained doublet pattern in the ¹H NMR spectra can be attributed to ¹⁵NH₄⁺. The ratio of the ¹⁴NH₄⁺/¹⁵NH₄⁺ products is proportional to the initial feed gas ratio of ¹⁴N₂/¹⁵N₂ (1.86 vs. 2.00), showing that the product originates electrocatalytic N₂ gas reduction rather than the contamination and/or decomposition of the catalysts.³⁷⁻³⁹ In addition, the almost linear correlation between the NH₃ concentration and electrolysis duration further demonstrate that MoS_{1.59}-H/T is a stable catalyst for electrochemical nitrogen fixation (Fig. S11†). The slightly decreased ammonia formation rate can be ascribed to the changes in pH (the pH change of the electrolyte was from 6.36 to 9.11 within 30 h) or the accumulation of formed ammonia that slightly modifies the thermodynamic equilibrium potential for NH₃ formation, thus making it impossible to apply a constant driving force for nitrogen fixation.³⁸

Electrochemical *in situ* Fourier-transform infrared (FTIR) spectroscopy was employed to monitor the complex nitrogen reduction pathway. Fig. 5a shows the catalyst interfacial FTIR spectrum at -0.4 V vs. RHE for 4000 s in N₂-saturated electrolyte. The resonance peak at 1110 cm⁻¹ can be assigned to the N-N stretching of adsorbed N₂H_x (1 ≤ x ≤ 4) species, with the peak intensity increasing with increasing reaction time.^{40,41} This clearly reflects that the N≡N triple bond is cleaved into a single bond within the catalyst/electrolyte interface. Notably, extra peaks that increased with the reaction time were observed, located at 1320 and 1465 cm⁻¹, corresponding to H-N-H bending and -NH₂ wagging,³⁸ respectively. These results indicate the formation of N₂H_x (1 ≤ x ≤ 4) species on the MoS_{1.79}-H/T interface during the associative nitrogen reduction process. In detail, the molecular N₂ reactant is firstly locked on the surface of the heterogeneous electrocatalyst, and then a proton is attached to dinitrogen to form a -N≡N-H bond, which initially activates the stable triple bond. In the subsequent step, the further hydrogenation process directs the formation of the -H-N=N-H intermediates. Thereafter, along with the continuous electron transfer and hydrogenation, the -H-N=N-H intermediates were further weakened and the double bond was cleaved to form -H-N-NH₂ species, and finally NH₃ was formed on the surface of MoS_{1.79}-H/T under ambient conditions.^{38,39} The MoS_{1.79}-H/T catalyst exhibits negligible changes in FEs and ammonia yielding rates even after 30 continuous electrolysis cycles (Fig. 5b), indicating remarkably stable catalytic activity. After 30 h of electrolysis, MoS_{1.79}-H/T still maintains good electrochemical durability without apparent current fluctuation (Fig. 5c and d). The high stability of the



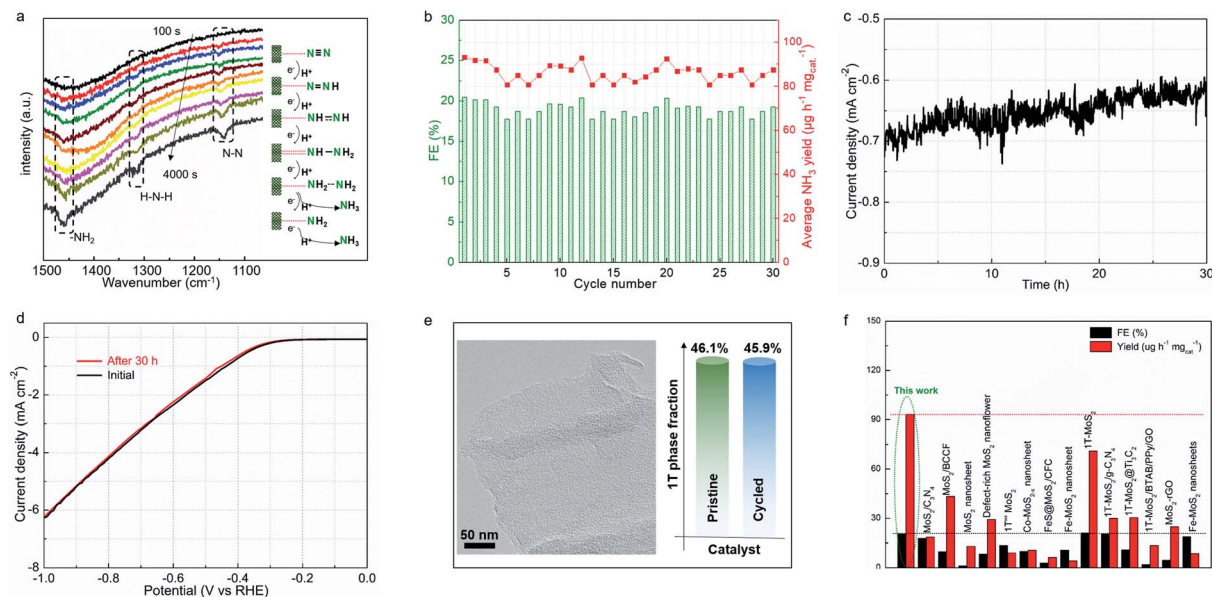


Fig. 5 Operando spectroscopy analysis and stability studies. (a) Electrochemical *in situ* FTIR spectra of the N_2 reduction on the $MoS_{1.79}$ -H/T electrode. (b) Ammonia formation rate and FE of cycles at -0.4 V versus RHE. (c) Evolution of current density for nitrogen reduction in N_2 -saturated electrolyte for 30 h at -0.4 V. (d) LSV curves before and after constant potential tests at -0.4 V vs. RHE. (e) High-resolution TEM image and evolution of the 1T content of $MoS_{1.79}$ -H/T after 30 h of stability testing. (f) NH_3 yield rates and the corresponding FEs of $MoS_{1.79}$ -H/T compared with the reported state-of-the-art MoS_2 -based catalysts.

$MoS_{1.79}$ -H/T monolayer catalyst was also further confirmed by TEM (structure stability) and XPS (phase stability) after stability measurements, from which it is apparent that the catalyst still retains its initial monolayer structure without aggregation and the phase content does not change, as shown in Fig. 5e. Also, as

compared in Fig. 5f, apart from the robustness of $MoS_{1.79}$ -H/T towards nitrogen fixation, the performance of our monolayer catalyst still surpasses those of previously reported MoS_2 -based materials, especially when considering the FEs and ammonia yield rates.^{24,31–35,42–54}


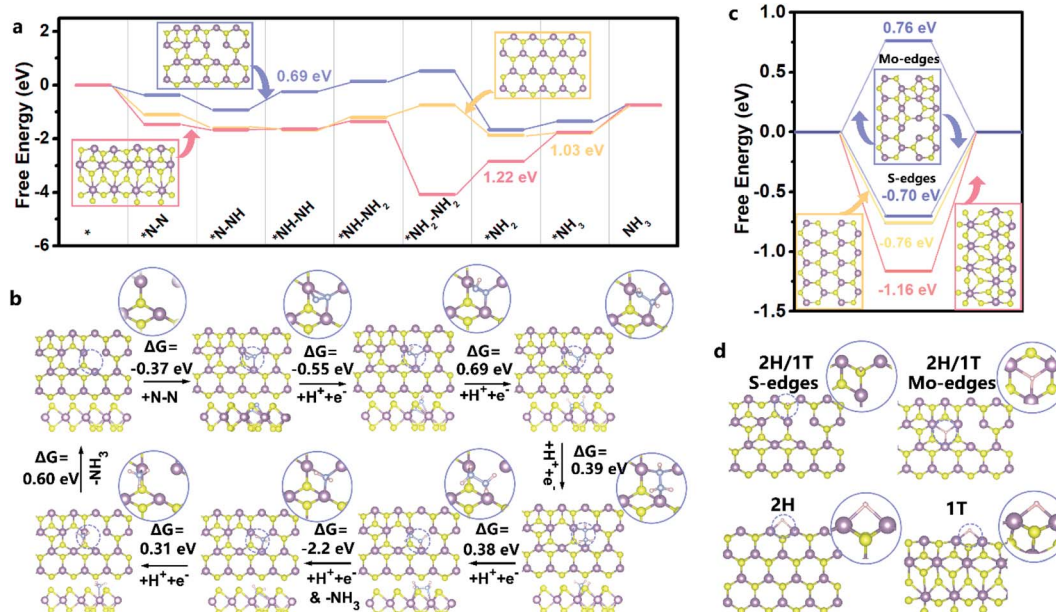


Fig. 6 Density functional theory results and the likely overall NRR mechanism. (a) Gibbs free energy diagrams of the 1T, 2H and SV-rich heterojunctions of the 2H/1T-phases of MoS_2 with the optimum NRR pathway. The PDS and original structures for each reaction are labeled. (b) The front and top views of the 1T, 2H and SV-rich heterojunctions of the 2H/1T-phases of MoS_2 along the bridge enzymatic-alternating-hybrid pathway. (c) HER Gibbs free energy diagrams of the 1T, 2H and SV-rich heterojunctions of the 2H/1T-phases in MoS_2 . (d) The front view of the 1T, 2H and SV-rich heterojunctions of 2H/1T-phases (with Mo and S-edges) in MoS_2 .



To gain deeper mechanistic insights into the nitrogen adsorption and conversion on the SV-rich heterojunctions of 2H/1T-MoS₂, first principle calculations based on DFT were carried out to identify a feasible NRR pathway (bridge enzymatic-alternating-hybrid pathway). The results of pristine 2H-MoS₂ and 1T-MoS₂ were also used for comparison (Fig. S12 and S13†). As shown in Fig. 6a and b, the computed Gibbs free energy diagrams demonstrate that 1T-MoS₂ adsorbs inert N₂ more strongly than the 2H- and heterojunctions of the 2H/1T-phase at the Mo atom (which existed in the heterojunctions and was neighbored by SVs) with the energy for N-N → *N-N being -0.37 eV, -1.46 eV and -1.10 eV for 2H/1T-MoS₂, 1T-MoS₂ and 2H-MoS₂, respectively. The potential-determining step (PDS) was identified as the second hydrogenation of *N-NH to produce *NH-NH for the 2H/1T-MoS₂ catalyst, with the effective energy barrier (U_{eff}) values of -0.69 eV, while the NH₃ desorption was the PDS for the 2H-MoS₂ catalyst, and a related high PDS (-1.22 eV) was calculated for the 1T-MoS₂ system. Besides this, the computed Gibbs free energy for N-N → *N-N were -0.37 eV and -0.04 eV for Mo edges adjacent to SVs and Mo-edges adjacent to sulfur atoms in 2H/1T-MoS₂, respectively, which demonstrated that Mo edges adjacent to SVs are preferential to adsorb nitrogen molecules. The results illustrate that the SVs and heterojunctions in 2H/1T-phase play a key role in enhancing NRR activity, with a lower barrier in PDS toward NRR than that of the 2H or 1T phases.^{12,31}

The HER activity on the 1T, 2H and vacancy-rich heterojunctions of 2H/1T-phases were also explored as it is the major competition to the NRR. As exhibited in Fig. 6c and d, the H atom bound stronger to the Mo atom at the edge of the 1T and 2H phases with hydrogen desorption or combination as the PDS, calculated as -1.16 eV and -0.76 eV, respectively. In addition, the more negative energy of ΔG (N-N → *N-N) in both 1T- and 2H-MoS₂ systems demonstrates that the Mo atom at the edge of the 1T and 2H phases are mainly covered by nitrogen adsorbate. However, in the 1T and 2H phases, the higher PDS ($|U_{\text{eff}}(\text{NRR-2H-MoS}_2)| = -1.22| > |U_{\text{eff}}(\text{HER-2H-MoS}_2)| = -1.16|$ and $|U_{\text{eff}}(\text{NRR-2H-MoS}_2)| = -1.03| > |U_{\text{eff}}(\text{HER-2H-MoS}_2)| = -0.76|$) inhibit the further NRR selectivity. In sharp contrast, the first step and energy barrier of the Mo edges of the 2H/1T-phases of MoS₂ (-0.37 and 0.69 eV) during the NRR is much lower than that of the HER process, which suggests that the Mo sites at the heterojunctions of the 2H/1T-phases prefer the NRR. Significantly, in S sites at heterojunctions of the 2H/1T-phase reaction, the ΔG (H⁺ → H*) = -0.70 eV is more negative than that of Mo, the hydrogenated S sites at heterojunctions act as a H provider to stabilize H_{ad}^{*} and promote the transformation of H_{ad}^{*} from S sites to adsorbed N₂ or nitrogen reduction intermediates on nearby Mo.^{31,44,51,52} Therefore, SV-rich heterostructured 1T/2H-MoS₂ can synchronously lower the energy barrier of the PDS and stabilize H_{ad}^{*}, resulting in a reduction of the competition between the HER and NRR, thus amplifying the selectivity and activity of the NRR.

3. Conclusions

In this contribution, based on molten-sodium-assisted intercalation, a new kind of vacancy- and phase-engineering strategy

was developed to prepare a multisite SV-rich heterostructured 1T/2H-MoS_x monolayer catalyst. The formation of SVs and a heterojunction induced by efficient transition from the 2H to 1T phase of MoS₂ change the local electron density and lower the nitrogen reduction energy barrier in PDS associated with the MoS_x electrocatalyst. The resultant monolayer catalyst exhibits intrinsic selectivities and achieves a faradaic efficiency of 20.5% at -0.4 V vs. RHE and an average rate of 93.2 μg h⁻¹ mg_{cat}⁻¹ for electrocatalytic NH₃ generation. The monolayer catalyst operated stably over 30 h. This study shows fundamental insight into the structure-property relationships of a SV-rich heterostructured MoS_x electrocatalyst for practical application in the conversion of nitrogen.

Data availability

Data available on request.

Author contributions

K. L. conceived and designed the project. H. Z. and B. S. performed all experimental and mechanism studies and wrote the required scripts. All authors were involved in the analysis of the results and further editing and reviewing process.

Conflicts of interest

The authors declare no competing financial interests.

Acknowledgements

This work was financially supported by the Natural Scientific Foundation of China (22109001), the Anhui Provincial Natural Science Foundation (2108085QB58), the Hefei National Laboratory for Physical Sciences at the Microscale (KF2020106), the China Postdoctoral Science Foundation (2022M713039), and the startup funds provided to K. L. from Anhui University.

References

- 1 J. Choi, H. Du, M. Chatti, B. H. R. Suryanto, A. N. Simonov and D. R. MacFarlane, *Nat. Catal.*, 2022, 5, 382.
- 2 M. Légaré, G. Bélanger-Chabot, R. D. Dewhurst, E. Welz, I. Krummenacher, B. Engels and H. Braunschweig, *Science*, 2018, 359, 896.
- 3 S. L. Foster, S. I. P. Bakovic, R. D. Duda, S. Maheshwari, R. D. Milton, S. D. Minter, M. J. Janik, J. N. Renner and L. F. Greenlee, *Nat. Catal.*, 2018, 1, 490.
- 4 S. Chu and A. Majumdar, *Nature*, 2012, 488, 294.
- 5 C. Tang and S. Z. Qiao, *Chem. Soc. Rev.*, 2019, 48, 3166.
- 6 S. Z. Andersen, V. Čolić, S. Yang, J. A. Schwalbe, A. C. Nielander, J. M. Mcenaney, K. Enemark-Rasmussen, J. G. Baker, A. R. Singh, B. A. Rohr, M. J. Statt, S. J. Blair, S. Mezzavilla, J. Kibsgaard, P. C. K. Vesborg, M. Cargnello, S. F. Bent, T. F. Jaramillo, I. E. L. Stephens, J. K. Nørskov and I. Chorkendorff, *Nature*, 2019, 570, 504.
- 7 G. Soloveichik, *Nat. Catal.*, 2019, 2, 377.



- 8 M. Ravi and J. W. Makepeace, *Chem. Sci.*, 2022, **13**, 890–908.
- 9 B. H. R. Suryanto, H. Du, D. Wang, J. Chen, A. N. Simonov and D. R. MacFarlane, *Nat. Catal.*, 2019, **2**, 290.
- 10 G. Qing, R. Ghazfar, S. T. Jackowski, F. Habibzadeh and T. W. Hamann, *Chem. Rev.*, 2020, **120**, 5437.
- 11 S. J. K. Forrest, B. Schluscha, E. Y. Yuzik-Klimova and S. Schneider, *Chem. Rev.*, 2021, **121**, 6522.
- 12 X. Chia, A. Y. S. Eng, A. Ambrosi, S. M. Tan and M. Pumera, *Chem. Rev.*, 2015, **115**, 11941.
- 13 J. Y. Tsai, J. Pan, H. Lin, A. Bansil and Q. Yan, *Nat. Commun.*, 2022, **13**, 492.
- 14 M. Chhowalla, H. S. Shin, G. Eda, L. J. Li, K. P. Loh and H. Zhang, *Nat. Chem.*, 2013, **5**, 263.
- 15 Y. Yu, F. Yang, X. F. Lu, Y. J. Yan, Y. Cho, L. Ma, X. Niu, S. Kim, Y. Son, D. Feng, S. Li, S. Cheong, X. H. Chen and Y. Zhang, *Nat. Nanotechnol.*, 2015, **10**, 270.
- 16 Z. Zheng, L. Yu, M. Gao, X. Chen, W. Zhou, C. Ma, L. Wu, J. Zhu, X. Meng, J. Hu, Y. Tu, S. Wu, J. Mao, Z. Tian and D. Deng, *Nat. Commun.*, 2020, **11**, 3315.
- 17 Y. Zhou, J. Zhang, E. Song, J. Lin, J. Zhou, K. Suenaga, W. Zhou, Z. Liu, J. Liu, J. Lou and H. J. Fan, *Nat. Commun.*, 2020, **11**, 2253.
- 18 J. Xu, G. Shao, X. Tang, F. Lv, H. Xiang, C. Jing, S. Liu, S. Dai, Y. Li, J. Luo and Z. Zhou, *Nat. Commun.*, 2022, **13**, 2193.
- 19 S. Li, Y. Liu, X. Zhao, K. Cui, Q. Shen, P. Li, X. Qu and L. Jiao, *Angew. Chem., Int. Ed.*, 2021, **133**, 20286.
- 20 Y. Wu, J. Wang, Y. Li, J. Zhou, B. Y. Wang, A. Yang, L. Wang, H. Y. Hwang and Y. Cui, *Nat. Commun.*, 2022, **13**, 3008.
- 21 K. F. Mak, K. He, C. Lee, G. H. Lee, J. Hone, T. F. Heinz and J. Shan, *Nat. Mater.*, 2021, **12**, nmat3505-211.
- 22 J. Hong, Z. Hu, M. Probert, K. Li, D. Lv, X. Yang, L. Gu, N. Mao, Q. Feng, L. Xie, J. Zhang, D. Wu, Z. Zhang, C. Jin, W. Ji, X. Zhang, J. Yuan and Z. Zhang, *Nat. Commun.*, 2015, **6**, 197.
- 23 K. F. Mak, C. Lee, J. Hone, J. Shan and T. F. Heinz, *Phys. Rev. Lett.*, 2010, **105**, 136805.
- 24 J. M. Lu, O. Zheliuk, I. Leermakers, N. F. Q. Yuan, U. Zeitler, K. T. Law and J. T. Ye, *Science*, 2015, **350**, 1353.
- 25 X. Li, T. Li, Y. Ma, Q. Wei, W. Qiu, H. Guo, X. Shi, P. Zhang, A. M. Asiri, L. Chen, B. Tang and X. Sun, *Adv. Energy Mater.*, 2018, **8**, 1801357.
- 26 J. Peng, Y. Liu, X. Luo, J. Wu, Y. Lin, Y. Guo, J. Zhao, X. Wu, C. Wu and Y. Xie, *Adv. Mater.*, 2019, **31**, 1900568.
- 27 M. Acerce, D. Voiry and M. Chhowalla, *Nat. Nanotechnol.*, 2015, **10**, 313.
- 28 J. Zou, F. Li, M. A. Bissett, F. Kim and L. J. Hardwick, *Electrochim. Acta*, 2020, **331**, 135284.
- 29 K. Lu, Y. Liu, F. Lin, I. A. Cordova, S. Gao, B. Li, B. Peng, H. Xu, J. Kaelin, D. Coliz, C. Wang, Y. Shao and Y. Cheng, *J. Am. Chem. Soc.*, 2020, **142**, 12613.
- 30 S. Park, C. Kim, S. O. Park, N. K. Oh, U. Kim, J. Lee, J. Seo, Y. Yang, H. Y. Lim, S. K. Kwak, G. Kim and H. Park, *Adv. Mater.*, 2020, **32**, 2001889.
- 31 J. Zhang, A. Yang, X. Wu, J. Groep, P. Tang, S. Li, B. Liu, F. Shi, J. Wan, Q. Li, Y. Sun, Z. Lu, X. Zheng, G. Zhou, C. Wu, S. Zhang, M. L. Brongersma, J. Li and Y. Cui, *Nat. Commun.*, 2018, **9**, 5289.
- 32 R. Liu, T. Guo, H. Fei, Z. Wu, D. Wang and F. Liu, *Adv. Sci.*, 2021, 2103583.
- 33 G. Lin, Q. Ju, X. Guo, W. Zhao, S. Adimi, J. Ye, Q. Bi, J. Wang, M. Yang and F. Huang, *Adv. Mater.*, 2021, 2007509.
- 34 X. Xua, X. Tian, B. Sun, Z. Liang, H. Cui, J. Tian and M. Shao, *Appl. Catal. B*, 2020, **272**, 118984.
- 35 H. Mao, Y. Fu, H. Yang, Z. Deng, Y. Sun, D. Liu, Q. Wu, T. Ma and X. Song, *ACS Appl. Mater. Interfaces*, 2020, **12**, 25189.
- 36 B. Pattengale, Y. Huang, X. Yan, S. Yang, S. Younan, W. Hu, Z. Li, S. Lee, X. Pan, J. Gu and J. Huang, *Nat. Commun.*, 2020, **11**, 4114.
- 37 Z. Shang, B. Song, H. Li, H. Zhang, F. Feng, J. Kaelin, W. Zhang, B. Xie, Y. Cheng, K. Lu and Q. Chen, *CCS Chem.*, 2021, **3**, 2104.
- 38 K. Lu, F. Xia, B. Li, Y. Liu, I. B. A. Razak, S. Gao, J. Kaelin, D. E. Brown and Y. Cheng, *ACS Nano*, 2021, **15**, 16887.
- 39 H. Cheng, L. Ding, G. Chen, L. Zhang, J. Xue and H. Wang, *Adv. Mater.*, 2018, **30**, 1803694.
- 40 M. Wang, S. Liu, H. Ji, T. Yang, T. Qian and C. Yan, *Nat. Commun.*, 2021, **12**, 3198.
- 41 Z. Shang, B. Song, H. Li, H. Zhang, F. Feng, J. Kaelin, W. Zhang, B. Xie, Y. Cheng, K. Lu and Q. Chen, *CCS Chem.*, 2022, **4**, 2115.
- 42 Y. Yao, H. Wang, X. Yuan, H. Li and M. Shao, *ACS Energy Lett.*, 2019, **4**, 1336.
- 43 P. Song, H. Wang, L. Kang, B. Ran, H. Song and R. Wang, *Chem. Commun.*, 2019, **55**, 687.
- 44 K. Chu, Y. Liu, Y. Li, Y. Guo and Y. Tian, *ACS Appl. Mater. Interfaces*, 2020, **12**, 7081.
- 45 Y. Liu, M. Han, Q. Xiong, S. Zhang, C. Zhao, W. Gong, G. Wang, H. Zhang and H. Zhao, *Adv. Energy Mater.*, 2018, **9**, 1803935.
- 46 L. Zhang, X. Ji, X. Ren, Y. Ma, X. Shi, Z. Tian, A. M. Asiri, L. Chen, B. Tang and X. Sun, *Adv. Mater.*, 2018, **30**, 1800191.
- 47 B. H. R. Suryanto, D. Wang, L. M. Azofra, M. Harb, L. Cavallo, R. Jalili, D. R. G. Mitchell, M. Chatti and D. R. MacFarlane, *ACS Energy Lett.*, 2018, **4**, 430.
- 48 J. Zhang, X. Tian, M. Liu, H. Guo, J. Zhou, Q. Fang, Z. Liu, Q. Wu and J. Lou, *J. Am. Chem. Soc.*, 2019, **141**, 19269.
- 49 Y. Guo, Z. Yao, B. J. J. T. X. Sheng, L. Fan, Y. Li, F. Zhang and L. Sun, *Nano Energy*, 2019, **62**, 282.
- 50 X. Zhao, X. Zhang, Z. Xue, W. Chen, Z. Zhou and T. Mu, *J. Mater. Chem. A*, 2019, **7**, 27417.
- 51 X. Xu, B. Sun, Z. Liang, H. Cui and J. Tian, *ACS Appl. Mater. Interfaces*, 2020, **12**, 26060.
- 52 X. Li, X. Ren, X. Liu, J. Zhao, X. Sun, Y. Zhang, X. Kuang, T. Yan, Q. Wei and D. Wu, *J. Mater. Chem. A*, 2019, **7**, 2524.
- 53 H. Su, L. Chen, Y. Chen, R. Si, Y. Wu, X. Wu, Z. Geng, W. Zhang and J. Zeng, *Angew. Chem., Int. Ed.*, 2020, **132**, 20591.
- 54 Y. Ma, T. Yang, H. Zou, W. Zang, Z. Kou, L. Mao, Y. Feng, L. Shen, S. J. Pennycook, L. Duan, X. Li and J. Wang, *Adv. Mater.*, 2020, **32**, 200217.

