

Cite this: *Nanoscale Adv.*, 2023, 5, 6913

# Formation of intermetallic PdIn nanoparticles: influence of surfactants on nanoparticle atomic structure†

Baiyu Wang,<sup>a</sup> Jette K. Mathiesen,<sup>b</sup> Andrea Kirsch,<sup>a</sup> Nicolas Schlegel,<sup>c</sup> Andy S. Anker,<sup>a</sup> Frederik L. Johansen,<sup>a</sup> Emil T. S. Kjær,<sup>a</sup> Olivia Aalling-Frederiksen,<sup>a</sup> Tobias M. Nielsen,<sup>a</sup> Maria S. Thomsen,<sup>a</sup> Rasmus K. Jakobsen,<sup>a</sup> Matthias Arenz<sup>c</sup> and Kirsten M. Ø. Jensen<sup>a\*</sup>

Bimetallic nanoparticles have been extensively studied as electrocatalysts due to their superior catalytic activity and selectivity compared to their monometallic counterparts. The properties of bimetallic materials depend on the ordering of the metals in the structure, and to tailor-make materials for specific applications, it is important to be able to control the atomic structure of the materials during synthesis. Here, we study the formation of bimetallic palladium indium nanoparticles to understand how the synthesis parameters and additives used influence the atomic structure of the obtained product. Specifically, we investigate a colloidal synthesis, where oleylamine was used as the main solvent while the effect of two surfactants, oleic acid (OA) and trioctylphosphine (TOP) was studied. We found that without TOP included in the synthesis, a Pd-rich intermetallic phase with the Pd<sub>3</sub>In structure initially formed, which transformed into large NPs of the CsCl-structured PdIn phase. When TOP was included, the syntheses yielded both In<sub>2</sub>O<sub>3</sub> and Pd<sub>3</sub>In. *In situ* X-ray total scattering with Pair Distribution Function analysis was used to study the formation process of PdIn bimetallic NPs. Our results highlight how seemingly subtle changes to material synthesis methods can have a large influence on the product atomic structure.

Received 1st August 2023  
Accepted 31st October 2023

DOI: 10.1039/d3na00582h

rsc.li/nanoscale-advances

## Introduction

Bimetallic nanoparticles (NPs) have drawn extensive attention due to their widespread use in (electro)catalysis.<sup>1</sup> Compared to monometallic NPs, bimetallic NPs provide greater flexibility as their catalytic properties can be tuned by optimizing their surface structure for specific reactions. Palladium based bimetallic systems have emerged as one of the most promising catalysts in the fields of environment protection and renewable energy conversion, as they usually show higher specific activity and selectivity than that of pure Pd for several important reactions.<sup>2–4</sup> For example, intermetallic PdIn NPs show higher selectivity for ethane dehydrogenation compared to monometallic Pd catalysts.<sup>5,6</sup> Furthermore, bimetallic catalysts such

as PdIn make use of non-precious metals to replace parts of Pd, which reduces catalyst costs.

Intermetallic NPs, where the different elements are ordered in specific sites in the crystal lattice, very often show better catalytic properties than disordered alloy structures.<sup>5,7,8</sup> The atomic ordering affects the interaction energy of the chemical intermediates that adsorb and react during the catalytic reaction, and the catalytic properties can be tuned.<sup>7,9,10</sup> When developing synthesis methods for bimetallic NPs, it is therefore important to be able to control the NP atomic structure. Pd–In based NPs are known in several different intermetallic structures, including PdIn, taking the CsCl-structure (Fig. 1a) and tetragonal Pd<sub>3</sub>In. PdIn is thermodynamically stable up to 1285 °C for Pd% *ca.* 50–60%, while Pd<sub>3</sub>In is thermodynamically stable to 1030 °C for Pd% *ca.* 68–70%.<sup>11,12</sup> The Pd<sub>3</sub>In structure reported in space group *P4/mmm* is shown in Fig. 1b.<sup>13</sup> Pd<sub>3</sub>In has, however, been described in several tetragonal structures with different levels of order between Pd and In, and neutron diffraction studies by Kohlman and Ritter<sup>12,14</sup> have shown that the atoms order further than the simple structure illustrated in Fig. 1b, leading to larger unit cells.<sup>12,14</sup> Other compositions and structures have also been reported, including orthorhombic In<sub>3</sub>Pd<sub>5</sub> and InPd<sub>2</sub>.<sup>11,12</sup>

<sup>a</sup>Department of Chemistry, University of Copenhagen, Universitetsparken 5, 2100 Copenhagen Ø, Denmark. E-mail: kirsten@chem.ku.dk

<sup>b</sup>Department of Physics, Technical University of Denmark, Fysikvej, 2800 Kongens Lyngby, Denmark

<sup>c</sup>Department of Chemistry, Biochemistry and Pharmaceutical Sciences, University of Bern, Freiestrasse 3, 3012 Bern, Switzerland

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3na00582h>

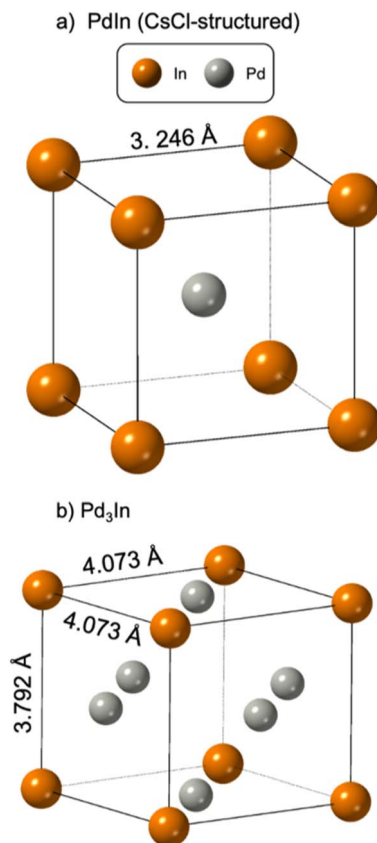


Fig. 1 Structure drawing of (a) PdIn (spacegroup  $Pm\bar{3}m$ ) and (b) Pd<sub>3</sub>In (spacegroup  $P4/mmm$ ).

Intermetallic PdIn NPs with the CsCl type structure are commonly synthesized using high temperature (*e.g.* 700 °C) annealing or by using harsh reducing agents (*e.g.* NaBH<sub>4</sub>).<sup>5,6,15</sup> However, due to the tendency of NPs to undergo sintering and degradation at high annealing temperatures, the ability to design small, monodisperse nanoparticles is severely constrained when using this synthesis approach. When using a harsh reducing agent, rapid nucleation can occur which hinders control of the NP formation and growth. Recently, new synthesis pathways of binary metal NPs using organic solvents have been developed, which enable controlled reactions at lower temperatures (*e.g.* 200 °C).<sup>16–18</sup> These methods rely on reduction of metal salts or seed-mediated approaches. However, despite the recent developments in the field, the reaction mechanism of the formation of intermetallic NPs, including PdIn are not well understood. To control NP structure and obtain the desired properties, it is critical to obtain insight into the relation between synthesis and structure.

By combining synthesis parameter studies and *in situ* X-ray scattering studies,<sup>19–22</sup> we here show that the formation of PdIn intermetallic NPs can be controlled by using selected capping agents in the synthesis. Our results show an initial formation of a Pd-rich, Pd<sub>3</sub>In-like phase which eventually transforms into PdIn NPs. The phase transformation process can be slowed down by using oleic acid (OA) as a surfactant in the synthesis. When adding trioctylphosphine (TOP) in the

synthesis, an indium hydroxide phase, In(OH)<sub>3</sub>, initially forms and transforms into an oxide phase (In<sub>2</sub>O<sub>3</sub>), which forms along with Pd<sub>3</sub>In. When OA and TOP are added together to the synthesis, the In<sub>2</sub>O<sub>3</sub> phase forms directly, followed by the formation of Pd<sub>3</sub>In. Our study thus shows how addition of surfactants and capping agents have a large influence on the NP formation pathway and their atomic structure.

## Methods

### Chemicals

Palladium(II) acetylacetonate (Pd(acac)<sub>2</sub>, 99%), palladium(II) bromide (PdBr<sub>2</sub>, 99%), indium(III) acetate (In(ac)<sub>3</sub>, 99.99%), trioctylphosphine (TOP, 97%), oleic acid (OA, 90%), ascorbic acid and oleylamine (OLA, 70%) were all purchased from Sigma-Aldrich. Indium(III) chloride (InCl<sub>3</sub>, 99%) was purchased from Alfa Aesar. Hexane (97%) and ethanol (96%) were bought from VWR Chemicals. All the chemicals were used as received.

### Synthesis of PdIn NPs

In a typical synthesis, a mixture of 1.12 mmol Pd-precursor (PdBr<sub>2</sub> or Pd(acac)<sub>2</sub>), 1.12 mmol In-precursor (In(ac)<sub>3</sub> or InCl<sub>3</sub>), 7.8 mL of OLA, 0.77 mL OA and 0.77 mL TOP were heated in air to 110 °C under magnetic stirring in a 100 mL three-neck flask for 30 minutes. The resulting mixture was further heated to 235 °C, where the NP formation was clearly observed by a color change in the solution from yellow to black. The colloidal suspension was maintained at this temperature for 2 hours before it was cooled to room temperature. The final product was collected by centrifugation at 9000 rpm and washed with an ethanol/hexane mixture five times. The product was dispersed in 4 mL of hexane.

### Characterization

The resulting samples were drop-casted and dried on a glass wafer and mounted on a zero-background sample holder. Laboratory powder X-ray diffraction (PXRD) measurements were performed on a Bruker D8 instrument with Cu K $\alpha$  radiation in the  $2\theta$  range 10°–80°. The PXRD data were analyzed using Rietveld refinement in Topas Academic.<sup>23</sup> The instrument resolution function was determined using a corundum (Al<sub>2</sub>O<sub>3</sub>) standard sample. Refined parameters include the scale factor and the lattice parameters for the respective phases. The average crystallite sizes were determined from all observed reflections using the integral breadth of the respective profile functions fitted with Gaussian and Lorentzian components and given by the Topas suite as LVol-IB.

TEM images were acquired on an FEI Tecnai Spirit using a Tungsten filament at an acceleration voltage of 80 kV. For sample preparation, the powders were first dispersed in ethanol ( $\sim 0.8$  mg mL<sup>−1</sup><sub>EtOH</sub>). Using both a bath and a horn sonicator, the dispersion was homogenized. The EtOH/sample vial was cooled in an ice bath when using the horn sonicator. Then, 20  $\mu$ L of the respective sample dispersion was pipetted onto a cuprous TEM grid (QUANTIFOIL, Classic Holey Carbon films). The grids were then left to dry at ambient conditions.



Absorption spectra were recorded on a Lambda 1050 UV/VIS/NIR absorption spectrometer from PerkinElmer using a halogen lamp as excitation source. The samples were prepared by filtering off any larger aggregates with syringe filters (Frisenette QMax RR syringe filters 13 mm PTFE hydrophobic). Heptane was used for the solvent background and was subtracted manually from the spectra. Slits were kept at 1 nm.

### *In situ* X-ray total scattering (TS) studies

All X-ray TS data were collected at beamline P21.1, DESY, Hamburg, Germany. All data were collected using an X-ray wavelength of 0.122 Å and an area detector, placed *ca.* 39 cm from the sample. The synthesis experiments were done using a 3 mm NMR tube, which was filled with precursor solution and heated to 235 °C using a block heater while collecting temperature-resolved X-ray TS patterns. Calibration of instrumental parameters was done using Fit2D and the data were integrated using Dioptas.<sup>24,25</sup> The total scattering data were corrected and normalized to obtain the reduced total scattering function  $F(Q)$ , which was Fourier transformed to obtain the Pair Distribution Function (PDF) using xPDFsuite.<sup>26</sup> The following parameters were used in xPDFsuite:  $Q_{\min} = 1.6 \text{ Å}^{-1}$ ,  $Q_{\max} = 18 \text{ Å}^{-1}$ ,  $Q_{\max_{\text{inst}}} = 23 \text{ Å}^{-1}$  and  $r_{\text{poly}} = 0.9 \text{ Å}$ . The PDFs were modeled using PDFgui.<sup>27</sup>

## Results and discussion

### Influence of metal precursor salt

We first consider how the metal ion precursors affect the atomic structure of the resulting NPs, as these can have a large influence on the NP formation process. Specifically, we investigate metal halides (chlorides and bromides) and metal acetyl acetonates. Metal halides are commonly used for synthesis of bi- and inter-metallic NPs.<sup>17,28</sup> Firstly, it is well-known that halide ions (*e.g.*  $\text{Cl}^-$ ,  $\text{Br}^-$ ) can modify reduction kinetics and the atom diffusion/exchange rate by coordinating with metal ions during the synthesis of metallic NPs.<sup>28</sup> Secondly, halide ions facilitate oxidative etching in the presence of oxygen, which can influence the growth mode.<sup>29</sup> Metal acetylacetonate (acac) and acetate precursors are also commonly used in NP synthesis due to their low decomposition temperatures, large coordination capacity, and potential for commercialization.<sup>30,31</sup> Acac and acetate ligands furthermore have a high degree of resonance stabilization, making them ideal leaving groups in reduction reactions.

Here, we investigate palladium(II) bromide ( $\text{PdBr}_2$ ) and indium(III) chloride ( $\text{InCl}_3$ ) as halide precursors, and palladium(II) acetylacetonate ( $\text{Pd}(\text{acac})_2$ ) and indium(III) acetate ( $\text{In}(\text{ac})_3$ ) as metal organic precursors. Four syntheses with different combinations of metal precursors were carried out: (a1)  $\text{InCl}_3 + \text{Pd}(\text{acac})_2$ , (b1)  $\text{InCl}_3 + \text{PdBr}_2$ , (c1)  $\text{In}(\text{ac})_3 + \text{PdBr}_2$ , and (d1)  $\text{In}(\text{ac})_3 + \text{Pd}(\text{acac})_2$ . The synthesis method used here is inspired by a study from Wang *et al.*,<sup>32</sup> where mixed metal precursors and oleylamine (OLA) are heated in air to a certain reaction temperature to obtain intermetallic NPs.

Powder X-ray diffraction (PXRD) patterns of the products from the four syntheses are shown in Fig. 2. If first considering

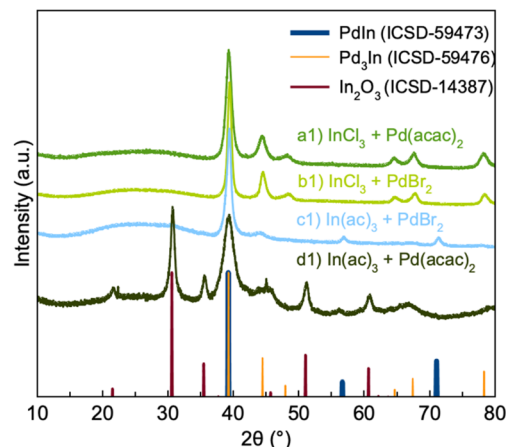


Fig. 2 PXRD patterns of PdIn NPs synthesized from different combinations of metal ion precursors: (a1)  $\text{InCl}_3 + \text{Pd}(\text{acac})_2$ , (b1)  $\text{InCl}_3 + \text{PdBr}_2$ , (c1)  $\text{In}(\text{ac})_3 + \text{PdBr}_2$ , and (d1)  $\text{In}(\text{ac})_3 + \text{Pd}(\text{acac})_2$ . The calculated diffraction patterns of  $\text{PdIn}$ ,  $\text{Pd}_3\text{In}$  and  $\text{In}_2\text{O}_3$  are plotted for reference.

synthesis a1 and b1, we see that the PXRD pattern from their products show diffraction peaks corresponding to  $\text{Pd}_3\text{In}$ . However, quantitative analysis through Rietveld analysis shows that a single  $\text{Pd}_3\text{In}$  phase does not give a sufficient description of the data. Fits were done using both the simple  $\text{Pd}_3\text{In}$  structure in spacegroup  $P4/mmm$  (Fig. 1b), and the structures described by Kohlman and Ritter to take the  $\text{TiAl}_3$  and  $\text{ZrAl}_3$  structures in spacegroup  $I4/mmm$ . The difference between the structures is the distribution of Pd and In atoms. As Pd and In scatter X-rays very similarly (46 and 49 electrons, respectively) we are not able to distinguish the structures, and they yield comparable, poor fit qualities for our data. Specifically, the asymmetry and width seen in the peak at *ca.* 45° are poorly fitted by all reported phases. Instead, we found that including a second  $\text{Pd}_3\text{In}$  phase, whose lattice parameters are refined independently of the first, provides an adequate description of the data (Fig. S1b†). For simplicity, both phases are described by the small unit cell in space group  $P4/mmm$ . The lattice parameters of the two phases in sample a1 (Table S1†) refine to  $a = 4.0929(8) \text{ Å}$ ,  $c = 3.759(1) \text{ Å}$  and  $a = 4.044(2) \text{ Å}$ ,  $c = 3.833(3) \text{ Å}$ . The need for two separate  $\text{Pd}_3\text{In}$  phases may relate to the presence of different stoichiometries than  $\text{Pd}_3\text{In}$  in the particles. In has a slightly larger metallic radius than Pd, and a higher In content will thus lead to larger unit cells. It has previously been suggested that intermetallics of the  $\text{Pd}_3\text{In}$  structure type may form even for non-ideal stoichiometries.<sup>12</sup> We thus hypothesize that the product from synthesis a1 and b1 may not be stoichiometric  $\text{Pd}_3\text{In}$ , but rather particles with a continuum of different Pd–In ratios, as will be discussed further below when describing the *in situ* experiments.

Our Rietveld analyses indicate average  $\text{Pd}_3\text{In}$  crystallite sizes (averaged over the two  $\text{Pd}_3\text{In}$  phases used for fitting the data) of *ca.* 6 and 10 nm for sample a1 and b1, respectively (Fig. S1b(e), (f) and Table S1†). The results suggest that bromide ions from the precursor may promote NP growth. A previous study has shown that  $\text{Br}^-$  ions allow NP growth by destabilizing the





interaction between the NP surface atoms and the stabilizing agents/surfactants in the synthesis.<sup>32</sup> Here, we thus hypothesize that  $\text{Br}^-$  ions in synthesis b1 destabilize the OLA-NPs surface interaction, resulting in the formation of larger  $\text{Pd}_3\text{In}$  NPs.

The PXRD pattern of the product from synthesis c1 displays peaks from both  $\text{Pd}_3\text{In}$  and  $\text{PdIn}$ . Quantitative analysis was again done through Rietveld refinement (Fig. S1a(a)†). For simplicity, the  $\text{Pd}_3\text{In}$  signal was here described with a single phase, which gives an adequate description of the data. The refinements indicate *ca.* equal amounts of  $\text{PdIn}$  (46%) and  $\text{Pd}_3\text{In}$  (54%) obtained from synthesis c1 (Table S1†). The only difference between synthesis b1 and c1 is the use of  $\text{In}(\text{ac})_3$  in synthesis c1, and the nature of the indium precursor thus appears to be critical for forming  $\text{PdIn}$ . The acetate ligand is a better leaving group compared to the chloride ion due to its high degree of resonance stabilization. We hypothesize that this leads to more indium to be incorporated into the NP structure, leading to the formation of a 1:1 intermetallic phase. The crystallite sizes refine to *ca.* 4 nm for  $\text{Pd}_3\text{In}$  and 10 nm for  $\text{PdIn}$ .

The PXRD pattern of the product from synthesis d1 shows peaks from both  $\text{Pd}_3\text{In}$  and  $\text{In}_2\text{O}_3$  along with sharp peaks around  $22^\circ$  and  $45^\circ$   $2\theta$  which likely originate from unreduced metal precursors. This again suggests that the presence of bromide is important for forming the intermetallic  $\text{PdIn}$  phase.

### Influence of surfactants

As observed above, formation of  $\text{PdIn}$  can be promoted using specific metal ion precursors. Besides using the precursor salt for controlling the inherent ligand environment surrounding the metal, the local chemistry can also be tuned through ligand exchange by introducing different surfactants of varying binding affinities. Normally, surfactants are introduced in colloidal NP syntheses to obtain different NP sizes and morphologies.<sup>33,34</sup> However, surfactants can also influence the formation of nanocrystals by forming metal–ligand complexes through ligand exchange.<sup>35</sup> We here consider the use of oleic acid (OA) and trioctylphosphine (TOP) as surfactants. OA is often used as a surfactant because of its ability to form metal–oleate complexes. Previously, Park *et al.* have shown that metal–oleate complexes formed from metal ions and OA ligands thermally decompose into monodisperse NPs.<sup>36</sup> TOP has been used as surfactant in the synthesis of cubic metal NPs to promote certain facets.<sup>37,38</sup> Together with OA, TOP has furthermore been used to obtain shape control of nanocrystals.<sup>39</sup> In order to study the effect of OA and TOP in the synthesis of  $\text{PdIn}$  NPs, we performed three additional syntheses. PXRD data from these are shown in Fig. 3a, where the syntheses are labeled as (c1) OLA, (c2) OLA + OA, (c3) OLA + TOP, and (c4) OLA + OA + TOP. In all four syntheses,  $\text{In}(\text{ac})_3$  and  $\text{PdBr}_2$  were used as metal precursors. TEM images from the four syntheses are shown in Fig. 3b–e.

We first investigate synthesis c2 with the addition of OLA and OA. As also seen when only using OLA (*i.e.*, synthesis c1), synthesis c2 produces both  $\text{PdIn}$  and  $\text{Pd}_3\text{In}$  NPs. Rietveld refinement (Fig. S1a(b)†) reveals that NPs from synthesis c2 also consist of *ca.* equal amounts of the two phases (53%  $\text{PdIn}$  and

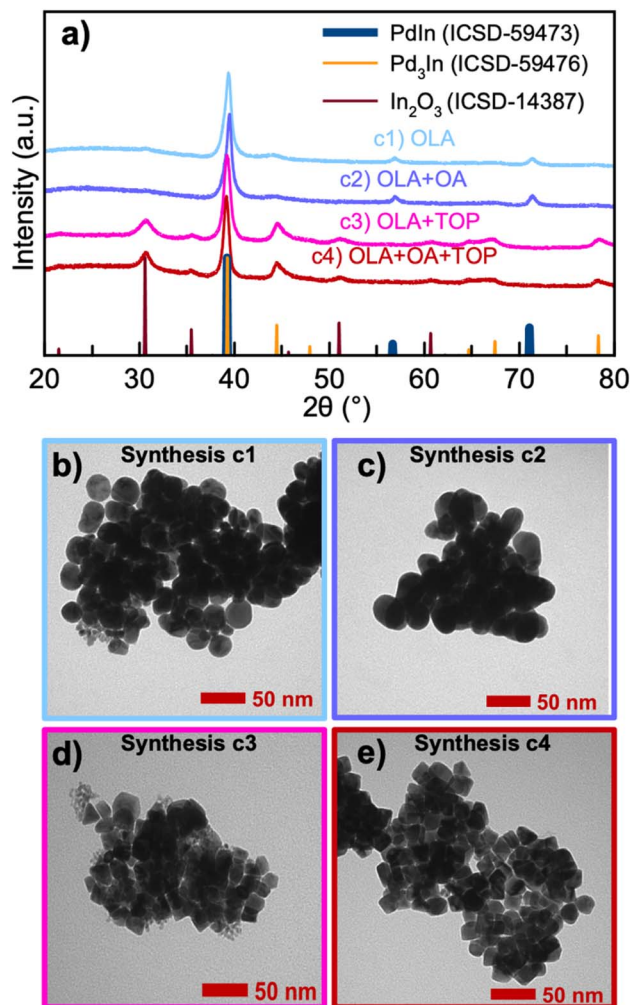


Fig. 3 (a) PXRD patterns from  $\text{PdIn}$  NPs synthesized from different combinations of surfactants: (c1) OLA, (c2) OLA + OA, (c3) OLA + TOP, (c4) OLA + OA + TOP. The calculated diffraction patterns of  $\text{PdIn}_3$ ,  $\text{PdIn}$  and  $\text{In}_2\text{O}_3$  are plotted for reference. (b)–(e) TEM images of NPs from synthesis c1–c4 respectively.

47%  $\text{Pd}_3\text{In}$ ), and as was seen for synthesis c1, the  $\text{PdIn}$  crystallites are much larger than the  $\text{Pd}_3\text{In}$  particles (11.0(1) and 3.9(2) nm, respectively). At a first glance, the addition of OA thus has little effect on the synthesis, although this will be discussed further when describing *in situ* results below.

The TEM images for synthesis c1 and c2 show highly agglomerated nanoparticles of mostly spherical shape. While the agglomeration makes further analysis from these images difficult, the TEM images show nanoparticles of varying sizes. The image presented for synthesis c1 show the presence of smaller nanoparticles (less than 5–10 nm) along with larger particles in the 20–40 nm size range. The large size distribution agrees with the PXRD results, and indicates that the  $\text{Pd}_3\text{In}$  and  $\text{PdIn}$  phases exist as separate particles. However, we note that our current analysis does not allow to determine if core–shell, core–satellites, or janus particles have formed, or if the OA addition has a significant effect on the particle shape. Further high resolution TEM analyses of the nanostructure in the



samples would be needed to address this, which is beyond the scope of the study.

Both syntheses c3 and c4 with the presence of TOP produce NPs with a mix of two phases: Pd<sub>3</sub>In and In<sub>2</sub>O<sub>3</sub> (see Fig. 3a). Rietveld refinement (Fig. S1a(c), (d) and Table S1†) shows that c3 leads to *ca.* 67 w% Pd<sub>3</sub>In, while c4 leads to *ca.* 76 w% Pd<sub>3</sub>In. Here, we have again described the Pd<sub>3</sub>In component with two phases with different lattice parameters, which indicates the presence of Pd<sub>3</sub>In-structured nanoparticles with different compositions. The presence of In<sub>2</sub>O<sub>3</sub> shows that part of the In<sup>3+</sup> ions are not reduced. It is well-known that TOP coordinates with Pd<sup>2+</sup> ions to form a Pd(II)–TOP complex,<sup>40–42</sup> and a change in the absorption is indeed observed when Pd(II) is added to a solution containing TOP (Fig. S2†). The presence of TOP may therefore have slowed down the reduction of Pd as TOP binds with Pd<sup>2+</sup> and blocks access from the OLA. This hinders the formation of the bimetallic phase with In, which leads to the formation of In<sub>2</sub>O<sub>3</sub>. Indeed, previous studies have shown that thermal decomposition of In(ac)<sub>3</sub> in air is followed by the formation of In<sub>2</sub>O<sub>3</sub>.<sup>43</sup> It is observed from TEM images, see Fig. 3d and e, that NPs with different morphologies start to emerge in syntheses c3 and c4. NPs in rectangular or triangular shapes with sharp edges are present in both syntheses. This can be related to the fact that TOP favors binding on specific facets and thereby influences the shape of NPs.<sup>37,44</sup>

To promote In<sup>3+</sup> reduction, syntheses with ascorbic acid (AA) were performed. AA is commonly used in NP synthesis to facilitate faster reduction of metal ion species. We conducted four additional syntheses, using (c5) OLA + AA, (c6) OLA + OA + AA, (c7) OLA + TOP + AA and (c8) OLA + OA + TOP + AA. As seen in Fig. S3,† syntheses c5 and c6 produce PdIn and Pd<sub>3</sub>In, and the results are thus comparable to syntheses c1 and c2. Nevertheless, slightly more PdIn forms in the presence of AA, with 64 w% PdIn for c5, and 67 w% PdIn for c6. However, when comparing syntheses c3 and c4 (with TOP present) with syntheses c7 and c8 (with TOP and AA present), they all produce both Pd<sub>3</sub>In and In<sub>2</sub>O<sub>3</sub> NPs. This suggests that the addition of AA does not directly promote the reduction of In<sup>3+</sup> due to the continued presence of In<sub>2</sub>O<sub>3</sub>. However, AA promotes the formation of PdIn when the right conditions for its formation are already present, as is the case for synthesis c5 and c6.

### Influence of reaction temperature

We also carried out syntheses c1 and c2 (synthesis in pure OLA and with the addition of OA) with all synthetic conditions kept the same, except a reaction temperature of 180 °C instead of 235 °C. Fig. 4 compares the PXRD patterns for the products from syntheses c1 and c2 and those obtained at lower reaction temperature, referred to as syntheses ci and cii. Interestingly, synthesis ci produces Pd<sub>3</sub>In and In<sub>2</sub>O<sub>3</sub> NPs. Rietveld refinements are shown in Fig. S1b(c) and (d).† On the other hand, synthesis cii with OA does not yield In<sub>2</sub>O<sub>3</sub>. Instead, Rietveld refinements show that the product can again be described by two Pd<sub>3</sub>In phases. However, the lattice parameters for one of the phases refines to be almost cubic and close to that of pure Pd (Table S1,† *a* = 4.009(2) Å and *c* = 3.906(2) Å). A similar fit

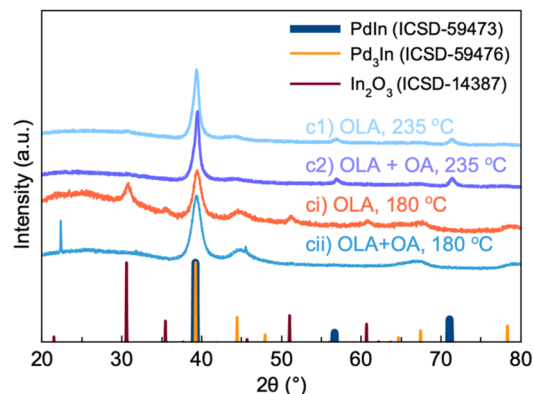


Fig. 4 PXRD patterns of NPs synthesized at 180 °C for 2 h, using PdBr<sub>2</sub> and In(ac)<sub>3</sub> as metal precursors, including (ci) OLA and (cii) OLA + OA. PXRD patterns from synthesis c1 and c2 are shown for comparison.

quality can be obtained if using a cubic fcc Pd phase along with the tetragonal Pd<sub>3</sub>In phase. The results from reaction ci and cii show that the reaction temperature is crucial for forming the PdIn intermetallic phase. At 235 °C, more indium appears to be incorporated into the NPs, which can promote the formation of stoichiometric PdIn.

We here note that while most pronounced in sample cii, the tendency of the second Pd<sub>3</sub>In phase to refine towards a cubic phase is also present in the other samples (Table S1†). In general, the lattice parameters for Pd<sub>3</sub>In vary significantly stronger than the ones of PdIn and In<sub>2</sub>O<sub>3</sub>, which always refine to the same values. This fact strengthens our hypothesis that the Pd<sub>3</sub>In structure can form with different chemical distributions of Pd and In.

### In situ studies of PdIn nanoparticle formation: influence of OA


From the parametric synthesis study, we found that in both pure OLA and with OA added (syntheses c1 and c2), a two-phase mixture of Pd<sub>3</sub>In and PdIn was formed, while the addition of TOP (syntheses c3 and c4) lead to Pd<sub>3</sub>In and In<sub>2</sub>O<sub>3</sub> NPs. To obtain further insight into the formation process and role of surfactants, we performed *in situ* X-ray scattering experiments. *In situ* X-ray TS with Pair Distribution Function (PDF) analysis allows us to follow the real-time structural changes during the reaction and to identify the key intermediate structures involved.

Fig. 5 displays *in situ* data from synthesis c1 and c2. The data are presented as the reduced structure function  $F(Q)$ , which is obtained from the X-ray scattering data as:

$$F(Q) = \frac{Q}{Nf^2} ([I_{\text{coh}}(Q) + \langle f^2 \rangle - \langle f^2 \rangle] - 1)$$

here,  $\langle f \rangle$  is the average form factor for the atoms present in the sample, and  $I_{\text{coh}}$  is the coherent scattering signal obtained from the corrected and background subtracted data.<sup>45</sup>  $Q$  is defined as  $Q = 4\pi \sin(\theta)/\lambda$ . The presentation of the reduced structure function  $F(Q)$  rather than the raw scattering data highlights the scattering features also at higher  $Q$ -values.



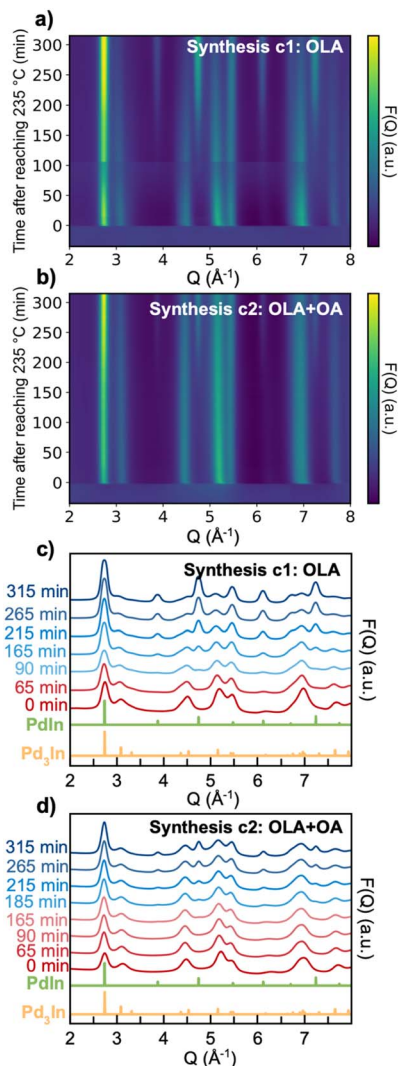


**Fig. 5** *In situ* X-ray TS data of the formation of intermetallic PdIn NPs. (a) and (b) *In situ* X-ray data plotted as the reduced structure function  $F(Q)$  from syntheses c1 and c2, respectively. (c) and (d) Selected experimental background-subtracted  $F(Q)$ s from different reaction times as indicated. The time scale displayed for the datasets is defined from when 235 °C has been reached in each experiment (i.e.,  $t = 0$  minutes). Note that in 5a at ca. 130 min, the peak intensities decrease and then increase again due to NPs forming and precipitating at the bottom of the capillary, which therefore leads to NPs moving out of the beam. After moving the setup upwards, the peak intensities were recovered.

As seen from the  $F(Q)$  contour plots in Fig. 5a and b, we observe three different stages during the formation of PdIn NPs in both synthesis c1 and c2. In the first stage, before the reaction temperature has been reached (i.e., before  $t = 0$  min), we do not observe any Bragg peaks, but only very broad scattering features. These are expected to arise from the small precursor-ligand complex structure. When the temperature reaches 235 °C ( $t = 0$  min), rapid crystallization takes place for both syntheses and Bragg peaks agreeing with the Pd<sub>3</sub>In phase appear (see Fig. 5c and d, showing selected  $F(Q)$ s). With continuous heating, a new phase emerges, which from its Bragg peaks can be

identified as PdIn. For synthesis c1, peaks from PdIn slowly appear after approximately 90 min with heating at 235 °C. PdIn forms slower in synthesis c2, where the first indication of the intermetallic phase is observed after 185 min at 235 °C.

Fig. 6 shows the real-space representation of the TS data, presented as the reduced Pair Distribution Function (PDF),  $G(r)$ .  $G(r)$  is the Fourier transform of the normalized and corrected scattering data:

$$G(r) = \frac{2}{\pi} \int_0^\infty F(Q) \sin(Qr) dQ$$

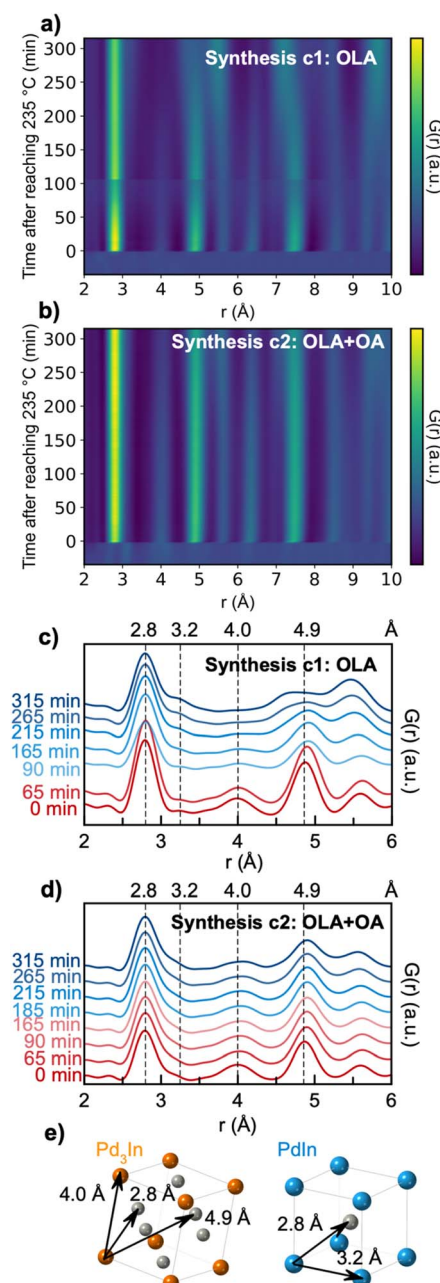

**Fig. 6** (a) and (b) *In situ* PDFs (presented as  $G(r)$ ) from syntheses c1 and c2 respectively. (c) and (d) Selected experimental PDFs from different times during the reaction of syntheses c1 and c2 respectively. (e) Sketch of Pd<sub>3</sub>In and PdIn unit cells with relevant interatomic distances labelled.





The PDF represents a histogram of interatomic distances present in the sample, and is thus an intuitive tool for studying structural changes during the reaction.<sup>46</sup> The PDFs of the precursor structures from synthesis c1 and c2 are shown in Fig. S4.† The relatively low concentration of metal precursor in the solution means that the majority of the scattered signal comes from the OLA solvent, which is subtracted before the Fourier transform. This limits the quality and resolution of the PDF from the small precursor complex. However, the data indicate that the precursor PDFs from the two syntheses are similar. The first highlighted peak at *ca.* 2.1 Å can be assigned to the In–O bond in In(ac)<sub>3</sub>, while the broad shoulder at 2.0 Å relates to the Pd–N coordination to OLA. The second highlighted peak at *ca.* 2.5 Å can be assigned to a Pd–Br pair.<sup>47</sup> Peaks at higher *r*-values may originate from distances between Pd or In and C in acetate, however, these are difficult to distinguish from noise.

Fig. 6a and b present the time-resolved PDFs from synthesis c1 and c2, respectively, while selected PDFs are plotted in Fig. 6c and d. Calculated PDFs of the Pd<sub>3</sub>In and PdIn structures are plotted in Fig. S5.† PDF peaks at 2.8 Å and 4.0 Å can be assigned to the nearest Pd–In and second nearest In–In distances in the Pd<sub>3</sub>In structure, and peaks at 4.9 Å can be assigned to the third closest Pd–In distance as indicated in Fig. 6e. If considering first synthesis c1, the formation of the PdIn structure results in gradual disappearance of the Pd<sub>3</sub>In peaks. In the meantime, a shoulder at 3.2 Å slowly shows up, relating to the nearest In–In bond distance in the PdIn structure. The data from synthesis c2 (Fig. 6d) show a similar trend. However, for c2, the peaks related to Pd<sub>3</sub>In are pronounced until the end of the reaction.

To obtain quantitative information from the data we performed sequential fitting of the PDFs. The PDFs were modelled with the PdIn and Pd<sub>3</sub>In structure. Due to the very small amount of PdIn in the early stage of the reaction, a single phase Pd<sub>3</sub>In model was used to fit the data from 0 to 115 min of heating at 235 °C in synthesis c1, and 0 to 190 min for synthesis c2. The parameters obtained from single-phase modelling are plotted in orange, while the parameters obtained from two-phase modelling are plotted in red and blue in Fig. 7. PDF fits of the last frame in each experiment and *R*<sub>wp</sub> values of the sequential refinements can be found in Fig. S6, S7 and Table S2.† For the total scattering data, we were able to describe the Pd<sub>3</sub>In signal with a single phase, as the RA-PDF setup used limits the *Q*-resolution in the data, making it difficult to distinguish Bragg peaks from materials with similar lattice parameters.

For both syntheses, the refined phase fractions (Fig. 7a and b) show that the amount of PdIn increases at the expense of Pd<sub>3</sub>In. The refinements show that the final product in synthesis c1 consists of 84% PdIn and 16% Pd<sub>3</sub>In. For synthesis c2 the final product contains 54% PdIn and 46% Pd<sub>3</sub>In. The only difference between the two synthesis approaches is the addition of OA in synthesis c2, which indicates that the transformation rate is influenced by the local chemistry affected by the surfactant used.<sup>48</sup> However, OA does not prevent the transformation process to occur, and it is reasonable to assume that if the reaction time has been prolonged, the Pd<sub>3</sub>In phase would fully convert to PdIn in both syntheses.


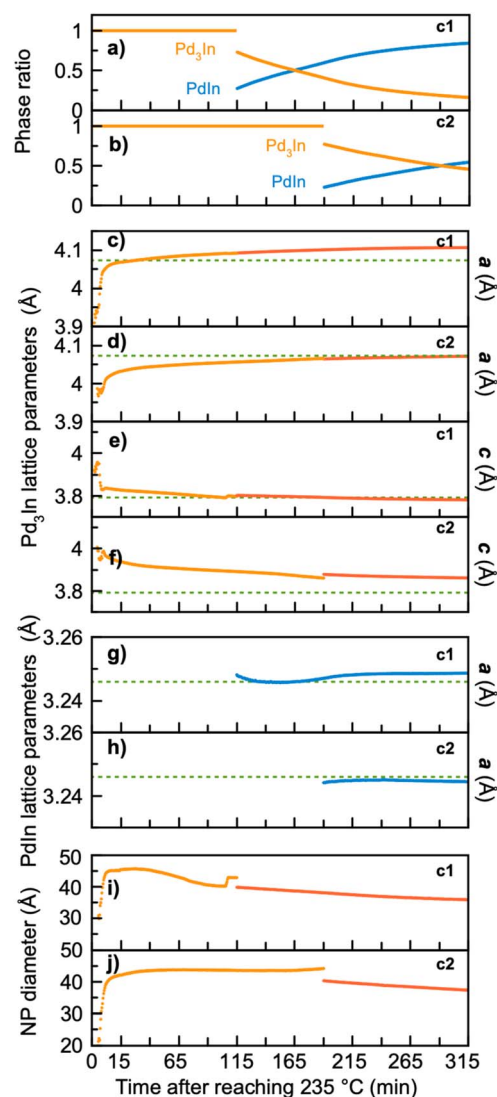


Fig. 7 Results from sequential PDF refinement showing the temporal evolution in (a) and (b) phase ratio, (c)–(f) Pd<sub>3</sub>In lattice parameters *a* and *c*, (g) and (h) PdIn lattice parameters, (i) and (j) NP diameter of Pd<sub>3</sub>In during the experiment. Parameters from synthesis c1 are shown in (a), (c), (e) and (g) while (b), (d), (f) and (h) present parameters from synthesis c2. In (c)–(h) the data in red are from Pd<sub>3</sub>In single-phase modelling, while the data in orange and blue are from two-phase modelling. In (c)–(f) the green dashed line represents the standard unit cell parameters from Pd<sub>3</sub>In.<sup>13</sup> For both syntheses, the Pd<sub>3</sub>In single-phase modelling starts from 15 min after reaching 235 °C due to continued presence of the precursor cluster.

Fig. 7c–f show the refined lattice parameters for Pd<sub>3</sub>In and PdIn during the reaction. The *in situ* data show a clear change in the Pd<sub>3</sub>In structure as the synthesis takes place. During the reaction, lattice parameter *a* increases, while lattice parameter *c* slowly decreases. In has a larger atomic radius than Pd, and the changing parameters and increase in unit cell volume (Fig. S7b†) could thus indicate that more indium incorporates into the Pd<sub>3</sub>In structure during the reaction. This observation agrees with the *ex situ* study described above, where the Pd<sub>3</sub>In signal was best described when using two Pd<sub>3</sub>In phases with




different lattice parameters. The data thus support our hypothesis that nanoparticles with different stoichiometries can take the  $\text{Pd}_3\text{In}$  structure. We expect this change in structure to be due to the different reduction rates of Pd and In. Pd exhibit a much higher reduction potential compared to In (0.915 V compared to  $-0.34$  V). The Pd rich phase thus forms first, and as more and more In reduce, the NP stoichiometry changes.

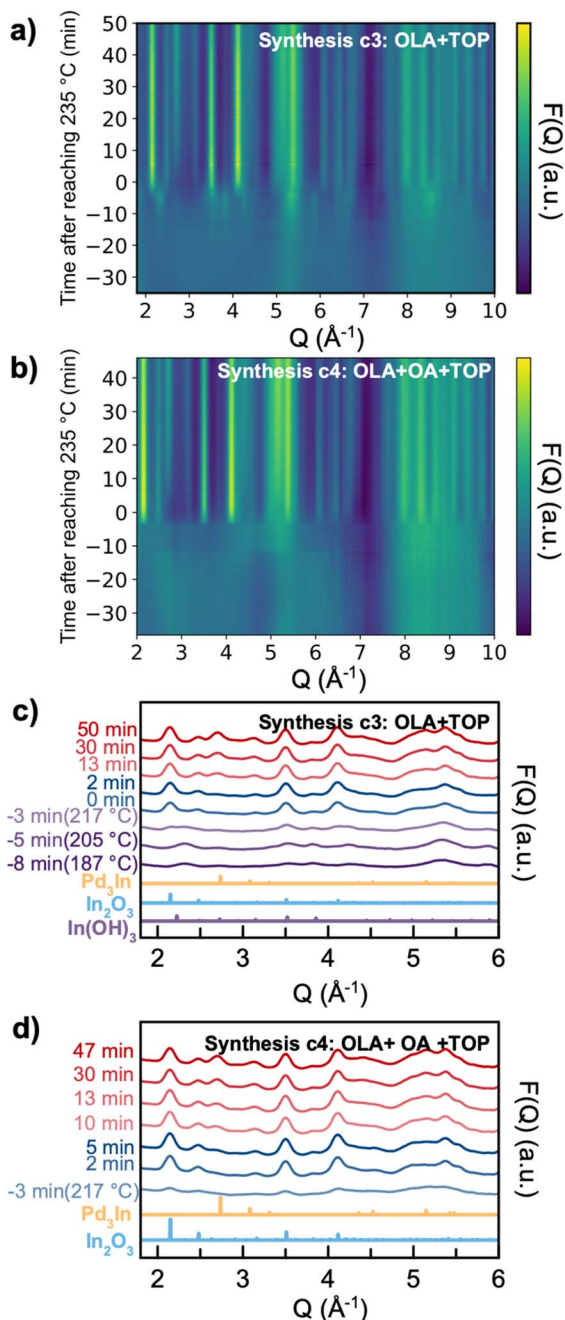

**Fig. 8** *In situ* X-ray TS data of the formation of  $\text{Pd}_3\text{In}$  and  $\text{In}_2\text{O}_3$  NPs. (a) and (b) *In situ* data plotted as the reduced structure function  $F(Q)$  from syntheses c3 and c4, respectively. (c) and (d) Selected experimental background-subtracted  $F(Q)$ s from synthesis c3 and c4 from different reaction times as indicated. The time scale displayed for the datasets is defined from when  $235^\circ\text{C}$  has been reached in each experiment (i.e.,  $t = 0$  minutes).

Eventually, stoichiometric  $\text{PdIn}$  eventually appears. The lattice parameters of  $\text{PdIn}$  from both syntheses (Fig. 7g and h) are stable around the standard values indicated by green dashed lines. To analyse the change from  $\text{Pd}_3\text{In}$  to  $\text{PdIn}$  further, we consider the refined crystallite diameter of  $\text{Pd}_3\text{In}$  in Fig. 7i and j. For both syntheses, the  $\text{Pd}_3\text{In}$  phase forms as NPs of *ca.* 2–3 nm followed by rapid growth to *ca.* 4 nm. A small decrease in size is seen as the  $\text{PdIn}$  particles form. The  $\text{PdIn}$  particle size is not shown here, as the size refines to larger values than can be robustly and reliably quantified from PDF analysis. This agrees well with the TEM analysis described above, showing  $\text{PdIn}$  sizes in the range from 20–40 nm. The large differences in particle size between  $\text{Pd}_3\text{In}$  and  $\text{PdIn}$  speaks against the stoichiometry changing gradually all the way from  $\text{Pd}_3\text{In}$  and  $\text{PdIn}$  within the individual nanoparticles. The reaction does thus not take place through the conventional Bain transformation, which we have previously observed for  $\text{PdCu}$ .<sup>17</sup> Instead, the  $\text{PdIn}$  particles may

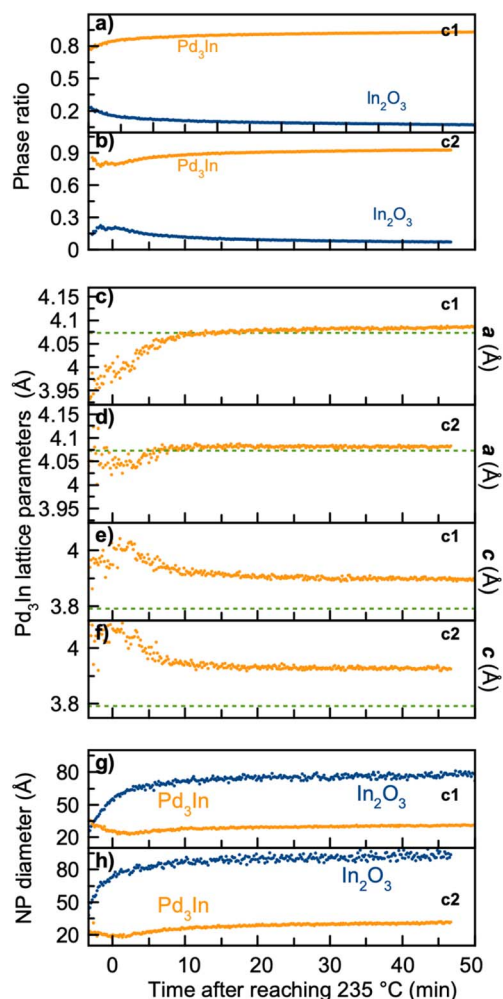

**Fig. 9** Results from sequential PDF refinements showing the temporal evolution in (a) and (b) scale factor, (c)–(f)  $\text{Pd}_3\text{In}$  unit cell parameters  $a$  and  $c$ , (g) and (h) NP diameter of  $\text{Pd}_3\text{In}$  and  $\text{In}_2\text{O}_3$  during the experiment. Parameters from synthesis c3 are shown in (a), (c), (e) and (g) while (b), (d), (f) and (h) present parameters from synthesis c4. Parameters related to  $\text{Pd}_3\text{In}$  are shown in orange, and parameters from  $\text{In}_2\text{O}_3$  are shown in blue. In (c)–(f) the green dashed line represents the standard unit cell parameters from  $\text{Pd}_3\text{In}$  structure.<sup>13</sup>



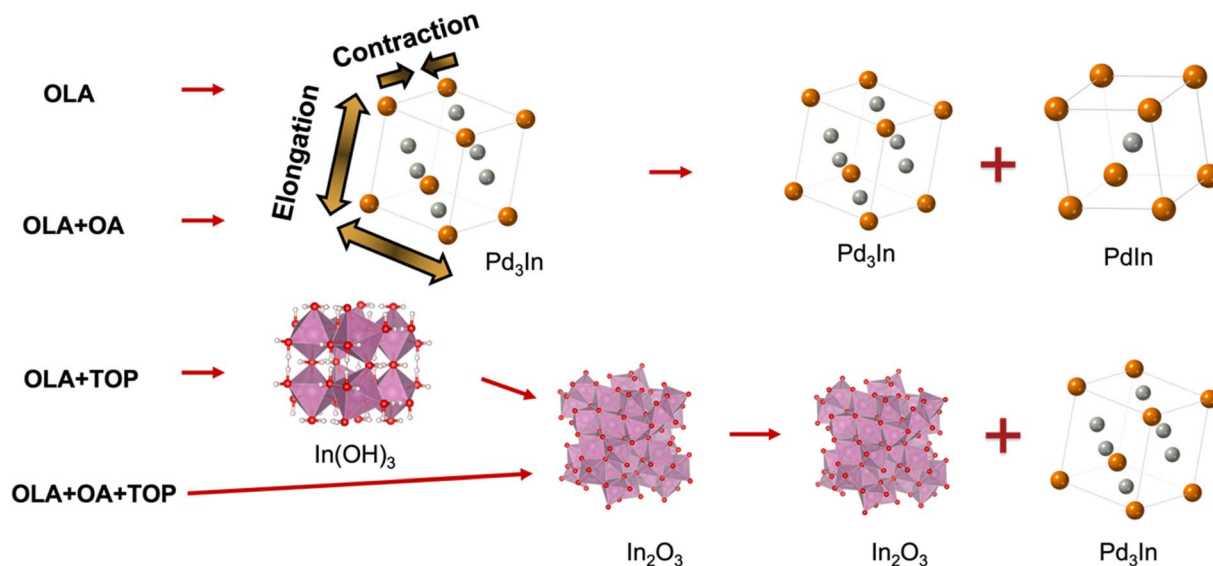


Fig. 10 Reaction scheme of syntheses of Pd–In bimetallic NPs using a colloidal synthesis at 235 °C.

form either through dissolution-precipitation of the  $\text{Pd}_3\text{In}$ -structured nanoparticles, or through rapid growth from several  $\text{Pd}_3\text{In}$ -structured nanoparticles when enough reduced Pd and In is available in the synthesis. Further characterization using *e.g.* HR-TEM and STEM-EDX would be required to fully address the nanostructural changes taking place during PdIn growth.

### Insights into formation pathways of $\text{Pd}_3\text{In}$ NPs from TOP-derived synthesis

We next investigate the reaction pathway for syntheses c3 (with OLA + TOP) and c4 (with OLA + OA + TOP). From the *ex situ* studies presented above, we learned that the products for both syntheses are  $\text{Pd}_3\text{In}$  and  $\text{In}_2\text{O}_3$ . *In situ* TS data of syntheses c3 and c4 are shown in Fig. 8. Here, we again set the time relative to the time reached the reaction temperature 235 °C (*i.e.*,  $t = 0$  minutes) and show the data as the reduced structure function  $F(Q)$ . We first consider synthesis c3 (Fig. 8a). From the beginning of the reaction until 10 minutes before reaching the reaction temperature ( $t = -10$  minutes), we see no sharp Bragg peaks, showing that the precursor mixture has no long-range order. In the time from  $-10$  to  $-3$  min, a crystalline intermediate phase appears, which we identify as  $\text{In}(\text{OH})_3$  as shown in Fig. 8c. Upon heating, the  $\text{In}(\text{OH})_3$  phase disappears, as it transforms to  $\text{In}_2\text{O}_3$ . A similar reaction pathway has been reported by Nielsen *et al.*<sup>49</sup> in a solvothermal synthesis. Soon after the temperature has reached 235 °C, we observe formation of  $\text{Pd}_3\text{In}$  NPs, whose Bragg peaks increase in intensity along with the  $\text{In}_2\text{O}_3$  phase. In synthesis c4 (Fig. 8b), Bragg peaks do not appear until  $-3$  min. Differently from synthesis c3, we do not observe  $\text{In}(\text{OH})_3$ ; instead,  $\text{In}_2\text{O}_3$  appears to nucleate directly from solution, at least within the time resolution available here. The  $\text{In}_2\text{O}_3$  phase appears at  $-3$  min, and is followed by  $\text{Pd}_3\text{In}$  at  $t = 5$  min.

PDFs from precursor solutions are shown in Fig. S8,<sup>†</sup> where the highlighted peak at *ca.* 2.4 Å shown may be assigned to a Pd–

Br pair from the initial precursor.<sup>47</sup> The precursor PDFs from syntheses c3 and c4 are quite different from the ones from syntheses c1 and c2 (Fig. S4<sup>†</sup>), indicating that with TOP included in the synthesis, the initial precursor complex structures are different. However, the low quality of the precursor PDF prevents further analysis of the precursor complex here.

Quantitative analysis of the sequential data was again performed through PDF modelling. The resulting parameters from the refinement are shown in Fig. 9, while PDF fits of the last frame and the  $R_{\text{wp}}$  values from sequential refinements are shown in Fig. S9, S10 and Table S3.<sup>†</sup> For both syntheses, a model with  $\text{In}_2\text{O}_3$  and a single  $\text{Pd}_3\text{In}$  phase was used to describe the data. As seen in Fig. 9a and b, both syntheses result in *ca.* 90 wt%  $\text{Pd}_3\text{In}$  and 10 wt%  $\text{In}_2\text{O}_3$ . This may explain why PdIn does not form, as there is not sufficient surplus of free indium to form the stoichiometric phase in the later stage of the reaction. Fig. 9c–f show the refined  $\text{Pd}_3\text{In}$  lattice parameters. The refinements again show that lattice parameter  $a$  increases, while lattice parameter  $c$  slowly decreases. The  $a$  parameter reaches the value expected for bulk  $\text{Pd}_3\text{In}$  (indicated by the green dashed lines in the figure) and remains stable for the rest of the reaction. However, the  $c$  parameter value does not reach the bulk value of 3.79 Å, but stays at *ca.* 3.91 Å. We also notice that for both syntheses, the starting value of  $\text{Pd}_3\text{In}$  lattice parameters,  $a$  and  $c$ , are the same, indicating that the initial  $\text{Pd}_3\text{In}$  unit cell is initially pseudo-cubic and possibly Pd rich.

The refined NPs sizes are shown in Fig. 9g and h. For both syntheses, the NP diameter of the  $\text{Pd}_3\text{In}$  phase is stable with a diameter of *ca.* 3 nm. For the  $\text{In}_2\text{O}_3$  phase, the diameter is much larger, and refines to *ca.* 8 nm in synthesis c3 and 9 nm in synthesis c4.

## Conclusion

In summary, we have demonstrated how to control the formation of intermetallic PdIn by using selected surfactants, OA and



TOP. Through synthesis parameter studies and *in situ* X-ray TS and PDF analysis, new insights into the formation of PdIn are provided and more intermediate structures are revealed. The results are summarized in Fig. 10. We first found that the choice of anion in the metal precursor is essential, and PdIn was only obtained when using indium acetate and palladium bromide in the synthesis. For both syntheses c1 and c2, we observe initial formation of a Pd-rich Pd<sub>3</sub>In phase, which is then transformed into PdIn with the CsCl structure. We expect that the phase transformation happens when sufficient In has reduced to form the stoichiometric phase, and our data indicate that Pd<sub>3</sub>In-structured nanoparticles with different compositions appear in the reaction. *In situ* studies show that OA slows down the reaction. With the addition of TOP in the synthesis (synthesis c3 and c4), In<sub>2</sub>O<sub>3</sub> forms initially, followed by Pd<sub>3</sub>In. This may be related to the strong coordination between TOP and Pd(II). The In<sub>2</sub>O<sub>3</sub> phase is stable also at the reaction temperature,<sup>50</sup> and the lack of In in the solution hinders the formation of the stoichiometric PdIn phase. Our studies have focused on the evolution of atomic structure and has provided insight into how nanoparticles with different crystal structures can form. However, questions remain on the evolution of nanoscale structure during synthesis, and further studies are needed to resolve these.

## Author contributions

BW, JKM and KMØJ conceptualized the project. BW performed the material synthesis with guidance from JKM. AK performed Rietveld refinements. NS performed TEM analysis. BW, ASA, FLJ, AK, OAF and TMN collected synchrotron data. ETSK and ASA assisted BW in treatment of synchrotron data. MST and RKJ collected UV-vis spectroscopy data. MA and KMØJ supervised the project.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

We are grateful for funding from the Villum Foundation through a Villum Young Investigator Grant (VKR00015416). Funding from the Danish Ministry of Higher Education and Science through the SMART Lighthouse is gratefully acknowledged. We acknowledge support from the Danish National Research Foundation Center for High Entropy Alloy Catalysis (DNRF 149). M. A. received funding from the Swiss National Science Foundation (SNSF) *via* the project no. 200021 184742. The Danish Research Council is acknowledged for covering travel expenses in relation to the synchrotron experiment (DanScatt). We acknowledge DESY (Hamburg, Germany), a member of the Helmholtz Association HGF, for the provision of experimental facilities. Parts of this research were carried out at beamline P21.1 and we would like to thank Soham Banerjee and Ann-Christin Dippel for assistance in using the beamline. Beamtime was allocated for proposal I-20210946 EC.

## References

- 1 M. Sankar, N. Dimitratos, P. J. Miedziak, P. P. Wells, C. J. Kiely and G. J. Hutchings, Designing bimetallic catalysts for a green and sustainable future, *Chem. Soc. Rev.*, 2012, **41**(24), 8099–8139.
- 2 L. Zhang, Z. Xie and J. Gong, Shape-controlled synthesis of Au–Pd bimetallic nanocrystals for catalytic applications, *Chem. Soc. Rev.*, 2016, **45**(14), 3916–3934.
- 3 M. Cui, G. Johnson, Z. Zhang, S. Li, S. Hwang, X. Zhang and S. Zhang, AgPd nanoparticles for electrocatalytic CO<sub>2</sub> reduction: bimetallic composition-dependent ligand and ensemble effects, *Nanoscale*, 2020, **12**(26), 14068–14075.
- 4 W. Du, K. E. Mackenzie, D. F. Milano, N. A. Deskins, D. Su and X. Teng, Palladium–tin alloyed catalysts for the ethanol oxidation reaction in an alkaline medium, *ACS Catal.*, 2012, **2**(2), 287–297.
- 5 Z. Wu, E. C. Wegener, H.-T. Tseng, J. R. Gallagher, J. W. Harris, R. E. Diaz, Y. Ren, F. H. Ribeiro and J. T. Miller, Pd–In intermetallic alloy nanoparticles: highly selective ethane dehydrogenation catalysts, *Catal. Sci. Technol.*, 2016, **6**(18), 6965–6976.
- 6 D. Pavesi, F. Dattila, R. C. Van de Poll, D. Anastasiadou, R. García-Muelas, M. Figueiredo, G.-J. M. Gruter, N. López, M. T. Koper and K. J. P. Schouten, Modulation of the selectivity of CO<sub>2</sub> to CO electroreduction in palladium rich palladium-indium nanoparticles, *J. Catal.*, 2021, **402**, 229–237.
- 7 Y. Yan, J. S. Du, K. D. Gilroy, D. Yang, Y. Xia and H. Zhang, Intermetallic nanocrystals: syntheses and catalytic applications, *Adv. Mater.*, 2017, **29**(14), 1605997.
- 8 M. Armbrüster, Intermetallic compounds in catalysis—a versatile class of materials meets interesting challenges, *Sci. Technol. Adv. Mater.*, 2020, **21**(1), 303–322.
- 9 E. Casado-Rivera, D. J. Volpe, L. Alden, C. Lind, C. Downie, T. Vázquez-Alvarez, A. C. Angelo, F. J. DiSalvo and H. D. Abruña, Electrocatalytic activity of ordered intermetallic phases for fuel cell applications, *J. Am. Chem. Soc.*, 2004, **126**(12), 4043–4049.
- 10 Z. Cui, H. Chen, M. Zhao and F. J. DiSalvo, High-performance Pd<sub>3</sub>Pb intermetallic catalyst for electrochemical oxygen reduction, *Nano Lett.*, 2016, **16**(4), 2560–2566.
- 11 H. Okamoto, In–Pd (indium–palladium), *J. Phase Equilib.*, 2003, **24**(5), 481.
- 12 H. Kohlmann and C. Ritter, Refinement of the Crystal Structures of Palladium-rich In–Pd Compounds by X-Ray and Neutron Powder Diffraction, *Zeitschrift für Naturforschung B*, 2007, **62**(7), 929–934.
- 13 I. Harris, M. Norman and A. Bryant, A study of some palladium-indium, platinum-indium and platinum-tin alloys, *J. Less-Common Met.*, 1968, **16**(4), 427–440.
- 14 H. Kohlmann and C. Ritter, Reaction Pathways in the Formation of Intermetallic InPd<sub>3</sub> Polymorphs, *Z. Anorg. Allg. Chem.*, 2009, **635**(11), 1573–1579.



- 15 D. Pavesi, F. S. Ali, D. Anastasiadou, T. Kallio, M. Figueiredo, G.-J. M. Gruter, M. T. Koper and K. J. P. Schouten, CO<sub>2</sub> electroreduction on bimetallic Pd–In nanoparticles, *Catal. Sci. Technol.*, 2020, **10**(13), 4264–4270.
- 16 Q. Feng, S. Zhao, Y. Wang, J. Dong, W. Chen, D. He, D. Wang, J. Yang, Y. Zhu and H. Zhu, Isolated single-atom Pd sites in intermetallic nanostructures: high catalytic selectivity for semihydrogenation of alkynes, *J. Am. Chem. Soc.*, 2017, **139**(21), 7294–7301.
- 17 J. K. Mathiesen, E. D. Bøjesen, J. K. Pedersen, E. T. Kjær, M. Juelsholt, S. Cooper, J. Quinson, A. S. Anker, G. Cutts and D. S. Keeble, Breaking with the Principles of Coreduction to Form Stoichiometric Intermetallic PdCu Nanoparticles, *Small Methods*, 2022, 2200420.
- 18 C. Y. Wang, D. P. Chen, X. H. Sang, R. R. Unocic and S. E. Skrabalak, Size-Dependent Disorder-Order Transformation in the Synthesis of Monodisperse Intermetallic PdCu Nanocatalysts, *ACS Nano*, 2016, **10**(6), 6345–6353.
- 19 K. M. Ø. Jensen, C. Tyrsted, M. Bremholm and B. B. Iversen, In Situ Studies of Solvothermal Synthesis of Energy Materials, *ChemSusChem*, 2014, **7**(6), 1594–1611.
- 20 Y. Sun and Y. Ren, In situ synchrotron X-ray techniques for real-time probing of colloidal nanoparticle synthesis, *Part. Part. Syst. Charact.*, 2013, **30**(5), 399–419.
- 21 S. Wu, M. Li and Y. Sun, In Situ Synchrotron X-ray Characterization Shining Light on the Nucleation and Growth Kinetics of Colloidal Nanoparticles, *Angew. Chem., Int. Ed.*, 2019, **58**(27), 8987–8995.
- 22 K. Bakken, O. G. Grendal and M.-A. Einarsrud, In situ characterisation for studying nucleation and growth of nanostructured materials and thin films during liquid-based synthesis, *J. Sol-Gel Sci. Technol.*, 2023, **105**(2), 596–605.
- 23 A. Coelho, TOPAS and TOPAS-Academic: an optimization program integrating computer algebra and crystallographic objects written in C++, *J. Appl. Crystallogr.*, 2018, **51**(1), 210–218.
- 24 A. Hammersley, FIT2D: a multi-purpose data reduction, analysis and visualization program, *J. Appl. Crystallogr.*, 2016, **49**(2), 646–652.
- 25 C. Prescher and V. B. Prakapenka, DIOPTAS: a program for reduction of two-dimensional X-ray diffraction data and data exploration, *High Pressure Res.*, 2015, **35**(3), 223–230.
- 26 X. Yang, P. Juhas, C. L. Farrow and S. J. Billinge, xPDFsuite: an end-to-end software solution for high throughput pair distribution function transformation, visualization and analysis, *arXiv*, 2014, preprint arXiv:14023163.
- 27 C. L. Farrow, P. Juhas, J. W. Liu, D. Bryndin, E. S. Bozin, J. Bloch, T. Proffen and S. J. Billinge, PDFfit2 and PDFgui: computer programs for studying nanostructure in crystals, *J. Phys.: Condens. Matter*, 2007, **19**(33), 335219.
- 28 A. L. Wang, L. Zhu, Q. Yun, S. Han, L. Zeng, W. Cao, X. Meng, J. Xia and Q. Lu, Bromide Ions Triggered Synthesis of Noble Metal-Based Intermetallic Nanocrystals, *Small*, 2020, **16**(40), 2003782.
- 29 Y. Zheng, J. Zeng, A. Ruditskiy, M. Liu and Y. Xia, Oxidative etching and its role in manipulating the nucleation and growth of noble-metal nanocrystals, *Chem. Mater.*, 2014, **26**(1), 22–33.
- 30 A. M. Pourrahimi, D. Liu, L. K. Pallon, R. L. Andersson, A. M. Abad, J.-M. Lagarón, M. S. Hedenqvist, V. Ström, U. W. Gedde and R. T. Olsson, Water-based synthesis and cleaning methods for high purity ZnO nanoparticles—comparing acetate, chloride, sulphate and nitrate zinc salt precursors, *RSC Adv.*, 2014, **4**(67), 35568–35577.
- 31 R. K. Sodhi and S. Paul, An overview of metal acetylacetonates: developing areas/routes to new materials and applications in organic syntheses, *Catal. Surv. Asia*, 2018, **22**(1), 31–62.
- 32 C. Wang, D. P. Chen, X. Sang, R. R. Unocic and S. E. Skrabalak, Size-dependent disorder–order transformation in the synthesis of monodisperse intermetallic PdCu nanocatalysts, *ACS Nano*, 2016, **10**(6), 6345–6353.
- 33 Y. Xia, Y. Xiong, B. Lim and S. E. Skrabalak, Shape-controlled synthesis of metal nanocrystals: simple chemistry meets complex physics?, *Angew. Chem., Int. Ed.*, 2009, **48**(1), 60–103.
- 34 D. Zhrebetsky, M. Scheele, Y. Zhang, N. Bronstein, C. Thompson, D. Britt, M. Salmeron, P. Alivisatos and L.-W. Wang, Hydroxylation of the surface of PbS nanocrystals passivated with oleic acid, *Science*, 2014, **344**(6190), 1380–1384.
- 35 M. Xie, Z. Lyu, R. Chen and Y. Xia, A Mechanistic Study of the Multiple Roles of Oleic Acid in the Oil-Phase Synthesis of Pt Nanocrystals, *Chem.–Eur. J.*, 2020, **26**(67), 15636–15642.
- 36 J. Park, K. An, Y. Hwang, J.-G. Park, H.-J. Noh, J.-Y. Kim, J.-H. Park, N.-M. Hwang and T. Hyeon, Ultra-large-scale syntheses of monodisperse nanocrystals, *Nat. Mater.*, 2004, **3**(12), 891–895.
- 37 J. Li, F. Li, S.-X. Guo, J. Zhang and J. Ma, PdCu@Pd nanocube with Pt-like activity for hydrogen evolution reaction, *ACS Appl. Mater. Interfaces*, 2017, **9**(9), 8151–8160.
- 38 W. Zhao, L. Yang, Y. Yin and M. Jin, Thermodynamic controlled synthesis of intermetallic Au<sub>3</sub>Cu alloy nanocrystals from Cu microparticles, *J. Mater. Chem. A*, 2014, **2**(4), 902–906.
- 39 S. L. Bueno, X. Zhan, J. Wolfe, K. Chatterjee and S. E. Skrabalak, Phase-Controlled Synthesis of Pd–Sn Nanocrystal Catalysts of Defined Size and Shape, *ACS Appl. Mater. Interfaces*, 2021, **13**(44), 51876–51885.
- 40 N. Ortiz and S. E. Skrabalak, Manipulating local ligand environments for the controlled nucleation of metal nanoparticles and their assembly into nanodendrites, *Angew. Chem., Int. Ed.*, 2012, **124**(47), 11927–11931.
- 41 Z. Yang and K. J. Klabunde, Synthesis of nearly monodisperse palladium (Pd) nanoparticles by using oleylamine and trioctylphosphine mixed ligands, *J. Organomet. Chem.*, 2009, **694**(7–8), 1016–1021.
- 42 Y. Liu, C. Wang, Y. Wei, L. Zhu, D. Li, J. S. Jiang, N. M. Markovic, V. R. Stamenkovic and S. Sun, Surfactant-





- induced postsynthetic modulation of Pd nanoparticle crystallinity, *Nano Lett.*, 2011, **11**(4), 1614–1617.
- 43 S. I. Al-Resayes, Isothermal decomposition of  $\gamma$ -irradiated indium acetate, *J. Saudi Chem. Soc.*, 2009, **13**(3), 243–246.
  - 44 Q. Gao, Y. M. Ju, D. An, M. R. Gao, C. H. Cui, J. W. Liu, H. P. Cong and S. H. Yu, Shape-Controlled Synthesis of Monodisperse PdCu Nanocubes and Their Electrocatalytic Properties, *ChemSusChem*, 2013, **6**(10), 1878–1882.
  - 45 T. Egami and S. J. L. Billinge, *Underneath the Bragg peaks*, Pergamon, Oxford, 1 edn, 2003, vol. 16, pp. 1–404.
  - 46 T. L. Christiansen, S. R. Cooper and K. M. Jensen, There's no place like real-space: elucidating size-dependent atomic structure of nanomaterials using pair distribution function analysis, *Nanoscale Adv.*, 2020, **2**(6), 2234–2254.
  - 47 A. A. Wells, The crystal structure of certain bridged palladium compounds, *Proc. R. Soc. London, Ser. A*, 1938, **167**(929), 169–189.
  - 48 E. Bøjesen and B. Iversen, The chemistry of nucleation, *CrystEngComm*, 2016, **18**(43), 8332–8353.
  - 49 I. G. Nielsen, S. Sommer and B. B. Iversen, Phase control for indium oxide nanoparticles, *Nanoscale*, 2021, **13**(7), 4038–4050.
  - 50 G. Korotcenkov, V. Brinzari, M. Ivanov, A. Cerneavski, J. Rodriguez, A. Cirera, A. Cornet and J. Morante, Structural stability of indium oxide films deposited by spray pyrolysis during thermal annealing, *Thin Solid Films*, 2005, **479**(1–2), 38–51.

