





Cite this: *Nanoscale*, 2023, **15**, 5327

CoO_x nanoparticles loaded on carbon spheres with synergistic effects for effective inhibition of shuttle effect in Li–S batteries†

Ning Chai,^{†a,b} Yujie Qi,^{†b,c} Qinhua Gu,^{b,c} Junnan Chen,^{b,c} Ming Lu,^{b,d} Xia Zhang ^{*,a} and Bingsen Zhang ^{*,b,c}

Lithium–sulfur (Li–S) batteries, as one of the new energy storage batteries, show immense potential due to their high theoretical specific capacity and theoretical energy density. However, there are still some problems to be solved, among which the shuttle effect of lithium polysulfides is one extremely serious issue with respect to the industrial application of Li–S batteries. Rational design of electrode materials with effective catalytic conversion ability is an effective route to accelerate the conversion of lithium polysulfides (LiPSs). Herein, considering the adsorption and catalysis of LiPSs, CoO_x nanoparticles (NPs) loaded on carbon sphere composites (CoO_x/CS) were designed and constructed as cathode materials. The CoO_x NPs obtained, with ultralow weight ratio and uniform distribution, consist of CoO, Co₃O₄, and metallic Co. The polar CoO and Co₃O₄ enable chemical adsorption towards LiPSs through Co–S coordination, and the conductive metallic Co can improve electronic conductivity and reduce impedance, which is beneficial for ion diffusion at the cathode. Based on these synergistic effects, the CoO_x/CS electrode exhibits accelerated redox kinetics and enhanced catalytic activity for conversion of LiPSs. Consequently, the CoO_x/CS cathode delivers improved cycling performance, with an initial capacity of 980.8 mA h g^{−1} at 0.1C and a reversible specific capacity of 408.4 mA h g^{−1} after 200 cycles, along with enhanced rate performance. This work provides a facile route to construct cobalt-based catalytic electrodes for Li–S batteries, and promotes understanding of the LiPSs conversion mechanism.

Received 23rd December 2022,

Accepted 12th February 2023

DOI: 10.1039/d2nr07194k

rsc.li/nanoscale

Introduction

Rapid consumption of fossil fuels has brought about a serious energy crisis, and developing renewable energy is of fundamental importance for the sustainable development of human society. The energy demands of electric vehicles and portable devices with high energy density and low cost are growing even more rapidly.^{1–3,4–6} Consequently, the design and development of promising energy storage systems have received extensive

attention. Most notably, lithium–sulfur (Li–S) batteries have been regarded as a new generation of rechargeable battery system due to their ultrahigh theoretical specific capacity (1675 mA h g^{−1}), high energy density (2600 W h kg^{−1}), low cost, and environmental friendliness.^{7–10}

So far, however, use of Li–S batteries faces tough challenges, including the shuttle effect of lithium polysulfides (LiPSs), the sluggish redox kinetics of the insulating lithium sulfide and sulfur, the dendrite effect of the lithium anode, and the volume expansion of the cathode.^{8,11} These issues bring about low coulombic efficiency and specific capacity, poor cycling stability, and performance degradation of the electrode materials, which hampers the industrialization process for Li–S batteries.^{9,12} Specifically, the shuttle effect has been considered to be one of the main obstacles, and leads to rapid capacity decay and low sulfur utilization. Therefore, rational design and synthesis of catalytic electrode materials are reasonable and effective ways to accelerate polysulfide conversion for active inhibition of the shuttle effect.^{13–20} So far, strenuous research efforts have been made to improve the adsorption and conversion efficiency of LiPSs, such as through the construction of self-supporting conductive substrates,^{21–23}

^aDepartment of Chemistry, College of Science, Northeastern University, Shenyang 110819, China. E-mail: xzhang@mail.neu.edu.cn

^bShenyang National Laboratory for Materials Science, Institute of Metal Research, Chinese Academy of Sciences, Shenyang 110016, China. E-mail: bszhang@imr.ac.cn

^cSchool of Materials Science and Engineering, University of Science and Technology of China, Shenyang 110016, China

^dThe Joint Laboratory of MXene Materials, Key Laboratory of Functional Materials Physics and Chemistry of the Ministry of Education, Key Laboratory of Preparation and Application of Environmental Friendly Materials of the Ministry of Education, Jilin Normal University, Changchun 130103, China

†Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d2nr07194k>

‡These authors contributed equally to this work.



heteroatom doping,^{23–25} introduction of quantum dots (QD),^{26,27} design of heterostructures,²⁸ construction of catalytic host materials,^{29–36} and so on. Generally, these feasible routes can be combined into valid strategies to accelerate LiPSs conversion and restrain the shuttle effect effectively. Notably, cobalt-based materials, including Co-based single-atom catalysts (SACs),^{32,35} metallic Co,^{37,38} oxides,^{39,40} sulfides,^{41–43} nitrides,^{44,45} phosphides,^{46–48} and organic hybrid compounds,^{49–51} have attracted much interest in the field of Li-S battery research due to their low cost, superior electrocatalytic performance, and large anchoring capacity for LiPSs. Despite these advantages, obstacles to developing cobalt-based cathode materials still exist. For instance, poor conductivity of oxides and sulfides is unfavorable for the redox reaction;^{39–43} difficulty in regulating morphology and structure of sulfides;⁴¹ easy accumulation of nitrides;^{44,45} production of toxic gas during the synthesis process and harsh synthetic conditions for phosphides;^{46–48} complex reaction processes, excessive by-products and difficult extraction for organic hybrid compounds.^{49–51}

Recently, the strategy of integrated cobalt oxides and metallic Co as electrocatalysts, such as Co@CoO@N-C/rGO membranes and CC/Co@CoO_{1-x} composites,^{52,53} has been shown to be appealing and valid, by integrating the strong affinity of oxides to LiPSs and the high catalytic activity of metallic Co. Inspired by this, here we have designed and synthesized CoO_x nanoparticles (NPs) loaded on carbon sphere (CoO_x/CS) composites as the cathode for Li-S batteries based on the synergistic effects of Co-based materials. The size and chemical composition of CoO_x NPs can be regulated by sintering conditions. The obtained CoO_x NPs with ultralow Co weight ratio (0.043%) and uniform distribution consist of CoO, Co₃O₄, and Co phases. As polarized oxide particles exhibit intrinsic sulfiphilic

properties, CoO and Co₃O₄ show chemical adsorption towards LiPSs. Metallic Co improves the electronic conductivity and enhances ion diffusion in the electrode simultaneously. The synergistic effects of CoO, Co₃O₄, and Co accelerate the redox kinetics of LiPSs conversion. In addition, the porous CS matrix provides a fast diffusion path for electrons and ions, facilitating inhibition of the shuttle effect. Compared with the CS/S electrode, the CoO_x/CS/S electrode exhibits notably improved cycle performance, with an initial capacity of 980.8 mA h g⁻¹ at 0.1C and a reversible specific capacity of 408.4 mA h g⁻¹ after 200 cycles, along with an enhanced rate performance of 1037.6 mA h g⁻¹ at 0.1C.

Results and discussion

The synthetic process for the CoO_x/CS/S electrode material is shown schematically in Fig. 1a. After carbonization, porous carbon spheres (CS) possess abundant nanoscale pores and functional groups (*e.g.*, carboxyl group),⁵⁴ which can provide enough space and active sites for embedding cobalt ions and growing CoO_x NPs. In order to improve catalytic activity, regulation of particle size is vitally important. In this work, the reaction time was optimized initially, to obtain supported Co-based NPs catalysts. As shown in Fig. S1 (ESI†), Co-based NPs with uniform size and distribution could be synthesized with a heating time of 20 min at 600 °C.

In order to obtain microstructure information of the as-prepared composites heated at 600 °C for 20 min, transmission electron microscopy (TEM) characterization was performed. Clearly, the NPs are uniformly distributed on the surface of CS with a particle size of 5–10 nm (Fig. 2d and e, S2, and S3†),

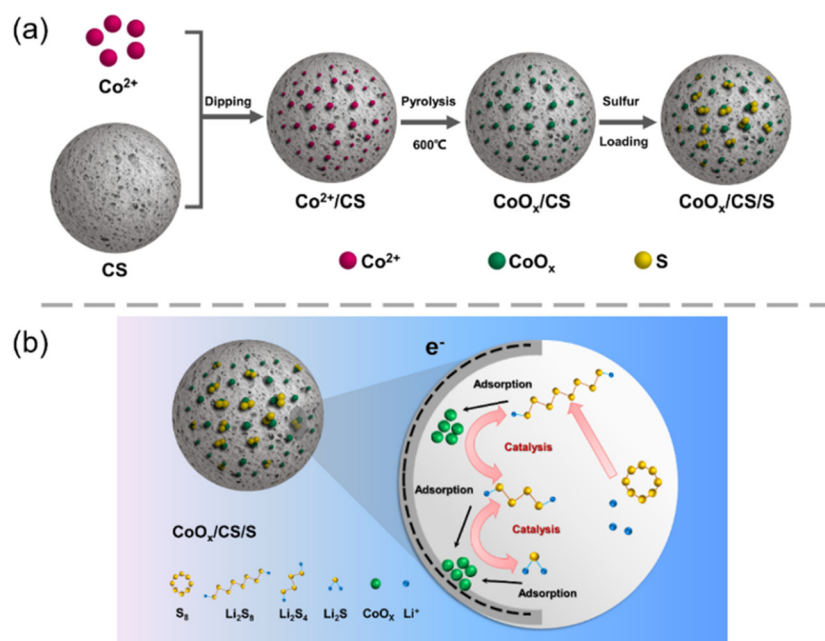


Fig. 1 (a) Schematic diagram of synthesis process of CoO_x/CS/S composites. (b) Schematic illustration of electrochemical reactions of the CoO_x/CS cathode in the Li-S battery.



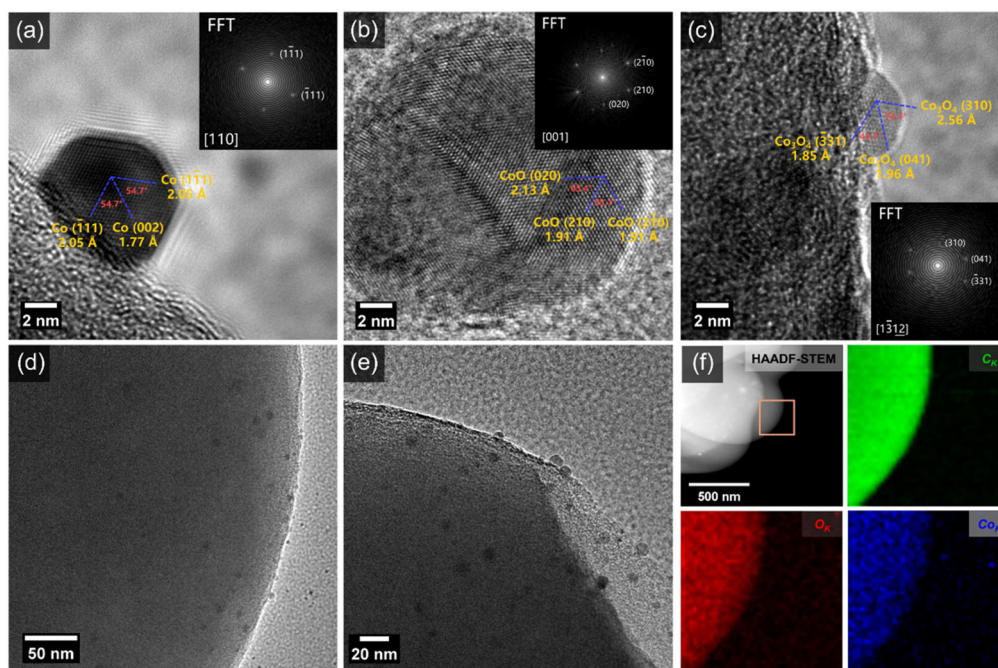


Fig. 2 HRTEM images of (a) Co, (b) CoO, and (c) Co₃O₄ NPs loaded on CoO_x/CS composites heated at 600 °C for 20 min. TEM images of CoO_x/CS composites (d and e), HAADF-STEM image of CoO_x/CS composites and corresponding EDX elemental maps for C, O, and Co elements (f).

which is consistent with the high-angle annular dark-field imaging (HAADF) and energy-dispersive X-ray spectroscopy (EDX) results showing the homogeneous distribution of C, O, and Co elements (Fig. 2f). Typical high-resolution TEM (HRTEM) images of NPs with basal spacings of 2.05 Å and 1.77 Å, 2.13 Å and 1.91 Å, 2.56 Å and 1.96 Å can be seen in Fig. 2a–c, which can be assigned to (111) and (002) structures of metallic Co, (020) and (210) structures of CoO, and (310) and (041) structures of Co₃O₄, respectively. The NPs loaded on the surface of the CS exhibit a mixed phase structure involving CoO, Co₃O₄, and metallic Co. The as-prepared composites are abbreviated as CoO_x/CS.

X-ray diffraction (XRD) patterns of CS and CoO_x/CS composites heated at 600 °C for 20 min and 2 h are presented in Fig. S4 and S5.† In general, the broad diffraction peak at 21.7° can be attributed to the coexistence of nanocrystalline graphite and amorphous carbon, and the diffraction peak at 43.7° corresponds to the graphite (101) structure.⁵⁵ For the CoO_x/CS composites heated at 600 °C for 20 min (Fig. S4†), the diffraction peak located at 36.8° corresponds to the (310) structure of Co₃O₄ (JCPDS 43-1003). There exist no obvious peaks for the Co and CoO phases, which can be ascribed to the low content of Co and CoO. This coincides with actual Co loading amount of 0.043 wt%, measured by inductivity coupled plasma optical emission spectrometry (ICP-OES). Simultaneously, the diffraction peaks of CoO, Co₃O₄, and Co can be observed in the XRD pattern of CoO_x/CS composites prepared with longer heating times (Fig. S5†), indicating the stable state of the mixed phase of CoO, Co₃O₄, and Co. The above experimental results demonstrate that CoO_x NPs with low weight ratio were successfully loaded onto CS with uniform distribution.

According to the Brunauer–Emmett–Teller (BET) results (Fig. 3a and b and Table S1†), CoO_x/CS composites exhibit higher specific area than CS, which is attributed to the pyrolysis process. The scanning electron microscopy (SEM) characterization (Fig. S6†) indicates that the introduction of CoO_x NPs has negligible influence on the morphology of the CS matrix. In addition, visualized adsorption tests of CoO_x/CS composites and CS in Li₂S₆ solution have been conducted (Fig. S7†). The CS matrix exhibits weak adsorption capability towards LiPSs due to its nonpolar nature. By contrast, CoO_x/CS composites show improved chemical interaction with LiPSs due to the polar CoO_x NPs. As presented in Fig. S8,† the thermogravimetric analysis (TGA) curves show that the sulfur loading amount for CoO_x/CS/S reaches 66.5%, which is close to the theoretical sulfur loading amount of 70% (derived from the preparation protocol). This indicates that most of the elemental sulfur penetrates into the pores of the CS matrix, and that CoO_x NP blocking effect has little influence on the sulfur loading. To further confirm the composition and the chemical state of the resulting CoO_x/CS composites, full-scale and corresponding high-resolution X-ray photoelectron spectroscopy (XPS) of C 1s, O 1s, and Co 2p has been carried out and the results are shown in Fig. 3c–f. The C 1s spectra can be deconvoluted into four affiliated peaks, corresponding to C–C, C–O, C=O, and O–C=O functional groups. The O 1s spectra could be decomposed into four peaks, belonging to C–O, O–C=O, C=O, and Co–O bonds. The calculated contents for C and O for different chemical bonds for CS and CoO_x/CS composites are summarized in Tables S2 and S3.† It was found that the relative contents of C and O change little for CS and CoO_x/CS composites, demonstrating the minor influence of CS



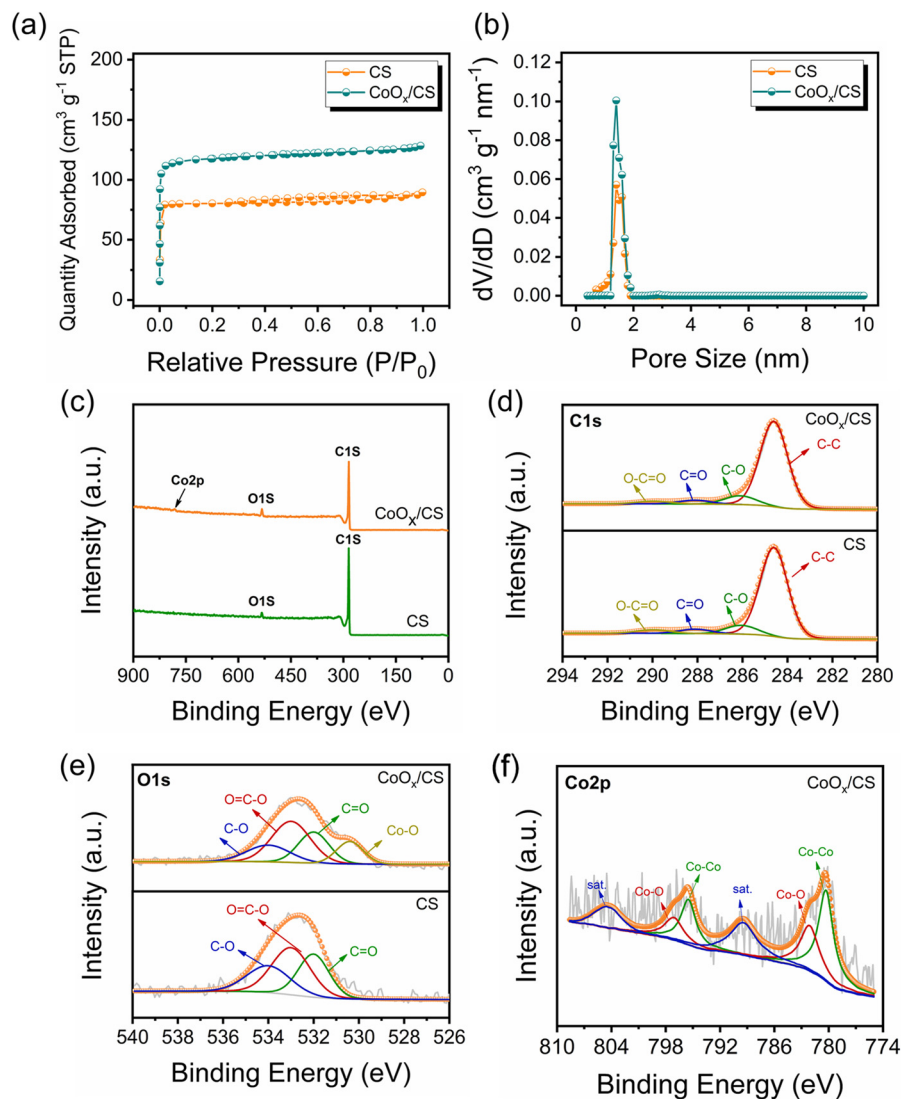


Fig. 3 (a) N₂ adsorption–desorption isotherms and (b) density functional theory pore size distributions for CS and CoO_x/CS composites. XPS full spectra (c), C 1s (d), and O 1s spectra (e) of CoO_x/CS composites and CS, Co 2p spectra of CoO_x/CS composites (f).

on the chemical state when introducing CoO_x NPs. The Co 2p spectrum (Fig. 3f) could be divided into six individual peaks, which can be attributed to Co 2p_{1/2} and 2p_{3/2} of metallic Co (795.5 and 780.3 eV), Co 2p_{1/2} and 2p_{3/2} of Co–O band (797.1 and 782.1 eV), and satellite peaks of Co 2p_{1/2} and 2p_{3/2} (804.4 and 789.4 eV).^{52,53,56}

The diffusion coefficient of lithium ion is a key parameter to evaluate the diffusion and conversion of LiPSs. Generally, the cathodic and anodic peak currents are linear with respect to the square root of scanning rates calculated from CV curves, as shown in Fig. 4c and d. Herein, the diffusion coefficients of lithium ion for anodic reactions (peak A, Li₂S → Li₂S_x and peak B, Li₂S_x → S₈) and the cathodic reactions (peak C, S₈ → Li₂S_x and peak D, Li₂S_x → Li₂S) have been deduced using the Randles–Sevcik equation,^{57–61} and the calculated results are presented in Table 1. Clearly, the diffusion coefficients for the CoO_x/CS/S electrode are significantly higher than those for the

CS/S electrode, demonstrating that the introduction of CoO_x NPs contributes to the diffusion and conversion of LiPSs. In addition, the CV curves of symmetric cells using CS and CoO_x/CS as electrodes with Li₂S₆ electrolyte were measured, to demonstrate the catalytic performance of CoO_x on redox processes of LiPSs (Fig. 4e). Compared with CS, the CoO_x/CS electrode exhibits higher redox current and smaller polarization, suggesting accelerated redox kinetics and enhanced catalytic activity. Potentiostatically, Li₂S precipitation tests on CS and CoO_x/CS electrodes were also performed to evaluate the conversion from LiPSs to solid Li₂S. Potentiostatic curves discharged at 2.05 V could be obtained with Li₂S₈/tetraglyme solution as catholyte, as shown in Fig. 4f, and the CoO_x/CS electrode could shorten the Li₂S precipitation time (≈10 000 s) compared with the CS electrode. In addition, the CoO_x/CS electrode shows a higher Li₂S nucleation capacity of 326.23 mA h g⁻¹, while that for the CS electrode is 174.05 mA h g⁻¹. Thus,



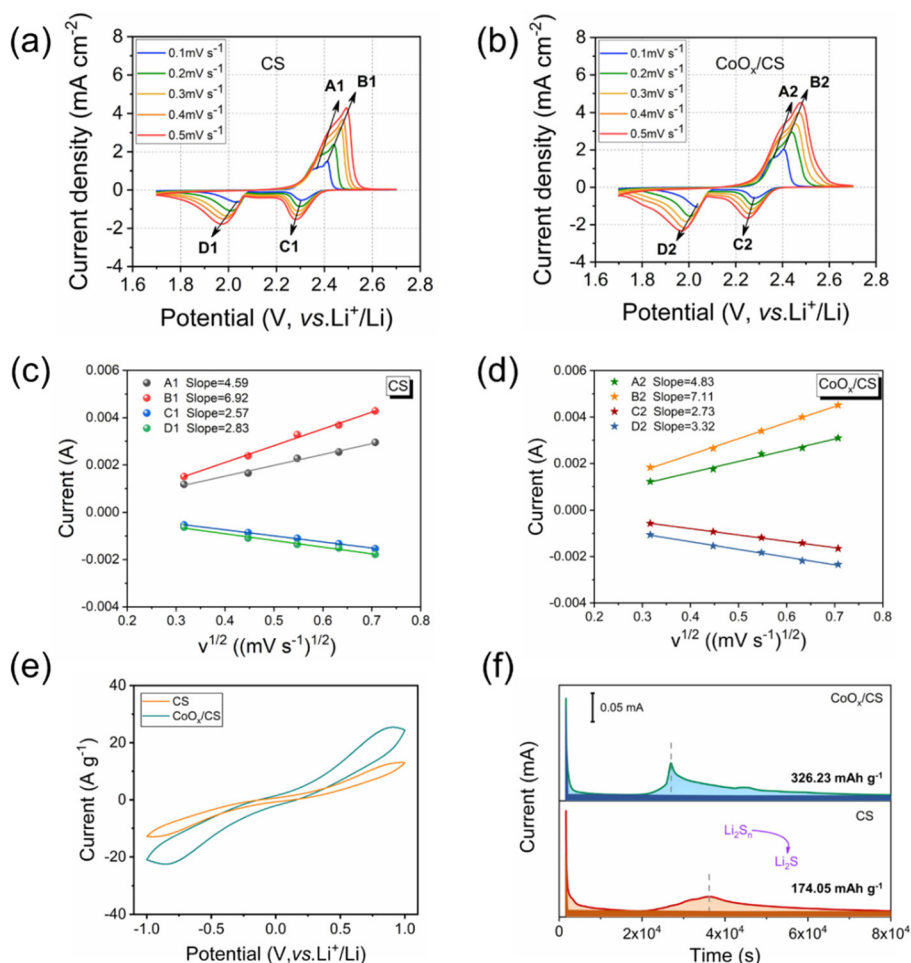


Fig. 4 CV curves of CS (a) and CoO_x/CS electrodes (b) at various scanning rates. (c and d) Corresponding plot of square root of CV peak current versus scanning rate. (e) CV curves of CS and CoO_x/CS symmetrical cells. (f) Potentiostatic discharge curves of Li₂S₈/tetraglyme solution at 2.05 V on CS and CoO_x/CS electrodes.

Table 1 The calculated Li⁺ diffusion coefficients in this work

| D_{Li^+} (cm ² s ⁻¹) | CS | CoO _x /CS |
|--|-------------------------|-------------------------|
| A (anodic peak at 2.35 V) | 1.873×10^{-10} | 1.931×10^{-10} |
| B (anodic peak at 2.4 V) | 8.434×10^{-11} | 9.822×10^{-11} |
| C (cathodic peak at 2.3 V) | 3.293×10^{-11} | 3.737×10^{-11} |
| D (cathodic peak at 2.0 V) | 1.343×10^{-10} | 2.053×10^{-10} |

the catalysis of CoO_x NPs for the conversion of LiPSs to Li₂S could be verified.

In order to demonstrate the catalytic polysulfide conversion of CoO_x, electrochemical measurements of CoO_x/CS/S and CS/S electrodes were performed on CR2032-type coin cells. Fig. 5a presents initial CV curves of CoO_x/CS/S and CS/S electrodes at 0.1 mV s⁻¹. Clearly, the anodic peak for the CoO_x/CS/S electrode displays a negative shift to 2.40 V and the cathodic peak shows a positive shift to 2.04 V, demonstrating the improved reaction kinetics and higher utilization rate of active materials. The catalytic activity of CoO_x NPs was further investigated by Tafel plots (Fig. S9†), which were calculated from the reduction

peak and oxidation peak in Fig. 5a. The CoO_x/CS/S electrode exhibits lower Tafel slopes of 71.2 mV dec⁻¹ and 140.9 mV dec⁻¹ for reduction and oxidation processes, while the CS/S electrode shows higher Tafel slopes of 93.0 mV dec⁻¹ and 183.5 mV dec⁻¹ calculated from the reduction peak at 2.0 V and the oxidation peak at 2.4 V, indicating noticeable kinetic promotion of sulfur species during the charging and discharging processes. Electrochemical impedance spectra of cells with CoO_x/CS/S and CS/S as cathodes before cycling and after 10 cycles at 0.1C are shown in Fig. 5b. Two semicircles can be seen in the high frequency region, which can be attributed to the resistance of the Li₂S layer and the formation of a solid-electrolyte interface (SEI) (R_g) and the charge transfer resistance (R_{ct}).⁶² The low frequency line represents the ion diffusion resistance in the cathode (W), and the intersection between the real axis and the first semicircle involves electrolyte resistance (R_e).⁶³

The smaller semicircles for the CoO_x/CS/S electrode indicate more rapid electron transportation and faster faradaic reaction, compared with the CS/S electrode. In addition, the galvanostatic charge-discharge profiles of the CoO_x/CS/S and



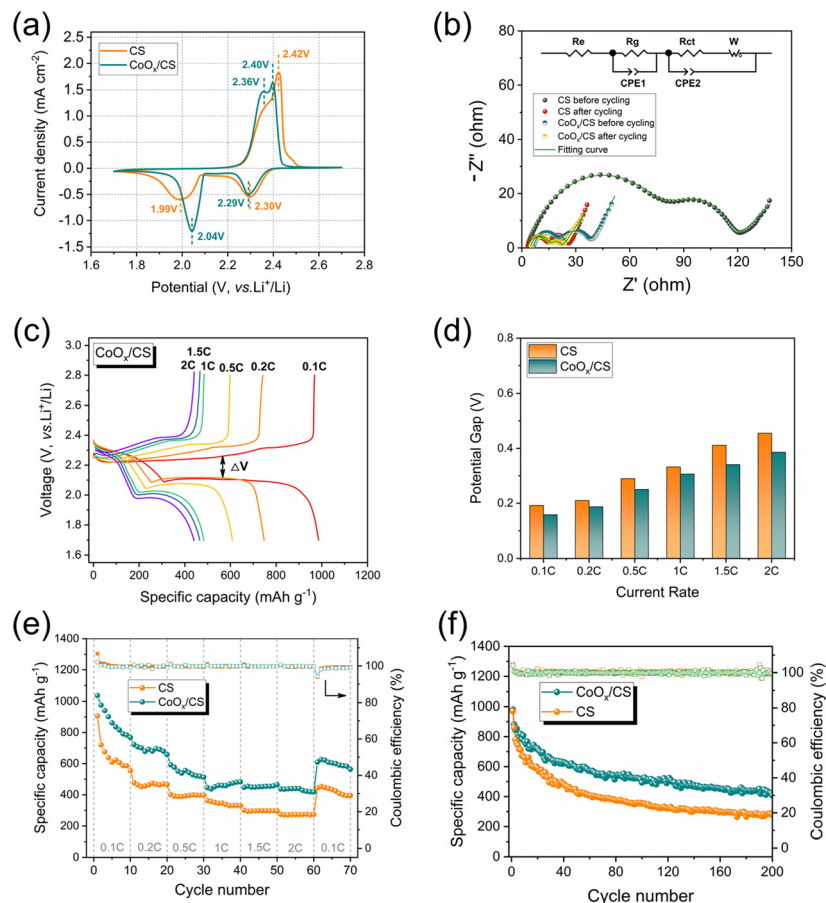


Fig. 5 (a) Initial CV curves of CS/S and CoO_x/CS/S electrodes with scanning rate of 0.1 mV s⁻¹. (b) Nyquist plots of CS/S and CoO_x/CS/S electrodes. (c) Charge and discharge profiles of CoO_x/CS/S electrode at various current densities. (d) Potential differences (ΔV) between discharge and charge plateaus of CoO_x/CS/S and CS/S electrodes at different current rates. Rate performances (e) and cycling performances (f) of CoO_x/CS/S and CS/S electrodes.

CS/S electrodes under various current densities were measured, as shown in Fig. 5c and S10.† The charge–discharge profiles for the CoO_x/CS/S electrode show smooth curves and stable plateaus, suggesting fast kinetic reaction and rapid flow of electrons and ions. The potential differences (ΔV) between the discharge and charge plateaus of the electrodes at different current rates are presented in Fig. 5d. The CoO_x/CS/S electrode exhibits smaller potential differences compared with the CS/S electrode, indicating that the introduction of CoO_x accelerates the redox reaction and promotes conversion of LiPSs.

The rate capacities and cyclabilities of CoO_x/CS/S and CS/S electrodes were also evaluated on cells with an S loading of 1.2 mg cm⁻², as displayed in Fig. 5e and f. The CoO_x/CS/S electrode presented enhanced rate performance at various current densities, and achieved capacities of 1037.6 mA h g⁻¹, 722.9 mA h g⁻¹, 592.6 mA h g⁻¹, 483.4 mA h g⁻¹, 465.4 mA h g⁻¹, and 440.3 mA h g⁻¹ at 0.1C, 0.2C, 0.5C, 1C, 1.5C, and 2C, respectively. By contrast, the CS/S electrode showed lower rate capacities of 906.2 mA h g⁻¹, 478.2 mA h g⁻¹, 402.3 mA h g⁻¹, 363.5 mA h g⁻¹, 300.8 mA h g⁻¹, and 275.3 mA h g⁻¹ at 0.1C, 0.2C, 0.5C, 1C, 1.5C, and 2C, respectively. Meanwhile, the

enhanced cycling performance of the CoO_x/CS/S electrode can be seen in Fig. 5f and S11,† with the CoO_x/CS/S electrode delivering a maximum capacity of 980.8 mA h g⁻¹ at a current density of 0.1C and retaining a stable reversible capacity of 408.4 mA h g⁻¹ after 200 cycles with almost 100% coulombic efficiency. The CS/S electrode exhibits decayed capacity from 970.5 to 281.3 mA h g⁻¹ after 200 cycles with almost 28.9% retention, demonstrating the preferable cycling stability and active suppression of the shuttle effect for the CoO_x/CS/S electrode. Furthermore, the cycling performance of the CoO_x/CS/S electrode with a high S loading of 4.4 mg cm⁻² was also measured (Fig. S12†). The CoO_x/CS/S electrode exhibited a maximum capacity of 703.0 mA h g⁻¹ and maintained a stable capacity retention over 70 cycles with a relatively low capacity decay of 0.397% per cycle, which demonstrates the good cycling stability of the CoO_x/CS/S electrode at high S loading.

To explore the catalytic mechanism of CoO_x NPs, XPS and SEM characterization of the CoO_x/CS/S electrode before cycling and after 10 cycles at 0.2C was conducted, as shown in Fig. 6, S13, and S14.† The C 1s, O 1s, and S 2p decomposed spectra for the CoO_x/CS/S electrode before and after cycling are dis-



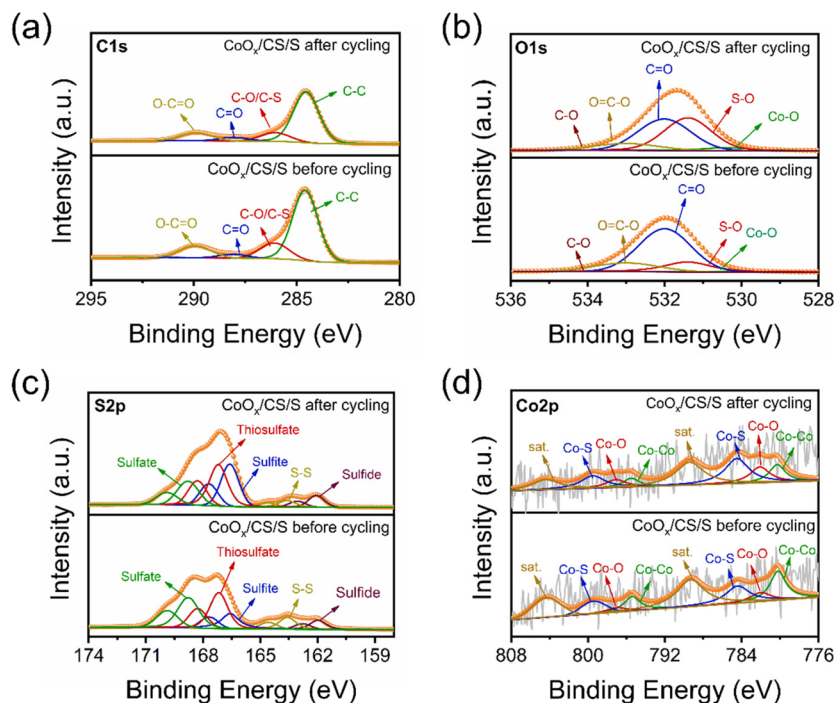


Fig. 6 Decomposed XPS spectra of C 1s (a), O 1s (b), S 2p (c), and Co 2p (d) for $\text{CoO}_x/\text{CS}/\text{S}$ electrodes before and after cycling.

played in Fig. 6a, b and c, respectively. The C 1s spectra could be deconvoluted into C-C, C-O/C-S, C=O, and O-C=O peaks.^{64–66} The O 1s spectra are composed of five peaks, corresponding to Co-O, S-O, C=O, O-C=O, and C-O groups.^{67,68} The content of the C-C, C-O/C-S, C=O, and O-C=O groups in the C 1s spectra remain substantially unchanged before and after cycling (Table S4†); however, increased concentration of the S-O group and attenuated content of the C=O bond can be found in the O 1s spectrum after cycling (Table S5†). As for the S 2p spectra, there are five deconvoluted peaks at 162.0, 163.6, 166.6, 167.2, and 168.8 eV, corresponding to sulfide, S-S, sulfite, thiosulfate, and sulfate groups.^{69–73} Most notably, the relative content of metallic Co for the $\text{CoO}_x/\text{CS}/\text{S}$ electrode after cycling reduced significantly, from 25.6% to 15.4%, compared to the $\text{CoO}_x/\text{CS}/\text{S}$ electrode before cycling (Fig. 6d). Simultaneously, the content of the Co-O bond increased substantially from 10.0% to 17.2%, the content of the Co-S bond rose to 32.6% from a primary of 22.8%, and the content of the satellite peak decreased slightly to 34.8% from 41.6% (Table S7†). The declining content of metallic Co, and the increasing content of the Co-S bond and Co-O bond indicate the strong affinity between CoO_x NPs and LiPSs, and the improved adsorption effect.⁷⁴

In summary, the enhanced electrochemical performance of CoO_x/CS composites can be illustrated for the following reasons. First, CoO_x NPs loaded on CS with ultralow weight ratio and uniform distribution were obtained in this work. CoO_x NPs avoid agglomeration with sizes in the range of 5–10 nm, resulting from precise regulation of the experimental parameters, which ensures efficient exposure of active sites

and a low proportion of Co-based catalysts. Second, as shown by HRTEM and XPS analysis, CoO_x NPs are composed of a stable mixed phase of CoO, Co_3O_4 , and Co. The synergistic effects of the Co-based materials, including strong adsorption of LiPSs from polar CoO and Co_3O_4 , good electrical conductivity of Co, along with charge transfer between CoO_x NPs and the CS matrix, can contribute to the catalytic conversion of LiPSs during the cycling process, leading to enhanced electrochemical performance. Third, the strong physical confinement of LiPSs from the CS matrix, which has been verified by our recent work,⁵⁴ could also play an important role in inhibiting the shuttle effect. Moreover, CoO_x/CS composites with porous structure improve sulfur utilization and provide short diffusion routes for transportation of electrons and ions in the electrolyte, promoting redox kinetics.

Conclusions

We employed CoO_x/CS composites as cathode materials to catalyze the conversion of LiPSs in Li-S batteries. The microstructure of CoO_x has been investigated and confirmed, and the nature of the CoO_x NPs with ultralow weight ratio and uniform distribution is a stable mixed phase of CoO, Co_3O_4 , and Co. The synergistic effects of polar CoO, Co_3O_4 , and metallic Co, along with efficient charge transfer between CoO_x NPs and the CS matrix could contribute to promoting the redox kinetics of sulfur species. In addition, the porous structure of the CS matrix is beneficial to the strong physical confinement of LiPSs, and provides a short diffusion route for ions and elec-



trons, which also further suppresses the shuttle effect. As a result, the CoO_x/CS/S electrode presents enhanced cycling performance with specific capacity of 980.8 mA h g⁻¹ at 0.1C, and retains a stable reversible capacity of 408.4 mA h g⁻¹ after 200 cycles, with 0.292% capacity decay per cycle. This work highlights a facile and rational method to construct cobalt-based catalytic electrode materials to accelerate polysulfide conversion and restrain the shuttle effect, which could pave the way for the application of high-performance Li-S batteries.

Experimental

Synthesis of CoO_x/CS composites

CoO_x/CS composites were prepared by the wet impregnation method using cobalt tetrahydrate ((CH₃COO)₂Co·4(H₂O)) as the cobalt source and carbon spheres (CS) as the active material carrier. CSs were synthesized by hydrothermal carbonization using sucrose as carbon source.⁷⁵ In general, 0.2 g porous carbon spheres and 0.03113 g cobalt acetate tetrahydrate were evenly dispersed in 50 mL ethanol solution, stirred vigorously, and treated with ultrasound for 1 h to obtain a uniform solution. Afterwards, the mixed solution was filtered and dried to obtain the precursor powder. Finally, the CoO_x/CS composites were prepared by calcining precursor powder at 600 °C for 20 min in an argon atmosphere.

Synthesis of CS/S and CoO_x/CS/S electrode materials

CoO_x/CS/S electrode was prepared by the melt diffusion method. Sublimated sulfur and CoO_x/CS composite materials were mixed and ground evenly at a mass ratio of 7:3, and transferred to a 10 mL high-pressure reactor. CoO_x/CS/S electrode material was obtained by heating at 155 °C for 12 h and naturally cooling to room temperature. CS/S electrode material was prepared in the same way as the control group.

Electrochemical measurements

Electrode material powders (CoO_x/CS/S or CS/S composites), super-P, and polyvinylidene fluoride (PVDF) were weighed in a mortar with appropriate amounts of *N*-methyl-2-pyrrolidone (NMP) and mixed evenly to obtain a slurry (mass ratio 7:2:1). The slurry was evenly coated on aluminum foil, vacuum dried at 55 °C for 12 h, and pressed into a circular electrode sheet with a diameter of 10 mm using a tablet press.

CR2032 button cells with CS/S and CoO_x/CS/S cathode materials were assembled in an argon-filled MBraun glovebox. Lithium foil was used as the anode, Celgard 2400 polypropylene film as the diaphragm, 1.0 M DME/DOL (V:V = 1:1), and 1 wt% LiNO₃ as the electrolyte. The areal sulfur loading was 1.2 mg cm⁻² or 4.4 mg cm⁻², and the electrolyte/sulfur (E/S) ratio was 10:1. Cyclic voltammetry and electrochemical impedance spectroscopy tests were carried out on a VMP3 electrochemical workstation (BioLogic). The constant current discharge-charge (GCD) test was carried out in a NEWARE battery test system (CT-4800).

The CS and CoO_x/CS symmetrical cells were fabricated as follows: CS or CoO_x/CS powders and PVDF were mixed in 2 ml NMP with a weight ratio of 5:1, then the slurry was coated on carbon paper. The carbon paper was cut into circular discs with a diameter of 10 mm and used as working and counter electrodes. Afterwards, two identical electrodes, polypropylene films, and 40 μl electrolyte of 0.2 M Li₂S₆ were assembled in CR2032 cells. CV measurements of symmetrical cells were performed at a scanning rate of 50 mV s⁻¹. All the electrochemical tests were carried out at room temperature.

Li₂S nucleation measurement

The 0.2 M Li₂S₈ electrolyte was prepared by mixing sulfur powder and lithium sulfide according to a stoichiometric ratio of 7:1 in tetraglyme with vigorous stirring. The CS and CoO_x/CS powders were dispersed in NMP and loaded on carbon papers with a diameter of 10 mm as cathodes, and lithium foil was used as the anode. During the process of cell assembly, 20 μl Li₂S₈ electrolyte was added as catholyte and 20 μl electrolyte without Li₂S₈ was added as anolyte. The assembled cells were first galvanostatically discharged to 2.06 V with a current of 0.112 mA, then discharged potentiostatically at 2.05 V for Li₂S nucleation and growth.⁷⁶

Li₂S₆ visualized adsorption experiment

The 0.3 mM Li₂S₆ solution was initially prepared by dissolving Li₂S and sulfur powders with a molar ratio of 1:5 in DOL/DME (v:v = 1:1). In order to conduct visualized adsorption tests, 50 mg of CoO_x/CS and CS powders were added into 2 ml Li₂S₆ solution, respectively.

Instruments and characterization

SEM images were collected on an FEI Nova NanoSEM 450. TEM images were obtained on an FEI Tecnai G2 F20 with an acceleration voltage of 200 kV. The XRD patterns were acquired using an X-ray diffractometer (Rigaku D/MAX-2400) equipped with CuKα radiation (λ = 1.5406 Å). X-ray photoelectron spectra were obtained on a Thermo ESCALAB 250 equipped with a monochromatic AlKα of 1486.6 eV. The cobalt loading amount was determined using an ICP-OES device (PerkinElmer Optima 7300 DV). BET analysis was carried out using a micro-pore physisorption analyzer (TriStar II 3020). TGA was performed using a NETZSCH STA 449F5 apparatus from 20 °C to 500 °C with a heating rate of 5 °C min⁻¹.

Conflicts of interest

The authors declare that they have no conflict of interest.

Acknowledgements

The authors gratefully acknowledge the financial support provided by the National Natural Science Foundation of China (No. 51932005, 22072164), Liaoning Revitalization Talents



Program (No. XLYC1807175), and the Research Fund of Shenyang National Laboratory for Materials Science.

References

- 1 L. P. Hou, X. Q. Zhang, B. Q. Li and Q. Zhang, *Mater. Today*, 2021, **45**, 62–76.
- 2 M. Lu, W. J. Han, H. J. Li, W. Shi, J. H. Wang, B. S. Zhang, Y. Zhou, H. B. Li, W. Zhang and W. T. Zheng, *Energy Storage Mater.*, 2019, **16**, 163–168.
- 3 M. Lu, W. J. Han, H. B. Li, W. Zhang and B. S. Zhang, *J. Energy Chem.*, 2020, **48**, 344–363.
- 4 F. F. Liu, Z. W. Zhang, S. F. Ye, Y. Yao and Y. Yu, *Acta Phys.-Chim. Sin.*, 2021, **37**, 2006021.
- 5 C. X. Bi, M. Zhao, L. P. Hou, Z. X. Chen, X. Q. Zhang, B. Q. Li, H. Yuan and J. Q. Huang, *Adv. Sci.*, 2022, **9**, 2103910.
- 6 J. F. Ding, R. Xu, X. X. Ma, Y. Xiao, Y. X. Yao, C. Yan and J. Q. Huang, *Angew. Chem., Int. Ed.*, 2022, **61**, e202115602.
- 7 Y. F. Zhang, S. C. Wu and Q. H. Yang, *EnergyChem*, 2021, **3**, 100063.
- 8 S. Feng, Z. H. Fu, X. Chen and Q. Zhang, *InfoMat*, 2022, **4**, e12304.
- 9 C. X. Bi, M. Zhao, L. P. Hou, Z. X. Chen, X. Q. Zhang, B. Q. Li, H. Yuan and J. Q. Huang, *Adv. Sci.*, 2022, **9**, 2103910.
- 10 Z. X. Chen, M. Zhao, L. P. Hou, X. Q. Zhang, B. Q. Li and J. Q. Huang, *Adv. Mater.*, 2022, **34**, 2201555.
- 11 X. Y. Yue, C. Ma, J. Bao, S. Y. Yang, D. Chen, X. J. Wu and Y. N. Zhou, *Acta Phys.-Chim. Sin.*, 2021, **37**, 2005012.
- 12 X. G. Qiu, W. Liu, J. D. Liu, J. Z. Li, K. Zhang and F. Y. Cheng, *Acta Phys.-Chim. Sin.*, 2021, **37**, 2009012.
- 13 R. Xu, J. F. Ding, X. X. Ma, C. Yan, Y. X. Yao and J. Q. Huang, *Adv. Mater.*, 2021, **33**, 2105962.
- 14 M. Zhao, B. Q. Li, X. Q. Zhang, J. Q. Huang and Q. Zhang, *ACS Cent. Sci.*, 2020, **6**, 1095–1104.
- 15 Y. Chen, T. Y. Wang, H. J. Tian, D. W. Su, Q. Zhang and G. X. Wang, *Adv. Mater.*, 2021, **33**, 2003666.
- 16 R. Xiao, T. Yu, S. Yang, K. Chen, Z. Li, Z. B. Liu, T. Hu, G. Hu, J. Li, H. M. Cheng, Z. H. Sun and F. Li, *Energy Storage Mater.*, 2022, **51**, 890–899.
- 17 C. Y. Zhang, C. Zhang, J. L. Pan, G. W. Sun, Z. Shi, C. Li, X. Chang, G. Z. Sun and J. Y. Zhou, *eScience*, 2022, **2**, 405–415.
- 18 H. Shi, Z. Sun, W. Lv, S. Xiao, H. Yang, Y. Shi, K. Chen, S. Wang, B. Zhang, Q. H. Yang and F. Li, *J. Energy Chem.*, 2020, **45**, 135–141.
- 19 R. Xiao, K. Chen, X. Zhang, Z. Z. Yang, G. Hu, Z. Sun, H. M. Cheng and F. Li, *J. Energy Chem.*, 2021, **54**, 452–466.
- 20 X. Wang, X. Zhao, C. Ma, Z. Yang, G. Chen, L. Wang, H. Yue, D. Zhang and Z. Sun, *J. Mater. Chem. A*, 2020, **8**, 1212–1220.
- 21 Q. H. Q. Xiao, J. L. Yang, X. D. Wang, Y. R. Deng, P. Han, N. Yuan, L. Zhang, M. Feng, C. A. Wang and R. P. Liu, *Carbon Energy*, 2021, **3**, 271–302.
- 22 Z. T. Wu, T. X. Shang, Y. Q. Deng, Y. Tao and Q. H. Yang, *Adv. Sci.*, 2020, **7**, 1903077.
- 23 M. D. Zhang, B. Chen and M. B. Wu, *Acta Phys.-Chim. Sin.*, 2022, **38**, 2101001.
- 24 Q. H. Gu, Y. J. Qi, W. X. Hua, T. X. Shang, J. N. Chen, L. Z. Jiang, L. N. Li, M. Lu, Y. X. Zhang, X. Liu, Y. Wan and B. S. Zhang, *J. Energy Chem.*, 2022, **69**, 490–496.
- 25 Y. Gao, Z. C. Xiao, D. B. Kong, R. Iqbal, Q. H. Yang and L. J. Zhi, *Nano Energy*, 2019, **64**, 103879.
- 26 Y. Liu, Z. Y. Ma, G. Yang, Z. Wu, Y. T. Li, J. Gu, J. Gautam, X. X. Gong, A. N. Chishti, S. Q. Duan, C. Chen, M. Chen, L. B. Ni and G. W. Diao, *Adv. Funct. Mater.*, 2022, **32**, 2109462.
- 27 Z. B. Liu, L. Wang and W. T. Yang, *Chin. Chem. Lett.*, 2021, **32**, 2919–2922.
- 28 B. Guan, X. Sun, Y. Zhang, X. Wu, Y. Qiu, M. X. Wang, L. S. Fan and N. Q. Zhang, *Chin. Chem. Lett.*, 2021, **32**, 2249–2253.
- 29 Z. Liang, J. Shen, X. Xu, F. Li, J. Liu, B. Yuan, Y. Yu and M. Zhu, *Adv. Mater.*, 2022, **34**, 2200102.
- 30 J. Shen, X. Xu, J. Liu, Z. Wang, S. Zuo, Z. Liu, D. Zhang, J. Liu and M. Zhu, *Adv. Mater.*, 2021, **11**, 2100673.
- 31 J. Shen, X. Xu, J. Liu, Z. Liu, F. Li, R. Hu, J. Liu, X. Hou, Y. Feng, Y. Yan and M. Zhu, *ACS Nano*, 2019, **13**, 8986–8996.
- 32 Z. Du, X. Chen, W. Hu, C. Chuang, S. Xie, A. Hu, W. Yan, X. Kong, X. Wu, H. Ji and L. J. Wan, *J. Am. Chem. Soc.*, 2019, **141**, 3977–3985.
- 33 Z. Wang, J. Shen, J. Liu, X. Xu, Z. Liu, R. Hu, L. Yang, Y. Feng, J. Liu, Z. Shi, L. Ouyang, Y. Yu and M. Zhu, *Adv. Mater.*, 2019, **31**, 1902228.
- 34 Y. Zhang, J. Liu, J. Wang, Y. Zhao, D. Luo, A. Yu, X. Wang and Z. W. Chen, *Angew. Chem., Int. Ed.*, 2021, **60**, 26622–26629.
- 35 E. Andritsos, C. Lekakou and Q. Cai, *J. Phys. Chem. C*, 2021, **125**, 18108–18118.
- 36 H. Zhao, B. Tian, C. Su and Y. Li, *ACS Appl. Mater. Interfaces*, 2021, **13**, 7171–7177.
- 37 Z. S. Wang, J. D. Shen, X. J. Xu, J. J. Yuan, S. Y. Zuo, Z. B. Liu, D. C. Zhang and J. Liu, *Small*, 2022, **18**, 2106640.
- 38 H. D. Shi, Y. G. Li, P. F. Lu and Z. S. Wu, *Acta Phys.-Chim. Sin.*, 2021, **37**, 2008033.
- 39 R. L. Li, D. W. Rao, J. B. Zhou, G. Wu, G. Z. Wang, Z. X. Zhu, X. Han, R. B. Sun, H. Li, C. Wang, W. S. Yan, X. S. Zheng, P. X. Cui, Y. E. Wu, G. M. Wang and X. Hong, *Nat. Commun.*, 2021, **12**, 3102.
- 40 W. C. Ren, W. Ma, M. M. Umair, S. F. Zhang and B. T. Tang, *ChemSusChem*, 2018, **11**, 2695–2702.
- 41 Q. Wang, H. Q. Zhao, B. Y. Li, C. H. Yang, M. Y. Li, Y. N. Li, P. Han, M. M. Wu, T. Y. Li and R. P. Liu, *Chin. Chem. Lett.*, 2021, **32**, 1157–1160.
- 42 J. T. Zhang, L. Yu and X. W. Lou, *Nano Res.*, 2017, **10**, 4298–4304.
- 43 R. J. Li, Z. Bai, W. S. Hou, J. S. Qiao, W. Sun, Y. Bai, Z. H. Wang and K. N. Sun, *Chin. Chem. Lett.*, 2021, **32**, 4063–4069.



- 44 H. Wu, H. Jiang, Y. Q. Yang, C. Y. Hou, H. T. Zhao, R. Xiao and H. Z. Wang, *J. Mater. Chem. A*, 2020, **8**, 14498–14505.
- 45 H. Zhang, D. X. Tian, Z. B. Zhao, X. G. Liu, Y. N. Hou, Y. J. Tang, J. J. Liang, Z. C. Zhang, X. Z. Wang and J. S. Qiu, *Energy Storage Mater.*, 2019, **21**, 210–218.
- 46 Y. R. Zhong, L. C. Yin, P. He, W. Liu, Z. S. Wu and H. L. Wang, *J. Am. Chem. Soc.*, 2018, **140**, 1455–1459.
- 47 A. M. Elshahawy, C. Guan, X. Li, H. Zhang, Y. T. Hu, H. J. Wu, S. J. Pennycook and J. Wang, *Nano Energy*, 2017, **39**, 162–171.
- 48 S. L. Yu, W. L. Cai, L. Chen, L. X. Song and Y. Z. Song, *J. Energy Chem.*, 2021, **55**, 533–548.
- 49 S. Y. Hu, M. J. Yi, X. Y. Huang, D. Wu, B. B. Lu, T. S. Wang, N. Li, Z. Y. Zhu, X. L. Liu and J. H. Zhang, *J. Mater. Chem. A*, 2021, **9**, 2792–2805.
- 50 C. X. Zhao, X. Y. Li, M. Zhao, Z. X. Chen, Y. W. Song, W. J. Chen, J. N. Liu, B. Wang, X. Q. Zhang, C. M. Chen, B. Q. Li, J. Q. Huang and Q. Zhang, *J. Am. Chem. Soc.*, 2021, **143**, 19865–19872.
- 51 A. A. Razzaq, G. W. Chen, X. H. Zhao, X. T. Yuan, J. P. Hu, Z. W. Li, Y. F. Chen, J. B. Xu, R. H. Shah, J. Zhong, Y. Peng and Z. Deng, *J. Energy Chem.*, 2021, **61**, 170–178.
- 52 H. H. Li, Y. X. Wang, H. Q. Chen, B. X. Niu, W. C. Zhang and D. P. Wu, *Chem. Eng. J.*, 2021, **406**, 126802.
- 53 D. L. Fang, G. Z. Wang, S. Z. Huang, T. C. Li, J. Z. Yu, D. B. Xiong, D. Yan, X. L. Li, J. T. Zhang, Y. V. Lim, S. A. Yang and H. Y. Yang, *Chem. Eng. J.*, 2021, **411**, 128546.
- 54 Y. J. Qi, N. Chai, Q. H. Gu, J. N. Chen, M. Lu, X. Zhang and B. S. Zhang, *Chem. Eng. J.*, 2022, **435**, 135112.
- 55 Y. J. Qi, L. Qi, L. P. Liu, B. S. Dai, D. C. Wei, G. M. Shi and Y. Qi, *Carbon*, 2019, **150**, 259–267.
- 56 C. Y. Fan, S. Y. Liu, H. H. Li, Y. H. Shi, H. C. Wang, H. F. Wang, H. Z. Sun, X. L. Wu and J. P. Zhang, *J. Mater. Chem. A*, 2017, **5**, 11255–11262.
- 57 M. F. Chen, Q. Lu, S. X. Jiang, C. Huang, X. Y. Wang, B. Wu, K. X. Xiang and Y. T. Wu, *Chem. Eng. J.*, 2018, **335**, 831–842.
- 58 X. Y. Tao, J. G. Wang, C. Liu, H. T. Wang, H. B. Yao, G. Y. Zheng, Z. W. Seh, Q. X. Cai, W. Y. Li, G. M. Zhou, C. X. Zu and Y. Cui, *Nat. Commun.*, 2016, **7**, 11203.
- 59 X. D. Ren, Q. Zhao, W. D. McCulloch and Y. Y. Wu, *Nano Res.*, 2017, **10**, 1313–1321.
- 60 A. Ottmann, G. S. Zakharova, B. Ehrstein and R. Klingeler, *Electrochim. Acta*, 2015, **17**, 4682–4687.
- 61 K. Tang, X. Q. Yu, J. P. Sun, H. Li and X. J. Huang, *Electrochim. Acta*, 2011, **56**, 4869–4875.
- 62 H. Wang, S. A. He, Z. Cui, C. T. Xu, J. Q. Zhu, Q. Liu, G. J. He, W. Lou and R. J. Zou, *Chem. Eng. J.*, 2021, **420**, 129693.
- 63 H. L. Wu, Y. Li, J. Ren, D. W. Rao, Q. J. Zheng, L. Zhou and D. M. Lin, *Nano Energy*, 2019, **55**, 82–92.
- 64 Y. J. Qi, D. C. Wei, G. M. Shi, M. Zhang and Y. Qi, *Sci. Rep.*, 2019, **9**, 12429.
- 65 H. L. Xu, X. W. Yin, M. Zhu, M. K. Han, Z. X. Hou, X. L. Li, L. T. Zhang and L. F. Cheng, *ACS Appl. Mater. Interfaces*, 2017, **9**, 6332–6341.
- 66 W. L. Song, M. S. Cao, L. Z. Fan, M. M. Lu, Y. Li, C. Y. Wang and H. F. Ju, *Carbon*, 2014, **77**, 130–142.
- 67 W. Shi, B. S. Zhang, Y. M. Lin, Q. Wang, Q. Zhang and D. S. Su, *ACS Catal.*, 2016, **6**, 7844–7854.
- 68 T. I. T. Okpalugo, P. Papakonstantinou, H. Murphy, J. McLaughlin and N. M. D. Brown, *Carbon*, 2005, **43**, 153–161.
- 69 L. L. Peng, Z. Y. Wei, C. Z. Wan, J. Li, Z. Chen, D. Zhu, D. Baumann, H. T. Liu, C. S. Allen, X. Xu, A. I. Kirkland, I. Shakir, Z. Almutairi, S. Tolbert, B. Dunn, Y. Huang, P. Sautet and X. F. Duan, *Nat. Catal.*, 2020, **3**, 762–770.
- 70 X. Liang, C. Hart, Q. Pang, A. Garsuch, T. Weiss and L. F. Nazar, *Nat. Commun.*, 2015, **6**, 5682.
- 71 Z. L. Xu, J. K. Kim and K. Kang, *Nano Today*, 2018, **19**, 84–107.
- 72 L. Zhang, L. W. Ji, P. A. Glans, Y. G. Zhang, J. F. Zhu and J. H. Guo, *Phys. Chem. Chem. Phys.*, 2012, **14**, 13670–13675.
- 73 C. X. Zu and A. Manthiram, *Adv. Energy Mater.*, 2013, **3**, 1008–1012.
- 74 Z. Zhang, L. L. Kong, S. Liu, G. R. Li and X. P. Gao, *Adv. Energy Mater.*, 2017, **7**, 1602543.
- 75 Y. J. Qi, M. Zhang, L. Qi and Y. Qi, *RSC Adv.*, 2016, **6**, 20814–20823.
- 76 W. X. Hua, H. Li, C. Pei, J. Y. Xia, Y. F. Sun, C. Zhang, W. Lv, Y. Tao, Y. Jiao, B. S. Zhang, S. Z. Qiao, Y. Wan and Q. H. Yang, *Adv. Mater.*, 2021, **33**, 2101006.

