


Cite this: *RSC Adv.*, 2023, 13, 17923

# Structural, dielectric and transport properties of $\text{Na}_x\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ ( $x = 1$ and $2/3$ )†

Faouzi Missaoui,<sup>a</sup> Kawthar Trablsi,<sup>a</sup> Krimi Moufida,<sup>a</sup> Ayten Ates,<sup>b</sup> Abdelfattah Mahmoud,<sup>c</sup> Frédéric Boschini<sup>c</sup> and Abdallah Ben Rhaïem<sup>\*a</sup>

$\text{Na}_x\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  ( $x = 1$  and  $2/3$ ) layered oxides were prepared by an improved solid-state synthesis method. The XRD analysis confirmed the high purity of these samples. The Rietveld refinement of the crystalline structure illustrated that the prepared materials crystallize in a hexagonal system in the  $R\bar{3}m$  space group with the P3 structure for  $x = 1$  and in a rhombohedral system with the  $P6_3/mmc$  space group and P2 structure type for  $x = 2/3$ . The vibrational study undertaken using IR and Raman spectroscopy techniques yielded the existence of an  $\text{MO}_6$  group. Their dielectric properties were determined in frequency range  $0.1\text{--}10^7$  Hz for a temperature range  $333\text{--}453$  K. The permittivity results indicated the presence of two types of polarization, namely dipolar polarization and space charge polarization. The frequency dependence of the conductivity was interpreted in terms of Jonscher's law. The DC conductivity followed the Arrhenius laws either at low or at high temperatures. The temperature dependence of the power law exponent which corresponds to the grain ( $s_2$ ) suggested that the conduction of the  $\text{P3-NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  compound is ascribed to the CBH model, while  $\text{P2-Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  can be attributed to the OLPT model.

Received 18th April 2023

Accepted 5th June 2023

DOI: 10.1039/d3ra02570e

rsc.li/rsc-advances

## 1. Introduction

The layered sodium-transition metal oxides  $\text{NaMO}_2$  are considered among the most promising cathode materials for Na-ion batteries (NIBs) by providing comparable activity to canonical Li-ion batteries (LIBs).<sup>1–14</sup> Indeed,  $\text{Na}_x\text{MO}_2$  ( $M = \text{Fe}, \text{Mn}, \text{Ni}, \text{Cr},$  and  $\text{Co}$ , *etc.*), have received much interest and have been extensively explored as outstanding cathode materials for NIBs owing to their high theoretical capacities, high working voltage as well as simple synthesis processes and importantly their structure rearrangement.<sup>15–17</sup> The structure of  $\text{Na}_x\text{MO}_2$  compounds can be divided into two major groups, O and P type structures, based on the location of sodium ions at either octahedral or prismatic sites, respectively, squeezed between the edge-sharing sheets of  $[\text{MO}_6]$  octahedra.<sup>17</sup> First,  $\text{Na}_x\text{MnO}_2$  crystallizes in two structures as described by Parant, *et al.*<sup>18</sup> At low temperature,  $\alpha\text{-NaMnO}_2$  has an O3 shell structure with a monoclinic structural distortion because of the Jahn–Teller effect of  $\text{Mn}^{3+}$  ions. However, the orthorhombic  $\beta\text{-NaMnO}_2$  crystallizes at high temperature in a unique layered structure

containing  $\text{MnO}_2$  sheets made up of a double stack of edge-sharing  $\text{MnO}_6$  octahedra. The octahedral positions between two adjacent sheets are occupied by Na ions.<sup>19</sup> Second, Tetsuaki Nishida *et al.*<sup>20</sup> reported that  $\text{NaFeO}_2$  has two polymorphs, namely  $\beta$  phase of orthorhombic symmetry and the  $\alpha$  phase of rhombohedral symmetry which is classified as O3-like shell structure according to Delmas notation.<sup>21</sup> In addition, different transition metal elements can be mixed in the transition metal layers to form  $\text{Na}_x\text{M}_{1-y}\text{M}'_y\text{O}_2$  with enhanced electrochemical properties. In this respect,  $\text{NaNi}_{1/2}\text{Mn}_{1/2}\text{O}_2$  provides a discharge capacity of  $125\text{ mA g}^{-1}$  between 3.8 V and 2 V, with 75% capacity retention after 50 cycles at 0.2 C, whereas  $\text{Na}_{2/3}\text{Ni}_{1/3}\text{Mn}_{2/3}\text{O}_2$  delivers a high capacity of  $161\text{ mA h g}^{-1}$  with poor cycle stability,<sup>21,22</sup>  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  provides a capacity of  $110\text{ mA h g}^{-1}$  in the potential range of 1.5–4.3 V, whereas  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  exhibits a high capacity of  $190\text{ mA h g}^{-1}$ .<sup>23</sup> Numerous XRD studies of  $\text{NaFe}_x\text{Mn}_{1-x}\text{O}_2$  have highlighted the layered structure for these compounds. Basically,  $\text{NaFe}_x\text{Mn}_{1-x}\text{O}_2$  is characterized by either a P3 layered structure or an O3 layered structure.<sup>22</sup> If Fe:Mn ratio is  $1/3:2/3$  and  $1/2:1/2$ , the  $\text{NaFe}_x\text{Mn}_{1-x}\text{O}_2$  compounds exhibit the P3 shell structure. However if the Fe:Mn ratio is  $2/3:1/3$ , the material forms O3 structure.<sup>23</sup> The two samples (for  $x = 1$  and  $2/3$ ) crystallize in different layered structures. All diffraction peaks of  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  are indexed in  $xh$  a  $P6_3/mmc$  space group (hexagonal lattice). These mesh parameters include unit cell lengths  $a = b = 2.9154(2)\text{ \AA}$  and  $c = 11.2599(1)\text{ \AA}$ , unit cell angles  $\alpha = \beta = 90^\circ$  and  $\gamma = 120^\circ$ . However, the diffraction lines of  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  are assigned to

<sup>a</sup>Laboratory LaSCOM, University of Sfax, BP1171, 3000, Sfax, Tunisia. E-mail: abdallahrhaïem@yahoo.fr

<sup>b</sup>Department of Chemical Engineering, Engineering Faculty, Sivas Cumhuriyet University, 58140 Sivas, Turkey

<sup>c</sup>GREENMAT, CESAM, Institute of Chemistry B6, University of Liège, 4000 Liège, Belgium

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3ra02570e>



a rhombohedral lattice with space group  $R\bar{3}m$ , these lattice parameters which include unit cell lengths  $a = b = 2.9590(6)$  Å and  $c = 16.522(2)$  Å, unit cell angles  $\alpha = \beta = 90^\circ$  and  $\gamma = 120^\circ$ .<sup>23</sup> The  $\text{P2-Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  provides higher discharge capacity at low C-rate of  $12 \text{ mA g}^{-1}$  in the voltage range of 1.5 to 4.3 V, and about  $190 \text{ mA h g}^{-1}$ , relative to  $\text{O3-NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  which has a discharge capacity of about  $105 \text{ mA h g}^{-1}$ . This suggests that more  $\text{Na}^+$  extraction/insertion occurs through the  $\text{P2-Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  structure. Mortemard de Boisse and al have also shown that the O3 phases have discharge capacities of about  $135\text{--}140 \text{ mA h g}^{-1}$ , slightly lower than those of the P2 phases ( $145\text{--}150 \text{ mA h g}^{-1}$ ).<sup>24</sup> The promising crystal structures and the prominent electrochemical results of these compounds  $\text{Na}_x\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  ( $x = 1$  and  $2/3$ ) incite us to explore other physical properties of these materials such as vibrational, and electrical properties. Indeed, this type of structure influences the electrical properties of these compounds, in particular the electrical conductivity because the  $\text{Na}^+$  charge carrier is free. Moreover, at the band gap between the valence band and the conduction band, which indicates semiconductor behavior, 3d transition metals, are characterized by the overlap between the narrow 3d bands.

In this research work, the layered  $\text{P3/P2-Na}_x\text{Fe}_{0.5}\text{Mn}_{0.5}\text{O}_2$  with  $x = 1$  and  $2/3$  samples were synthesized and the related atomic structures were carefully investigated using Rietveld refinement. The vibrational study of both compounds was undertaken using IR and Raman spectroscopy. The electrical properties were examined to thoroughly clarify the transport phenomena by combining conductivity and impedance studies. This study provides and demonstrates the convenient model accounting for the conduction mechanism of these materials.

## 2. Experimental part

$\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  and  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  were synthesized using a solid-state process,<sup>23,27</sup> using  $\text{Na}_2\text{CO}_3$  (Sigma Aldrich, 99%),  $\text{Fe}_2\text{O}_3$  (Sigma Aldrich, 99%), and  $\text{Mn}_2\text{O}_3$  (Sigma Aldrich, 99%) as precursors with the molar ratios of  $1 : 1/2 : 1/2$  and  $2/3 : 1/2 : 1/2$ , respectively. The precursors were mixed and thoroughly ground using a mortar and pestle, and then pressed into pellets.

The pellets were heated at  $700^\circ\text{C}$  for 36 h for  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  and  $1000^\circ\text{C}$  for 12 h for  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  in air. Subsequently, they were quenched to room temperature and stored in an Ar-filled glove box until use.

In order to confirm the purity of the produced samples, the Bruker D8 Discover Twin-X-ray Twin's diffraction was used on powder at room temperature with  $\text{Cu K}\alpha$  radiation ( $\lambda = 1.5406$  Å,  $10^\circ \leq 2\theta \leq 90^\circ$ ). With a 15 kV accelerating voltage and high vacuum, a scanning electron microscope (XL30 FEG ESEM, FEI) was utilized to examine their morphology. A PerkinElmer spectrum 100 FT-IR spectrometer was invested for the IR spectroscopic study, which was conducted in the  $350\text{--}1200 \text{ cm}^{-1}$  spectral region. Raman spectra were measured using a micro-Raman system (Renishaw inVia Qontor, UK) equipped with a 785 nm laser.

Finally, the electric measurements were carried out using the Soltran SI 1260 impedance analyzer in serial mode with an alternate current in the temperature ranges of  $[333\text{--}453 \text{ K}]$  and frequency  $[10^{-1}\text{--}10^7 \text{ Hz}]$ . Pellets were placed between two electrodes in a customized container and coated on the opposing sides with a thin layer of silver to provide satisfactory contact. Using a  $5 \text{ t cm}^{-2}$  pressure, the powder was crushed to create a disc that was 8 mm in diameter, 1 mm thick and with an area of  $50.24 \times 10^{-3} \text{ mm}^2$ .

## 3. Results and discussion

### 3.1. X-ray diffraction and structural analysis

The X-ray diffraction patterns of the compounds  $\text{Na}_x\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  for  $x = 1$  and  $2/3$  are depicted in Fig. 1. The reflection peaks of  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  diagram were indexed by trigonal with space group  $R\bar{3}m$  (isostructural at  $\alpha\text{-NaFeO}_2$  (ICSD #187705)) and characterized by a P3 layered structure. It is noteworthy that several traces of  $\text{NaFeO}_2$  were observed. Furthermore, the  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  diagram was indexed by hexagonal lattice with space group  $P6_3/mmc$  (PDF# 16-3250), which is isostructural with P2-type  $\text{Na}_x\text{CoO}_2$ . This result is in good agreement with the result reported by Yuliang Cao *et al.*<sup>25</sup> Certain impurity peaks were detected from the diffraction patterns. These impurities correspond to  $\text{Na}_3\text{FeO}_3$  and  $\text{Mn}_2\text{O}_3$  phases. Table 1 displays the cell parameters and the refinement parameters. The schematic

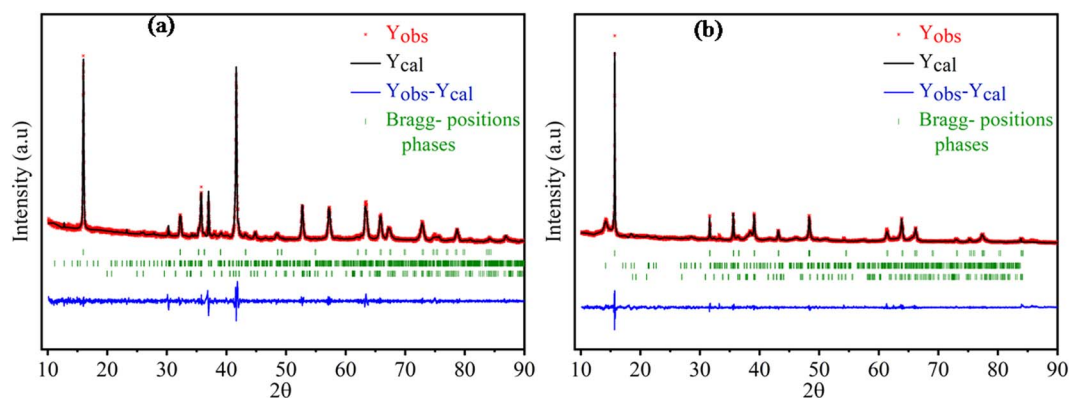


Fig. 1 The Rietveld refinement XRD of synthesized of (a)  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ , (b)  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  at room temperature.




**Table 1** Crystal data of  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  and  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ 

Compounds	$\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$	$\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$
System	Trigonal	Hexagonal
Space group	$R\bar{3}m$	$P6_3/mmc$
Formula units ( $\text{\AA}$ )	$a = b = 2.9327(2)$ $c = 16.6268(17)$ $\gamma = 120^\circ$	$a = b = 2.918(5)$ $c = 11.301(2)$ $\gamma = 120^\circ$
$R_B$	0.754	1.247
$R_f$	0.489	1.371
$\chi^2$	1.43	1.61

diagram of the P3 and P2-structure is provided in Fig. 2(a) and (b). In P2- $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ , the Na ions in prismatic sites are sandwiched between the  $\text{MO}_2$  sheets to form a layered structure. It is clearly observed that the repetitive unit number of

$\text{MO}_2$  sheets is 2 and the Na ions in prismatic site have two different types,  $\text{Na}_f$  (shares face) and  $\text{Na}_e$  (shares edge), sharing face or edge with  $\text{MO}_6$  octahedra, respectively. Both sites are simultaneously occupied by Na ions to minimize electrostatic repulsion between sodium ions.<sup>26</sup> In P3- $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ , the  $\text{Na}^+$  ions occupy prismatic sites which share faces and edges with the surrounding  $\text{MO}_6$  octahedra.<sup>27</sup> The atomic positions of each sample are illustrated in Table 1S† and the interatomic distances of Na–O and FeMn–O are portrayed in Table 2.

The investigation of the sample morphology and particle size is carried out using the scanning electron microscope (SEM). The SEM images of the investigated materials are summarized in Fig. 3. The micrographs show the agglomeration of the primary particles, and a Lorentzian fit indicating that the average particle size is 1.088  $\mu\text{m}$  for  $x = 1$  and 1.297  $\mu\text{m}$  for  $x = 2/3$  (Fig. S1†). Fig. S2† reveals the elemental composition and

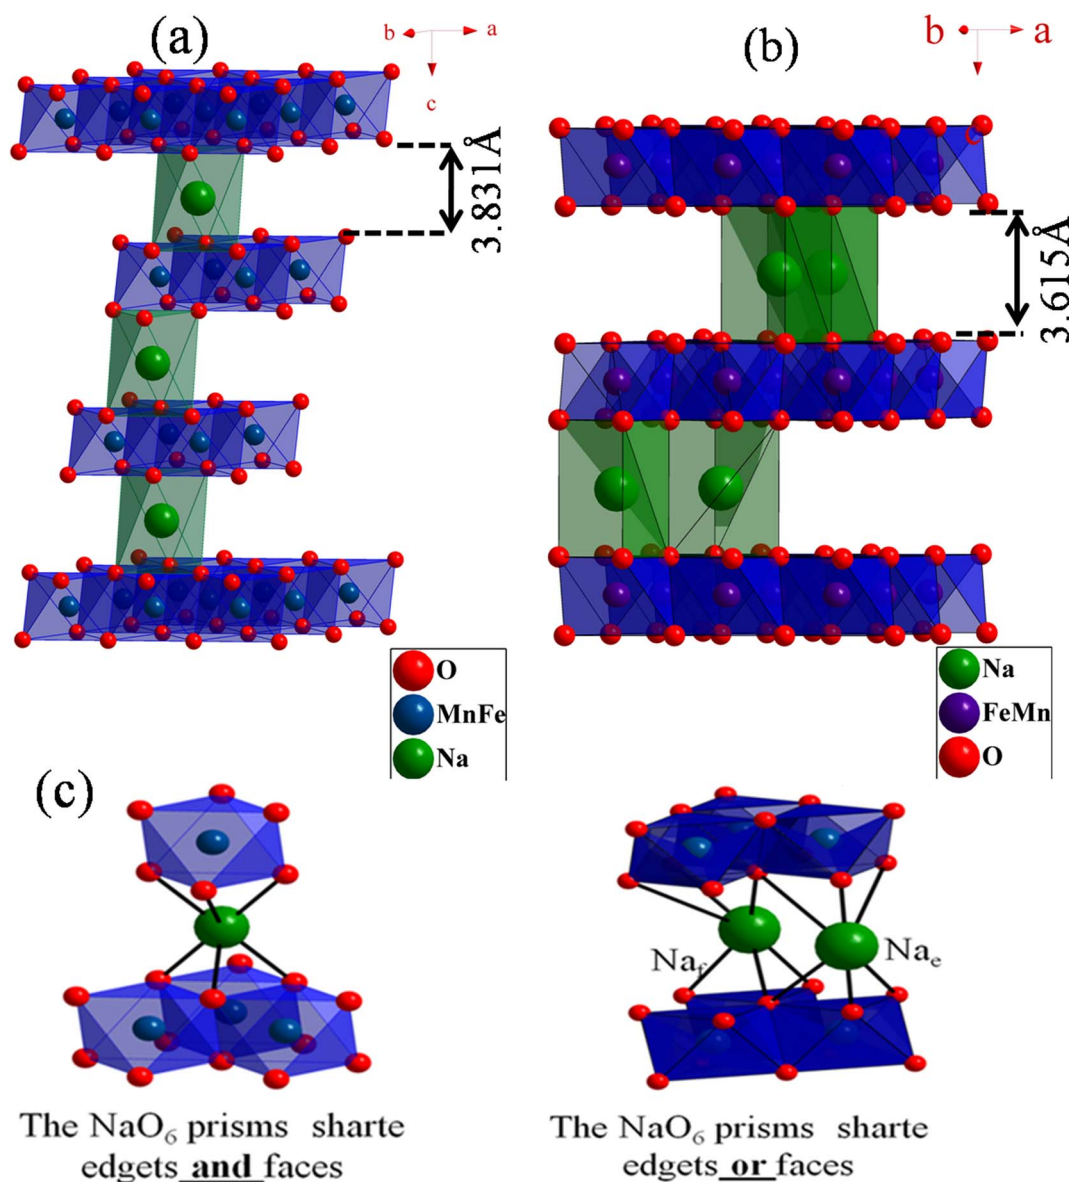

**Fig. 2** View of lamellar structure of (a) P3- $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ , (b) P2- $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  (c) the  $\text{Na}^+$  geometric site in P3 structure vs. P2 structure.



Table 2 Interatomic distances

$\text{Na}_x\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$	$x = 1$	$x = 2/3$
$\text{Na}_1\text{-O}$ (Å)	2.412	3.604
$\text{Na}_2\text{-O}$ (Å)		3.403
$\text{Mn-Fe-O}$ (Å)	1.994	2.956
$\text{Na}_1\text{-Na}_2$ (Å)		1.664

homogeneity investigated through EDX microanalysis. We infer the homogenous distribution of all elements (Na, Fe, Mn, and O), which is indicative that they are all stable at high temperatures of 700 and 1000 °C for  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  and  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ , respectively.

### 3.2. FTIR and Raman studies

At room temperature, between 350 and 1200  $\text{cm}^{-1}$ , the FTIR spectra of  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  and  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  powders were carried out (Fig. 4a). The both spectra confirm the presence of the octahedral groups  $\text{MO}_6$  ( $\text{M} = \text{Mn}$  and  $\text{Fe}$ ) in the compounds. Indeed, the observed band at 355  $\text{cm}^{-1}$  for both compounds is attributed to the deformation vibration  $\nu_4$  ( $\text{F}_{1u}$ ). The weak bands

observed at 535 and 684  $\text{cm}^{-1}$  for  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  compound and at 538 and 688  $\text{cm}^{-1}$  for  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  compound correspond to the stretch vibration at  $\nu_3$  ( $\text{F}_{1u}$ ). Notably, the stretching vibration of the Na-O band is represented by the peaks detected at about 868 and 904  $\text{cm}^{-1}$  for composition  $x = 1$  and at 866 and 902  $\text{cm}^{-1}$  for  $x = 2/3$ .<sup>28,29</sup>

Fig. 4b displays the pure Raman spectra in the 100–800  $\text{cm}^{-1}$  wave number range of  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  and  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  compounds. Two main bands are found, which is in good consistency with what the results that have been reported in the literature. The elongation vibration is attributed to  $\nu_1$  ( $\text{A}_{1g}$ ) observed band at 587 and 613  $\text{cm}^{-1}$  for  $x = 1$  and  $x = 2/3$ , respectively. The band observed at 448  $\text{cm}^{-1}$  for the compound  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  and those observed at 469 and 368  $\text{cm}^{-1}$  for the compound  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  are ascribed to  $\nu_2$  ( $\text{E}_g$ ). The distortion vibration assigned to the  $\nu_4$  ( $\text{F}_{1u}$ ) band observed at 253  $\text{cm}^{-1}$  corroborates the presence of octahedra  $\text{MO}_6$  in sample 1. The deformation vibration  $\nu_5$  ( $\text{F}_{2g}$ ) observed at 155  $\text{cm}^{-1}$  in the compound  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ ,<sup>30</sup> can be accounted for in terms of the fact that the vibrational studies at room temperature confirm the octahedral environment  $\text{MO}_6$  ( $\text{M} = \text{Fe}$ ,  $\text{Mn}$ ) observed in the structural study for these materials.

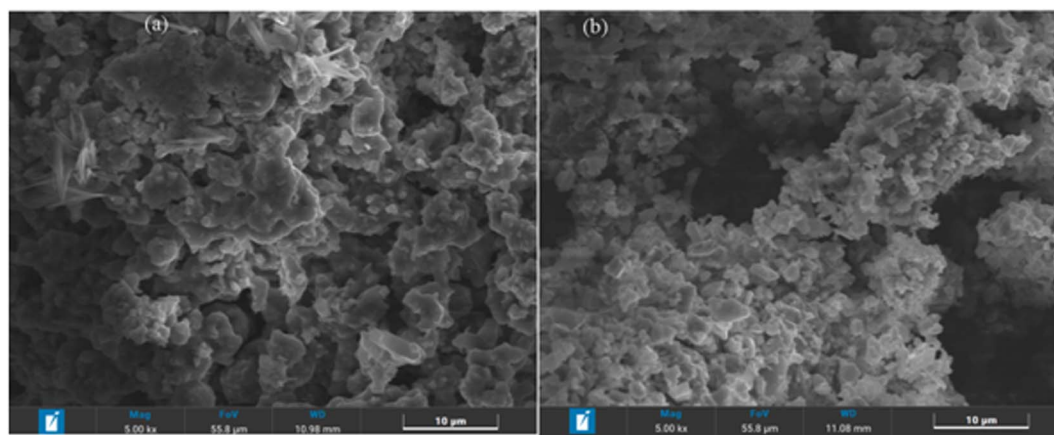


Fig. 3 SEM images, (a)  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ , (b)  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ .

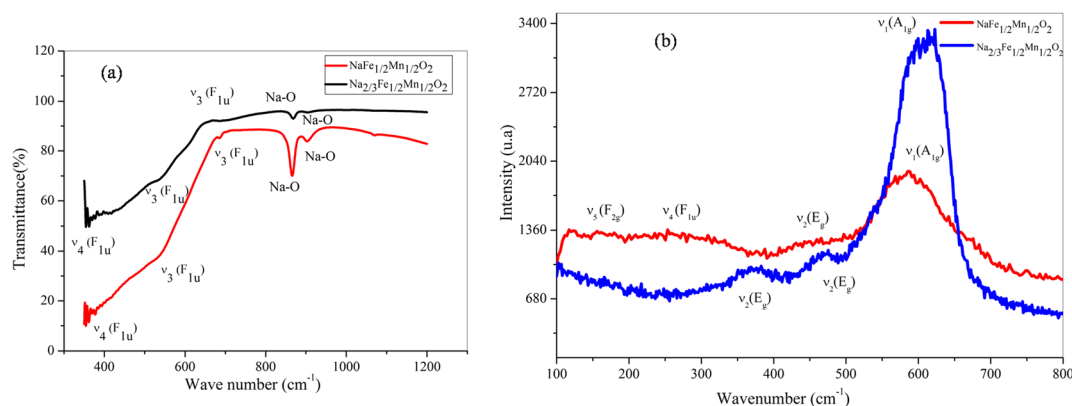


Fig. 4 (a) Fourier transform infrared (FTIR) of  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  and  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ . (b) Raman of  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  and  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ .





### 3.3. Dielectric study

Al though multiple reports have focused on lamellar oxide, numerous mechanisms have not been fully investigated to account for the different behaviors of dielectric features. Additionally, in the state of artworks, the dielectric study of these particular lamellar oxides was not fully deciphered and thoroughly addressed.

Impedance spectroscopy stands as one of the most outstanding and powerful tools to investigate the dielectric and electrical properties of these materials in large frequency and temperature ranges. Furthermore, the dependence of dielectric parameters on frequency and temperature can be analyzed as follows<sup>31</sup>

$$\varepsilon = \varepsilon' + i \cdot \varepsilon''$$

where  $\varepsilon$  stands for the dielectric constant which can be regarded as a complex number.  $\varepsilon'$  and  $\varepsilon''$  indicate the real and imaginary parts of the dielectric constant which refer to the stored energy and the energy dissipation of the applied electric field, respectively. These two parameters can therefore be calculated using the following equations.<sup>31</sup>

$$\varepsilon' = \frac{Z''}{2\pi f C_0 (Z'^2 + Z''^2)}$$

$$\varepsilon'' = \frac{Z'}{2\pi f C_0 (Z'^2 + Z''^2)}$$

where  $Z'$  and  $Z''$  express the real and the imaginary parts of the impedance, respectively.  $f$  corresponds to the frequency and  $C_0$  refers to the free space capacitance ( $C_0 = \frac{\varepsilon_0 A}{d}$  where  $d$  is the pellet thickness and  $A$  is the area).

Fig. 5a and b illustrate the real ( $\varepsilon'$ ) component of the dielectric permittivity for  $x = 1$  and  $x = 2/3$ . It is obvious that lower frequencies have greater values for these dielectric constants.<sup>32</sup> Basically, the capability for storing energy decreases as the  $\varepsilon'$  value drops at higher frequencies.<sup>33</sup> The Maxwell-interfacial Wagner's polarization may account for

the observed dielectric behavior for both compounds. This explanation interpretation is in good accordance with Koop's phenomenological theory of dielectric materials. Relying upon these models, the dielectric structure of the prepared sample is presumed to involve good-conductive grains separated by poor-conductive grain boundaries. The sample grains and grain borders need to be crossed by electrons during the exchange process. The inter-grain conductivity drops refer to the weakening of the electron hopping triggered by the grain boundary.<sup>34,35</sup> We can also infer from Fig. 6a and b that the dielectric constants ( $\varepsilon'$ ) rapidly fall at low frequencies before becoming frequency independent at high frequencies. This is in good conformity with previous findings.<sup>36,37</sup> As the electrons in the grain can no longer follow the alternating field, the consistency of ( $\varepsilon'$ ) is at high frequencies. Since the electrons hopping are thermally stimulated, it is also detected that  $\varepsilon'$  increases as the temperature increases.

Such physical phenomena, such as the conduction process, the dielectric relaxation, the interfacial polarization, and the molecular dipole moment, were chiefly responsible for the dielectric loss that quantitatively defined the electrical energy dissipation.<sup>38</sup> The dissipation factor was computed based on the following equation.

$$\tan \delta = \frac{\varepsilon''}{\varepsilon'}$$

where  $\varepsilon'$  and  $\varepsilon''$  are the real and imaginary parts of the dielectric constant ( $\varepsilon^*$ ), respectively.

Fig. 6a and b reveal that  $\tan \delta$  has relatively modest values of 1.01–12.69 for both compounds. It is to be noted that materials with little energy loss are needed for possible applications in electronic devices, which makes the compounds  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  and  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  an optimum choice. The dielectric loss factor proved to drop with an increase in frequency. Resting on Koop's theory, existing imperfections or impurities in the material build up a potential barrier for the transportation of the charge carriers. The space charge polarization restricts the partial conduction of charges until they are clogged at a possible barrier or grain boundary. These compounds equally depict two relaxation peaks in a low and a high-frequency region,

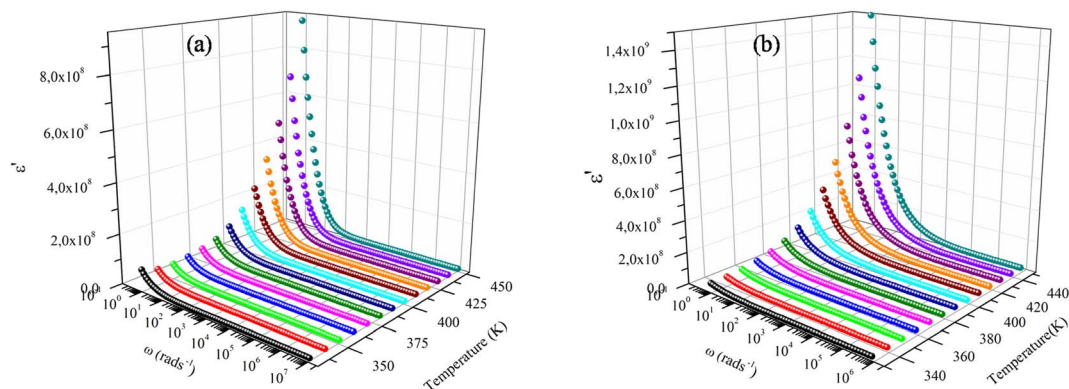


Fig. 5 Dielectric constants of the samples (a)  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ , (b)  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  at different temperatures.



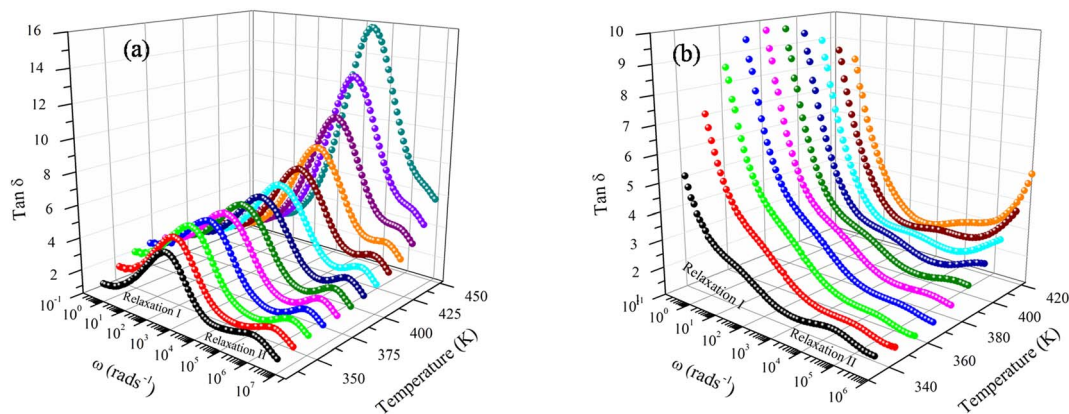


Fig. 6 Frequency-dependent dielectric loss ( $\tan \delta$ ) of (a)  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ , (b)  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ .

respectively. These peaks are indexed for space charge and dipole polarization, respectively. The heights of the relaxation peaks for  $x = 1$  are higher than those for  $x = 2/3$ , while the relaxation peaks for  $x = 1$  are found at higher frequencies compared to the peaks for  $x = 2/3$ . Consequently,  $\tan \delta$  has high values in the lower frequencies zone, and then decreases in the higher frequencies range. The space charge polarization makes it harder for charge carriers to move around in the low frequency domain, requiring additional energy. The values of  $\tan(\delta)$  are hence higher in this frequency range. The material's resistivity drops with frequency, which results in less energy being used by the passage of charge carriers. As a result, the high frequency region's dielectric loss lowers. Additionally, it is evident that  $\tan(\delta)$  gets darker as the temperature increases. It is worth noting that low energy loss plays a crucial role for the materials in battery applications. In this context, the compound  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  is a promising candidate compared to  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  for such applications.<sup>27</sup>

Fig. 8 outlines the plot of  $\ln(\omega_\delta)$  vs.  $1000/T$  ( $\omega_\delta$  is the angular frequency of grain boundary relaxation). It is noteworthy that the values of  $\omega_\delta$  go down with the increase in temperature, which indicates the thermally activated process. The temperature-dependent characteristics of  $\omega_\delta$  follow the Arrhenius relation, as presented below:

$$\omega_\delta = \omega_0 \exp\left(-\frac{E_a}{k_B T}\right)$$

where  $E_a$  is the activation energy.

The  $E_a$  values estimated from the slope of the linear fit plot (see Fig. 7a and b) amount to 0.74 eV ( $T > 363$  K) and 0.1 eV ( $T < 363$  K) for  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  and correspond to 0.62 eV for  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ .

### 3.4. Electrical impedance spectroscopy

Complex impedance spectroscopy (CIS) stands for a basic and powerful procedure invested to explore the electrical behaviour of the material. It supplies information on the relaxation time electrical conductivity and movement.<sup>40</sup>

The complex frequency-dependent impedance corresponds to a non-destructive technique depicting the electrode contribution, the grain boundary, and the bulk (grain) in the compound when the time-reversed electric field is applied. The charge carrier notably tends to become active and triggers dipole orientation.

Fig. 8 and 9 exhibit Nyquist diagrams of  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  and  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  respectively at different temperatures. The equivalent circuit parameters are foregrounded in Tables 2Sa and b.† The features of these spectra involve three distinct

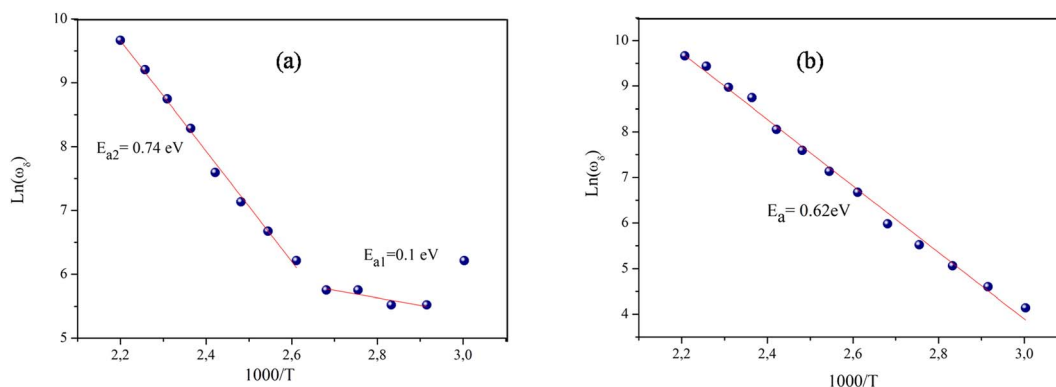


Fig. 7 The variation of  $\ln(\omega_\delta)$  versus the inverse of temperature (a)  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ , (b)  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ .



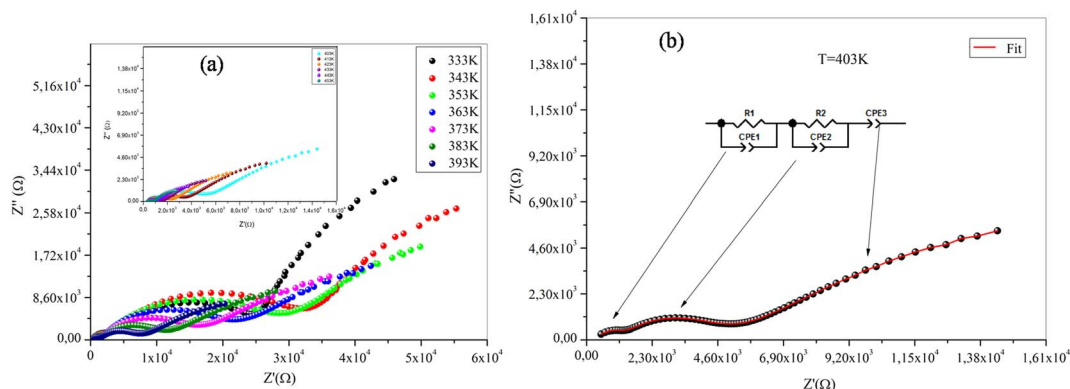


Fig. 8 (a) Nyquist diagrams of  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  sample, (b) equivalent circuit for  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  sample.

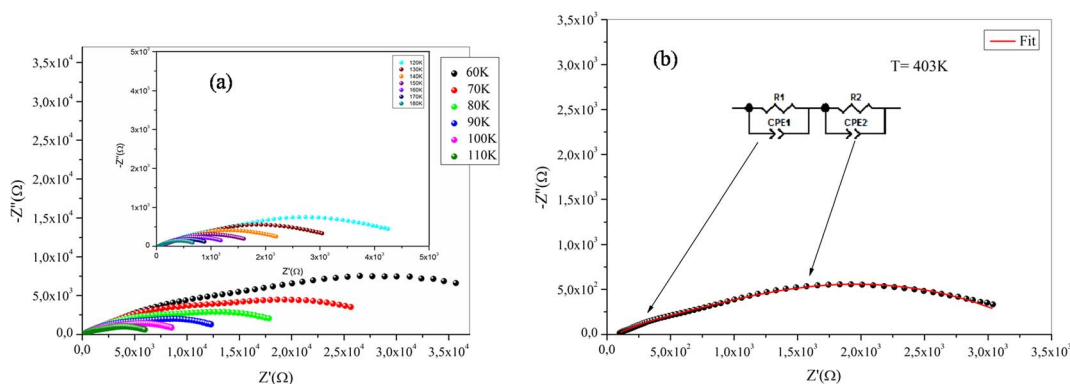


Fig. 9 (a) Nyquist diagrams of  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  sample, (b) equivalent circuit for  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  sample.

frequency domains, comprising the grain effect, correlated with high frequency, the grain boundary effect, and electrode effect, respectively at medium and low frequency of  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  compound. However, the  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  compound is marked with the two distinct frequency domains, involving the grain effect, correlated with high grain boundary effect at low frequency. Basically, the loss peak occurs when the jump frequency roughly matches the frequency of an applied external AC field. Furthermore, the hopping mechanism indicates that electrical conductivity rises with temperature which causes the thermally activated charge carriers.<sup>37</sup>

The Nyquist diagrams for both compounds indicate that the resistance drops as a function of temperature, which may refer to the improvement of the number of charge carriers and their mobility temperature. Therefore, conductivity rises with the rise in temperature. Such behaviour confirms that the conduction process is thermally activated, hence proving the semi-conducting characteristic of samples.

Adapted circuits are those that express the conformity of theoretical and experimental spectra with low error values. In our case, for  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ , the selected equivalent circuit is defined by three cells in series, as displayed in Fig. 8b. The first cell indicates the grain effect, the second stands for the grain boundary effect and the last corresponds to the electrode effect. For the  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  sample the selected equivalent circuit

is defined by two cells in series, as exhibited in Fig. 9b. The first cell indicates the grain effect and the second represents the grain boundary effect. In Fig. 10, we can infer that the grain and grain boundary resistance values of these compounds drop with increasing temperature, suggesting the behavior of a semi-conductor for our samples.<sup>39</sup> In addition, it was found that the values of  $R_{bg}$  proved to be higher than those of  $R_g$ . This may be assigned to the fact that the atomic arrangement near the grain boundary region is disordered, yielding increased electron scattering.

### 3.5. AC conductivity

Investigating charge carrier physics not only allows the classification of conduction types but also provides details on conduction modes. Fig. 11a portrays the variation of  $(\sigma_{ac})$  as a function of  $\ln(\omega)$  of the  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  sample at different temperatures. We report the existence of three domains, the first at high frequency suggesting the grain effect, the second at medium frequency representing the grain boundary effect and the third at low frequency corresponding to the electrode effect. Notably, two domains, the first at high frequency indicating the grain effect and the second at low frequency suggesting the grain boundary effect, characterize the variation of conductivity as a function of the frequency for the compound  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  (Fig. 11b). The low frequency ( $\ln(\omega) \geq 4 \text{ rad s}^{-1}$ ) spike



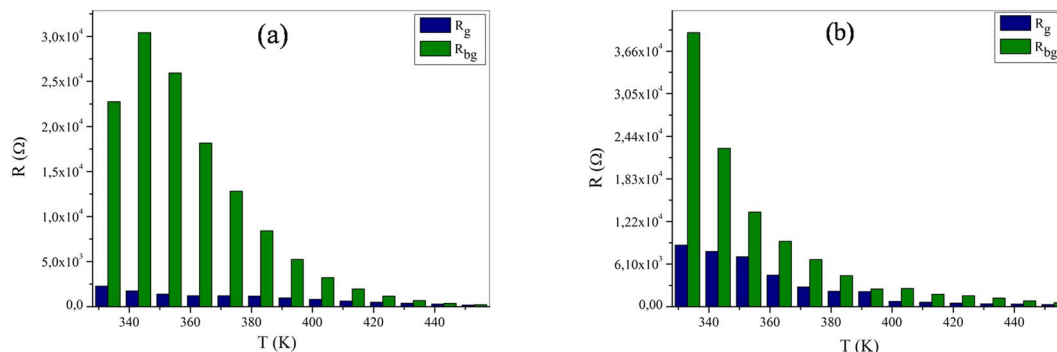


Fig. 10 The variation of (a)  $R_g$ ,  $R_{bg}$  versus the temperature for  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  and (b)  $R_g$ ,  $R_{bg}$  versus the of temperature for  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ .

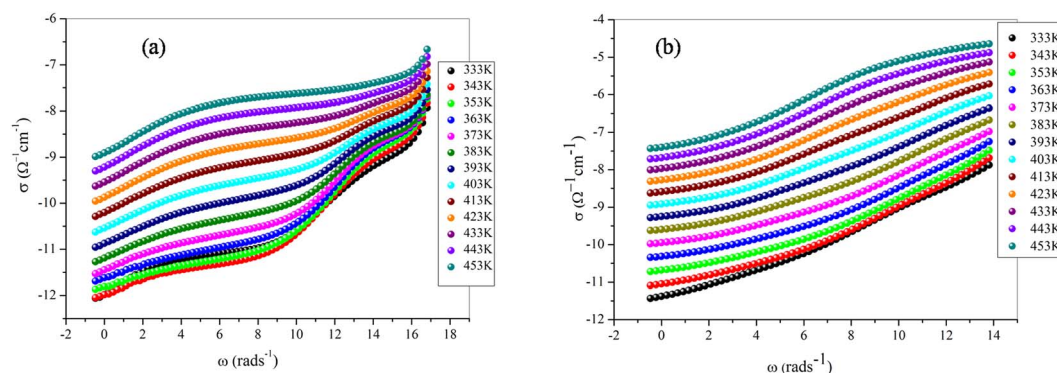


Fig. 11 Frequency dependence of conductivity of the samples (a)  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ , (b)  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  versus the inverse of temperature.

characterizing electrode–electrolyte interfacial phenomena is assigned to the space charge polarization at the blocking electrodes of  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  compound. In each frequency domain, the conductivity is estimated relying on Jonscher's law:<sup>40</sup>

$$\sigma_{ac} = \sigma_{dc} + A\omega^s$$

where  $\sigma_{dc}$  is the sample direct current conductivity,  $A$  is a temperature-dependent constant that determines the strength of polarizability and the exponent  $s$  is the power law exponent.  $s$  is used to identify the interaction between mobile ions with the environments surrounding them where  $0 < s < 1$ .

The  $\text{Na}^+$  ion presents the same high frequency conduction behavior as both compounds exhibit only one high frequency dispersion region. The latter is related to hopping conduction, in which mobile ions can cross barriers more easily when temperature increases. Conductivity proved to be caused by mobile ions ( $\text{Na}^+$ -ions), depending on their environment. Moreover, the Fe/MnO<sub>6</sub> octahedra exert a significant impact on the mobility of  $\text{Na}^+$  ions.

According to Yabuuchi *N. et al.* the compounds with higher conductivity have high electrochemical performance. Therefore, the conductivity of  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  compound demonstrates almost twice the conductivity of  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  compound. Thus, we concluded that the variation of sodium

content influences the electrochemical performance of the cathode material in sodium-ion batteries.

At the low frequency region, the curves indicate that our samples exhibit semiconducting behaviour in all temperature ranges. The experimental data of dc conductivity are well fitted by the Mott and Davis law, which determines small polaron hopping (SPH) (Fig. 12a and b)<sup>40</sup> in terms of:

$$\sigma_{dc}T = \sigma_0 e^{\left(-\frac{E_a}{k_B T}\right)}$$

where  $E_a$  represents the activation energy of the dc-conductivity and  $\sigma_0$  expresses the pre-exponential factor when the temperature tends to infinite values. These activation energy as obtained from a linear fit of the experimental data are  $E_a = 0.2$  eV for  $T < 363$  K and  $E_a = 0.53$  eV for  $T > 363$  K of  $x = 1$  as a consequence  $E_a = 0.42$  eV of  $x = 2/3$ . We observe a shift in slope for the  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  compound approaching  $T = 363$  K. At low temperature, a small number of the charge carriers were thermally active and their movement was not the same as that at high temperature. It is noted that both compounds are characterized by the same activation energy at high temperature. For the compound  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ , the doubling of the activation energy at 363 K can be accounted for in terms of a change in the charge carrier (from a small polaron to a large polaron or from a single polaron to a double polaron).





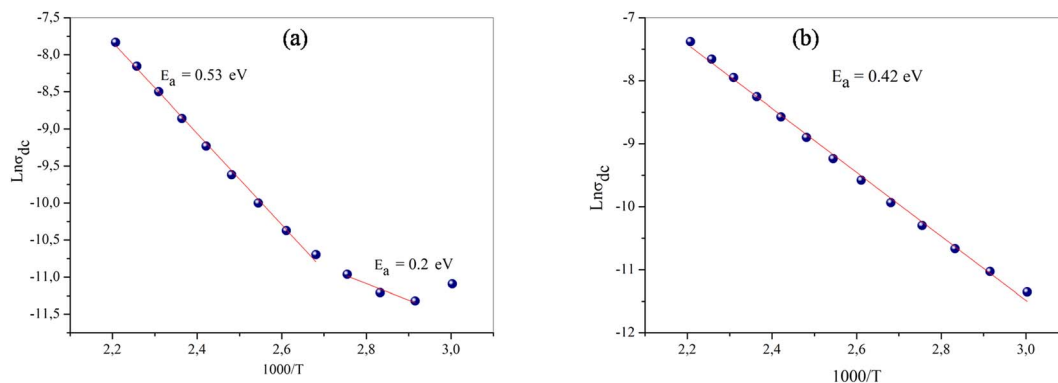


Fig. 12 The variation of  $\ln(\sigma_{dc})$  of the samples (a)  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ , (b)  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  versus  $1000/T$ .

The conductivity value of  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  almost doubles that of  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  referring to the fact that the  $\text{Na}^+$  ions are freer in the first compound. Indeed, the Na–O inter-atomic distance in the P2 type structure is equal to 3.604 Å, which is larger than that of P3 structure (2.412 Å). In addition, the mobility of sodium is easier in this structure and therefore the ionic conduction is greater in this compound.

Particularly, when compared to other similar compounds such as  $\text{LiCoO}_2$ , which is the most preferred positive electrode material, an enhancement of conduction in  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  and  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  was recorded. Indeed, at room temperature  $\text{LiCoO}_2$  has conductivity of  $2.29 \times 10^{-4} (\Omega \text{ cm})^{-1}$ ,<sup>41</sup> which is lower than that of  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  and  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ , whose conductivities are  $4.62 \times 10^{-4}$  and  $9.32 \times 10^{-4} (\Omega \text{ cm})^{-1}$ , respectively. Thus,  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  is a viable option and potential cathode candidate for Na ion batteries.

To gain a deeper and better insight into the change in the activation energy at 363 K for  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  compound and the increase in conductivity by the reduction in the rate of sodium (x), undertaking a study of the mechanism of conduction in these materials is intrinsic.

The originality as well as the main contribution of our study lies basically in extracting of our study different  $s$  values for different relaxation processes. The variation of  $s_1$  (the power law exponent which corresponds to the grain boundary) and  $s_2$  (the power law exponent which corresponds to the grain) for the compound  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  is plotted in Fig. 13a and b. The exponent  $s_1$  increases in the temperature range 333–363 K and then decreases (low value  $s_1 < 0.5$ ) at the beginning of the temperature 363 K, which confirms that the grain boundary conduction mechanism changes from the non-overlapping small polaron tunneling (NSPT) to the overlapping large-polaron tunneling model (OLPT) model.<sup>42,43</sup> The exponent  $s_2$  decreases with temperature and lies between 0.65 and 0.95, indicating that the grain conduction phenomenon in this material corresponds to the correlated barrier hopping (CBH) model.<sup>42</sup> As far as this model is concerned, the exponent ( $s$ ) can be identified by the following relation:  $s = 1 - \frac{6K_B T}{W_M}$ .<sup>42</sup> It is clear that there is a change of slope in the variation of  $s$ . Fitting the curve of  $s$  through the use of this equation allows to calculate

the energy for self-trapping  $W_M$  (Fig. S3†). The value of  $W_{M2} = 0.42$  eV for  $T > 363$  is the double of  $W_{M1} = 0.18$  eV for  $T < 363$  K, which proves that there is a transition from a CBH model of a single polaron at low temperature to a CBH model of double polaron for  $T > 363$  K.<sup>42</sup> Fig. 13c and d portray the variation of  $s_1$  and  $s_2$  of the compound  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ . The coefficient  $s_1$  which corresponds to the grain boundary decreases, increases to a great extent according to the temperature and the one which corresponds to the grain ( $s_2$ ) decreases according to the temperature and it is lower than 0.32. According to Elliott,<sup>43</sup> the OLPT is the most appropriate model in both frequency domains.

Since the frequency dependence of conductivity is important for exploring the mechanism of conduction, the temperature dependence of conductivity is equally fundamental to trace the evolution of the CBH and OLPT models at the grain level in both compounds. Fig. S4a.† demonstrates the variation of AC conductivity as a function of the inverse of the temperature at different frequencies. The correlated barrier hopping corresponds to a model of electron transfer by thermal activation over the barrier between two sites, each displaying a coulombic potential associated related to it. The good accordance between the experimental data and the theoretical calculation fit corroborated that the CBH model characterizes well the behavior of the  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  sample well, allowing a better estimation of the parameters according to the equation.<sup>44</sup>

$$\delta_{AC} = \frac{n\pi^2 NN_p \epsilon' R_\omega^6}{24}$$

where  $n$  refers to the number of polaron involved in the hopping process,  $NN_p$  is proportional to the square of the concentration of states and  $\epsilon'$  stands for the dielectric constant for a fixed frequency value. The hopping can be indicated by a single polaron or by a bipolaron, where:

$$NN_p = N_T^2 \text{ (for bipolar hopping)}$$

$$NN_p = N_T^2 e^{\frac{-U_{eff}}{2K_B T}} \text{ (for single polaron)}$$



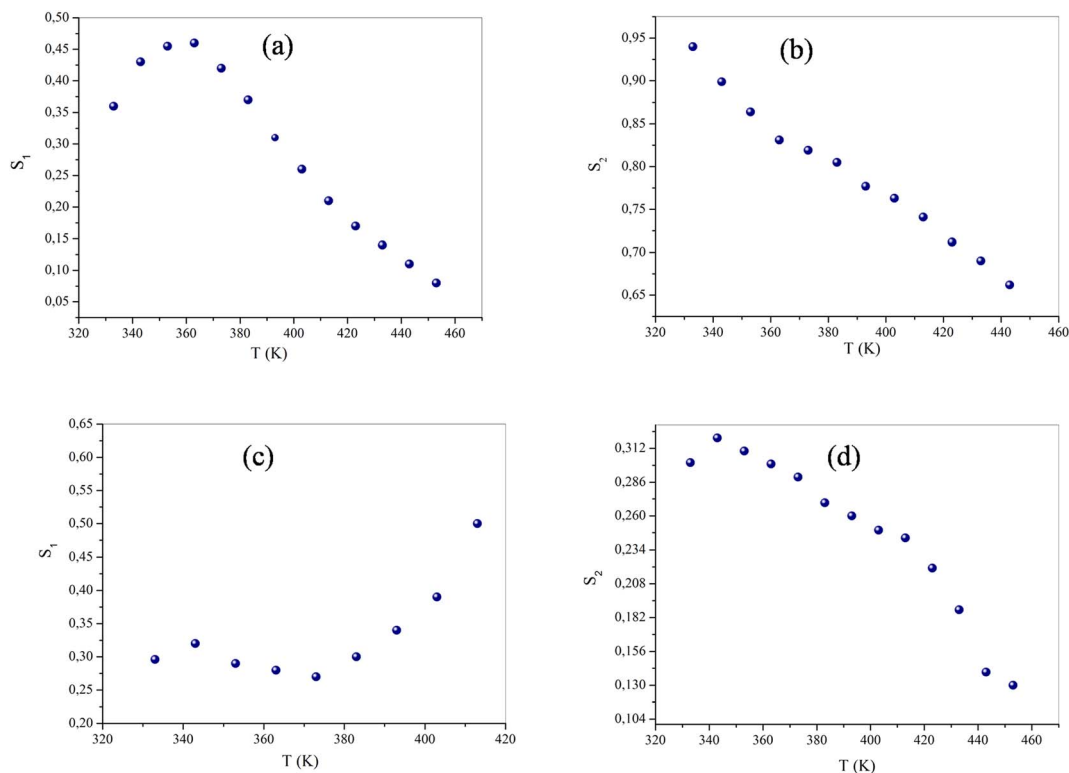


Fig. 13 The variation of the exponent  $s$  (a and c) grain boundary, (b and d) grain of  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  and  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  of compounds respectively as a function of temperature.

The hopping length  $R_\omega$  is determined by the expression:

$$R_\omega = \frac{4ne^2}{\pi\epsilon'\epsilon_0[W_M + K_B T \ln(\omega\tau_0)]}$$

where  $W_M$  stands for the height of the maximum barrier, whose value drops to a value  $\omega$ , provided in the case of a single polaron by the following expression:

$$W = W_M - \frac{e^2}{\pi\epsilon'\epsilon_0 R}$$

The multiple parameters invested in the fitting procedure are outlined in Tables 3Sa and b.† The negative sign of the effective energy for the single polaron CBH model is associated with the strong interaction between electron and photon. Fig. 14 reveals that the density states decrease with increasing frequency, which is quite expected since the frequency increase stimulates the mobility of the charge carriers, indicating their non-localization.

Fig. S4b† exhibits the variation of  $\ln(\sigma_{ac})$  conductivity as a function of the inverse of temperature for  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  sample. These curves are fitted using the following expression which corresponds to the OLPT model:<sup>45</sup>

$$\sigma_{ac}(\omega) = \frac{\pi^4}{12} e^2 (kT)^2 N^2(E_F) \frac{\omega R_\omega^4}{2\alpha kT + \frac{\omega_{H_0} r_p}{R_\omega^2}}$$

where  $R_\omega$  is the intersite separation,  $r_p$  is the radius of the large polaron, and  $\omega_{H_0}$  is denoted by

$$\omega_{H_0} = \frac{e^2}{4\epsilon_p r_p}$$

where  $\epsilon_p$  is the effective dielectric constant and the tunneling distance for a fixed frequency that can be computed with reference to the equation:

$$R_\omega = \frac{1}{4\alpha} \left[ \ln\left(\frac{1}{\omega\tau_0}\right) - \frac{\omega_{H_0}}{K_B T} \right] + \left[ \left[ \ln\left(\frac{1}{\omega\tau_0}\right) - \frac{\omega_{H_0}}{K_B T} \right]^2 + \frac{8\alpha r_p \omega_{H_0}}{K_B T} \right]^2$$

where  $N(E_F)$  represents the density of the contained state,  $\tau_0$  indicates the relaxation time considered as a constant of the order of  $10^{-13}$  s in numerous prior works,  $\omega_{H_0}$  expresses the activation energy related to the transfer of charge between the overlapping sites,  $K_B$  is the Boltzmann constant,  $r_p$  refers to the radius of the polaron and  $R_\omega$  stands for the distance of the tunnel polarons.

These expressions were used in order to better and deeper understand the changes occurring in the material when this model takes place. However, in the OLPT model (Table 4S†), the increase of the frequency entails the decrease of the density of the charge carrier  $N_T$  (Fig. 14c), the polaron radius  $r_p$  and its hopping energy  $\omega_{H_0}$ . This indicates that the increase in frequency stimulates the mobility of the charge carrier and triggers the reduction of the polaron radius and therefore its hopping energy.<sup>46,47</sup>



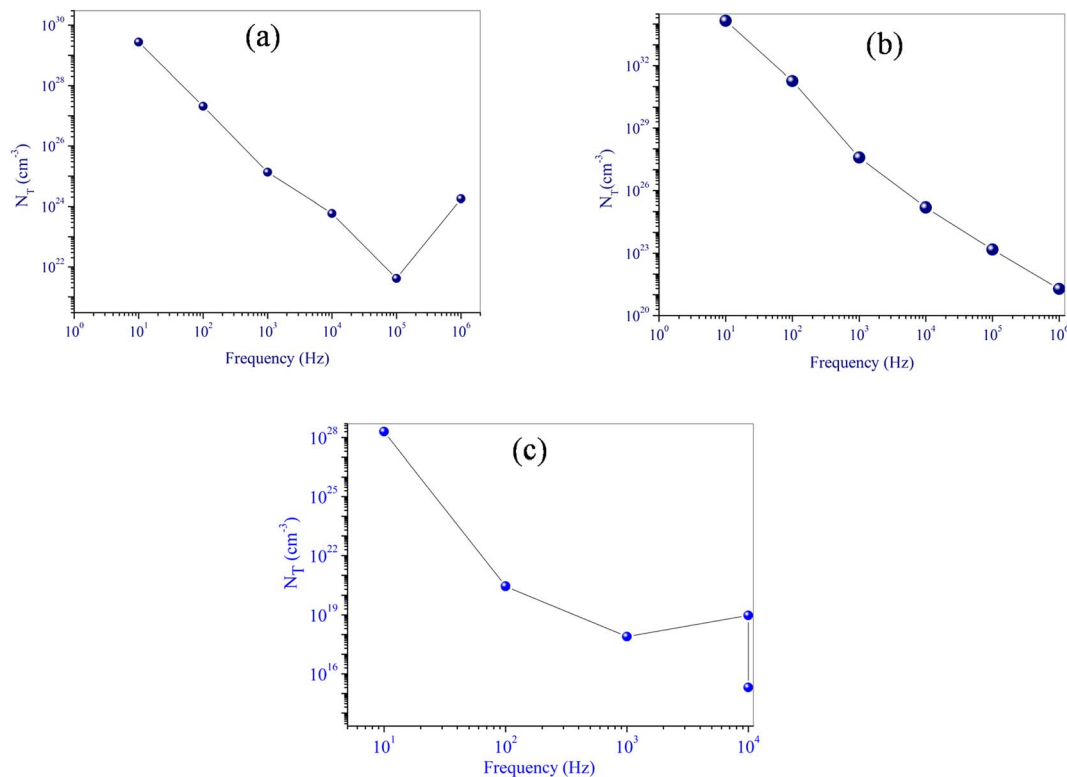


Fig. 14 Frequency dependency of the density states  $N_T$  for  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  (a) single polaron (b) bipolaron (c)  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ .

In the current research work, we proved that the environment of Na in the materials  $\text{Na}_x\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  ( $x = 1$  and  $2/3$ ) impacts the conduction model. For  $x = 1$ , the structure is of P3 type, where  $\text{Na}^+$  occupies prismatic sites which share faces and edges with the octahedra  $\text{MO}_6$ . The conductivity obeys, therefore, the jump model. However, for  $x = 2/3$ , the structure is of P2 type, where  $\text{Na}^+$  occupies prismatic sites which share only the edges with the octahedra  $\text{MO}_6$ . The conductivity obeys, therefore, the tunnel model. Indeed, the height of the  $\text{NaO}_6$  prism in the P2 structure is higher than that in the P3 structure, which gives rise to the tunnel model (OLPT) in the compound  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$ .

## 5. Conclusion

In this work, we successfully synthesized  $\text{Na}_x\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  samples ( $x = 1$  and  $2/3$ ) using a solid state method. We confirmed that the compounds present hexagonal and rhombohedral lattices, with  $R\bar{3}m$  and  $P6_3/mmc$  space groups, respectively, for  $x = 1$  and  $2/3$ . Therefore the compound  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  has a P3 type structure, while the compound  $\text{Na}_{2/3}\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  has a P2 type structure. The presence of the  $\text{MO}_6$  group in these materials was confirmed by the FTIR and Raman vibration spectra. SEM analysis reveals that these samples have a homogeneous morphology with regularly shaped grains. The analysis of complex impedance measurements proved the presence of grain and grain boundary effects for both compounds. The study of dielectric and conductivity  $\sigma_{dc}$  of  $\text{NaFe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  compound demonstrated a change in

activation energy at  $T = 363$  K, which is confirmed by a change in conduction mechanism. We found that the values of the dielectric loss for  $x = 2/3$  are lower than those for  $x = 1$ . It has been found that the grain conduction mechanism in these materials is dependent on the sodium environment. It is of the CBH type in the P3 structure and of the OLPT type in the P2 structure. It is inferred for both compounds that the density states decrease with increasing frequency, which is expected since increasing frequency stimulates the mobility of charge carriers, indicating their non-localization.

## Conflicts of interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

## References

- 1 N. Yabuuchi, K. Kubota, M. Dahbi and S. Komaba, *Chem. Rev.*, 2014, **114**, 11636–11682.
- 2 A. Tripathi, S. Xi, R. S. Gajjala and P. Balaya, *Chem. Commun.*, 2020, **56**(73), 10686–10689, DOI: [10.1039/d0cc03701](https://doi.org/10.1039/d0cc03701).
- 3 Y. Sui, Y. Hao, X. Zhang, J. Li, G. Wen, S. Zhong, Z. Zhang and L. Wu, *Ceram. Int.*, 2021, **47**(4), 5227–5234, DOI: [10.1016/j.ceramint.2020.10.102](https://doi.org/10.1016/j.ceramint.2020.10.102).
- 4 Z. Shadik, E. Zhao, Y. N. Zhou, *et al*, Advanced characterization techniques for sodium-ion battery studies, *Adv. Energy Mater.*, 2018, **8**, 1702588.



- 5 M. Fehse, D. Bessas, A. Mahmoud, A. Diatta, R. P. Hermann, L. Stievano and M. T. Sougrati, *Batteries Supercaps*, 2020, **3**, 1341–1349.
- 6 P. K. Nayak, L. Yang, W. Brehm and P. Adelhelm, *Angew. Chem., Int. Ed.*, 2018, **57**, 102–120.
- 7 Y. Lia, Y. Lu, C. Zhao, Y. S. Hu, M. M. Titirici, H. Li, X. Huang and L. Chen, *Energy Storage Mater.*, 2017, **7**, 130–151.
- 8 Y. Lu, C. Zhao, X. Qi, Y. Qi, H. Li, X. Huang, L. Chen and S. Y. Hu, *Adv. Energy Mater.*, 2018, **8**(27), 1800108, DOI: [10.1002/aenm.201800108](https://doi.org/10.1002/aenm.201800108).
- 9 Y. Li, Y. Lu, C. Zhao, S. Y. Hu, M. M. Titirici, H. Li, X. Huang and L. Chen, *Energy Storage Mater.*, 2017, **7**, 130–151, DOI: [10.1016/j.ensm.2017.01.002](https://doi.org/10.1016/j.ensm.2017.01.002).
- 10 R. Berthelot, D. Carlier and C. Delmas, Electrochemical Investigation of the P2– $\text{Na}_x\text{CoO}_2$  Phase Diagram, *Nat. Mater.*, 2011, **10**(1), 74–80.
- 11 M. Guignard, C. Didier, J. Darriet, P. Bordet, E. Elkaïm and C. Delmas, P2- $\text{Na}_x\text{VO}_2$  System As Electrodes for Batteries and Electron-Correlated Materials, *Nat. Mater.*, 2013, **12**(1), 74–80.
- 12 X. Ma, H. Chen and G. Ceder, Electrochemical Properties of Monoclinic  $\text{NaMnO}_2$ , *J. Electrochem. Soc.*, 2011, **158**(12), A1307–A1312.
- 13 D. Yuan, X. Liang, L. Wu, Y. Cao, X. Ai, J. Feng and H. Yang, A Honeycomb-Layered  $\text{Na}_3\text{Ni}_2\text{SbO}_6$ , A High-Rate and Cycle-Stable Cathode for Sodium-Ion Batteries, *Adv. Mater.*, 2014, **26**(36), 6301–6306.
- 14 I. Hasa, D. Buchholz, S. Passerini and J. Hassoun, A Comparative Study of Layered Transition Metal Oxide Cathodes for Application in Sodium-Ion Battery, *ACS Appl. Mater. Interfaces*, 2015, **7**(9), 5206–5212.
- 15 J. Li, S. L. Glazier, J. Paulsen, J. R. Dahn, X. Ma and J. Harlow, *J. Electrochem. Soc.*, 2018, **165**, 3195–3204.
- 16 C. Fang, Y. Huang, W. Zhang, J. Han, Z. Deng, Y. Cao and H. Yang, *Adv. Energy Mater.*, 2016, **6**, 5.
- 17 C. Delmas, C. Fouassier and P. Hagenmuller, *Physica B+C*, 1980, **99**, 81–85.
- 18 J. P. Parant, R. Olazcuaga, M. Devalette, C. Fouassier and E. T. P. Hagenmuller, *J. Solid State Chem.*, 1971, **3**, 1.
- 19 S. Kikkawa, S. Miyazaki and M. Koizumi, *J. Power Sources*, 1985, **14**, 231.
- 20 J. Zhao, L. Zhao, N. Dimov, S. Okada and T. Nishida, *J. Electrochem. Soc.*, 2013, **160**(5), A3077–A3081.
- 21 C. Delmas, C. Fouassier and P. Hagenmuller, *Physica B+C*, 1980, **99**, 81.
- 22 X. Lu, Y. Wang, P. Liu, L. Gu, Y. S. Hu, H. Li, G. P. Demopoulos and L. Chen, Direct imaging of layered O3-and P2- $\text{Na}_x\text{Fe}_{1/2}\text{Mn}_{1/2}\text{O}_2$  structures at the atomic scale, *Phys. Chem. Chem. Phys.*, 2014, **16**(40), 21946–21952.
- 23 N. Yabuuchi, M. Kajiyama, J. Iwatate, H. Nishikawa, S. Hitomi, R. Okuyama, R. Usui, Y. Yamada and S. Komaba, P2-type  $\text{Na}_x[\text{Fe}_{1/2}\text{Mn}_{1/2}]\text{O}_2$  made from earth-abundant elements for rechargeable Na batteries, *Nat. Mater.*, 2012, **11**(6), 512–517.
- 24 B. Mortemard de Boisse, D. Carlier, M. Guignard and C. Delmas, *J. Electrochem. Soc.*, 2013, **160**, A569–A574.
- 25 B. D. Yuan, X. Hu, J. Qian, F. Pei, F. Wu, R. Mao, X. Ai, H. Yang and Y. Cao, *Electrochim. Acta*, 2014, **116**, 300–305.
- 26 C. Delmas, C. Fouassier and P. Hagenmuller, *Physica B Condens.*, 1980, **99**, 81.
- 27 I. Ben Slima, K. Karoui, A. Mahmoud, F. Boschini and A. Ben Rhaïem, Structural, optical, electric and dielectric characterization of a  $\text{NaCu}_{0.2}\text{Fe}_{0.3}\text{Mn}_{0.5}\text{O}_2$  compound, *RSC Adv.*, 2022, **12**, 1563.
- 28 S. Singh, A. Kumar, T. Gurmeet and S. Lotey, Optical and Luminescence Properties of b- $\text{NaFeO}_2$  Nanoparticles, *Electron. Mater. Lett.*, 2018, **14**, 594–596, DOI: [10.1007/s133910180067-5](https://doi.org/10.1007/s133910180067-5).
- 29 K. Nakamoto, *Infrared and Raman Spectra of Inorganic and Coordination Compounds, Part A: Theory and Applications in Inorganic Chemistry*, J. Wiley, S. Inc, 6th edn, 2009.
- 30 Wiley and S. Ltd, *Handbook of Vibrational Spectroscopy*, 2006.
- 31 R. Kalthoum, M. Ben Bechir, A. Ben Rhaïem and M. Gargouri, *Phys. Status Solidi*, 2021, **218**, 2100485.
- 32 F. Hcini, S. Hcini, B. Alzahrani, S. Zemni and M. L. Bouazizi, *J. Mater. Sci.: Mater. Electron.*, 2020, **31**, 14986.
- 33 F. Hcini, S. Hcini, B. Alzahrani, S. Zemni and M. L. Bouazizi, *Appl. Phys. A*, 2020, **126**, 362.
- 34 K. W. Wagner, *Ann. Phys.*, 1913, **40**, 817.
- 35 C. G. Koops, *Phys. Rev.*, 1951, **83**, 121.
- 36 S. Hcini, A. Omri, M. Boudard, M. L. Bouazizi, A. Dhahri and K. Touileb, *J. Mater. Sci.: Mater. Electron.*, 2018, **29**, 6879.
- 37 M. Ben Bechir and M. H. Dhaou, *Mater. Res. Bull.*, 2021, **144**, 111473.
- 38 P. Sengupta, P. Sadhukhan, A. Ray, R. Ray, S. Bhattacharyya and S. Das, *Appl. Phys.*, 2020, **127**, 204103.
- 39 K. Trabelsi, K. Karoui, F. Jomni and A. Ben Rhaïem, *J. Alloys Compd.*, 2021, **867**, 159099.
- 40 M. Ben Bechir and A. Ben Rhaïem, *Phys. E*, 2021, **130**, 114686.
- 41 B. Nageswara Rao, M. Venkateswarlu and N. Satyanarayana, *Ionics*, 2014, **20**, 175.
- 42 M. Krimi, K. Karoui, J. J. Suñol and A. B. Rhaïem, *Phase Transitions*, 2019, **92**, 737.
- 43 I. Ben Slima, K. Karoui, A. Mahmoud, F. Boschini and A. Ben Rhaïem, *J. Alloys Compd.*, 2022, **920**, 166002.
- 44 M. Krimi, K. Karoui, J. J. Suñol and A. B. Rhaïem, Optical and electrical properties of  $\text{Li}_2\text{WO}_4$  compound, *Phase Transitions*, 2019, 1639701, DOI: [10.1080/01411594](https://doi.org/10.1080/01411594).
- 45 M. Krimi, K. Karoui, J. J. Suñol and A. Ben Rhaïem, Phase transition, impedance spectroscopy and conduction mechanism of  $\text{Li}_{0.5}\text{Na}_{1.5}\text{WO}_4$  material, *Phys. E*, 2018, **102**, 137.
- 46 W. Nasr and A. Ben Rhaïem, Ferroelectric properties and alternative current conduction mechanisms of lithium rubidium molybdate, *Ionics*, 2019, **25**, 4003.
- 47 W. Ben Nasr, A. Mahmoud, F. Boschini and A. Ben Rhaïem, Optical and AC conductivity studies on  $\text{Li}_2\text{xRb}_x\text{MoO}_4$  (x= 0, 0.5, 1) compounds, *J. Alloys Compd.*, 2019, **522**, 788.

