


Cite this: *RSC Adv.*, 2023, 13, 35562

Received 29th October 2023  
Accepted 29th November 2023

DOI: 10.1039/d3ra07367j

rsc.li/rsc-advances

# Hydrophilic amorphous Cr<sub>2</sub>O<sub>3</sub> supported Co species toward efficient hydrogen production from ammonia borane under visible light irradiation†

Fenglong Wu \* and Jin Song \*

Herein, we synthesized a hydrophilic support formed from amorphous Cr<sub>2</sub>O<sub>3</sub> and KIT-6 containing P123 using a simple solvent-free thermal method for Co species. The obtained catalyst (denoted as Co/Cr<sub>2</sub>O<sub>3</sub>-F-X) exhibits high activity for hydrogen production from ammonia borane (NH<sub>3</sub>BH<sub>3</sub>). The optimal Co/Cr<sub>2</sub>O<sub>3</sub>-F-0.5 exhibits the highest catalytic performance with the turnover frequency (TOF) value of 111.1 min<sup>-1</sup>. Advanced characterizations suggest the high catalytic performance is attributed to the synergistic effect of the strong interaction between amorphous Cr<sub>2</sub>O<sub>3</sub> and KIT-6 containing P123 and improved wettability of the catalyst.

## 1. Introduction

Hydrogen (H<sub>2</sub>) as clean energy has attracted much attention owing to zero carbon emissions and high combustion value.<sup>1–3</sup> Ammonia borane (NH<sub>3</sub>BH<sub>3</sub>) as a promising hydrogen storage material with high hydrogen content (19.6 wt%) can present the solution for the challenges of safe transportation and storage of H<sub>2</sub>.<sup>4,5</sup> The hydrolysis of NH<sub>3</sub>BH<sub>3</sub> (NH<sub>3</sub>BH<sub>3</sub> + 2H<sub>2</sub>O → NH<sub>4</sub>BO<sub>2</sub> + 3H<sub>2</sub>) is considered a promising strategy to generate H<sub>2</sub> due to the mild reaction conditions.<sup>6,7</sup> Supported heterogeneous catalysts play an important role in accelerating the reaction rate.<sup>8–10</sup> Various metal based catalysts including precious and non-precious metals have been employed for hydrolysis of NH<sub>3</sub>BH<sub>3</sub>.<sup>11–18</sup> However, the high cost of precious metals and low activity of non-precious metals hinder the large-scale application of NH<sub>3</sub>BH<sub>3</sub>. Many efforts have been made to decrease the dosage of precious metals and enhance the activity of non-precious metal based catalysts. Regulating the electronic structure of active metals is a common strategy to improve the activity of catalysts. Recently, introducing light irradiation into reaction systems, especially non-precious metals working as catalysts, has been proven to be an effective method to boost the charge imbalance distribution and then catalytic performance.<sup>19–22</sup> Nevertheless, the activity of non-precious metal catalyst is still far from satisfaction. As a result, it is urgent to rationally design the structure of non-noble metal catalysts to obtain high activity level.

Earth-abundant Co catalysts have been utilized in NH<sub>3</sub>BH<sub>3</sub> hydrolysis.<sup>23–26</sup> For example, Co-Co<sub>3</sub>O<sub>4</sub> has been employed as

excellent catalyst for H<sub>2</sub> generation from NH<sub>3</sub>BH<sub>3</sub> due to electronic structures at the interface and abundant adsorption site.<sup>27</sup> Our group have also prepared high performance Co/Cr<sub>2</sub>O<sub>3</sub> composed of electron-deficient Co species and mesoporous Cr<sub>2</sub>O<sub>3</sub>. Cr<sub>2</sub>O<sub>3</sub> is selected as support due to several reasons. Firstly, Cr<sub>2</sub>O<sub>3</sub> has been widely applied in photoinduced reaction.<sup>28</sup> Secondly, Cr<sub>2</sub>O<sub>3</sub> with relatively high work function induces electron transfer from Co. Importantly, electron-deficient Co species can decrease H<sub>2</sub>O activation and dissociation energy barriers (rate-determining step in NH<sub>3</sub>BH<sub>3</sub> hydrolysis) and then accelerate the rate of reaction.<sup>29</sup> To date, the design of catalyst has mainly focused on tuning electronic structures of active metal, while neglects catalyst wettability. The appropriate wettability of a catalyst can significantly enhance the adsorption and transfer of reactants, resulting in enhancement activity.<sup>30</sup> For example, Zhao group reported the activity of NiFe/NiFe:Pi toward oxygen evolution is significantly enhanced by tuning the wettability of the catalyst.<sup>31</sup> Xiao group reported the conversion of syngas to methane, dimethyl ether, and olefins can be regulated by controlling the catalyst hydrophobicity.<sup>32</sup> Accordingly, regulating catalyst wettability is an effective strategy to further boost the rate of NH<sub>3</sub>BH<sub>3</sub> hydrolysis. Introduction of hydrophilic SiO<sub>2</sub> into reaction system can alter H<sub>2</sub>O adsorption behaviour.<sup>33</sup> Therefore, introduction of material containing hydrophilic SiO<sub>2</sub> is effective strategy to enhance the catalyst activity.

Herein, we prepared hydrophilic Co-based catalyst Co/Cr<sub>2</sub>O<sub>3</sub>-F composed with amorphous Cr<sub>2</sub>O<sub>3</sub> and functionalized with KIT-6 containing P123 and Co species based our group previous report. The optimal Co/Cr<sub>2</sub>O<sub>3</sub>-F-0.5 exhibits a high catalytic performance with TOF value of 111.1 min<sup>-1</sup>. Advanced characterizations reveal the synergistic effect of strong interaction at interface and improved wettability is responsible for the high catalytic performance.

Department of Chemical and Environmental Engineering, Hetao College, Bayan Nur 015000, China. E-mail: wufenglong1983@126.com; jinsonght@sina.com

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3ra07367j>



## 2. Experimental

### 2.1 Materials

Cobalt chloride hexahydrate ( $\text{CoCl}_2 \cdot 6\text{H}_2\text{O}$ ), ammonia borane ( $\text{NH}_3\text{BH}_3$ ), deuterium oxide ( $\text{D}_2\text{O}$ ), potassium iodide (KI), tetraethyl orthosilicate ( $\text{C}_8\text{H}_{20}\text{O}_4\text{Si}$ ) and sodium borohydride ( $\text{NaBH}_4$ ) were obtained from Aladdin. Chromium(III) nitrate nonahydrate ( $\text{Cr}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}$ ) was obtained from Macklin. Isopropyl alcohol ( $\text{C}_3\text{H}_8\text{O}$ ) was purchased from Tianjin Yongda Chemical Reagent Co. Ltd, poly(ethylene glycol)-*block*-poly(propylene glycol)-*block*-poly(ethylene glycol) was obtained from Sigma-Aldrich. Potassium dichromate ( $\text{K}_2\text{Cr}_2\text{O}_7$ ) were obtained from Sinopharm Chemical Reagent Co., Ltd.

### 2.2 Synthesis and photocatalytic $\text{H}_2$ production

Preparation of  $\text{Cr}_2\text{O}_3\text{-F-0.5}$ : KIT-6-F was firstly synthesized according to reported literature with minor modification.<sup>34</sup> We didn't calcine the sample to maintain the p123 in pore and on the surface of KIT-6. Next, a 0.5 g KIT-6-F and 0.2 g  $\text{Cr}(\text{NO}_3)_3$  were ground and transferred into a Teflon-lined stainless steel and maintained at 240 °C for 3.5 h. Meanwhile, we prepared five other samples denoted as  $\text{Cr}_2\text{O}_3\text{-F-X}$  (X represents the quality of KIT-6-F). The KIT-6-E was prepared by calcination KIT-6-F at 550 °C for 3 h. The  $\text{Cr}_2\text{O}_3\text{-E-0.5}$  was synthesized by KIT-6-E with same procedure as  $\text{Cr}_2\text{O}_3\text{-F-0.5}$  for comparison.

Preparation of  $\text{Co/Cr}_2\text{O}_3\text{-F-0.5}$  and catalytic  $\text{H}_2$  production: 16.0 mg  $\text{Cr}_2\text{O}_3\text{-F-0.5}$  was dispersed in containing 0.034 mmol  $\text{CoCl}_2 \cdot 6\text{H}_2\text{O}$  aqueous solution (0.9 mL) for in reactor 1 h. Next, 0.068 mmol  $\text{NaBH}_4$  acted as reduction and 1.71 mmol  $\text{NH}_3\text{BH}_3$  were dissolved in 1.5 mL  $\text{H}_2\text{O}$  and was injected into the reactor. Meanwhile, the  $\text{H}_2$  generated under visible light irradiation and in the dark. Five other samples including  $\text{Co/Cr}_2\text{O}_3\text{-F-0.1}$ ,  $\text{Co/Cr}_2\text{O}_3\text{-F-0.3}$ ,  $\text{Co/Cr}_2\text{O}_3\text{-E-0.5}$ ,  $\text{Co/KIT-6-F}$  and  $\text{Co/KIT-6-E}$  were prepared by same method.

### 2.3 Catalyst characterization

Powder X-ray diffraction (PXRD) on D8 Advance with  $\text{Cu-K}\alpha$  radiation was employed to obtain crystalline structures and component of samples. Transmission electron microscopy (TEM, JEM-2100F) were used to observe the morphologies of samples. X-ray photoelectron spectroscopy (XPS) was conducted on a Thermo Scientific K-Alpha with pass energies = 50 eV and the calibrated using the C 1s peak at 284.8 eV was reference. PerkinElmer Lambda 750 was employed to collect UV-vis spectra of sample. Contact angle measurements were carried out on Dataphysics OCA40. TriStar II Plus 3.03 was used to measure the surface area of samples. The transient photocurrent and electrochemical impedance spectroscopy (EIS) were conducted on an electrochemical station (CHI600E) in 0.5 M  $\text{Na}_2\text{SO}_4$  electrolyte. Fourier transform infrared (FTIR) was performed on FTIR-7600 spectrometer.

## 3. Results and discussion

### 3.1 Chemical structure analysis

As described in Fig. 1a, the catalyst  $\text{Co/Cr}_2\text{O}_3\text{-F-0.5}$  was prepared by two-step method. Firstly,  $\text{Cr}_2\text{O}_3\text{-F-0.5}$  was obtained by

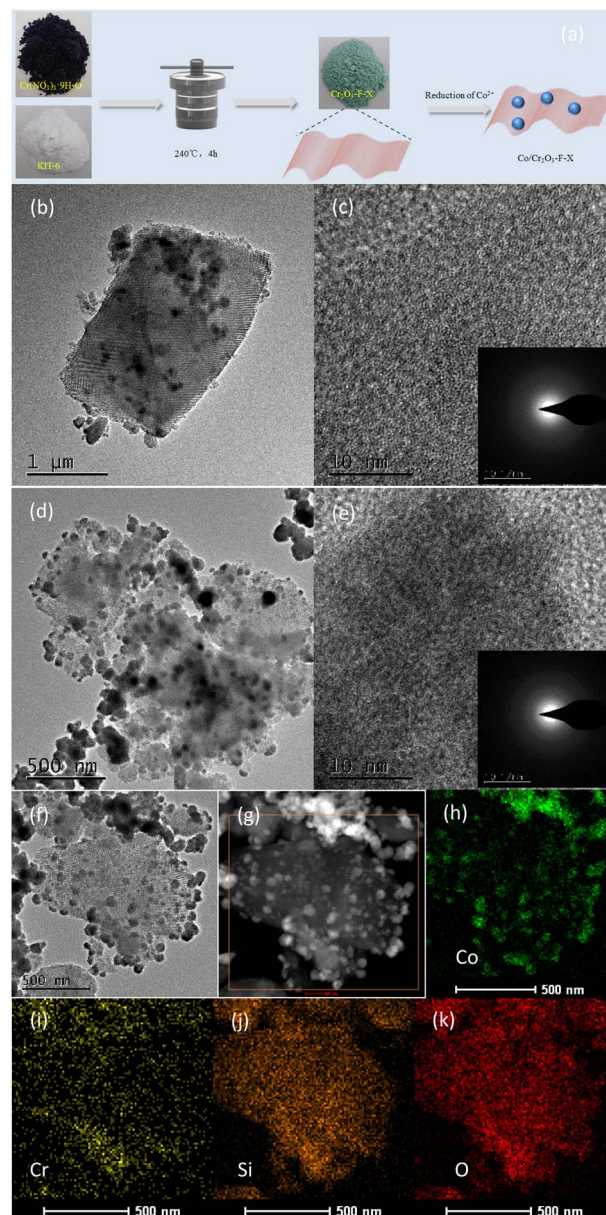


Fig. 1 (a) The illustration preparation process of  $\text{Co/Cr}_2\text{O}_3\text{-F-0.5}$ , (b and c) TEM images of  $\text{Cr}_2\text{O}_3\text{-F-0.5}$  with different magnifications, (d–k) TEM images of  $\text{Co/Cr}_2\text{O}_3\text{-F-0.5}$  with different magnifications, and the corresponding dark field elemental mappings.

solvent-free thermal method. TEM image in Fig. 1b, S1a and S1b† shows the compound inherits the morphology of KIT-6. However, no long range ordered structure can be observed from HRTEM image, further confirming the amorphous nature of  $\text{Cr}_2\text{O}_3\text{-F-0.5}$  (Fig. 1c). Moreover, the SAED of  $\text{Cr}_2\text{O}_3\text{-F-0.5}$  (inset in Fig. 1c) demonstrates rings composed of diffraction spots, further verifying the amorphous feature of  $\text{Cr}_2\text{O}_3\text{-F-0.5}$ . XRD pattern displays a broad peak indexed to KIT-6,<sup>35</sup> and no characteristic peak assigned to  $\text{Cr}_2\text{O}_3$  was clearly observed suggesting the sample is composed with KIT-6-F and amorphous  $\text{Cr}_2\text{O}_3$  (Fig. 2). Additionally, samples including KIT-6-F,  $\text{Cr}_2\text{O}_3\text{-F-0.1}$ ,  $\text{Cr}_2\text{O}_3\text{-F-0.3}$ , and  $\text{Cr}_2\text{O}_3\text{-F-0.6}$  were also tested to further confirm the amorphous nature of support (Fig. 2). The result



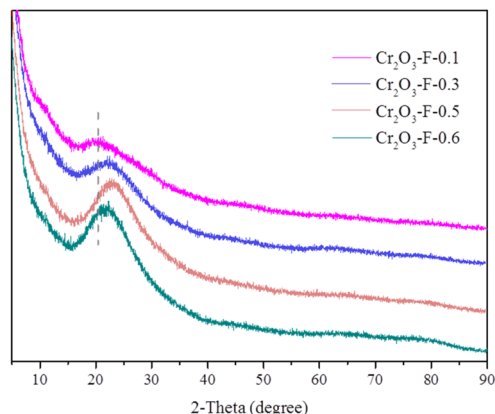


Fig. 2 XRD patterns of samples.

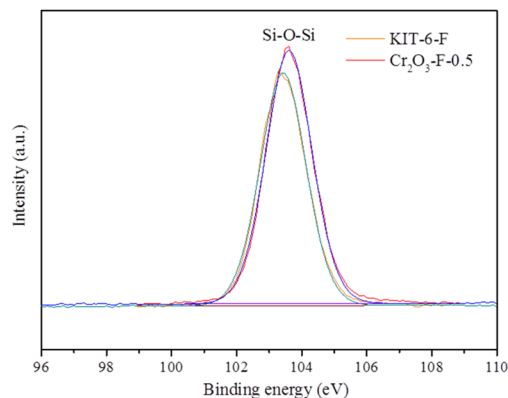


Fig. 3 XPS spectra of Si 2p in  $\text{Cr}_2\text{O}_3\text{-F-0.5}$  and KIT-6-F.

shows the compound sample remains amorphous after adjusting the quality of KIT-6-F. Moreover, a closer look at the abroad peaks in the compound shifts to big larger  $2\theta$  angle with increasing KIT-6-F, suggesting the strong electronic interaction between KIT-6-F and  $\text{Cr}_2\text{O}_3$ . Similar phenomenon has been observed in metal alloys due to changed electronic structure.<sup>36</sup> Additionally, the image and structure of  $\text{Cr}_2\text{O}_3\text{-E-0.5}$  also be tested for comparison. As shown in Fig. S2,<sup>†</sup>  $\text{Cr}_2\text{O}_3\text{-E-0.5}$  displays the same morphology as KIT-6 and  $\text{Cr}_2\text{O}_3\text{-F-0.5}$ . XRD pattern shows an amorphous nature of  $\text{Cr}_2\text{O}_3\text{-E-0.5}$  which is similar to the  $\text{Cr}_2\text{O}_3\text{-F-0.5}$  (Fig. S3<sup>†</sup>). Therefore, the introduction of P123 cannot significantly affect the crystallinity of support. After loading Co species, TEM images from Fig. 1d and S4<sup>†</sup> show Co species are formed on the surface of  $\text{Cr}_2\text{O}_3\text{-F-0.5}$ . The long-range order also can't be observed in HRTEM image of Co/ $\text{Cr}_2\text{O}_3\text{-F-0.5}$  in Fig. 1e, indicating the catalyst is composed of amorphous component. The SAED of Co/ $\text{Cr}_2\text{O}_3\text{-F-0.5}$  (inset in Fig. 1e) further confirms the amorphous feature of catalyst. Additionally, the element mapping (Fig. 1f-k) and EDX further the Co species has supported on the surface of  $\text{Cr}_2\text{O}_3\text{-F-0.5}$  (Fig. S5<sup>†</sup>). No obvious sharp peak assigned to Co is observed in XRD pattern of Co/ $\text{Cr}_2\text{O}_3\text{-F-0.5}$  (Fig. S6<sup>†</sup>), suggesting the formation of amorphous Co species which is consistent with previous reports.<sup>37</sup> Additionally, the broad peak around  $45^\circ$  assigned to Co can further confirm the existence of amorphous Co.<sup>38</sup> BET surface area of  $\text{Cr}_2\text{O}_3\text{-F-0.5}$  was calculated to be  $246.2512 \text{ m}^2 \text{ g}^{-1}$  which is smaller than Co/ $\text{Cr}_2\text{O}_3\text{-F-0.5}$  ( $296.8048 \text{ m}^2 \text{ g}^{-1}$ ) (Fig. S7 and S8<sup>†</sup>). The result suggests Co species mainly disperse on the surface of  $\text{Cr}_2\text{O}_3\text{-F-0.5}$  rather than channel of KIT-6 maybe due to the interaction between  $\text{Co}^{2+}$  and amorphous  $\text{Cr}_2\text{O}_3$ .

XPS was employed to confirm the component  $\text{Cr}_2\text{O}_3\text{-F-0.5}$  and complete XPS spectra for KIT-6-F for comparison. The full spectra display Si and O signal suggesting the coexisting of two elements in KIT-6-F. In addition to the aforementioned elemental signals, a faint Cr signal is also present in  $\text{Cr}_2\text{O}_3\text{-F-0.5}$  (Fig. S9<sup>†</sup>), suggesting the compound is composed of Si, O and Cr elements. As shown in Fig. 3, in the high resolution XPS spectrum of Si 2p, a peak located at 103.5 eV assigns to the Si-O-Si band for KIT-6-F and  $\text{Cr}_2\text{O}_3\text{-F-0.5}$ .<sup>39</sup> Notably, high resolution XPS

spectrum of Si 2p in  $\text{Cr}_2\text{O}_3\text{-F-0.5}$  shifts to high binding energy compared with KIT-6-F. Similar phenomenon is observed in O 1s, suggesting the strong interaction between  $\text{Cr}_2\text{O}_3$  and KIT-6-F (Fig. S10<sup>†</sup>). Additionally, high resolution XPS spectrum of Si in KIT-6-E and  $\text{Cr}_2\text{O}_3\text{-E-0.5}$  also is collected to the effect of P123 on interaction between  $\text{Cr}_2\text{O}_3$  and KIT-6. Compared to KIT-6-E, the Si 2p spectra in  $\text{Cr}_2\text{O}_3\text{-E-0.5}$  undergo a shift to lower binding energy (Fig. S11<sup>†</sup>). This phenomenon is different from  $\text{Cr}_2\text{O}_3\text{-F-0.5}$  due to the absence of P123.

FTIR spectra of KIT-6-F and  $\text{Cr}_2\text{O}_3\text{-F-0.5}$  were collected to investigate the structure of samples and interaction. As shown in Fig. 4, the bands in two samples at around 1635, 1081, 960, 799 and  $464 \text{ cm}^{-1}$  correspond to absorbed water, symmetric stretching vibrations of Si-O-Si, asymmetric stretching vibrations of Si-O-Si, and bending vibrations of Si-O-Si, respectively.<sup>40,41</sup> Notably, compared with pristine KIT-6-F, the band at  $1635$  and  $464 \text{ cm}^{-1}$  in compound are red-shifted, indicating the strong interaction between pristine KIT-6-F and  $\text{Cr}_2\text{O}_3$ , which is facilitated to regulate electron density of catalyst and obtain high performance.<sup>42</sup> Combined with the above characterization result,  $\text{Cr}_2\text{O}_3\text{-F-0.5}$  strong interaction between amorphous  $\text{Cr}_2\text{O}_3$  and KIT-6-F had been successfully synthesized. Additionally, The IR spectra of KIT-6-F were collected after five months (Fig. S12<sup>†</sup>). The result shows no

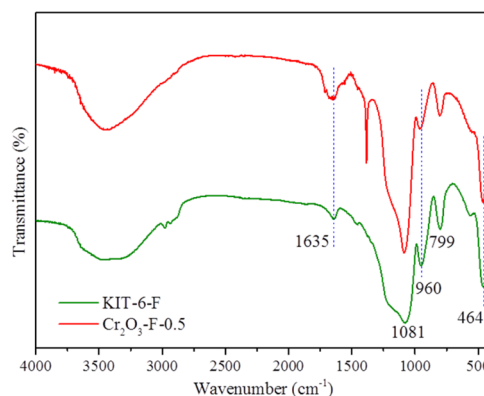


Fig. 4 IR spectra of  $\text{Cr}_2\text{O}_3\text{-F-0.5}$  and KIT-6-F.





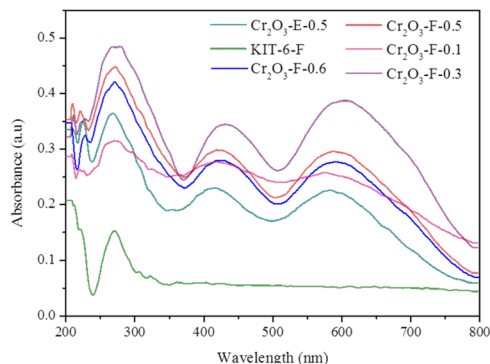


Fig. 5 UV-vis spectra of samples.

obvious change in characteristic peak is observed, suggesting reserved P123 on the surface of KIT-6 does not leach out.

UV-vis spectra were conducted to investigate the optical characterization of samples. As shown in Fig. 5, KIT-6-F is not capable of absorbing visible light while after coupling with  $\text{Cr}_2\text{O}_3$ , visible light absorption capacity is significantly improved and exhibits two absorbing peaks which is similar that of  $\text{Cr}_2\text{O}_3$ . Absorption strength is increasing with decreasing content of KIT-6-F because large quantities of KIT-6-F can form the light-shield effect and  $\text{Cr}_2\text{O}_3$ -F-0.3 has the strongest visible light reaction absorption. Notably,  $\text{Cr}_2\text{O}_3$ -F-0.1 doesn't show the best visible light response. This result may be due to too few KIT-6-F not beneficial to the formation of  $\text{Cr}_2\text{O}_3$ . Additionally, compared with  $\text{Cr}_2\text{O}_3$ -F-0.5, the  $\text{Cr}_2\text{O}_3$ -E-0.5 prepared by calcined KIT-6-F displays weak absorption of visible light, indicating the reserved p123 can strengthen the interaction between KIT-6-F and  $\text{Cr}_2\text{O}_3$ .

Separation efficiency of photogenerated electrons and holes has important influence in catalytic performance of catalyst. Transient photocurrent density was conducted to test the effect of reserved P123 on photogenerated carrier separation efficiency of compound.  $\text{Cr}_2\text{O}_3$ -E-0.5 also was test for comparison. As shown in Fig. 6a, the photogenerative carrier of the  $\text{Cr}_2\text{O}_3$ -E-0.5 can be effectively separated under visible light irradiation. In contrast,  $\text{Cr}_2\text{O}_3$ -F-0.5 exhibits stronger signal, revealing that  $\text{Cr}_2\text{O}_3$ -F-0.5 is benefit to carrier separation and transfer due to the strong interaction between KIT-6 and  $\text{Cr}_2\text{O}_3$  with assistance of P123. EIS was performed to confirm the effect of different structure of samples on electron transition. As shown in Fig. 6b,

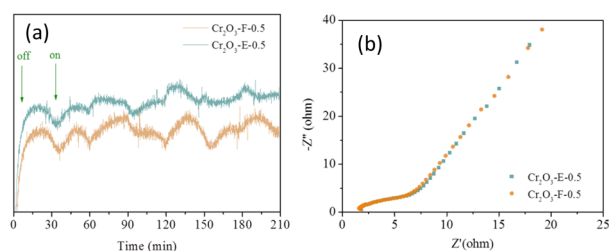


Fig. 6 (a) Profiles of time versus transient photocurrent density of two supports, (b) EIS Nyquist plots of samples.

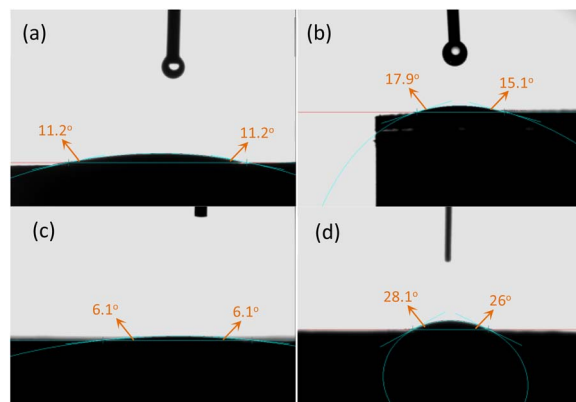


Fig. 7 Water contact angle measurements for (a)  $\text{Cr}_2\text{O}_3$ -F-0.5, (b)  $\text{Cr}_2\text{O}_3$ -E-0.5, (c)  $\text{Co}/\text{Cr}_2\text{O}_3$ -F-0.5 and (d)  $\text{Co}/\text{Cr}_2\text{O}_3$ -E-0.5.

$\text{Cr}_2\text{O}_3$ -F-0.5 shows a slightly smaller arc radius, suggesting relatively small resistance to electron transport.

To investigate the effect of reserved P123 on wettability of support, contact angle measurements were conducted for  $\text{Cr}_2\text{O}_3$ -F-0.5,  $\text{Cr}_2\text{O}_3$ -E-0.5,  $\text{Co}/\text{Cr}_2\text{O}_3$ -F-0.5 and  $\text{Co}/\text{Cr}_2\text{O}_3$ -E-0.5. Generally speaking, the lower the contact angle is liable to better  $\text{H}_2\text{O}$  adsorption. As illustrated in Fig. 7, the  $\text{Cr}_2\text{O}_3$ -E-0.5 shows the water-droplet contact angle of  $17.9^\circ$  while contact angles of water droplet on the surface of the  $\text{Cr}_2\text{O}_3$ -F-0.5 decrease values with  $11.2^\circ$ , confirming reserved P123 can enhance the wettability of support and favour the charge transfer and accelerate the rate of  $\text{NH}_3\text{BH}_3$  hydrolysis. The contact angles of water droplet on surface of  $\text{Co}/\text{Cr}_2\text{O}_3$ -E-0.5 ( $28.1^\circ$ ) is larger than  $\text{Cr}_2\text{O}_3$ -E-0.5. Conversely, the contact angles of water droplet on surface of  $\text{Co}/\text{Cr}_2\text{O}_3$ -F-0.5 ( $6.1^\circ$ ) is smaller than  $\text{Cr}_2\text{O}_3$ -F-0.5. The result suggests water can easily spread on the surface of  $\text{Co}/\text{Cr}_2\text{O}_3$ -F-0.5, leading to an increased  $\text{H}_2$  evolution rate.

### 3.2 Photocatalytic performance

The photocatalytic activity of  $\text{Co}/\text{Cr}_2\text{O}_3$ -F-0.5 was tested in a reactor under visible light irradiation. Additionally, control experiments including  $\text{Co}/\text{KIT-6-F}$ ,  $\text{Co}/\text{Cr}_2\text{O}_3$ -F-0.1,  $\text{Co}/\text{Cr}_2\text{O}_3$ -F-0.3,  $\text{Co}/\text{Cr}_2\text{O}_3$ -F-0.5,  $\text{Co}/\text{Cr}_2\text{O}_3$ -F-0.6,  $\text{Co}/\text{Cr}_2\text{O}_3$ -E-0.5 and  $\text{Co}/\text{KIT-6-E}$  were also conducted to reveal the origin of activity of catalyst. As shown in Fig. 8, both  $\text{Co}/\text{KIT-6-F}$  and  $\text{Co}/\text{KIT-6-E}$  exhibits similar activity in dark at same condition (Fig. 8a and b). Importantly, the activity of two catalysts is further boosted under visible irradiation (Fig. 8c and d). The enhanced catalytic performance is mainly attributed to the electronic structure changed induced by interband electron transfer of Co. In sharp contrast, the activity of  $\text{Co}/\text{Cr}_2\text{O}_3$ -F-0.5 exhibits greatly enhanced under visible irradiation than that of  $\text{Co}/\text{KIT-6-F}$ , while slightly boosted in dark. The TOF value of  $\text{Co}/\text{Cr}_2\text{O}_3$ -F-0.5 is  $111.1 \text{ min}^{-1}$  which is much higher than that of some tested non-precious metal based catalysts (Table 1). The enhanced performance is primarily attributed to the following aspects: firstly, introduction of  $\text{Cr}_2\text{O}_3$  with high visible light utilization ratio induces the generation of photogenerative



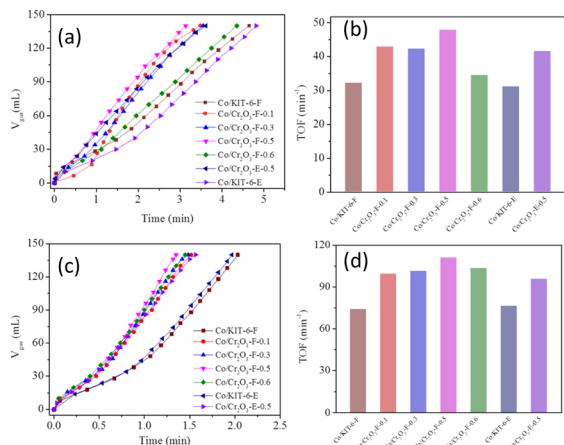


Fig. 8 Plots of time versus volume of H<sub>2</sub> evolution from NH<sub>3</sub>BH<sub>3</sub> over Co-based catalysts (a) in dark, (b) corresponding TOF value (c) under visible light irradiation, (d) corresponding TOF value.

carriers to provide a greater drive for reaction progression. Secondly, the electron-deficiency degree of Co nanosheets is improved under visible irradiation, resulting in greatly decreased H<sub>2</sub>O activation and dissociation energy barrier.<sup>29</sup> Thirdly, the increased NH<sub>3</sub>BH<sub>3</sub> hydrolysis rate over Co/Cr<sub>2</sub>O<sub>3</sub>-E-0.5 under visible irradiation further conform the effect of Cr<sub>2</sub>O<sub>3</sub> on activity of catalyst. Notably, the activity of Co/Cr<sub>2</sub>O<sub>3</sub>-E-0.5 with TOF 95.7 min<sup>-1</sup> is lower than Co/Cr<sub>2</sub>O<sub>3</sub>-F-0.5. Combined with the UV-vis, EIS, transient photocurrent density and water contact angle measurements experimental result, the reserved P123 on surface of KIT-6 not only construct strong interaction among multiple interfaces but also improve catalyst wettability, which is benefit to adsorption of reactant molecules and carrier transfer and accelerate the NH<sub>3</sub>BH<sub>3</sub> hydrolysis rate. Additionally, we added a control experiment over Co supported on Cr<sub>2</sub>O<sub>3</sub>-F-0.5-M (physically mixed KIT-6-F and Cr<sub>2</sub>O<sub>3</sub>) to provide evidence for the effect of strong interaction between KIT-6-F and Cr<sub>2</sub>O<sub>3</sub> on Co-based catalytic activity. As expected, the performance of Co/Cr<sub>2</sub>O<sub>3</sub>-F-0.5-M with TOF of 76.9 min<sup>-1</sup> is greatly reduced in comparison to Co/Cr<sub>2</sub>O<sub>3</sub>-F-0.5 (Fig. S13†). Therefore, the synergistic effect of high visible light utilization, strong

interaction between KIT-6-F and Cr<sub>2</sub>O<sub>3</sub> and improved wettability leads to a significant enhanced catalyst performance under visible irradiation.

In order to reveal the influence of interface effect on catalyst performance, the control experiments were performed based on Co/Cr<sub>2</sub>O<sub>3</sub>-F-0.1, Co/Cr<sub>2</sub>O<sub>3</sub>-F-0.3, Co/Cr<sub>2</sub>O<sub>3</sub>-F-0.5, Co/Cr<sub>2</sub>O<sub>3</sub>-F-0.6. It can be clearly observed that the introduction of amorphous Cr<sub>2</sub>O<sub>3</sub> in support can slightly boost the activity of Co-based catalyst in dark (Fig. 8c). However, the activity of catalyst containing KIT-6-F can significantly improve under visible irradiation. Moreover, the activity enhances with increased KIT-6-F mass and the catalyst Co/Cr<sub>2</sub>O<sub>3</sub>-F-0.5 exhibits highest performance. The activity decreases when the mass of KIT-6-F in support is continued to increase due to light-shield effect.

Photogenerated carriers can not only tune the electronic structure of catalyst but also induce the generation of radical intermediates such as hydroxyl radicals (<sup>•</sup>OH), which have significantly effect on the performance of catalyst in light induced reaction. Therefore, we investigated the influence of <sup>•</sup>OH to the performance of Co/Cr<sub>2</sub>O<sub>3</sub>-F-0.5 using trapping experiment and EPR characterization. In capture experiment, electrons, holes and <sup>•</sup>OH was captured by K<sub>2</sub>Cr<sub>2</sub>O<sub>7</sub> (100 μM), KI(100 μM) and 2-propanol (IPA) (100 μL), respectively.<sup>47</sup> The result was shown in Fig. 9a and b, the adding of sacrificial agents in reaction system can decrease the hydrolysis rate of NH<sub>3</sub>BH<sub>3</sub>, suggesting the photogenerated carriers and radical intermediates can boost the activity of Co/Cr<sub>2</sub>O<sub>3</sub>-F-0.5. It is worth noting that the effect of photogenerated carriers and radical intermediates on enhanced activity is different based on different catalyst. ESR measurements was conducted to confirm the existing of <sup>•</sup>OH and superoxide anions (<sup>•</sup>O<sub>2</sub><sup>-</sup>) originated from the reaction of dissolved O<sub>2</sub> and photogenerated electron was also measured which can improve the rate of NH<sub>3</sub>BH<sub>3</sub> hydrolysis.<sup>46</sup> As shown in Fig. 9c, no characteristic signal of <sup>•</sup>OH is observed in the dark based on Cr<sub>2</sub>O<sub>3</sub>-F-0.5, but the signal with 1 : 2 : 2 : 1 strength appears under irradiation. The same phenomenon is observed in <sup>•</sup>O<sub>2</sub><sup>-</sup> detection (Fig. 9d). These results further confirm the existing of <sup>•</sup>OH and <sup>•</sup>O<sub>2</sub><sup>-</sup> under light irradiation.

Table 1 Activities of catalysts in the H<sub>2</sub> evolution from NH<sub>3</sub>BH<sub>3</sub>

Catalyst	TOF (min <sup>-1</sup> )	References	Temperature (K)	Irradiation
Co/Cr <sub>2</sub> O <sub>3</sub> -F-0.3	101.4	This work	298	With
Co/Cr <sub>2</sub> O <sub>3</sub> -F-0.5	111.1	This work	298	With
Co/Cr <sub>2</sub> O <sub>3</sub> -F-0.6	103.4	This work	298	With
Co/Cr <sub>2</sub> O <sub>3</sub>	106.8	29	298	With
NiCo-NC	35.2	43	298	Without
Co <sub>3</sub> O <sub>4</sub> -SnO <sub>2</sub>	17.6	44	298	Without
Ni/Ni <sub>2</sub> P	68.3	4	298	Without
Co@N-C-700	5.6	23	298	With
NiCu/CNS	30.6	22	298	With
NiCu/SiO <sub>2</sub>	25.3	45	298	Without
Cu <sub>0.5</sub> Co <sub>0.5</sub> O-rGO	81.7	24	room	Without
Cu/MIL-101	28.22	46	298	With

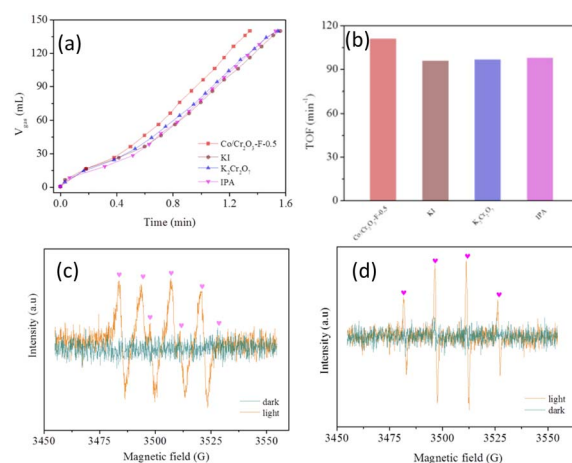


Fig. 9 (a) and (b) Role of hydroxyl radicals and superoxide anions in NH<sub>3</sub>BH<sub>3</sub> hydrolysis under light irradiation. (c) and (d) DMPO ESR spin-labeling for <sup>•</sup>O<sub>2</sub><sup>-</sup> and <sup>•</sup>OH.



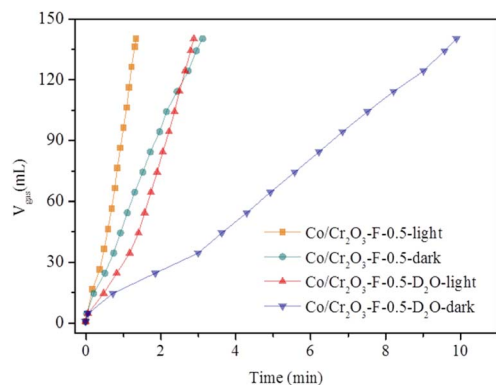


Fig. 10 Plots of time versus volume of hydrogen evolution from  $\text{NH}_3\text{BH}_3$  in  $\text{H}_2\text{O}$  or  $\text{D}_2\text{O}$  over  $\text{Co/Cr}_2\text{O}_3\text{-F-0.5}$  under visible light irradiation and in dark.

The cleavage of O–H bond in  $\text{H}_2\text{O}$  molecules is the rate-determining step in  $\text{NH}_3\text{BH}_3$  hydrolysis.<sup>48,49</sup> To further confirm the conclusion, the kinetic isotope effect (KIE: KH/KD) is conducted. As shown in Fig. 10 the  $\text{H}_2$  evolution rates greatly decreases using  $\text{D}_2\text{O}$  to replace  $\text{H}_2\text{O}$  both light irradiation and in dark. The value of KIE is 2.89 in darkness and is 2.13 under light irradiation. This result indicates the cleavage of O–H bond is the rate-determining step over  $\text{Co/Cr}_2\text{O}_3\text{-F-0.5}$  toward the hydrolysis of  $\text{NH}_3\text{BH}_3$ .

According to characterization, experimental results and previous report, we propose a possible mechanism for  $\text{NH}_3\text{BH}_3$  hydrolysis induced by visible light. Firstly, Co species and  $\text{Cr}_2\text{O}_3\text{-F-0.5}$  absorbs visible light. Secondly, photoinduced electrons and holes are generated and transfer to the surface of Co species and  $\text{Cr}_2\text{O}_3\text{-F-0.5}$ . Meanwhile, photoinduced electrons transfer from active species to support then  $\cdot\text{OH}$  and  $\cdot\text{O}_2^-$  are formed in this process. Thirdly, the B–H bond in  $\text{NH}_3\text{BH}_3$  and O–H bond in  $\text{H}_2\text{O}$  are broken and  $\text{H}_2$  is generated.  $\cdot\text{OH}$  and  $\cdot\text{O}_2^-$  can accelerate the breaking of two kinds of bonds. Notably, the strong interaction among multicomponent and enhanced wettability can favor the transition of photoinduced carriers,  $\cdot\text{OH}$  and  $\cdot\text{O}_2^-$  and then improve the production rate of  $\text{H}_2$ .

## 4. Conclusions

We synthesized a hydrophilic support by simple solvent-free thermal method. The compound works as amazing support for Co species. The optimal  $\text{Co/Cr}_2\text{O}_3\text{-F-0.5}$  exhibits a highest catalytic performance for hydrogen production from  $\text{NH}_3\text{BH}_3$  with TOF value of  $111.1 \text{ min}^{-1}$ . XRD, IR and XPS results indicate strong interaction between KIT-6-F and  $\text{Cr}_2\text{O}_3\text{-F}$ . Contact angle measurement verifies  $\text{Cr}_2\text{O}_3\text{-F-0.5}$  has improved wettability. The synergistic effect of strong interaction and improved wettability induces high catalytic performance of  $\text{Co/Cr}_2\text{O}_3\text{-F-0.5}$ .

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The authors gratefully acknowledge the financial support from the National Natural Science Foundation of China (52161038), Young Talents of Science and Technology in Universities of Inner Mongolia Autonomous Region (NJYT23033), Natural Science Foundation of Inner Mongolia Autonomous Region (2022MS05012), and the Talent Development Fund Project of Inner Mongolia Autonomous Region ([2022]-110).

## References

- N. Dubouis, A. Serva, R. Berthin, G. Jeanmairet, B. Porcheron, E. Salager, M. Salanne and A. Grimaud, *Nat. Catal.*, 2020, **3**, 656–663.
- J. He, Z. Huang, W. Che, X. Xiao, Z. Yao, Z. Liang, L. Zhan, L. Lv, J. Qi, X. Fan and L. Chen, *Chem. Eng. J.*, 2022, **431**, 133697.
- M. K. Sarmah, T. P. Singh, P. Kalita and A. Dewan, *RSC Adv.*, 2023, **13**, 25253–25275.
- Y. Lin, L. Yang, H. Jiang, Y. Zhang, D. Cao, C. Wu, G. Zhang, J. Jiang and L. Song, *J. Phys. Chem. Lett.*, 2019, **10**, 1048–1054.
- Y. Meng, Q. Sun, T. Zhang, J. Zhang, Z. Dong, Y. Ma, Z. Wu, H. Wang, X. Bao, Q. Sun and J. Yu, *J. Am. Chem. Soc.*, 2023, **145**, 5486–5495.
- L. Wei, Y. Lu, R. Lua and Y. Cui, *RSC Adv.*, 2023, **13**, 7614–7620.
- C. Wang, J. Tuninetti, Z. Wang, C. Zhang, R. Ciganda, L. Salmon, S. Moya, J. Ruiz and D. Astruc, *J. Am. Chem. Soc.*, 2017, **139**, 11610–11615.
- C. D. Mboyi, D. Poinot, J. Roger, K. Fajerwerger, M. L. Kahn and J.-C. Hierro, *Small*, 2021, **17**, 2102759.
- H. Wu, Y. Chen, Y. Fan, X. Lu, L. Li, B. Liu, B. Li and S. Lu, *Int. J. Hydrogen Energy*, 2020, **45**, 30325–30340.
- S. Guan, Y. Liu, H. Zhang, R. Shen, H. Wen, N. Kang, J. Zhou, B. Liu, Y. Fan, J. Jiang and B. Li, *Adv. Sci.*, 2023, **10**, 2300726.
- Y. Ren, J. Duan, X. Liu, L. Bian, Y. Fan and B. Liu, *Energy Fuels*, 2021, **35**, 16222–16231.
- S. Akbayrak and S. Özkaz, *J. Colloid Interface Sci.*, 2021, **596**, 100–107.
- L.-T. Guo, Y.-Y. Cai, J.-M. Ge, Y.-N. Zhang, L.-H. Gong, X.-H. Li, K.-X. Wang, Q.-Z. Ren, J. Su and J.-S. Chen, *ACS Catal.*, 2015, **5**, 388–392.
- W. Chen, G. Lv, J. Fu, H. Ren, J. Shen, J. Cao and X. Liu, *ACS Appl. Mater. Interfaces*, 2021, **13**, 50017–50026.
- B. Wang, L. Xiong, H. Hao, H. Cai, P. Gao, F. Liu, X. Yu, C. Wu and S. Yang, *J. Alloys Compd.*, 2020, **844**, 156253.
- J. Liao, Y. Wu, Y. Shao, Y. Feng, X. Zhang, W. Zhang, J. Li, M. Wu, H. Dong, Q. Liu and H. Li, *Chem. Eng. J.*, 2022, **449**, 137755.
- F. Qiu, X. Hao, W. Huang, Y. Wu, R. Chu, J. Yang, W. Fu, G. Ren, C. Xu and W. Bao, *RSC Adv.*, 2023, **13**, 632–637.
- L. Zhang, J. Ye, Y. Tu, Q. Wang, H. Pan, L. Wu, X. Zheng and J. Zhu, *Nano Res.*, 2022, **15**, 3034–3041.
- H. Yin, Y. Kuwahara, K. Mori and H. Yamashita, *J. Mater. Chem. A*, 2018, **6**, 10932–10938.



- 20 N. Kang, Q. Wang, R. Djeda, W. Wang, F. Fu, M. M. Moro, M. de los A. Ramirez, S. Moya, E. Coy, L. Salmon, J.-L. Pozzo and D. Astruc, *ACS Appl. Mater. Interfaces*, 2020, **12**, 53816–53826.
- 21 N. Kang, X. Wei, R. Shen, B. Li, E. G. Cal, S. Moya, L. Salmon, C. Wang, E. Coy, M. Berlande, J.-L. Pozzo and D. Astruc, *Appl. Catal., B*, 2023, **320**, 121957.
- 22 S. Zhang, M. Li, L. Li, F. Dushimimana, J. Zhao, S. Wang, J. Han, X. Zhu, X. Liu, Q. Ge and H. Wang, *ACS Catal.*, 2020, **10**, 14903–14915.
- 23 H. Wang, Y. Zhao, F. Cheng, Z. Tao and J. Chen, *Catal. Sci. Technol.*, 2016, **6**, 3443–3448.
- 24 H. Zheng, K. Feng, Y. Shang, Z. Kang, X. Sun and J. Zhong, *Inorg. Chem. Front.*, 2018, **5**, 1180–1187.
- 25 H. Zhang, X. Gu, P. Liu, J. Song, J. Cheng and H. Su, *J. Mater. Chem. A*, 2017, **5**, 2288–2296.
- 26 J. Song, X. Gu, Y. Cao and H. Zhang, *J. Mater. Chem. A*, 2019, **7**, 10543–10551.
- 27 H. Wu, M. Wu, B. Wang, X. Yong, Y. Liu, B. Li, B. Liu and S. Lu, *J. Energy Chem.*, 2020, **48**, 43–53.
- 28 Y. Chen, G. Mao, Y. Tang, H. Wu, G. Wang, L. Zhang and Q. Liu, *Chin. J. Catal.*, 2021, **42**, 225–234.
- 29 J. Song and F. Wu, *Nanoscale*, 2023, **15**, 16741–16751.
- 30 L. Wang and F.-S. Xiao, *ChemCatChem*, 2014, **6**, 3048–3052.
- 31 Y. Li and C. Zhao, *ACS Catal.*, 2017, **7**, 2535–2541.
- 32 C. Wang, L. Liu, H. Li, L. Wang and F.-S. Xiao, *Matter*, 2023, **6**, 2697–2710.
- 33 X. Zhang, Y. Zhao, X. Jia, Y. Zhao, L. Shang, Q. Wang, G. I. N. Waterhouse, L.-Z. Wu, C.-H. Tung and T. Zhang, *Adv. Energy Mater.*, 2018, **8**, 1702780.
- 34 K. Soni, B. S. Rana, A. K. Sinha, A. Bhaumik, M. Nandi, M. Kumar and G. M. Dhar, *Appl. Catal., B*, 2009, **90**, 55–63.
- 35 H. Al-shaikh, J. Lasri, J. G. Knight and S. T. Al-Goul, *Fuel*, 2022, **325**, 124962.
- 36 P. Liu, X. Gu, H. Zhang, J. Cheng, J. Song and H. Su, *Appl. Catal., B*, 2017, **204**, 497–504.
- 37 J. Song, F. Wu, H. Ma, Y. Liu, N. Song, J. Yu and Y. Wang, *ACS Appl. Energy Mater.*, 2021, **4**, 8377–8385.
- 38 J. Pang, S. Jin, J. Hou, G. Wang, K. Sun, Y. Zheng, H. Li, Y. Shen, X. Yang and L. Chen, *Sens. Actuators, B*, 2023, **374**, 132725.
- 39 Y. Ding, J. Wang, M. Liao, J. Li, L. Zhang, J. Guo and H. Wu, *Chem. Eng. J.*, 2021, **418**, 129470.
- 40 P. Han, T. Liu, X. Ji and S. Tang, *Chin. Chem. Lett.*, 2018, **29**, 1305–1309.
- 41 X. Zhou, H. Zhao, S. Liu, D. Ye, R. Qu, C. Zheng and X. Gao, *Appl. Surf. Sci.*, 2020, **525**, 146382.
- 42 P. Zhou, S.-X. Guo, L. Li, T. Ueda, Y. Nishiwaki, L. Huang, Z. Zhang and J. Zhang, *Angew. Chem., Int. Ed.*, 2023, **62**, e202214881.
- 43 L. Zhao, Q. Wei, L. Zhang, Y. Zhao and B. Zhang, *Renewable Energy*, 2021, **173**, 273–282.
- 44 H.-Z. Wang, Y.-X. Shao, Y.-F. Feng, Y.-J. Tan, Q.-Y. Liao, X.-D. Chen, X.-F. Zhang, Z.-H. Guo and H. Li, *Rare Met.*, 2023, **42**, 3013–3023.
- 45 K. Guo, Y. Ding, J. Luo, M. Gu and Z. Yu, *ACS Appl. Energy Mater.*, 2019, **2**, 5851–5861.
- 46 M. Wen, Y. Cui, Y. Kuwahara, K. Mori and H. Yamashita, *ACS Appl. Mater. Interfaces*, 2016, **8**, 21278–21284.
- 47 S. Jo, P. Verma, Y. Kuwahara, K. Mori, W. Choi and H. Yamashita, *J. Mater. Chem. A*, 2017, **5**, 21883–21892.
- 48 S. Zhou, Y. Yang, P. Yin, Z. Ren, L. Wang and M. Wei, *ACS Appl. Mater. Interfaces*, 2022, **14**, 5275–5286.
- 49 Z. Li, T. He, L. Liu, W. Chen, M. Zhang, G. Wu and P. Chen, *Chem. Sci.*, 2017, **8**, 781–788.

