


# Rare earth nanoalloys

Showcasing research from Professor Yaping Du's laboratory, Center for Rare Earth and Inorganic Functional Materials, Nankai University, Tianjin, China.

Laves phase  $\text{Ir}_2\text{Sm}$  intermetallic nanoparticles as a highly active electrocatalyst for acidic oxygen evolution reaction

Rare earth alloys are significant for fundamental explorations and promising for practical applications. Herein,  $\text{Ir}_2\text{Sm}$  nanoparticles were synthesized as acidic oxygen evolution reaction catalysts.  $\text{Ir}_2\text{Sm}$  alloy with ordered atomic arrangement is a new phase belonging to the C15 cubic  $\text{MgCu}_2$ -type in the Laves phase family. Alloying Sm with Ir atoms modulates the electronic nature of Ir, thereby enhancing the oxygen evolution reaction activity. This study provides a new perspective on the rational design and practical application of high-performance rare earth alloy catalysts.

As featured in:

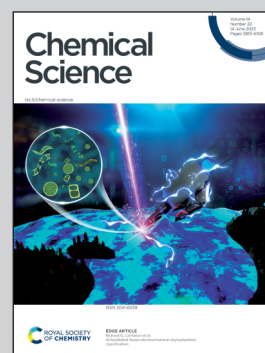

See Yaping Du *et al.*,  
*Chem. Sci.*, 2023, **14**, 5887.

Cite this: *Chem. Sci.*, 2023, 14, 5887

All publication charges for this article have been paid for by the Royal Society of Chemistry

# Laves phase Ir<sub>2</sub>Sm intermetallic nanoparticles as a highly active electrocatalyst for acidic oxygen evolution reaction†

Shuai Zhang,<sup>a</sup> Leilei Yin,<sup>a</sup> Qingqing Li,<sup>a</sup> Siyuan Wang,<sup>a</sup> Weihua Wang<sup>ID</sup><sup>b</sup> and Yaping Du<sup>ID</sup><sup>\*a</sup>

Rare earth (RE) intermetallic nanoparticles (NPs) are significant for fundamental explorations and promising for practical applications in electrocatalysis. However, they are difficult to synthesize because of the unusually low reduction potential and extremely high oxygen affinity of RE metal–oxygen bonds. Herein, intermetallic Ir<sub>2</sub>Sm NPs were firstly synthesized on graphene as a superior acidic oxygen evolution reaction (OER) catalyst. It was verified that intermetallic Ir<sub>2</sub>Sm is a new phase belonging to the C15 cubic MgCu<sub>2</sub> type in the Laves phase family. Meanwhile, intermetallic Ir<sub>2</sub>Sm NPs achieved a mass activity of 1.24 A mg<sub>Ir</sub><sup>-1</sup> at 1.53 V and stability of 120 h at 10 mA cm<sup>-2</sup> in 0.5 M H<sub>2</sub>SO<sub>4</sub> electrolyte, which corresponds to a 5.6-fold and 12-fold enhancement relative to Ir NPs. Experimental results together with density functional theory (DFT) calculations show that in the structurally ordered intermetallic Ir<sub>2</sub>Sm NPs, the alloying of Sm with Ir atoms modulates the electronic nature of Ir, thereby reducing the binding energy of the oxygen-based intermediate, resulting in faster kinetics and enhanced OER activity. This study provides a new perspective for the rational design and practical application of high-performance RE alloy catalysts.

Received 25th February 2023

Accepted 15th April 2023

DOI: 10.1039/d3sc01052j

rsc.li/chemical-science

## Introduction

In catalytic reactions, the electronic structure of the active sites plays a key role in the overall reactivity and selectivity of the catalysts. Alloying provides an effective strategy for modulating the electronic structure to improve the catalytic performance.<sup>1–3</sup> RE alloys can integrate the unique electronic structure of RE into materials, resulting in significant changes in the electronic structure of catalytic materials.<sup>4–7</sup> The unusually negative alloying energy and alloy formation enthalpy provide RE alloys with excellent stability under harsh conditions (strong acid or high-temperature environments).<sup>8,9</sup> In addition to the stable structure of RE alloys, lanthanide contraction makes it possible to precisely tailor the electronic structure of the active site.<sup>10–12</sup> The robust and tuneable catalytic properties of RE alloys make them one of the most promising advanced catalytic materials.<sup>13</sup> However, the synthesis of RE alloy NPs for practical applications is still hindered by many factors. For example, the RE elements

have an extremely low standard reduction potential (–2.30 V for Sm<sup>3+</sup>/Sm) and demand a strong reducing agent to be reduced to a metallic state; thus the traditional wet chemical synthesis route is not applicable.<sup>14</sup> In addition, RE elements show extremely high oxygen affinity, and the alloying process needs to be carried out in an inert atmosphere.<sup>15</sup> For the above reasons, the theoretical research and practical application of RE nano-alloys are severely limited.<sup>10,16,17</sup> Therefore, it is necessary to deepen the understanding of the intermetallic RE systems and explore their application directions.

Iridium-based materials are considered to have strong potential for use as OER catalysts in acidic media, but the problems of low mass activity and abundance hinder their wide application.<sup>18,19</sup> Alloying with transition metals addresses these critical issues in two ways. Firstly, alloying greatly changes the electronic structure of Ir, thereby optimizing the adsorption and desorption of the surface adsorbates. Secondly, the introduction of foreign atoms can also reduce the use of Ir metal and thus reduce the cost of the catalyst. However, due to the disordered arrangement of solid solution alloys, corrosion and dissolution would inevitably occur, which compromises the benefits of alloying. Therefore, the development of an improved Ir alloy catalyst to exhibit higher activity and durability under acidic operating conditions is urgently needed.<sup>20–24</sup> Theoretically, constructing an intermetallic with an ordered atomic arrangement can enhance the electrocatalytic activity and durability, and reduce the use of noble metals.<sup>25,26</sup> Alloys modify

<sup>a</sup>Tianjin Key Lab for Rare Earth Materials and Applications, Center for Rare Earth and Inorganic Functional Materials, Haihe Laboratory of Sustainable Chemical Transformations, Smart Sensing Interdisciplinary Science Center, School of Materials Science and Engineering, National Institute for Advanced Materials, Nankai University, Tianjin 300350, China

<sup>b</sup>College of Electronic Information and Optical Engineering, Nankai University, Tianjin 300350, China

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3sc01052j>



the electronic state of catalytically active elements through electronic effects, and the degree of modification depends largely on the nature and composition of the second metal.<sup>27</sup> RE elements have a unique electronic structure of  $[\text{Xe}]4f^{n-1}5d^{0-1}6s^2$  ( $n = 1-15$ ), which can provide an additional route for adjusting the electronic structure of catalytically active elements.<sup>28,29</sup> The electronic perturbation caused by RE doping in transition metals could optimize the valence band of transition metal-based materials.<sup>30-33</sup> Due to the difference in electronegativity, electron transfer occurs between Sm and adjacent Ir atoms, which can optimize the electronic structure of Ir. The outer electron shell arrangement of Sm atoms is  $4f^66s^2$ , which makes it possible to induce the 4f electron configuration to participate in the optimization and regulation of the Ir d-band center ( $\epsilon_d$ ) through alloying.

Herein, we synthesized a new phase of intermetallic  $\text{Ir}_2\text{Sm}$  NPs on graphene through a facile solid-state synthesis strategy. The structure of  $\text{Ir}_2\text{Sm}$  has been confirmed to be a cubic system belonging to the  $Fd\bar{3}m$  space group.<sup>34,35</sup> The synthesized catalyst exhibited enhanced acidic OER activity. To further improve the performance of the catalyst, we optimized the particle size of the intermetallic  $\text{Ir}_2\text{Sm}$  NPs. The  $\text{Ir}_2\text{Sm}$  NPs achieved a much lower OER overpotential of 275 mV at 10 mA  $\text{cm}^{-2}$ , better than those of the commercialized Ir/C benchmark (378 mV) and most documented Ir-based alloy catalytic materials. Meanwhile, intermetallic  $\text{Ir}_2\text{Sm}$  NPs with 1–2 atomic layers of  $\text{IrO}_x$  have robust stability, showing long-term stability with a current density of 10 mA  $\text{cm}^{-2}$  for more than 120 h. The alloying-induced electronic interaction between Sm and Ir tunes the  $\epsilon_d$  of the Ir in intermetallic  $\text{Ir}_2\text{Sm}$ , thereby accelerating the rate-determining step (RDS) of the OER and enhancing the OER activity.


## Results and discussion

In this study, sodium vapor was used to obtain intermetallic  $\text{Ir}_2\text{Sm}$  NPs supported on graphene. As shown in Scheme 1, a mixture of graphene,  $\text{H}_2\text{IrCl}_6 \cdot 6\text{H}_2\text{O}$ ,  $\text{SmCl}_3$ , and cyanamide was used as the precursor. After annealing treatment, the graphene-supported intermetallic  $\text{Ir}_2\text{Sm}$  NPs could be obtained by pickling and drying. Intermetallic  $\text{Ir}_2\text{Sm}$  NPs with high crystallinity (denoted as  $\text{Ir}_2\text{Sm-L/G}$ ) were obtained using an annealing

time of 6 h, which facilitated the determination of the crystal structure by XRD Rietveld refinement (Fig. 1a). The lattice parameters are summarized in Table S1.† Fig. 1b shows the unit cell structure, which indicates that  $\text{Ir}_2\text{Sm}$  belongs to the C15 cubic  $\text{MgCu}_2$ -type phase in the Laves phase family.

HAADF-STEM images show that the  $\text{Ir}_2\text{Sm-L/G}$  are dispersed on the graphene and exhibit a roughly spherical shape (Fig. 1c and d). Statistical analysis of 300 nanocrystals showed that  $\text{Ir}_2\text{Sm-L/G}$  have an average concentration size distribution of 26.4 nm (ESI, Fig. S1†). As shown in Fig. 1e, the spatial distances between the two atoms measured along two orthogonal directions are 0.439 and 0.268 nm, corresponding to the interplanar spacing of the (111) and (220) planes, respectively. The HAADF image was analyzed along the  $[\bar{1}12]$  zone axis of the intermetallic  $\text{Ir}_2\text{Sm}$  NPs. To confirm that the experimentally resolved atomic configuration is consistent with that of the cubic crystal system (space group:  $Fd\bar{3}m$ ), a HAADF image of  $[\bar{1}12]$  was simulated (Fig. 1g),<sup>36</sup> and the results show the same brightness pattern as Fig. 1f. Furthermore, elemental mapping tested by energy-dispersive X-ray spectroscopy (EDS) revealed that Ir and Sm elements are homogeneously distributed in individual intermetallic NPs (ESI, Fig. S2 and S3†). In previous work on intermetallic NPs, under acidic conditions, the non-noble metal elements on the surface were etched to form a noble metal surface layer with a thickness of 1–2 atomic layers. Benefiting from higher thermodynamic stability, the inner alloy will stabilize the noble metal elements on the surface layer, thereby increasing the stability of the catalyst.<sup>37</sup> There is a small amount of O atoms on the surface of the intermetallic  $\text{Ir}_2\text{Sm}$  NPs, which may be caused by the oxidation of Ir element on the NPs surface.

The atomic resolution HAADF-STEM (Fig. 2a) image of the  $\text{Ir}_2\text{Sm-L/G}$  shows that the  $\text{Ir}_2\text{Sm}$  NPs have an orderly atomic arrangement, and the nanopore structure existing on the NPs still shows the intermetallic structure of  $\text{Ir}_2\text{Sm}$  NPs, which indicates that the intermetallic NPs after pickling still maintained the intermetallic compound structure. The surface of the intermetallic NPs has only about 0.23–0.42 nm of amorphous structure (Fig. 2b), and the phase structure of the  $\text{Ir}_2\text{Sm}$  NPs is still well maintained. ICP measurement showed that the atomic ratio of Ir and Sm is about 2 : 1 (ESI, Table S2†). These results indicate that the alloy can exist stably under acidic conditions. Considering the presence of few oxygen atoms on the catalyst

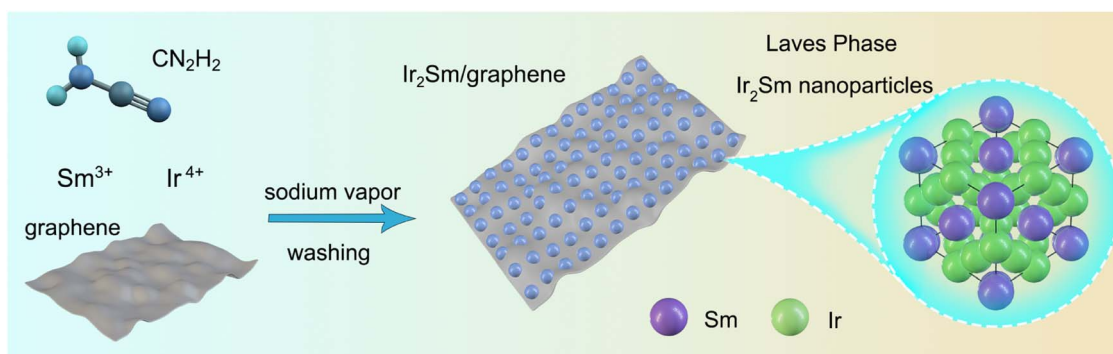

Scheme 1 Schematic illustration of the synthesis method for intermetallic  $\text{Ir}_2\text{Sm}$  NPs on graphene.



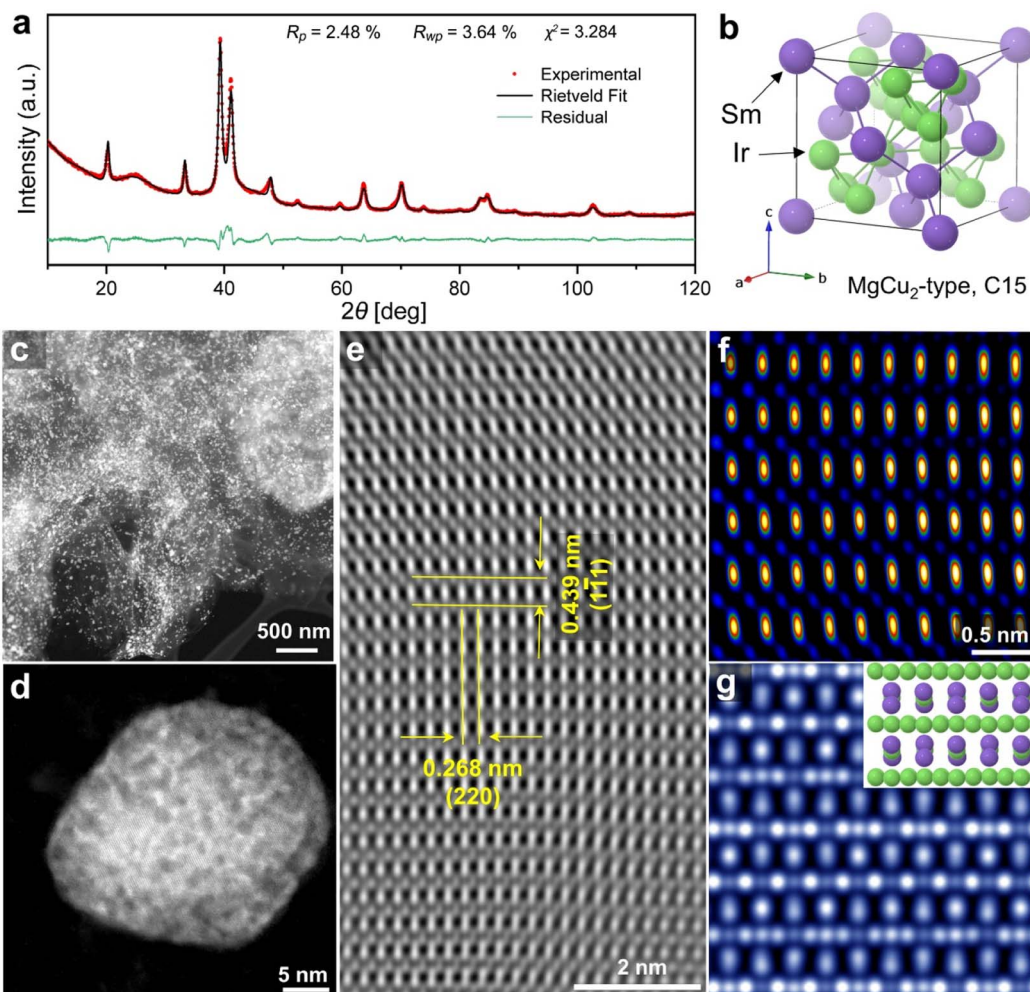


Fig. 1 Structural characterization of Ir<sub>2</sub>Sm-L/G. (a) XRD Rietveld refinement result, (b) the corresponding crystal structure, (c–e) aberration-corrected HAADF-STEM images at different magnifications, (f) HAADF image, and (g) simulated HAADF image. Inset is the atomic model of Ir<sub>2</sub>Sm, where green and blue spheres are Ir and Sm atoms, respectively.

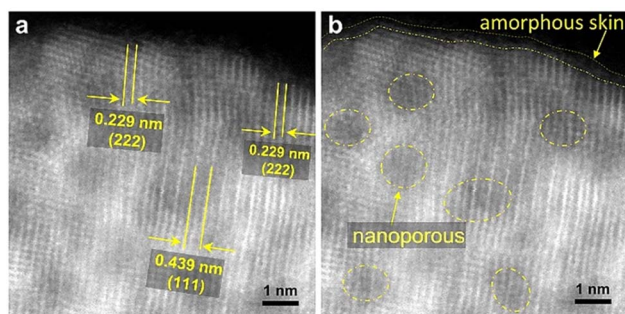


Fig. 2 HAADF-STEM images of Ir<sub>2</sub>Sm-L/G. (a) Crystal face information and (b) nanoporous and amorphous skin distribution.

surface (ESI, Fig. S2c†), the amorphous surface layer of the NPs consists of Ir and O atoms. To explore the reason for the formation of porous structures in the intermetallic NPs, the EDS elemental mapping of the sample Ir<sub>2</sub>Sm-L/G precursor (after sodium vapor reduction, without acid etching) was investigated

(ESI, Fig. S4 and S5†), where the sample was prepared for TEM testing with ultradry tetrahydrofuran in an argon atmosphere. STEM-EDS line scan showed that Na element is distributed in the intermetallic NPs, which indicates that the nanoporous structure on the alloy surface is caused by the dissolution of the Na remnant during the pickling process.

After confirming the structure of the intermetallic Ir<sub>2</sub>Sm, the synthesis process was optimized to obtain smaller intermetallic NPs and further increase the number of active sites of the catalyst (ESI, Fig. S6†). As shown in Fig. S7 (ESI†), the average concentrated size distribution of the 300 nanoparticles statistically analyzed was 5.9 nm (denoted as Ir<sub>2</sub>Sm-S/G). STEM images show that the intermetallic Ir<sub>2</sub>Sm NPs are uniformly dispersed on the graphene. The lattice stripes shown in Fig. S6c (ESI†) easily point to the (311) and (111) planes of the intermetallic Ir<sub>2</sub>Sm, and the EDS elemental mapping shows that the Ir and Sm elements are uniformly distributed in a single intermetallic particle.

Furthermore, pure Ir NPs were also prepared in the absence of Sm precursor and characterized (denoted as Ir/G). X-ray



photoelectron spectroscopy (XPS) analysis showed partial spontaneous oxidation on the intermetallic NPs surface (Fig. 3). Compared with the Ir<sup>4+</sup> valence state signal of Ir/G, the Ir 4f signal of the intermetallic Ir<sub>2</sub>Sm is shifted to lower binding energies, which indicates the existence of electron transfer from Sm to Ir in the intermetallic.<sup>38–40</sup> In the Sm 3d spectrum, the main peak  $\Delta E$  of 27.5 eV indicates that Sm is mainly in the metallic valence state.<sup>30</sup>

Next, the OER performance of Ir<sub>2</sub>Sm-L/G, Ir<sub>2</sub>Sm-S/G, Ir/G and commercial Ir/C catalysts was investigated using a typical three-electrode setup in 0.5 M H<sub>2</sub>SO<sub>4</sub> (see ESI† for more details). Fig. 4a shows the linear sweep voltammetry (LSV) curves at 5 mV s<sup>-1</sup> for various catalysts. It can be observed that the overpotentials at a current density of 10 mA cm<sup>-2</sup> are 275 mV (Ir<sub>2</sub>Sm-S/G) and 310 mV (Ir<sub>2</sub>Sm-L/G), which are much lower than those for Ir/G (389 mV) and Ir/C (379 mV), respectively, indicating that the alloying of Sm and Ir effectively enhances the OER activity in acidic medium. Compared with other Ir-based alloy materials, including Ir-Cu, Ir-Ni, and Ir-Rh, Ir<sub>2</sub>Sm-S/G could work at much lower overpotentials (Table S3†).<sup>23,41–45</sup> As shown in Fig. 4b, the intermetallic Ir<sub>2</sub>Sm NPs exhibit lower Tafel slopes (72.9 mV dec<sup>-1</sup> for Ir<sub>2</sub>Sm-S/G and 81.3 mV dec<sup>-1</sup> for Ir<sub>2</sub>Sm-L/G), indicating that the Sm element effectively modulates the reaction kinetics of Ir in the acidic OER.

The double-layer capacitance ( $C_{dl}$ ) of the catalysts derived from the cyclic voltammetry (CV) curves (ESI, Fig. S8†) was used to calculate the electrochemically active surface area (ECSA).<sup>46–49</sup> As shown in Fig. 4c, Ir<sub>2</sub>Sm-S/G has the largest ECSA, which indicates that the synthesis of small-sized intermetallic NPs effectively increases the ECSA (Fig. 4d). To quantitatively evaluate the OER activity of Ir in the catalyst, the current density and the mass activity of Ir at 1.53 V (vs. RHE) were compared. Ir<sub>2</sub>Sm-L/G yielded a current density of 8.47 mA cm<sup>-2</sup> and a mass activity of 0.59 A mg<sub>Ir</sub><sup>-1</sup> at 1.53 V (vs. RHE). Ir<sub>2</sub>Sm-S/G has

a current density of 18.27 mA cm<sup>-2</sup> and a mass activity of 1.24 A mg<sub>Ir</sub><sup>-1</sup>, which are 5.2 and 5.6 times higher than that of Ir/G (3.52 mA cm<sup>-2</sup>, 0.22 A mg<sub>Ir</sub><sup>-1</sup>), respectively. This confirms the significant enhancement of the electrocatalytic activity after the increase of the number of active sites in the intermetallic Ir<sub>2</sub>Sm NPs. In addition, the EIS results of Ir<sub>2</sub>Sm-S/G, Ir<sub>2</sub>Sm-L/G, Ir/G and Ir/C in Fig. 4e exhibit semicircular curves. The semicircle radius of the intermetallic Ir<sub>2</sub>Sm NPs is smaller than that of Ir/G and Ir/C, which indicates that the alloying of Ir with Sm atoms effectively accelerates the electron transfer in OER electrolysis. There was little difference in the solution resistances ( $R_s$ ) of all of the samples. Ir<sub>2</sub>Sm-S/G has the smallest charge transfer resistance ( $R_{ct}$ ) of 157.5  $\Omega$ , compared with Ir/G (603.0  $\Omega$ ), Ir/C (532.9  $\Omega$ ) and Ir<sub>2</sub>Sm-L/G (206.8  $\Omega$ ), indicating the excellent charge transfer rate and electron conductivity (Table S4†).

The chronopotentiometry curve was used to test the stability of the catalyst. Ir<sub>2</sub>Sm-S/G showed long-term stability with a current density of 10 mA cm<sup>-2</sup> for more than 120 h (Fig. 4f), while Ir/G started to deactivate after 10 h. After 120 h of OER testing, the stability of Ir<sub>2</sub>Sm-S/G was determined from the crystal structure and chemical state of the samples. As shown in Fig. S9a and b,† the morphology and phase of the Ir<sub>2</sub>Sm NPs catalyst remained stable, similar to the pristine sample. XPS analysis (ESI, Fig. S9c and d)† showed that the Ir 4f and Sm 3d spectra of Ir<sub>2</sub>Sm-S/G were similar before and after electrocatalysis, except for a slight increase of Ir<sup>4+</sup> species. These results further demonstrated the stability of Ir<sub>2</sub>Sm-S/G. The above results indicate that the alloying of Ir with Sm atoms improves both the catalytic activity and the stability.

To further understand the properties of intermetallic Ir<sub>2</sub>Sm NPs towards the acidic OER, DFT calculations were employed to reveal the active sites and the reaction mechanisms. Based on the surface features obtained from experiments, the Ir (111) and Ir<sub>2</sub>Sm (111) were used to simulate the surfaces. Considering the slight oxidation of the intermetallic NPs surface and the corrosion of the Sm atoms in the surface layer, Ir atoms are enriched on the surface of Ir<sub>2</sub>Sm (111). The Ir atoms on the intermetallic NPs surface are slightly oxidized, but mainly keep a metallic state before and after the OER test, thus allowing partial oxidation of the surface of the model (ESI, Fig. S10†). First, by comparing the PDOS of the Ir-5d orbital, the  $\epsilon_d$  was identified, revealing the binding strength and catalytic activity of the Ir sites (Fig. 5a). The f-d orbital coupling further shows that Sm modified the d-band center of Ir through the ligand and strain effect. Compared with pure Ir metal ( $\epsilon_d$ , -2.72 eV), the  $\epsilon_d$  of the Ir<sub>2</sub>Sm intermetallic is shifted up to -2.14 eV, and the Ir-5d orbitals become less dispersed, which is attributed to the ligand and strain effect in Ir<sub>2</sub>Sm.

In intermetallic Ir<sub>2</sub>Sm, the Sm-4f orbitals show splitting near the Fermi level ( $E_F$ ), which indicates the existence of electronic interaction between Ir and Sm atoms, and the overlap of the Ir-5d and Sm-4f orbitals supports fast electron transfer and protects Ir sites under acidic media (Fig. 5b). The  $\epsilon_d$  is enhanced by alloying and the electrocatalytic activity of Ir is activated. Furthermore, the Ir-5d orbitals are up-shifted and relatively localized, supporting enhanced electrical activity to guarantee an efficient OER process. For OER, free energy maps of the Ir

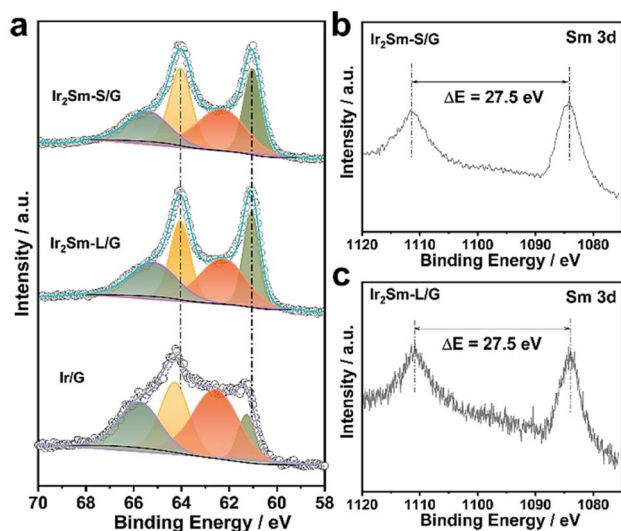


Fig. 3 High-resolution XPS spectra and local structure analysis. (a) Ir 4f core levels of Ir<sub>2</sub>Sm-S/G, Ir<sub>2</sub>Sm-L/G and Ir/G, (b) Sm 3d core levels of Ir<sub>2</sub>Sm-S/G, (c) Sm 3d core levels of Ir<sub>2</sub>Sm-L/G.



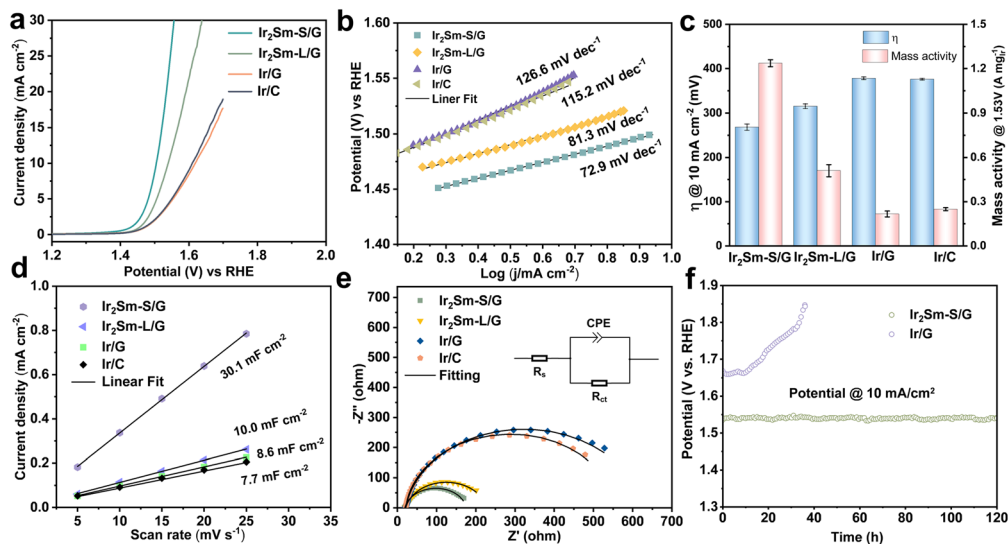


Fig. 4 The electrochemical performance of Ir<sub>2</sub>Sm-L/G, Ir<sub>2</sub>Sm-S/G, Ir/G and Ir/C in 0.5 M H<sub>2</sub>SO<sub>4</sub> electrolyte. (a) IR-corrected OER polarization curves and (b) Tafel plots. (c) Overpotentials at a current density of 10 mA cm<sup>-2</sup> and current density at 1.53 V vs. RHE. (d) C<sub>dl</sub> curves by plotting current density versus scan rate. (e) The Nyquist plots. Inset is an equivalent circuit. (f) Chronopotentiometry curves for Ir<sub>2</sub>Sm-S/G and Ir/G.

(111) and Ir<sub>2</sub>Sm (111) surfaces at  $U = 0$  V vs. RHE and 1.23 V vs. RHE are shown in Fig. 5c and d, respectively. The first step is the adsorption of water molecules on the Ir<sub>2</sub>Sm (111) surface to form OH\*, and the second step is the deprotonation of OH\* species to form O\*. Then, the adsorption of another water molecule occurs to form OOH\*. Finally, molecular oxygen is generated. The free energy diagrams (Fig. 5c and d) show that the step of forming the \*OOH group from the \*O group is strongly suppressed, which is considered to be the RDS. The initial adsorption and dissociation of H<sub>2</sub>O is more favored on

the Ir<sub>2</sub>Sm than the initial oxidation step on Ir, indicating a stronger reaction tendency. The  $\Delta G$  value of the RDS corresponding to Ir (111) is 1.54 eV, and the  $\Delta G$  value of the RDS corresponding to Ir<sub>2</sub>Sm (111) is 1.45 eV, indicating that the OER of Ir<sub>2</sub>Sm is more favorable. The alloying-induced electronic interaction between Sm and Ir changes the position of the Ir  $\varepsilon_d$  in the Ir<sub>2</sub>Sm alloy, which affects the adsorption strength of the adsorbate on the catalyst surface. The DFT calculations are in good agreement with the experimental results.

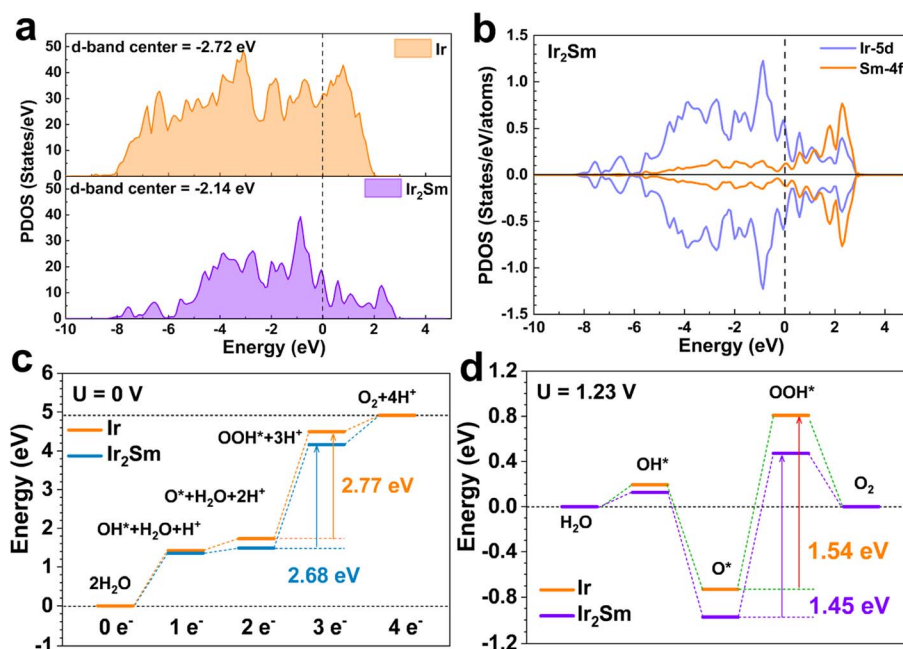


Fig. 5 Theoretical calculations. (a) Density of states of d-orbitals of the Ir sites on Ir (111) and Ir<sub>2</sub>Sm (111) surfaces. (b) The PDOS of Ir-5d and Sm-4f orbitals in Ir<sub>2</sub>Sm (111). (c) Pathways of the acidic OER at  $U = 0$  V and (d)  $U = 1.23$  V (vs. RHE).



## Conclusions

In summary, a new Laves phase of intermetallic Ir<sub>2</sub>Sm NPs was successfully synthesized, which belongs to the *Fd3m* space group. Through optimizing the NPs size, the Ir<sub>2</sub>Sm-S/G exhibits enhanced OER activity in 0.5 M H<sub>2</sub>SO<sub>4</sub> electrolyte. Specifically, the Ir<sub>2</sub>Sm-S/G delivers a mass activity of 1.24 A mg<sub>Ir</sub><sup>-1</sup> at 1.53 V and excellent stability for 120 h at 10 mA cm<sup>-2</sup>. Experimental results together with theoretical studies show that the alloying of Ir and Sm atoms tailors the electronic properties of Ir, resulting in favorable adsorption energies for OER intermediates and further lowering the reaction barrier for the RDS. The synthesis of intermetallic RE NPs will inspire a new strategy for the rational design of efficient electrocatalysts.

## Data availability

The data that support the finding of this study are available in the main text and the ESI.†

## Author contributions

Y. D. proposed the whole research direction and guided the project. S. Z., L. Y., S. W., Q. L. and Y. D. designed and carried out all the synthesis, characterizations and electrochemical measurements. W. W. helped to analyze the theoretical part. All the authors contributed to the formal analysis and writing – original draft.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

We gratefully acknowledge the support from the Natural Science Foundation of China (21971117), Functional Research Funds for the Central Universities, Nankai University (63186005), Tianjin Key Lab for Rare Earth Materials and Applications (ZB19500202), 111 Project (No. B18030) from China, the Outstanding Youth Project of Tianjin Natural Science Foundation (20JCJQJC00130), the Key Project of Tianjin Natural Science Foundation (20JCZDJC00650), the National Postdoctoral Program for Innovative Talents (BX20220157), Open Foundation of State Key Laboratory of Featured Metal Materials and Life-cycle Safety for Composite Structures (Grant No. 2022GXYSOF07), Tianjin “131” Innovative Talent Team Construction Project, and Haihe Laboratory of Sustainable Chemical Transformations. This work was also supported by the PhD Candidate Research Innovation Fund of NKU School of Materials Science and Engineering.

## References

- 1 T. N. Ye, S. W. Park, Y. Lu, J. Li, M. Sasase, M. Kitano, T. Tada and H. Hosono, *Nature*, 2020, **583**, 391–395.

- 2 J. Guo, Y. Zheng, Z. Hu, C. Zheng, J. Mao, K. Du, M. Jaroniec, S. Z. Qiao and T. Ling, *Nat. Energy*, 2023, **8**, 264–272.
- 3 M. Zhou, C. Li and J. Fang, *Chem. Rev.*, 2021, **121**, 736–795.
- 4 B. Zheng, J. Fan, B. Chen, X. Qin, J. Wang, F. Wang, R. Deng and X. Liu, *Chem. Rev.*, 2022, **122**, 5519–5603.
- 5 S. Zhang, S. E. Saji, Z. Yin, H. Zhang, Y. P. Du and C. H. Yan, *Adv. Mater.*, 2021, **33**, 2005988.
- 6 Y. T. Gong, J. Z. Wu, M. Kitano, J. J. Wang, T. N. Ye, J. Li, Y. Kobayashi, K. Kishida, H. Abe, Y. Niwa, H. S. Yang, T. Tada and H. Hosono, *Nat. Catal.*, 2018, **1**, 178–185.
- 7 Y. Yan, J. S. Du, K. D. Gilroy, D. Yang, Y. Xia and H. Zhang, *Adv. Mater.*, 2017, **29**, 1605997.
- 8 S. G. Peera, T. G. Lee and A. K. Sahu, *Sustain. Energy Fuels*, 2019, **3**, 1866–1891.
- 9 C. Kim, F. Dionigi, V. Beermann, X. Wang, T. Moller and P. Strasser, *Adv. Mater.*, 2019, **31**, 1805617.
- 10 S. Zhang, Z. Zeng, Q. Li, B. Huang, X. Zhang, Y. P. Du and C. H. Yan, *Energy Environ. Sci.*, 2021, **14**, 5911–5918.
- 11 J. Shan, C. Ye, C. Zhu, J. Dong, W. Xu, L. Chen, Y. Jiao, Y. Jiang, L. Song, Y. Zhang, M. Jaroniec, Y. Zhu, Y. Zheng and S. Z. Qiao, *J. Am. Chem. Soc.*, 2022, **144**, 23214–23222.
- 12 H. Mizoguchi, S. W. Park, K. Kishida, M. Kitano, J. Kim, M. Sasase, T. Honda, K. Ikeda, T. Otomo and H. Hosono, Zeolitic Intermetallics: LnNiSi (Ln = La–Nd), *J. Am. Chem. Soc.*, 2019, **141**, 3376–3379.
- 13 M. E. Escribano, P. Malacrida, M. H. Hansen, U. G. V. Hansen, A. V. Palenzuela, V. Tripkovic, J. Schiotz, J. Rossmeisl, I. E. L. Stephens and I. Chorkendorff, *Science*, 2016, **352**, 73–76.
- 14 Y. Hu, J. O. Jensen, L. N. Cleemann, B. A. Brandes and Q. Li, *J. Am. Chem. Soc.*, 2020, **142**, 953–961.
- 15 J. S. Kanady, P. Leidinger, A. Haas, S. Titlbach, S. Schunk, K. S. Arndt, E. J. Crumlin, C. H. Wu and A. P. Alivisatos, *J. Am. Chem. Soc.*, 2017, **139**, 5672–5675.
- 16 Y. Hu, J. O. Jensen, P. Norby, L. N. Cleemann, F. Yang and Q. Li, *Chem. Mater.*, 2021, **33**, 535–546.
- 17 R. Ryoo, J. Kim, C. Jo, S. Han, W. J. C. Kim, H. Park, J. Han, H. S. Shin and J. W. Shin, *Nature*, 2020, **585**, 221–224.
- 18 J. Wang, L. Han, B. Huang, Q. Shao, H. L. Xin and X. Huang, *Nat. Commun.*, 2019, **10**, 5692.
- 19 S. Hao, H. Sheng, M. Liu, J. Huang, G. Zheng, F. Zhang, X. Liu, Z. Su, J. Hu, Y. Qian, L. Zhou, Y. He, B. Song, L. Lei, X. Zhang and S. Jin, *Nat. Nanotechnol.*, 2021, **16**, 1371–1377.
- 20 Y. Ge, X. Wang, B. Chen, Z. Huang, Z. Shi, B. Huang, J. Liu, G. Wang, Y. Chen, L. Li, S. Lu, Q. Luo, Q. Yun and H. Zhang, *Adv. Mater.*, 2022, **34**, 2107399.
- 21 L. Li, P. Wang, Q. Shao and X. Huang, *Adv. Mater.*, 2021, **33**, 2004243.
- 22 C. Tang, L. Chen, H. Li, L. Li, Y. Jiao, Y. Zheng, H. Xu, K. Davey and S. Z. Qiao, *J. Am. Chem. Soc.*, 2021, **143**, 7819–7827.
- 23 J. Feng, F. Lv, W. Zhang, P. Li, K. Wang, C. Yang, B. Wang, Y. Yang, J. Zhou, F. Lin, G. C. Wang and S. Guo, *Adv. Mater.*, 2017, **29**, 1703798.
- 24 J. Kibsgaard and I. Chorkendorff, *Nat. Energy*, 2019, **4**, 430–433.



- 25 H. Zhang, P. Shi, X. Ma, C. Ma, S. Han, C. He, H. Wu, L. Zhu, B. Zhang, Y. Lu, W. Cao, H. Yin, X. Meng, J. Xia, J. Zhang, A. L. Wang and Q. Lu, *Adv. Energy Mater.*, 2022, **13**, 2202703.
- 26 J. Li, S. Sharma, X. Liu, Y. T. Pan, J. S. Spendelov, M. Chi, Y. Jia, P. Zhang, D. A. Cullen, Z. Xi, H. Lin, Z. Yin, B. Shen, M. Muzzio, C. Yu, Y. S. Kim, A. A. Peterson, K. L. More, H. Zhu and S. Sun, *Joule*, 2019, **3**, 124–135.
- 27 Y. Nakaya and S. Furukawa, *Chem. Rev.*, 2023, **123**, 5859–5947.
- 28 B. Zheng, J. Fan, B. Chen, X. Qin, J. Wang, F. Wang, R. Deng and X. Liu, *Chem. Rev.*, 2022, **122**, 5519–5603.
- 29 C. Fan, X. Wang, X. Wu, Y. Chen, Z. Wang, M. Li, D. Sun, Y. Tang and G. Fu, *Adv. Energy Mater.*, 2022, **32**, 2203244.
- 30 X. Sun, K. Yuan and Y. W. Zhang, *J. Rare Earth*, 2020, **38**, 801–818.
- 31 X. Shi, B. Cao, J. Liu, J. Zhang and Y. P. Du, *Small*, 2021, **17**, 2005371.
- 32 Q. Miao, S. Yang, Q. Xu, M. Liu, P. Wu, G. Liu, C. Yu, Z. Jiang, Y. Sun and G. F. Zeng, *Small Struct.*, 2022, **3**, 2100225.
- 33 Y. Peng, Y. Bai, C. L. Liu, S. Cao, Q. Q. Kong and H. Pang, *Coord. Chem. Rev.*, 2022, **466**, 214602.
- 34 A. Morozkin, Y. D. Seropegin, A. Gribanov and J. Barakatova, *J. Alloys Compd.*, 1997, **256**, 175–191.
- 35 Z. Blazina, R. C. Mohanty and A. Raman, *Int. J. Mater. Res.*, 1989, **80**, 192–196.
- 36 J. Barthel, *Ultramicroscopy*, 2018, **193**, 1–11.
- 37 Q. Shi, C. Zhu, D. Du and Y. Lin, *Chem. Soc. Rev.*, 2019, **48**, 3181–3192.
- 38 Y. Inami, H. Ogihara, S. Nagamatsu, K. Asakura and I. Yamanaka, *ACS Catal.*, 2019, **9**, 2448–2457.
- 39 T. Toliński, G. Chełkowska, B. Andrzejewski, A. Kowalczyk, M. Kováč and J. Timko, *Phys. Status Solidi A*, 2003, **196**, 294–296.
- 40 H. Jin, X. Liu, P. An, C. Tang, H. Yu, Q. Zhang, H.-J. Peng, L. Gu, Y. Zheng, T. Song, K. Davey, U. Paik, J. Dong and S. Z. Qiao, *Nat. Commun.*, 2023, **14**, 354.
- 41 M. Li, Z. Zhao, Z. Xia, M. Luo, Q. Zhang, Y. Qin, L. Tao, K. Yin, Y. Chao and L. J. Gu, *Angew. Chem., Int. Ed.*, 2021, **133**, 8324–8331.
- 42 Y. Pi, J. Guo, Q. Shao and X. Huang, *Chem. Mater.*, 2018, **30**, 8571–8578.
- 43 J. Zhu, M. Xie, Z. Chen, Z. Lyu, M. Chi, W. Jin and Y. J. Xia, *Adv. Energy Mater.*, 2020, **10**, 1904114.
- 44 D. Cao, H. Xu and D. J. Cheng, *Adv. Energy Mater.*, 2020, **10**, 1903038.
- 45 H. Y. Guo, Z. W. Fang, H. Li, D. Fernandez, G. Henkelman, S. M. Humphrey and G. H. Yu, *ACS Nano*, 2019, **13**, 13225–13234.
- 46 L. Li and Z. C. Zhang, *Rare Met.*, 2022, **41**, 3943–3945.
- 47 J. M. Luo, E. Matios, H. Wang, X. Y. Tao and W. Y. Li, *InfoMat*, 2020, **2**, 1057–1076.
- 48 H. X. Huang, J. J. Zha, S. S. Li and C. L. Tan, *Chin. Chem. Lett.*, 2022, **33**, 163–176.
- 49 Y. Zhang, L. X. Xue, H. B. Liang, Y. Z. Chen, J. J. Liu, C. Shen, Q. Li, Y. Q. Cai, C. L. Tan and Z. M. Luo, *Appl. Surf. Sci.*, 2021, **561**, 150079.

