

Cite this: *Chem. Sci.*, 2023, 14, 8214

All publication charges for this article have been paid for by the Royal Society of Chemistry

Zn-induced electron-rich Sn catalysts enable highly efficient CO₂ electroreduction to formate†

Xingxing Tan,^{ab} Shunhan Jia,^{ab} Xinning Song,^{ab} Xiaodong Ma,^{ab} Jiaqi Feng,^a Libing Zhang,^{ab} Limin Wu,^{ab} Juan Du,^c Aibing Chen,^c Qinggong Zhu,^{ab} Xiaofu Sun^{ab} and Buxing Han^{abd}

Renewable-energy-driven CO₂ electroreduction provides a promising way to address the growing greenhouse effect issue and produce value-added chemicals. As one of the bulk chemicals, formic acid/formate has the highest revenue per mole of electrons among various products. However, the scaling up of CO₂-to-formate for practical applications with high faradaic efficiency (FE) and current density is constrained by the difficulty of precisely reconciling the competing intermediates (*COOH and HCOO*). Herein, a Zn-induced electron-rich Sn electrocatalyst was reported for CO₂-to-formate with high efficiency. The faradaic efficiency of formate (FE_{formate}) could reach 96.6%, and FE_{formate} > 90% was maintained at formate partial current density up to 625.4 mA cm⁻¹. Detailed study indicated that catalyst reconstruction occurred during electrolysis. With appropriate electron accumulation, the electron-rich Sn catalyst could facilitate the adsorption and activation of CO₂ molecules to form a CO₂* intermediate and then promoted the carbon protonation of CO₂* to yield a HCOO* intermediate. Afterwards, the HCOO* → HCOOH* proceeded via another proton-coupled electron transfer process, leading to high activity and selectivity for formate production.

Received 1st June 2023
Accepted 8th July 2023

DOI: 10.1039/d3sc02790b

rsc.li/chemical-science

Introduction

The electrochemical CO₂ reduction reaction (eCO₂RR) to value-added chemicals and fuels utilizing renewable electricity offers a sustainable route to offset the extra carbon footprint.^{1–3} However, this reaction is highly energetic and unfavorable, and a thermodynamic potential of -1.90 V vs. the standard hydrogen electrode (SHE) is needed to activate CO₂ to *CO₂.⁴ Due to the competing hydrogen evolution reaction (HER) and the similarity of the redox potentials (from -0.2 to 0.6 V vs. SHE) for all the subsequent proton-assisted processes,^{5,6} eCO₂RR pathways generally result in a mixture of products. Different studies have aimed to understand the fundamental factors that control the product selectivity, including optimizing catalytic conditions and developing novel catalysts.^{7–12} The adsorption behavior of key

intermediates is strongly dependent on the geometric and electronic structure of the catalyst surface.^{3,13–16} Although some breakthroughs have been made in improving the selectivity for a desired product, it is still in the initial stage of meeting the demands of scaling up the eCO₂RR for practical applications with high faradaic efficiency (FE) and current density.

Among various CO₂-derived products, formic acid/formate presents the highest revenue per mole of electrons.^{17,18} Formic acid is a commonly used feedstock in the pharmaceutical and chemical industries.¹⁷ In addition, with its impressive energy density and convenient transportation, formic acid is also extensively studied as a promising hydrogen carrier for fuel cells.^{19,20} In the reaction pathway of the eCO₂RR to formate, activated CO₂ undergoes a proton-coupled electron transfer (PCET) process to give the HCOO* intermediate and then experiences another transfer to reduce HCOO* to HCOO⁻.²¹ This combination of processes is generally related to the intrinsic properties of the catalyst. Sn is a promising candidate toward formic acid/formate because of its favorable binding energy for HCOO*.^{22,23} However, Sn also shows a certain binding energy to *COOH, resulting in the generation of a CO by-product.²⁴ A promising approach to direct the eCO₂RR over Sn to the HCOO* pathway is to introduce metallic heteroatom doping to construct Sn-based catalysts, which can manipulate the electronic structure of the catalysts to facilitate both the formation and stabilization of the HCOO* intermediate.^{25–27} Notably, Sn-based catalysts may undergo structural evolution during the electrochemical process,

^aBeijing National Laboratory for Molecular Sciences, Key Laboratory of Colloid and Interface and Thermodynamics, Center for Carbon Neutral Chemistry, Institute of Chemistry, Chinese Academy of Sciences, Beijing 100190, P. R. China. E-mail: sunxiaofu@iccas.ac.cn; hanbx@iccas.ac.cn

^bSchool of Chemical Sciences, University of Chinese Academy of Sciences, Beijing 100049, P. R. China

^cCollege of Chemical and Pharmaceutical Engineering, Hebei University of Science and Technology, Shijiazhuang 050018, P. R. China

^dShanghai Key Laboratory of Green Chemistry and Chemical Processes, School of Chemistry and Molecular Engineering, East China Normal University, Shanghai 200062, P. R. China

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3sc02790b>



and then the actual active sites will be created to trigger an efficient catalytic reaction. Therefore, it is significant to reveal the structural evolution of Sn-based catalysts and reveal active sites to achieve efficient CO₂ reduction.²²

Herein, we have constructed a Sn–Zn electrocatalyst (Sn–Zn–O_x) for the eCO₂RR to formate. It exhibited a maximum faradaic efficiency for formate (FE_{formate}) of 96.6% and >90% FE_{formate} was maintained with a partial current density of formate (*j*_{formate}) up to 625.4 mA cm⁻¹. Experimental and density functional theory (DFT) calculations revealed that the reconstructed Sn sites could facilitate the adsorption and activation of CO₂ molecules to form a CO₂^{*} intermediate and then promoted the carbon protonation of CO₂^{*} to intermediate HCOO*. Successively, HCOO* adsorbed on Sn–Zn–O_x enabled H* to adsorb and react with it more accessibly, which could lower the thermodynamic barrier in the second PCET process for the formation of formate.

Results and discussion

The Sn–Zn–O_x nanocomposites were synthesized using a facile coprecipitation method followed by pyrolyzing at 500 °C for 2 h

in an argon atmosphere. The Sn/Zn atomic ratio of the obtained catalysts was 0.85, which was determined by inductively coupled plasma optical emission spectrometry (ICP-OES). Scanning electron microscopy (SEM) and transmission electron microscopy (TEM) images show that Sn–Zn–O_x composites displayed a uniform truncated cubic morphology with edge lengths of about 500 nm (Fig. 1A, B, S1 and S2†). The truncated cube was composed of smaller nanoparticles and was rich in mesopores with a massive pore volume of 6.3 nm, which favored the exposure of more active sites during the eCO₂RR. Only a broad diffraction peak can be observed for Sn–Zn–O_x in the X-ray diffraction (XRD) patterns (Fig. S3†), perhaps due to the small size of the granules. The high-resolution TEM (HRTEM) image shows a lattice spacing of 0.267 nm and 0.330 nm, corresponding to the (110) and (101) planes of SnO₂,²⁸ respectively (Fig. 1C). The energy dispersive X-ray (EDX) elemental mapping and line-scan analysis confirmed that Sn, Zn, and O elements were distributed uniformly over the entire architectures (Fig. 1D and E). Using the same method, we also synthesized ZnO and SnO₂ for comparison. Their SEM and TEM images are shown in Fig. S4 and S5.†

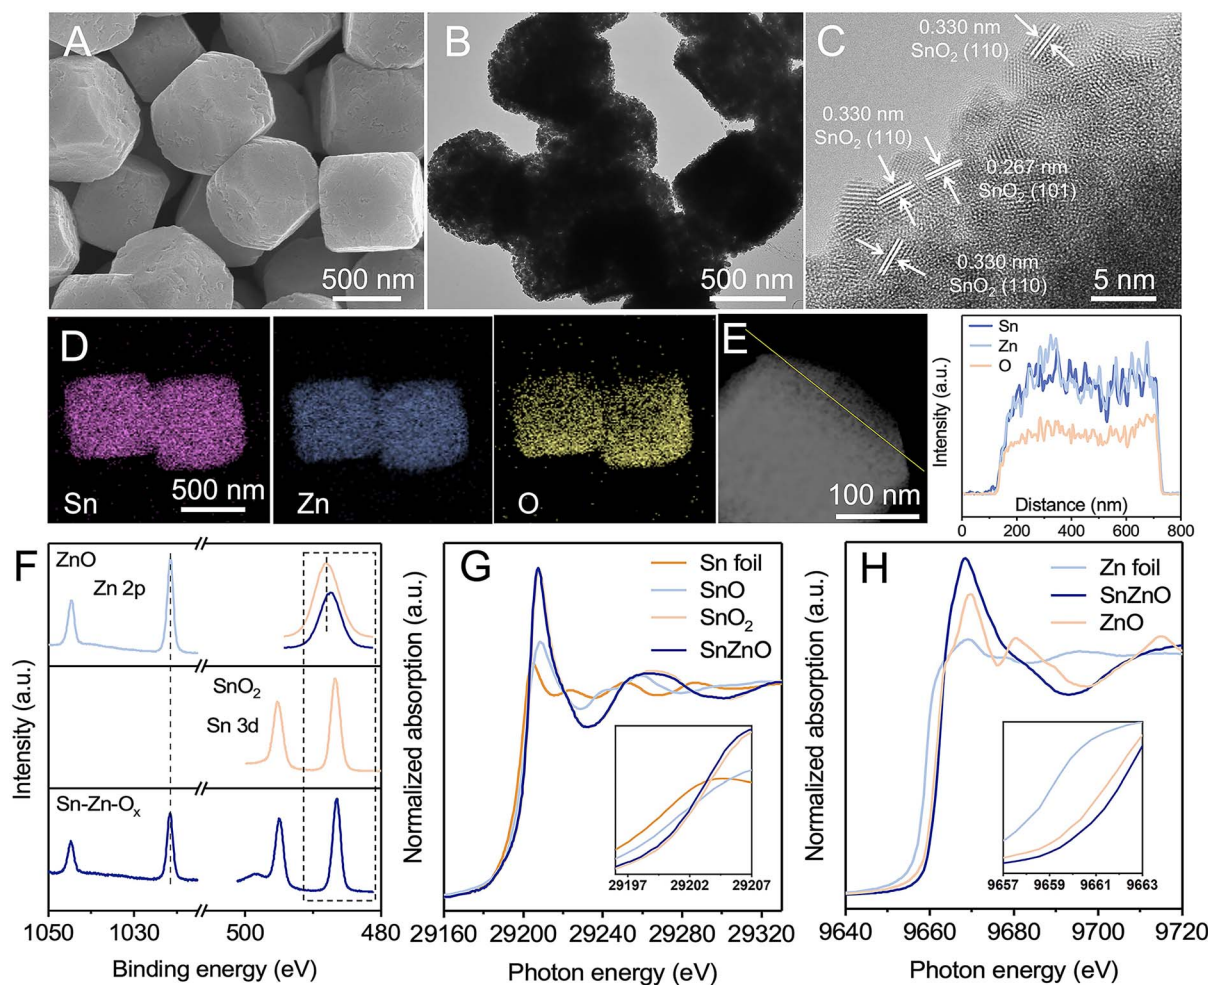


Fig. 1 Morphology and structure characterization of the as-prepared catalysts. (A) SEM image, (B) TEM image, and (C) HR-TEM image of Sn–Zn–O_x. (D) EDS mapping and (E) line scan of Sn–Zn–O_x. (F) XPS spectra of Sn 3d and Zn 2p orbits. (G) Sn K-edge XANES spectra of Sn–Zn–O_x, SnO₂, SnO reference (SnO-ref), and Sn foil (Sn-ref). (H) Zn K-edge XANES spectra of Sn–Zn–O_x, ZnO, and Zn foil (Zn-ref).



X-ray photoelectron spectroscopy (XPS) and X-ray absorption spectroscopy (XAS) were then performed to reveal the composition and structural information of Sn–Zn–O_x. As illustrated in Fig. 1F, the Zn 2p_{3/2} and Zn 2p_{1/2} peaks of Sn–Zn–O_x at 1021.63 eV and 1044.79 eV are slightly higher than those of Zn²⁺ in ZnO. The Sn 3d_{5/2} and Sn 3d_{3/2} peaks of Sn–Zn–O_x, located at 486.52 eV and 494.97 eV, shifted to a lower binding energy by about 0.21 eV compared with SnO₂. The opposite shifts for Zn 2p and Sn 3d orbital peaks indicate the interaction between Zn and Sn, resulting in a modified electronic structure.²⁹ O 1s spectra were also recorded and are shown in Fig. S6.† The peaks at 530 and 531.7 eV can be assigned to the lattice oxygen and oxygen vacancies, respectively.³⁰ Sn–Zn–O_x showed a lower binding energy and an enlarged peak area of oxygen vacancies compared with ZnO and SnO₂. The increased defect degree could improve eCO₂RR activity.³¹ The X-ray absorption near-edge structure (XANES) spectra of Sn K-edge and Zn K-edge were obtained and are shown in Fig. 1G and H. The Sn absorption edge of Sn–Zn–O_x was analogous to the curve of SnO₂, while a slight negative shift of the absorption edge position compared to SnO₂ indicates a lower oxidation state of Sn in Sn–Zn–O_x. Meanwhile, the Zn absorption-edge showed an

opposite shift compared with ZnO, which revealed the electron transfer from Zn to Sn in Sn–Zn–O_x.³² These results are in agreement with the XPS data.

The eCO₂RR performances were investigated in a flow cell using 1 M KOH as electrolyte. The gaseous and liquid products were analyzed by gas chromatography (GC) and ¹H nuclear magnetic resonance (NMR) spectroscopy, respectively. Formate was the only liquid product and its FEs at different potentials are shown in Fig. 2A. The FE_{formate} could be maintained above 90% over Sn–Zn–O_x in a wide potential window of –0.7 to –1.2 V vs. the reversible hydrogen electrode (RHE), and a maximum FE_{formate} of 96.6% can be achieved at –0.8 V vs. RHE. However, the maximum FE_{formate} of the as-synthesized SnO₂ and ZnO was only 79.4% and 43.4%, and H₂ and CO were detected as the by-products (Fig. S7–S11†).

The partial current density of formate was plotted and is shown in Fig. 2B. A high *j*_{formate} of 625.4 mA cm^{–2} was achieved over Sn–Zn–O_x at –1.2 V vs. RHE with a high FE_{formate} above 90%, which is much higher than that of SnO₂ and ZnO. When *j*_{formate} increased to 819.6 mA cm^{–2}, the FE_{formate} still maintained above 76%. Moreover, the Sn–Zn–O_x catalyst exhibited a high formation rate of formate of 11 667.4 μmol h^{–1} cm^{–2} at

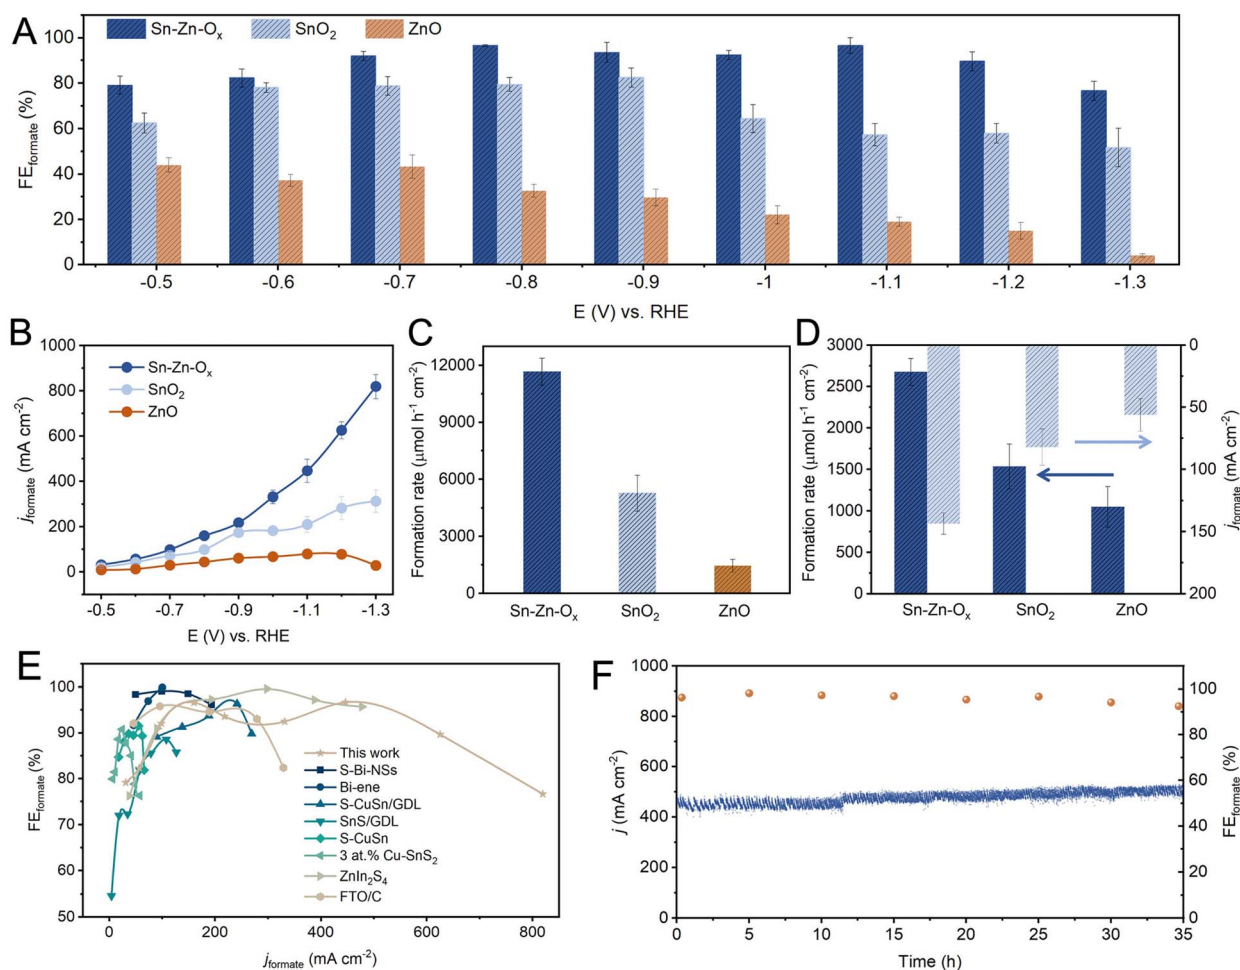


Fig. 2 eCO₂RR performances. (A) The FE_{formate} and (B) *j*_{formate} at different applied potentials on Sn–Zn–O_x, SnO₂ and ZnO. (C) The formation rates of formate at –1.1 V vs. RHE. (D) The ECSA-normalized formate formation rate and partial current density of Sn–Zn–O_x, SnO₂, and ZnO catalysts at –1.1 V vs. RHE. (E) Comparison of FE_{formate} and *j*_{formate} on various reported catalysts. (F) Stability test of Sn–Zn–O_x at –1.1 V vs. RHE.



-1.2 V vs. RHE, which was 2.2 and 8.0 times higher than that of SnO_2 and ZnO , respectively (Fig. 2C). The electrochemically active surface area (ECSA) was further assessed according to the double-layer capacitance (C_{dl}) (Fig. S12 and S13[†]). As shown in Fig. 2D, the ECSA-normalized j_{formate} and formate formation rates were calculated and the value over the Sn-Zn-O_x catalyst was still the highest, indicating its high intrinsic activity. The attained activity of CO_2 -to-formate can be competitive with those of the best catalysts reported, as the high $\text{FE}_{\text{formate}}$ and large j_{formate} were both available over Sn-Zn-O_x (Fig. 2E). In addition, an average $\text{FE}_{\text{formate}}$ of $>90\%$ was maintained during continuous electrolysis for 35 h at -1.1 V vs. RHE, demonstrating the long-term stability of the Sn-Zn-O_x catalyst (Fig. 2F).

To directly relate the enhanced selectivity of formate to the influence of the Zn component in the Sn-Zn-O_x catalyst, Zn(II) species was selectively removed from Sn-Zn-O_x by the acid-washing method and used for comparison. After the acid-washing process for 1 h, the Sn/Zn atomic ratio was increased to 4.35. The truncated cubic morphology was still maintained without obvious structural collapse, and Sn, Zn, and O elements were dispersed evenly in the sample (Fig. S14[†]). However, the sample after removal of Zn species showed much lower CO_2 -to-formate performance than Sn-Zn-O_x (Fig. S15–S17[†]), indicating the critical role of Zn species in the Sn-Zn-O_x catalyst.

The structural evolution during the eCO_2RR was investigated to gain insight into eCO_2RR enhancement. As revealed by SEM and TEM images (Fig. 3A and B), the catalyst maintained the

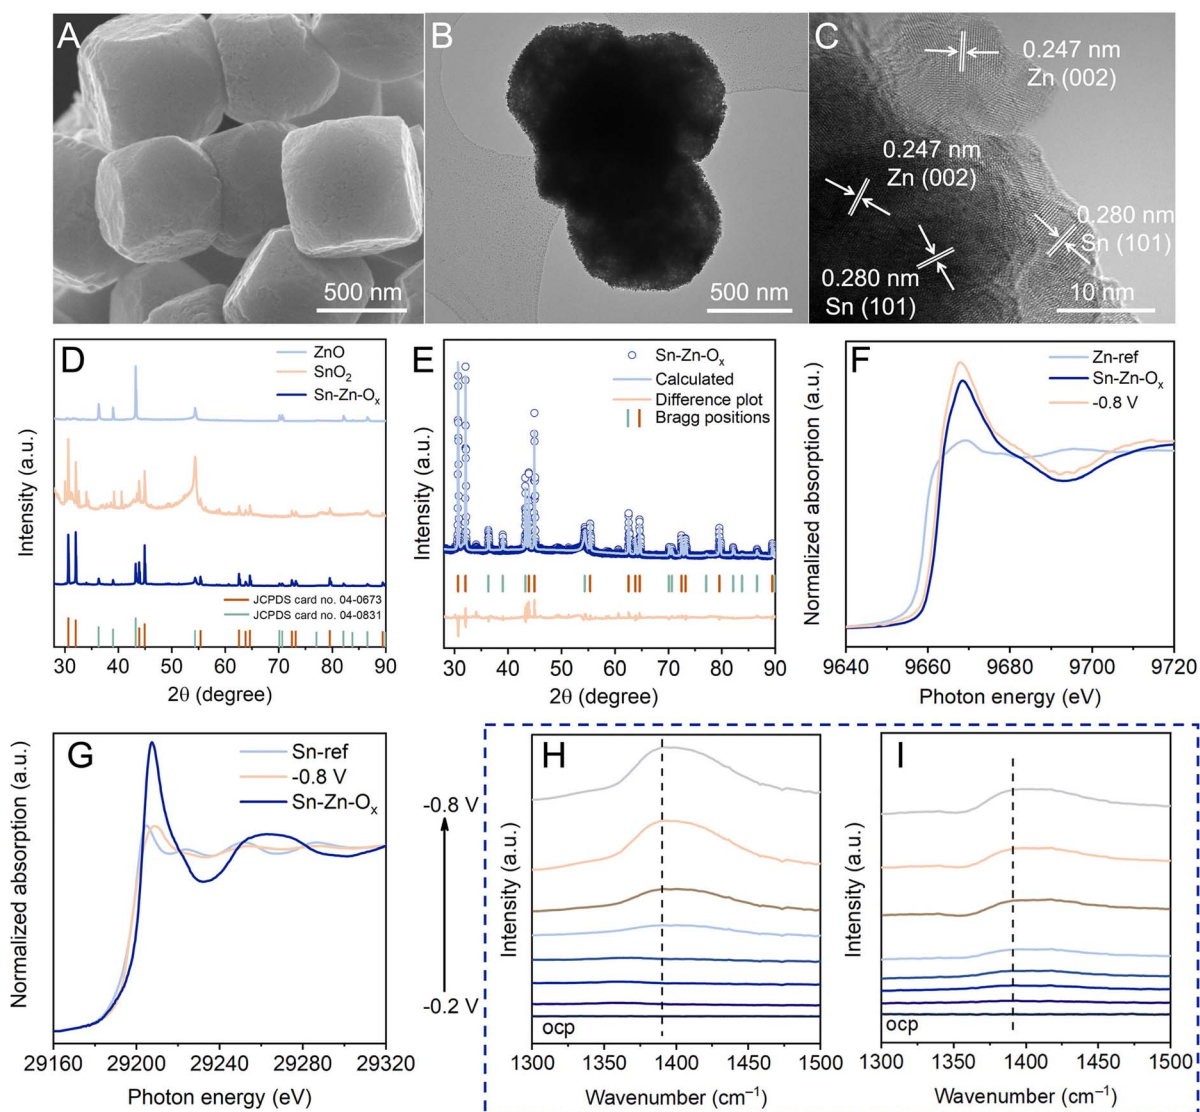


Fig. 3 The structural evolution of the catalysts during the eCO_2RR . (A) SEM image, (B) TEM image, and (C) HR-TEM image of Sn-Zn-O_x after the eCO_2RR . (D) Quasi-*in situ* XRD pattern after the eCO_2RR . (E) Rietveld refinement of the Sn-Zn-O_x catalyst after the eCO_2RR using the XRD pattern in (D). Blue circle marks, blue solid line, and light peach solid line represent observed intensities, Rietveld-fit profile, and difference plot, respectively. The sea green and orange tick marks show the positions of the Bragg reflections. (F) Zn K-edge and (G) Sn K-edge XANES spectra of Sn-Zn-O_x before and after the eCO_2RR at -0.8 V vs. RHE. *In situ* attenuated total reflection surface-enhanced infrared absorption spectroscopy (ATR-SEIRAS) spectra of (H) Sn-Zn-O_x and (I) SnO_2 .



truncated cubic morphology without obvious structural collapse. Sn, Zn, and O elements still existed and were dispersed evenly in Sn-Zn-O_x after the eCO₂RR (Fig. S18[†]). The HRTEM image displays clear lattice spacings of Sn(101) and Zn(002) planes,^{27,33} indicating the reduction of Sn-Zn-O_x during the eCO₂RR (Fig. 3C). The diffraction peaks of Sn (JCPDS 04-0673) and Zn (JCPDS 04-0831) could be detected from quasi-*in situ* XRD measurement (Fig. 3D). According to the Rietveld refinement analysis of the XRD data, the contents of Sn (JCPDS 04-0673) and Zn (JCPDS 04-0831) were estimated to be 85.28% and 14.72% in Sn-Zn-O_x after the eCO₂RR (Fig. 3E). From this apparent difference in the content of the two phases, it could be speculated that oxidized Sn exhibited a greater reduction degree than oxidized Zn. Further investigation of the structural evolution was conducted by *in situ* XANES to eliminate interference from air oxidation (Fig. S19[†]). At the applied potential, the Zn K-edge was shifted to lower energy located between that of the Zn foil (Zn⁰) reference and Sn-Zn-O_x (Fig. 3F). After the eCO₂RR, similar features to Sn were detected, where a lower-energy shift of the Sn absorption edge was observed in Sn-Zn-O_x (Fig. 3G), implying a slightly lower valence state of Sn in Sn-Zn-O_x compared to Sn foil.^{27,34} According to the above results, the Sn oxides in Sn-Zn-O_x was reduced to metallic Sn during eCO₂RR. However, the change in the oxidation state of Zn was relatively small, resulting in more electron accumulation on Sn. It contributes to CO₂ activation and HCOO* intermediate adsorption, leading to enhanced eCO₂RR performance.

In situ ATR-SEIRAS measurements were performed to monitor possible reaction intermediates. According to Fig. 3H and I, the IR band at 1390 cm⁻¹ associated with O-C-O vibration in the bidentate HCOO* intermediate was monitored,^{35,36} and its intensities increased with the increasing potential. This is in agreement with the trend in formate formation rates. Moreover, the band intensity of HCOO* over Sn-Zn-O_x was stronger than that over SnO₂. This phenomenon is consistent with the results of CO₂-to-formate performance, implying that the HCOO* intermediate was the main factor in the generation of formate.³⁷ The sharp contrast suggested that the introduction of Zn played an important role in promoting the HCOO* intermediate production.³⁵

The dissociation of H₂O in an alkaline environment is a sluggish step, which can be detrimental to the PECT processes during the eCO₂RR to formate. Therefore, a catalyst with optimal water dissociation is required to ensure the proton-feeding rate in the eCO₂RR to formate. As shown in Fig. S20,[†] a negative IR band at 1630 cm⁻¹ ascribed to adsorbed H₂O was detected.³⁸ The band intensity of Sn-Zn-O_x was stronger than that of SnO₂, indicating that the introduction of Zn could accelerate the activation of H₂O. As the cathodic potential was applied, H₂O molecules underwent activation to yield protons for the further protonation of *CO₂ to form the HCOO* intermediate, which was confirmed using a stronger IR band for the HCOO* intermediate. These results illustrated that Sn-Zn-O_x favored the formation and stabilization of the HCOO* intermediate, which contributed to the enhanced eCO₂RR performance.

In addition, DFT calculations were performed to elucidate the mechanism for enhanced activity and selectivity of the

eCO₂RR. According to the catalyst characterization data and structural optimization, Sn(101) and Sn(101)-ZnO_x models were constructed to represent SnO₂ and Sn-Zn-O_x, respectively. The detailed data about the computational structure models and relevant parameters are shown in Fig. S21-S24.[†] The electronic structure and interactions of Sn(101)-ZnO_x were investigated using the calculated charge density distribution. As shown in Fig. 4A, the charge density was depleted around Zn atoms and accumulated around Sn atoms, revealing the electron transfer from Zn atoms to Sn atoms and resulting in electron-rich Sn atoms. CO₂ binding capability is a prerequisite for the eCO₂RR. As shown in Fig. 4B, the CO₂ adsorption free energy on Sn(101)-ZnO_x was much lower than that on Sn(101), which was in agreement with the results of the CO₂ adsorption isotherms in Fig. S25.[†] The above results indicate preferable CO₂ adsorption on electron-rich Sn in the Sn-Zn-O_x catalyst.

Fig. 4C displays the Gibbs free energy profiles for the pathway of the eCO₂RR to formate on Sn(101). As the first step, the CO₂ activation process (CO₂ → *CO₂) is essential for the formation of the key intermediate HCOO* in the eCO₂RR to formate.^{39,40} The formation of *CO₂ on Sn (101) was endergonic, and the high free energy of *CO₂ formation (0.31 eV) was not conducive to HCOO* generation. By contrast, Sn(101)-ZnO_x showed a lower energy barrier (0.11 eV) for *CO₂ formation (Fig. 4D), which was favorable for the subsequent hydrogenation reaction to form the HCOO* intermediate. This makes the free-energy step involved in the first PECT toward formate formation more thermodynamically accessible for Sn(101)-ZnO_x. The process of HCOO* undergoing the second PECT to form *HCOOH was the rate-determining step (RDS) for the HCOOH pathway on Sn(101). The Gibbs free energy for this RDS was found to be up to 0.85 eV. Sn(101)-ZnO_x could effectively reduce the free energy of *HCOOH formation to 0.09 eV and convert the RDS into *CO₂ → HCOO*. The changed RDS pathway led to a decrease in the energy barrier for HCOOH formation on Sn(101)-ZnO_x. These results indicate that the Sn-Zn-O_x catalyst with electron-rich Sn enabled a promotion in the formation of formate compared to SnO₂. Furthermore, Sn(101)-ZnO_x presented a significantly higher free energy barrier for *COOH formation than for HCOO* formation, suggesting that the HCOOH pathway was more thermodynamically favorable than the CO pathway.⁴¹ This clarified the high selectivity of Sn(101)-ZnO_x toward formate formation. In addition, Sn(101)-ZnO_x showed a higher energy barrier for the generation of *H intermediates compared to Sn(101) (Fig. 4E), indicating that the HER was inhibited on Sn(101)-ZnO_x.

To further elucidate the promoting effect of Sn(101)-ZnO_x, the projected density of states (PDOS) was analyzed to explore the interaction between the O atoms in key intermediate HCOO* and the Sn atoms on catalyst models. As illustrated in Fig. 4F, Sn(101)-ZnO_x shows more harmonic p-p and p-s overlaps between the O 2p and Sn 5s and 5p orbitals than Sn(101), indicating the enhancement of interactions between the active site and HCOO* intermediate after the introduction of Zn.²² In addition, the upshift of the O 2p orbital away from the Fermi level (*E*_f) suggests an increased antibonding state of the O atom in adsorbed HCOO* on Sn(101)-ZnO_x compared to



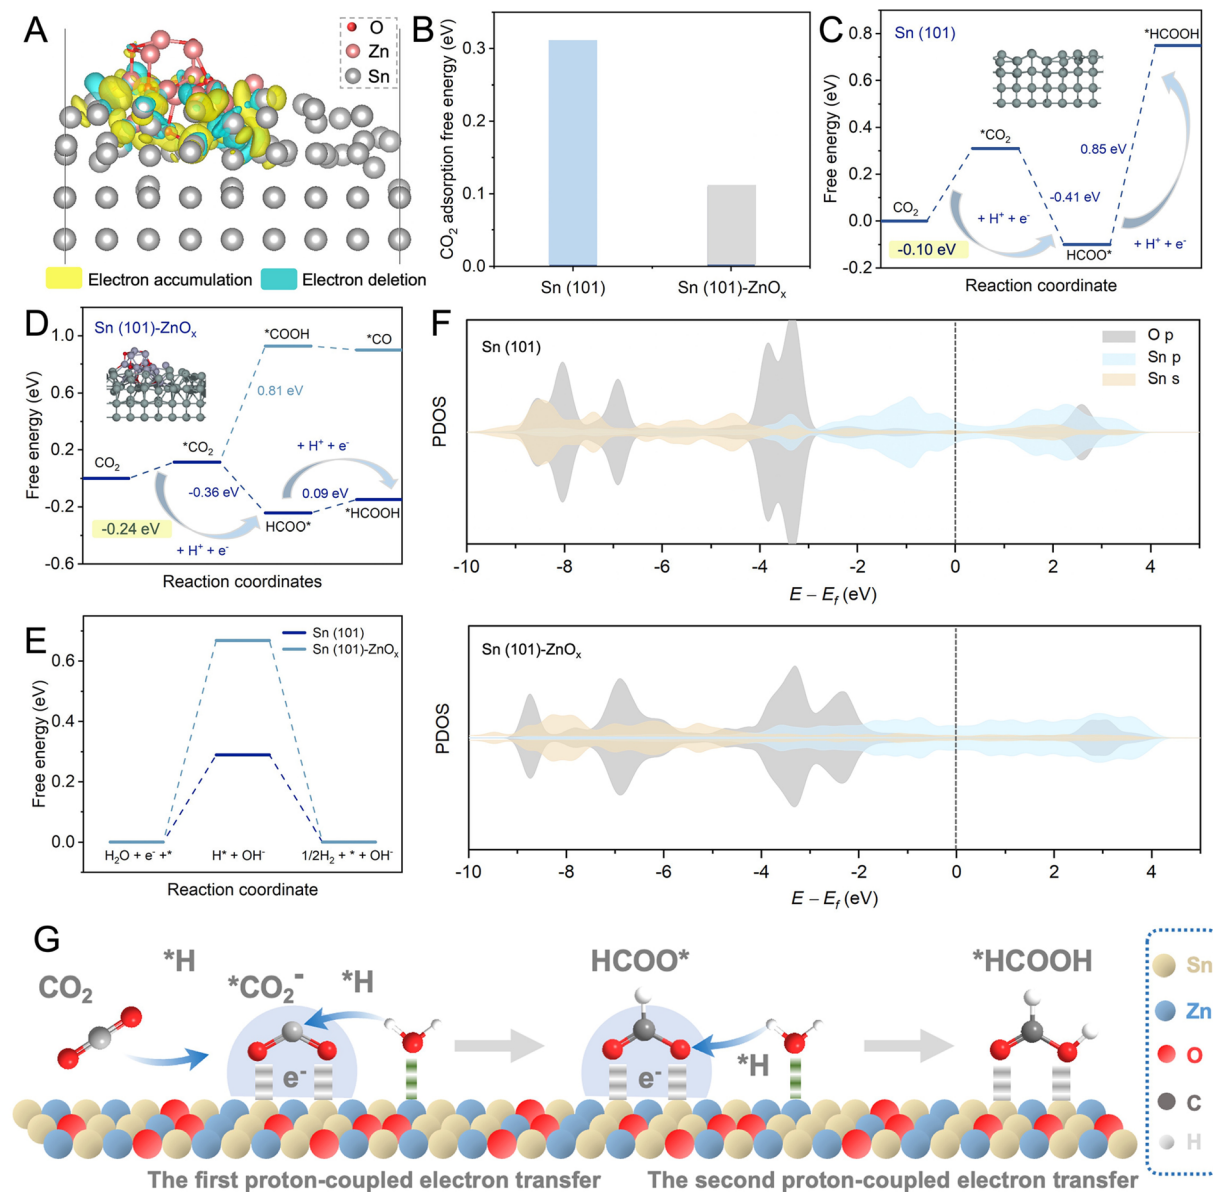


Fig. 4 DFT calculations and eCO₂RR mechanism discussion. (A) Schematic of calculated charge densities among Sn and Zn atoms. (B) CO₂ adsorption free energy. (C) Gibbs free-energy diagrams of the eCO₂RR to HCOOH on Sn(101). (D) Gibbs free-energy diagrams of the eCO₂RR to HCOOH and CO on Sn(101)-ZnO_x. (E) Gibbs free-energy diagrams for the HER process on Sn(101) and Sn(101)-ZnO_x. (F) PDOS of the p orbital of the O atom and s and p orbitals of the Sn atom on the Sn(101) and Sn(101)-ZnO_x models with adsorbed HCOO*. (G) Schematic of the eCO₂RR-to-HCOOH catalytic mechanism over the Sn-Zn-O_x catalyst.

that on Sn(101).^{42,43} This means that HCOO* absorbed on Sn(101)-ZnO_x enables H* to adsorb and react with it more accessibly, leading to a decline in the Gibbs free energies of the PECT process for the formation of HCOOH. Based on the discussion above, the catalytic mechanism of Sn-Zn-O_x for the eCO₂RR was outlined and is shown in Fig. 4G. First, electron-rich Sn could promote the adsorption and activation of CO₂ molecules to generate *CO₂. Meanwhile, the positive-valence Zn sites were more likely to drag the O atom in the absorbed H₂O, which might promote the combination of H* and carbonaceous intermediates in the PCET process. Then, the lower energy barriers for the formation of HCOO* and *HCOOH are conducive to *CO₂ → HCOO* → *HCOOH proceeding rapidly.

Moreover, electron-rich Sn electrocatalysts induced by Zn species in Sn-Zn-O_x might suppress H₂ evolution. As a consequence, the rationally constructed electron-rich Sn catalyst achieved high catalytic activity and excellent selectivity for the eCO₂RR to formate.

Conclusions

In summary, Sn-Zn-O_x has been successfully prepared and used as an efficient electrocatalyst for CO₂-to-formate. The highest FE_{formate} of 96.6% could be achieved and it can maintain a high FE_{formate} above 90% at *j*_{formate} up to 625.4 mA cm⁻¹. The *in situ* experimental results demonstrated the structural



evolution of the catalysts and their significant role in improving the eCO₂RR-to formate performance. The accumulation of electron density around Sn facilitates the activation of CO₂ molecules to form a CO₂^{*} intermediate, which is conducive to the formation HCOO^{*} species. Moreover, Sn–Zn–O_x can modulate the adsorption configuration of HCOO^{*} by increasing the antibonding state of the O atom in absorbed HCOO^{*}, thereby lowering the energy barrier for the PECT for HCOO^{*} → HCOOH^{*} and facilitating CO₂-to-formate conversion. This work offers an effective strategy that coupled electronic structure manipulation and intermediate optimization for CO₂ electro-reduction to formate.

Data availability

All experimental data is available in the ESI.†

Author contributions

X. X. T. performed all the experiments. S. H. J., X. N. S., X. D. M., J. Q. F, L. B. Z., and L. M. W. performed the analysis of the experimental data. J. D., A. B. C. and Q. G. Z. participated in discussions. X. F. S. and B. X. H. co-supervised the whole project. All authors discussed the results and commented on the manuscript.

Conflicts of interest

The authors declare no competing financial interests.

Acknowledgements

The work was supported financially by the Beijing Natural Science Foundation (J210020), National Natural Science Foundation of China (22002172 and 22121002), National Key Research and Development Program of China (2020YFA0710203), Hebei Natural Science Foundation (B2021208074) and Photon Science Center for Carbon Neutrality. The X-ray absorption spectroscopy measurements were performed at Beamline BL14W1 at the Shanghai Synchrotron Radiation Facility (SSRF) and Beamline 1W1B at the Beijing Synchrotron Radiation Facility (BSRF).

Notes and references

- 1 T. Zheng, M. Zhang, L. Wu, S. Guo, X. Liu, J. Zhao, W. Xue, J. Li, C. Liu, X. Li, Q. Jiang, J. Bao, J. Zeng, T. Yu and C. Xia, *Nat. Catal.*, 2022, 5, 388–396.
- 2 Y. Xie, P. Ou, X. Wang, Z. Xu, Y. C. Li, Z. Wang, J. E. Huang, J. Wicks, C. McCallum, N. Wang, Y. Wang, T. Chen, B. T. W. Lo, D. Sinton, J. C. Yu, Y. Wang and E. H. Sargent, *Nat. Catal.*, 2022, 5, 564–570.
- 3 J. Timoshenko, A. Bergmann, C. Rettenmaier, A. Herzog, R. M. Arán-Ais, H. S. Jeon, F. T. Haase, U. Hejral, P. Grosse, S. Kühn, E. M. Davis, J. Tian, O. Magnussen and B. Roldan Cuenya, *Nat. Catal.*, 2022, 5, 259–267.
- 4 H. S. Shafaat and J. Y. Yang, *Nat. Catal.*, 2021, 4, 928–933.
- 5 P. Saha, S. Amanullah and A. Dey, *Acc. Chem. Res.*, 2022, 55, 134–144.
- 6 Y. Wang, J. Liu and G. Zheng, *Adv. Mater.*, 2021, 33, 2005798.
- 7 R. Shi, J. Guo, X. Zhang, G. I. N. Waterhouse, Z. Han, Y. Zhao, L. Shang, C. Zhou, L. Jiang and T. Zhang, *Nat. Commun.*, 2020, 11, 3028.
- 8 S. S. A. Shah, T. Najam, M. Wen, S.-Q. Zang, A. Waseem and H.-L. Jiang, *Small Struct.*, 2021, 3, 2100090.
- 9 C. J. Chang, Y. A. Lai, Y. C. Chu, C. K. Peng, H. Y. Tan, C. W. Pao, Y. G. Lin, S. F. Hung, H. C. Chen and H. M. Chen, *J. Am. Chem. Soc.*, 2023, 145, 6953–6965.
- 10 T. L. Soucy, W. S. Dean, J. Zhou, K. E. Rivera Cruz and C. C. L. McCrory, *Acc. Chem. Res.*, 2022, 55, 252–261.
- 11 Y. Li, Z. Pei, D. Luan and X. W. D. Lou, *Angew. Chem., Int. Ed. Engl.*, 2023, 62, e202302128.
- 12 X. Tan, W. Guo, S. Liu, S. Jia, L. Xu, J. Feng, X. Yan, C. Chen, Q. Zhu, X. Sun and B. Han, *Chem. Sci.*, 2022, 13, 11918–11925.
- 13 X. Su, Z. Jiang, J. Zhou, H. Liu, D. Zhou, H. Shang, X. Ni, Z. Peng, F. Yang, W. Chen, Z. Qi, D. Wang and Y. Wang, *Nat. Commun.*, 2022, 13, 1322.
- 14 S. Kong, X. Lv, X. Wang, Z. Liu, Z. Li, B. Jia, D. Sun, C. Yang, L. Liu, A. Guan, J. Wang, G. Zheng and F. Huang, *Nat. Catal.*, 2022, 6, 6–15.
- 15 S. Liu, X. F. Lu, J. Xiao, X. Wang and X. W. D. Lou, *Angew. Chem., Int. Ed.*, 2019, 58, 13828–13833.
- 16 Q. Qu, S. Ji, Y. Chen, D. Wang and Y. Li, *Chem. Sci.*, 2021, 12, 4201–4215.
- 17 P. Zhu and H. Wang, *Nat. Catal.*, 2021, 4, 943–951.
- 18 T. Zheng, C. Liu, C. Guo, M. Zhang, X. Li, Q. Jiang, W. Xue, H. Li, A. Li, C. W. Pao, J. Xiao, C. Xia and J. Zeng, *Nat. Nanotechnol.*, 2021, 16, 1386–1393.
- 19 A. Boddien and H. Junge, *Nat. Nanotechnol.*, 2011, 6, 265–266.
- 20 S. Chatterjee, I. Dutta, Y. Lum, Z. Lai and K.-W. Huang, *Energy Environ. Sci.*, 2021, 14, 1194–1246.
- 21 G. Wang, J. Chen, Y. Ding, P. Cai, L. Yi, Y. Li, C. Tu, Y. Hou, Z. Wen and L. Dai, *Chem. Soc. Rev.*, 2021, 50, 4993–5061.
- 22 W. Wang, Z. Wang, R. Yang, J. Duan, Y. Liu, A. Nie, H. Li, B. Y. Xia and T. Zhai, *Angew. Chem., Int. Ed.*, 2021, 60, 22940–22947.
- 23 L. Li, A. Ozden, S. Guo, A. d. A. F. P. Garci, C. Wang, M. Zhang, J. Zhang, H. Jiang, W. Wang, H. Dong, D. Sinton, E. H. Sargent and M. Zhong, *Nat. Commun.*, 2021, 12, 5223.
- 24 Y. Deng, J. Zhao, S. Wang, R. Chen, J. Ding, H. J. Tsai, W. J. Zeng, S. F. Hung, W. Xu, J. Wang, F. Jaouen, X. Li, Y. Huang and B. Liu, *J. Am. Chem. Soc.*, 2023, 145, 7242–7251.
- 25 B. Ren, G. Wen, R. Gao, D. Luo, Z. Zhang, W. Qiu, Q. Ma, X. Wang, Y. Cui, L. Ricardez-Sandoval, A. Yu and Z. Chen, *Nat. Commun.*, 2022, 13, 2486.
- 26 Y. J. Ko, J. Y. Kim, W. H. Lee, M. G. Kim, T. Y. Seong, J. Park, Y. Jeong, B. K. Min, W. S. Lee, D. K. Lee and H. S. Oh, *Nat. Commun.*, 2022, 13, 2205.
- 27 S. Yan, C. Peng, C. Yang, Y. Chen, J. Zhang, A. Guan, X. Lv, H. Wang, Z. Wang, T. K. Sham, Q. Han and G. Zheng, *Angew. Chem., Int. Ed.*, 2021, 60, 25741–25745.



- 28 S. Liu, J. Xiao, X. F. Lu, J. Wang, X. Wang and X. W. D. Lou, *Angew. Chem., Int. Ed.*, 2019, **58**, 8499–8503.
- 29 G. Wen, B. Ren, M. G. Park, J. Yang, H. Dou, Z. Zhang, Y. P. Deng, Z. Bai, L. Yang, J. Gostick, G. A. Botton, Y. Hu and Z. Chen, *Angew. Chem., Int. Ed.*, 2020, **59**, 12860–12867.
- 30 Y. Zhang, H. Jang, X. Ge, W. Zhang, Z. Li, L. Hou, L. Zhai, X. Wei, Z. Wang, M. G. Kim, S. Liu, Q. Qin, X. Liu and J. Cho, *Adv. Energy Mater.*, 2022, **12**, 2202695.
- 31 H. Han, S. Jin, S. Park, Y. Kim, D. Jang, M. H. Seo and W. B. Kim, *Nano Energy*, 2021, **79**, 105492.
- 32 H. Zhong, M. Ghorbani-Asl, K. H. Ly, J. Zhang, J. Ge, M. Wang, Z. Liao, D. Makarov, E. Zschech, E. Brunner, I. M. Weidinger, J. Zhang, A. V. Krasheninnikov, S. Kaskel, R. Dong and X. Feng, *Nat. Commun.*, 2020, **11**, 1409.
- 33 A. G. A. Mohamed, E. Zhou, Z. Zeng, J. Xie, D. Gao and Y. Wang, *Adv. Sci.*, 2022, **9**, 2104138.
- 34 K. Ye, Z. Zhou, J. Shao, L. Lin, D. Gao, N. Ta, R. Si, G. Wang and X. Bao, *Angew. Chem., Int. Ed.*, 2020, **59**, 4814–4821.
- 35 Y. Li, J. Chen, S. Chen, X. Liao, T. Zhao, F. Cheng and H. Wang, *ACS Energy Lett.*, 2022, **7**, 1454–1461.
- 36 C. Cao, D. D. Ma, J. F. Gu, X. Xie, G. Zeng, X. Li, S. G. Han, Q. L. Zhu, X. T. Wu and Q. Xu, *Angew. Chem., Int. Ed.*, 2020, **59**, 15014–15020.
- 37 X. Zhong, S. Liang, T. Yang, G. Zeng, Z. Zhong, H. Deng, L. Zhang and X. Sun, *ACS Nano*, 2022, **16**, 19210–19219.
- 38 S. Chen, Z. Zhang, W. Jiang, S. Zhang, J. Zhu, L. Wang, H. Ou, S. Zaman, L. Tan, P. Zhu, E. Zhang, P. Jiang, Y. Su, D. Wang and Y. Li, *J. Am. Chem. Soc.*, 2022, **144**, 12807–12815.
- 39 Z. Li, B. Sun, D. Xiao, Z. Wang, Y. Liu, Z. Zheng, P. Wang, Y. Dai, H. Cheng and B. Huang, *Angew. Chem., Int. Ed.*, 2023, **62**, e202217569.
- 40 L. Lin, X. He, X. G. Zhang, W. Ma, B. Zhang, D. Wei, S. Xie, Q. Zhang, X. Yi and Y. Wang, *Angew. Chem., Int. Ed.*, 2022, **62**, e202214959.
- 41 F. Yang, X. Ma, W. B. Cai, P. Song and W. Xu, *J. Am. Chem. Soc.*, 2019, **141**, 20451–20459.
- 42 Z. Chen, X. Zhang, M. Jiao, K. Mou, X. Zhang and L. Liu, *Adv. Energy Mater.*, 2020, **10**, 5076–5080.
- 43 Z. Chen, Y. Song, J. Cai, X. Zheng, D. Han, Y. Wu, Y. Zang, S. Niu, Y. Liu, J. Zhu, X. Liu and G. Wang, *Angew. Chem., Int. Ed.*, 2018, **57**, 5076–5080.

