

Cite this: *Chem. Sci.*, 2023, 14, 9943

All publication charges for this article have been paid for by the Royal Society of Chemistry

Received 8th June 2023
Accepted 30th August 2023DOI: 10.1039/d3sc02943c
rsc.li/chemical-science

An artificial light-harvesting system constructed from a water-soluble metal–organic barrel for photocatalytic aerobic reactions in aqueous media†

Danyang Li,^a Linlin Yang,^b Wangjian Fang,^c Xinmei Fu,^a Hechuan Li,^a Jianxu Li,^a Xuezhao Li^a and Cheng He^{a*}

An artificial light-harvesting system constructed from a water-soluble host–guest complex can be regarded as a high-level conceptual model of its biological counterpart and can convert solar energy into chemical energy in an aqueous environment. Herein, a water-soluble metal–organic barrel **Ga-tpe** with twelve sulfonic acid units was obtained by subcomponent self-assembly between Ga^{3+} ions and tetra-topic ligands with tetraphenylethylene (TPE) cores. By taking advantage of host–guest interactions, cationic dye rhodamine B (RB) was constrained in the pocket of **Ga-tpe** to promote the Förster resonance energy transfer (FRET) process for efficient photocatalytic aerobic oxidation of sulfides and cross-dehydrogenative coupling (CDC) reaction in aqueous media.

Introduction

The construction of molecular containers has provided a sustainable way to mimic and rival natural organisms and enzymes.¹ Among such cage-like hosts, the coordination-driven assembly of metal–organic cages, which can be functionalized with both organic ligands and metal centers, has been considered an excellent candidate to mimic enzymes, due to their precisely controlled, well-defined topology obtained using facile synthesis and stability in common solvents.^{2,3} With highly selective recognition toward substrates inside their large inner cavity, such discrete coordination constructs have proven useful as molecular devices for substrate encapsulation,⁴ separation,⁵ and reaction vessels to catalytically accelerate chemical processes.^{6,7}

Specifically, supramolecular assemblies formed by cage hosts and encapsulated guests with essential components being forced into close proximity have also attracted constant attention to developing supramolecular charge/energy donor–acceptor systems, which led to efficiency enhancements in energy, electron, or substance transfers based on short through-space and long through-bond pathways.^{8,9} For example, inspired by nature, significant advances have been made in

using supramolecular donor–acceptor systems to mimic light antenna harvesting systems using the FRET process.^{10–14} Previously, we reported a highly efficient supramolecular FRET system using a large metal–organic cage as a donor. It was thought that encapsulation of the guest within the inner cavity of the cage would render the interaction between the donor and the acceptor stronger and more robust in close proximity and the rigid coordination cage could provide an isolated micro-environment in which the donors could be fixed at a high local concentration without further aggregation.¹⁵

It is nearly universal in natural systems that most host–guest interactions based on biological processes are executed under aqueous conditions.¹⁶ Nevertheless, most metal–organic cages have been prepared and studied in organic solvents. It is appealing to create water-soluble metal–organic cages that could be regarded as high-level conceptual models for their biological counterparts.¹⁷ Water-soluble metal–organic cages with large inner pockets have found widespread use in the selective storage and transport of a variety of guest molecules, as well as in the promotion of chemical reactions.^{18–20} To achieve this goal, the design of water-soluble and stable metal–organic cages is highly desired but has been challenging due to the following: first, these discrete coordination structures need to maintain rigidity and stability, which requires the ligands to contain nonpolar aromatic backbones; however, in this case, the aromatic ligand is poorly soluble in aqueous solutions. Second, due to the coordinating ability of water, it can bind to metal centers, compete with ligands, and reduce the formation of metal–organic cages. Third, hydrophobic effects may change the way ligands organize around metal ions, leading to aggregation as opposed to the formation of hollow cages.

^aState Key Laboratory of Fine Chemicals, Dalian University of Technology, Dalian 116012, P. R. China. E-mail: hecheng@dlut.edu.cn

^bXinxiang Key Laboratory of Forensic Science Evidence, School of Forensic Medicine, Xinxiang Medical University, Xinxiang 453003, P. R. China

^cInstitute for Molecular Design and Synthesis, School of Pharmaceutical Science & Technology, Tianjin University, Tianjin 300072, P. R. China

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3sc02943c>



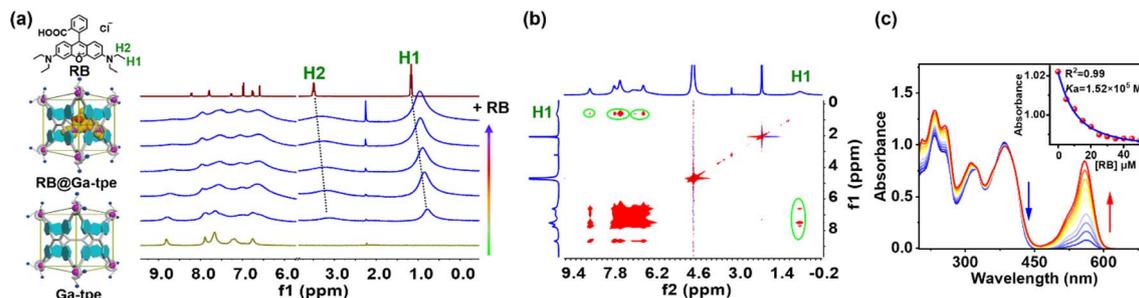


Fig. 3 (a) The ^1H NMR titration spectra between Ga-tpe ($[\text{Ga-tpe}] = 2.0 \times 10^{-3} \text{ M}$) and RB (1 equiv. per session) in D_2O ; (b) the NOESY spectrum of Ga-tpe with RB in D_2O ; (c) the absorbance spectra of Ga-tpe ($[\text{Ga-tpe}] = 1.0 \times 10^{-5} \text{ M}$) upon the addition of RB in water. Inset: nonlinear fitting of the titration curve at 385 nm, showing the calculated associate constant $K_a = 1.52 \times 10^5 \text{ M}^{-1}$.

ions were located at the vertices of the barrel, whereas the three ligands served as the three faces of the barrel to form a pocket for the recognition and localization of guests (such as RB or MB) in the host. Moreover, the results suggested that coordination-driven restricted rotation of the TPE-ligand would prohibit nonradiative decay.²²

Host-guest complex with encapsulated RB

Driven by possible aromatic interactions, H bond interactions, and electrostatic interactions in the Ga-tpe pocket, the cationic energy acceptor RB with a suitable size was expected to be encapsulated in the Ga-tpe cage as a guest, not only avoiding the aggregation-caused quenching effect of the aggregated dye but also forcing close proximity between the energy donor and acceptor to meet the need for a highly efficient FRET process. The mode of interaction between Ga-tpe and RB was studied by isothermal titration calorimetry assays, and the combined number indicated that the presence of RB triggered the formation of an RB@Ga-tpe 1:1 host-dye complex in water (Fig. S10, ESI[†]). Curve fitting by computer simulation using an “independent” model showed an association constant of $1.22 \times 10^5 \text{ M}^{-1}$.

The formation of the host-guest complex was further evidenced by the ^1H NMR titration experiment between metal-organic barrel Ga-tpe and RB (Fig. 3a). The addition of RB to Ga-tpe showed significant upfield shifts (0.42 ppm and 0.38 ppm) where the methyl (H1 and $-\text{CH}_3$) and the methylene (H2 and $-\text{CH}_2-$) protons of RB were observed. Furthermore, H-H interactions between the aromatic rings, $-\text{NH}-$ of Ga-tpe and methyl (H1) protons of RB could be observed in the nuclear Overhauser effect (NOESY) spectrum of RB@Ga-tpe (Fig. 3b), which showed the guest RB to reside within the pocket of Ga-tpe and the donor host and acceptor guest were close enough in space for efficient energy transfer. The binding constant of RB with Ga-tpe was detected by UV-Vis titration in water and nonlinear fitting of the titration curve with an association constant ($K_a = 1.52 \times 10^5 \text{ M}^{-1}$) (Fig. 3c). With a gradually increasing ratio of RB to Ga-tpe , the absorption peak of Ga-tpe at 385 nm gradually decreased, causing significant variation in these bands with sharp isosbestic points at 360 nm and 415 nm, suggesting the formation of a host-guest complex between Ga-tpe and RB .

Artificial light harvesting by Förster resonance energy transfer

The effective FRET process requires not only an appropriate distance and dipole orientation between different chromophores but also a match in the spectral overlap between the donor emission and acceptor excitation. RB was chosen as an energy acceptor because of the good overlap between the fluorescence band of Ga-tpe and the absorption spectra of RB (Fig. 4a). The FRET process was shown by fluorescence titration of RB with the aqueous solution of Ga-tpe (Fig. 4b). Interestingly, with an increasing concentration of RB in Ga-tpe , the broad emission peak of Ga-tpe at 505 nm was gradually decreased, while a new emission peak of RB@Ga-tpe at 590 nm appeared when excited at 385 nm. Moreover, the CIE chromaticity diagram confirmed the obvious fluorescence color change from blue to pink under UV light (Fig. 4c). Alternatively, the addition of Ga-tpe to the solution of RB showed that the intensity of Ga-tpe and RB gradually increased when excited at 385 nm, revealing the highly efficient energy transfer from Ga-tpe to RB (Fig. 4d).

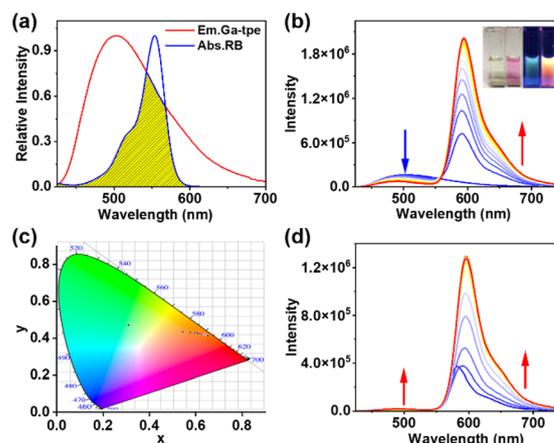


Fig. 4 (a) Normalized fluorescence spectrum of Ga-tpe and the absorbance spectrum of RB ; (b) fluorescence spectrum of Ga-tpe ($[\text{Ga-tpe}] = 1.0 \times 10^{-5} \text{ M}$) in water with different concentrations of RB (0.05 equiv. per session); (c) the CIE chromaticity diagram changes of Ga-tpe upon titration with RB ; (d) fluorescence spectrum of RB ($[\text{RB}] = 1.0 \times 10^{-5} \text{ M}$) in water with different concentrations of Ga-tpe .



Compared to that of **Ga-tpe** (1.37%), the quantum yield of **RB@Ga-tpe** increased to 15.76%, which further confirmed the occurrence of the FRET process (Fig. S12, Table S1 ESI†). In addition, the fluorescence lifetime of **Ga-tpe** followed a double exponential decay, which showed $\tau_{\text{int}} = 1.04$ ns when emitting at 405 nm (Fig. S13, Table S2 ESI†). In contrast, the fluorescence lifetime of **RB@Ga-tpe** was found to be shorter in the presence of **RB** ($\tau_{\text{int}} = 0.98$ ns), which suggested that energy could be transferred from the donor **Ga-tpe** to the acceptor **RB**. As a result, the Φ_{ET} of **RB@Ga-tpe** reached 56.1% (ESI, Table S3†).

In addition, the importance of host-guest interaction in the FRET system was identified by preventing the FRET process by binding an inhibition guest in the pocket of **Ga-tpe**. Methylene blue 2B (**MB**) is a cationic dye similar to **RB**, which is smaller than **RB**. **MB** was chosen as a competitive guest introduced into the host-guest system. The fluorescence and UV-Vis absorption titration indicated that **MB** was a suitable competitive guest for binding into the pocket of **Ga-tpe** to replace **RB** (Fig. S14, ESI†). Notably, upon the gradual addition of **MB** to the mature **RB@Ga-tpe** FRET system, the emission peak of the system at 590 nm gradually decreased (Fig. S15, ESI†). This showed that **MB** competed with **RB** for binding into **Ga-tpe** to inhibit the FRET process, resulting in a decrease in the emission intensity of **RB@Ga-tpe**. The effect of the host-guest interaction on the FRET processes was also identified using the fluorescence titration of **RB** with a solution of ligand **L**. Even though the absorption of **RB** overlapped well with the emission of **L**, the broad emission peak of ligand **L** at 520 nm slightly decreased upon the gradual addition of **RB** to a solution of ligand **L** (Fig. S16, ESI†).

Research on reactive oxygen species (ROS)

To better display the versatility of **RB@Ga-tpe**, we explored its use in photocatalytic oxidation reactions. Subsequently, we investigated the capacity of **RB@Ga-tpe** to generate ROS using 3,3',5,5'-tetramethylbenzidine (TMB) as a probe molecule. Upon adding **RB@Ga-tpe** into a methanol solution containing TMB, the characteristic absorption peak of the oxidized TMB at around 670 nm increased significantly with Xe light irradiation time in an air atmosphere (Fig. 5a), suggesting the formation of ROS. For comparison, the absorption became lower under similar conditions when performed with **Ga-tpe** or **RB** only (Fig. 5b and S18, ESI†), respectively, indicating that the artificial light-harvesting system benefitted oxygen activation.

To clarify the various types of ROS that were generated when using **RB@Ga-tpe**, the electron paramagnetic resonance (EPR) spectra using 2,2,6,6-tetramethylpiperidine (TEMP) and 5,5-dimethyl-1-pyrroline *N*-oxide (DMPO) as ROS trapping agents were recorded under xenon lamp irradiation and in an air-saturated CH₃OH solution (Fig. 5c and d). The obvious characteristics of singlet oxygen (¹O₂) and superoxide (O₂^{•-}) were trapped. The results showed that the active oxygen species ¹O₂ and O₂^{•-} could be produced by using **RB@Ga-tpe** as a photocatalyst, generated by an energy transfer process and single electron transfer.

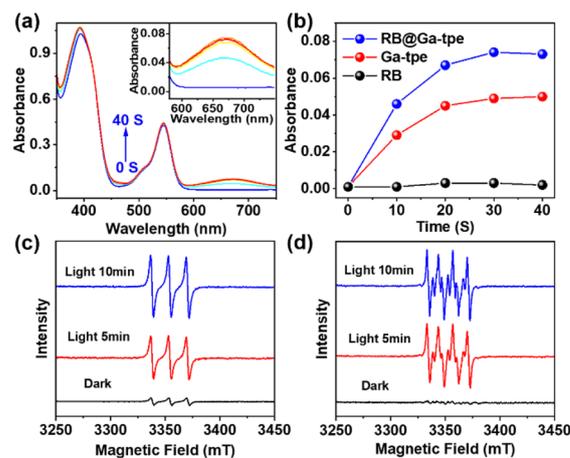


Fig. 5 (a) Evolution of the UV-Vis spectra during the continuous irradiation of **RB@Ga-tpe** with Xe light in the presence of TMB in an air atmosphere; (b) time-dependent corresponding absorption of TMB at 670 nm; (c) the detection of ¹O₂ in a mixture of TEMP and **RB@Ga-tpe** in methanol solution under xenon lamp irradiation using EPR spectra in an air atmosphere; (d) the detection of O₂^{•-} in a mixture of DMPO and **RB@Ga-tpe** in methanol solution under xenon lamp irradiation using EPR spectra in an air atmosphere.

Photooxidation of sulfides to sulfoxides

To use the output energy to simulate the natural photosynthetic process, the above artificial light-harvesting system based on **RB@Ga-tpe** was applied as a photocatalyst for the oxidation of thioanisole in water (Table 1). As expected, an excellent yield (90%) and selectivity capability (>99%) on the sulfide being transformed into sulfoxide have been achieved in an aqueous

Table 1 Photooxidation of sulfide to sulfoxide^a

Entry	Photocatalyst	Light	Conv. (%)	Selectivity (%)	
				1a	1b
1	RB@Ga-tpe	Xe	90	>99	<1
2	RB	Xe	13	>99	<1
3	Ga-tpe	Xe	n.d.	0	0
4	L	Xe	10	>99	<1
5	L&RB	Xe	30	>99	<1
6	Blank	Xe	n.d.	0	0
7 ^b	RB@Ga-tpe	Xe	n.d.	0	0
8	RB@Ga-tpe	Dark	n.d.	0	0
9	Ga-tpe	395 nm	23	>99	<1
10	RB	395 nm	n.d.	0	0
11	RB@Ga-tpe	395 nm	55	>99	<1

^a Reaction conditions, thioanisole (0.2 mmol, 1 equiv.), catalyst (0.5 mol%), water (2 ml), room temperature, 12 h, air. ^b Ar. The yields were determined by GC analysis (using 1,3,5-trimethoxybenzene as the internal standard).




solution and when irradiated with a Xe light (Table 1, entry 1). Exhilaratingly, the yield of **1a** increased dramatically upon using the light-harvesting system **RB@Ga-tpe** compared with using either **RB** or **Ga-tpe** only (Table 1, entries 2 and 3). Meanwhile, the control experiments using ligand **L** or **L&RB** yielded a trace of the product under the same conditions, confirming that the supramolecular host using the preorganization of an artificial light-harvesting system is essential (Table 1, entries 4 and 5). Furthermore, a series of control experiments were carried out to confirm that the presence of light, photosensitizer, and O₂ is essential for the catalytic reaction under similar conditions (Table 1, entries 6–8). Then, 395 nm light (the near absorption of **Ga-tpe**) triggered the photocatalytic reaction, the slightly high yield (**RB@Ga-tpe** as the photocatalyst) was 55%, and the lower yield (**Ga-tpe** or **RB** as the photocatalyst) was obtained (Table 1, entries 9–11). The results indicated that the photooxidation reaction could also use 395 nm light through the absorption of **Ga-tpe**, expanding the range of the catalytic light source.

Encouraged by the remarkable photocatalytic performance, the substrate compatibility of **RB@Ga-tpe** with various sulfides was further explored. As shown in Table S4,† **RB@Ga-tpe** exhibited excellent activity and selectivity toward other methylphenyl sulfide derivatives with different substituents, such as methoxy (–OMe) and fluorine (–F). Due to the limited solubility of the substrate in aqueous solution, when a small amount of methanol was added to the system, the yield of sulfoxides (**1e–i**) was significantly improved. In the photooxidation of sulfides, a series of quenching experiments were carried out by introducing various scavengers, such as sodium azide (NaN₃, a scavenger of ¹O₂), 1,4-benzoquinone (BQ, a scavenger of O₂^{•–}), isopropanol (IPA, a scavenger of [•]OH), and AgNO₃ (as an electron trapping agent), respectively. The photooxidation reactions were effectively prohibited by adding sodium azide and BQ, whereas other scavengers exerted less influence than them, which revealed that ¹O₂ and O₂^{•–} should be the dominant reactive species (Fig. S19a and S20, ESI†).²³

Photocatalytic aerobic CDC reaction

The **RB@Ga-tpe** assembly with catalytic efficiency for the oxidation of sulfides was then expanded to other photocatalytic oxidative organic transformations, such as photocatalytic aerobic CDC reactions (Table 2), a highly efficient and powerful strategy for the construction of new carbon–carbon and carbon–heteroatom bonds, which has been considered a waste-minimized and sustainable synthetic alternative to classic coupling procedures.²⁴ In particular, the photocatalytic C–H functionalization of tertiary amines is the most atom-economic and sustainable reaction process. The aerobic CDC reaction of *N*-phenyl-1,2,3,4-tetrahydroisoquinoline **2a** and nitromethane with **RB@Ga-tpe** as a photocatalyst was selected as a model photocatalytic reaction. The blank reaction was performed under the same conditions, and a moderate yield was shown (50%, Table 2, entry 5). Alone, **Ga-tpe**, **RB**, or **L**, as the photocatalyst, produced relatively low yields in aqueous solution (52–65%, Table 2, entries 2–4). For comparison, the activity of

Table 2 Photocatalytic aerobic CDC reaction^a



Entry	Photocatalyst	Light	Yield rate (%)
1	RB@Ga-tpe	Xe	90
2	Ga-tpe	Xe	65
3	RB	Xe	59
4	L	Xe	52
5	Blank	Xe	50
6	RB@Ga-tpe	Dark	n.d.
7	L&RB	Xe	70
8	Ga-tpe	395 nm	34
9	RB	395 nm	25
10	RB@Ga-tpe	395 nm	51


^a Reaction conditions: *N*-phenyl-1,2,3,4-tetrahydroisoquinoline (0.1 mmol, 1 equiv.), nitromethane (0.3 ml), catalyst (1.0 mol%), water solution (2 ml), room temperature, 12 h. The yields were determined by ¹H NMR analysis using 1,3,5-trimethoxybenzene as an internal standard.

RB@Ga-tpe in the photocatalytic CDC reaction was investigated; an excellent yield of 90% was achieved under the same conditions (Table 2, entry 1). However, a moderate reaction yield was obtained by the assembly resembling **L&RB** (70%, Table 2, entry 7). These above results revealed that light energy harvested using **Ga-tpe** could be efficiently transferred to **RB** within the host–guest encapsulated system, and the **RB@Ga-tpe** system could be an ideal reaction platform for organic reactions in aqueous solutions.

A series of quenching experiments were also carried out by introducing various scavengers into the CDC reaction (Fig. S19b, ESI†). Unsurprisingly, the abovementioned studies demonstrated that the superoxide radical anion is the active intermediate in the photocatalytic CDC reactions. According to the above findings and literature results,²⁵ the photocatalytic CDC reaction mechanism between *N*-phenyl-1,2,3,4-tetrahydroisoquinoline and nitromethane was proposed (Fig. S21, ESI†). The **RB@Ga-tpe** assembly was excited using Xe light in an aqueous solution, and the excited state of **Ga-tpe** transferred the energy to the acceptor dye **RB** to form the excited state of **RB**. As shown in Table 3, we further explored the substrate scope; generally, *N*-phenyl-1,2,3,4-tetrahydroisoquinoline derivatives with different electronic properties could be converted to the desired reaction products **3a–h** in excellent yields (71–94%).

Overall, these results confirmed that the photocatalytic aerobic reaction was initiated by the supramolecular assembly in the aqueous phase, and dye-loaded capsule **RB@Ga-tpe** could be regarded as one kind of biological counterpart. The host–guest species **RB@Ga-tpe** with excellent photocatalytic ability can serve as an efficient light-harvesting system where the output energy was successfully utilized for catalytic chemical transformation for practical application in the aqueous phase. The reason why the dye-loaded capsule **RB@Ga-tpe** exhibited

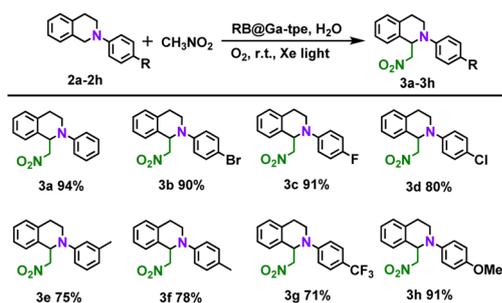

Table 3 The substrate scope of the CDC reaction^a

^a Reaction conditions: *N*-phenyl-1,2,3,4-tetrahydroisoquinoline derivative (0.1 mmol, 1 equiv.), nitromethane (0.3 ml). **RB@Ga-tpe** assembly solution (**RB**:**Ga-tpe** = 1:1, 1.0 mol%, 2 ml), Xe light, oxygen ball, room temperature, 18 h. The yields were determined by ¹H NMR analysis using 1,3,5-trimethoxybenzene as an internal standard.

high catalytic efficiency might be that the host-guest arrangement between the cage **Ga-tpe** and **RB** in a confined space avoids unnecessary fluorescence quenching, and the photobleaching effect of **RB** upon long-time irradiation was also decreased because of the formation of a supramolecular assembly. Thus, we believe that such an efficient host-guest system with an energy transfer process would provide new insight into the fabrication of artificial photosynthetic systems.

Conclusions

In summary, a new negatively charged metal-organic barrel **Ga-tpe** endowed with water solubility was reported for the construction of a light-harvesting system by host-guest interactions to accelerate light-driven aerobic reactions in aqueous media. The energy acceptor **RB** was matched to generate the FRET process by rendering the host-guest interaction between the donor and the acceptor stronger and more robust in close proximity. The artificial light-harvesting system **RB@Ga-tpe** had suitable potential for the photooxidation of sulfides to sulfoxides reaction and photocatalytic CDC reactions in simulating the photosynthesis process. Overall, this work presents an ideal way for the creation of a water-soluble artificial light-harvesting system *via* host-guest encapsulation to enhance the efficiency of the FRET process, serving as a versatile platform for mimicking natural photosynthesis in a simulated enzymatic environment. The further development of metal-organic host-guest assemblies in aqueous solutions that mimic natural organisms will be facilitated and accelerated in the future.

Experimental

Preparation of **Ga-tpe**

A mixture of 4,4',4'',4'''-(ethene-1,1,2,2-tetrayl)tetra (benzohydrazide) (84.7 mg, 0.15 mmol), 5-sulfosalicylaldehyde sodium salt (134.8 mg, 0.6 mmol), NaOH (48 mg, 1.2 mmol), and gallium tris(acetylacetonate) (110.1 mg, 0.3 mmol) was dissolved in 30 mL CH₃OH and then heated at 60 °C for 24 h to give

a clear yellow solution. The mixture was repeatedly recrystallized from dichloromethane and acetone to afford a yellow solid with 65.6% yield (based on the solid dried under vacuum). ¹H NMR (400 MHz, D₂O) δ 8.76 (s, 4H), 7.84 (s, 4H), 7.61 (s, 12H), 7.13 (s, 8H), 6.70 (s, 4H). ¹³C NMR (100 MHz, MeOD) δ 193.78, 180.44, 170.44, 168.75, 161.46, 156.96, 147.08, 134.59, 133.11, 132.02, 128.35, 122.01, 118.21.

General procedure for the **RB@Ga-tpe** photocatalytic oxidation of thioanisole

Thioanisole (0.2 mmol, 1 equiv.), catalyst (0.5 mol%), and H₂O (2 ml) were added to a glass reactor and irradiated with a Xe lamp at room temperature for 12 h in an air atmosphere. At the end of the reaction, it was extracted using dichloromethane. The yields were monitored using gas chromatography (GC) and ¹H NMR analysis relative to the internal standard 1,3,5-trimethoxybenzene.

General procedure for the **RB@Ga-tpe** photocatalytic aerobic CDC reaction

N-Phenyl-1,2,3,4-tetrahydroisoquinoline (0.1 mmol, 1 equiv.), nitromethane (0.3 ml), catalyst (1.0 mol%), and H₂O (2 ml) were added to a glass reactor and irradiated using a Xe lamp at room temperature for 12 h in an air atmosphere. After the indicated time, it was extracted using ethyl acetate and concentrated under vacuum distillation. The yields were determined by ¹H NMR analysis using 1,3,5-trimethoxybenzene as an internal standard.

Data availability

All the data supporting this article have been included in the main text and the ESI.†

Author contributions

C. He and D. Li designed the research and co-wrote the manuscript. D. Li, H. Li, and J. Li performed all experiments. W. Fang carried out structural optimization calculations. X. Fu performed ESI-MS. L. Yang and X. Li assisted in analyzing the data.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was supported by the National Natural Science Foundation of China 22171033 and the Fundamental Research Funds for the Central Universities [DUT17RC(3)094].

Notes and references

- (a) T. R. Cook, Y.-R. Zheng and P. J. Stang, *Chem. Rev.*, 2013, **113**, 734–777; (b) T. R. Cook and P. J. Stang, *Chem. Rev.*, 2015,



- 115, 7001–7045; (c) D. Zhang, T. K. Ronson and J. R. Nitschke, *Acc. Chem. Res.*, 2018, **51**, 2423–2436.
- 2 (a) Y. Tamura, H. Takezawa and M. Fujita, *J. Am. Chem. Soc.*, 2020, **142**, 5504–5508; (b) M. D. Ludden, C. G. P. Taylor and M. D. Ward, *Chem. Sci.*, 2021, **12**, 12640–12650; (c) S. Hasegawa, S. L. Meichsner, J. J. Holstein, A. Baksi, M. Kasanmascheff and G. H. Clever, *J. Am. Chem. Soc.*, 2021, **143**, 9718–9723; (d) M. Ueda, N. Kishida, L. Catti and M. Yoshizawa, *Chem. Sci.*, 2022, **13**, 8642–8648; (e) L. R. Holloway, P. M. Bogie, Y. Lyon, C. Ngai, T. F. Miller, R. R. Julian and R. J. Hooley, *J. Am. Chem. Soc.*, 2018, **140**, 8078–8081; (f) R. Banerjee, D. Chakraborty and P. S. Mukherjee, *J. Am. Chem. Soc.*, 2023, **145**, 7692–7711.
- 3 (a) W.-X. Gao, H.-N. Zhang and G.-X. Jin, *Coord. Chem. Rev.*, 2019, **386**, 69–84; (b) X.-X. Gou, T. Liu, Y.-Y. Wang and Y.-F. Han, *Angew. Chem., Int. Ed.*, 2020, **59**, 16683–16689; (c) H. Wang, Y. Li, N. Li, A. Filosa and X. Li, *Nat. Rev. Mater.*, 2021, **6**, 145–167; (d) Y. Hou, Z. Zhang, S. Lu, J. Yuan, Q. Zhu, W.-P. Chen, S. Ling, X. Li, Y.-Z. Zheng, K. Zhu and M. Zhang, *J. Am. Chem. Soc.*, 2020, **142**, 18763–18768; (e) J. Dong, Y. Liu and Y. Cui, *Acc. Chem. Res.*, 2021, **54**, 194–206.
- 4 (a) M. D. Ward, C. A. Hunter and N. H. Williams, *Acc. Chem. Res.*, 2018, **51**, 2073–2082; (b) A. Galan and P. Ballester, *Chem. Soc. Rev.*, 2016, **45**, 1720–1737; (c) H. Amouri, C. Desmarts and J. Moussa, *Chem. Rev.*, 2012, **112**, 2015–2041.
- 5 (a) D. Zhang, T. K. Ronson, Y.-Q. Zou and J. R. Nitschke, *Nat. Rev. Chem.*, 2021, **5**, 168–182; (b) D. Zhang, T. K. Ronson, R. Lavendomme and J. R. Nitschke, *J. Am. Chem. Soc.*, 2019, **141**, 18949–18953; (c) P. C. Purba, M. Maity, S. Bhattacharyya and P. S. Mukherjee, *Angew. Chem., Int. Ed.*, 2021, **60**, 14109–14116; (d) D. Chakraborty, R. Saha, J. K. Clegg and P. S. Mukherjee, *Chem. Sci.*, 2022, **13**, 11764–11771.
- 6 (a) R. Saha, B. Mondal and P. S. Mukherjee, *Chem. Rev.*, 2022, **122**, 12244–12307; (b) C. J. Brown, F. D. Toste, R. G. Bergman and K. N. Raymond, *Chem. Rev.*, 2015, **115**, 3012–3035; (c) Y. Xue, X. Hang, J. Ding, B. Li, R. Zhu, H. Pang and Q. Xu, *Coord. Chem. Rev.*, 2021, **430**, 213656–221378.
- 7 (a) J.-S. Wang, K. Wu, C. Yin, K. Li, Y. Huang, J. Ruan, X. Feng, P. Hu and C.-Y. Su, *Nat. Commun.*, 2020, **11**, 4675–4684; (b) Q.-Q. Wang, S. Gonell, S. H. A. M. Leenders, M. Duerr, I. Ivanovic-Burmazovic and J. N. H. Reek, *Nat. Chem.*, 2016, **8**, 225–230.
- 8 (a) L. Zhao, X. Jing, X. Li, X. Guo, L. Zeng, C. He and C. Duan, *Coord. Chem. Rev.*, 2019, **378**, 151–187; (b) M. R. Wasielewski, *Acc. Chem. Res.*, 2009, **42**, 1910–1921.
- 9 (a) H. Sunohara, K. Koyamada, H. Takezawa and M. Fujita, *Chem. Commun.*, 2021, **57**, 9300–9930; (b) D. M. Daiton, S. R. Ellis, E. M. Nichols, R. A. Mathies, F. D. Toste, R. G. Bergman and K. N. Raymond, *J. Am. Chem. Soc.*, 2015, **137**, 10128–10131; (c) A. J. Musser, P. P. Neelakandan, J. M. Richter, H. Mori, R. H. Friend and J. R. Nitschke, *J. Am. Chem. Soc.*, 2017, **139**, 12050–12059.
- 10 (a) Y.-X. Hu, W.-J. Li, P.-P. Jia, X.-Q. Wang, L. Xu and H.-B. Yang, *Adv. Opt. Mater.*, 2020, **8**, 2000265; (b) K. Wang, K. Velmurugan, B. Li and X.-Y. Hu, *Chem. Commun.*, 2021, **57**, 13641–13654; (c) X.-M. Chen, X. Chen, X.-F. Hou, S. Zhang, D. Chen and Q. Li, *Nanoscale Adv.*, 2023, **5**, 1830–1852.
- 11 (a) M. Hao, G. Sun, M. Zuo, Z. Xu, Y. Chen, X. Y. Hu and L. Wang, *Angew. Chem., Int. Ed.*, 2020, **59**, 10095–10100; (b) J.-J. Li, H.-Y. Zhang, X.-Y. Dai, Z.-X. Liu and Y. Liu, *Chem. Commun.*, 2020, **56**, 5949–5952; (c) Y. Xia, M. Chen, S. Li, M. Li, X. Li, T. Yi and D. Zhang, *J. Mater. Chem. C*, 2022, **10**, 12332–12337; (d) Z. Lian, J. He, L. Liu, Y. Fan, X. Chen and H. Jiang, *Nat. Commun.*, 2023, **14**, 2752–2762; (e) P. Sutar, V. M. Suresh, K. Jayaramulu, A. Hazra and T. K. Maji, *Nat. Commun.*, 2018, **9**, 3587–3598.
- 12 (a) K. Acharyya, S. Bhattacharyya, H. Sepehrpour, S. Chakraborty, S. Lu, B. Shi, X. Li, P. S. Mukherjee and P. J. Stang, *J. Am. Chem. Soc.*, 2019, **141**, 14565–14569; (b) Y. Li, Y. Dong, L. Cheng, C. Qin, H. Nian, H. Zhang, Y. Yu and L. Cao, *J. Am. Chem. Soc.*, 2019, **141**, 8412–8415; (c) L. Xu, Z. Wang, R. Wang, L. Wang, X. He, H. Jiang, H. Tang, D. Cao and B. Z. Tang, *Angew. Chem., Int. Ed.*, 2020, **59**, 9908–9913.
- 13 (a) W.-J. Li, X.-Q. Wang, D.-Y. Zhang, Y.-X. Hu, W.-T. Xu, L. Xu, W. Wang and H.-B. Yang, *Angew. Chem., Int. Ed.*, 2021, **60**, 18761–18768; (b) Y.-N. Jing, S.-S. Li, M. Su, H. Bao and W.-M. Wan, *J. Am. Chem. Soc.*, 2019, **141**, 16839–16848.
- 14 (a) D. Zhang, W. Yu, S. Li, Y. Xia, X. Li, Y. Li and T. Yi, *J. Am. Chem. Soc.*, 2021, **143**, 1313–1317; (b) Z. Zhang, Z. Zhao, Y. Hou, H. Wang, X. Li, G. He and M. Zhang, *Angew. Chem., Int. Ed.*, 2019, **58**, 8862–8866; (c) J. R. Piper, L. Cletheroe, C. G. P. Taylor, A. J. Metherell, J. A. Weinstein, I. V. Sazanovich and M. D. Ward, *Chem. Commun.*, 2017, **53**, 408–411; (d) A. Kumar, R. Saha and P. S. Mukherjee, *Chem. Sci.*, 2021, **12**, 5319–5329; (e) S. Ahmed, A. Kumar and P. S. Mukherjee, *Chem. Mater.*, 2022, **34**, 9656–9665; (f) P.-P. Jia, Y.-X. Hu, Z.-Y. Peng, B. Song, Z.-Y. Zeng, Q.-H. Ling, X. Zhao, L. Xu and H.-B. Yang, *Inorg. Chem.*, 2023, **62**, 1950–1957.
- 15 D. Li, X. Liu, L. Yang, H. Li, G. Guo, X. Li and C. He, *Chem. Sci.*, 2023, **14**, 2237–2244.
- 16 (a) G. V. Oshovsky, D. N. Reinhoudt and W. Verboom, *Angew. Chem., Int. Ed.*, 2007, **46**, 2366–2393; (b) L. L. K. Taylor, I. A. Riddell and M. M. J. Smulders, *Angew. Chem., Int. Ed.*, 2019, **58**, 1280–1307.
- 17 (a) E. G. Percástegui, T. K. Ronson and J. R. Nitschke, *Chem. Rev.*, 2020, **120**, 13480–13544; (b) O. Bistri and O. Reinaud, *Org. Biomol. Chem.*, 2015, **13**, 2849–2865.
- 18 (a) P. Mal, B. Breiner, K. Rissanen and J. R. Nitschke, *Science*, 2009, **324**, 1697–1699; (b) G. Wu, Y. Chen, S. Fang, L. Tong, L. Shen, C. Ge, Y. Pan, X. Shi and H. Li, *Angew. Chem., Int. Ed.*, 2021, **60**, 16594–16599; (c) E. G. Percástegui, J. Mosquera, T. K. Ronson, A. J. Plajer, M. Kieffer and J. R. Nitschke, *Chem. Sci.*, 2019, **10**, 2006–2018; (d) P. Howlader, B. Mondal, P. C. Purba, E. Zangrando and P. S. Mukherjee, *J. Am. Chem. Soc.*, 2018, **140**, 7952–7960.
- 19 (a) H. Takezawa, K. Shitozawa and M. Fujita, *Nat. Chem.*, 2020, **12**, 574–578; (b) D. H. Leung, D. Fiedler, R. G. Bergman and K. N. Raymond, *Angew. Chem., Int. Ed.*,



- 2004, **43**, 963–966; (c) W. Cullen, M. C. Misuraca, C. A. Hunter, N. H. Williams and M. D. Ward, *Nat. Chem.*, 2016, **8**, 231–236.
- 20 (a) W. Cullen, H. Takezawa and M. Fujita, *Angew. Chem., Int. Ed.*, 2019, **58**, 9171–9173; (b) L.-X. Cai, S.-C. Li, D.-N. Yan, L.-P. Zhou, F. Guo and Q.-F. Sun, *J. Am. Chem. Soc.*, 2018, **140**, 4869–4876; (c) X. Han, C. Guo, C. Xu, L. Shi, B. Liu, Z. Zhang, Q. Bai, B. Song, F. Pan, S. Lu, X. Zhu, H. Wang, X.-Q. Hao, M.-P. Song and X. Li, *ACS Nano*, 2023, **17**, 3723–3736.
- 21 H. Wang, C. H. Liu, K. Wang, M. Wang, H. Yu, S. Kandapal, R. Brzozowski, B. Xu, M. Wang, P. Eswara, M. P. Nieh, J. Cai and X. Li, *J. Am. Chem. Soc.*, 2019, **141**, 16108–16116.
- 22 (a) J. Mei, N. L. C. Leung, R. T. K. Kwok, J. W. Y. Lam and B. Z. Tang, *Chem. Rev.*, 2015, **115**, 11718–11940; (b) X. Yan, T. R. Cook, P. Wang, F. Huang and P. J. Stang, *Nat. Chem.*, 2015, **7**, 342–348; (c) X. Yan, M. Wang, T. R. Cook, M. Zhang, M. L. Saha, Z. Zhou, X. Li, F. Huang and P. J. Stang, *J. Am. Chem. Soc.*, 2016, **138**, 4580–4588; (d) V. M. Suresh, A. De and T. K. Maji, *Chem. Commun.*, 2015, **51**, 14678–14681.
- 23 (a) S.-D. Wang, C.-L. Lai, Y.-X. Zhang, S.-T. Bao, K.-L. Lv and L.-L. Wen, *J. Mater. Chem. A*, 2022, **10**, 20975–20983; (b) M. Forchetta, F. Sabuzi, L. Stella, V. Conte and P. Galloni, *J. Org. Chem.*, 2022, **87**, 14016–14025.
- 24 (a) Y. Zhi, S. Ma, H. Xia, Y. Zhang, Z. Shi, Y. Mu and X. Liu, *Appl. Catal., B*, 2019, **244**, 36–44; (b) Y. Cheng, W. Ji, X. Wu, X. Ding, X. Liu and B. Han, *Appl. Catal., B*, 2022, **306**, 121110–121122.
- 25 (a) C.-Q. Ma, X.-L. Li, N. Han, Y. Wang, R.-Z. Wang, S. Yu, Y.-B. Wang and L.-B. Xing, *J. Mater. Chem. A*, 2022, **10**, 16390–16395; (b) Y. Wang, C.-Q. Ma, X.-L. Li, R.-Z. Dong, H. Liu, R.-Z. Wang, S. Yu and L.-B. Xing, *J. Mater. Chem. A*, 2023, **11**, 2627–2633.

