

Cite this: *Chem. Sci.*, 2023, 14, 13908

All publication charges for this article have been paid for by the Royal Society of Chemistry

# Dimethyl carbonate synthesis from CO<sub>2</sub> and methanol over CeO<sub>2</sub>: elucidating the surface intermediates and oxygen vacancy-assisted reaction mechanism†

Dragos Stoian,<sup>ab</sup> Toshiyuki Sugiyama,<sup>c</sup> Atul Bansode,<sup>af</sup> Francisco Medina,<sup>b</sup> Wouter van Beek,<sup>e</sup> Jun-ya Hasegawa,<sup>bc</sup> Akira Nakayama<sup>bd\*cd</sup> and Atsushi Urakawa<sup>ib\*af</sup>

Surface intermediate species and oxygen vacancy-assisted mechanism over CeO<sub>2</sub> catalyst in the direct dimethyl carbonate (DMC) synthesis from carbon dioxide and methanol are suggested by means of transient spectroscopic methodologies in conjunction with multivariate spectral analysis. How the two reactants, *i.e.* CO<sub>2</sub> and methanol, interact with the CeO<sub>2</sub> surface and how they form decisive surface intermediates leading to DMC are unraveled by DFT-based molecular dynamics simulation by precise statistical sampling of various configurations of surface states and intermediates. The atomistic simulations and uncovered stability of different intermediate states perfectly explain the unique DMC formation profile experimentally observed upon transient operations, strongly supporting the proposed oxygen vacancy-assisted reaction mechanism.

Received 25th August 2023  
Accepted 19th November 2023

DOI: 10.1039/d3sc04466a

rsc.li/chemical-science

## Introduction

The increasing interest in dimethyl carbonate (DMC) has been witnessed in the last decades for its usefulness: polar solvent for paints and coatings, methylating and carbonylating agent in organic synthesis, electrolytes in Li-ion batteries, and an appropriate substitute for methyl *tert*-butyl ether (MTBE) as a fuel additive owing to its high oxygen content.<sup>1–7</sup> While one of the major synthesis paths of DMC is *via* the reaction of methanol with phosgene (COCl<sub>2</sub>), nowadays the industrially

recognized processes involve either oxidative carbonylation reactions using CO (Enichem, Ube and Bayer AG), transesterification reactions of organic carbonates with methanol (Asahi Kasei), or a two-step urea methanolysis method developed by Catalytic Distillation Technologies, Inc.<sup>8</sup> Despite these improvements, it can be easily understood why a safer, more eco-efficient and economic pathway for DMC synthesis is desired. The development of the direct reaction between CO<sub>2</sub> and short chain alcohols, particularly methanol (MeOH) and ethanol (EtOH), for the synthesis of organic carbonates such as DMC or diethyl carbonate (DEC) (Scheme 1, DMC synthesis) has drawn great attention in the light of urged CO<sub>2</sub> chemical fixation, green chemistry (high atom efficiency processes), and safety by replacing the highly toxic and corrosive phosgene molecule by CO<sub>2</sub> as carbonyl source.

In the last 20 years, various homogeneous and heterogeneous catalysts were reported for the direct carboxylation reaction of methanol using CO<sub>2</sub>. Heterogeneous catalysts are more widely investigated and different materials have been tested under both batch and continuous operation. Among them, zirconia (ZrO<sub>2</sub>), ceria (CeO<sub>2</sub>), and ZrO<sub>2</sub>–CeO<sub>2</sub> solid solutions<sup>9–11</sup> have been reported as the most effective catalysts in the direct

<sup>a</sup>Institute of Chemical Research of Catalonia (ICIQ), The Barcelona Institute of Science and Technology (BIST), Av. Països Catalans 16, 43007 Tarragona, Spain

<sup>b</sup>Department of Chemical Engineering, University Rovira i Virgili, Av. Països Catalans 26, 43007 Tarragona, Spain


<sup>c</sup>Institute for Catalysis, Hokkaido University, Sapporo 001-0021, Japan

<sup>d</sup>Department of Chemical System Engineering, The University of Tokyo, Tokyo 113-8656, Japan. E-mail: nakayama@chemsys.t.u-tokyo.ac.jp

<sup>e</sup>The Swiss-Norwegian Beamlines (SNBL) ESRF – The European Synchrotron Radiation Facility, BP 220, F-38043 Grenoble, France

<sup>f</sup>Catalysis Engineering, Department of Chemical Engineering, Delft University of Technology, Van der Maasweg 9, 2629 HZ Delft, The Netherlands. E-mail: A. Urakawa@tudelft.nl

† Electronic supplementary information (ESI) available: A complete description of the reagents and lab-based/synchrotron setup is given. Multivariate curve resolution technique is briefly presented together with more results on its application over XAS/Raman data. Computational details for the DFT calculations and MD simulations, adsorption structures for the reagents and reaction intermediates and a comprehensive discussion are also included. See DOI: <https://doi.org/10.1039/d3sc04466a>



Scheme 1 Direct DMC synthesis from CO<sub>2</sub> and methanol.



DMC synthesis, while other catalyst materials afforded no or very little formation of DMC.<sup>12</sup> Generally, the presence of both acidic and basic sites is required for the activation of CO<sub>2</sub> and methanol. Indeed, the aforementioned reported active catalysts possess both the acidic and basic properties.<sup>13</sup> Nevertheless, in practice the reaction is highly thermodynamically limited and the DMC yield can be enhanced only up to about 1% even under thermodynamically favourable high-pressure conditions (*ca.* 400 bar).<sup>14</sup> Recently, a drastic improvement in DMC yield (>90%) was reported by Tomishige *et al.* over CeO<sub>2</sub> as the unique catalyst through *in situ* dehydration where 2-cyanopyridine (2-CP) serves as organic dehydrating agent to remove the water byproduct (Scheme 1). CeO<sub>2</sub> functions as catalyst in both DMC synthesis and dehydration reaction optimally at *ca.* 120 °C. This strategy has been demonstrated for batch as well as continuous operations.<sup>14–17</sup> It is noteworthy that the rate determining step of the DMC synthesis is unaltered by the presence of 2-CP. This implies that understanding the simpler reaction system without the dehydrating agent would be of direct relevance in understanding more complex yet more practical system with the dehydrating agent.<sup>16</sup>

The unique catalytic performance of CeO<sub>2</sub> in this reaction may originate from the synergy between its acid-base and redox properties. Izumi *et al.* studied the reducibility of CeO<sub>2</sub> promoted with Cu (0.1 to 0.5 wt%) by X-ray absorption spectroscopy (XAS) after high temperature reduction treatment (400 °C) and subsequent CO<sub>2</sub> adsorption. They suggested that the partial reduction of Ce<sup>4+</sup> sites to Ce<sup>3+</sup> may be beneficial for DMC formation.<sup>18</sup> Also, Aresta *et al.* correlated by *ex situ* X-ray photoelectron spectroscopy (XPS) the origin of catalyst deactivation, thus the activity, with the oxidation state of Ce.<sup>19,20</sup> In a more recent study, Li *et al.* synthesized Zr-doped CeO<sub>2</sub> nano-rods, and they linked the DMC production rate to the highest number of oxygen vacancies (*i.e.* extracted from *ex situ* Raman and XPS measurements; *versus* bare CeO<sub>2</sub>) that allows an increased CO<sub>2</sub> adsorption rate.<sup>21</sup> Despite all these indications, the contribution and importance of the redox properties or surface defects of CeO<sub>2</sub> in the reaction has not been proven under working (*operando*) reaction conditions. Particularly, the reaction is commonly performed at relatively low temperatures (100–150 °C) where the reduction of surface and bulk CeO<sub>2</sub> is unlikely to occur according to temperature programmed reduction studies<sup>22–24</sup> and the detection of electronic structure change of Ce, if any, is expected to be challenging. Furthermore, no *operando* spectroscopic investigation has been reported bridging the type of surface species present under reaction conditions with DMC formation by simultaneous detection of the product concentration.

Following this background, in this work we elucidate the surface chemical intermediate, at its energetically resting state, leading to DMC formation by means of *operando* diffuse reflectance infrared Fourier transform spectroscopy (DRIFTS) coupled with multivariate spectral analysis<sup>25–27</sup> which enables unreferenced spectral separations (ESI, Fig. S1†). Furthermore, through density functional theory (DFT) calculations, XAS and Raman spectroscopy, the critical roles of surface oxygen

vacancies of CeO<sub>2</sub> at the rate limiting step are uniquely unravelled.

## Results and discussions

Fig. 1 presents time-resolved *operando* DRIFT spectra and DMC concentration profile under a periodic concentration change of methanol (16.5 vol% in He, the first half period of 128 s) and CO<sub>2</sub> (the second half period of 128 s) performed at 120 °C (averaged over 8 periods to improve S/N). The MS signal (Fig. 1, left) shows that DMC was formed under the studied condition. The production level of DMC increased upon switching from CO<sub>2</sub> to methanol, reaching a constant level after *ca.* 40 s. Interestingly, the DMC production was boosted by *ca.* 4 times upon switching from methanol to CO<sub>2</sub> and then gradually ceased with time, almost completely under the flow of CO<sub>2</sub>. The stable activity after 40 s is at the same level as that of the steady-state activity of DMC formation by passing MeOH + CO<sub>2</sub> (ESI, Fig. S3†). This means that MeOH *vs.* CO<sub>2</sub> perturbation creates favourable condition for DMC formation, enhancing the formation rate by 4 times compared to the steady-state activity. The differential DRIFT spectra in the low frequency region from 950 to 1800 cm<sup>-1</sup> (Fig. 1, right; the last spectrum of the period, *i.e.*, at the end of the CO<sub>2</sub> period, was used as the background) shows the characteristic C–O stretching vibrations of bridged and terminal methoxy species appearing at *ca.* 1060 and 1120 cm<sup>-1</sup>, respectively,<sup>10</sup> as positive bands (in red) when the atmosphere was switched to methanol. Likewise, the absorbance of the methoxy bands (hence the concentration of methoxy species) for the MeOH + CO<sub>2</sub> *vs.* CO<sub>2</sub> experiment is *ca.* 4 time less compared to the case of MeOH *vs.* CO<sub>2</sub>, well in-line with the semi-quantitative analysis of the MS profiles and the observation from Fig. 1, left which tells us that methanol adsorption needs to take place first in order to activate the DMC formation (ESI, Fig. S4† for more detailed discussion).

At the same time, several negative bands characteristic of carbonates/bicarbonates were observed in the region from 1150–1800 cm<sup>-1</sup> under the flow of MeOH. According to literature, these bands originate from carboxylate and protonated carboxylate species on the surface of the catalyst (1695 cm<sup>-1</sup>), bridged (bi)carbonates (1235 and 1645 cm<sup>-1</sup>), and monodentate

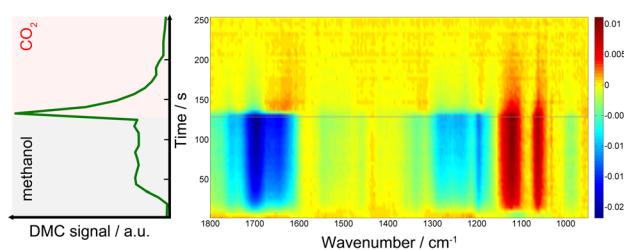


Fig. 1 (left) MS signal of DMC ( $m/z = 59$ ) and (right) time-resolved DRIFT spectra taken during methanol (the first half period) *vs.* CO<sub>2</sub> (the second half period) concentration perturbation experiment performed at 120 °C at 7 ml min<sup>-1</sup>. The time-axes (*y*-axis) of both figures are identical. The DRIFT spectra were calculated taking the last spectrum in the CO<sub>2</sub> atmosphere as background.



and bidentate carbonates ( $1336$ ,  $1458$   $\text{cm}^{-1}$  and  $1282$ ,  $1548$   $\text{cm}^{-1}$ , respectively).<sup>10,28–31</sup> The results clearly indicate that carbonates/bicarbonates formed under  $\text{CO}_2$  atmosphere were replaced (thus the bands appear negative) by the methoxy species under methanol atmosphere, and *vice versa* under  $\text{CO}_2$  atmosphere. At first glance, the DRIFT spectra do not show signatures of transient surface species whose concentration is similar to that of DMC, except a few slightly positive signals at *ca.*  $1310$  and  $1630$   $\text{cm}^{-1}$  appearing upon switching to  $\text{CO}_2$ . This sort of ambiguousness in spectral analysis is often encountered and arises from overlapping peaks and also impossibility to deconvolute the spectral contributions of different chemical species due to the unavailability of proper reference spectra of the chemical species that are only present/detected under reaction conditions and/or under transient conditions.

To overcome this limitation, multivariate spectral analysis was employed to disentangle overlapping peaks into the spectra of “kinetically pure” components (*i.e.*, surface species). Besides the spectral separation, it yields conveniently the corresponding concentration profiles of the components. Provided that the data quality is good in terms of S/N, the multivariate spectral analysis can overpower another famous technique used for detection of minor species, *i.e.*, modulation excitation spectroscopy (MES, using phase sensitive detection), especially when there is a high degree of spectral overlap and species with extremely different kinetics are involved. For more details and comparison between the multivariate spectral analysis and MES, the reader is redirected elsewhere.<sup>26,32–34</sup> Fig. 2 shows the results of the multivariate spectral analysis on the DRIFT spectra shown in Fig. 1. For comparison, the results obtained *via* MES analysis are included in the ESI, Fig. S5.† The analysis identified three kinetically distinct components. Most strikingly, the analysis could separate the spectral component (Fig. 2, green) with the concentration profile perfectly matching with that of DMC (Fig. 1, left). The other two components show characteristic features of (i) methoxy species (Fig. 2, black) and (ii) carbonate/bicarbonate species (Fig. 2, red). The corresponding concentration profiles of these components (Fig. 2, right) obviously reflect the atmosphere of the gas phase.

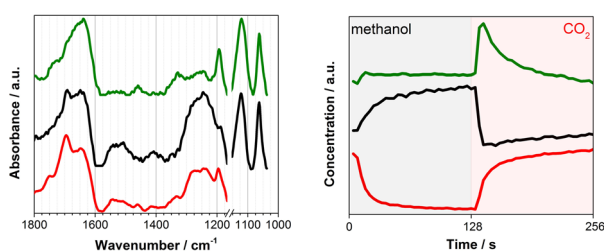


Fig. 2 (left) Three components spectra and (right) the corresponding concentration profiles obtained by multivariate spectral analysis applied on the DRIFT spectra shown in Fig. 1 (the first half is methanol and the second half is  $\text{CO}_2$  atmosphere). To ease the data analysis and improve component separation, the spectral analysis has been performed on two separate regions of methoxy (below  $1170$   $\text{cm}^{-1}$ ) and carbonates (above  $1180$   $\text{cm}^{-1}$ ). Both spectra and concentration profiles are normalized for clarity.

*In situ* infrared and Raman studies reported by Tomishige, Bell and their co-workers over  $\text{ZrO}_2$  materials suggested the formation of monomethyl carbonate (MMC,  $\text{CH}_3\text{O}-\text{COO}-\text{Zr}$ ) as possible intermediate species through the reaction between methoxy species ( $\text{CH}_3\text{O}^-$ ) and  $\text{CO}_2$ .<sup>35–37</sup> MMC further reacts with methanol (methoxy) to afford DMC. Later, it was indicated that the reaction proceeds *via* the same intermediate (*i.e.* MMC) over  $\text{CeO}_2$  catalysts.<sup>10,16</sup> There are also reports supporting the existence of a different intermediate like carbomethoxide ( $\text{CH}_3\text{OCO}-\text{Ce}$ ) species as suggested by Wang *et al.*<sup>28</sup> The spectral characteristics of the captured intermediate (Fig. 2, green) whose concentration profile resembles that of gas phase DMC generally show the mixed features of methoxy ( $1060$  and  $1120$   $\text{cm}^{-1}$ ) and (bi)carbonates (*e.g.*  $1200$ – $1800$   $\text{cm}^{-1}$ ), although they are somehow different especially in the region of  $1200$ – $1600$   $\text{cm}^{-1}$  where the characteristic bands of MMC are expected to appear according to the literature.<sup>10,20,28,38</sup> More precisely, Lavalley *et al.* assigned the two bands we observed at *ca.*  $1330$  and  $1460$   $\text{cm}^{-1}$  to a coupling between the bending mode of  $\text{CH}_3$  and the stretching vibration of  $\text{OCO}$ .<sup>39</sup> This clearly indicates that the captured intermediate is MMC or species alike. The spectral features of the intermediate (Fig. 2, green) in the methoxy region appear similarly to those of methoxy species (Fig. 2, black). A closer look verifies that they are similar but there are noticeable differences especially in the band of terminal methoxy at *ca.*  $1120$   $\text{cm}^{-1}$  of the intermediate, showing a broadening and a small shift towards lower vibrational frequency (ESI, Fig. S2†). This implies that the terminal methoxy has reacted or is interacting with the  $\text{CO}_2$  molecule trapped on the surface, resulting in the red shift. Also, intriguingly the species responding to the gas-phase methanol concentration (Fig. 2, black) show the spectral features of (bi) carbonates in the region  $1200$ – $1800$   $\text{cm}^{-1}$ . This is indicative of the formational correlation of methoxy species with specific surface (bi)carbonate species. The dissociation of  $\text{MeOH}$  into  $\text{MeO}$  and  $\text{H}$  is known<sup>10</sup> to take place upon methanol adsorption over  $\text{CeO}_2$  and this surface adsorbed  $\text{H}$  may lead to more pronounced formation of bicarbonates from carbonates (see the discussion below for DFT calculations) and the spectral feature of the methoxy species may reflect the accompanied formation of bicarbonate surface species since the multivariate spectral analysis cannot disentangle spectral components behaving kinetically identical. A similar discussion for the high frequency region (above *ca.*  $2000$   $\text{cm}^{-1}$ ) is presented in the ESI (Fig. S6 and S7†) including the difference DRIFT spectra and the corresponding multivariate spectral analysis results.

Under similar transient conditions we looked into the change in the oxidation state of  $\text{Ce}$  by XAS at  $\text{Ce K}$  and  $\text{L3-edges}$  and structural changes by Raman spectroscopy. Under oxidation ( $\text{O}_2$ ) and reduction ( $\text{H}_2$ ) treatment at high temperature ( $350$   $^\circ\text{C}$ ), the multivariate spectral analysis on the XAS and Raman data could clearly extract the redox features of  $\text{CeO}_2$  (ESI, Fig. S8–S10†), whereas these redox features could not be observed at the reaction temperature of  $100$ – $150$   $^\circ\text{C}$  which was obviously too low for the redox to take place as expected. Although we could not detect spectral changes in the bulk-sensitive XAS under the transient reaction conditions of



MeOH vs. CO<sub>2</sub> flow, there was a clear change in the F<sub>2g</sub> Raman active mode at *ca.* 460 cm<sup>-1</sup>, corresponding to the symmetric breathing of O<sup>2-</sup> atoms vibrations around the Ce<sup>4+</sup> cations (Fig. 3). The width and position of this band is known to be extremely sensitive to any structural disorder of the O-sub-lattice.<sup>40</sup> Multivariate spectral analysis on the Raman data disentangled the two spectral components with contrasting concentration profiles: one increasing upon CO<sub>2</sub> exposure which is obviously assigned to the band associated with the Ce<sup>4+</sup> state (Fig. 3, Component 1, red), and the other increasing with methanol with the band feature slightly red-shifted and broadened (Fig. 3, Component 2, black). These changes are in accordance with the reports on CeO<sub>2</sub>-based materials under reduction-oxidation cycles.<sup>41-43</sup> Yoshimura *et al.* use the changes in Raman-allowed F<sub>2g</sub> mode (*i.e.* shifts to lower energies, and the line shape getting progressively asymmetric with the crystal size decrease) in a study about the identification of defects in ceria-based nanocrystals by UV resonance Raman spectroscopy.<sup>44</sup> This subtle change took place on the surface of the material and therefore could not be measured by XAS. Likewise, the change was less obvious when a longer wavelength excitation laser (785 nm) was used in Raman since in this case we sample more bulk of the material (ESI, Fig. S11†). Given the magnitude of the spectral change and the mild reaction conditions it becomes rather difficult to state the existence of a complete Ce<sup>4+</sup> ⇌ Ce<sup>3+</sup> cycle despite a recent publication by Tomishige *et al.* which reported the redox properties of CeO<sub>2</sub> catalysts in organic reactions (*i.e.* synthesis of imines from alcohols and amines) at temperature as low as 30 °C.<sup>45</sup> In literature, Mullins *et al.* probed the surface sites of CeO<sub>2</sub> nanocrystals with well-defined surface planes *via* methanol adsorption, and they observed slight reduction of the rods (110) and cubes (100) surfaces at room temperature by a UV Raman study. In addition, surface science reports on methanol adsorption over thin-film model CeO<sub>2</sub> catalyst support the reduction phenomenon occurring in the topmost oxide layers even at ambient or sub-ambient temperatures (Mullins *et al.* and Skala *et al.*).<sup>46-48</sup> Based on what has been reported, the creation of a nonstoichiometric CeO<sub>2-δ</sub> surface *via* the formation of some surface and subsurface O-vacancies (*i.e.* defective surface) is possible and explains the Raman results. Such defective surface formation would lead to a more electron

deficient or more electron rich CeO<sub>2</sub> state depending on the gas atmosphere. Glatzel *et al.* have previously invoked this picture of an electron sponge for CeO<sub>2</sub> nanoparticles studied by HERFD-XAS.<sup>49</sup> They found an increase of the interatomic distances between Ce and O during the catalytic decomposition of hydrogen peroxide while stating that the redox partner is not a local Ce<sup>3+</sup> site, but the electron density that is received and released during the reaction is delocalized over the atoms of the nanoparticles. Furthermore, the emergence of two bands in the 2000–2250 cm<sup>-1</sup> region of the DRIFT spectra that can be linked to Ce<sup>3+</sup> surface sites formation induced by methanol adsorption over CeO<sub>2</sub> can further support the Raman results and thus methanol adsorption-induced Ce<sup>3+</sup> formation (ESI, Fig. S6†) which is important for the enhanced DMC formation (Fig. 1, left, Fig. S3†).

The mechanistic investigation by DFT calculations strongly supports our experimental observations and clarifies atomistic and electronic insights. The computational details are described in ESI.† While methanol adsorption occurs preferentially *via* the dissociation of the molecule into CH<sub>3</sub>O<sup>-</sup> and H<sup>+</sup>, the favoured and most stable adsorption state of CO<sub>2</sub> is represented by a monodentate carbonate species involving a covalent bond between the C atom of the CO<sub>2</sub> molecule and surface O atoms belonging to CeO<sub>2</sub> (see ESI, Fig. S12† for adsorption structures).

Here, we considered the two reaction pathways for DMC formation, one starting from an adsorbed CO<sub>2</sub> molecule that is a monodentate carbonate species, CO<sub>2</sub>(m) (Path A), and the other starting from the dissociative adsorption of a methanol molecule (Path B), as shown in Fig. 4. In Path A, this monodentate structure is attacked by the methoxy species (CH<sub>3</sub>O<sup>-</sup>), leading to the formation of surface monomethyl carbonate species (MMC<sub>s</sub>). After removal of the hydroxyl group by accepting a proton, an intermediate species (INT\_1) is formed by releasing a water molecule. Subsequently, another methoxy moiety attacks the carbon atom, forming an intermediate structure INT\_2, and then the carbon and surface oxygen bond is broken to release a DMC molecule. In Path B, a CO<sub>2</sub> molecule

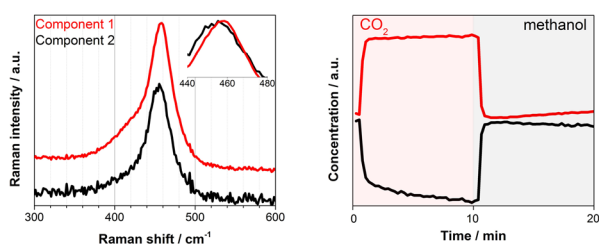


Fig. 3 Multivariate spectral analysis applied for F<sub>2g</sub> band of CeO<sub>2</sub> during DMC synthesis experiment (CO<sub>2</sub> vs. methanol) at 140 °C. The Raman measurement was performed with a 532 nm laser (green). Both spectra (left) and concentration (right) profiles are normalized for clarity.

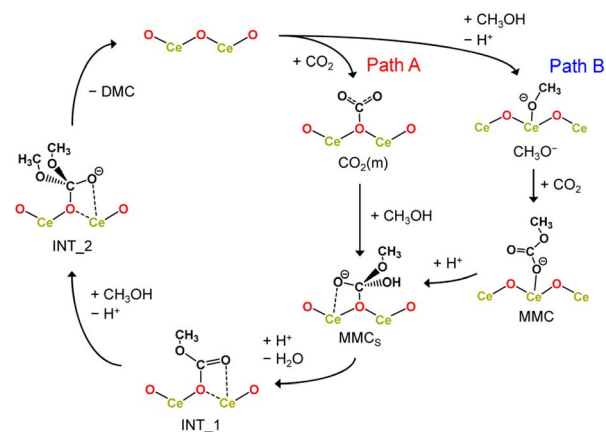


Fig. 4 Reaction mechanism of DMC formation from CO<sub>2</sub> and methanol. Path A starts with an adsorbed CO<sub>2</sub> molecule while Path B starts from the dissociative adsorption of a methanol molecule.



is inserted into the adsorbed methoxy species, leading to the formation of monomethyl carbonate (**MMC**) species. This **MMC** species is nucleophilically attacked by the surface oxygen atom, which results in the formation of **MMC<sub>s</sub>** by accepting a proton from nearby methanol molecule. The subsequent reaction pathway from **MMC<sub>s</sub>** is the same as that in Path A.

Fig. 5 shows the free energy profiles along the reaction pathways. In the first step of Path A, the  $\text{CO}_2$  molecule is adsorbed on the  $\text{CeO}_2$  surface with a small barrier of  $21 \text{ kJ mol}^{-1}$  ( $\text{CO}_2^* \rightarrow \text{CO}_2(\text{m})$ ), forming a monodentate structure  $\text{CO}_2(\text{m})$ . Then, the surface monomethyl carbonate species (**MMC<sub>s</sub>**) is generated with an activation energy of  $77 \text{ kJ mol}^{-1}$  ( $\text{CO}_2(\text{m}) \rightarrow \text{MMC}_s$ ). Before reaching to this transition state configurations, we find that a proton is transferred from a neighbouring methanol molecule to the surface carbonate species, resulting in the bicarbonate species. This bicarbonate species is attacked by methoxy moiety to form **MMC<sub>s</sub>** structure (see the inset of  $\text{CO}_2(\text{m}) \rightarrow \text{MMC}_s$  in Fig. 5 and the snapshot near the transition state structure is shown in ESI, Fig. S13†). The resulting **MMC<sub>s</sub>** structure is less stable, and the carbomethoxy species (**INT\_1.1**) is formed with a small barrier of  $13 \text{ kJ mol}^{-1}$  by eliminating a water molecule (snapshot near the transition state structure is also provided in ESI, Fig. S13†). This carbomethoxy configuration is meta-stable and it readily changes its configuration with a more stable monomethyl carbonate state accompanied by the creation of an oxygen vacancy during the MD simulation (shown as **INT\_1.2**, and snapshot is provided in ESI, Fig. S13†). This intermediate is further attacked by another methoxy moiety, leading to the formation of **INT\_2** with an activation barrier of  $49 \text{ kJ mol}^{-1}$ . During this attack of methoxy species, the surface vacancy is refilled by the oxygen atom. The final step is a bond cleavage between the carbon and surface oxygen atom, and this step requires an activation energy of  $52 \text{ kJ mol}^{-1}$ . The free energy difference between **INT\_1** and the transition state between

**INT\_2** and **DMC\*** is estimated to be  $87 \text{ kJ mol}^{-1}$ , which is comparable to the experimental value of  $73 \text{ kJ mol}^{-1}$  reported in ref. 16.

Next, the reaction mechanism of Path B is analysed in detail. In the first step, the monomethyl carbonate species is formed by the reaction between a dissociated methanol and  $\text{CO}_2$  with an activation barrier of  $37 \text{ kJ mol}^{-1}$  ( $\text{CH}_3\text{O}^* \rightarrow \text{MMC}$ ). The conformation of **MMC** species during the MD simulation is close to the adsorption structure of DM1 or DM2 shown in ESI, Fig. S12,† where in the MD simulations the hydrogen bond of the carbonyl group is observed with hydrogen in the methanol molecule (snapshot is provided in ESI, Fig. S13†). The next step is a nucleophilic attack of the surface oxygen atom to the carbon atom accompanying a proton transfer to the carboxylate group (**MMC**  $\rightarrow$  **MMC<sub>s</sub>**). This process requires activation energy of  $82 \text{ kJ mol}^{-1}$ .

The gaseous product (**DMC**) profile (Fig. 1) is in good agreement with the mechanistic insights obtained by the DFT calculations. Upon switching from  $\text{CO}_2$  to methanol, there is an induction period before reaching a stable **DMC** production. This clearly indicates a strong  $\text{CO}_2$  adsorption to the surface sites; it takes some time to replace the strongly adsorbed  $\text{CO}_2$  molecules by methanol. This competitive adsorption and replacement by methoxy retards the **DMC** formation and also implies that the methoxy and  $\text{Ce}^{3+}$  generation are crucial for the reactivity towards **DMC** formation. Also, the spectral features of bicarbonates in the region  $1200\text{--}1800 \text{ cm}^{-1}$  in the methanol atmosphere (Fig. 2, black) correspond to the bicarbonate species before the formation of **MMC<sub>s</sub>** structure. On the other hand, upon switching from methanol to  $\text{CO}_2$  there is an immediate formation of **DMC** with a boost in productivity, demonstrating that for the  $\text{CO}_2$  molecules it is much easier to kick out the previously adsorbed methanol from the surface through **MMC** intermediate. After that, **DMC** production ceases quite fast suggesting a very strong  $\text{CO}_2$  absorption to  $\text{CeO}_2$  surface and the lack of any methoxy species in the proximity. Based on the discussion above, we can also conclude that the stability of the intermediate (**INT\_1.2**) and the creation of a defective surface is the key to make  $\text{CeO}_2$  an efficient catalyst for the direct synthesis of **DMC** while the reaction invokes the image of a Langmuir–Hinshelwood type of mechanism with methanol and  $\text{CO}_2$  molecules adsorbed in the immediate vicinity of a Ce–O pair.

## Conclusions

In summary, the present study describes the *in situ* creation of a defective  $\text{CeO}_2$  surface and its involvement in the gas phase **DMC** synthesis from  $\text{CO}_2$  and methanol by using a combination of experimental and theoretical tools. While methanol seems to increase the electron density around Ce sites,  $\text{CO}_2$  behaves as an oxidizing agent leading to fully oxidized  $\text{Ce}^{4+}$ . Furthermore, a boost in **DMC** production is observed when  $\text{CO}_2$  is passed over methoxy covered surface. The surface intermediate species directly correlated with **DMC** formation was elucidated by *operando* DRIFTS with the aid of the multivariate spectral analysis. It shows the feature of both methoxy and (bi)

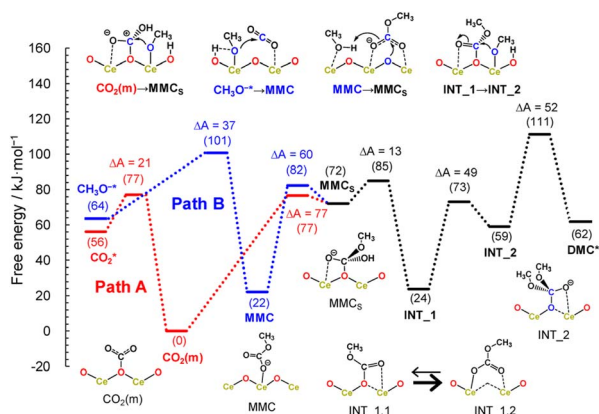


Fig. 5 Free energy profiles along the two reaction pathways. The free energy of the monodentate structure  $\text{CO}_2(\text{m})$  is set to zero, and relative energy is shown in parenthesis. Activation energy ( $\Delta A$  in  $\text{kJ mol}^{-1}$ ) in each step is also included. The inset on the bottom (**INT\_1** = **INT\_1.1**  $\rightarrow$  **INT\_1.2**) evidences the key step in the stabilization of the reaction intermediate and formation of an O-vacancy in the catalytic cycle over  $\text{CeO}_2$ .



carbonates, in good agreement with the reported structure of monodentate methyl carbonate. We demonstrate, for the first time ever, the reconfiguration of this species on the CeO<sub>2</sub> surface *via* a vacancy-assisted mechanism, observation which correlates well with the *operando* Raman results.

Ultimately, direct DMC synthesis from methanol and CO<sub>2</sub> is un-equivocally driven forward by the presence of neighbouring acid–base pairs over CeO<sub>2</sub> surface. Nevertheless, the influence of O-vacancies in the reaction mechanism and the extraordinary redox (surface) properties of this oxide cannot be neglected anymore. It has already been shown that an increased surface reducibility which can ease the formation of surface defect sites – responsible for the intermediate stabilization – plays critical roles in the overall reaction mechanism involving the *in situ* water removal by 2-CP molecules (while the DMC formation mechanism is unchanged by the dopants and mainly catalysed by CeO<sub>2</sub> surface).<sup>50</sup> Hence, this study establishes new directions for designing better and more stable catalysts for this newly implemented and highly active route to DMC synthesis by direct methanol carboxylation reaction.

## Data availability

Data will be made available on request.

## Author contributions

D. S. performed all experiments and T. S. performed the DFT-based calculations. A. B. and W. v. B. supported synchrotron X-ray-based experiments. F. M., J. H., A. N. and A. U. conceived and supervised this work. D. S., T. S., A. N. and A. U. analysed the data. The manuscript was drafted with the support and contribution from all authors.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

We thank Generalitat de Catalunya for financial support through CERCA Programme and recognition (2014 SGR 893) and thank MINECO (CTQ2016-75499-R (FEDER-UE)) for financial support through Severo Ochoa Excellence Accreditation 2014–2018 (SEV-2013-0319). The authors acknowledge the financial support by PRESTO from Japan Science and Technology Agency (JST) (Grant Number JPMJPR16S8). A part of this work is based on results obtained from a project commissioned by the New Energy and Industrial Technology Development Organization (NEDO). A part of the calculations was performed on supercomputers at RCCS (Okazaki, project no. 23-IMS-C172), RIIT (Kyushu Univ.), and CCMS, IMR (Tohoku Univ., proposal no. 202212-SCKXX-0002).

## Notes and references

- 1 A.-A. G. Shaikh and S. Sivaram, *Chem. Rev.*, 1996, **96**, 951–976.
- 2 T. Sakakura, J.-C. Choi and H. Yasuda, *Chem. Rev.*, 2007, **107**, 2365–2387.
- 3 Y. Ono, *Appl. Catal. Gen.*, 1997, **155**, 133–166.
- 4 M. Aresta and E. Quaranta, *ChemTech*, 1997, **27**, 32–40.
- 5 N. Keller, G. Rebmann and V. Keller, *J. Mol. Catal. Chem.*, 2010, **317**, 1–18.
- 6 D. Delledonne, F. Rivetti and U. Romano, *Appl. Catal. Gen.*, 2001, **221**, 241–251.
- 7 M. A. Pacheco and C. L. Marshall, *Energy Fuels*, 1997, **11**, 2–29.
- 8 I. Garcia-Herrero, R. M. Cuéllar-Franca, V. M. Enríquez-Gutiérrez, M. Alvarez-Guerra, A. Irabien and A. Azapagic, *ACS Sustain. Chem. Eng.*, 2016, **4**, 2088–2097.
- 9 K. Tomishige, T. Sakaihorii, Y. Ikeda and K. Fujimoto, *Catal. Lett.*, 1999, **58**, 225–229.
- 10 Y. Yoshida, Y. Arai, S. Kado, K. Kunimori and K. Tomishige, *Catal. Today*, 2006, **115**, 95–101.
- 11 K. Tomishige, Y. Furusawa, Y. Ikeda, M. Asadullah and K. Fujimoto, *Catal. Lett.*, 2001, **76**, 71–74.
- 12 K. Tomishige, *Curr. Top. Catal.*, 2002, **3**, 81–101.
- 13 M. G. Cutrufello, I. Ferino, V. Solinas, A. Primavera, A. Trovarelli, A. Auroux and C. Picciau, *Phys. Chem. Chem. Phys.*, 1999, **1**, 3369–3375.
- 14 A. Bansode and A. Urakawa, *ACS Catal.*, 2014, **4**, 3877–3880.
- 15 M. Honda, M. Tamura, Y. Nakagawa, S. Sonehara, K. Suzuki, K. Fujimoto and K. Tomishige, *ChemSusChem*, 2013, **6**, 1341–1344.
- 16 M. Honda, M. Tamura, Y. Nakagawa, K. Nakao, K. Suzuki and K. Tomishige, *J. Catal.*, 2014, **318**, 95–107.
- 17 D. Stoian, A. Bansode, F. Medina and A. Urakawa, *Catal. Today*, 2017, **283**, 2–10.
- 18 S. Wada, K. Oka, K. Watanabe and Y. Izumi, *Front. Chem.*, 2013, **1**, 1–8.
- 19 M. Aresta, A. Dibenedetto, C. Pastore, C. Cuocci, B. Aresta, S. Cometa and E. De Giglio, *Catal. Today*, 2008, **137**, 125–131.
- 20 M. Aresta, A. Dibenedetto, C. Pastore, A. Angelini, B. Aresta and P. Imre, *J. Catal.*, 2010, **269**, 44–52.
- 21 B. Liu, C. Li, G. Zhang, X. Yao, S. S. C. Chuang and Z. Li, *ACS Catal.*, 2018, **8**, 10446–10456.
- 22 A. Trovarelli, *Comments Inorg. Chem.*, 1999, **20**, 263–284.
- 23 S. Kumar Meher and G. Ranga Rao, *ACS Catal.*, 2012, **2**, 2795–2809.
- 24 H. C. Yao and Y. F. Yu, *J. Catal.*, 1984, **86**, 254–265.
- 25 A. Malik, A. de Juan and R. Tauler, in *40 Years of Chemometrics – From Bruce Kowalski to the Future*, American Chemical Society, 2015, vol. 1199, pp. 95–128.
- 26 A. Voronov, A. Urakawa, W. van Beek, N. E. Tsakoumis, H. Emerich and M. Rønning, *Anal. Chim. Acta*, 2014, **840**, 20–27.
- 27 T. Hyakutake, W. van Beek and A. Urakawa, *J. Mater. Chem. A*, 2016, **4**, 6878–6885.



- 28 L. Chen, S. Wang, J. Zhou, Y. Shen, Y. Zhao and X. Ma, *RSC Adv.*, 2014, **4**, 30968–30975.
- 29 S.-Y. Zhao, S.-P. Wang, Yu-J. Zhao and X.-B. Ma, *Chin. Chem. Lett.*, 2017, **28**, 65–69.
- 30 G. N. Vayssilov, M. Mihaylov, P. S. Petkov, K. I. Hadjiivanov and K. M. Neyman, *J. Phys. Chem. C*, 2011, **115**, 23435–23454.
- 31 O. Pozdnyakova, D. Teschner, A. Wootsch, J. Kröhnert, B. Steinhauer, H. Sauer, L. Toth, F. C. Jentoft, A. Knop-Gericke, Z. Paál and R. Schlögl, *J. Catal.*, 2006, **237**, 17–28.
- 32 P. Müller and I. Hermans, *Ind. Eng. Chem. Res.*, 2017, **56**, 1123–1136.
- 33 D. Ferri, M. A. Newton and M. Nachtegaal, *Top. Catal.*, 2011, **54**, 1070.
- 34 A. Urakawa, *Curr. Opin. Chem. Eng.*, 2016, **12**, 31–36.
- 35 K. Tomishige, Y. Ikeda, T. Sakaihorii and K. Fujimoto, *J. Catal.*, 2000, **192**, 355–362.
- 36 S. Xie and A. T. Bell, *Catal. Lett.*, 2000, **70**, 137–143.
- 37 K. T. Jung and A. T. Bell, *J. Catal.*, 2001, **204**, 339–347.
- 38 J. Lamotte, V. Morávek, M. Bensitel and J. C. Lavalley, *React. Kinet. Catal. Lett.*, 1988, **36**, 113–118.
- 39 M. Bensitel, V. Morávek, J. Lamotte, O. Saur and J.-C. Lavalley, *Spectrochim. Acta Part A Mol. Spectrosc.*, 1987, **43**, 1487–1491.
- 40 W. Y. Hernández, O. H. Laguna, M. A. Centeno and J. A. Odriozola, *J. Solid State Chem.*, 2011, **184**, 3014–3020.
- 41 M. Machida, T. Kawada, H. Fujii and S. Hinokuma, *J. Phys. Chem. C*, 2015, **119**, 24932–24941.
- 42 L. E. Gómez, J. F. Múnera, B. M. Sollier, E. E. Miró and A. V. Boix, *Int. J. Hydrogen Energy*, 2016, **41**, 4993–5002.
- 43 S. Lorentzou, G. Karagiannakis, D. Dimitrakis, C. Pagkoura, A. Zygogianni and A. G. Konstandopoulos, *Energy Procedia*, 2015, **69**, 1800–1809.
- 44 T. Taniguchi, T. Watanabe, N. Sugiyama, A. K. Subramani, H. Wagata, N. Matsushita and M. Yoshimura, *J. Phys. Chem. C*, 2009, **113**, 19789–19793.
- 45 M. Tamura and K. Tomishige, *Angew. Chem., Int. Ed.*, 2015, **54**, 864–867.
- 46 Z. Wu, M. Li, D. R. Mullins and S. H. Overbury, *ACS Catal.*, 2012, **2**, 2224–2234.
- 47 D. R. Mullins, M. D. Robbins and J. Zhou, *Surf. Sci.*, 2006, **600**, 1547–1558.
- 48 V. Matolín, J. Libra, M. Škoda, N. Tsud, K. C. Prince and T. Skála, *Surf. Sci.*, 2009, **603**, 1087–1092.
- 49 J.-D. Cafun, K. O. Kvashnina, E. Casals, V. F. Puentes and P. Glatzel, *ACS Nano*, 2013, **7**, 10726–10732.
- 50 D. Stoian, F. Medina and A. Urakawa, *ACS Catal.*, 2018, **8**, 3181–3193.

