

Cite this: *RSC Sustainability*, 2023, 1, 1416Received 16th January 2023
Accepted 14th June 2023

DOI: 10.1039/d3su00021d

rsc.li/rscsus

Mechanosynthesis of urea–hydroxybenzoic acid cocrystals as sustained-release nitrogen fertilizer†

Trishna Rajbongshi,^a Shalika Parakatawella,^b Diptajyoti Gogoi,^a Poonam Deka,^a Nadeesh M. Adassooriya *^c and Ranjit Thakuria *^a

Nitrogen is a key nutrient source in agriculture, which has a crucial impact on crop productivity. Out of available nitrogen fertilizers, urea is identified as the major nitrogen source, accounting for ~60% of global use. However, due to the low nutrient usage efficiency of urea, it has become unsustainable, as 50–70% nitrogen applied is lost due to leaching, volatilization and nitrification, causing a series of environmental hazards and economic losses. Moreover, the recent global pandemic as well as war disrupt the food supply chain and fertilizer market. Here we used mechanochemistry to prepare a series of novel urea cocrystals that showed sustained-release behavior with significant improvement (~4 times), lower volatilization, and improved hydration stability compared to commercial urea. Therefore, the proposed urea cocrystal based fertilizer system demonstrates a potential sustained-release nitrogen source in agriculture where excessive use of fertilizer and nutrient loss can be minimised.

Sustainability spotlight

Increased population, the recent global pandemic as well as war situations disrupt the food supply chain and fertilizer market. Rapid industrialization and shrinkage in cultivated land necessitate an increase in crop production while maintaining the minimal use of fertilizer. To maintain a balance between the current demands of food supply and population growth, sustainable agricultural practices have been identified as a vital solution. This current study aligns with point 2 of the UN's Sustainable Development Goals "Zero Hunger". Here we have extended the concept of cocrystallisation to prepare a series of novel urea cocrystals that showed sustained-release behavior, lower volatilization, and improved hydration stability compared to commercial urea, which will help with minimal use of fertilizer with improved agriculture productivity.

Introduction

Urea $\text{CO}(\text{NH}_2)_2$ is one of the most widely used nitrogen fertilizers, making up ~60% of global nitrogen fertilizer requirements.^{1–3} However, almost 40% of the total nitrogen fertilizer applied to plants is lost to the environment as unreactive atmospheric dinitrogen, affecting the global nitrogen cycle.⁴ This inherent mismatch between plant demand and nitrogen supply leads to nutrient loss through leaching that

affects plant growth. Urea has very high solubility in water (*ca.* 110–170 g/100 mL, in the 20–40 °C range)⁵ and its high hygroscopicity also results in mobility and runoff.⁶ It negatively impacts the environment and human health *via* groundwater contamination, eutrophication of fresh water, and estuarine ecosystems.⁷ As a result, excessive amounts of urea are used so that sufficient quantities are available for plants and crops. In order to overcome these problems, slow-release fertilizer technologies have been developed in recent years, but they are not cost efficient;^{8–13} moreover, there is a possibility of irregular nutrient release. Furthermore, decomposition of urea by soil microbes also contributes to tropospheric pollution related to emissions of nitrogen oxides, ammonia gas, as well as accumulation of nitrous oxide (N_2O), a potent greenhouse gas that depletes stratospheric ozone.¹⁴ In order to reduce enzymatic urease hydrolysis in soil, exogenous inorganic or organic molecules are often introduced that may inhibit urease activity. It has been established that even naturally occurring humic materials (various organic compounds with phenolic rings) also show urease inhibition activity.¹⁵ Because of the special hydrogen-bond donor and acceptor abilities of urea, a large number of cocrystals have been reported, with amides,¹⁶ carboxylic acids,^{17–20} phenols,^{21,22} *etc.*^{23,24} In recent years, a few


^aDepartment of Chemistry, Gauhati University, Guwahati 781014, Assam, India. E-mail: ranjit.thakuria@gmail.com; ranjit.thakuria@gauhati.ac.in

^bPostgraduate Institute of Science, University of Peradeniya, 20400 Peradeniya, Sri Lanka

^cDepartment of Chemical & Process Engineering, Faculty of Engineering, University of Peradeniya, 20400 Peradeniya, Sri Lanka. E-mail: nadeeshm@eng.pdn.ac.lk

† Electronic supplementary information (ESI) available: Crystallographic data (CCDC deposition numbers 2190718–2190721) and details of synthesis, measurements for urea adducts; crystallographic parameters of all urea adduct; experimental details of urea release study and solubility study; thermogravimetric traces of urea adduct; powder X-ray diffraction patterns of various LAG and hydration stability study and hydrogen bond parameters of urea adducts. For ESI and crystallographic data in CIF or other electronic format see DOI: <https://doi.org/10.1039/d3su00021d>



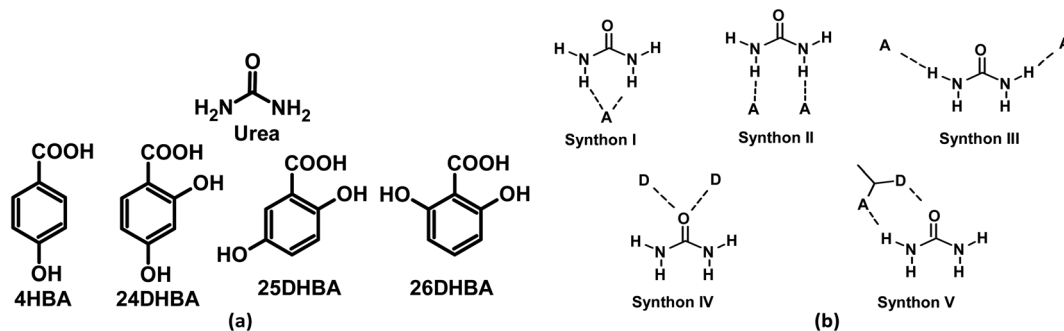

Scheme 1 (a) Molecular structures of urea and substituted hydroxybenzoic acid cofomers used in this study. (b) Plausible supramolecular synthons in cocrystals of urea. D and A represents hydrogen-bond donor and acceptor groups.

research groups, namely those of Baltrusaitis,^{25–34} Friščić,³¹ Užarević,²⁶ Thakuria and Adasooriya,^{35,36} Aakeröy and coworkers³⁷ introduced the concept of crystal engineering in order to prepare cocrystals (ionic/neutral) of urea with various inorganic and organic cofomers to decrease its solubility as well as to improve its hydration behaviour along with inhibition of urease activity.^{25–27,29–33,38} The selection of a neutral cofomer (catechol, salicylic acid, adipic acid, 4-nitrophenol, pimelic acid, citric acid *etc.*) to prepare a urea cocrystal in order to improve fertilizer activity is a recent trend and only a handful reports are available.^{28,34,36,37} In a recent highlight, we have emphasised this topic and discussed the importance of mechanochemistry in order to develop sustained-release urea cocrystals as a potential nitrogen source.³⁵ As an extension to our recent report on a 2 : 1 urea·adipic acid polymorphic cocrystal that exhibited lower solubility and sustained-release behaviour compared to commercially available urea³⁶ we have selected a few hydroxybenzoic acids (Scheme 1a) to prepare urea cocrystals using mechanochemistry. The reason for selecting hydroxybenzoic acid cofomers is their low solubility as well as the fact they can be considered non-toxic model humic materials.

Results and discussion

Urea cocrystals are one of the most widely studied systems that form various plausible supramolecular synthons. Along with organic cocrystals, several organometallic complexes of urea are reported in the literature.³⁹ Based on the hydrogen-bond donor and acceptor groups present in the cofomers, urea can form five different supramolecular synthons shown in Scheme 1b. The powder materials of all the multicomponent solids of urea with hydroxybenzoic acids were prepared by taking stoichiometric amounts of urea (60 mg, 1.0 mmol) and respective cofomers in a mortar and pestle in the presence of 100 μ L of acetonitrile as an added liquid (liquid assisted grinding, LAG) for 30 min. Single crystals suitable for X-ray diffraction were grown from most laboratory solvents, such as acetonitrile, ethanol, methanol, and nitromethane. Single crystal X-ray diffraction (SCXRD) analysis confirms the urea·4HBA and urea·24DHBA cocrystals to be of 0.5 : 1 stoichiometry, whereas

urea·25DHBA and urea·26DHBA resulted in 1 : 1 molecular adducts. Urea·4HBA and urea·24DHBA contain 0.5 molecule of urea and one molecule of the respective cofomers in the asymmetric unit and solved in the monoclinic ($P2_1/n$) and orthorhombic ($Pnma$) space group, respectively. Both cocrystals contain a usual infinite urea chain connecting the *p*-hydroxy group of 4HBA/24DHBA acting both as hydrogen-bond donor and acceptor using synthons II and IV, as shown in Fig. 1a and b. The urea·25DHBA cocrystal contains one molecule each of urea and 25DHBA in the asymmetric unit and solved in a chiral monoclinic $P2_1$ space group. The crystal structure analysis shows the cocrystal contains all possible supramolecular synthons, *viz.* III, IV and V, between the urea and 25DHBA molecules. The 5-OH and COOH groups of 25DHBA connect the urea through O–H \cdots O and N–H \cdots O hydrogen bonds, as shown in Fig. 1c. Surprisingly, urea·26DHBA forms a salt structure with a positional disorder of protonated urea molecules having s.o.f. of 0.495/0.505 for N2A/O1B over two positions. The crystal structure was solved in the monoclinic $P2_1/c$ space group with one molecule each of protonated urea and 26DHBA anion in the asymmetric unit. The crystallographic parameters of all the urea hydroxybenzoic acid molecular adducts are summarised in Table S1.† The most interesting urea·26DHBA salt structure forms a peculiar cyclic hexameric motif with alternating urea and 26DHBA molecules connected *via* synthons II and III (Fig. 1d). In 3D these two independent sheets of the hexagonal network intertwined, resulting in a 2-fold honeycomb network structure, as shown in Fig. 1e. This is the first report on the molecular salts of urea with organic acid, although a few salt structures of urea with phosphoric acid and nitric acid were reported in earlier literature.^{40–44} The reason behind the formation of molecular salt with 26DHBA is the cooperative effect of two intramolecular hydrogen bonds resulting from the 2- and 6-hydroxyl groups of 26DHBA with the carboxylic acid functional. The carboxylic acid C–O bond distances (–C=O and –C–O) of the hydroxybenzoic acids of all molecular adducts of urea are represented in Table S2.† From the table it is evident that C–O bond distances (–C=O and –C–O) of the 26DHBA cofomer in urea·26DHBA are nearly identical (1.2577(1) and 1.2613(1) Å), which indicates a resonating carboxylate anion; *i.e.* the formation of a molecular salt. On the other hand, in all



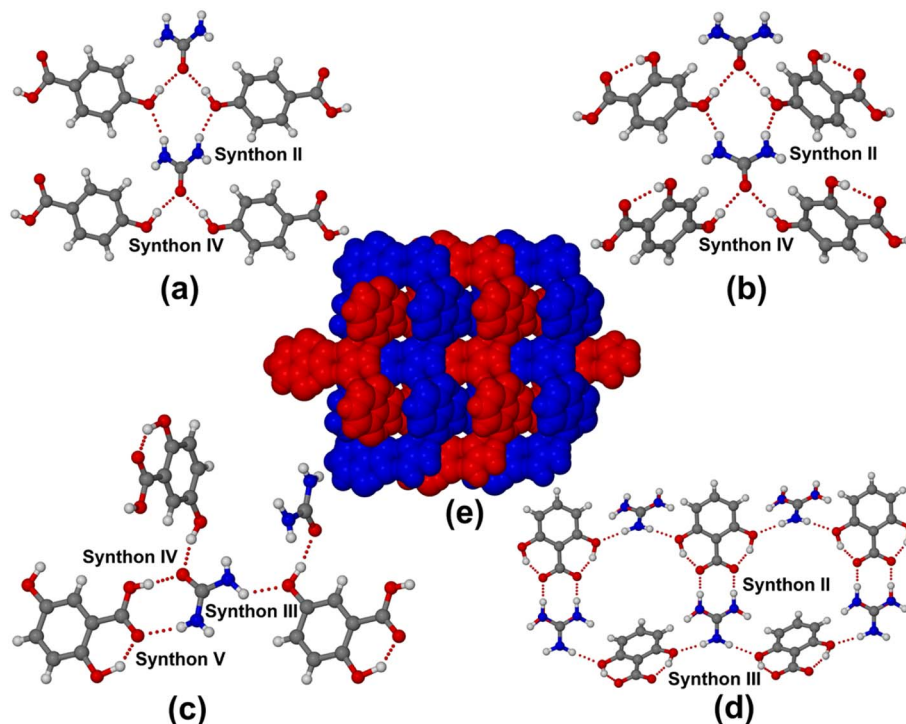


Fig. 1 Various hydrogen-bond synthons present in (a) urea·4HBA, (b) urea·24DHBA, (c) urea·25DHBA, and (d) urea·26DHBA and (e) 2-fold interpenetration of urea·26DHBA salt structure.

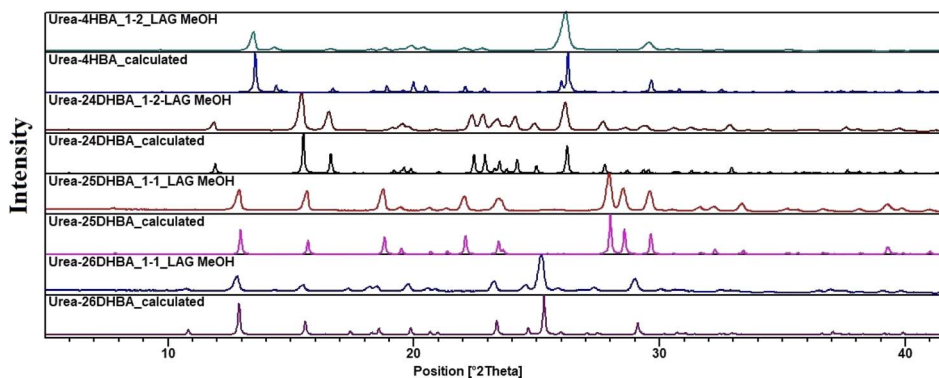


Fig. 2 Comparison of the experimental and calculated powder patterns of urea·4HBA, urea·24DHBA, urea·25DHBA cocrystals and urea·26DHBA molecular salt prepared using LAG (MeOH as liquid) shows an exact match with the respective calculated powder patterns obtained from SCXRD, confirming the phase purity of the bulk solids.

other crystal structures, the carboxylic acid C–O bond distances (–C=O and –C–O) of the hydroxybenzoic acids are different, supporting the formation of cocrystals for the rest.

In order to perform solubility, stability and leaching studies we had to ensure the phase purity of the materials; hence mechanochemical grinding was carried out, and the bulk purity of the urea cocrystals/salt was verified using PXRD analysis without the presence of any possible polymorphic phase (Fig. 2 and see ESI Fig. S1†).

Thermal stability of the urea multicomponent solids

Thermogravimetric analysis (TGA) measurements were performed using powder samples of urea cocrystals/salt prepared

using LAG, in the 30–450 °C range with a heating rate of 10 °C min⁻¹. The phase purity of the materials was confirmed using PXRD analysis prior to thermal measurements. No weight loss was observed prior to decomposition of all the multicomponent solids, confirming their guest-free nature. TGA measurements also show the materials to be stable up to *ca.* 180 °C, and they decompose immediately after melting (see ESI Fig. S2†).

Solubility measurement

The solubility of urea is very high (\approx 110–170 g per 100 mL at 20–40 °C). Based on the reported procedure,^{28,36} solubility measurement of all the urea hydroxybenzoic acid multicomponent solids was conducted in a controlled manner. 1 g of urea





Fig. 3 (Left) Comparison of solubilities for urea·4HBA, urea·24DHBA, urea·25DHBA, urea·26DHBA with pure urea under controlled experiments; (Right) powder samples of urea and respective hydroxybenzoic acid cocrystals/salt stored under 75% RH and ambient temperature. All the multicomponent solids remain as powders without showing deliquescence behaviour even after a period of 2 months, whereas urea deliquesces after a period of ~1.5 months.

was taken in a vial and dissolved in 1 mL of distilled water; in a second vial, 1 g equivalent of urea cocrystals/salt (for details see ESI, Experimental procedure and Table S3†) were taken and 1 mL of distilled water was added. The material was observed to be almost insoluble (Fig. 3-left). Therefore, in a separate vial in 1 mL of distilled water, a definite amount of the respective cocrystals/salt was added slowly until it precipitated. Based on our observation, the approximate solubility of the urea adducts was calculated (Table 1). From Table 1, it was obvious that the lower solubility of the coformers resulted in a significant decrease in the approximate solubility of the urea cocrystals/salt. BFDH morphology calculation shows (see ESI Fig. S3†) that urea has a block-shaped crystal morphology with a larger number of crystal facets (isotropic morphology) exposed to the solvent medium. Moreover, two amino groups (H-bond donor) and the carbonyl group (H-bond acceptor) of urea are exposed to the crystal surface that facilitates better solvation. On the other hand, for all the urea–hydroxybenzoic acid multicomponent solids, in addition to the H-bond donor/acceptor groups, exposure of the hydrophobic benzene C–H groups of coformers to the crystal surface diminishes solvation energies. Moreover, although all the urea cocrystals/salt are block in shape, one of the crystal facets is larger in size (anisotropic morphology) resulting a relatively smaller number of crystal facets exposed to the solvent medium. In addition, stronger intermolecular hydrogen-bond interactions between urea and coformers, and the presence of intramolecular hydrogen bonds in all the dihydroxybenzoic acids might also contribute to the lower solvation energies of the urea–hydroxybenzoic acid cocrystals/salt.

Hydration stability study

Urea absorbs atmospheric moisture and as a result it undergoes deliquescence and is difficult to store or transport. To investigate the hydration stabilities of the synthesised multicomponent adducts of urea, powder materials of the respective samples were stored in a bell jar under 75% relative humidity (RH) and ambient temperature (saturated aqueous sodium chloride (NaCl) solution resulting in an RH of 75%) and PXRDs were recorded after a regular interval of time based on a reported procedure.⁴⁵ PXRD

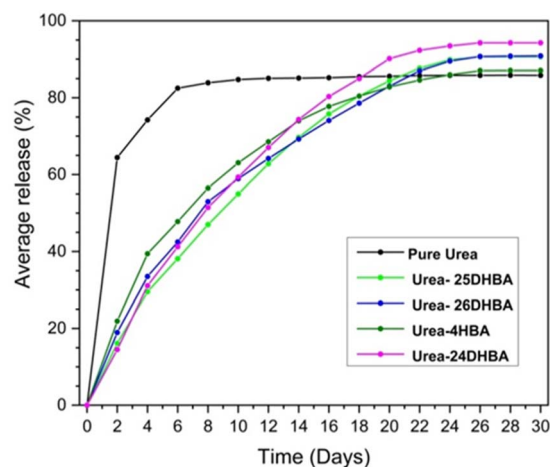


Fig. 4 Urea release profile of urea–hydroxybenzoic acid multicomponent adducts compared with commercial urea for a period of 30 days.

Table 1 Approximate solubility of the urea–hydroxybenzoic acid cocrystals/salt compared with commercial urea

Compound	Approximate solubility (mg mL ⁻¹)	Coformer solubility (mg mL ⁻¹)	Extent of decrease in solubility of urea (%)
Urea	1000		
Urea·4HBA cocrystal	9.2	5.0	99
Urea·24DHBA cocrystal	11.4	5.8	99
Urea·25DHBA cocrystal	37.4	5.0	95
Urea·26DHBA salt	15.5	7.49	98



Table 2 Approximate cost of urea, cofomers and urea–hydroxybenzoic acid cocrystals/salt calculated considering the prices of the reagents taken from the same supplier, TCI Chemicals

Compounds used for the current study	Price for 25 g of compound in INR	1 mol. equiv. of N in urea cocrystal w.r.t. commercial urea	Price for 1 mol. equiv. of urea cocrystal w.r.t. commercial urea available for 26 days in INR	Price of equiv. amount of urea cocrystal leached out compared to commercial urea in INR	Price of urea cocrystal absorbed by plant in 26 days compared to commercial urea in INR
Urea	4400	Urea	$4400 \times 3.25 = 14\ 300$	$14\ 300 \times 15\% = 2145$	$14\ 300 \times 85\% = 12\ 155$
4HBA	2000	(Urea)(4HBA) ₂	$4400 + 2 \times 2000 = 8400$	$8400 \times 15\% = 1260$	$8400 \times 85\% = 7140$
24DHBA	3100	(Urea)(24HBA) ₂	$4400 + 2 \times 3100 = 10\ 600$	$10\ 600 \times 6\% = 636$	$10\ 600 \times 94\% = 9964$
25DHBA	4100	(Urea)(25HBA)	$4400 + 4100 = 8500$	$8500 \times 10\% = 850$	$8500 \times 90\% = 7650$
26DHBA	6000	(Urea)(26HBA)	$4400 + 6000 = 10\ 400$	$10\ 400 \times 10\% = 1040$	$10\ 400 \times 90\% = 9360$

data were collected in the 2θ range between 5° and 50° at ambient temperature and compared with freshly prepared powder samples. PXRDs of the powder materials and the outcomes of the humidity study of urea multicomponent solids are summarised in ESI Fig. S4 and Table S4,† respectively. From the PXRD analysis it was observed that all the multicomponent solids of urea are stable at 75% RH and ambient temperature. There is no change in the relative intensity or peak position of any of the powder materials, which suggests better stability of the powder materials. On the other hand, under identical conditions, commercial urea absorbs moisture and deliquesces after a period of ~ 1.5 months, as observed from the image shown in Fig. 3-right.

Nitrogen release behaviour

The urea concentration of the eluted samples was determined using FT-IR spectroscopy, based on a previously published method.⁹ The linear relationship between the concentration of urea and the peak area of N–C–N stretching of urea at around 1465 cm^{-1} (normalized) is used to determine unknown concentrations of urea present in eluted samples (see ESI Fig. S5–S7 and Table S5†). The urea release profile shows that more than 60% of commercial urea has been leached out within two days, whereas urea–hydroxybenzoic acid molecular adducts showed only around 15–20% release. Due to the intense release of urea, crops do not have sufficient time to take up an appropriate amount of its nitrogen and the majority is wasted. This is a great loss not only from the agricultural point of view but also economically and environmentally, which makes commercial urea unsustainable. Out of urea–hydroxybenzoic acid cocrystals/salt, urea–4HBA shows a relatively higher urea release rate in the first couple of days and by the 10th day it has released almost 60% of its urea, while the other cocrystals are found to release around 55% of urea. After the 26th day it reaches a plateau with a maximum of 85% release following the same trend as pure urea. This continuous release over 26 days can be considered as sustainable release, since the process is slow and there is sufficient time for crops to uptake nitrogen. The 15% loss of urea can be attributed to its degradation into ammonium by-products. The controlled released behaviour and lower volatilisation resulted from the presence of strong hydrogen-bond interactions between hydroxybenzoic acid cofomer functionals and urea molecules (see ESI Table S6†). 4HBA

possesses only one OH group and it possesses a lower number of hydrogen-bonding interactions in urea–4HBA cocrystal compared to the rest of the dihydroxy benzoic acid derivatives. 25DHBA and 26DHBA have the same number of OH groups and they have similar numbers of interactions with urea in their respective crystal structures, leading to a similar trend in urea release profile (maximum around 90% by the 26th day). In the case of urea–24DHBA, its release profile closely resembles that of urea–26DHBA up to the 10th day. However after the 10th day it deviates and shows a more sustained release, achieving up to 94% maximum urea release, which is significantly high compared to our previous report on the urea–adipic acid cocrystal.³⁶ This may be due to the combined effect of stronger intramolecular hydrogen bonds and the presence of more intermolecular hydrogen-bond interactions between urea and cofomer, as well as the urease inhibition activity of hydroxybenzoic acid (model humic materials) cofomers. The urea release profile of all the synthesised adducts with respect to commercial urea is shown in Fig. 4.

In order to support the sustainability of the synthesised cocrystals compared to commercial urea as an alternative fertilizer, we calculated the approximate preparation cost of the materials based on nitrogen release data. We considered 26 days as the reference, according to the urea release profile study for cocrystals as well as urea. As the time taken for maximum urea release is ~ 8 days, in order to compare the value with urea cocrystals, we multiplied the cost factor by $26/8 = 3.25$ times; *i.e.* 3.25 times more urea is required to release the equivalent amount of N ($\sim 85\%$) compared to the respective cocrystals (85–95%). Table 2 shows a reasonably lower cost of production as well as leaching rate for urea cocrystals compared to urea, that supports urea cocrystals being a better alternative.

Conclusions

The mechanochemical syntheses of a few urea cocrystals/salt with substituted hydroxybenzoic acids as model humic materials with improved physicochemical properties have been investigated. The lower solubility of the urea cocrystals/salt indicates the high potential of their use as sustained-release nitrogenous fertilizers. The results prove that considerable changes to the solid forms of urea can be promptly made through a systematic cocrystallisation technique by selecting



suitable cofomers. Furthermore, these cocrystals/salt with drastically improved hydration stability suggest easy transport and storage of the material compared to commercial urea. Moreover, the urea release profile showed significant improvement in nitrogen absorption by soil with the sustained-release behaviour of the synthesised cocrystals/salt that will help the plant body to absorb nitrogen for a longer period of time compared to commercial urea. The release profiles showed that the novel urea-hydroxybenzoic acid based cocrystal fertilizer system takes 26 days to release ~90% urea, whereas pure urea reaches a plateau within 8 days with ~85% urea release, confirming the sustained-release behaviour of the hydroxybenzoic acid based cocrystal fertilizer. Currently we are working on field trials (pot trials) in order to investigate any possible toxicity with some selected crops. To conclude, if the fertilizer industry can adopt the cocrystallisation technique to prepare sustained-release urea cocrystals as alternate fertilizer, the excessive use of fertilizer and nutrient loss can be minimised.

Author contributions

T. R. synthesized and characterized the urea cocrystals/salt. D. G. and P. D. carried out the solubility and hydration stability study. S. P. carried out the nitrogen release study of the synthesized cocrystals/salt. N. M. A. and R. T. designed the project and all authors together finalized the manuscript.

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was funded by Science and Engineering Research Board under the Teachers Associateship for Research Excellence (TARE) grant (Project No. TAR/2021/000251). P. D. thanks the UGC for the Junior Research Fellowship (PhD scholar). R. T. thankfully acknowledges the Sophisticated Analytical Instrumentation Facility (SAIF), GU for the provision of the single crystal X-ray diffractometer and the Department of Chemistry, GU for the Rigaku powder X-ray diffractometer, basic instrumentation facility, and infrastructure. NMA is thankful to National Research Council, Sri Lanka (Grant No. 22-114) and Department of Chemical & Process Engineering, UoP for laboratory facilities.

Notes and references

- X. Zhang, E. A. Davidson, D. L. Mauzerall, T. D. Searchinger, P. Dumas and Y. Shen, *Nature*, 2015, **528**, 51–59.
- D. Coskun, D. T. Britto, W. Shi and H. J. Kronzucker, *Nat. Plants*, 2017, **3**, 1–10.
- A. M. Dave, M. H. Mehta, T. M. Aminabhavi, A. R. Kulkarni and K. S. Soppimath, *Polym.-Plast. Technol. Eng.*, 1999, **38**, 675–711.
- J. N. Galloway, F. J. Dentener, D. G. Capone, E. W. Boyer, R. W. Howarth, S. P. Seitzinger, G. P. Asner, C. C. Cleveland, P. Green and E. A. Holland, *Biogeochemistry*, 2004, **70**, 153–226.
- F.-M. Lee and L. E. Lahti, *J. Chem. Eng. Data*, 1972, **17**, 304–306.
- C. W. Whittaker, F. O. Lundstrom and S. B. Hendricks, *Ind. Eng. Chem.*, 1933, **25**, 1280–1282.
- K. Goulding, S. Jarvis and A. Whitmore, *Philos. Trans. R. Soc., B*, 2008, **363**, 667–680.
- J. Shi, J. Li, W. Zhou and D. Zhang, *Front. For.*, 2007, **2**, 104–109.
- N. Kottegoda, C. Sandaruwan, G. Priyadarshana, A. Siriwardhana, U. A. Rathnayake, D. M. Berugoda Arachchige, A. R. Kumarasinghe, D. Dahanayake, V. Karunaratne and G. A. J. Amaratunga, *ACS Nano*, 2017, **11**, 1214–1221.
- N. Kottegoda, I. Munaweera, N. Madusanka and V. Karunaratne, *Curr. Sci.*, 2011, 73–78.
- N. Madusanka, C. Sandaruwan, N. Kottegoda, D. Sirisena, I. Munaweera, A. De Alwis, V. Karunaratne and G. A. J. Amaratunga, *Appl. Clay Sci.*, 2017, **150**, 303–308.
- A. S. Giroto, G. G. F. Guimarães, M. Foschini and C. Ribeiro, *Sci. Rep.*, 2017, **7**, 46032.
- C. Wang, J. Lv, J. Xie, J. Yu, J. Li, J. Zhang, C. Tang, T. Niu and B. E. Patience, *Sci. Rep.*, 2021, **11**, 8070.
- M. Zaman, S. Saggar, J. D. Blennerhassett and J. Singh, *Soil Biol. Biochem.*, 2009, **41**, 1270–1280.
- L. Dong, A. L. Córdova-Kreylos, J. Yang, H. Yuan and K. M. Scow, *Soil Biol. Biochem.*, 2009, **41**, 1612–1621.
- K. Moribe, M. Tsuchiya, Y. Tozuka, K. Yamaguchi, T. Oguchi and K. Yamamoto, *J. Inclusion Phenom. Macrocyclic Chem.*, 2006, **54**, 9–16.
- S. Aitipamula, L. K. Mapp, A. B. H. Wong, P. S. Chow and R. B. H. Tan, *CrystEngComm*, 2015, **17**, 9323–9335.
- A. Alhalaweh, S. George, D. Boström and S. P. Velaga, *Cryst. Growth Des.*, 2010, **10**, 4847–4855.
- S. Bolton, *J. Pharm. Sci.*, 1963, **52**, 1071–1074.
- D. M. Altwein, J. N. Delgado and F. P. Cosgrove, *J. Pharm. Sci.*, 1965, **54**, 603–606.
- M. Pickering and R. Small, *Acta Crystallogr., Sect. B: Struct. Crystallogr. Cryst. Chem.*, 1982, **38**, 3161–3163.
- R. B. Hammond, C. Ma, K. J. Roberts, P. Y. Ghi and R. K. Harris, *J. Phys. Chem. B*, 2003, **107**, 11820–11826.
- R. Lee, S. A. Mason, E. Mossou, G. Lamming, M. R. Probert and J. W. Steed, *Cryst. Growth Des.*, 2016, **16**, 7175–7185.
- Y. Zhou, F. Guo, C. E. Hughes, D. L. Browne, T. R. Pekkett and K. D. M. Harris, *Cryst. Growth Des.*, 2015, **15**, 2901–2907.
- K. Barčauskaitė, Z. Brazienė, D. Avižienytė, M. Silva, D. Drapanauskaite, K. Honer, K. Gvildienė, R. Slinksiene, K. Jancaitiene, R. Mazeika, G. Staugaitis, T. Dambrauskas, K. Baltakys and J. Baltrusaitis, *J. Environ. Chem. Eng.*, 2020, **8**, 103965.
- I. Brekalo, V. Martinez, B. Karadeniz, P. Orešković, D. Drapanauskaite, H. Vriesema, R. Stenekes, M. Etter, I. Dejanović, J. Baltrusaitis and K. Užarević, *ACS Sustainable Chem. Eng.*, 2022, **10**, 6743–6754.



- 27 L. Casali, L. Mazzei, O. Shemchuk, K. Honer, F. Grepioni, S. Ciurli, D. Braga and J. Baltrusaitis, *Chem. Commun.*, 2018, **54**, 7637–7640.
- 28 L. Casali, L. Mazzei, O. Shemchuk, L. Sharma, K. Honer, F. Grepioni, S. Ciurli, D. Braga and J. Baltrusaitis, *ACS Sustainable Chem. Eng.*, 2019, **7**, 2852–2859.
- 29 K. Honer, E. Kalfaoglu, C. Pico, J. McCann and J. Baltrusaitis, *ACS Sustainable Chem. Eng.*, 2017, **5**, 8546–8550.
- 30 K. Honer, C. Pico and J. Baltrusaitis, *ACS Sustainable Chem. Eng.*, 2018, **6**, 4680–4687.
- 31 P. A. Julien, L. S. Germann, H. M. Titi, M. Etter, R. E. Dinnebier, L. Sharma, J. Baltrusaitis and T. Friščić, *Chem. Sci.*, 2020, **11**, 2350–2355.
- 32 L. Mazzei, V. Broll, L. Casali, M. Silva, D. Braga, F. Grepioni, J. Baltrusaitis and S. Ciurli, *ACS Sustainable Chem. Eng.*, 2019, **7**, 13369–13378.
- 33 C. Navizaga, J. Boecker, A. M. Sviklas, J. Galeckiene and J. Baltrusaitis, *ACS Sustainable Chem. Eng.*, 2017, **5**, 1747–1754.
- 34 M. Silva, K. Barcauskaite, D. Drapanauskaite, H. Tian, T. Bučko and J. Baltrusaitis, *ACS Earth Space Chem.*, 2020, **4**, 1018–1028.
- 35 N. M. Adassooriya, S. P. Mahanta and R. Thakuria, *CrystEngComm*, 2022, **24**, 1679–1689.
- 36 S. Parakatawella, D. Gogoi, P. Deka, Y. Xu, C. Sandaruwan, A. C. A. Jayasundera, M. Arhangelskis, R. Thakuria and N. M. Adassooriya, *ChemSusChem*, 2022, **15**, e202102445.
- 37 B. Sandhu, A. S. Sinha, J. Desper and C. B. Aakeröy, *Chem. Commun.*, 2018, **54**, 4657–4660.
- 38 S. G. Davey, *Nat. Rev. Chem.*, 2022, **1**.
- 39 S. K. Chandran, R. Thakuria and A. Nangia, *CrystEngComm*, 2008, **10**, 1891–1898.
- 40 S. Harkema and D. Feil, *Acta Crystallogr., Sect. B: Struct. Sci.*, 1969, **25**, 589–591.
- 41 Y. V. Nelyubina, K. A. Lyssenko, D. G. Golovanov and M. Y. Antipin, *CrystEngComm*, 2007, **9**, 991–996.
- 42 Y.-L. Liu and W. Zhang, *Dalton Trans.*, 2018, **47**, 45–48.
- 43 C. Wilson, *Acta Crystallogr., Sect. B: Struct. Sci.*, 2001, **57**, 435–439.
- 44 A. Parkin, S. M. Harte, A. E. Goeta and C. C. Wilson, *New J. Chem.*, 2004, **28**, 718–721.
- 45 K. K. Sarmah, P. Sarma, D. R. Rao, P. Gupta, N. K. Nath, M. Arhangelskis and R. Thakuria, *Cryst. Growth Des.*, 2018, **18**, 2138–2150.

