


Cite this: *Energy Adv.*, 2023,  
2, 180

# Highly active and selective Li/MgO catalysts for methane transformation to C<sub>2</sub> hydrocarbons: experimental and DFT study†

Rohan Singh Pal,<sup>ab</sup> Swati Rana,<sup>a</sup> Souvik Sadhu,<sup>a</sup> Tuhin Suvra Khan,<sup>ab</sup>  
Mukesh Kumar Poddar,<sup>a</sup> Rajib Kumar Singha,<sup>a</sup> Suman Sarkar,<sup>c</sup>  
Rahul Sharma<sup>d</sup> and Rajaram Bal  <sup>\*ab</sup>

The development of energy-efficient and economically attractive ways of utilization of methane for the production of chemicals/liquid fuels remains one of the long-standing challenges in catalysis. Li/MgO catalysts synthesized by a successive deposition–sublimation method show high activity and stability during the oxidative conversion of methane to olefins. A surfactant-assisted solvothermal method was used to synthesize the MgO support and then Li was deposited onto the support MgO by applying a successive deposition–sublimation method, where the initially deposited Li was sublimated and stabilized at 900 °C and this process was done for two consecutive times to prepare the final Li-doped MgO catalyst. For comparison purposes, several Li loaded catalysts were also prepared by the deposition method only. Different analytical techniques were used to characterise the prepared catalysts in order to understand and relate their physico-chemical properties to their catalytic activity. The catalyst prepared by the deposition–sublimation method (3.6Li/MgO<sup>Dep-Sub</sup>) showed high methane conversion and C<sub>2</sub> selectivity compared to the catalysts prepared by only deposition method. The 3.6Li/MgO<sup>Dep-Sub</sup> catalyst showed ~38% CH<sub>4</sub> conversion with 55% ethylene selectivity and 23% ethane selectivity with a total C<sub>2</sub> selectivity of 78% at 700 °C, and the catalyst was highly stable without losing its activity even after 24 h time on stream. It was found that the catalyst prepared by the deposition method deactivates rapidly with time and the activity is also low. DFT studies showed that Li doping to MgO has a significant promotional effect on the methane C–H activation. The C–H activation barrier was reduced by nearly 85 kcal mol<sup>−1</sup> over the Li-doped MgO surface, Li<sub>2</sub>–MgO(100), compared to the undoped MgO(100) surface.

Received 27th April 2022,  
Accepted 8th December 2022

DOI: 10.1039/d2ya00096b

rsc.li/energy-advances

## 1. Introduction

Methane, a primary component of natural gas, is an abundant resource of hydrocarbons mainly used as an inexpensive and clean-burning fuel. Because of the abundance of natural gas globally, it is economically beneficial to convert methane into more valuable products. Natural gas reserves are sometimes located far from the place of being used. Because it is not always cost-effective to transport liquefied natural gas, efficient

methods for converting methane into transportable liquid products are required. Oxidative dimerization of methane followed by oligomerization of C<sub>2</sub> products becomes a positive approach for this. For more than a decade, scientists around the globe have been trying to develop suitable methods to convert methane to ethane, ethylene, methanol, *etc.* Methane can be transformed into value-added C<sub>2</sub> hydrocarbons like ethane and ethylene by heating it in two conventional ways.<sup>1</sup> One is called “oxidative coupling of methane” (OCM), where heat treatment of methane is performed in the presence of oxygen, and the other one is called “non-oxidative coupling of methane” (NOCM), where methane is heat-treated in the absence of oxygen.<sup>2</sup> The non-oxidative process involves the coupling of methane to olefins, and the process is thermodynamically limited and hence requires higher energy for large-scale applications. Therefore, most of the research for direct conversion is focused on the OCM process.<sup>2</sup> OCM in the presence of an oxidant is an exothermic process. The OCM is expressed by the following chemical reaction:

<sup>a</sup> Light Stock Processing Division, CSIR-Indian Institute of Petroleum, Dehradun, 248005, India. E-mail: raja@iip.res.in; Fax: +91 135 2660202;



Tel: +91 135 2525917

<sup>b</sup> Academy of Scientific and Innovative Research (AcSIR), Ghaziabad, 201002, India

<sup>c</sup> Indian Institute of Technology, Jammu, NH-44, PO Nagrota, Jagti, Jammu and Kashmir, 181221, India

<sup>d</sup> GAIL (India) Ltd, GAIL Training Institute Plot No. 24, Sector 16-A, Noida, Uttar Pradesh, India

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d2ya00096b>



Spectroscopic studies conducted by several researchers have confirmed the presence of different surface oxygen species present in the catalysts, such as peroxide ( $\text{O}_2^{2-}$ ), lattice oxygen ( $\text{O}^{2-}$ ), carbonate ( $\text{CO}_3^{2-}$ ), superoxide ( $\text{O}_2^-$ ), and hydroxide ions ( $\text{OH}^-$ ).<sup>3,4</sup> Among all these, surface lattice oxygen ( $\text{O}^{2-}$ ) and superoxide anions ( $\text{O}_2^-$ ) play an important role in the selective  $\text{C}_2$  hydrocarbon formation.<sup>4</sup> On the other hand, surface electrophilic anions usually result in the overoxidation of alkane to  $\text{CO}_x$  products.<sup>5,6</sup> After the pioneering work by Keller and Bhasin,<sup>7</sup> a large number of catalysts were tested for the OCM reaction. But none of the catalysts has yet to find a successful path in the industry due to a failure to suppress combustion reactions at relatively high  $\text{CH}_4$  conversions.<sup>8–12</sup> Nanowire catalysts by the Siluria group are the only catalysts that have gained some popularity, reaching a pilot plant level.<sup>13,14</sup> Earlier studies were carried out to maximize  $\text{C}_2$  yield by varying the composition of the catalyst and reaction parameters, but economic evaluation revealed that the selectivity of  $\text{C}_2$  hydrocarbons is more important than  $\text{C}_2$  yields.<sup>8,15</sup> Studies say that catalysts play the primary role in producing  $\text{C}_2$  hydrocarbons that affect methane conversion and  $\text{C}_2$  selectivity in OCM. To date, several catalysts have been developed; including lanthanide series oxides,<sup>16–18</sup> Na–W–Mn mixed metal oxides,<sup>19</sup> and alkaline-earth metal oxides<sup>20–22</sup> for OCM reaction. It is reported that the surface basicity of the catalysts, especially intermediates and strong basic sites, contributes to better  $\text{C}_2$  hydrocarbon selectivity by a synergistic effect.<sup>16,21,23</sup> The Li–MgO catalysts were extensively studied for OCM, but their low stability due to the vaporization of Li is a major concern.<sup>24–30</sup> Recently, Huang *et al.* reported that a single-site Li–MgO catalyst exposes fourfold-coordinated  $\text{Mg}^{2+}$  sites (*i.e.*,  $\text{Mg}_4\text{C}_2^+$ ) of MgO (110) facets which efficiently catalyze methane activation by the methyl radical route.<sup>31</sup> They have reported 35.2% methane conversion and 58.2%  $\text{C}_2$  selectivity but the drawback is that the catalyst is stable for only 5 hours. Weaver *et al.* investigated the OCM reaction using rare earth oxide catalysts supported on nanoparticle magnesium oxide doped with alkali and alkaline earth metals (Li, Na) (Mg, Ca), where it was found that Li– $\text{TbO}_x/\text{MgO}$  performed better than all other combinations of rare earth oxide.<sup>21</sup> There are recent reports that indicate that the amount of Li in Li–MgO catalysts affects the MgO microstructure, which can be demonstrated by measuring the methyl radical intermediates during catalysis.<sup>24,32–34</sup> The  $\text{Li}^+$  ions were incorporated into the MgO lattice as substitutional ions on magnesium sites with oxygen vacancies for charge compensation. As a result, lithium promotion does not create additional active sites but increases the concentration of defect sites in MgO. This is in agreement with previous work that lithium cations ( $\text{Li}^+$ ) and oxygen vacancies at the MgO surface tend to separate at steps and corners, improving the number of low-coordinated  $\text{Mg}^{2+}\text{O}^{2-}$  sites. As a result, catalyst activity and selectivity can be improved.<sup>35</sup> Sweeney *et al.* proposed that there were two forms of Mg:  $\text{Mg}^{2+}$  at a Li site and a  $\text{Mg}^+$  complex.<sup>36</sup>

In the present work, we have prepared a stable Li/MgO catalyst *via* a successive deposition–sublimation method and the catalyst shows ~38% conversion with 55% ethylene selectivity and 23% ethane selectivity and by combining them a total  $\text{C}_2$  selectivity of 78%, and the catalyst was highly stable without losing its activity even after 24 h time-on-stream.

## 2. Experimental section

### 2.1. Materials

$\text{LiNO}_3$  (99.8%) and  $\text{Mg}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$  were purchased from Alfa Aesar, and cetyltrimethylammonium bromide (CTAB) was purchased from Sigma Aldrich. All chemicals were used without further purification.

**2.1.1. Catalyst synthesis.** The catalyst was synthesized by a method that consists of two steps. First, the MgO support was synthesized by the solvothermal method using cetyltrimethylammonium bromide (CTAB) as a template, and Li was then supported on the MgO support following a sequential wet impregnation method modified by us.

**2.1.2. Synthesis of MgO.** In a typical preparation method, in a 1 L round-bottom (RB) flask, 300 mL of ethanol, CTAB, and magnesium nitrate hexahydrate were mixed together stoichiometrically. After that, RB was placed on a hot plate with magnetic stirring and was heated at 50 °C. After 2 hours of continuous stirring, the plate was heated to 80 °C and maintained for 18 hours. Afterwards, the ethanol was evaporated, and the gel was dried overnight at 90 °C. To produce magnesium oxide, the dried powders were calcined in ambient air for 6 hours at 800 °C with a 5 °C  $\text{min}^{-1}$  heating rate.

**2.1.3. Li-loading on the MgO support by the deposition method.** We used a surfactant CTAB-induced preparation method to load the desired wt% of Li on the synthesized MgO support. For a typical synthesis of 5% Li/MgO catalyst, 5 g of synthesized MgO support was first dispersed in 200 mL of ethanol and sonicated for 2–3 hours. In a separate beaker, 50 mL of ethanol was mixed with distilled water, 25 mL, then 3.281 g of CTAB was added to it and stirred until it dissolved completely. Then, 2.483 g of  $\text{LiNO}_3$  was added to it and stirred until dissolved completely, followed by the dropwise addition of this solution to the support solution in which MgO was dispersed using sonication. The resultant solution was dried at 60 °C in an oil bath while stirring was maintained, and the powder was then dried at 100 °C for 6 h followed by calcination at 800 °C for 6 hours at a ramp rate of 1 °C per minute in a quartz tube in air to obtain a 5% Li/MgO catalyst. The catalyst was denoted as 1.9Li/MgO<sup>Dep</sup>.

In a similar manner, 10% and 15% Li/MgO catalysts were synthesized by varying the  $\text{LiNO}_3$  amount and the catalysts are denoted as 3.8Li/MgO<sup>Dep</sup> and 7.4Li/MgO<sup>Dep</sup>.

**2.1.4. Synthesis of the Li/MgO catalyst by the deposition–sublimation method.** We used a successive deposition–sublimation method to synthesize this Li/MgO catalyst. In a typical preparation method, initially 5% Li was deposited on the



MgO support in the same way as the catalyst prepared by the deposition method, and then the catalyst was sublimed at 900 °C in a flow of zero-air for 12 h followed by heating at 900 °C in N<sub>2</sub> flow for 12 h. Then on the as-prepared material, again 5% Li was loaded in the same way as for the deposition method followed by sublimation at 900 °C in the flow of air for 12 h followed by heating at 900 °C in N<sub>2</sub> flow for 12 h. The finally obtained catalyst is denoted as 3.6Li/MgO<sup>Dep-Sub</sup>.

## 2.2. Catalyst characterizations

All the synthesized fresh and spent catalysts were characterized by various analytical techniques. Details of characterization techniques are given in the ESI†

## 2.3. Catalytic activity study

Details of the catalytic activity measurements are given in the ESI.†


# 3. Results and discussion

## 3.1. BET surface area and ICP-AES analysis

The Li amounts present in the catalysts were determined from the ICP-AES analysis of all the fresh and spent catalysts and the results are shown in Table 1. The MgO support showed a surface area of 62.8 m<sup>2</sup> g<sup>-1</sup> and the surface area was decreased after Li loading due to the surface coverage of Li.<sup>37</sup> The ICP analysis shows that during high-temperature heat treatments, a significant amount of Li loss was also noticed (Table 1). All the samples (1.9Li/MgO<sup>Dep</sup>, 3.8Li/MgO<sup>Dep</sup>, 7.4Li/MgO<sup>Dep</sup>) show a considerable decrease in Li amount after high temperature heat treatment in air. From the ICP analysis, 1.9Li/MgO<sup>Dep</sup> contains only 1.9% Li, i.e. 3.1% (~62%) loss from the actual loaded Li% (5%) was noticed during the calcination process, while 3.8Li/MgO<sup>Dep</sup> contains 3.8 wt% Li, and 7.4Li/MgO<sup>Dep</sup> has 7.4 wt% of Li after the calcination from the actually loaded Li (10%, 15% respectively). The catalyst prepared by deposition–sublimation (Li/MgO<sup>Dep-Sub</sup>) contains 3.6% Li. It has to be noted that the 3.6Li/MgO<sup>Dep-Sub</sup> catalyst showed almost negligible loss of Li (0.1% loss after 24 h reaction) after the OCM reaction as compared to the catalysts prepared by the deposition method, suggesting that the Li species are stable for the 3.6Li/MgO<sup>Dep-Sub</sup> catalyst as compared to the higher loading Li catalyst (3.8Li/MgO<sup>Dep</sup> and 7.4Li/MgO<sup>Dep</sup> catalyst) prepared by the deposition method.

**Table 1** The amounts of Li and the BET surface areas of various Li/MgO catalysts

Catalyst	Li%		BET surface area (m <sup>2</sup> g <sup>-1</sup> )	
	After calcination	After reaction at 700 °C	After calcination	After reaction at 700 °C
MgO	—	—	62.8	48.6
1.9Li/MgO <sup>Dep</sup>	1.9	1.1	23.4	22.1
3.8Li/MgO <sup>Dep</sup>	3.8	2.6	16.6	13.1
3.6Li/MgO <sup>Dep-Sub</sup>	3.6	3.6	13.3	13.2
7.4Li/MgO <sup>Dep</sup>	7.4	4.8	5.3	3.4

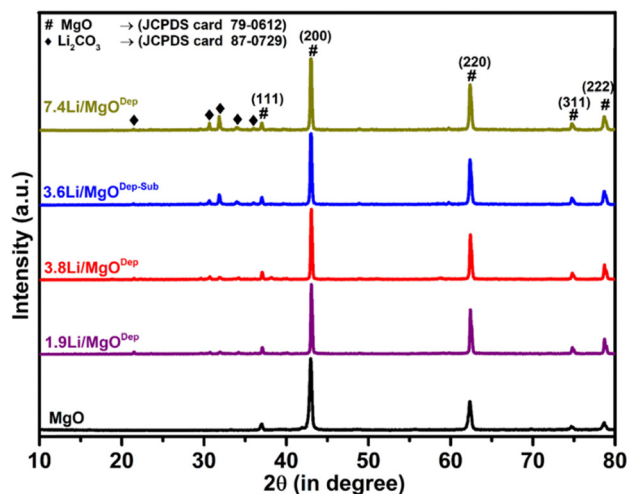

**Fig. 1** XRD pattern of MgO and the Fresh Li/MgO Catalyst.

## 3.2. XRD analysis

Fig. 1 shows the XRD patterns of the synthesized MgO support and Li/MgO catalysts. All the XRD patterns exhibited sharp peaks with the highest intensity peak at a 2θ value of 42.88° for the (200) plane of MgO (JCPDS Card 79-0612) indicating higher crystalline nature of the catalysts. The XRD pattern of all the lithium supported on MgO catalysts shows additional peaks corresponding to Li<sub>2</sub>CO<sub>3</sub> (JCPDS Card 87-0729). This is because Li is highly basic in nature and Li<sub>2</sub>O decomposed from LiNO<sub>3</sub> reacted quickly with acidic CO<sub>2</sub> in air to generate Li<sub>2</sub>CO<sub>3</sub> at room temperature. Above 500 °C, Li<sub>2</sub>CO<sub>3</sub> dissociates into Li<sub>2</sub>O and CO<sub>2</sub>,<sup>38</sup> implying that Li<sub>2</sub>O should be in the predominant state at reaction temperatures above 600 °C.<sup>39</sup> The XRD pattern also showed that as the Li loading increases, the peaks corresponding to Li<sub>2</sub>CO<sub>3</sub> were intensified, showing the higher Li<sub>2</sub>CO<sub>3</sub> formation. In addition, the peak width of all Li-supported catalysts decreases slightly compared to the parent MgO.

It was noticed that the peak for the [200] plane of MgO at 42.88° shifted to a higher value at 43.00°. Vegard's law states that if the doping element (Li) is smaller than the replaced element (Mg), the lattice parameter will decrease for the parent material (MgO). In fact, a decrease in the lattice parameter from 2.1037 Å for pure MgO to 2.0987 Å for all Li doped samples confirms Li substitution in the MgO matrix.<sup>40,41</sup> This observation revealed that some of the Li atoms replaced Mg atoms in the MgO crystal lattice and decreased the lattice size of MgO.<sup>42,43</sup>

XRD of the spent catalysts were also analysed (Fig. S1, ESI†) and all the spent catalysts have similar XRD patterns to that of the fresh catalysts. All the spent catalysts show peaks corresponding to Li<sub>2</sub>CO<sub>3</sub>, which suggests that Li is still present in the catalyst in the form of Li<sub>2</sub>CO<sub>3</sub> after the catalysis; however, a decrease in the intensity of Li<sub>2</sub>CO<sub>3</sub> peaks in all the catalysts except the 3.6Li/MgO<sup>Dep-Sub</sup> catalyst was observed, indicating Li sublimation during catalysis. We also calculated the crystal size of the catalyst and tabulated the results in Table S1 (in ESI†).





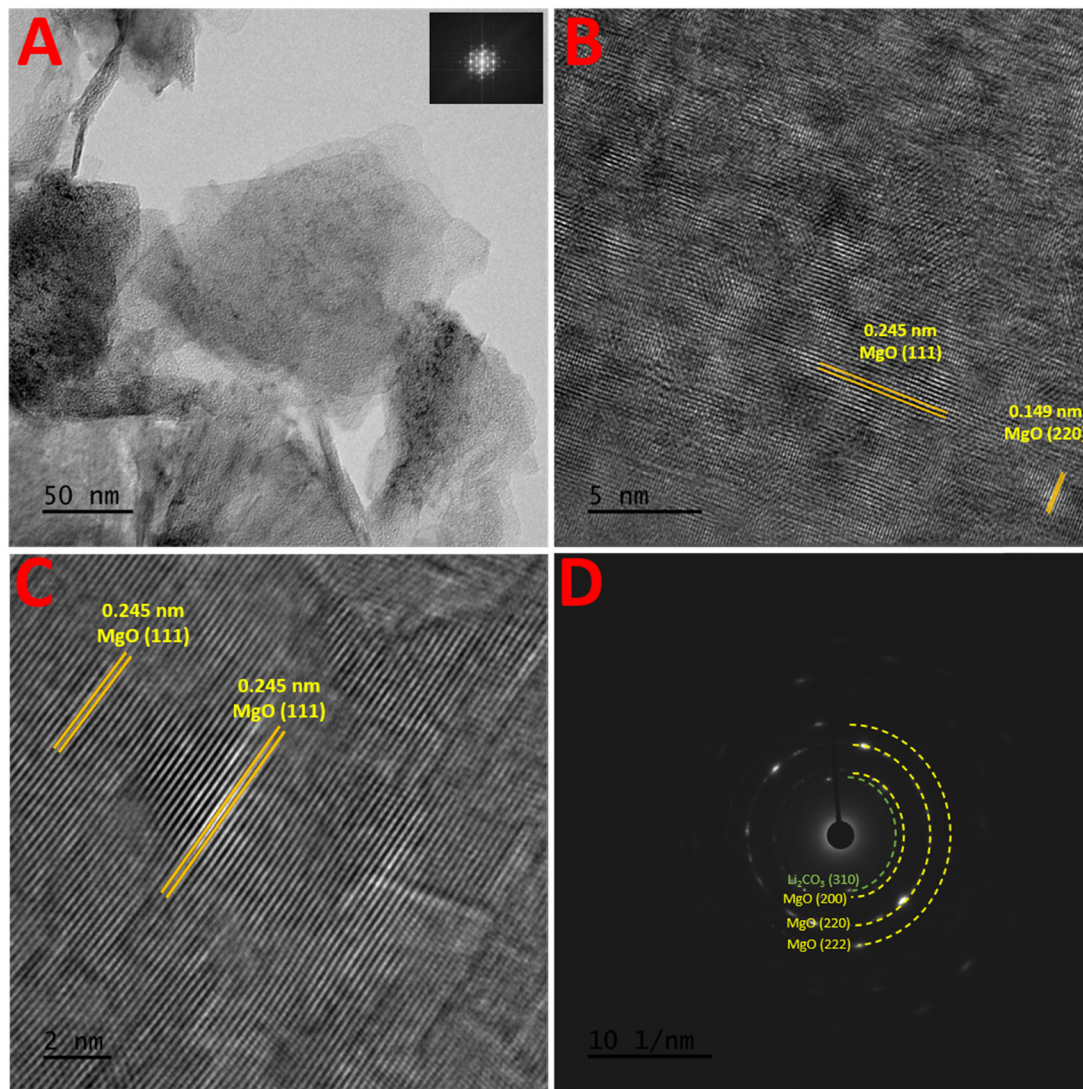


Fig. 2 (A–C) STEM images, and (D) SAED pattern of 3.6Li/MgO<sup>Dep-Sub</sup> catalyst.

### 3.3. STEM-EELS analysis

Using STEM, the morphologies of the prepared 3.6Li/MgO<sup>Dep-Sub</sup> catalyst were examined, and the images obtained from the direct beam contrast bright field image STEM analysis (This is high magnification bright field image) are provided in Fig. 2A. The FFT image is also shown in the inset of Fig. 2A. The high-resolution phase contrast images of the same region are also included in Fig. 2B and C. Lattice fringes with  $d$  spacing value of 0.245 nm, corresponding to MgO [111] facets can be seen. Additionally, 0.149 nm lattice fringes can also be observed in the catalyst, which correspond to the MgO [220] plane.

The  $d$  spacing (2.25 Å) calculated from the SAED pattern (Fig. 2D) confirms the presence of lithium corresponding to the (310) plane of Li<sub>2</sub>CO<sub>3</sub>. Also, the EELS spectra have been obtained from the region and shown in Fig. S9 (in the ESI<sup>†</sup>). The low loss region of the spectrograph confirms the presence of lithium in the 3.6Li/MgO<sup>Dep-Sub</sup> catalyst where the signature of 55.1 eV energy loss for Lithium is observed.

### 3.4. CO<sub>2</sub>-TPD analysis

According to XPS measurement (discussed later), there was a carbonate species present on the catalyst surface and hence carbon dioxide was strongly adsorbed on the catalyst surface, suggesting that the catalyst surface is basic. That's why surface basic properties of catalysts were investigated by CO<sub>2</sub>-TPD analysis. Fig. 3 represents the CO<sub>2</sub> desorption profiles of catalysts with different Li-loaded MgO catalysts. There is almost no difference in the shape of the desorption peak in the temperature range between 50 and 800 °C for all the prepared catalysts. The temperature interval at which the CO<sub>2</sub> chemisorbed on the basic sites is desorbed can be used to describe the strength of a certain group of basic sites. The area under the TPD curve of the basic sites was used to estimate their basic strength. Furthermore, the CO<sub>2</sub>-TPD profile of the Li/MgO catalysts (Fig. 3) shows only two types of peaks, mostly known as weak and moderate basic sites, whereas the third kind of site (strong basic sites) appeared to be absent or present only in



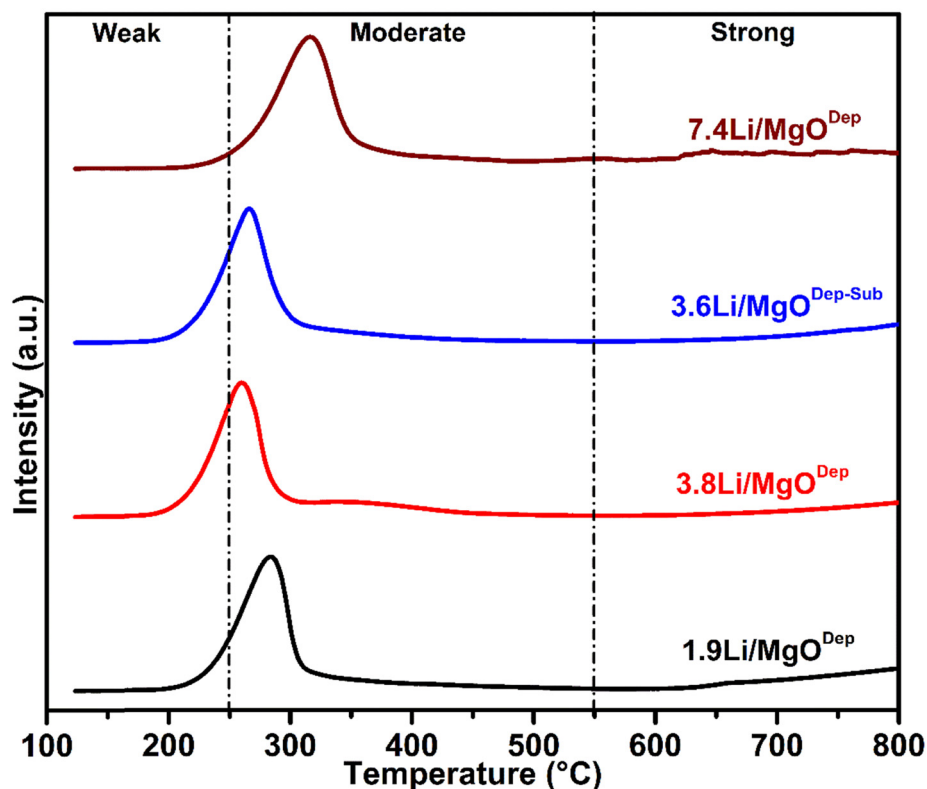


Fig. 3 CO<sub>2</sub>-TPD spectra of different Li/MgO catalysts.

negligible amounts. The peak in the temperature range below 250 °C, which corresponds to weak basic sites, might be assigned to the metal–oxygen pair, *i.e.* Mg–O in this case, as well as surface oxygen anions. The higher temperature peak (between 250 and 550 °C) corresponding to moderate basic sites may be ascribed to the presence of unsaturated oxygen (O<sub>2</sub><sup>−</sup>) ions and the lattice oxygen anions.<sup>18,44</sup> The amounts of different basic sites are tabulated in Table 2. It was found that the total amount of basic sites was maximum in the case of the 7.4Li/MgO<sup>Dep</sup> catalyst. The strength of basic sites is found to vary with the substitution of Mg<sup>2+</sup> with the alkali metal cation Li<sup>+</sup>. As previously stated, low-coordination oxygen anions are responsible for the high amount of basic sites; the greater the electron-donating ability of anionic oxygen, the stronger its basicity.<sup>45,46</sup> It has to be noted that alkali metal cations such as Li<sup>+</sup> have a lower electronegativity than alkaline earth metal ions like Mg<sup>2+</sup>, so by introducing alkali metal cations Li<sup>+</sup> to the vicinity of Mg<sup>2+</sup>, the electron-donating properties of oxygen

anions adjacent to Mg<sup>2+</sup> increases, which increases the basic strength.

CO<sub>2</sub>-TPD study could provide useful information on catalytic performance because the generation of methyl radicals is likely related to the basicity of the catalyst. As shown in Fig. 3 and Table 2, the CO<sub>2</sub>-desorption signals and the amount of moderate as well as total basic sites of the 3.6Li/MgO<sup>Dep-Sub</sup> catalyst are greater than those of the catalyst prepared by the deposition method (1.9Li/MgO<sup>Dep</sup> and 3.8Li/MgO<sup>Dep</sup>). The OCM activity is closely correlated with the number of basic sites derived from CO<sub>2</sub>-TPD data (Table 2). Despite its significantly stronger basicity than other prepared catalysts, the 7.4Li/MgO<sup>Dep</sup> catalyst was shown to be less OCM active than the other catalysts. We believe that the competitive deep oxidation or larger crystallite size could be responsible for the 7.4Li/MgO<sup>Dep</sup> catalyst's poor OCM performance showing less C<sub>2</sub> selectivity. Furthermore, the lack of activity and selectivity of this catalyst would be explained by the loosely bound surface active oxygen species and lattice oxygen.

In the case of the 3.6Li/MgO<sup>Dep-Sub</sup> catalyst, a sufficient amount of moderate basic sites is responsible for its high activity and selectivity. In addition, the active oxygen species (O<sub>2</sub><sup>−</sup> and lattice oxygen) responsible for the basicity of the catalyst are tightly bound to its surface due to high temperature heat treatment during the synthesis procedure, explaining why it shows stable activity during the reaction.

### 3.5. XPS analysis

Fig. 4 shows Mg 2p, Mg 1s, Li 1s and O 1s peaks of all the prepared catalysts. The position of the Mg 1s peaks is similar in

Table 2 Amount of CO<sub>2</sub> desorbed during CO<sub>2</sub>-TPD experiments

Catalyst	Amount of basic sites (cm <sup>3</sup> g <sup>−1</sup> )		
	Weak basic sites	Medium basic sites	Total basic sites
1.9Li/MgO <sup>Dep</sup>	1.09	8.81	9.90
3.8Li/MgO <sup>Dep</sup>	3.36	10.71	14.07
3.6Li/MgO <sup>Dep-Sub</sup>	4.84	11.84	16.68
7.4Li/MgO <sup>Dep</sup>	2.30	17.50	19.80



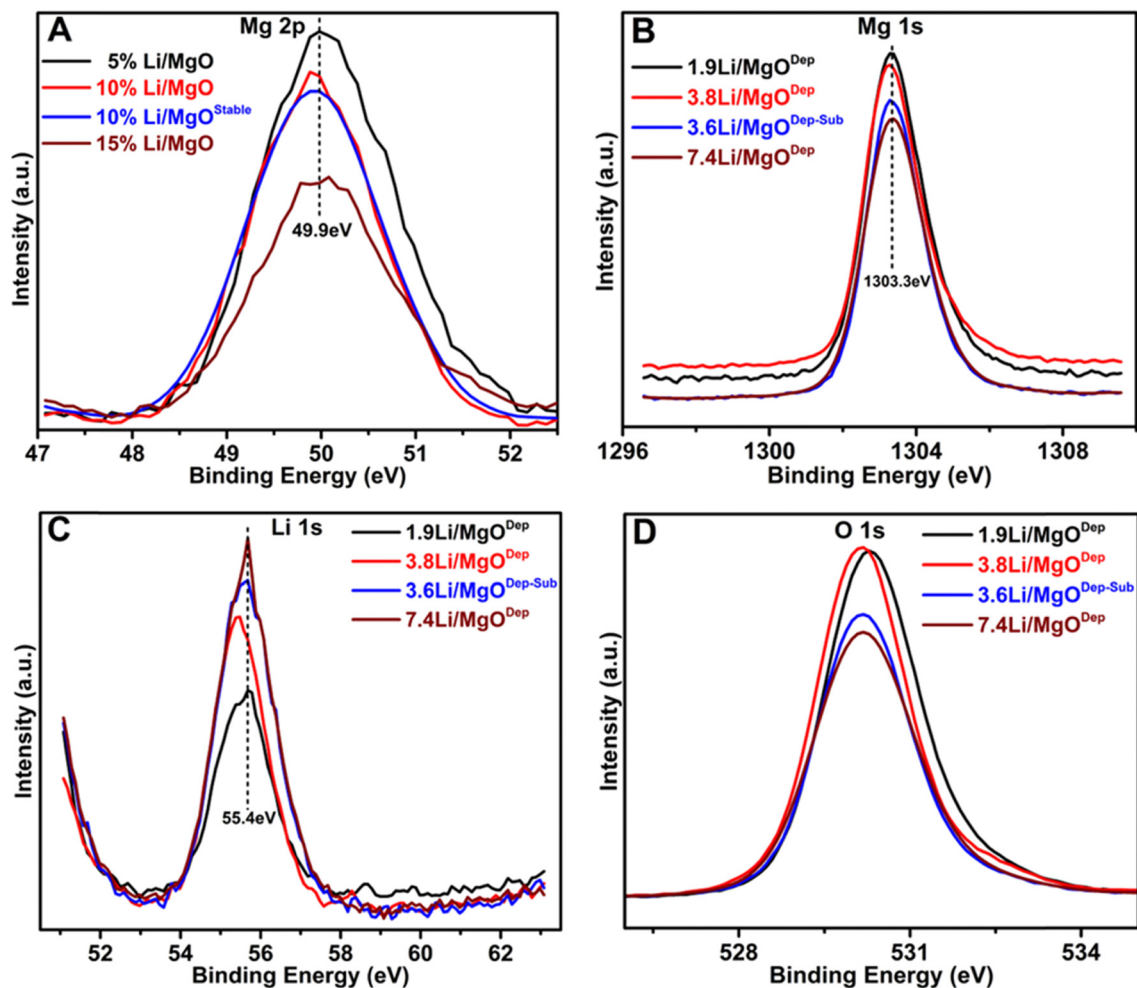


Fig. 4 XPS analysis of the fresh catalyst: (A) Mg 2p spectra, (B) Mg 1s spectra, (C) Li 1s spectra and (D) O 1s spectra.

all samples at approximately 1303.3 eV, which is the typical B.E for Mg 1s,<sup>31</sup> this implying that the status of Mg–O bonds is unaffected by the doping of Li. The Mg 1s peak in the Li–MgO catalysts becomes weaker with increasing Li loading, and a similar pattern is also observed with the Mg 2p peak at 49.9 eV.

Furthermore, in all the catalysts, the peak of Li 1s appears at around 55.4 eV, which is almost around the typical B.E for Li.<sup>31</sup> The deconvoluted O 1s peaks are shown in Fig. 5. It was found that three types of oxygen species, *i.e.* superoxide species ( $\text{O}_2^-$ ), negatively charged oxygen species (lattice oxygen;  $\text{O}^{2-}$ ), and hydroxyl species ( $\text{OH}^-$ ) or carbonate species ( $\text{CO}_3^{2-}$ ) are present over all the catalysts. It was found that the relative superoxide species concentration ( $\text{O}_2^-$ ) follows the order:  $3.6\text{Li}/\text{MgO}^{\text{Dep-Sub}} > 3.8\text{Li}/\text{MgO}^{\text{Dep}} > 1.9\text{Li}/\text{MgO}^{\text{Dep}} > 7.4\text{Li}/\text{MgO}^{\text{Dep}}$ . So, it is evident that the formation of superoxide species ( $\text{O}_2^-$ ) is higher in the case of the  $3.6\text{Li}/\text{MgO}^{\text{Dep-Sub}}$  catalyst and this species is responsible for activating methane by showing higher activity than all others.

If we look at the O 1s peak in all the prepared catalysts, we observe that all show the O 1s peak between 528 and 533 eV and that the intensity of the O 1s peak is highest for the  $3.8\text{Li}/$

$\text{MgO}^{\text{Dep}}$  catalyst as compared to the  $1.9\text{Li}/\text{MgO}^{\text{Dep}}$ ,  $7.4\text{Li}/\text{MgO}^{\text{Dep}}$  and  $3.6\text{Li}/\text{MgO}^{\text{Dep-Sub}}$  catalyst, which may be due to higher Li loading on the MgO support.

Furthermore, Fig. 5 shows the deconvoluted spectra of O 1s peaks for all the prepared catalysts, which shows the peak at B.E  $\sim 529.8$  eV which corresponds to lattice oxide  $\text{O}^{2-}$ ,  $\sim 530.5$  eV corresponding to the superoxide species ( $\text{O}_2^-$ ) and  $\sim 531.7$  eV which may correspond to carbonates ( $\text{CO}_3^{2-}$ ) or may be hydroxide species ( $\text{OH}^-$ ).<sup>47,48</sup> Formation of carbonate species might be due to carbon dioxide adsorbed from the atmosphere and also it is indicative of the highly basic nature of the prepared material, which is also shown by  $\text{CO}_2$ -TPD analysis. The presence of significant hydroxide species from the XPS analysis could be explained by the fact that Li and MgO are very hygroscopic in nature and formed hydroxide species by adsorbing water from the air.

Moreover a slightly positive shift from 529 eV to 529.8 eV of the metal oxide peak ( $\text{O}^{2-}$ ) is observed in the deconvoluted O 1s XPS spectra. This shift has been determined to be a true chemical effect, rather than a result of charging or instrumental error. Such a shift represents the slightly more oxidised environment of oxygens existing in the near-surface





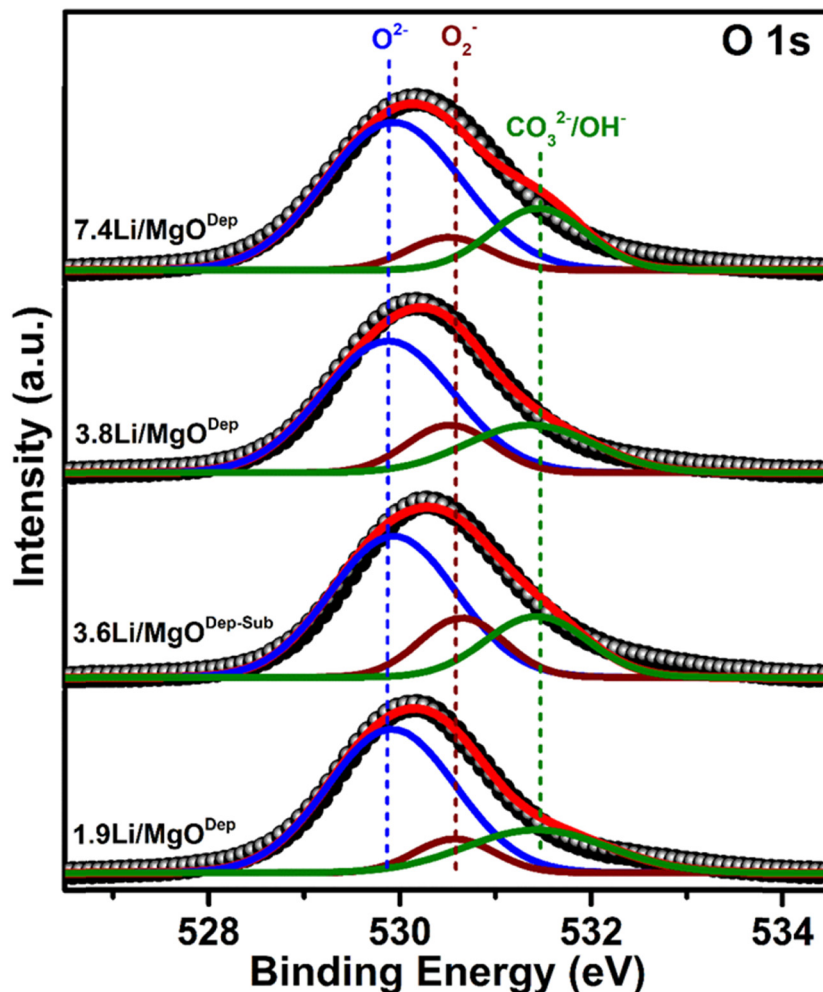


Fig. 5 O 1s XPS deconvoluted pattern for all the prepared Li/MgO catalysts.

region.<sup>49</sup> This chemical effect, which may arise due to the different metal to oxygen bond environment, appeared after Li loading.

### 3.6. Raman analysis

Raman analysis results are shown in Fig. 6. The results show that pure MgO has a Raman-active mode due to surface effects, which can lead to surface modes, and these are expected in nanostructured catalysts, as proven by DFT experiments on MgO nanotubes.<sup>50</sup> When the Raman spectrum of commercial MgO was compared with the prepared MgO support, it was observed that the commercial MgO has only minor G-band at around  $1500\text{ cm}^{-1}$  and a D-band at  $1931\text{ cm}^{-1}$  which could be due to the lack of Raman activity in the commercial MgO. Literature reports also suggest that crystal symmetry is responsible for the inactivity of Raman for bulk MgO.<sup>51,52</sup> Fig. 6 reveals that all the Li doped samples have essentially identical Raman spectra to the pure MgO support, which could be owing to the lack of active Raman modes for  $\text{Li}_2\text{O}$  or  $\text{Li}_2\text{CO}_3$ . For all samples, a weak peak is observed around  $1088\text{ cm}^{-1}$  and surface phonon modes are responsible for this peak.<sup>52,53</sup> For all the prepared catalysts, a broad peak at  $1261\text{ cm}^{-1}$  is due to the D-band and

additionally there is also a sharp peak at about  $1500\text{ cm}^{-1}$  due to the presence of the G-band.<sup>54,55</sup> Similarly, a broad band at about  $2360\text{ cm}^{-1}$  represents a G-band and a strong D-band can also be seen at lower frequencies at  $\sim 1931\text{ cm}^{-1}$ . It is reported that these peaks appear because carbon is bonded to MgO forming  $\text{MgCO}_3$ .<sup>55</sup> The Raman spectra of all Li-doped catalysts are nearly identical to those of pure MgO, although the D and G bands shift slightly to lower wavelengths as the Li loading increases.

We also conducted an *in situ* Raman investigation of the  $3.6\text{Li/MgO}^{\text{Dep-Sub}}$  catalyst in  $\text{CH}_4 + \text{O}_2$  flow at various temperatures to obtain information about any structural changes in the catalyst during reaction. As can be observed in Fig. 7, the intensity or integrated peak area of the peaks corresponding to the D and G bands decreased as the temperature increased. Increased disorder in the structure of MgO and partial decomposition of  $\text{MgCO}_3$  present in the catalyst at higher temperatures could explain this decrease in peak intensity with increasing temperature.<sup>56</sup> It is noteworthy that in the reaction environment ( $\text{CH}_4 + \text{O}_2$ ) at  $800^\circ\text{C}$ , the same bands with comparable peak shapes but with a decreased intensity still exist, indicating that some changes are occurring





An Electron Paramagnetic Resonance (EPR) spectrum recorded at room temperature (Fig. S7 in ESI†) characterized the freshly prepared 3.6Li/MgO<sup>Dep-Sub</sup> catalyst showing  $g$  values at 2.07, 2.04, 2.00 and 1.99. It has to be noted that EPR is an amenable method to detect species having unpaired electrons, such as O<sub>2</sub><sup>-</sup> and O<sup>-</sup> species and electrons trapped by oxygen vacancies. The  $g$  values obtained from the spectrum of the 3.6Li/MgO<sup>Dep-Sub</sup> catalyst can be compared well with O<sub>2</sub><sup>-</sup> signals reported by Lunsford *et al.* at  $g_{xx} = 1.994$ ,  $g_{yy} = 2.006$ ,  $g_{zz} = 2.040$  on La<sub>2</sub>O<sub>3</sub>,<sup>60</sup> and Wang *et al.* at  $g_{xx} = 2.0001$ ,  $g_{yy} = 2.0045$ ,  $g_{zz} = 2.0685$  on SrF<sub>2</sub>/La<sub>2</sub>O<sub>3</sub>.<sup>61</sup> Thus signals on the 3.6Li/MgO<sup>Dep-Sub</sup> catalyst in this investigation can be attributed to surface electrophilic O<sub>2</sub><sup>-</sup> species. A signal that appeared at a  $g$  value of 2.07 can also be attributed to the superoxide species coordinated to Mg<sup>2+</sup>



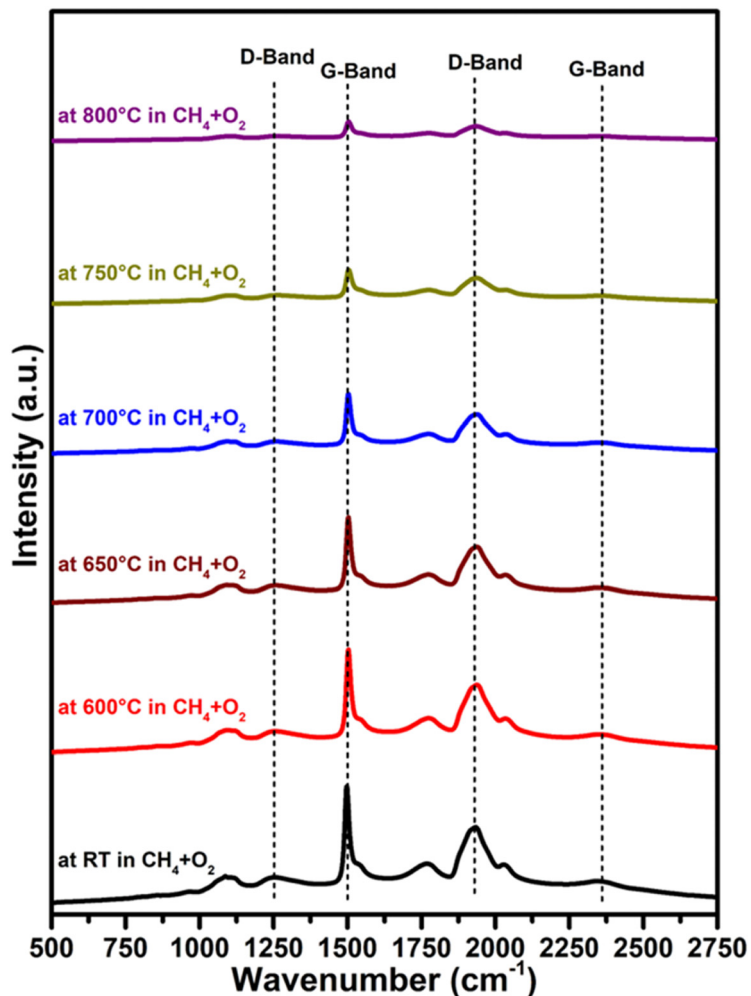


Fig. 7 *In situ* Raman spectra of the 3.6Li/MgO<sup>Dep-Sub</sup> catalyst at the indicated temperature in CH<sub>4</sub> + O<sub>2</sub> flow in 2 : 1 ratio.

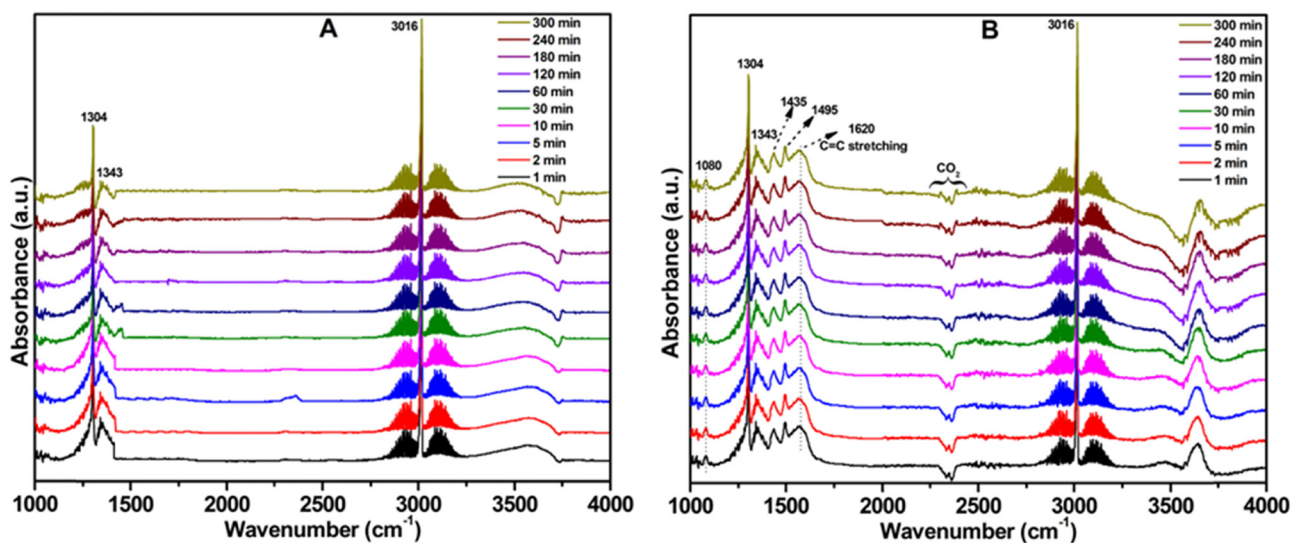


Fig. 8 *In situ* DRIFTS analysis: (A) MgO support and (B) 3.6Li/MgO<sup>Dep-Sub</sup> catalyst. Reaction conditions: temperature = 450 °C, N<sub>2</sub>:CH<sub>4</sub>:O<sub>2</sub> = 7 : 2 : 1, pressure = 1 bar, GHSV = 11 250 mL h<sup>-1</sup> g<sub>cat</sub><sup>-1</sup>.



ions as reported by Lunsford *et al.*<sup>62</sup> Additionally, some researchers attribute the signal that appeared at a  $g$  value of 2.00 to anionic vacancies or oxygen vacancies.<sup>63,64</sup> Earlier reports suggest that oxygen-centred radicals (such as  $\cdot\text{O}_2^-$ ,  $\cdot\text{OH}$ , and  $\cdot\text{OOH}$ ) can be formed on the surfaces of metal oxides having oxygen vacancies and could be detected by EPR and owing to the coordinatively unsaturated character of metal oxides, oxygen vacancies on the catalyst surface might act as sites for molecular oxygen activation *via* adsorption.<sup>63,64</sup>

## 4. Catalytic activity

The conversion of methane to ethane and ethylene is carried out at temperatures ranging between 600 and 800 °C for all the prepared catalysts including the support MgO. It was found that the synthesized MgO showed negligible activity, where the  $\text{C}_2$  selectivity was only 23.8% at 700 °C and this activity was due to the presence of defects in the MgO crystals.<sup>65</sup> Fig. 9(b) shows that methane conversion increases after Li loading, and the selectivity of the  $\text{C}_2$  products also increases. It has to be noted that various Li doping catalysts resulted in the displacement of  $\text{Mg}^{2+}$  by  $\text{Li}^+$ , leading to the formation of a negatively charged O centre and formation of the defect in the MgO matrix, which accounts for the

increased activity of the different Li-MgO catalysts compared to pure MgO.<sup>22</sup> The activity of our prepared Li-MgO catalyst is high compared to the earlier reported catalysts in the literature (see Table S2, ESI†). Fig. 9 shows the activity of the catalysts at different temperatures. At 700 °C, a higher methane conversion was observed for Li-doped MgO than for undoped MgO, and the  $\text{C}_2$  selectivity was greater than 80%. These findings show the generation of active species resulting from Li doping on MgO for the OCM reaction. In the case of methane conversion, all the Li-doped catalysts show low conversion at 600 °C and conversion increases with increasing temperature up to 800 °C. It was found that the activity of the catalyst follows the order:  $3.6\text{Li}/\text{MgO}^{\text{Dep-Sub}} > 1.9\text{Li}/\text{MgO}^{\text{Dep}} > 3.8\text{Li}/\text{MgO}^{\text{Dep}} > 7.4\text{Li}/\text{MgO}^{\text{Dep}}$  catalyst at 700 °C, as shown in Fig. 9.  $\text{C}_2$  selectivity was high at 600 °C for all Li-doped MgO catalysts and decreases with increasing temperature up to 800 °C, whereas  $\text{CO}_x$  (CO and  $\text{CO}_2$ ) selectivity increases with increasing temperature indicating that at high temperatures, over-oxidation of  $\text{C}_2$  products into  $\text{CO}_x$  occurs.

### 4.1. Effect of GHSV on $\text{CH}_4$ conversion, $\text{C}_2$ selectivity and $\text{C}_2$ yield as a function of temperature

In order to optimize the catalytic system, we tested the effect of GHSV with respect to the temperatures for all the catalysts.


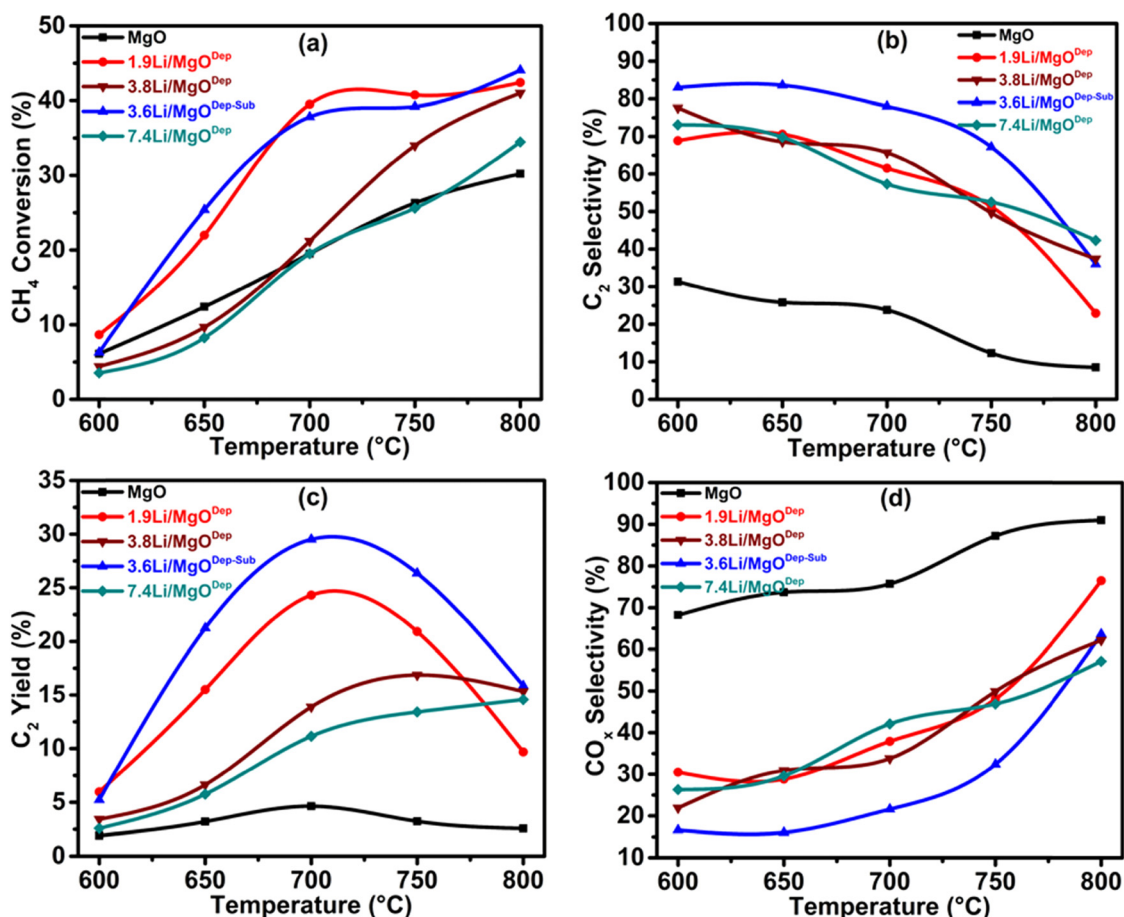


Fig. 9 Effect of temperature on (a)  $\text{CH}_4$  conversion, (b)  $\text{C}_2$  selectivity, (c)  $\text{C}_2$  yield and (d)  $\text{CO}_x$  selectivity. Reaction Conditions: temperature – 600–800 °C, pressure – atmospheric, GHSV –  $11250 \text{ mL h}^{-1} \text{ g}_{\text{cat}}^{-1}$ , catalyst weight – 0.30 g.



The activation of the methane first C-H bond is known to be the rate limiting step in oxidative methane coupling reaction. To understand the effect of Li doping in the OCM reaction as observed in experiments, the activation of CH<sub>4</sub> molecules was

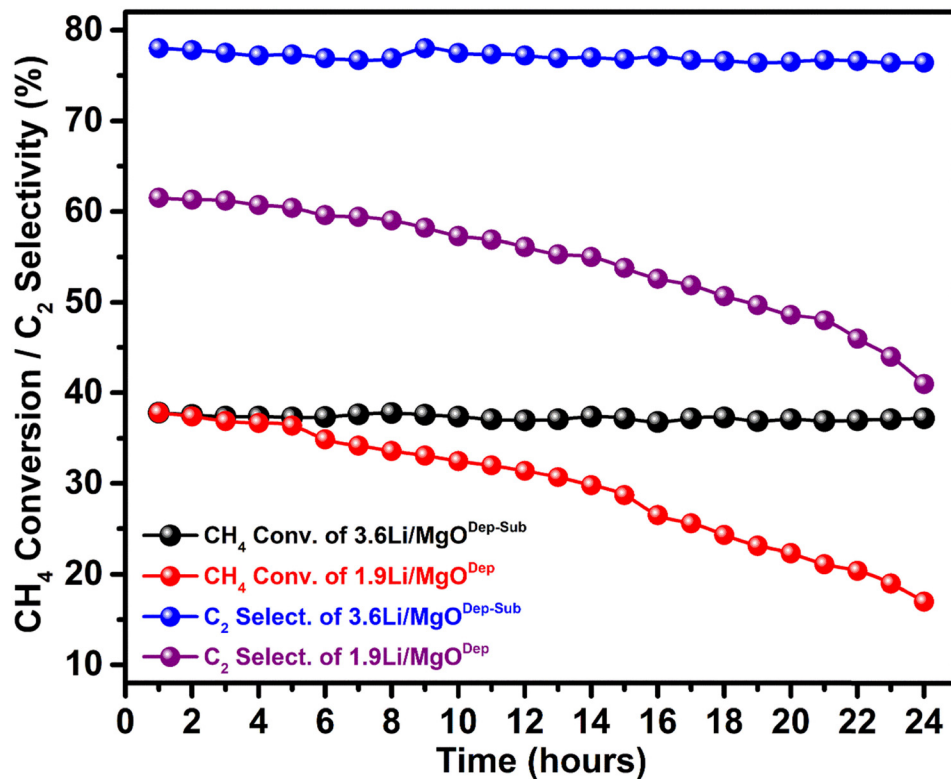


Fig. 11 Effect of TOS (Time on stream) on CH<sub>4</sub> conversion and C<sub>2</sub> selectivity for the 3.6Li/MgO<sup>Dep-Sub</sup> and 1.9Li/MgO<sup>Dep</sup> catalysts.

studied over the MgO(100) and doped Li<sub>2</sub>-MgO(100) surfaces, as shown in Fig. 14 and 15, respectively. As shown in Fig. 14(a), the CH<sub>4</sub> molecule adsorb physically over the MgO(100) surface.

The TS for C-H activation at the MgO(100) surface has been shown in Fig. 14(a'), where the C-H bond elongated from 1.1 Å in the reactant state (Fig. 14(a)) to 3.7 Å in the TS (Fig. 14(a')).

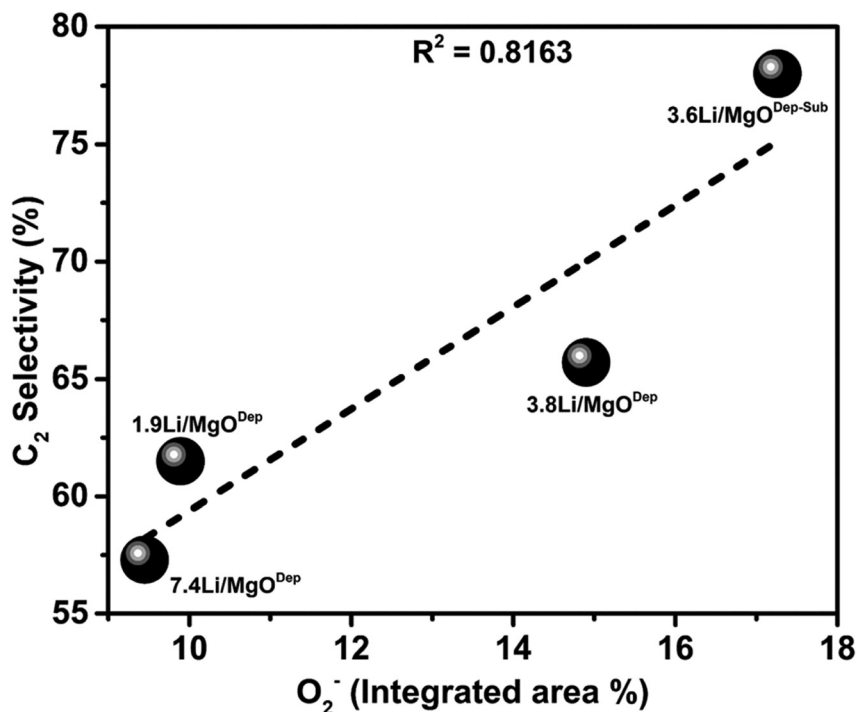


Fig. 12 Graph of superoxide (O<sub>2</sub><sup>-</sup>) area% vs. C<sub>2</sub> selectivity.



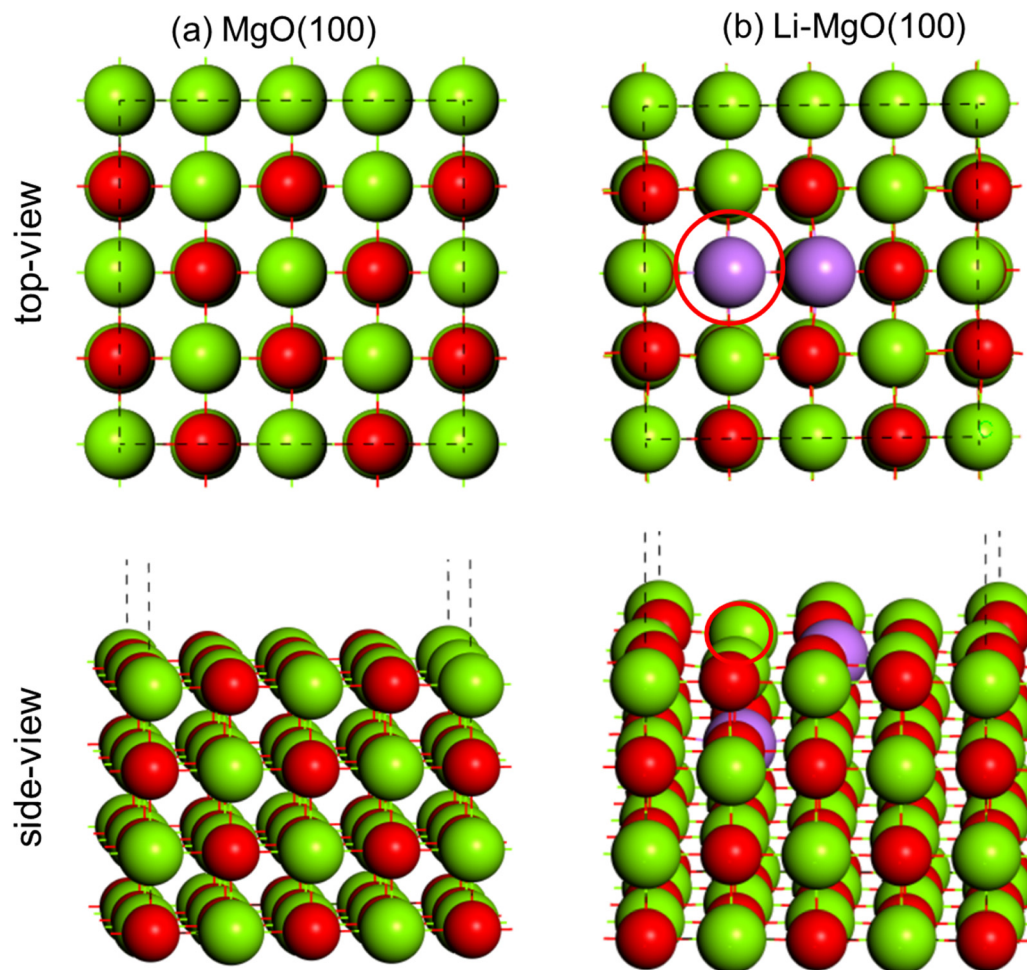


Fig. 13 DFT optimized geometry of (a) MgO(100) and (b)  $\text{Li}_2\text{-MgO(100)}$  surfaces. Color code: Mg (green), O (red) and Li (purple).

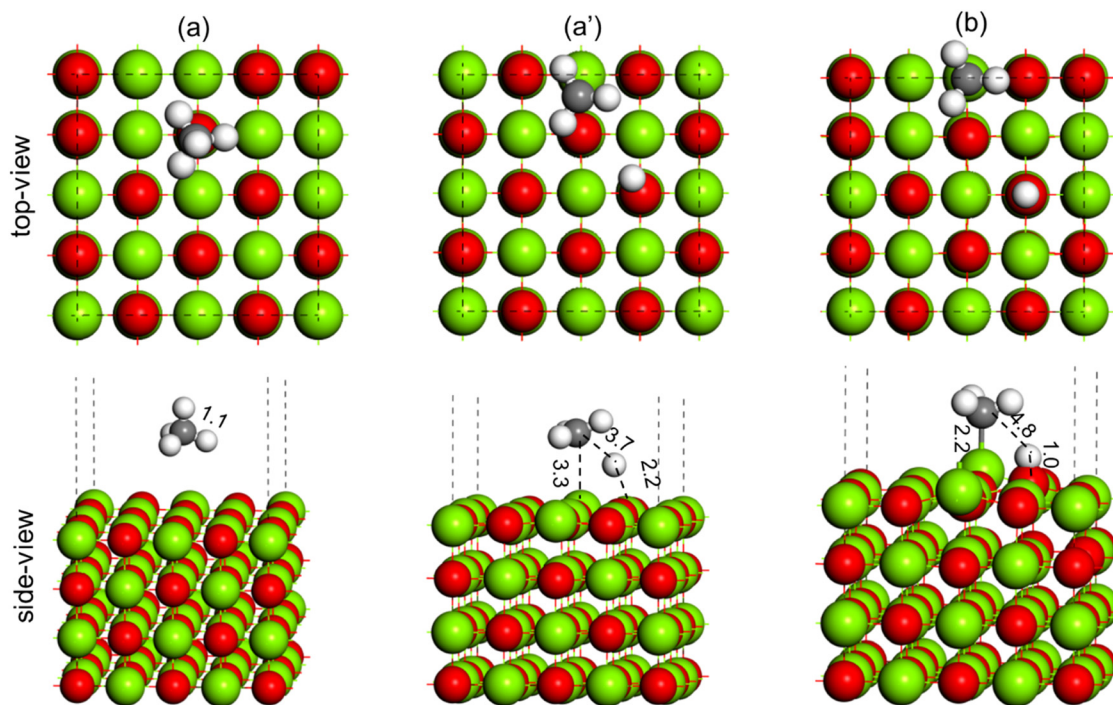


Fig. 14 Methane C–H bond activation over the MgO(100) surface, (a) reactant ( $\text{CH}_4$ ), (a') TS ( $\text{CH}_3\text{-H}$ ) and (b) product ( $\text{CH}_3 + \text{H}$ ). Color code: Mg (green), O (red), C (black) and H (white).



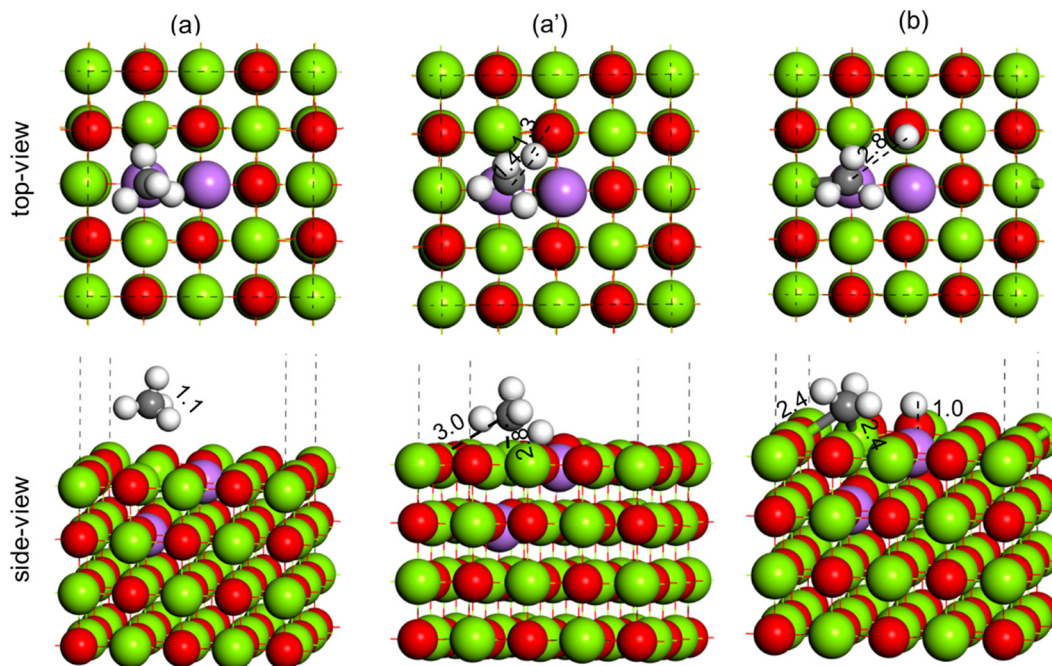


Fig. 15 Methane C–H bond activation over the  $\text{Li}_2\text{-MgO}(100)$  surface, (a) reactant ( $\text{CH}_4$ ), (a') TS ( $\text{CH}_3\text{-H}$ ) and (b) product ( $\text{CH}_3 + \text{H}$ ). Color code: Mg (green), O (red), Li (purple), C (black) and H (white).

Table 3 Methane C–H bond activation barrier and reaction energy over pure and Li-doped MgO catalyst surfaces

Catalytic system	Activation barrier (kcal mol <sup>-1</sup> )	Reaction energy (kcal mol <sup>-1</sup> )
MgO(100)	114.1	55.5
$\text{Li}_2\text{-MgO}(100)$	29.0	7.6
$\text{Li}_3\text{-MgO}(100)$	64.3	15.3
$\text{Li}_4\text{-MgO}(100)$	86.9	25.9

The Mg–C and O–H bond distances at the TS (Fig. 14(a')) were measured to be 3.3 Å and 2.2 Å, respectively. The activation barrier for methane C–H bond activation over the MgO(100) surface was calculated to be 114.1 kcal mol<sup>-1</sup> (Table 3). In the product state, the C–H bond of  $\text{CH}_4$  is completely dissociated to  $\text{CH}_3 + \text{H}$ , as O–H bonds (1.0 Å) and Mg–C (2.2 Å) bonds were formed, as can be seen in Fig. 14(b). Based on our calculation, the  $\text{CH}_4$  dissociation to  $\text{CH}_3 + \text{H}$  has an endothermic reaction energy of 55.5 kcal mol<sup>-1</sup> (Table 3).

To understand the promotional effect of Li doping to MgO in the OCM reaction, the  $\text{CH}_4$  dissociation to  $\text{CH}_3 + \text{H}$  was performed over the  $\text{Li}_2\text{-MgO}(100)$  surface, as shown in Fig. 15. The  $\text{CH}_4$  molecule physically adsorbs at the  $\text{Li}_2\text{-MgO}(100)$  surface, as shown in Fig. 15(a), where the C–H bond length was calculated to be 1.1 Å, similar to the undoped MgO(100) surface. In the TS, the C–H bond was elongated to 1.4 Å, whereas the O–H bond length was calculated to be 1.3 Å (Fig. 15(a')), much smaller compared to the undoped MgO(100) surface (3.7 Å and 3.3 Å, respectively), indicating higher stabilization of the TS in the  $\text{Li}_2\text{-MgO}(100)$  surface. The activation barrier for the  $\text{CH}_4$  C–H activation over the

$\text{Li}_2\text{-MgO}(100)$  surfaces was calculated to be 29.0 kcal mol<sup>-1</sup> (Table 3), nearly 85 kcal mol<sup>-1</sup> lower compared to the undoped MgO(100) surface. The reaction energy for  $\text{CH}_4$  dissociation to  $\text{CH}_3 + \text{H}$  at the  $\text{Li}_2\text{-MgO}(100)$  surface was also calculated to be less endothermic by 7.6 kcal mol<sup>-1</sup> (Table 3), nearly 50 kcal mol<sup>-1</sup> lower than that of the MgO(100) surface. The lower C–H activation barrier and low endothermic reaction energy indicate the higher OCM activity of the  $\text{Li}_2\text{-MgO}(100)$  catalyst surface compared to the undoped MgO(100) surface as seen in the experiments in Fig. 9.

To understand the effect of Li-loading on the OCM reaction,  $\text{Li-MgO}(100)$  surfaces with three Li atoms ( $\text{Li}_3\text{-MgO}(100)$ ) and four Li atoms ( $\text{Li}_4\text{-MgO}(100)$ ) were modelled to represent the MgO catalyst with high Li loading. Two different configurations were studied for the  $\text{Li}_3\text{-MgO}(100)$  surface, as shown in Fig. S8 (ESI†), where Li added close to the oxygen vacancy site (Fig. S8(a), ESI†) was found to be more stable by ~50 kJ mol<sup>-1</sup>, than where Li was added away from the oxygen vacancy site (Fig. S8(b), ESI†). Following same principle in the  $\text{Li}_4\text{-MgO}(100)$  surface the fourth Li atom was also kept near the oxygen vacancy site. Methane C–H activation was studied over  $\text{Li}_3\text{-MgO}(100)$  and  $\text{Li}_4\text{-MgO}(100)$  surfaces, as shown in Fig. 16 and 17, respectively.

During the C–H bond activation over the  $\text{Li}_3\text{-MgO}(100)$  surface, the C–H bond in methane (1.1 Å, Fig. 16(a)) was elongated to 2.2 Å in the TS (Fig. 16(a')), and the O–H bond length was calculated to be 2.4 Å (Fig. 16(a')), which are much higher compared to the  $\text{Li}_2\text{-MgO}(100)$  surface (1.4 Å and 1.3 Å, respectively), indicating destabilization of the TS in the  $\text{Li}_3\text{-MgO}(100)$  surface due to the additional Li atom. The activation barrier for C–H activation over the  $\text{Li}_3\text{-MgO}(100)$  surfaces was





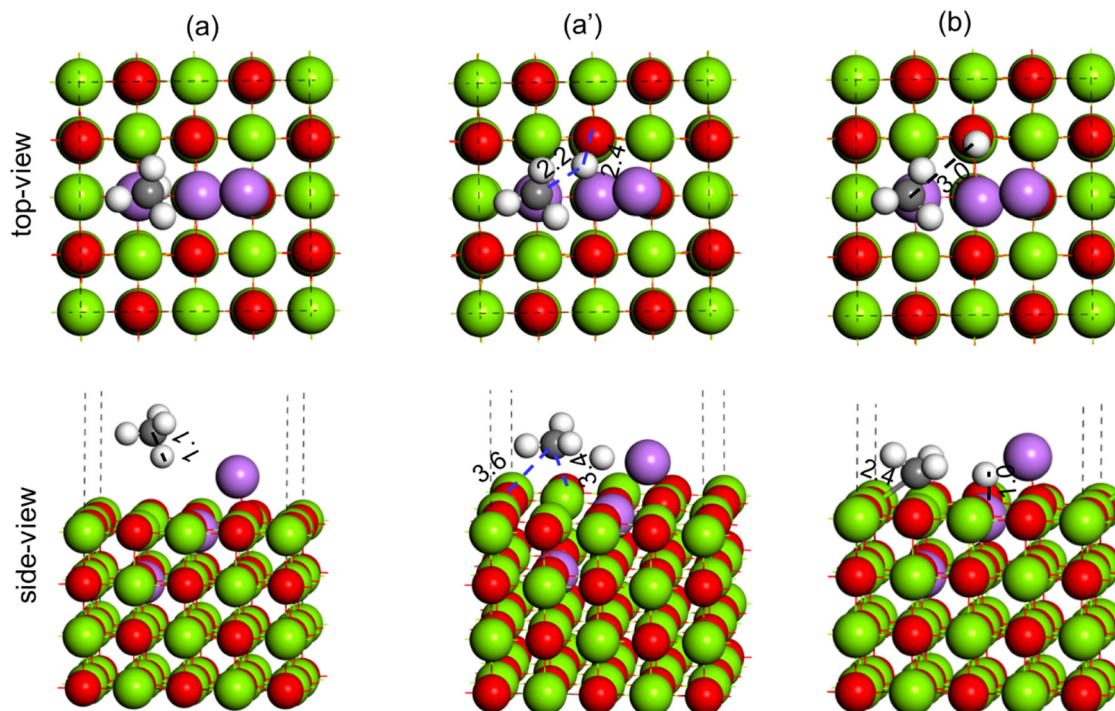


Fig. 16 Methane C–H bond activation over the  $\text{Li}_3\text{-MgO}(100)$  surface, (a) reactant ( $\text{CH}_4$ ), (a') TS ( $\text{CH}_3\text{-H}$ ) and (b) product ( $\text{CH}_3 + \text{H}$ ). Color code: Mg (green), O (red), Li (purple), C (black) and H (white).

also calculated to be much higher ( $64.3 \text{ kcal mol}^{-1}$ ) compared to the  $\text{Li}_2\text{-MgO}(100)$  surface ( $29.0 \text{ kcal mol}^{-1}$ ), as given in Table 3. The reaction energy for  $\text{CH}_4$  dissociation to  $\text{CH}_3 + \text{H}$

at the  $\text{Li}_3\text{-MgO}(100)$  surface was also calculated to be less endothermic by  $15.3 \text{ kcal mol}^{-1}$  (Table 3), nearly  $8 \text{ kcal mol}^{-1}$  higher than the  $\text{Li}_2\text{-MgO}(100)$  surface. Methane C–H activation

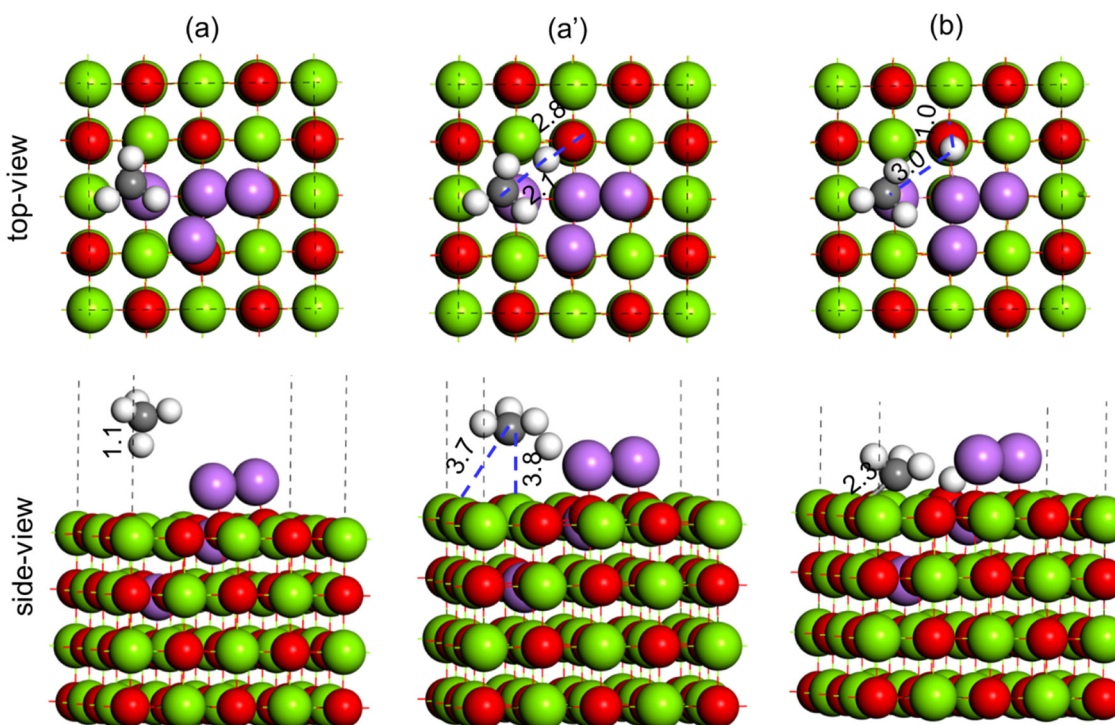


Fig. 17 Methane C–H bond activation over the  $\text{Li}_4\text{-MgO}(100)$  surface, (a) reactant ( $\text{CH}_4$ ), (a') TS ( $\text{CH}_3\text{-H}$ ) and (b) product ( $\text{CH}_3 + \text{H}$ ). Color code: Mg (green), O (red), Li (purple), C (black) and H (white).



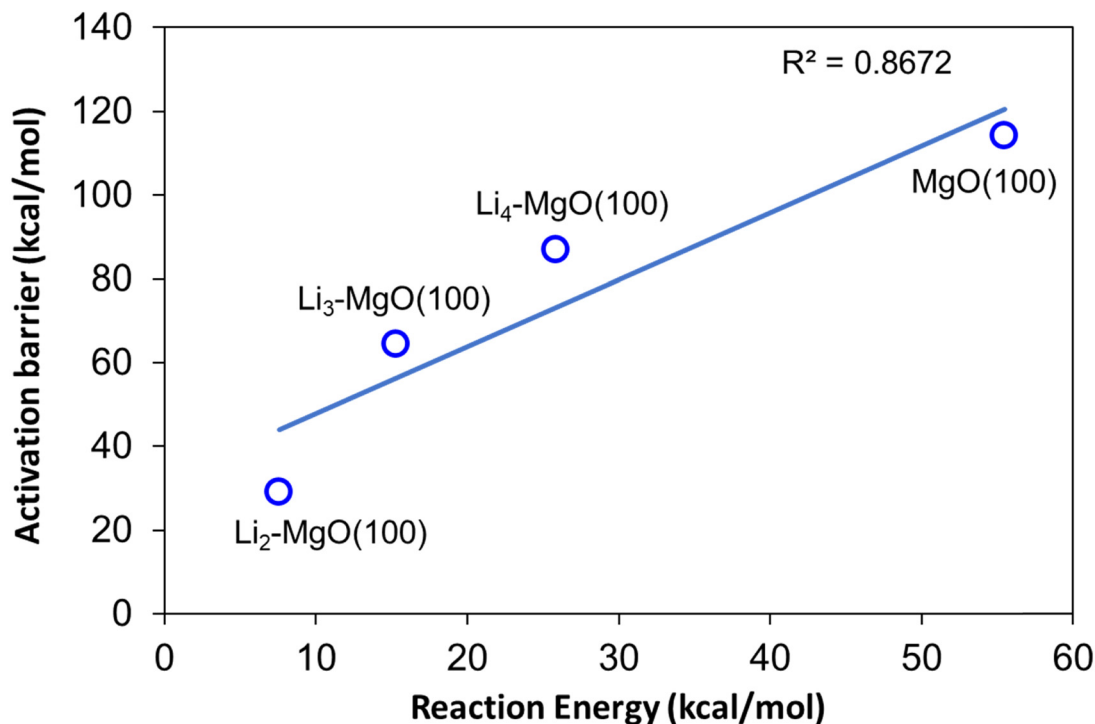


Fig. 18 BEP relationship between the activation barriers and reaction energies for methane C–H bond activation over the MgO(100) and Li-doped MgO(100) surfaces.

over the Li<sub>3</sub>-MgO(100) surface, shown in Fig. 17, shows similar trends. The activation barrier for the CH<sub>4</sub> C–H activation over the Li<sub>4</sub>-MgO(100) surfaces was also calculated to be even higher (86.9 kcal mol<sup>−1</sup>, Table 3), due to higher deactivation of the TS due to the presence of two extra Li atoms (Fig. 17).

The amount of Li doping was found to be an important factor in determining the OCM activity of the Li/MgO catalyst system, where the methane C–H bond activation barrier was found to decrease on Li doping on the MgO(100) surface; however, higher Li addition lead to an increase in methane activation barrier, which can cause a decrease in the overall OCM activity, as also observed in the experimental findings. The methane C–H bond activation barrier was found to follow the trend: Li<sub>2</sub>-MgO(100) < Li<sub>3</sub>-MgO(100) < Li<sub>4</sub>-MgO(100) < MgO(100). A BEP relationship was also observed for the MgO(100) and Li-doped MgO(100) surfaces, where the activation barrier and the reaction energies of the methane C–H bond dissociation reaction were found to follow a linear relationship, as shown in Fig. 18.

## 5. Conclusions

Li/MgO catalysts synthesized by a successive deposition–sublimation method showed high activity and stability during the oxidative conversion of methane to olefins. The XRD analysis of the Li–MgO catalyst showed Mg<sup>2+</sup> displacement by Li<sup>+</sup> in its crystal lattice and the formation of superoxide species (O<sub>2</sub><sup>−</sup>) and lattice oxygen species (O<sup>2−</sup>) that trigger the methane

activation. The substitution of Li<sup>+</sup> by Mg<sup>2+</sup> in the crystal lattice of MgO, resulting in the formation of active O negative sites, and the formation of a larger number of these defect sites played a significant role in the methane activation. Higher methane conversion was attributed to surface Li species, but higher C<sub>2</sub> selectivity was attributed to Li–MgO defect sites and negatively charged oxygen species. It is found that the amount of Li in the Li/MgO catalyst affects the catalytic activity during the methane oxidative coupling reaction. According to our results, the conversion and selectivity of methane to C<sub>2</sub>H<sub>4</sub> and C<sub>2</sub>H<sub>6</sub> increased as the Li loading increased, reached its highest value at 3.8%, and then decreased further with an increased Li loading. Active site Li<sup>+</sup>O<sup>−</sup> dispersion, which results from replacing Mg<sup>2+</sup> with Li<sup>+</sup> in the magnesium oxide lattice, depends on the amount of Li loaded. On the highly dispersed active sites Li<sup>+</sup>O<sup>−</sup>, methane activation is controlled thermodynamically, favouring the production of ethane and ethylene, whereas the kinetic factor dominates when the poorly dispersed Li<sup>+</sup>O<sup>−</sup> active sites dominate the reaction, resulting in low selectivity for ethane and ethylene and high selectivity for other by-products such as CO<sub>x</sub>. The activation barrier for the C–H activation of CH<sub>4</sub> over the Li<sub>2</sub>-MgO(100) surfaces was calculated to be 29.0 kcal mol<sup>−1</sup>, which is nearly 85 kcal mol<sup>−1</sup> lower compared to the undoped MgO(100) surface (114.1 kcal mol<sup>−1</sup>). However, as the Li doping was increased, the activation barrier for CH<sub>4</sub> dissociation was increased by 35 kcal mol<sup>−1</sup> and 57 kcal mol<sup>−1</sup> for Li<sub>3</sub>-MgO(100) and Li<sub>4</sub>-MgO(100), respectively. The lower activation barrier and lower endothermicity of the methane C–H activation obtained from DFT indicate the higher OCM





activity of the Li-MgO(100) catalyst compared to the undoped MgO(100) surface, as also seen in the experimental catalytic activity studies. The best C<sub>2</sub> yield was obtained over our 3.6Li/MgO<sup>Dep-Sub</sup> catalyst. Although the C<sub>2</sub> selectivity was sufficient above the 3.8% Li-loaded catalyst (7.4Li/MgO<sup>Dep</sup>) due to increasing defect sites, methane conversion was reduced due to a decrease in the active surface area of the catalyst.

## Author contributions

Rohan Singh Pal – design and performing experiments of the research work, manuscript writing; Swati Rana, Souvik Sadhu, Mukesh Kumar Poddar contributed to catalyst characterization; Tuhin Suvra Khan – design and performing DFT studies, manuscript writing and correction; Rajib Kumar Singha contributed to catalyst characterization and manuscript writing; Suman Sarkar – STEM and EELS analysis; Rahul Sharma – funding collaborator; Rajaram Bal – conceptualization and design of the whole study, design of experiments of the research work, manuscript correction.

## Conflicts of interest

The authors declare no conflicts of interest.

## Acknowledgements

R. S. P. thanks UGC, New Delhi, India for the fellowship. R. B. and the authors thank GAIL (India) Ltd. for the funding in the form of a collaborative project. The Director, CSIR-IIP, is acknowledged for his help and encouragement. The authors thank the Analytical Science Division, Indian Institute of Petroleum for analytical services.

## References

- 1 Y. Chen, X. Mu, X. Luo, K. Shi, G. Yang and T. Wu, *Energy Technol.*, 2020, **8**, 1900750.
- 2 X. Guo, G. Fang, G. Li, H. Ma, H. Fan, L. Yu, C. Ma, X. Wu, D. Deng and M. Wei, *Science*, 2014, **344**, 616–619.
- 3 J. T. Grant, J. M. Venegas, W. P. McDermott and I. Hermans, *Chem. Rev.*, 2018, **118**, 2769–2815.
- 4 I. Kim, G. Lee, H. B. Na, J.-M. Ha and J. C. Jung, *Mol. Catal.*, 2017, **435**, 13–23.
- 5 J. T. Grant, J. M. Venegas, W. P. McDermott and I. Hermans, *Chem. Rev.*, 2017, **118**, 2769–2815.
- 6 V. Lomonosov and M. Y. Sinev, *Kinet. Catal.*, 2016, **57**, 647–676.
- 7 G. Keller and M. Bhasin, *J. Catal.*, 1982, **73**, 9–19.
- 8 U. Zavyalova, M. Holena, R. Schlögl and M. Baerns, *ChemCatChem*, 2011, **3**, 1935–1947.
- 9 C. Hammond, S. Conrad and I. Hermans, *ChemSusChem*, 2012, **5**, 1668–1686.
- 10 P. Schwach, X. Pan and X. Bao, *Chem. Rev.*, 2017, **117**, 8497–8520.
- 11 H. Schwarz, *Angew. Chem., Int. Ed.*, 2011, **50**, 10096–10115.
- 12 P. Wang, G. Zhao, Y. Wang and Y. Lu, *Sci. Adv.*, 2017, **3**, e1603180.
- 13 A. Galadima and O. Muraza, *J. Ind. Eng. Chem.*, 2016, **37**, 1–13.
- 14 C. Karakaya, H. Zhu, C. Loebick, J. G. Weissman and R. J. Kee, *Catal. Today*, 2018, **312**, 10–22.
- 15 V. V. Thyssen, V. B. Vilela, D. Z. de Florio, A. S. Ferlauto and F. C. Fonseca, *Chem. Rev.*, 2022, **122**, 3966–3995.
- 16 J. Xu, L. Peng, X. Fang, Z. Fu, W. Liu, X. Xu, H. Peng, R. Zheng and X. Wang, *Appl. Catal., A*, 2018, **552**, 117–128.
- 17 Y. Zhang, J. Xu, X. Xu, R. Xi, Y. Liu, X. Fang and X. Wang, *Catal. Today*, 2020, **355**, 518–528.
- 18 J. Xu, Y. Zhang, Y. Liu, X. Fang, X. Xu, W. Liu, R. Zheng and X. Wang, *Eur. J. Inorg. Chem.*, 2019, 183–194.
- 19 D. Kiani, S. Sourav, J. Baltrusaitis and I. E. Wachs, *ACS Catal.*, 2019, **9**, 5912–5928.
- 20 S. Lim, J.-W. Choi, D. J. Suh, U. Lee, K. H. Song and J.-M. Ha, *Catal. Today*, 2020, **352**, 127–133.
- 21 T. W. Elkins, S. J. Roberts and H. E. Hagelin-Weaver, *Appl. Catal., A*, 2016, **528**, 175–190.
- 22 S. Arndt, G. Laugel, S. Levchenko, R. Horn, M. Baerns, M. Scheffler, R. Schlögl and R. Schomäcker, *Catal. Rev.*, 2011, **53**, 424–514.
- 23 Istadi and N. A. S. Amin, *J. Mol. Catal. A: Chem.*, 2006, **259**, 61–66.
- 24 L. Luo, R. You, Y. Liu, J. Yang, Y. Zhu, W. Wen, Y. Pan, F. Qi and W. Huang, *ACS Catal.*, 2019, **9**, 2514–2520.
- 25 Z. Zhang and S. F. Ji, *Adv. Mater. Res.*, 2014, 648–652.
- 26 S. Arndt, U. Simon, S. Heitz, A. Berthold, B. Beck, O. Görke, J.-D. Epping, T. Otremba, Y. Aksu and E. Irran, *Top. Catal.*, 2011, **54**, 1266–1285.
- 27 P. Myrach, N. Nilius, S. V. Levchenko, A. Gonchar, T. Risse, K. P. Dinse, L. A. Boatner, W. Frandsen, R. Horn and H. J. Freund, *ChemCatChem*, 2010, **2**, 854–862.
- 28 V. Alexiadis, J. Thybaut, P. Kechagiopoulos, M. Chaar, A. Van Veen, M. Muhler and G. Marin, *Appl. Catal., B*, 2014, **150**, 496–505.
- 29 U. Simon, S. Arndt, T. Otremba, T. Schlingmann, O. Görke, K.-P. Dinse, R. Schomäcker and H. Schubert, *Catal. Commun.*, 2012, **18**, 132–136.
- 30 N. A. S. Amin and S. E. Pheng, *Chem. Eng. J.*, 2006, **116**, 187–195.
- 31 K. Qian, R. You, Y. Guan, W. Wen, Y. Tian, Y. Pan and W. Huang, *ACS Catal.*, 2020, **10**, 15142–15148.
- 32 L. Luo, X. Tang, W. Wang, Y. Wang, S. Sun, F. Qi and W. Huang, *Sci. Rep.*, 2013, **3**, 1–7.
- 33 L. Luo, Y. Jin, H. Pan, X. Zheng, L. Wu, R. You and W. Huang, *J. Catal.*, 2017, **346**, 57–61.
- 34 R. You and W. Huang, *ChemCatChem*, 2020, **12**, 675–688.
- 35 K. Kwapien, J. Paier, J. Sauer, M. Geske, U. Zavyalova, R. Horn, P. Schwach, A. Trunschke and R. Schlögl, *Angew. Chem., Int. Ed.*, 2014, **53**, 8774–8778.
- 36 K. Sweeney, L. Halliburton, D. Bryan, R. Rice, R. Gerson and H. Tomaschke, *J. Appl. Phys.*, 1985, **57**, 1036–1044.
- 37 U. Zavyalova, M. Geske, R. Horn, G. Weinberg, W. Frandsen, M. Schuster and R. Schlögl, *ChemCatChem*, 2011, **3**, 949–959.



- 38 L. Leveles, K. Seshan, J. A. Lercher and L. Lefferts, *J. Catal.*, 2003, **218**, 307–314.
- 39 Y.-m Wu, S. Li and C.-y Li, *J. Fuel Chem. Technol.*, 2016, **44**, 1334–1340.
- 40 P. Bera, K. R. Priolkar, P. R. Sarode, M. S. Hegde, S. Emura, R. Kumashiro and N. P. Lalla, *Chem. Mater.*, 2002, **14**, 3591–3601.
- 41 S. Adak, R. S. Pal, T. S. Khan, M. K. Poddar, M. S. Ahmad, V. V. D. N. Prasad, M. A. Haider and R. Bal, *ChemistrySelect*, 2021, **6**, 13051–13059.
- 42 M. Rouchdi, E. Salmani, B. Fares, N. Hassanain and A. Mzerd, *Results Phys.*, 2017, **7**, 620–627.
- 43 R. Yousefi, A. K. Zak and F. Jamali-Sheini, *Mater. Sci. Semicond. Process.*, 2013, **16**, 771–777.
- 44 S. K. Sharma, B. Paul, P. Bhanja, M. K. Poddar, C. Samanta, T. S. Khan, M. A. Haider and R. Bal, *ChemCatChem*, 2021, **13**, 3290–3302.
- 45 H. Wang, M. Wang, S. Liu, N. Zhao, W. Wei and Y. Sun, *J. Mol. Catal. A: Chem.*, 2006, **258**, 308–312.
- 46 S. Xia, X. Guo, D. Mao, Z. Shi, G. Wu and G. Lu, *RSC Adv.*, 2014, **4**, 51688–51695.
- 47 S. Jain, J. Shah, N. S. Negi, C. Sharma and R. K. Kotnala, *Int. J. Energy Res.*, 2019, **43**, 4743–4755.
- 48 Y.-j Hao, B. Liu, L.-g Tian, F.-t Li, J. Ren, S.-j Liu, Y. Liu, J. Zhao and X.-j Wang, *ACS Appl. Mater. Interfaces*, 2017, **9**, 12687–12693.
- 49 A. J. Naylor, E. Makkos, J. Maibach, N. Guerrini, A. Sobkowiak, E. Björklund, J. G. Lozano, A. S. Menon, R. Younesi and M. R. Roberts, *J. Mater. Chem. A*, 2019, **7**, 25355–25368.
- 50 L. Chen, C. Xu, X.-F. Zhang and T. Zhou, *Phys. E*, 2009, **41**, 852–855.
- 51 J. H. Park, *Metall. Mater. Trans. B*, 2013, **44**, 938–947.
- 52 K. Ishikawa, N. Fujima and H. Komura, *J. Appl. Phys.*, 1985, **57**, 973–975.
- 53 H. Böckelmann and R. Schlecht, *Phys. Rev. B: Solid State*, 1974, **10**, 5225.
- 54 A. Weibel, D. Mesguich, G. Chevallier, E. Flahaut and C. Laurent, *Carbon*, 2018, **136**, 270–279.
- 55 B. C. Liu, B. Yu and M. X. Zhang, *Chem. Phys. Lett.*, 2005, **407**, 232–235.
- 56 J. H. Lunsford, X. Yang, K. Haller, J. Laane, G. Mestl and H. Knoezinger, *J. Phys. Chem.*, 1993, **97**, 13810–13813.
- 57 G. Karamullaoglu, S. Onen and T. Dogu, *Chem. Eng. Process.*, 2002, **41**, 337–347.
- 58 R. Martins, C. Veloso and M. Schmal.
- 59 S. C. Bhumkar and L. L. Lobban, *Ind. Eng. Chem. Res.*, 1992, **31**, 1856–1864.
- 60 J. X. Wang and J. H. Lunsford, *J. Phys. Chem.*, 1986, **90**, 3890–3891.
- 61 L. Wang, X. Yi, W. Weng, C. Zhang, X. Xu and H. Wan, *Catal. Lett.*, 2007, **118**, 238–243.
- 62 J. Lunsford, *Catal. Rev.*, 1974, **8**, 135–157.
- 63 S. Bhandari, R. Khatun, M. K. Poddar, A. C. Kothari and R. Bal, *Mol. Catal.*, 2022, **528**, 112473.
- 64 J. Lunsford, *Catalysis*, 1987, 227–256.
- 65 V. R. Choudhary, V. H. Rane and R. V. Gadre, *J. Catal.*, 1994, **145**, 300–311.
- 66 C. Trionfetti, I. V. Babich, K. Seshan and L. Lefferts, *Langmuir*, 2008, **24**, 8220–8228.

