


 Cite this: *Chem. Commun.*, 2024, 60, 2812

 Received 4th December 2023,  
Accepted 8th February 2024

DOI: 10.1039/d3cc05877h

rsc.li/chemcomm

**H-type supramolecular polymers with preferred helicity and highly efficient emission have been prepared from the self-assembly of chiral tetraphenylene-based monomers. Implementation of the one-dimensional fibers into dielectric nanoparticle arrays allows for a significant reshaping of fluorescence due to weak light–matter coupling.**

Tunable emission in optically active materials is a desirable feature for a wide range of applications, from optoelectronics to biomedicine.<sup>1–4</sup> Due to their structural and electronic properties,  $\pi$ -conjugated chromophores are ideal building blocks for the preparation of functional materials for optical technologies.<sup>5,6</sup> By exploiting the supramolecular interactions between  $\pi$ -surfaces, the molecular arrangement and aggregate morphology can be precisely controlled at the microscopic scale.<sup>7</sup> Nevertheless, drastic quenching of fluorescence is often observed in stacked architectures of emissive chromophores, limiting optical performance.

The proper molecular design of organic building blocks provides however an effective strategy for the preparation of luminescent assemblies. Recently, this phenomenon is often referred to as aggregation-induced emission (AIE), but it has been known for much longer.<sup>8,9</sup> The emission in these cases results from the suppression of non-radiative deactivation pathways through the restriction of intramolecular rotational or vibrational modes in the aggregate state, with tetraphenylethylene (TPE) serving as a prototypical example.<sup>10</sup> The optical properties of these emissive materials make them interesting

## Tunable emission from H-type supramolecular polymers in optical nanocavities†

 Giulia Lavarda,<sup>a</sup> Anton M. Berghuis,<sup>b</sup> Kripa Joseph,<sup>a</sup> Joost J. B. van der Tol,<sup>a</sup> Shunsuke Murai,<sup>c</sup> Jaime Gómez Rivas<sup>b</sup> and E. W. Meijer<sup>\*a</sup>

candidates for implementation in light-emitting, sensing and imaging technologies, among others.<sup>8,11–13</sup>

Therefore, the study of fluorescent H-type aggregates – where molecular units are stacked in a face-to-face arrangement – is critical to the advancement of emission-based applications. In this context, long-range ordered supramolecular polymers can be conveniently used as model systems to gain insights into the fundamental effects underlying optoelectronic materials.<sup>14,15</sup> Despite numerous reports on TPE aggregates, this core has rarely been employed in the preparation of H-type one-dimensional supramolecular polymers.<sup>16–19</sup> Instead,  $C_3$ -symmetric discotics decorated with amide motifs are typically used for the latter, ensuring the formation of helical fibers.<sup>20</sup>

On the other hand, light–matter coupling has attracted much attention in the last decades as a tool to engineer the optical properties of materials, showing significant potential for improving the performance of organic electronics.<sup>21,22</sup> In the weak coupling regime, excitonic transitions exchange energy with resonant photonic modes, resulting in the modification of emission properties.<sup>23,24</sup> Although this research area is rapidly expanding, the effect of light–matter coupling on the optical properties of H-type supramolecular polymers received little attention.<sup>25</sup>

In this communication, we report the tuning of emission from one-dimensional H-type assemblies *via* weak coupling to the surface lattice resonances in arrays of dielectric TiO<sub>2</sub> nanoparticles. To induce self-assembly into fluorescent supramolecular polymers, we designed a monomer featuring a TPE core decorated at the *para*-position of the phenyl rings with amide functionalities and solubilizing (*S*)-3,7-dimethyloctyl chains (**S-TPE**, Fig. 1). The target compound was synthesized by an amidation reaction between tetrakis(4-carboxy)-tetraphenylethylene precursor and 3,7-dimethyloctylamine using COMU as the coupling reagent. The product was purified by conventional laboratory techniques and fully characterized by <sup>1</sup>H-NMR, <sup>13</sup>C-NMR and mass spectrometry (see ESI† for further details).

UV-vis measurements of **S-TPE** solutions in 1,1,2,2-tetrachloroethane (TCE) show the typical absorption profile of TPE

<sup>a</sup> Institute for Complex Molecular Systems and Laboratory of Macromolecular and Organic Chemistry, Eindhoven University of Technology, Eindhoven 5600 MB, The Netherlands. E-mail: g.lavarda@tue.nl, e.w.meijer@tue.nl

<sup>b</sup> Eindhoven Hendrik Casimir Institute and Institute for Complex Molecular Systems, Eindhoven University of Technology, Eindhoven 5600 MB, The Netherlands

<sup>c</sup> Department of Material Chemistry, Graduate School of Engineering, Kyoto University, Katsura, Nishikyo, Kyoto 6158510, Japan

† Electronic supplementary information (ESI) available: Experimental methods, synthetic procedures and characterization data of new compounds, self-assembly studies and dispersion of the arrays. See DOI: <https://doi.org/10.1039/d3cc05877h>





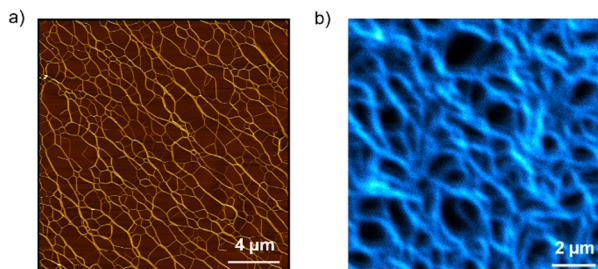


Fig. 3 (a) AFM image of a spin-coated sample prepared by deposition of a 20  $\mu\text{M}$  **S-TPE** solution in decalin/TCE 9 : 1 (v/v) on freshly cleaved mica. (b) Emission microscopy image of a drop-casted sample prepared by deposition of a 20  $\mu\text{M}$  **S-TPE** solution in decalin/TCE 9 : 1 (v/v) on glass ( $\lambda_{\text{ex}} = 405 \text{ nm}$ ).

are consistent with the knowledge gained from the study of hydrogen-bonded supramolecular polymers made of  $C_3$ -symmetric discotics.<sup>20</sup>

Next, we investigated the emissive properties of **S-TPE** supramolecular polymers embedded in optical nanocavities. The latter consist of dielectric nanoparticles arranged in a square lattice with a spacing close to the wavelength of visible light. These cavities exhibit high-quality optical resonances, known as Mie Surface Lattice Resonances (M-SLRs), resulting from the interaction between the localized Mie resonances of the individual nanoparticles and the in-plane diffraction orders (DOs) of the array.<sup>30–35</sup> The M-SLRs concentrate the electromagnetic fields near the array surface. Consequently, when an equilibrated solution of supramolecular TPE assemblies is drop casted onto the nanocavity surface (Fig. S13, ESI<sup>†</sup>),<sup>36</sup> the strong fields enhance the interaction of (the excitons in the) TPE fibers with light, resulting in enhanced emission at the resonant wavelengths of the cavity. These resonant wavelengths, which control the directional emission from the TPE fibers, can be tuned by modifying the cavity properties such as particle size, particle material, lattice symmetry, or lattice period.

In this connection, we designed an optical nanocavity consisting of  $\text{TiO}_2$  nanodisks with a diameter of 130 nm and a height of 94 nm on a quartz substrate (Fig. 4a), and varied the lattice period between 360 nm and 425 nm to control the emission spectrum of the TPE fibers on the cavity (Fig. 4c for SEM images and ESI<sup>†</sup> for fabrication details). The resonant energies of the in-plane diffraction orders of these arrays can be calculated using the 2D lattice equation:

$$E_{\text{DO}}(k_x)^2 = \left(\frac{\hbar c}{n_{\text{eff}}}\right)^2 \left[ k_x^2 + 2k_x \frac{2\pi}{a_x} q + \left(\frac{2\pi}{a_x} p\right)^2 + \left(\frac{2\pi}{a_y} q\right)^2 \right] \quad (1)$$

where  $k_x = k_0 \sin \theta$  is the incident wave vector along the  $x$  direction,  $n_{\text{eff}}$  is the effective refractive index of the surrounding medium,  $(p, q)$  are the grating orders along the  $x$  and  $y$  directions and  $a_x$  and  $a_y$  are the lattice vectors along the  $x$  and  $y$  directions.

We plot the calculated  $(\pm 1, 0)$ ,  $(0, \pm 1)$  and  $(\pm 1, \pm 1)$  diffraction orders for an array with a lattice period of 395 nm in Fig. 4b. With TPE fibers placed on the array, angle-resolved emission is measured using a Fourier microscope (see ESI<sup>†</sup> for further details). The observed emission from the coupled system closely matches the dispersion of the calculated diffraction orders (Fig. 4d). Thus, the lattice design provides direct control over the emission spectrum of the TPE fibers on the array. It should be noted that due to the interaction of the DOs with the Mie resonances of the individual particles and excitons in the fibers, the actual resonances are slightly shifted with respect to the calculated DOs.<sup>37</sup> The emission spectra at an angle of 18 degrees for different lattice constants ( $a_x$ ) are plotted in Fig. 4e, showing the tunability of the emission peak from 430 up to 510 nm. In Fig. 4f the emission in the normal direction is plotted, where the redistribution of fluorescence is controlled by the resonant wavelength ( $\lambda_{\text{res}}$ ) of the first

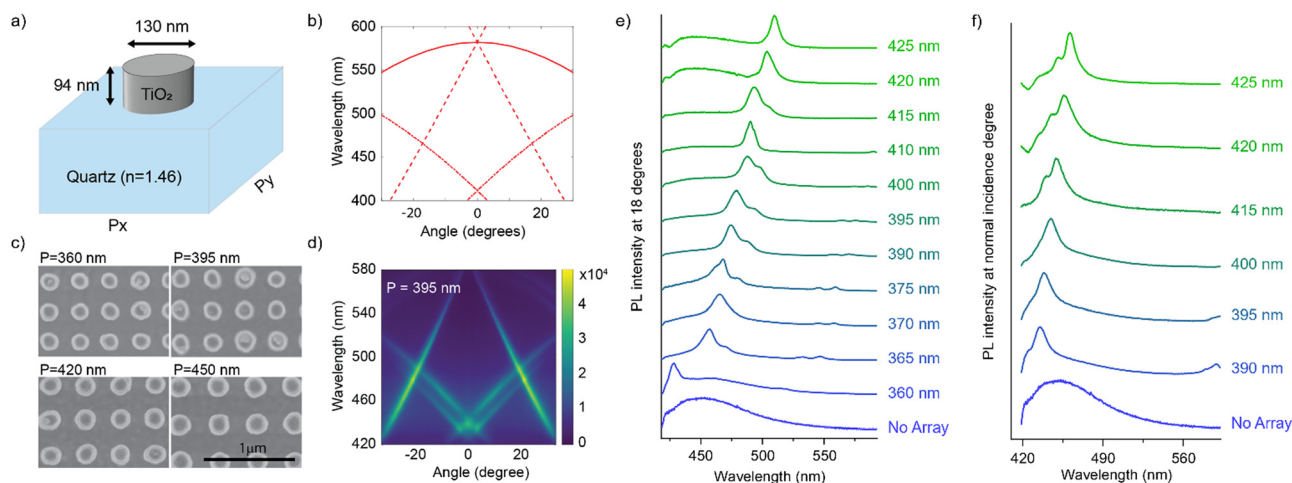


Fig. 4 (a) Schematic representation of one unit cell of the nano-cavity. (b) Calculated energies of the in-plane diffraction orders for an array with  $P_x = P_y = 395 \text{ nm}$  and  $n_{\text{eff}} = 1.47$ . The solid curve indicates the  $(\pm 1, 0)$  orders, the dashed curve the  $(0, \pm 1)$ , and the dash dotted curve the  $(\pm 1, \pm 1)$  orders. (c) SEM images of the cavity for a period of 360, 395, 420 and 450 nm. (d) Angle dependent fluorescence intensity from the TPE fibers on top of the cavity with 395 nm period. (e) and (f) Normalized fluorescence intensity of the TPE-fibers on different arrays at an angle of (e) 18 degrees and (f) 0 degrees.



diffraction order of the cavity. For these cases, eqn (1) simplifies to:

$$\lambda_{\text{res}} = \frac{a_x}{n_{\text{eff}}} \quad (2)$$

In summary, we have investigated the modulation of emission from H-type supramolecular polymers based on TPE chromophores by exploiting the surface lattice resonances of dielectric TiO<sub>2</sub> nanoparticles. Spectroscopic studies in dilute decalin/TCE solutions revealed the hydrogen bonding-driven assembly of TPE-based monomers into one-dimensional assemblies with preferred helicity. Within the stacks, restriction of intramolecular rotation of the phenyl moieties allows emission. AFM and confocal microscopy revealed the formation of tens of micrometers long fibers. Implementation of the latter into optical nanocavities composed of TiO<sub>2</sub> nanoparticle arrays resulted in a drastic redistribution of emission as a consequence of weak coupling to the M-SLR. The insights gained from this work pave the way for further studies on exciton-photon coupling in aggregated emissive systems and materials, opening new possibilities for the implementation of well-designed supramolecular assemblies in optoelectronics and photonics. The properties of H-type supramolecular polymers under different regimes of light-matter coupling and within chiral cavities will be investigated in the future in our laboratories.<sup>38,39</sup>

The authors acknowledge the support of the ICMS microscopy facilities, Dr Yuyang Wang for assistance with emission microscopy measurements, Stef Jansen for the computational modeling of supramolecular polymerization, Dr Stefan Meskers for fruitful discussion and the ICMS Animation Studio for the cartoon of the assembly. This work received funding from the European Research Council (H2020-EU.1.1., SYNMAT project, ID 788618), the Dutch Ministry of Education, Culture and Science for the Gravitation Program Functional Molecular Systems (024.001.035) and the Japan Society for the Promotion of Science for a Bilateral Joint Research Project (JPJSBP12 0239921). G. L. acknowledges a Marie Skłodowska-Curie Postdoctoral Individual Fellowship (101026072) for financial support. J. G. R. acknowledges the Nederlandse Organisatie voor Wetenschappelijk Onderzoek (NWO) for financial support through the Vici Grant No. 680-47-628.

## Conflicts of interest

There are no conflicts to declare.

## Notes and references

- H. Kobayashi, M. Ogawa, R. Alford, P. L. Choyke and Y. Urano, *Chem. Rev.*, 2010, **110**, 2620–2640.
- J. Han, S. Guo, H. Lu, S. Liu, Q. Zhao and W. Huang, *Adv. Opt. Mater.*, 2018, **6**, 1800538.
- X. Dai, Y. Deng, X. Peng and Y. Jin, *Adv. Mater.*, 2017, **29**, 1607022.
- M. Pan, W.-M. Liao, S.-Y. Yin, S.-S. Sun and C.-Y. Su, *Chem. Rev.*, 2018, **118**, 8889–8935.
- J. Li and K. Pu, *Chem. Soc. Rev.*, 2019, **48**, 38–71.
- A. Mateo-Alonso, *Chem. Mater.*, 2023, **35**, 1467–1469.
- Q. Li and Z. Li, *Acc. Chem. Res.*, 2020, **53**, 962–973.
- J. Mei, N. L. C. Leung, R. T. K. Kwok, J. W. Y. Lam and B. Z. Tang, *Chem. Rev.*, 2015, **115**, 11718–11940.
- F. Würthner, *Angew. Chem., Int. Ed.*, 2020, **59**, 14192–14196.
- J. Liu, H. Zhang, L. Hu, J. Wang, J. W. Y. Lam, L. Blancafort and B. Z. Tang, *J. Am. Chem. Soc.*, 2022, **144**, 7901–7910.
- F. Hu, S. Xu and B. Liu, *Adv. Mater.*, 2018, **30**, 1801350.
- Z. Zhao, H. Zhang, J. W. Y. Lam and B. Z. Tang, *Angew. Chem., Int. Ed.*, 2020, **59**, 9888–9907.
- J. Li, J. Wang, H. Li, N. Song, D. Wang and B. Z. Tang, *Chem. Soc. Rev.*, 2020, **49**, 1144–1172.
- L. Brunsveld, B. J. B. Folmer, E. W. Meijer and R. P. Sijbesma, *Chem. Rev.*, 2001, **101**, 4071–4097.
- T. Aida, E. W. Meijer and S. Stupp, *Science*, 2012, **335**, 813–817.
- H. Li, B. S. Li and B. Z. Tang, *Chem. – Asian J.*, 2019, **14**, 674–688.
- S. K. Saraswathi and J. Joseph, *ACS Appl. Nano Mater.*, 2022, **5**, 3018–3027.
- R. Liu, Z. Feng, X. Yan, Y. Lv, J. Wei, J. Hao and Z. Yang, *J. Am. Chem. Soc.*, 2023, **145**(31), 17274–17283.
- J. S. Oh, K. Y. Kim, M. Kim, S. H. Jung and J. H. Jung, *Angew. Chem., Int. Ed.*, 2023, **62**, e202300913.
- S. Cantekin, T. F. A. de Greef and A. R. A. Palmans, *Chem. Soc. Rev.*, 2012, **41**, 6125–6137.
- D. S. Dovzhenko, S. V. Ryabchuk, Y. P. Rakovich and I. R. Nabiev, *Nanoscale*, 2018, **10**, 3589–3605.
- Y. Xu, D. Ji, H. Song, N. Zhang, Y. Hu, T. D. Anthopoulos, E. M. Di Fabrizio, S. Xiao and Q. Gan, *Adv. Opt. Mater.*, 2018, **6**, 1800444.
- E. M. Lindh, P. Lundberg, T. Lanz, J. Mindemark and L. Edman, *Sci. Rep.*, 2018, **8**, 6970.
- C. Zang, S. Liu, M. Xu, R. Wang, C. Cao, Z. Zhu, J. Zhang, H. Wang, L. Zhang, W. Xie and C.-S. Lee, *Light: Sci. Appl.*, 2021, **10**, 116.
- J. Ren, Q. Liao, H. Huang, Y. Li, T. Gao, X. Ma, S. Schumacher, J. Yao, S. Bai and H. Fu, *Nano Lett.*, 2020, **20**, 7550–7557.
- T. Takeda, S. Yamamoto, M. Mitsuishi and T. Akutagawa, *Org. Biomol. Chem.*, 2016, **14**, 8922–8926.
- Although exciton coupling theory predicts a hypsochromic shift of the absorption band for H-type aggregates, additional factors (such as geometric changes of the monomer core upon assembly or gas-to-crystal shifts) may contribute to the displacement of the absorption features of the aggregate relative to the monomeric state.
- D. H. Zhao and J. S. Moore, *Org. Biomol. Chem.*, 2003, **1**, 3471–3491.
- Since the used mass-balance model for cooperative polymerization is based on a two species (monomer  $\rightleftharpoons$  polymer) equilibrium, the discrepancy between the experimental data and the optimized fit suggests the coexistence of additional processes affecting the concentration of monomeric units involved in the (monomer  $\rightleftharpoons$  polymer) process.
- V. E. Babicheva and A. B. Evlyukhin, *Laser Photonics Rev.*, 2017, **11**, 1700132.
- J. Li, N. Verellen and P. Van Dorpe, *J. Appl. Phys.*, 2018, **123**, 083101.
- G. W. Castellanos, P. Bai and J. Gómez Rivas, *J. Appl. Phys.*, 2019, **125**, 213105.
- G. W. Castellanos, S. Murai, T. V. Raziman, S. Wang, M. Ramezani, A. G. Curto and J. Gómez Rivas, *ACS Photonics*, 2020, **7**, 1226–1234.
- R. Heilmann, A. I. Väkeväinen, J.-P. Martikainen and P. Törmä, *Nanophotonics*, 2020, **9**, 267–276.
- F. Todisco, R. Malureanu, C. Wolff, P. A. D. Gonçalves, A. S. Roberts, N. A. Mortensen and C. Tserkezis, *Nanophotonics*, 2020, **9**, 803–814.
- Equilibrated solutions were obtained upon heating at 100 °C for 20 minutes and subsequent cooling to 20 °C at a rate of 1 °C min<sup>-1</sup>.
- J. Bohn, T. Bucher, K. E. Chong, A. Komar, D.-Y. Choi, D. N. Neshev, Y. S. Kivshar, T. Pertsch and I. Staude, *Nano Lett.*, 2018, **18**, 3461–3465.
- C. Genet, *ACS Photonics*, 2022, **9**, 319–332.
- H. Hübener, U. De Giovannini, C. Schäfer, J. Andberger, M. Ruggenthaler, J. Faist and A. Rubio, *Nat. Mater.*, 2021, **20**, 438–442.

