



Cite this: *Phys. Chem. Chem. Phys.*,
2024, 26, 19658

Zinc-doped C_4N_3 /BiOBr S-scheme heterostructured hollow spheres for efficient photocatalytic degradation of tetracycline†

Yaqi Liu,^{ab} Guicheng Luo,^{bc} Yichen Liu,^{ab} Zuozheng Xu,^{ab} Hengxin Shen,^b
Yuxiang Sheng,^b Yuan Zhu,^b Shuyi Wu,^{*d} Lizhe Liu^{id} ^{*a} and Yun Shan^{id} ^{*b}

Photocatalytic degradation of organic pollutants in water is of great significance to the sustainable development of the environment, but encounters limited efficiency when a single compound is used. Thus, there have been enormous efforts to find novel photocatalytic heterostructured composites with high performance. In this work, a novel S-scheme heterostructure is constructed with BiOBr and Zn^{2+} doped C_4N_3 ($Zn-C_4N_3$) by a solvothermal method for efficient photodegradation of tetracycline (TC), a residual antibiotic difficult to be removed from the aquatic environment. Thanks to Zn^{2+} -doping induced improvement in chemical affinity between $Zn-C_4N_3$ and BiOBr, well-formed $Zn-C_4N_3$ /BiOBr heterostructured hollow spheres are formed. This structure can efficiently suppress fast recombination of photogenerated electron-hole pairs to enhance the photocatalytic activity of BiOBr dramatically. At a room temperature of 25 °C and neutral pH 7, the catalyst can degrade a significant portion of TC pollutants within 30 min under visible light. Also, the $Zn-C_4N_3$ /BiOBr heterostructure displays good stability after recycling experiments. Free radical capture experiments and ESR tests show that $\bullet O_2^-$ is the main active substance for photocatalytic degradation of TC. This study provides new insights for constructing heterostructures with an intimate interface between the two phases for photocatalytic applications.

Received 9th March 2024,
Accepted 23rd June 2024

DOI: 10.1039/d4cp01043d

rsc.li/pccp

1. Introduction

Semiconductor-based heterostructures are considered to be promising photocatalyst candidates due to their ability to separate photogenerated charges efficiently.¹ A current attention attracting topic is S-scheme heterojunctions, which are composed of an oxidation type semiconductor and a reduction type semiconductor.² The formation of S-scheme heterojunctions requires that the conduction band (CB) position and the

Fermi level of the reduction photocatalyst (RP) must be higher than those of the oxidation photocatalyst (OP) at the same time.³ When the OP contacts the RP, the electrons in the RP are transferred to the OP through their interfaces and the band bends within the interface region, thus forming a built-in electric field from the RP to the OP.⁴ In the S-scheme heterojunction, the relatively useless electrons in the CB of the OP and the relatively useless holes in the conduction band (VB) of the RP are recombined and eliminated at the interface after photoexcitation.⁵ Besides effective separation of photogenerated electrons and holes, they also retain high oxidation and reduction potential which is a great benefit for degradation of aquatic organic pollutants.⁶ In general, at least one semiconductor in the heterostructure needs to be a good absorber of visible light to take advantage of solar energy efficiently.⁷ Among several proposed materials to harvest light, BiOBr with a suitable band gap (2.6–2.9 eV) stands out combining prominent optoelectronic properties with excellent stability and low cost.⁸ Indeed, various morphologies of BiOBr such as nanospheres and nanosheets have been widely used in CO_2 reduction,⁹ photocatalytic H_2O_2 ,¹⁰ degradation of organic pollutants,¹¹ photocatalytic nitrogen fixation,¹² etc. In particular, hollow flower-like spherical BiOBr with a large specific

^a Key Laboratory of Modern Acoustics, MOE, Institute of Acoustics and Collaborative Innovation Center of Advanced Microstructures, National Laboratory of Solid State Microstructures, Nanjing University, Nanjing, 210093, China.
E-mail: lzliu@nju.edu.cn

^b Nanjing Key Laboratory of Advanced Functional Materials, Nanjing Xiaozhuang University, Nanjing, 211171, People's Republic of China.
E-mail: yshan@njxc.edu.cn

^c School of Chemistry and Chemical Engineering, Nantong University, Nantong, 226019, China

^d Jiangsu Key Laboratory of Micro and Nano Heat Fluid Flow Technology and Energy Application, School of Physical Science and Technology, Suzhou University of Science and Technology, Suzhou, 215009, People's Republic of China.
E-mail: wsy@usts.edu.cn

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d4cp01043d>

surface area is beneficial to the absorption of visible light, which promotes the charge separation and accelerates the catalytic process.¹³

As an oxidation type semiconductor with a low valence band, BiOBr has been connected to many semiconductors with strong reduction ability to construct S-scheme heterostructured photocatalysts. For example, Zan *et al.*¹⁴ prepared CNQDs by an acid etching ultrasonic method and then compounded them on the surface of BiOBr by a hydrothermal method to form a novel 0D/2D CNQDs/BiOBr s-type heterojunction with close interface contact, showing an effective photocatalytic degradation ability for various organic compounds such as rhodamine B (RhB), Congo red (CR) and tetracycline (TC). BiOBr nanosheets were successfully assembled on several layers of the BP surface by liquid-phase ultrasonication combined with solvothermal treatment to construct a layered nanoheterojunction.¹⁵ The special structure created favorable conditions for the rapid transfer and separation of photogenerated electron-hole pairs, thereby enhancing the visible light photocatalytic removal of tetracycline (TC) and oxygen evolution activity. Wen *et al.*² fabricated S-scheme heterostructured AgBr/BiOBr-OV (ABO) *in situ* through a simple hydrothermal method, which induced the creation of surface oxygen vacancies and possessed the capacity to photocatalytically degrade sulfonamide antibiotics such as sulfoxazole (SIZ). Zhang *et al.*¹⁶ constructed a Bi₂Sn₂O₇/BiOBr (BSOB) S-scheme heterojunction by forming a new Bi-O bond through the defect-exposed Bi and O atoms to enhance the built-in electric field, thereby triggering photocatalytic nitrogen reduction efficiently. Most of these pioneering studies, however, focus only on the formation of an intimate interface between BiOBr and the other semiconductor while being unable to control the morphologies of heterostructured composites simultaneously, possibly because of the difficulties in tuning the size and chemical affinity between the two materials.

As a special organic half-metallic material, C₄N₃ is synthesized by the trimerization reaction of nitrile-functionalized imidazolium ionic liquids, and the scaffold of C₄N₃ is conjugated by triazine rings connected by carbon atoms.¹⁷ The spin polarization of the central carbon atom allows this metal-free half-metal material to possess outstanding charge transfer ability, and the efficient electron-hole separation rate based on singlet-to-triplet conversion contributes to the enhancement of photocatalytic activity.¹⁸ Nevertheless, half-metallic C₄N₃ is seldomly used to construct S-scheme systems largely due to its narrow band gap and poor chemical affinity which makes the direct growth of other semiconductors from the C₄N₃ surface difficult. Tian *et al.*¹⁹ prepared mesoporous Zn-doped g-C₃N₄ wrapped CdIn₂S₄ microsphere nanostructures by a simple hydrothermal method. Zn can partially replace the C element in the g-C₃N₄ skeleton and enhance the separation of photogenerated electrons and holes. It also plays a key role in exfoliating the stacked layers of g-C₃N₄ and enhancing the response to light. Deng *et al.*²⁰ conducted a comprehensive electronic structure analysis through density functional theory (DFT), indicating that the Zn atoms can coordinate with the abundant nitrogen ligands near the vacancies in C₄N₃ and showing excellent catalytic activity.

Inspired by the above investigations, if a suitable approach is employed to construct intimate heterojunctions between BiOBr and half-metallic C₄N₃, the obtained nanocomposites can combine the advantages of both components and greatly improve the photocatalytic activity. In this work, Zn²⁺ ions were introduced into C₄N₃ by one-step thermal polymerization, and then BiOBr was directly grown on the surface of zinc-doped C₄N₃ (Zn-C₄N₃) to form a novel Zn-C₄N₃/BiOBr S-scheme heterostructure. Owing to Zn²⁺ doping, the chemical affinity between Zn-C₄N₃ and BiOBr is effectively improved, endowing the formed heterostructure with an intimate interface. At the same time, the band gap of C₄N₃ is reduced, thus enhancing the response to light. Moreover, Zn-C₄N₃ with suitable size and flexibility after facile grinding and ultrasonication allows retaining of the flower-like hollow spherical structure of pristine BiOBr. This special hollow structure endows the photocatalyst with highly exposed reaction sites and elevates photon capture cross-section, greatly boosting the photocatalytic degradation of several common pollutants, such as rhodamine B (RhB), Congo red (CR) and tetracycline (TC). Compared with the original Zn-C₄N₃ and BiOBr, a significant portion of the TC pollutants can be rapidly decomposed at the Zn-C₄N₃/BiOBr heterostructure within 30 min.

2. Experimental

2.1. Materials

All the chemicals used in this work were of analytical reagent grade without further treatment. 1-Butyl-3-methylimidazolium chloride ([bmim][Cl], 99%), potassium tricyanomethane (95%), zinc nitrate hexahydrate (Zn(NO₃)₂·6H₂O, 99%), bismuth nitrate pentahydrate (Bi(NO₃)₃·5H₂O, >99.0%), cetyltrimethylammonium bromide (CTAB, 99%), polyvinylpyrrolidone (PVP, *M_w* = 58000) and ethylene glycol (EG, 99.5%) were purchased from Aladdin Reagent Co., Ltd (Shanghai, China). Ammonium oxalate (AO, 99.99%), 1,4-benzoquinone (BQ, >99.5%), *t*-butanol (TBA, >99.5%), and L-tryptophan (99.5%) were purchased from Macklin Reagent Co., Ltd (Shanghai, China). Deionized water was used in the experiments.

2.2. Preparation of Zn-C₄N₃

Oily precursor of C₄N₃ was synthesized following the previously reported procedure.¹⁸ 0.5 g of the as-prepared oily precursor and 0.01 g of Zn(NO₃)₂·6H₂O were dissolved in 50 mL ethanol under stirring for 4 h at room temperature. The resulting solution was dried overnight at 80 °C to volatilize the ethanol, and the residual mixed oily liquid was then calcined at 450 °C for 1 h in a muffle furnace at a heating rate of 5 °C min⁻¹. The obtained Zn-doped C₄N₃ (Zn-C₄N₃) samples with half-metallic properties were thoroughly ground and ultrasonicated for subsequent use. The C₄N₃ samples were prepared *via* the same procedures, except for the absence of Zn(NO₃)₂·6H₂O in the oily precursor.

2.3. Preparation of BiOBr and the Zn-C₄N₃/BiOBr heterostructure

BiOBr hollow microspheres were fabricated by a solvothermal method using ethylene glycol (EG) as the solvent. Firstly,

1 mmol of $\text{Bi}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$ was dissolved in 5 mL of EG as solution A. 1 mmol of CTAB and 1.125 mg of PVP were dissolved in 20 mL of EG as solution B. After vigorously stirring for 1 h, solution A was slowly added into solution B. Then the mixed solution was transferred into a 50 mL Teflon-lined stainless steel autoclave and heated at 120 °C for 10 h. The final precipitate was washed three times with deionized water and then dried at 60 °C for 10 h. The $\text{Zn-C}_4\text{N}_3/\text{BiOBr}$ heterostructure was prepared *via* the same method as BiOBr, except that 0.05 g of $\text{Zn-C}_4\text{N}_3$ was added to solution B under sonication.

2.4. Characterization

The morphology and elemental mapping of the samples were characterized by scanning electron microscopy (SEM, Tescan Mira 4) equipped with energy-dispersive X-ray spectroscopy (EDX). Transmission electron microscopy (TEM) images were acquired using an FEI Talos F200X G2 microscope. X-ray diffraction (XRD) patterns were recorded on an X-ray diffractometer (Rigaku, Ultima IV) with Cu K α radiation ($\lambda = 0.15406$ nm). Fourier transform infrared (FTIR) spectroscopy was conducted on a PerkinElmer Spectrum Two FT-IR spectrometer. The Raman spectra were acquired on a Raman spectrometer (Horiba HR Evolution) using a 514.5 nm argon ion laser. The surface chemical composition of the samples was determined by X-ray photoelectron spectroscopy (XPS, Thermo Scientific ESCALAB 250Xi) with C 1s (284.80 eV) as the reference. The Brunauer–Emmett–Teller (BET) specific surface areas and pore diameter distributions of the samples were measured by nitrogen adsorption–desorption isothermal analysis using a Micromeritics 3Flex at 77 K. The light harvesting capacity was assessed using a Shimadzu UV-3600 Plus spectrometer through diffuse reflectance spectroscopy (DRS). Photoluminescence (PL) emission spectroscopy and transient time-resolved photoluminescence decay measurements were performed on a fluorescence spectrometer (Edinburgh FLS1000, UK).

2.5. Photocatalytic tests

The catalytic degradation test was carried out in a 120 mL condensing cup at a constant temperature of 25 °C. The photocatalytic performance was evaluated in a typical photocatalytic system, which contained 100 mL of 25 mg L^{-1} TC aqueous solution and 20 mg of the photocatalyst. The mixed solution was stirred at room temperature for 30 min to reach adsorption equilibrium in a dark environment. Next, the catalytic activity of the photocatalyst was tested under a 300 W xenon lamp equipped with an AM 1.5 filter. In the process of photocatalytic degradation of TC, 3 mL of solution was filtered with a 0.22 μm filter every 10 min to separate the photocatalyst and the filtrate was detected on a UV-2450 spectrophotometer, especially at the characteristic wavelength of 356 nm.

2.6. Active species capturing and ESR tests

Active species capturing experiments were carried out using sacrificial agents AO (ammonium oxalate), BQ (1,4-benzoquinone), TBA (tertiary butyl alcohol) and L-histidine to remove

holes (h^+), superoxide radicals ($\cdot\text{O}_2^-$), hydroxyl radicals ($\cdot\text{OH}$) and singlet oxygen ($^1\text{O}_2$), respectively. The electron spin resonance (ESR) was tested on a Bruker EMXplus-6/1 ESR spectrometer, employing 5,5-dimethyl-1-pyrrolidine-*N*-oxide (DMPO) as a spin trapping reagent under simulated sunlight. Briefly, 10.00 mg of the sample was dispersed in 0.50 mL of deionized water or 0.50 mL of methanol containing 45 μL of DMPO to determine the hydroxyl radical ($\text{DMPO} \cdot \text{OH}$) or superoxide radical ($\text{DMPO} \cdot \text{O}_2^-$).

2.7. Photoelectrochemical measurements

10 mg of the sample powder was dispersed in the mixture of 10 μL of 5 wt% Nafion solution and 1 mL of ethanol under ultrasonication for at least 30 min, and then the slurry was evenly dropped on 0.7×1.0 cm^2 of fluorine-doped tin oxide (FTO) glass. Next, the FTO glass was dried in vacuum at 313 K for 12 h. The electrochemical test was performed on a CHI 660E workstation using 0.1 M Na_2SO_4 as the electrolyte and a traditional three-electrode configuration, in which the working electrode was sample-coated FTO glass, and a carbon rod and an Ag/AgCl electrode served as the counter and the reference electrode, respectively. Before testing, the electrolytic solution was degassed with argon for 30 min to remove the oxygen. In the photocurrent test, a xenon lamp with an AM 1.5 filter was used as the light source and the power density of light was set to be 100 mW cm^{-2} . Electrochemical impedance spectroscopy (EIS) was conducted on a potentiostat, where the amplitude was set at 10 mV and the frequency range spanned from 0.1 to 100 kHz. The Mott–Schottky plots were computed at frequencies of 800 Hz, 1000 Hz and 1200 Hz, respectively.

2.8. Density functional theory

All simulations were performed using the spin-polarized density functional theory (DFT) implemented in the Vienna ab initio simulation package (VASP). The projector augmented wave method is used to describe the ion–electron interaction. The exchange correlation potential is expressed in the Perdew–Burke–Ernzerhof (PBE) form of generalized gradient approximation (GGA). The truncation energy of the plane wave basis set is 450 eV. The energy and force convergence thresholds of the self-consistent field (SCF) iteration are set to 10^{-5} eV and 0.02 eV \AA^{-1} , respectively. In addition, Grimme's DFT-D3 method was also used to consider van der Waals interactions. A $3 \times 3 \times 1$ grid centered at the gamma (Γ) point was used for geometric optimizations and a $5 \times 5 \times 1$ k -point grid for electronic structure calculations. In order to avoid the interaction between two periodic images, a vacuum space of 15 \AA in the z -axis direction was used.

3. Results and discussion

3.1. Characterization of the $\text{Zn-C}_4\text{N}_3/\text{BiOBr}$ heterostructure

Fig. 1a and b and Fig. S1 (ESI †) display the representative SEM images of C_4N_3 , $\text{Zn-C}_4\text{N}_3$, BiOBr and the $\text{Zn-C}_4\text{N}_3/\text{BiOBr}$ heterostructure, respectively. As shown in Fig. S1a (ESI †), pure

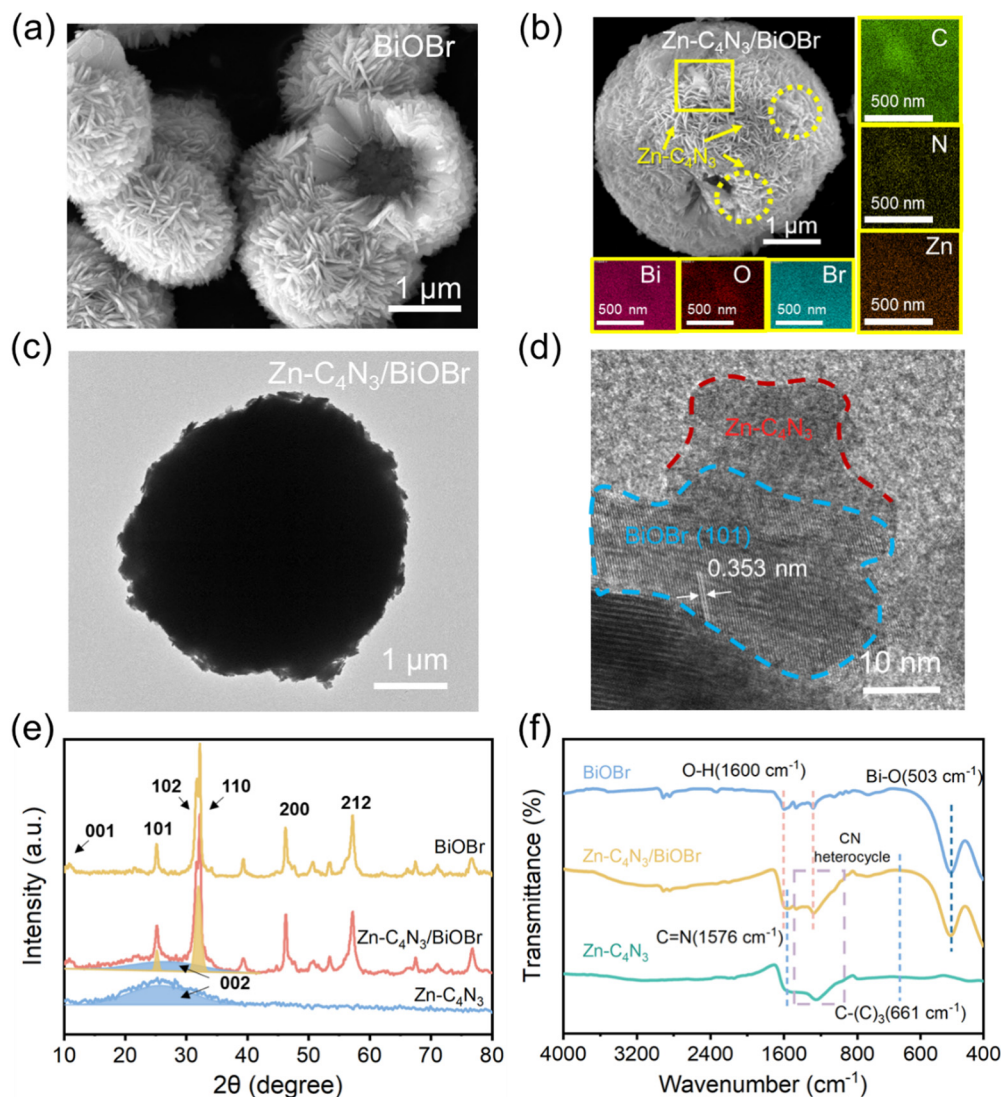


Fig. 1 (a) SEM image of BiOBr and (b) SEM image and EDS elemental mapping images of Zn-C₄N₃/BiOBr. (c) The whole TEM image of Zn-C₄N₃/BiOBr. (d) HRTEM images of the selected areas of Zn-C₄N₃/BiOBr. (e) XRD patterns and (f) FTIR spectra of Zn-C₄N₃, BiOBr and Zn-C₄N₃/BiOBr.

C₄N₃ exhibits an aggregated morphology composed of multi-layer smooth flakes, which is a typical structural characteristic of bulk C₄N₃ prepared by the thermal polymerization method.¹⁸ Compared with the stacked sheets of C₄N₃, Zn-doped C₄N₃ (Zn-C₄N₃) exhibits an unsmooth plane in Fig. S1b (ESI[†]). The uneven surface increases its affinity with BiOBr, making it easier for BiOBr to grow *in situ* on the surface of Zn-C₄N₃. The BiOBr sample obtained has the morphology of hollow microspheres composed of numerous nanosheets (Fig. 1a). Notably, the distinctive shape of hollow microspheres can give the material a large specific surface area and an enhanced cross-section for scattering photons, which makes it easier to capture and absorb incident irradiation.¹³ As shown in Fig. 1b, similar hollow microspheres are observed, except for an increase in the size of the nanosheets of the Zn-C₄N₃/BiOBr heterostructure after Zn-C₄N₃ loading. Besides, there exist some discernible regions characterized by lighter shades due

to the presence of Zn-C₄N₃. The elemental mapping of the area marked by a yellow box shows a conspicuous outline for the C, N and Zn elements, and Bi, O and Br elements are uniformly distributed. When using Zn-free C₄N₃ as seeds for the growth of BiOBr, there is an evident impact on the morphology, but no C₄N₃ can be discerned from the sleek BiOBr surface. Moreover, because C₄N₃ is too bulky, it is difficult to effectively combine with BiOBr to form heterojunctions. From Fig. S1c and d (ESI[†]), the difference before and after Zn doping can be clearly seen. These observations suggest that the incorporation of Zn element can lead to an improvement in chemical affinity between BiOBr and C₄N₃ to make BiOBr grow well from the surface of Zn-C₄N₃ for the formation of large-sized Zn-C₄N₃/BiOBr heterostructured nanosheets, which densely pack into a well-defined sphere of about 4 μ m diameter (Fig. 1c). As shown in Fig. 1d, the lattice spacing of the (101) crystal plane of BiOBr has a typical value of 0.353 nm,²¹ indicating that the flexible

sheet-like $\text{Zn-C}_4\text{N}_3$ does not affect the growth of BiOBr. More importantly, there exists an intimate interface between well-crystallized BiOBr and amorphous $\text{Zn-C}_4\text{N}_3$,¹⁸ which benefits fast charge transfer between them.

The powder XRD technique is used to unravel the structure of the as-obtained $\text{Zn-C}_4\text{N}_3/\text{BiOBr}$ hybrid nanocomposites (Fig. 1e). $\text{Zn-C}_4\text{N}_3$ displays a broad peak at about 26° designated to its (0 0 2) plane, characteristic of an interlayer stacked structure and weak crystallinity in the conjugated aromatic system.¹⁷ The addition of $\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ in the raw material has little effect on the structure of $\text{Zn-C}_4\text{N}_3$, and no relevant diffraction peak is observed. All diffraction peaks of the pure BiOBr sample located at 12.1° , 25.8° , 32.4° , 33.3° , 46.4° and 57.2° correspond to the crystal planes denoted by (0 0 1), (1 0 1), (1 0 2), (1 0 0), (2 0 0) and (2 1 2), respectively (JCPDS No. 09-0393). These distinct peaks corresponding to $\text{Zn-C}_4\text{N}_3$ and BiOBr are all detected in the $\text{Zn-C}_4\text{N}_3/\text{BiOBr}$ XRD pattern, which indicates the successful preparation of $\text{Zn-C}_4\text{N}_3/\text{BiOBr}$ hybrid nanocomposites.

Furthermore, the samples are characterized by Raman spectroscopy and the results are shown in Fig. S2 (ESI†). The vibration band at 110 cm^{-1} in BiOBr is related to the stretching A_{1g} mode of Bi-Br.²² The Raman spectrum of C_4N_3 can reveal the structural changes before and after Zn doping. In general, the peak located around 1358 cm^{-1} (D band) belongs to the “disordered” bonds which are related to the breathing mode of the six atom rings, while the peak located around 1560 cm^{-1} (G band) arises from the symmetric E_{2g} vibration which is caused by vibrational motion of the paired carbon sites.²³

The intensity ratio of I_D/I_G for $\text{Zn-C}_4\text{N}_3$ (1.315) is higher than that of C_4N_3 (1.125), indicating Zn doping increases the disordering of C_4N_3 ²⁴ and the zinc element has been successfully doped into the framework of C_4N_3 . The obvious peaks corresponding to $\text{Zn-C}_4\text{N}_3$ and BiOBr are observed in the Raman spectrum of $\text{Zn-C}_4\text{N}_3/\text{BiOBr}$, which once again proves the successful preparation of $\text{Zn-C}_4\text{N}_3/\text{BiOBr}$ hybrid nanocomposites.

The hybridization between $\text{Zn-C}_4\text{N}_3$ and BiOBr is further confirmed by FTIR spectroscopy. As illustrated in Fig. 1f, the pristine BiOBr demonstrates discernible peaks at 503 cm^{-1} (Bi-O bond²⁵) and 1600 cm^{-1} (associated with the bending and stretching vibrations of surface-adsorbed water^{21,26}). For $\text{Zn-C}_4\text{N}_3$, the absorption at 661 cm^{-1} appears due to the stretching vibration of C-(C)_3 . The bands at $1000\text{--}1500\text{ cm}^{-1}$ and 1576 cm^{-1} pertain to the CN heterocycle and C=N stretching vibrations, respectively. These typical characteristic peaks of $\text{Zn-C}_4\text{N}_3$ are all retained after combination. Added to that is the notable absorption peaks at 503 cm^{-1} and 1600 cm^{-1} from BiOBr, confirming the successful combination of BiOBr and $\text{Zn-C}_4\text{N}_3$.

The chemical compositions and valence states of BiOBr, C_4N_3 , $\text{Zn-C}_4\text{N}_3$ and $\text{Zn-C}_4\text{N}_3/\text{BiOBr}$ are revealed by XPS spectroscopy. Fig. 2a illustrates the C 1s high-resolution spectra of C_4N_3 , $\text{Zn-C}_4\text{N}_3$ and $\text{Zn-C}_4\text{N}_3/\text{BiOBr}$. The C 1s spectrum of C_4N_3 demonstrates three distinct peaks at 284.80 eV, 286.50 eV, and 288.84 eV, which can be ascribed to adventitious carbon, central carbon, and sp^2 -bonded carbon in triazine rings (N-C=N), respectively.²⁷ After Zn doping, the binding energies of center carbon and sp^2 -bonded carbon (N-C=N) shift to

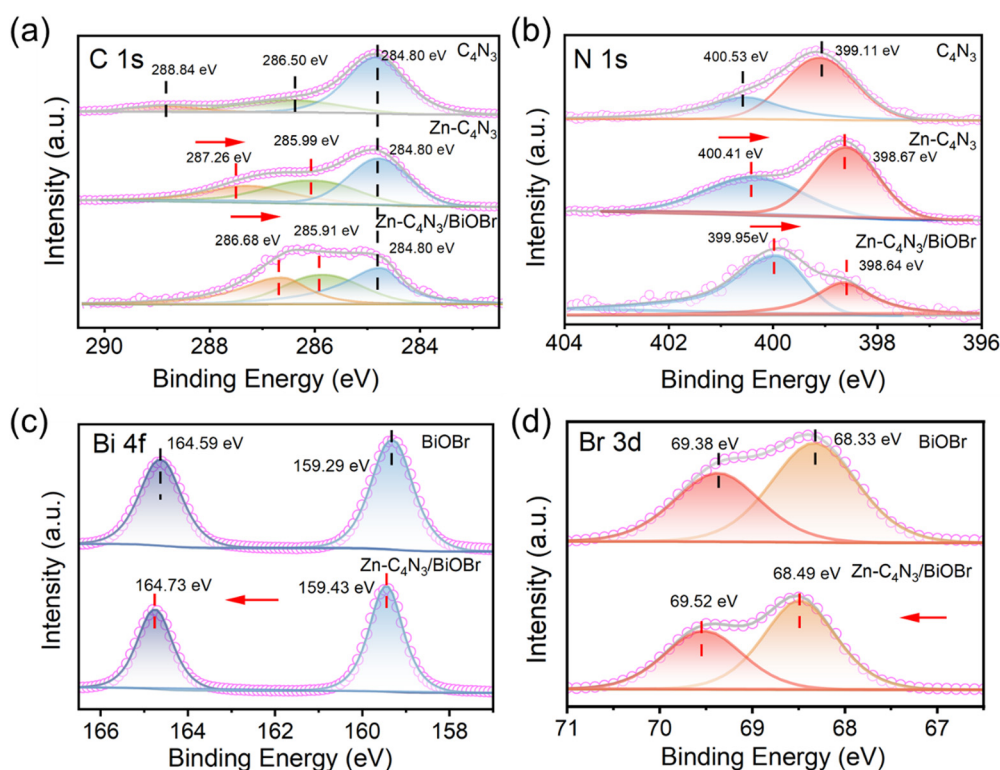


Fig. 2 C 1s (a), N 1s (b), Bi 4f (c) and Br 3d (d) XPS spectra of C_4N_3 , $\text{Zn-C}_4\text{N}_3$, BiOBr and $\text{Zn-C}_4\text{N}_3/\text{BiOBr}$.

lower values of 285.99 eV and 287.26 eV, respectively. Meanwhile, the peaks observed at 399.11 eV and 400.53 eV in the N 1s spectrum of C_4N_3 , originating from the nitrogen atoms present in $C-N=C$ and aliphatic $C=N$ groups, experience a shift to 398.67 eV and 400.41 eV, respectively (Fig. 2b). As shown in Fig. S3a (ESI[†]), Zn 2p spectra testify the existence of Zn^{2+} in $Zn-C_4N_3$ with spin-orbit splitting peaks of Zn 2p_{3/2} and Zn 2p_{1/2} peaks located at 1022.50 eV and 1045.52 eV, respectively.²² The incorporation of Zn makes the binding energies of C and N peaks shift negatively because the electronegativity of Zn (1.65) is lower than those of C (2.55) and N (3.04). From Raman and XPS analyses, it can be inferred that Zn has been successfully incorporated into the framework of C_4N_3 and regulates the electronic structure of C_4N_3 . After close contact with BiOBr, the binding energies of center carbon and sp²-bonded carbon (N-C=N) shift to lower values of 285.91 eV and 286.68 eV, respectively. Also, two peaks of N 1s experience a negative shift to 398.64 eV and 399.95 eV, respectively. Fig. 2c and d display the high-resolution XPS spectra of Bi 4f and Br 3d, respectively. For pure BiOBr, the binding energies of 159.29 eV and 164.59 eV can be, respectively, identified as Bi 4f_{7/2} and Bi 4f_{5/2} with a difference of 5.3 eV,⁷ confirming the presence of Bi³⁺. Br 3d_{5/2} and Br 3d_{3/2} can be observed at energy levels of 68.33 eV and 69.38 eV, respectively.²⁸ After the formation of the $Zn-C_4N_3$ /BiOBr heterostructure, the binding energies of Bi 4f and Br 3d both experience an upward shift. In addition, in the high-resolution O 1s spectra of BiOBr and $Zn-C_4N_3$ /BiOBr, the

lattice oxygen (O_{latt}) and surface oxygen vacancy (O_{vac}) can be detected at 530.12 eV and 531.44 eV respectively, with a slight increase in binding energy after combination (Fig. S3b, ESI[†]).²⁹ Note that the $n(O_{vac})/n(O_{latt})$ ratio of $Zn-C_4N_3$ /BiOBr is 0.74, obviously higher than 0.67 of BiOBr. Typically, a higher proportion of O_{vac} tends to enhance the formation of active radicals throughout the photocatalytic process. Moreover, the observed positive shift of Bi 4f, Br 3d and O 1s binding energies and the negative shift of C 1s and N 1s binding energies in $Zn-C_4N_3$ /BiOBr well verify the strong electronic interaction rather than a physical contact at the interface of $Zn-C_4N_3$ and BiOBr in the heterojunction.

3.2. Light utilization ability and charge transfer features

The Brunauer–Emmett–Teller (BET) specific surface area and pore size distributions of BiOBr and $Zn-C_4N_3$ /BiOBr are determined using N₂ adsorption–desorption isotherms. Based on the IUPAC classification, type IV isotherms and H₃-type hysteresis loops of the mesoporous structure are obtained at BiOBr and $Zn-C_4N_3$ /BiOBr (Fig. 3a), while pure $Zn-C_4N_3$ displays no hysteresis loop.²⁹ Notably, $Zn-C_4N_3$ /BiOBr exhibits a BET specific surface area of 23.90 m² g^{−1}, which is significantly higher than those of pure BiOBr (12.52 m² g^{−1}) and pure $Zn-C_4N_3$ (1.93 m² g^{−1}). The pore size distribution curves in Fig. S4 (ESI[†]) demonstrate two distinct ranges of pore size distribution in BiOBr. Pores with a size smaller than 10 nm are attributed to the compact arrangement of nanoparticles, while



Fig. 3 (a) N₂ adsorption–desorption isotherms of BiOBr and $Zn-C_4N_3$ /BiOBr. (b) UV-vis absorption spectra of the different catalysts (inset: digital pictures of photocatalysts). (c) and (d) The band gaps of BiOBr, C_4N_3 and $Zn-C_4N_3$.

pores larger than 10 nm originate from external irregular aggregation. Significantly, there is a decrease in the minimum pore proportion of Zn-C₄N₃/BiOBr. These observations indicate that the direct growth of BiOBr at Zn-C₄N₃ helps produce heterostructures with larger size, which self-assemble into nanosheets more loosely.

The optical absorption characteristics of the as-prepared BiOBr, Zn-C₄N₃, and Zn-C₄N₃/BiOBr are investigated by UV-vis diffuse reflectance spectroscopy (UV-vis DRS). Pure BiOBr demonstrates significant absorption within the wavelength range of 200 to 420 nm owing to its wide band gap (Fig. 3b). The conspicuous absorption band edge of BiOBr is situated at 441 nm, which corresponds to its pale yellow appearance (inset of Fig. 3b). Compared with C₄N₃, Zn-C₄N₃ exhibits an impressive absorption range that stretches to more than two thousand nanometers as a result of its dark appearance (Fig. 3b and Fig. S5, ESI[†]), covering the entire visible light spectrum. As a result, the heterostructure showcases significantly enhanced light absorption ability in both the visible light region and the ultraviolet region despite a relatively low weight ratio of Zn-C₄N₃. This improvement can be seen clearly from the distinct alteration in color, confirming the synergistic effect of combining Zn-C₄N₃ with BiOBr. The excellent light capture ability of Zn-C₄N₃ in the heterostructure opens up a way to optimize the photocatalytic process, which can absorb a wider spectrum, especially in the visible light range, thus improving the efficiency of the photocatalytic reaction. In addition, the UV-vis DRS spectrum can be used to calculate the band gap energy of BiOBr and Zn-C₄N₃ according to the formula: $\alpha h\nu = A(h\nu - E_g)^{n/2}$, where α , h , ν , A , E_g and n represent the absorption coefficient, Planck constant, light frequency, band gap and transition feature of the semiconductor, respectively ($n = 4$ for the indirect nature of BiOBr and $n = 1$ for the direct nature of C₄N₃^{18,30}). As illustrated in Fig. 3c and d, the calculated band gaps for BiOBr, C₄N₃ and Zn-C₄N₃ are 2.75 eV, 1.44 eV and 1.22 eV, respectively, which indicates that, due to the addition of Zn element, the band gap of C₄N₃ is significantly reduced and the light response is enhanced. The narrow band gap of C₄N₃ is consistent with its half-metallicity feature, contributing to its distinct electronic behavior. Besides, the Mott-Schottky curves of BiOBr and Zn-C₄N₃ are shown in Fig. S6 (ESI[†]). The positive slope of the curves suggests that the prepared samples are n-type semiconductors⁷ and the potential of the conduction band (CB) in n-type semiconductors is proximate to the potential of the flat band (FB).³¹ The conduction band (CB) positions of BiOBr and Zn-C₄N₃ are -0.191 eV and -0.679 eV, respectively, in relation to the Ag/AgCl electrode (pH = 7). Meanwhile, according to the conversion formula of the standard hydrogen electrode: $E_{\text{NHE}} = E_{\text{Ag/AgCl}} + E_{\text{Ag/AgCl}}^*$, these positions are 0.006 and -0.482 eV, respectively, in relation to the normal hydrogen electrode (NHE, pH = 7),¹⁴ where $E_{\text{Ag/AgCl}}$ is the experimental potential measured against the Ag/AgCl reference electrode, and $E_{\text{Ag/AgCl}}^*$ is the standard potential of Ag/AgCl at 298 K (0.197 V). Based on the empirical equation $E_{\text{VB}} = E_{\text{CB}} + E_g$, the VB potentials of BiOBr and Zn-C₄N₃ are 2.756 and 0.738 eV,

respectively, where E_{VB} , E_{CB} and E_g are the VB potential, CB potential and the value of band gap, respectively.³²

The photogenerated charge carriers in BiOBr can rapidly recombine to emit photons, as shown in Fig. 4a. The strong photoluminescence (PL) emission of BiOBr is composed of two main peaks. One emission band is centered at approximately 450 nm, which can be attributed to its band-to-band emission with energy equivalent to the bandgap of BiOBr (2.75 eV).⁷ The other peak located at about 570 nm can be attributed to defect emission.³³ In contrast, a very weak emission peak is discernible in the PL spectrum of Zn-C₄N₃, and to some degree it can be considered non-luminescent. As a result, the PL intensity of the Zn-C₄N₃/BiOBr heterostructure decreases sharply, indicating that the recombination of photogenerated carriers can be effectively inhibited.³⁴ The photogenerated charge transfer dynamics is studied using time-resolved photoluminescence (TRPL) spectroscopy of the ns-level in Fig. 4b. The radiative lifetimes (τ) can be calculated through a biexponential function fitting decay curves (Table S1, ESI[†]). The fluorescence lifetime of the photogenerated charge carriers in Zn-C₄N₃/BiOBr, expressed as short ($\tau_1 = 0.62$ ns), long ($\tau_2 = 4.43$ ns), and average ($\tau_{\text{av}} = 3.33$ ns), is comparatively shorter than that of pristine BiOBr ($\tau_1 = 1.38$ ns, $\tau_2 = 12.06$ ns, $\tau_{\text{av}} = 7.30$ ns). Additionally, the charge transfer rate, which can be determined using the formula $k = 1/\tau_{\text{av}}$,²¹ is found to be 0.137 ns⁻¹ for BiOBr and 0.300 ns⁻¹ for Zn-C₄N₃/BiOBr. The decrease in the fluorescence lifetime of Zn-C₄N₃/BiOBr indicates that there exists a special electron transfer channel.³⁵⁻³⁷ The effective charge separation and transfer at the heterojunction interface can reduce the recombination of photogenerated charges, making the photogenerated charges easily captured by the reactants for the subsequent redox reaction.

The effective separation of photogenerated electron-holes in the heterostructures is further confirmed by the photocurrent measurements. Fig. 4c illustrates the photocurrent response curves of BiOBr, Zn-C₄N₃, and Zn-C₄N₃/BiOBr fabricated on the electrodes by turning the irradiation light on and off for several rounds to collect the $I-t$ curves. Both BiOBr and Zn-C₄N₃ exhibit a low current intensity upon irradiation due to the lack of an efficient pathway for photogenerated carrier transfer. Impressively, Zn-C₄N₃/BiOBr shows remarkably improved photocurrent, which is advantageous to photocatalytic degradation. Consistently, the formation of the Zn-C₄N₃/BiOBr heterostructure greatly reduces the charge transfer resistance, as revealed by the electrochemical impedance spectroscopy (EIS) results in Fig. 4d. This enables fast and effective charge separation, leading to excellent performance in the following photocatalytic degradation.

3.3. Photocatalytic degradation of TC

3.3.1. Catalytic performance evaluation. As a model, the as-prepared photocatalysts were used for photodegradation of TC, a residual antibiotic in the aquatic environment. On one hand, TC has almost no degradation after 90 min of solar irradiation without the introduction of the catalyst, which implies that the

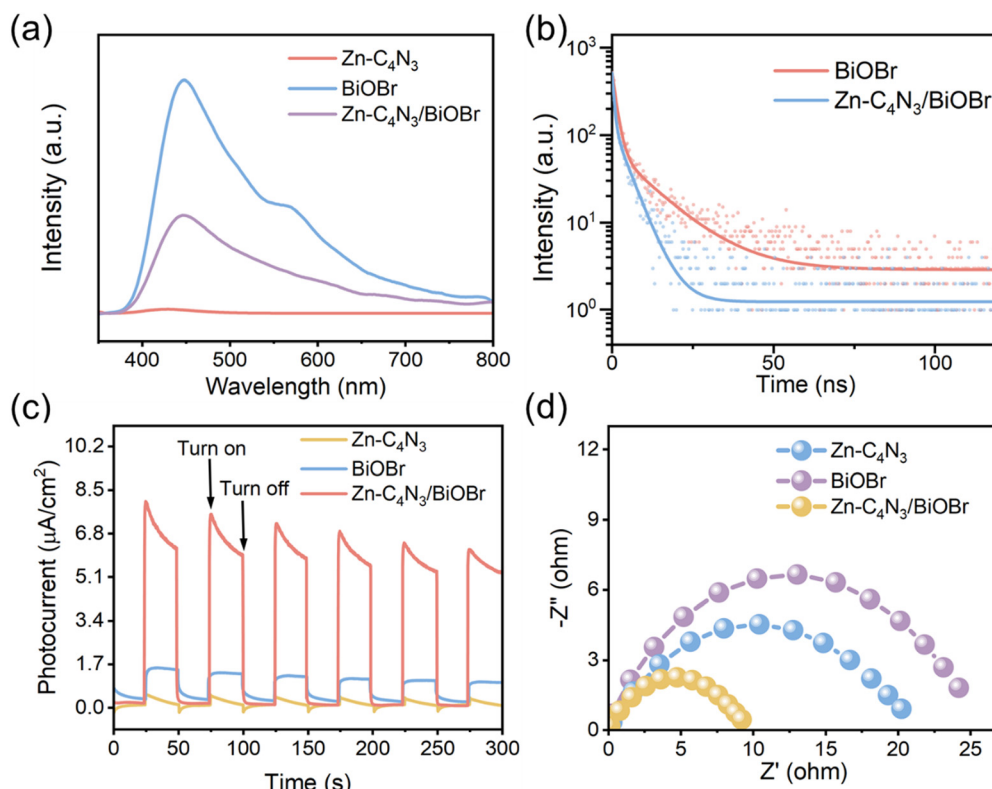


Fig. 4 (a) PL spectra (320 nm excitation) of photocatalysts. (b) Time-resolved PL decay curves (monitored at 440 nm) of photocatalysts. (c) Transient photocurrent responses and (d) EIS curves of photocatalysts.



Fig. 5 (a) Photodegradation of TC at photocatalysts. (b) Degradation reaction kinetics of TC over photocatalysts. (c) Effect of the initial pH value over Zn-C₄N₃/BiOBr in degradation of TC. (d) Five recycling runs over Zn-C₄N₃/BiOBr in degradation of TC. Note that the experiment in Fig. 5a was conducted without pH adjustment.

self-photocatalysis of TC can be ruled out (Fig. S7a, ESI†). On the other hand, TC is adsorbed almost completely within 30 min in the absence of light (Fig. S7b, ESI†). Thus, an absorption-desorption equilibrium between the catalyst and the pollutant is essentially established within 30 minutes before the photocatalytic reaction. Based on this consideration, the degradation efficiency as a function of time is presented in Fig. 5a. Compared to BiOBr and Zn-C₄N₃, the Zn-C₄N₃/BiOBr heterostructure exhibits superior degradation performance. 46.74% and 5.77% of TC can degrade at BiOBr and Zn-C₄N₃ after 60 min solar irradiation but about 49% of TC degradation at Zn-C₄N₃/BiOBr can occur within the initial 10 min. When the light irradiation is extended to 60 min, approximately 95.68% of TC can be removed. The variation in degradation can be verified through detailed UV-vis absorption spectra (Fig. S8a–c, ESI†). To quantitatively observe the behavior of different photocatalysts, the equation $\ln(C_0 - C_t) = kt$ based on the assuming pseudo-first-order kinetics can be employed to obtain the TC degradation rate constants (Fig. 5b). Among them, the slope k represents the apparent reaction rate constant. According to the results, the apparent reaction rate constant of Zn-C₄N₃/BiOBr is as high as $49.5 \times 10^{-3} \text{ min}^{-1}$, which is 5.5 times that of BiOBr ($9.0 \times 10^{-3} \text{ min}^{-1}$) and 81.1 times that of Zn-C₄N₃ ($0.61 \times 10^{-3} \text{ min}^{-1}$). The reason for the high apparent reaction rate constant of the composite is the successful construction of the separation system of photogenerated carriers, so that when the catalyst is excited by light, the photogenerated electrons on BiOBr quickly transfer to Zn-C₄N₃ to recombine with holes, thus maintaining the strong oxidation of holes on BiOBr and the strong reducibility on Zn-C₄N₃, which is beneficial to the photocatalytic degradation of TC. This is consistent with the spatial separation system of photogenerated carriers successfully constructed in Ag₃PO₄@MWCNTs@PPy composites mentioned by Lin *et al.*³⁸ The photogenerated electrons of Ag₃PO₄ are easily transferred to MWCNTs, and the photogenerated holes tend to migrate to the surface of PPy, so that the separation efficiency of photogenerated carriers is higher and the photocatalytic activity is greatly enhanced.

Due to the variety of pollutants, the ability to degrade other organic pollutants is of great significance for the practical application of Zn-C₄N₃/BiOBr. Here, the photocatalytic degradation performance of Zn-C₄N₃/BiOBr on several common pollutants was investigated (Fig. S9a, ESI†). The degradation efficiencies of Congo red (CR), methylene blue (MB) and rhodamine B (RhB) reached 84.45%, 71.71% and 74.57%, respectively, within 60 min light irradiation. These results illustrate the efficient degradation activity of Zn-C₄N₃/BiOBr for a variety of organic pollutants, which shows its great potential for practical application.

Fig. 5c presents the influence of pH on TC degradation, in which the rate of TC degradation increases with the initial pH rising from 1 to 7 but decreases as the pH further increases from 9 to 11. At low pH, H⁺ ions participate in trapping of the •OH species, thus inhibiting TC degradation.²⁹ Meanwhile, excessively alkaline conditions will also impact its degradation rate. This is likely attributable to the electrostatic repulsion

between the charge on the surface of the catalyst and the ions in the solution.³⁹ Therefore, the highest degradation rate of tetracycline occurs in solution close to neutral. The initial unadjusted pH of the TC solution is 6.62. At this pH, TC degradation closely approaches the optimal pH of 7, indicating that Zn-C₄N₃/BiOBr can be used for practical wastewater treatment without pH adjustment.

At a fixed dosage of the Zn-C₄N₃/BiOBr photocatalyst, distinct degradation efficiencies were obtained when treating different initial TC concentrations (20–40 mg L⁻¹) (Fig. S9b, ESI†). The highest degradation efficiency is found at a TC concentration of 25 mg L⁻¹. When an appropriate amount of TC solution is adsorbed on the surface of Zn-C₄N₃/BiOBr, it acts as a mediator for photogenerated electron-hole pairs, hindering their recombination on the surface of the catalyst.⁴⁰ However, an increased concentration of TC molecules in the reaction solution results in fewer photons entering the reaction solution, thus decreasing the absorption of photons by the Zn-C₄N₃/BiOBr photocatalyst and directly affecting the degradation rate. Therefore, the optimal concentration of TC is 25 mg L⁻¹ in the following experiments.

The impact of catalyst dosage on the TC degradation rate is also tested with different Zn-C₄N₃/BiOBr dosages, and the results are shown in Fig. S9c (ESI†). With the dosage of the catalyst increasing from 10 mg to 20 mg, the degradation rate of TC increases, mainly due to the increase of active sites with the increase of catalyst dosage, thus promoting the formation of active radicals. However, further increase to 30 mg will bring about a slight decrease in the degradation rate of TC. This can be attributed to the light scattering caused by excess dosage, resulting in the loss of partial visible light for exciting the photocatalyst.²⁵ Therefore, 20 mg is the best dosage of Zn-C₄N₃/BiOBr.

Apart from high degradation efficiency, the Zn-C₄N₃/BiOBr catalyst also has excellent stability (Fig. 5d). After five cycles in the process of degrading TC, Zn-C₄N₃/BiOBr still maintains high photocatalytic activity. In addition, the morphology of Zn-C₄N₃/BiOBr remains unchanged and the XRD pattern of Zn-C₄N₃/BiOBr still exhibits a distinguishable crystal structure after the long-term stability test (Fig. S10, ESI†), indicating that there is no obvious structural deterioration. Moreover, our proposed Zn-C₄N₃/BiOBr sample is superior to most previously reported catalysts at kinetic rates and degradation efficiency (Table S2, ESI†), exhibiting an obvious advantage in TC degradation.

3.3.2. Catalytic mechanism. The work function (Φ) is an important property reflecting the escape ability of free electrons from the Fermi level (E_f) to the vacuum level. In order to clarify the mechanism behind the excellent photocatalytic performance of Zn-C₄N₃/BiOBr, the work functions of BiOBr and Zn-C₄N₃ are calculated using density functional theory, and the results are shown in Fig. 6a and b. The work functions are calculated using the following equation: $\Phi = E_{\text{vac}} - E_f$, where E_{vac} represents the electrostatic potential of the vacuum level and E_f represents the Fermi energy.³² The calculated work functions of BiOBr and Zn-C₄N₃ are 6.982 eV and 5.048 eV,



Fig. 6 The work function of (a) BiOBr and (b) Zn-C₄N₃. (c) Schematic illustration of the Zn-C₄N₃/BiOBr heterostructure: before and after contact in the dark.

respectively, and the difference in work function is a prerequisite for the formation of an interfacial electric field between Zn-C₄N₃ and BiOBr. As observed in Fig. 6c, the E_f of Zn-C₄N₃ is higher than that of BiOBr.⁵ Hence, when Zn-C₄N₃ and BiOBr closely contact each other to form a heterojunction, the free electrons in Zn-C₄N₃ with high E_f will spontaneously drift to BiOBr with low E_f until a new equilibrium state E_f is established. The drift of electrons from Zn-C₄N₃ to BiOBr leads to the redistribution of charges on the interface of the heterojunction, in which the band edge of Zn-C₄N₃ is bent upward due to the loss of electrons, while BiOBr exhibits a downward band edge caused by obtaining electrons, thus forming an internal electric field from Zn-C₄N₃ to BiOBr.

In order to identify the types of reactive oxygen species (ROS) involved in TC degradation, various scavengers are introduced into the photocatalytic system. With the addition of AO (h^+ scavenger), BQ ($\bullet O_2^-$ scavenger), TBA ($\bullet OH$ scavenger), and L-histidine (1O_2 scavenger),³⁸ the degradation efficiency of TC decreases significantly from 95.68% to 77.82%, 19.61%, 82.78% and 93.55%, respectively (Fig. 7a). This indicates that the role of

ROSs in TC degradation decreases in the following order: $\bullet O_2^- > h^+ > \bullet OH > ^1O_2$.

To further validate the involvement of $\bullet O_2^-$ and $\bullet OH$ in the catalytic process, electron spin resonance (ESR) spectroscopy is employed using DMPO as a spin trapping reagent. There exist no ESR signals in the dark but six distinct peaks corresponding to DMPO- $\bullet O_2^-$ when the light is on (Fig. 7b), thus effectively verifying that the existence of $\bullet O_2^-$ is not dependent on the self-decomposition of Zn-C₄N₃/BiOBr in the photocatalytic process.^{41–43} Upon replacing the solvent methanol with water to capture DMPO- $\bullet OH$, a seven-line spectrum is acquired instead of the hydroxyl signal (Fig. S11, ESI†). This phenomenon occurs due to the strong oxidation of Zn-C₄N₃/BiOBr itself, resulting in the oxidation-induced ring opening of the capture agent DMPO.^{44,45}

According to the results of radical trapping experiments and ESR tests, two possible degradation mechanisms for the degradation of TC at the Zn-C₄N₃/BiOBr heterostructure can be proposed. The conventional type II heterojunction charge transfer mechanism (Fig. 7c) suggests that Zn-C₄N₃ and BiOBr






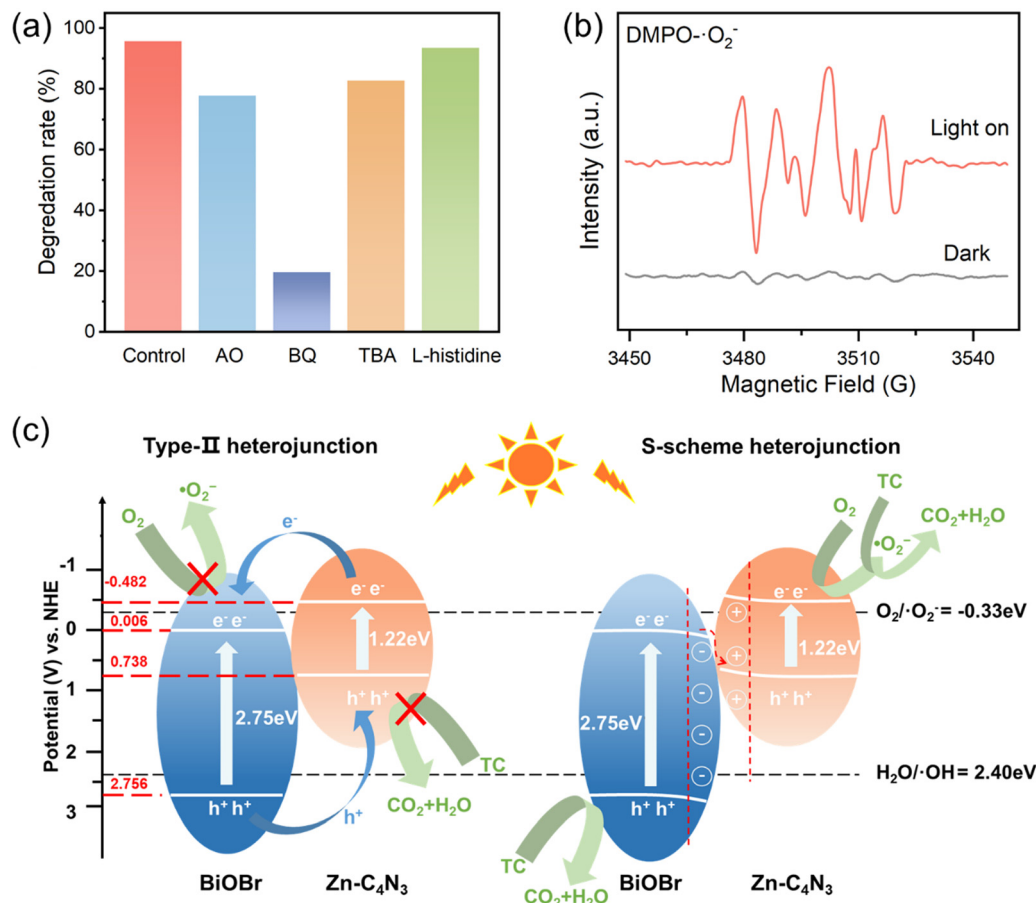


Fig. 7 (a) Trapping experiments of active species about the photocatalytic degradation of TC. (b) ESR spectra of DMPO- $\cdot\text{O}_2^-$ in methanol dispersions over Zn-C₄N₃/BiOBr after irradiation. (c) Possible photocatalytic mechanism for Zn-C₄N₃/BiOBr.

are excited by visible light to produce electrons (e^-) and holes (h^+), respectively. Then, the electrons transfer from the conduction band (CB) of Zn-C₄N₃ to the conduction band (CB) of BiOBr, and the holes transfer from the valence band (VB) of BiOBr to the valence band (VB) of Zn-C₄N₃. Nevertheless, the E_{CB} of BiOBr relative to NHE has been calculated to be 0.006 eV using the Mott-Schottky curves in Section 3.2, which is much higher than the $\text{O}_2/\cdot\text{O}_2^-$ potential (-0.33 eV).⁴⁶ In this mechanism, it suggests no $\cdot\text{O}_2^-$ generation, which contradicts the results obtained from the active radical species test. Instead, the S-scheme heterojunction supports the charge transfer mechanism better, in which BiOBr and Zn-C₄N₃ act as the electron donor and electron acceptor, respectively, to guarantee the effective separation of photogenerated electron and hole pairs. Specifically, the effects of the internal electric field (IEF) and bending band ensure that the photogenerated electrons spontaneously flow from BiOBr to Zn-C₄N₃ to recombine with the holes on the VB of Zn-C₄N₃ (eqn (1) and (2)). At the same time, electrons remain in the CB of Zn-C₄N₃ and holes remain in the VB of BiOBr. Because the CB potential of Zn-C₄N₃ (-0.48 V vs. NHE) is lower than the $E(\text{O}_2/\cdot\text{O}_2^-)$ (-0.33 V vs. NHE), the electrons in the CB of Zn-C₄N₃ can be captured by O_2 to produce $\cdot\text{O}_2^-$ (eqn (3)), which is consistent with the result

that $\cdot\text{O}_2^-$ is the primary reactive oxygen species of TC photocatalytic degradation. Simultaneously, one part of holes in the VB of BiOBr can directly react with pollutants, and the other can oxidize H_2O to produce $\cdot\text{OH}$ (eqn (4)) due to the fact that the VB potential of BiOBr (2.76 V vs. NHE) is more negative than the $E(\text{H}_2\text{O}/\cdot\text{OH})$ (2.40 V vs. NHE).^{47–49} Finally, numerous photo-generated h^+ , $\cdot\text{O}_2^-$ and $\cdot\text{OH}$ species trigger the high-efficiency degradation of the adsorbed TC molecules on the surface of Zn-C₄N₃/BiOBr (eqn (5)). It can be inferred that the S-type heterojunction maintains strong redox ability and is more suitable for the Zn-C₄N₃/BiOBr system.



3.4. Degradation pathway of TC

In the conceptual density functional theory framework, Fukui functions are tools used to predict reaction sites in molecules by evaluating electrophilicity and nucleophilicity, providing insights into electronic reactivity. Their application contributes to a deeper understanding of molecular reactivity and offers crucial information for catalyst design and reaction mechanism studies. The Fukui function, denoted as $f(\gamma)$, is precisely defined as $f(\gamma) = \left[\frac{\partial \rho(\gamma)}{\partial N} \right]_V$, where $\rho(\gamma)$ is the electron density at a point γ in space, N is the electron number in the current system, and the constant term V in the partial derivative represents the external potential. In the context of a chemical reaction, the Fukui function (f) can be calculated for electrophilic attack (f_A^-) and nucleophilic attack (f_A^+) using the atom charges q^A of atom A at the corresponding states: $f_A^- = q_A^{N-1} - q_A^N$ for electrophilic attack and $f_A^+ = q_A^N - q_A^{N+1}$ for nucleophilic attack.⁴¹ This calculation provides valuable insights into the reactivity of specific atomic sites during a chemical reaction.

Herein, natural population analysis (NPA) charges are introduced to investigate the charge distribution of nucleophilic attack (f^-) and electrophilic attack (f^+) Fukui indices in reactions (Table S3, ESI†). Through NPA, we accurately assess the

electron distribution in the reaction system, especially in the interaction between electrophilic and nucleophilic groups. Generally, as electrophilic groups, $\bullet\text{OH}$ and $\bullet\text{O}_2^-$ tend to attack reaction sites that are prone to electron loss. The active reaction region of the TC molecule exhibits larger Fukui indexes. Therefore, atoms such as O20, C10, O26, O22, O21, C16, C14 and O31 exhibit higher reactivity, indicated by their Fukui indices (f^0) of 0.0727, 0.0665, 0.034, 0.0402, 0.0409, 0.0454, 0.0457 and 0.0117, respectively (detailed atomic positions are illustrated in Fig. 8b). Furthermore, the electrostatic potential (ESP) mapping (Fig. 8a) reveals that regions marked in red show higher reactivity in the system, which is basically consistent with the atoms with higher f^0 values in the Fukui index.

In order to comprehensively explore the proposed degradation pathway of TC, qualitative analysis is conducted using LC-MS techniques based on the mass spectrum. Through experimental analysis, approximately eleven intermediates are detected except for TC, and their details are presented in Table S4 (ESI†). According to the mass spectra of TC and intermediate products obtained after degradation under visible light irradiation (Fig. S12, ESI†), three possible degradation paths can be considered (Fig. 8c). The photoexcited active species ($\bullet\text{O}_2^-$, h^+ and $\bullet\text{OH}$) play a crucial role in attacking the double bonds, aromatic rings, and amino groups during the

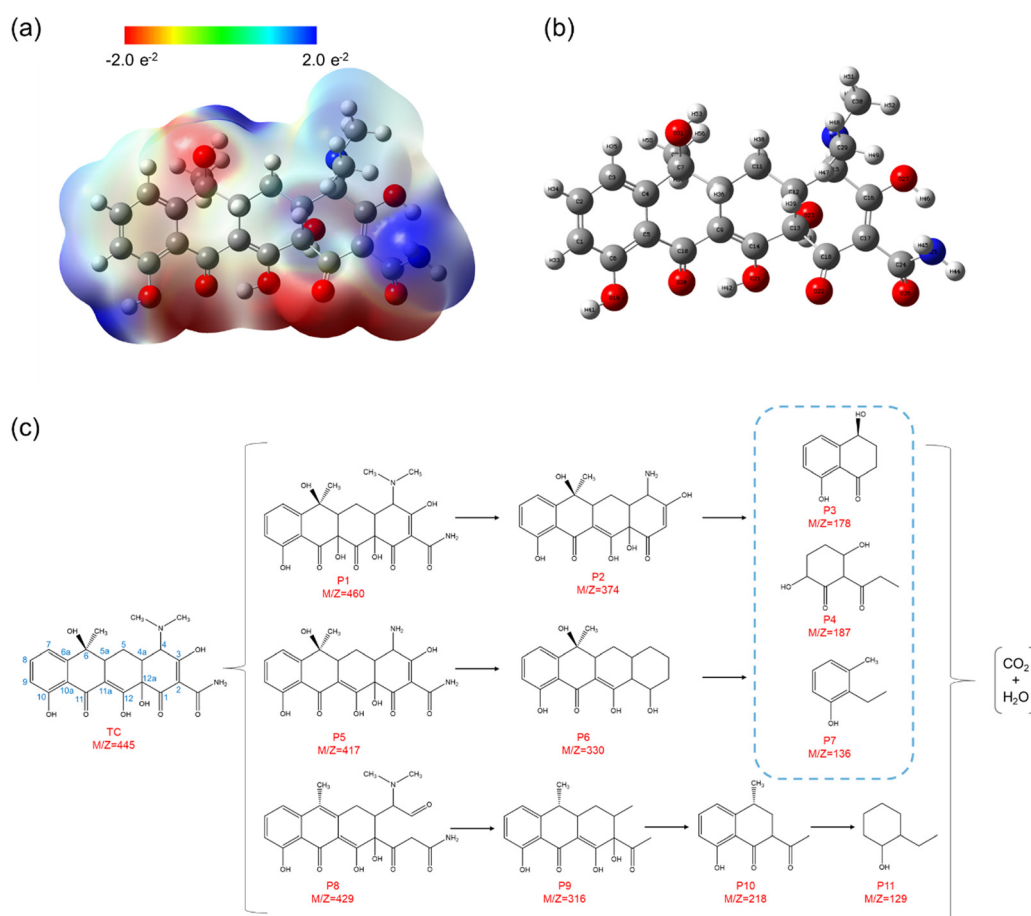


Fig. 8 (a) Electrostatic potential (ESP) map. (b) The detailed atomic position of TC. (c) Proposed degradation pathways for TC degradation.

degradation of tetracycline (TC). This implies that the intermediates primarily result from ring-opening reactions or cleavage of the main carbon bond.⁴¹ In the first pathway, a hydroxyl group attacks the double bond at C11a–C12 in the TC molecule to form P1 ($m/z = 460$) during the hydroxylation process, which is consistent with the previous study.³⁸ Subsequently, P2 ($m/z = 374$) is formed by the loss of the *N*-methyl group in the TC molecule at the C4 tertiary amine site due to the low bond energy of the N–C bond.⁴¹ In the second pathway, the TC molecule first undergoes *N*-dealkylation to form P5 ($m/z = 417$) through a mechanism similar to that of P2 formation. Then, P5 produces P6 ($m/z = 330$) after the deamination reaction.³⁸ In the above two reaction pathways, P2 and P5 are subsequently decomposed into P3 ($m/z = 178$), P4 ($m/z = 187$) and P7 ($m/z = 136$) under the constantly combined action of $\bullet\text{O}_2^-$, h^+ and $\bullet\text{OH}$.³⁸ In the third pathway, the hydroxyl group at the C6 position of the TC molecule may be attacked by active species to undergo the dehydration reaction, and the double bond at the C2–C3 position is attacked by superoxide radicals, thus forming P8 ($m/z = 429$).⁴² Then, *N*-dealkylation and deamination reactions occur to form P9 ($m/z = 316$), and further reaction occurs to form P10 ($m/z = 218$).⁴³ With the extension of reaction time, the intermediate will decompose into a smaller molecular structure of P11 ($m/z = 129$) under the joint attack of $\bullet\text{O}_2^-$, h^+ and $\bullet\text{OH}$. Finally, these small molecular products can be thoroughly decomposed into CO_2 and H_2O .⁴³

4. Conclusions

In summary, this study has demonstrated that BiOBr can directly grow from the surface of Zn^{2+} doped C_4N_3 to construct an S-scheme heterojunction with an intimate interface. More importantly, the original hollow structure of BiOBr is inherited, which provides highly exposed reaction sites and an elevated photon capture cross-section. The synergistic effect between BiOBr and $\text{Zn-C}_4\text{N}_3$, facilitated by Zn^{2+} doping, significantly boosts the photocatalytic activity of BiOBr, causing a significant portion of TC pollutants to be rapidly removed within 30 minutes. Our findings provide profound insights into the intricacies of advanced photocatalytic materials. This study not only contributes to the sustainable removal of organic pollutants but also introduces a transformative strategy for optimizing the catalytic performance of BiOBr in environmental applications.

Data availability

The data underlying this article are available in the article and in its online ESI.†

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

This work was supported by Hebei Natural Science Foundation (B2024205035), National Natural Science Foundation of China (Nos 12174183 and 21872071), and High Performance Computing Centers of Shenzhen.

References

- 1 S. Cao, J. Yu, S. Wageh, A. A. Al-Ghamdi, M. Mousavi, J. B. Ghasemi and F. Xu, H_2 -production and electron-transfer mechanism of a noble-metal-free $\text{WO}_3/\text{ZnIn}_2\text{S}_4$ S-scheme heterojunction photocatalyst, *J. Mater. Chem. A*, 2022, **10**(33), 17174–17184, DOI: [10.1039/d2ta05181h](https://doi.org/10.1039/d2ta05181h).
- 2 C. Wen, D. Li, J. Zhong, Z. Wang, S. Huang, H. Liu, J. Wu, P. Chen, W. Lv and G. Liu, In situ synthesis of S-scheme AgBr/BiOBr for efficient degradation of sulfonamide antibiotics: Synergistic effects of oxygen vacancies and heterojunctions promote exciton dissociation, *Chem. Eng. J.*, 2022, **450**, 138075, DOI: [10.1016/j.cej.2022.138075](https://doi.org/10.1016/j.cej.2022.138075).
- 3 Q. Xu, S. Wageh, A. A. Al-Ghamdi and X. Li, Design principle of S-scheme heterojunction photocatalyst, *J. Mater. Sci. Technol.*, 2022, **124**, 171–173, DOI: [10.1016/j.jmst.2022.02.016](https://doi.org/10.1016/j.jmst.2022.02.016).
- 4 J. Fu, Q. Xu, J. Low, C. Jiang and J. Yu, Ultrathin 2D/2D $\text{WO}_3/\text{g-C}_3\text{N}_4$ step-scheme H_2 -production photocatalyst, *Appl. Catal., B*, 2019, **243**, 556–565, DOI: [10.1016/j.apcatb.2018.11.011](https://doi.org/10.1016/j.apcatb.2018.11.011).
- 5 F. Li, X. Yue, Y. Liao, L. Qiao, K. Lv and Q. Xiang, Understanding the unique S-scheme charge migration in triazine/heptazine crystalline carbon nitride homojunction, *Nat. Commun.*, 2023, **14**(1), 3901, DOI: [10.1038/s41467-023-39578-z](https://doi.org/10.1038/s41467-023-39578-z).
- 6 J. Song, J. Zhang, A. Zada, Y. Ma and K. Qi, $\text{CoFe}_2\text{O}_4/\text{NiFe}_2\text{O}_4$ S-scheme composite for photocatalytic decomposition of antibiotic contaminants, *Ceram. Int.*, 2023, **49**(8), 12327–12333, DOI: [10.1016/j.ceramint.2022.12.088](https://doi.org/10.1016/j.ceramint.2022.12.088).
- 7 X. Ren, M. Gao, Y. Zhang, Z. Zhang, X. Cao, B. Wang and X. Wang, Photocatalytic reduction of CO_2 on BiOX: Effect of halogen element type and surface oxygen vacancy mediated mechanism, *Appl. Catal., B*, 2020, **274**, 119063, DOI: [10.1016/j.apcatb.2020.119063](https://doi.org/10.1016/j.apcatb.2020.119063).
- 8 R. Wang, P. Zhu, M. Duan, J. Xu, M. Liu and D. Luo, Synthesis and characterization of successive Z-scheme $\text{CdS}/\text{Bi}_2\text{MoO}_6/\text{BiOBr}$ heterojunction photocatalyst with efficient performance for antibiotic degradation, *J. Alloys Compd.*, 2021, **870**, 159385, DOI: [10.1016/j.jallcom.2021.159385](https://doi.org/10.1016/j.jallcom.2021.159385).
- 9 M. Yang, Y. Han, J. Ding, Y. Guo, C. Han and X. Gu, Constructing Defective Heterojunctions of BiOBr Nanosheets and Hollow NH_2 -functionalized MOFs for Visible-light-driven CO_2 Reduction with Nearly 100% CO Selectivity by Pure H_2O , *Chem. – Asian J.*, 2023, **18**(8), e202300033, DOI: [10.1002/asia.202300033](https://doi.org/10.1002/asia.202300033).
- 10 L. Feng, H. Fu, T. Zhang, Q. Zhang, S. Ren, J. Cheng, Q. Liang and X. Xiao, Synergy of oxygen vacancies and Bi nanoparticles on BiOBr nanosheets for enhanced

- photocatalytic H₂O₂ production, *New J. Chem.*, 2024, **48**(5), 1998–2007, DOI: [10.1039/d3nj03815g](https://doi.org/10.1039/d3nj03815g).
- 11 W. Zhang, Z. Bian, Y. Peng, H. Tang and H. Wang, Dual-function oxygen vacancy of BiOBr intensifies pollutant adsorption and molecular oxygen activation to remove tetracycline hydrochloride, *Chem. Eng. J.*, 2023, **451**, 138731, DOI: [10.1016/j.cej.2022.138731](https://doi.org/10.1016/j.cej.2022.138731).
 - 12 Y. Zhang, S. Gu, X. Zhou, K. Gao, K. Sun, D. Wu, J. Xia and X. Wang, Boosted photocatalytic nitrogen fixation by bismuth and oxygen vacancies in Bi₂MoO₆/BiOBr composite structures, *Catal. Sci. Technol.*, 2021, **11**(14), 4783–4792, DOI: [10.1039/d1cy00539a](https://doi.org/10.1039/d1cy00539a).
 - 13 J. Zhao, Z. Miao, Y. Zhang, G. Wen, L. Liu, X. Wang, X. Cao and B. Wang, Oxygen vacancy-rich hierarchical BiOBr hollow microspheres with dramatic CO₂ photoreduction activity, *J. Colloid Interface Sci.*, 2021, **593**, 231–243, DOI: [10.1016/j.jcis.2021.02.117](https://doi.org/10.1016/j.jcis.2021.02.117).
 - 14 Z. Zan, X. Li, X. Gao, J. Huang, Y. Luo and L. Han, 0D/2D Carbon Nitride Quantum Dots (CNQDs)/BiOBr S-Scheme Heterojunction for Robust Photocatalytic Degradation and H₂O₂ Production, *Acta Phys.-Chim. Sin.*, 2023, **39**(6), 2209016, DOI: [10.3866/pku.Whxb202209016](https://doi.org/10.3866/pku.Whxb202209016).
 - 15 X. Li, J. Xiong, X. Gao, J. Ma, Z. Chen, B. Kang, J. Liu, H. Li, Z. Feng and J. Huang, Novel BP/BiOBr S-scheme nano-heterojunction for enhanced visible-light photocatalytic tetracycline removal and oxygen evolution activity, *J. Hazard. Mater.*, 2020, **387**, 121690, DOI: [10.1016/j.jhazmat.2019.121690](https://doi.org/10.1016/j.jhazmat.2019.121690).
 - 16 Y. Zhang, J. Di, X. Zhu, M. Ji, C. Chen, Y. Liu, L. Li, T. Wei, H. Li and J. Xia, Chemical bonding interface in Bi₂Sn₂O₇/BiOBr S-scheme heterojunction triggering efficient N₂ photofixation, *Appl. Catal., B*, 2023, **323**, 122148, DOI: [10.1016/j.apcatb.2022.122148](https://doi.org/10.1016/j.apcatb.2022.122148).
 - 17 J. Wu, L. Xiong, Y. Hu, Y. Yang, X. Zhang, T. Wang, Z. Tang, A. Sun, Y. Zhou and J. Shen, *et al.*, Organic half-metal derived erythroid-like BiVO₄/hm-C₄N₃ Z-Scheme photocatalyst: Reduction sites upgrading and rate-determining step modulation for overall CO₂ and H₂O conversion, *Appl. Catal., B*, 2021, **295**, 120277, DOI: [10.1016/j.apcatb.2021.120277](https://doi.org/10.1016/j.apcatb.2021.120277).
 - 18 G. Zhou, Y. Shan, Y. Hu, X. Xu, L. Long, J. Zhang, J. Dai, J. Guo, J. Shen and S. Li, *et al.*, Half-metallic carbon nitride nanosheets with micro grid mode resonance structure for efficient photocatalytic hydrogen evolution, *Nat. Commun.*, 2018, **9**(1), 3366, DOI: [10.1038/s41467-018-05590-x](https://doi.org/10.1038/s41467-018-05590-x).
 - 19 S. Tian, H. Ren, W. Sun, Y. Song, H. Ge, A. Yang, W. Zheng and Y. Zhao, CdIn₂S₄ microspheres embedded with mesoporous Zn-doped g-C₃N₄ ultrathin nanosheets for efficient photocatalytic hydrogen evolution, *New J. Chem.*, 2024, **48**(8), 3695–3706, DOI: [10.1039/d3nj05590f](https://doi.org/10.1039/d3nj05590f).
 - 20 H. Deng, D. Deng, S. Jin, Z. Tian and L. M. Yang, Unraveling the Activity and Mechanism of TM@g-C₄N₃ Electrocatalysts in the Oxygen Reduction Reaction, *ACS Appl. Mater. Interfaces*, 2024, **16**(14), 17617–17625, DOI: [10.1021/acsami.4c01342](https://doi.org/10.1021/acsami.4c01342).
 - 21 X. Dou, Y. Chen and H. Shi, CuBi₂O₄/BiOBr composites promoted PMS activation for the degradation of tetracycline: S-scheme mechanism boosted Cu²⁺/Cu₊ cycle, *Chem. Eng. J.*, 2022, **431**, 134054, DOI: [10.1016/j.cej.2021.134054](https://doi.org/10.1016/j.cej.2021.134054).
 - 22 J. Hao, Y. Zhang, L. Zhang, J. Shen, L. Meng and X. Wang, Restructuring surface frustrated Lewis acid-base pairs of BiOBr through isomorphous Sn doping for boosting photocatalytic CO₂ reduction, *Chem. Eng. J.*, 2023, **464**, 142536, DOI: [10.1016/j.cej.2023.142536](https://doi.org/10.1016/j.cej.2023.142536).
 - 23 H. Guan, Y. Dong, X. Kang, Y. Han, Z. Cheng, L. Han, L. Xie, W. Chen and J. Zhang, Extraordinary electrochemical performance of lithium-sulfur battery with 2D ultrathin BiOBr/rGO sheet as an efficient sulfur host, *J. Colloid Interface Sci.*, 2022, **626**, 374–383, DOI: [10.1016/j.jcis.2022.06.148](https://doi.org/10.1016/j.jcis.2022.06.148).
 - 24 F. M. Aghamir, A. R. Momen-Baghdadabad and M. Etminan, Effects of deposition angle on synthesis of amorphous carbon nitride thin films prepared by plasma focus device, *Appl. Surf. Sci.*, 2019, **463**, 141–149, DOI: [10.1016/j.apsusc.2018.08.154](https://doi.org/10.1016/j.apsusc.2018.08.154).
 - 25 K. Perumal, S. Shanavas, A. Karthigeyan, T. Ahamad, S. M. Alshehri and P. Murugakoothan, Hydrothermal assisted precipitation synthesis of highly stable g-C₃N₄/BiOBr/CdS photocatalyst with enhanced visible light photocatalytic degradation of tetracycline, *Diamond Relat. Mater.*, 2020, **110**, 108091, DOI: [10.1016/j.diamond.2020.108091](https://doi.org/10.1016/j.diamond.2020.108091).
 - 26 W. D. Oh, S. K. Lua, Z. Dong and T. T. Lim, A novel three-dimensional spherical CuBi₂O₄ consisting of nanocolumn arrays with persulfate and peroxymonosulfate activation functionalities for 1H-benzotriazole removal, *Nanoscale*, 2015, **7**(17), 8149–8158, DOI: [10.1039/c5nr01428j](https://doi.org/10.1039/c5nr01428j).
 - 27 T. Di, B. Zhu, B. Cheng, J. Yu and J. Xu, A direct Z-scheme g-C₃N₄/SnS₂ photocatalyst with superior visible-light CO₂ reduction performance, *J. Catal.*, 2017, **352**, 532–541, DOI: [10.1016/j.jcat.2017.06.006](https://doi.org/10.1016/j.jcat.2017.06.006).
 - 28 X. Lv, D. Y. S. Yan, F. L.-Y. Lam, Y. H. Ng, S. Yin and A. K. An, Solvothermal synthesis of copper-doped BiOBr microflowers with enhanced adsorption and visible-light driven photocatalytic degradation of norfloxacin, *Chem. Eng. J.*, 2020, **401**, 126012, DOI: [10.1016/j.cej.2020.126012](https://doi.org/10.1016/j.cej.2020.126012).
 - 29 J. Kang, Y. Tang, M. Wang, C. Jin, J. Liu, S. Li, Z. Li and J. Zhu, The enhanced peroxymonosulfate-assisted photocatalytic degradation of tetracycline under visible light by g-C₃N₄/Na-BiVO₄ heterojunction catalyst and its mechanism, *J. Environ. Chem. Eng.*, 2021, **9**, 105524, DOI: [10.1016/j.jece.2021.105524](https://doi.org/10.1016/j.jece.2021.105524).
 - 30 X. Ren, J. Li, X. Cao, B. Wang, Y. Zhang and Y. Wei, Synergistic effect of internal electric field and oxygen vacancy on the photocatalytic activity of BiOBr_xI_{1-x} with isomorphous fluorine substitution, *J. Colloid Interface Sci.*, 2019, **554**, 500–511, DOI: [10.1016/j.jcis.2019.07.034](https://doi.org/10.1016/j.jcis.2019.07.034).
 - 31 S. Wu, X. Tan, J. Lei, H. Chen, L. Wang and J. Zhang, Ga-Doped and Pt-Loaded Porous TiO₂-SiO₂ for Photocatalytic Nonoxidative Coupling of Methane, *J. Am. Chem. Soc.*, 2019, **141**(16), 6592–6600, DOI: [10.1021/jacs.8b13858](https://doi.org/10.1021/jacs.8b13858).
 - 32 H. Jiang, Q. Wang, P. Chen, H. Zheng, J. Shi, H. Shu and Y. Liu, Photocatalytic degradation of tetracycline by using a regenerable (Bi)BiOBr/rGO composite, *J. Cleaner Prod.*, 2022, **339**, 130771, DOI: [10.1016/j.jclepro.2022.130771](https://doi.org/10.1016/j.jclepro.2022.130771).

- 33 H. Shang, H. Jia, W. Zhang, S. Li, Q. Wang, Q. Yang, C. Zhang, Y. Shi, Y. Wang and P. Li, *et al.*, Surface Hydrogen Bond-Induced Oxygen Vacancies of TiO₂ for Two-Electron Molecular Oxygen Activation and Efficient NO Oxidation, *Environ. Sci. Technol.*, 2023, 57(48), 20400–20409, DOI: [10.1021/acs.est.3c06593](https://doi.org/10.1021/acs.est.3c06593).
- 34 Q. Wu, H. Ma, Y. Wang, J. Chen, J. Dai, X. Xu and X. Wu, Surface Electron Localization in Cu-MOF-Bonded Double-Heterojunction Cu₂O Induces Highly Efficient Photocatalytic CO₂ Reduction, *ACS Appl. Mater. Interfaces*, 2022, 14(48), 54328–54337, DOI: [10.1021/acsami.2c15278](https://doi.org/10.1021/acsami.2c15278).
- 35 C. Gao, H. Yu, L. Zhang, Y. Zhao, J. Xie, C. Li, K. Cui and J. Yu, Ultrasensitive Paper-Based Photoelectrochemical Sensing Platform Enabled by the Polar Charge Carriers-Created Electric Field, *Anal. Chem.*, 2020, 92(4), 2902–2906, DOI: [10.1021/acs.analchem.9b05611](https://doi.org/10.1021/acs.analchem.9b05611).
- 36 Y. Yang, Z. Tang, B. Zhou, J. Shen, H. He, A. Ali, Q. Zhong, Y. Xiong, C. Gao and A. Alsaedi, *et al.*, In situ no-slot joint integration of half-metallic C(CN)₃ cocatalyst into g-C₃N₄ scaffold: An absolute metal-free in-plane heterosystem for efficient and selective photoconversion of CO₂ into CO, *Appl. Catal., B*, 2020, 264, 118470, DOI: [10.1016/j.apcatb.2019.118470](https://doi.org/10.1016/j.apcatb.2019.118470).
- 37 X. Bao, M. Zhang, Z. Wang, D. Dai, P. Wang, H. Cheng, Y. Liu, Z. Zheng, Y. Dai and B. Huang, Molten-salt assisted synthesis of Cu clusters modified TiO₂ with oxygen vacancies for efficient photocatalytic reduction of CO₂ to CO, *Chem. Eng. J.*, 2022, 445, 136718, DOI: [10.1016/j.cej.2022.136718](https://doi.org/10.1016/j.cej.2022.136718).
- 38 Y. Lin, X. Wu, Y. Han, C. Yang, Y. Ma, C. Du, Q. Teng, H. Liu and Y. Zhong, Spatial separation of photogenerated carriers and enhanced photocatalytic performance on Ag₃PO₄ catalysts via coupling with PPy and MWCNTs, *Appl. Catal., B*, 2019, 258, 117969, DOI: [10.1016/j.apcatb.2019.117969](https://doi.org/10.1016/j.apcatb.2019.117969).
- 39 S. Wu, Z. Yang, Z. Zhou, X. Li, Y. Lin, J. J. Cheng and C. Yang, Catalytic activity and reaction mechanisms of single-atom metals anchored on nitrogen-doped carbons for peroxymonosulfate activation, *J. Hazard. Mater.*, 2023, 459, 132133, DOI: [10.1016/j.jhazmat.2023.132133](https://doi.org/10.1016/j.jhazmat.2023.132133).
- 40 Y. Chen and K. Liu, Preparation and characterization of nitrogen-doped TiO₂/diatomite integrated photocatalytic pellet for the adsorption-degradation of tetracycline hydrochloride using visible light, *Chem. Eng. J.*, 2016, 302, 682–696, DOI: [10.1016/j.cej.2016.05.108](https://doi.org/10.1016/j.cej.2016.05.108).
- 41 J. Guo, L. Jiang, J. Liang, W. Xu, H. Yu, J. Zhang, S. Ye, W. Xing and X. Yuan, Photocatalytic degradation of tetracycline antibiotics using delafossite silver ferrite-based Z-scheme photocatalyst: Pathways and mechanism insight, *Chemosphere*, 2021, 270, 128651, DOI: [10.1016/j.chemosphere.2020.128651](https://doi.org/10.1016/j.chemosphere.2020.128651).
- 42 Y.-Y. Chen, Y.-L. Ma, J. Yang, L.-Q. Wang, J.-M. Lv and C.-J. Ren, Aqueous tetracycline degradation by H₂O₂ alone: Removal and transformation pathway, *Chem. Eng. J.*, 2017, 307, 15–23, DOI: [10.1016/j.cej.2016.08.046](https://doi.org/10.1016/j.cej.2016.08.046).
- 43 X. Jiang, S. Chen, X. Zhang, L. Qu, H. Qi, B. Wang, B. Xu and Z. Huang, Carbon-doped flower-like Bi₂WO₆ decorated carbon nanosphere nanocomposites with enhanced visible light photocatalytic degradation of tetracycline, *Adv. Compos. Hybrid Mater.*, 2022, 6, 9, DOI: [10.1007/s42114-022-00590-4](https://doi.org/10.1007/s42114-022-00590-4).
- 44 J. Yao, X. Zeng and Z. Wang, Enhanced degradation performance of sulfisoxazole using peroxymonosulfate activated by copper-cobalt oxides in aqueous solution: Kinetic study and products identification, *Chem. Eng. J.*, 2017, 330, 345–354, DOI: [10.1016/j.cej.2017.07.155](https://doi.org/10.1016/j.cej.2017.07.155).
- 45 S. Guo, H. Wang, W. Yang, H. Fida, L. You and K. Zhou, Scalable synthesis of Ca-doped α -Fe₂O₃ with abundant oxygen vacancies for enhanced degradation of organic pollutants through peroxymonosulfate activation, *Appl. Catal., B*, 2020, 262, 118250, DOI: [10.1016/j.apcatb.2019.118250](https://doi.org/10.1016/j.apcatb.2019.118250).
- 46 C. Feng, Q. Gu, J. Rong, Q. Liang, M. Zhou, X. Li, S. Xu and Z. Li, Porous dual Z-scheme InOOH/RCN/CoWO₄ heterojunction with enhanced photothermal-photocatalytic properties towards norfloxacin degradation, *Sep. Purif. Technol.*, 2023, 308, 122890, DOI: [10.1016/j.seppur.2022.122890](https://doi.org/10.1016/j.seppur.2022.122890).
- 47 X. Yao, X. Jiang, D. Zhang, S. Lu, M. Wang, S. Pan, X. Pu, J. Liu and P. Cai, Achieving improved full-spectrum responsive 0D/3D CuWO₄/BiOBr:Yb³⁺,Er³⁺ photocatalyst with synergetic effects of up-conversion, photothermal effect and direct Z-scheme heterojunction, *J. Colloid Interface Sci.*, 2023, 644, 95–106, DOI: [10.1016/j.jcis.2023.04.072](https://doi.org/10.1016/j.jcis.2023.04.072).
- 48 X. Fu, J. Tao, Z. He, Y. Gao, Y. Xia and Z. Zhao, Synergy of Z-scheme heterostructure with interfacial S–O bonding in In₂S₃/BiOBr for efficient tetracycline hydrochloride degradation and Cr(vi) reduction, *J. Alloys Compd.*, 2023, 936, 168202, DOI: [10.1016/j.jallcom.2022.168202](https://doi.org/10.1016/j.jallcom.2022.168202).
- 49 R. Weng, F. Tian, Z. Yu, J. Ma, Y. Lv and B. Xi, Efficient mineralization of TBBPA via an integrated photocatalytic reduction/oxidation process mediated by MoS₂/SnIn₄S₈ photocatalyst, *Chemosphere*, 2021, 285, 131542, DOI: [10.1016/j.chemosphere.2021.131542](https://doi.org/10.1016/j.chemosphere.2021.131542).