



Cite this: *Phys. Chem. Chem. Phys.*, 2024, 26, 14582

Investigation on acceptor–donor co-doped SnO₂ nanoparticles enriched with oxygen vacancies: a capacitive humidity sensor for respiration detection

Yuchuan Ding,^a Yong Chen^b and MaoHua Wang^{id}*^a

In this work, we develop a novel capacitive humidity sensor based on Al–Si acceptor–donor co-doped SnO₂ for real-time monitoring of ambient humidity and human respiration. XRD measurements reveal that all samples exhibit a tetragonal rutile phase and the crystallite size of SnO₂ decreases with increasing Al–Si content. The high intensity of the Raman peak at 762 cm⁻¹ confirms the presence of bridging mode oxygen vacancies in (Al + Si)_{0.02}Sn_{0.98}O₂. The EPR results show that the amount of singly ionized oxygen vacancies increases after the introduction of Al–Si. Both types and amounts of oxygen vacancy defects are particularly sensitive to the adsorption of water molecules. Moreover, according to DFT calculations, the contribution of the Si 3s orbital and Al 3s orbital to the band edge verifies the formation of acceptor–donor complexes in Al–Si co-doped SnO₂. The humidity sensing results reveal that the (Al + Si)_{0.02}Sn_{0.98}O₂ humidity sensor shows high sensitivity ($S = 839$), low hysteresis (1.94%) and fast response/recovery times (25 s/5 s). The respiratory intervals during shallow, medium and deep breathing states of (Al + Si)_{0.02}Sn_{0.98}O₂ were measured at 2.8 s, 3.8 s and 4.5 s, respectively. The chemical mechanism for the enhancement of humidity sensing performance corresponding to the oxygen vacancy defects induced by Al–Si interplay is proposed.

Received 18th March 2024,
Accepted 27th April 2024

DOI: 10.1039/d4cp01141d

rsc.li/pccp

1. Introduction

Nowadays, humidity sensors are indispensable information-gathering equipment in the age of artificial intelligence, which plays an important role in the field of detecting ambient humidity, controlling various industrial production and monitoring the human respiratory rate.^{1–3} To meet the needs of high performance such as linearity, fast response/recovery ability, low hysteresis and pronounced sensitivity, a wide range of humidity sensors, including capacitance, impedance, frequency, and other types, have been developed using sensing materials such as ceramics, polymers, and carbon-based materials.^{4,5} The utilization of nanoparticles from metal oxide semiconductors (SnO₂, Al₂O₃, TiO₂, etc.) as building humidity sensing materials is advantageous due to mechanical flexibility and excellent electrical/sensing properties.^{6–8}

Tin oxide (SnO₂), a kind of wide band-gap (3.6 eV) n-type semiconductor which has the advantages of high chemical stability, simple manufacturing and a favorable adsorption

capacity for water molecules, remains the focus of attention in the outline and advancement of high sensitivity humidity sensors.⁹ However, the intrinsic SnO₂-based humidity sensor suffers from long response and recovery times, as well as high hysteresis. In order to further enhance the sensing performance, such as the linearity and sensitivity, a number of elements including Zn,¹⁰ Cd,¹¹ Al,¹² Sb,¹³ N¹⁴ and P¹⁴ have been selected as dopants in SnO₂-based sensors. Among these doping elements, Al and Si have an edge on being resourceful, inexpensive, non-toxic and environmentally friendly. In addition, the radii of Al³⁺ (0.51 Å) and Si⁴⁺ (0.4 Å) are considerably smaller than Sn⁴⁺ (0.69 Å), which can lead to lattice distortion and trigger the formation of substitutional or interstitial defects. Generally, due to the fact that the Al acceptor has one less valence electron compared to the Si donor, the crystal-line structure inherently introduces an electronic hole in the SiO₂ energy band.^{15,16} The interplay of Al and Si ions can generate a significant number of positive charges and create a local electric field within the crystal, thereby facilitating the efficient separation of electron–hole pairs. Previous studies have reported that the incorporation of an Al acceptor and a Si donor into metal oxides is responsible for increasing the oxygen vacancy and electron content.^{17,18} Si behaves as a well-behaved shallow donor within the range of conducting oxides,

^a School of Petrochemical Engineering, Changzhou University, Changzhou 213164, People's Republic of China. E-mail: wmhjz2000@163.com

^b Huaide College, Changzhou University, Jingjiang 214500, People's Republic of China

while Al acts as an acceptor to facilitate p-type conductivity. Both the high activity of the oxygen vacancy and the significant contribution of electrons are considered to be responsible for enhancing sensing performance. The oxygen vacancy defects provide additional active surface adsorption sites for water molecules on the SnO₂ surface, which plays a crucial role in promoting the humidity sensitivity of the material.¹⁹ Therefore, the incorporation of Al–Si into SnO₂ can enhance the humidity sensitivity by increasing the number of oxygen vacancy defects.

In this study, we present a successful fabrication of a novel capacitive humidity sensor based on Al–Si acceptor–donor co-doped SnO₂ nanoparticles, enriched with oxygen vacancy defects. To explore the interactions between the Al–Si acceptor–donor complex and water molecules, as well as understand their impact on the sensing properties, the oxygen vacancy defects and the electronic structure were investigated by EPR and DFT. The capacitive humidity sensor based on the acceptor–donor complex demonstrates the potential for simultaneous detection of ambient humidity and human breath rate.

2. Experimental

2.1 Synthesis of Al–Si co-doped SnO₂

All the starting materials used in the experiment were of analytical grade and used directly without further purification. Fig. 1 depicts the synthesis of pure and Al–Si co-doped SnO₂ nanoparticles *via* a simple sol–gel method. In a typical procedure, 0.05 mol SnCl₂·2H₂O was dissolved in the solution mixed with 100 mL ethanol and 100 mL deionized water. Thereafter, (C₂H₅O)₄Si and Al(NO₃)₃·9H₂O were incorporated into Sn precursor solutions to prepare (Al + Si)_xSn_{1–x}O₂ ($x = 0, 0.5, 1, 1.5, 2$ mol%) and then stirred at 300 K for 6 h on a magnetic stirrer. (C₂H₅O)₄Si and Al(NO₃)₃·9H₂O were added into the solutions in

a 1:1 ratio to ensure the doping concentration of Al and Si. Then, a certain amount of ammonia water was dropped into the resultant solutions to regulate the pH to 8, until white turbid precipitates appeared at the bottom of solution. The reaction products were aged, filtered, and washed 3 times before drying for 1 hour in an oven at 100 °C. Moreover, the prepared samples were kept in a furnace and annealed at 500 °C for 60 min. Finally, Al–Si co-doped SnO₂ nanoparticles with different dopant contents were synthesized, respectively.

2.2 Characterization and calculation methods

The lattice structure of the SnO₂ sample was determined using an X-ray diffractometer (Ultima IV, Rigaku, Japan). The test range of 2θ was 20°–80°. The λ was 0.15406 nm and the scan rate was 5° min^{–1}. The morphology and structure of the prepared sample were observed by employing the SUPRA55 field emission scanning electron microscope, which was operated at 15 kV. Raman spectroscopy measurements were performed using a LabRAM UV-VIS-NIR system with an excitation wavelength of $\lambda = 590$ nm. The investigation of oxygen vacancies in the samples was carried out using electro paramagnetic resonance (EPR) spectroscopy with a Bruker A300-10/12 spectrometer operating at a field modulation frequency of 100 kHz under ambient conditions. By employing the density functional theory (DFT) module offered by Q-flow (Lonxun Quantum), we performed electronic structure calculations of SnO₂ within the DFT framework. The exchange–correlation functional was modeled using the Perdew–Burke–Ernzerhof potential within the GGA+*U* scheme. To conduct the calculations, we employed energy cut-offs of 120 Ry for the plane-wave expansion of the wave functions and the charge density. For Brillouin zone sampling, we utilized a 2 × 2 × 6 Monkhorst–Pack *k*-point grid. In order to account for the modeling of different impurities in oxides, we considered

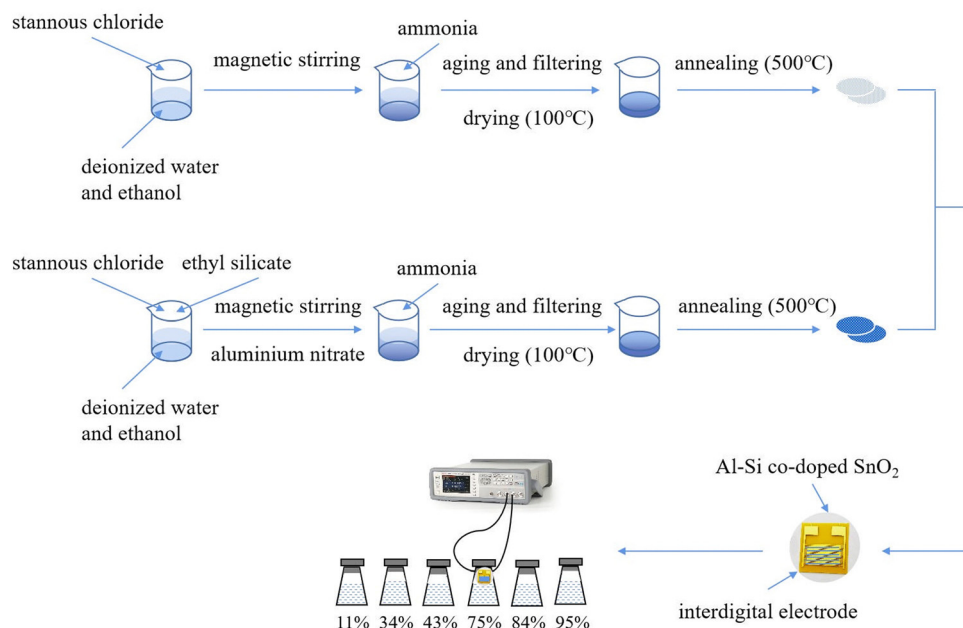


Fig. 1 Preparation of the pure and Al–Si co-doped SnO₂ and procedure for testing humidity sensing performance.

not only substitution (*S*) impurities but also interstitial (*I*) impurities, as well as their combinations with oxygen vacancies.

2.3 Humidity sensing performance testing and respiratory detection

The testing procedure for the pristine and Al–Si co-doped SnO₂ humidity sensors is shown in Fig. 2. In the testing procedures, a polyimide substrate (10 mm × 10 mm) with 15 pairs of interdigital electrodes was used to measure the humidity sensing performance. Then pure and Al–Si co-doped SnO₂ nanoparticles (2 mg) were mixed with ethanol (20 μL) to form a paste and coated on the surface of the electrode. Then, the electrodes were placed in the oven with a drying temperature of 70 °C for 10 min. After that, all prepared electrodes were sequentially placed in different air tight glass humidity chambers, which were added with saturated aqueous solution of LiCl, MgCl₂, K₂CO₃, NaCl, KCl and KNO₃. The above saturated salt solutions have 11%, 34%, 43%, 75%, 84% and 95% RH, respectively. The corresponding variations in the capacitance of sensing materials were recorded using an LCR digital instrument at room temperature with a working voltage of 1 V and a frequency range of 120 Hz–10 kHz. Fig. 2 shows the circuit and the physical diagram of the humidity sensor designed to enable respiratory monitoring across various states of human respiration. When the humidity sensor is exposed to different relative humidity (RH) levels, significant variations in the brightness of the LED can be observed. When a person breathes onto the humidity sensor, the presence of moisture influences the capacitance of the sensor, leading to an increase in the current within the circuit. Consequently, the LED reaches the breakover voltage and turns on.

3. Results and discussion

3.1 Structural and morphological properties

As shown in Fig. 3(a), the crystalline structure and phase purity of pure and Al–Si co-doped SnO₂ were determined by X-ray diffraction patterns. All the diffraction peaks observed are in agreement with the standard tetragonal rutile SnO₂ phase (JCPDS#41-1445). The strong diffraction peaks located at 2θ of 26.6°, 33.9° and 51.8° are respectively assigned to (110), (101) and (211) planes. There is no phase related to Al–Si oxides in the diffraction pattern, which confirms that the Al–Si ions are

homogeneously incorporated into SnO₂ lattice. The intensity of diffraction peak (101) exhibits a sharp increase with increasing Al–Si content, which shows the reduction of crystallinity for Al–Si co-doped samples.²⁰ This evidence suggests the substitution of dopants ions for Sn ions in the SnO₂ lattice.

We calculated the crystallite size *D* and micro strain ϵ using the following relations:¹⁸

$$D = \frac{K\lambda}{\beta \cos \theta} \quad (1)$$

$$\epsilon = \frac{\beta \cos \theta}{4} \quad (2)$$

where λ is the wavelength of X-ray radiation and β is the full width at half maximum (FWHM) of the peaks at the diffracting angle θ . From Fig. 3(b), it is evident that the crystallite size decreases from 44 to 25 nm with an increase in the doping rate. Simultaneously, the microstrain increases from 4.5×10^{-2} to 8.0×10^{-2} . This can be interpreted by the fact that the smaller Al³⁺/Si⁴⁺ ions can induce the interstitial or substitutional defects in the SnO₂ lattice.²¹ During the annealing process of Al–Si co-doped SnO₂ nanoparticles, the smaller ionic radii of Al³⁺ and Si⁴⁺ ions allow them to occupy the octahedral sites of Sn⁴⁺. This substitution of dopant ions in the octahedral sites leads to an increase in compression stresses and lattice distortion. Therefore, the crystalline structural properties of SnO₂ have been tuned by incorporating the Al–Si with different concentrations.

Fig. 4(a)–(f) presents the FESEM images and elemental mapping of the (Al + Si)_{0.02}Sn_{0.98}O₂ nanoparticles. The surface morphology of the nanoparticles shows the spherical grain with a size ranging from 21.5 to 39.2 nm. The elemental compositions of (Al + Si)_{0.02}Sn_{0.98}O₂ nanoparticles are studied by elemental mapping. The results show that the materials are composed of Al, Si, Sn and O, and the four elements are distributed homogeneously in (Al + Si)_{0.02}Sn_{0.98}O₂, which further confirms the introduction of dopants.

3.2 Oxygen vacancy defect analysis

Raman spectroscopy was used to investigate the structural defects and crystalline disorder induced by dopant ions in the SnO₂ lattice. Fig. 5 shows the Raman spectra of (Al + Si)_xSn_{1-x}O₂ ($x = 0, 0.01$ and 0.02) samples measured in the range of 200–900 nm and the corresponding plots of these Raman peak fitting by the Gaussian function. The typical lattice vibration mode at the Γ point of the Brillouin zone of SnO₂ are described as $A_{1g} + A_{2g} + A_{2u} + B_{1g} + B_{2g} + 2B_{1u} + E_g + 3E_u$.²² Among these modes A_{1g} , B_{1g} , B_{2g} and E_g are Raman active modes, A_{2u} and E_u are IR active modes, while A_{2g} and B_{1u} are inactive in both IR and Raman regions. Fig. 5(b) shows the B_{1u} (238 cm⁻¹), E_g (503 cm⁻¹), A_{1g} (627 cm⁻¹), A_{2u} (688 cm⁻¹) and B_{2g} (762 cm⁻¹) bands in the pure SnO₂. But in (Al + Si)_{0.01}Sn_{0.99}O₂ and (Al + Si)_{0.02}Sn_{0.98}O₂, the A_{1g} band exhibits a shift towards the higher wavenumber side, which is due to the incorporation of Al–Si ions into the SnO₂ lattice, as shown in Fig. 5(c) and (d). This observed blue shift of the A_{1g} modes from

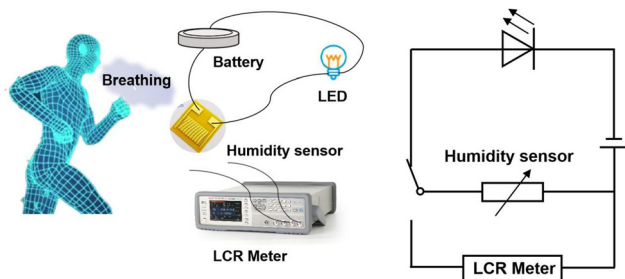


Fig. 2 Circuit diagram for the humidity sensor system for monitoring breathing (LED) and ambient humidity (LCR).

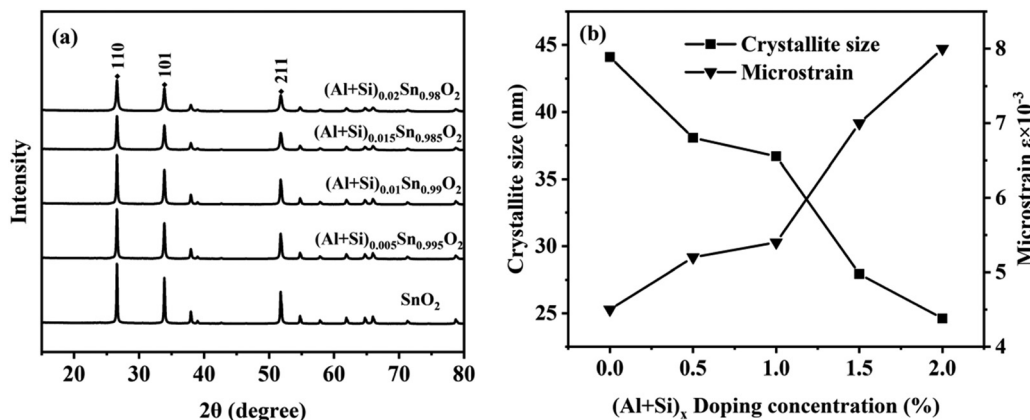


Fig. 3 (a) X-ray diffraction patterns of pure and Al–Si co-doped SnO₂. (b) Plots of crystallite size and microstrain versus doping concentrations of (Al + Si)_xSn_(1-x)O₂.


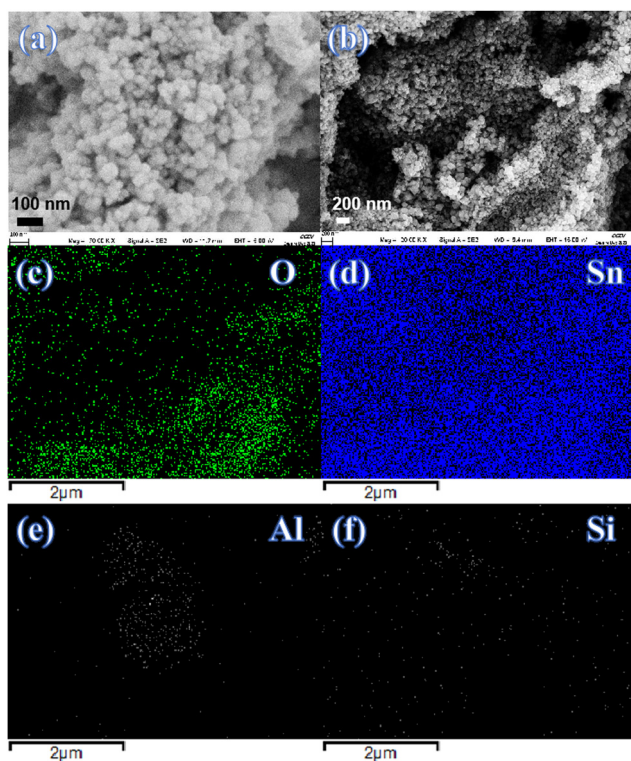


Fig. 4 (a) and (b) FESEM images of (Al + Si)_{0.02}Sn_{0.98}O₂ nanoparticles and (c)–(f) (Al + Si) elemental mapping images.

627 cm⁻¹ to 634 cm⁻¹ can be attributed to the substitution of Sn⁴⁺ with smaller Al³⁺ and Si⁴⁺ ions, as well as the decreased crystallite size resulting from phonon confinement.²³ In Fig. 5(d), the Raman peak at 507 cm⁻¹ in (Al + Si)_{0.02}Sn_{0.98}O₂ is observed to shift to a lower wavenumber compared to pure SnO₂ due to the rearrangement of the internal defect equilibrium. Moreover, in the Raman modes of (Al + Si)_{0.01}Sn_{0.99}O₂ and (Al + Si)_{0.02}Sn_{0.98}O₂, here a small peak appearing at 324 cm⁻¹ and 363 cm⁻¹ represents E_u transverse optical (TO) vibration and that in pure SnO₂ was absent.²⁴ This is due to

interstitial Si (Si_i) in the tin oxide lattice, and the high disordering and low crystallinity of the Al–Si co-doped SnO₂ samples. In the Al–Si addition the following equations may apply.²⁵



In the case of substituting Al³⁺ ions for Sn⁴⁺ and Si⁴⁺ ions, more oxygen vacancy defects V_O^{••} are formed in the (Al + Si)_{0.02}Sn_{0.98}O₂ lattice. Fig. 6 shows the distribution of different kinds of oxygen vacancies like bridging, sub-bridging or in-plane oxygen vacancy of SnO₂ on the surface layer. For different types of oxygen vacancy defects, the Raman mode shows different positions and intensities due to the external strain on the rutile structure. Generally, the peak of SnO₂ around 762 cm⁻¹ is attributed to the presence of bridging or sub-bridging mode of vacancy, while the peak at around 688 cm⁻¹ of the A_{2u} mode is corresponding to the presence of in-plane oxygen vacancy.²⁴ The bridging and sub-bridging modes of oxygen vacancies are sensitive to the adsorption of the water molecules and the conduction of charge carriers.²⁶ As shown in Fig. 5(b) and (c), the Raman peak at 762 cm⁻¹ of pure SnO₂ and (Al + Si)_{0.02}Sn_{0.98}O₂ indicates the presence of a similar concentration of bridging or sub-bridging oxygen vacancies in both materials. However, in Fig. 5(d), there is a notable increase in the intensity of the Raman peak around 762 cm⁻¹ of (Al + Si)_{0.02}Sn_{0.98}O₂, which suggests that the bridging or sub-bridging oxygen vacancy content is enhanced significantly. Hence, the incorporation of Al³⁺ and Si⁴⁺ into the SnO₂ lattice can potentially increase the presence of bridging oxygen vacancies and enhance the adsorption ability towards water molecules. Besides, other fitting small peaks including the E_g mode at 503 cm⁻¹ in the Raman spectra may imply the presence of

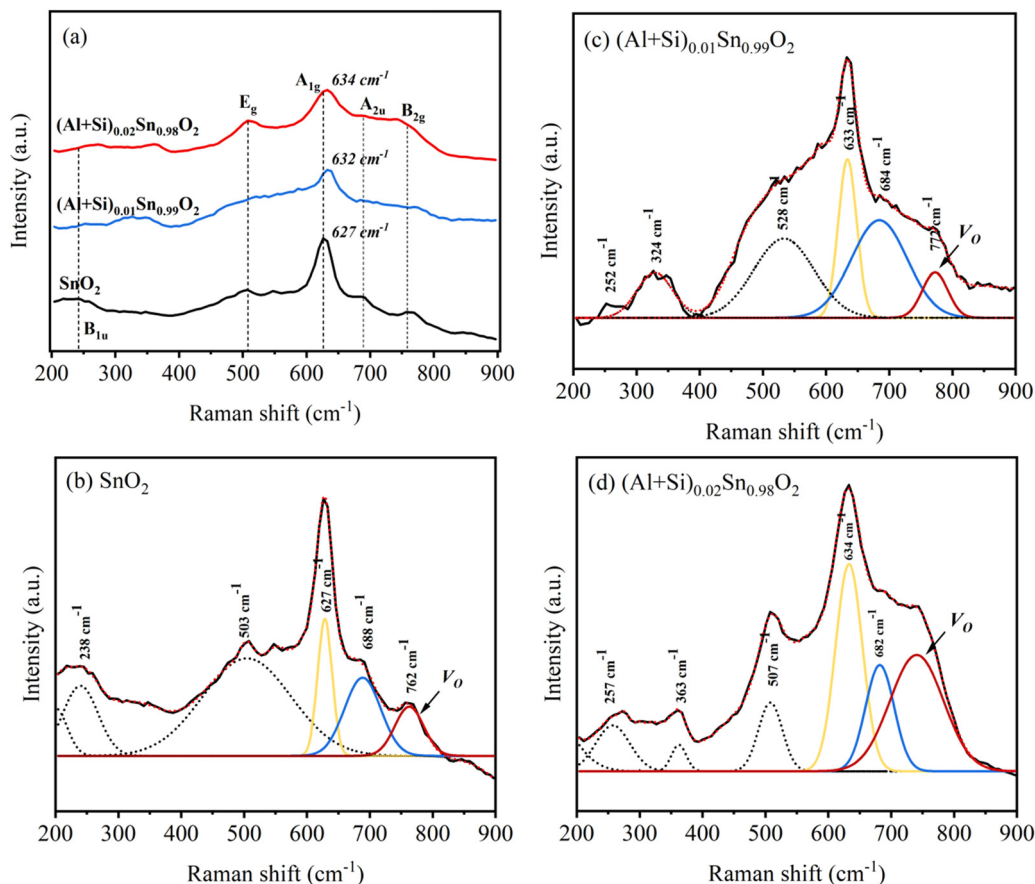


Fig. 5 Raman spectra of pure and Al–Si co-doped SnO₂ (a) general survey spectrum, (b)–(d) deconvolution of the Raman spectrum.

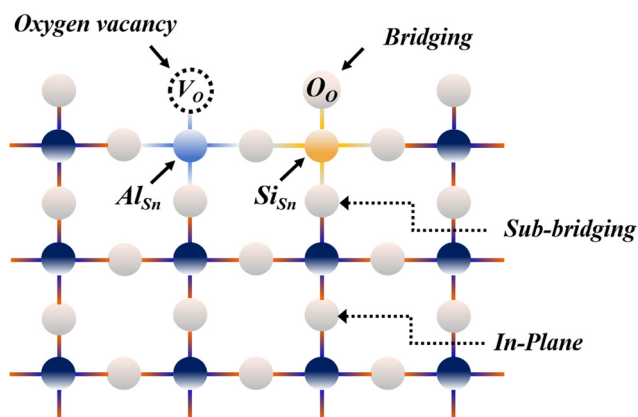


Fig. 6 The illustration of different modes of oxygen atoms on the SnO₂ surface.

defects like tin interstitials (Sn_i) or substitutional defects (Al_{Si}). It can be concluded that the structural defects have been introduced by doping Al–Si ions in the SnO₂ lattice structure.

Electron paramagnetic resonance (EPR) is a highly sensitive technique used to investigate the spin dynamics of paramagnetic centers, including those originating from Al and Si ion incorporated into SnO₂ and oxygen vacancies defects. The EPR

patterns of pure SnO₂ and (Al + Si)_{0.02}Sn_{0.98}O₂ are shown in Fig. 7(a). The *g* factor (EPR parameter) can be calculated to determine the type of defects in the SnO₂ particles. The following equation is commonly used to calculate the *g* factor:²⁷

$$g = \frac{h\nu}{\beta H} \quad (7)$$

where $h = 4.135 \times 10^{-15}$ eVs is the Planck constant, $\nu = 9.48$ GHz is the microwave frequency (Hz), $\beta = 5.788 \times 10^{-5}$ eV T⁻¹ is the electron Bohr magneton and H is the applied magnetic field. The strong symmetrical EPR signal observed at 3514 G ($g = 2.003$) in pure SnO₂ and (Al + Si)_{0.02}Sn_{0.98}O₂ can be ascribed to unpaired electrons originating from the presence of oxygen vacancies. As demonstrated in Fig. 7(b), the concentration of paramagnetic centers is the primary factor influencing the EPR signal intensity and the intensity of the EPR signal increases with the doping of Al and Si. This can be attributed to the increase in the number of oxygen vacancies in (Al + Si)_{0.02}Sn_{0.98}O₂. The number of the spins corresponding to oxygen vacancies was estimated by using the following formula²⁸

$$N_{\text{spins}} = 0.285I(\Delta H)^2 \quad (8)$$

where I represents the peak-to-peak height of the EPR signal (in arbitrary units), and ΔH represents the line width of the signal (in mT). The calculated N_{spins} of pure SnO₂ and

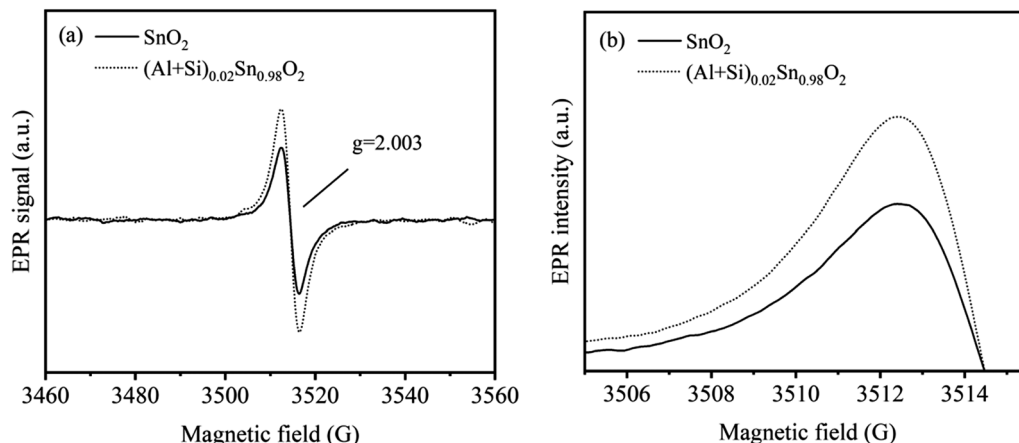


Fig. 7 (a) and (b) EPR spectrum and intensity comparison of pure SnO_2 and $(\text{Al} + \text{Si})_{0.02}\text{Sn}_{0.98}\text{O}_2$.

$(\text{Al} + \text{Si})_{0.02}\text{Sn}_{0.98}\text{O}_2$ are 86.5 and 132.9, respectively. As Al and Si are incorporated into SnO_2 , the calculated N_{spins} of $(\text{Al} + \text{Si})_{0.02}\text{Sn}_{0.98}\text{O}_2$ increase significantly, which is closely related to a 53.6% increase in oxygen vacancies.

3.3 DFT calculations

In order to determine the correlation between the theoretical results and the experimental findings, we performed DFT modeling to investigate the electronic structure of Al–Si co-doped SnO_2 . Fig. 8(a)–(d) shows the schematic representation of the optimized atomic structure of the (100) surface of (a) pure SnO_2 (b) with a single substitutional Al and one oxygen vacancy ($\text{Al}_{\text{Sn}} + \text{V}_{\text{O}}$) (c) with one interstitial Si (Si_{i}) and (d) substitutional Al, substitutional Si and one oxygen vacancy ($\text{Al}_{\text{Sn}} + \text{Si}_{\text{Sn}} + \text{V}_{\text{O}}$). In Table 1, the presence of various combinations of substitutional and interstitial defects results in the

variations in Fermi energy, band gap and lattice parameters. In the case of the pure SnO_2 , the band gap (0.7046 eV) estimated from PBE was an underestimate compared to the experimental values due to its lack of consideration of the discontinuity in the exchange–correlation potential.²⁹ However, this shortcoming has no bearing on our study as we focus on the relative changes in the electronic structure when Al and Si are introduced into SnO_2 .

To better understand the formation of oxygen vacancy defects upon the incorporation of Al–Si ions in SnO_2 , we investigate the DOS and PDOS corresponding to the pure and defective SnO_2 . As shown in Fig. 9(a), the density of partial wave states analysis indicates that the conduction band is primarily contributed by O 2p orbitals and the valence band is mainly composed of Sn 5s and Sn 5p orbitals. It is worth noting that the energy band gap of SnO_2 (0.2344 eV) narrowed significantly for the contributions of Al 3s orbitals to the valence band (Fig. 9b). Therefore the introduction of Al into the system plays the key role in the formation of oxygen vacancies and enhances the carrier transfer between the energy band. Fig. 9(c) shows the contributions of Si 3s orbitals to the electronic structure where the band gap of Si doped SnO_2 (1.3455 eV) has been broadened. This is due to the presence of excess electrons in the system. As seen in Fig. 9(d), the Sn atoms in the SnO_2 crystalline lattice were simultaneously substituted by an Al and a Si atom and oxygen vacancy was introduced, leading to a decrease of band gap to 1.0208 eV.

In general, Al defects and Si defects can act as acceptors and donors, respectively, and they interact with each other through complex mechanisms.³⁰ Li *et al.* reported that co-doping Mo

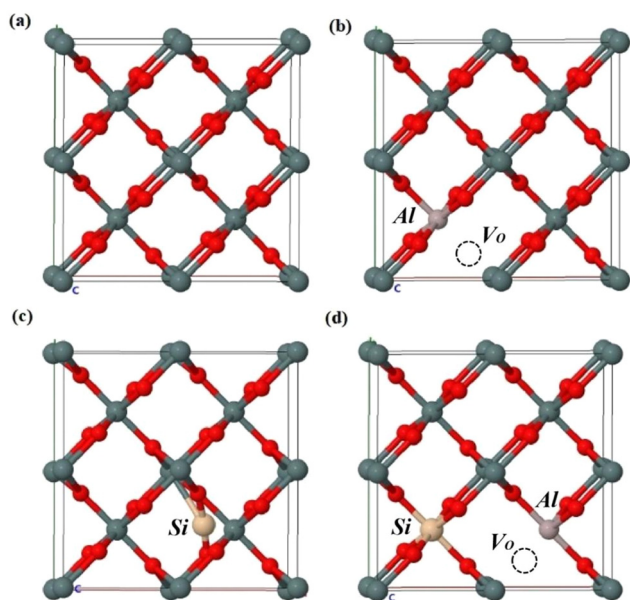


Fig. 8 The schematic representation of the optimized atomic structure of (a) pure SnO_2 , (b) $\text{Al}_{\text{Sn}} + \text{V}_{\text{O}}$, (c) Si_{i} and (d) $\text{Al}_{\text{Sn}} + \text{Si}_{\text{Sn}} + \text{V}_{\text{O}}$.

Table 1 Fermi energy, band gap and lattice parameters for pure and defective SnO_2

	Fermi energy (eV)	Band gap (eV)	a (Å)	b (Å)	c (Å)
Pure SnO_2	4.9084	0.7046	9.637	9.637	3.233
$\text{Al}_{\text{Sn}} + \text{V}_{\text{O}}$	5.0725	0.2344	9.407	9.407	3.203
Si_{i}	7.6627	1.3455	8.629	9.243	3.266
$\text{Al}_{\text{Sn}} + \text{Si}_{\text{sub}} + \text{V}_{\text{O}}$	5.9109	1.0208	9.241	9.209	3.140

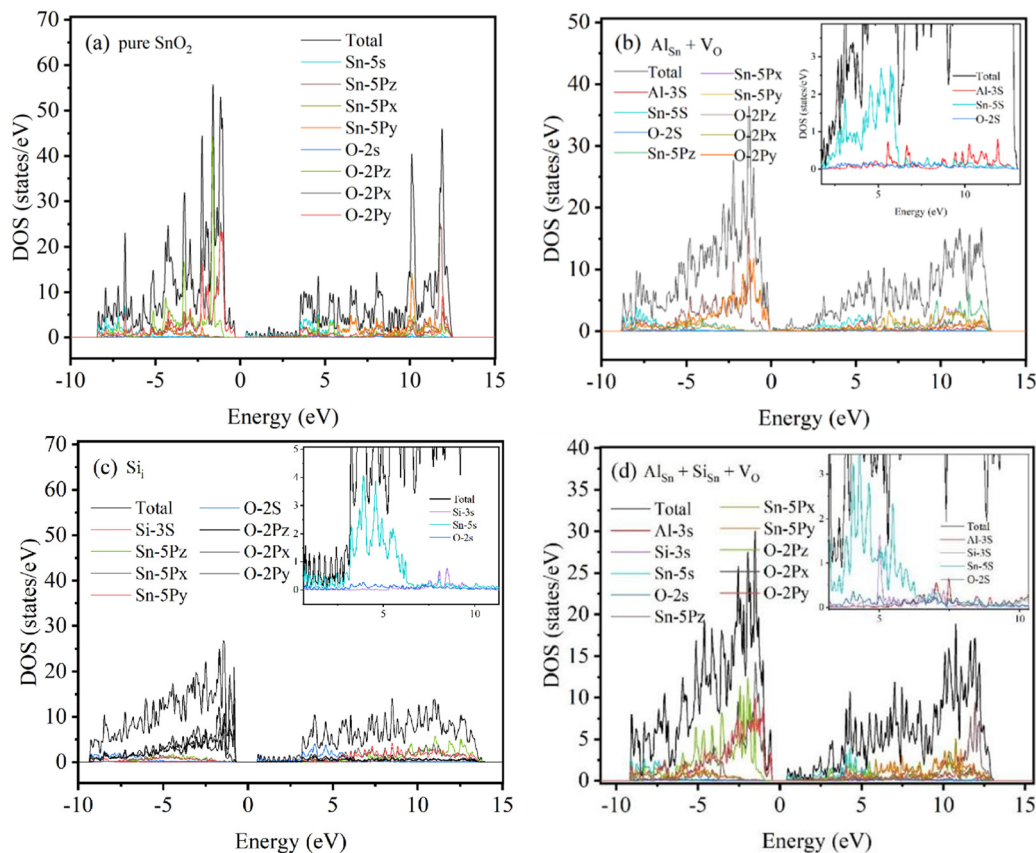


Fig. 9 TDOS and PDOS for (a) pure SnO_2 , (b) $\text{Al}_{\text{Sn}} + \text{V}_\text{O}$, (c) Si_i and (d) $\text{Al}_{\text{Sn}} + \text{Si}_{\text{Sn}} + \text{V}_\text{O}$.

and C can effectively shift the valence band edge while leaving the conduction band edge nearly unaffected.³¹ As shown in Fig. 10, the substitution of Al^{3+} for Sn^{4+} ions was consistently accompanied by the introduction of oxygen vacancies, where Al^{3+} ions played an acceptor role and the Si dopants state functions as temporary trap centers.³² The Si 3s orbitals and Al 3s orbitals have important contributions to the valence band which indicates that the crystalline and electronic structure has been changed with Al–Si co-doping in the SnO_2 . In the case of isovalent doping, the introduction of Si into SnO_2 is favorable for generating additional electrons and forming stable donor-like defects (Si_{Sn}) in the SnO_2 structure. The substitution of Sn^{4+} ions with dopant ions induces the disruption of the original electronic structure, which subsequently leads to the rearrangement of the internal defect equilibrium. Therefore, the contribution of Si 3s orbital and Al 3s orbital to the band edge verifies the presence of acceptor–donor complexes in Al–Si co-doped SnO_2 .

3.4 Humidity sensing properties and respiration detection

The sensing properties can be associated with the change in the capacitance of humidity sensors exposed to humidity at different levels. Fig. 11(a) shows the capacitance variation of the pure and Al–Si co-doped SnO_2 humidity sensors in different RH at a testing frequency of 1 kHz. It can be observed that the capacitance of all the humidity sensors increases with increasing

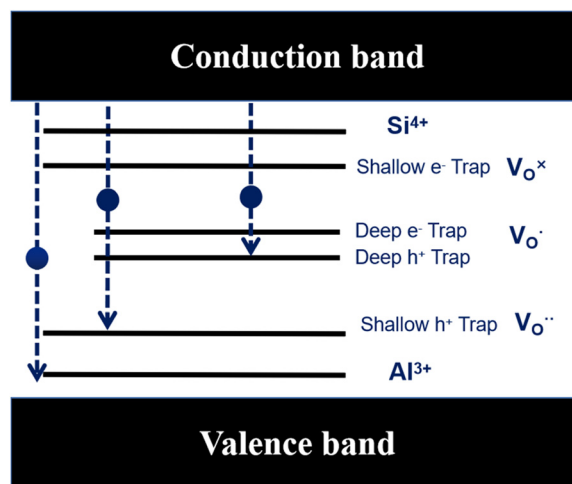


Fig. 10 A schematic band diagram with defect states.

humidity level, which means water molecules are gradually adsorbed on the SnO_2 surface. The sensitivity of the humidity sensor can be calculated using the following formula:³³

$$S = \frac{(C_1 - C_2)}{C_2} \quad (9)$$

where C_1 and C_2 represent the capacitance values at 95% RH

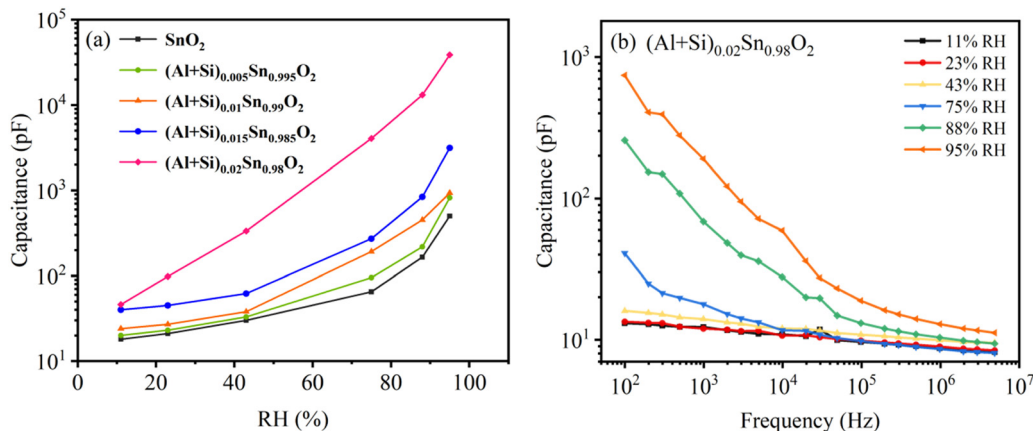


Fig. 11 (a) Capacitance relative humidity curves of pure and Al–Si co-doped SnO₂ humidity sensors. (b) Capacitance frequency curves of (Al + Si)_{0.02}Sn_{0.98}O₂ in different RH.

and 11% RH, respectively. The calculated sensitivity of pure and Al–Si co-doped SnO₂ humidity sensors corresponds to 27, 40, 38, 77 and 839, respectively. It can be found that the sensitivity of the humidity sensor is enhanced as the Al–Si co-doping concentration increases. In these samples (Al + Si)_{0.02}Sn_{0.98}O₂ ($S = 839$) exhibits better linearity and sensing performance due to the 31 times sensitivity of the pure SnO₂ sensor ($S = 27$). This phenomenon can be attributed to more oxygen vacancies formed on the surface of the doped sample where the interplay of Al and Si ions play a significant role. Fig. 11(b) reveals the effect of different frequencies on the capacitance of (Al + Si)_{0.02}Sn_{0.98}O₂ in the range from 11% RH to 95% RH. It can be observed that the capacitance of all the samples decreases as the frequency increases. This phenomenon occurs because the polarization speed of water molecules struggles to keep up with rapid changes in the electric field direction at high working frequencies. As a result, the capacitance decreases and its dependence on relative humidity (RH) diminishes. It can be clearly seen that the variations in the capacitance were clearly distinguishable at low frequencies while it became ambiguous at higher frequencies. The capacitance of the sensor increases with higher relative humidity

(RH). In the case of (Al + Si)_{0.02}Sn_{0.98}O₂, an increased number of oxygen vacancies on the surface allows for more adsorption of water molecules. This leads to the formation of effective ionic conduction, ultimately resulting in an increase in capacitance. As verified above in EPR and Raman analysis, the presence of oxygen vacancies was associated with the Raman peaks at 688 cm⁻¹ and 762 cm⁻¹ and higher intensity of the EPR signal. Furthermore, the electronic structure has been tuned by the contribution of Si 3s orbitals and Al 3s orbitals to the valence band after Al–Si co-doping, which has noticeable implications on the humidity sensing properties. As a result, the capacitance of the humidity sensor increases with rising humidity levels, leading to a humidity sensing response.

Humidity hysteresis is a key aspect to evaluate the dependability and stability of a humidity sensor. Fig. 12(a) and (b) reveals the humidity hysteresis for pure SnO₂ and (Al + Si)_{0.02}Sn_{0.98}O₂ sensors in the adsorption and desorption cycle. During the desorption cycle, the capacitance of the humidity sensor is higher compared to the adsorption process. This is due to the delayed separation of water molecules from the SnO₂ surface, resulting in a prolonged desorption process.³⁴ The equation for the calculated hysteresis of the humidity sensor

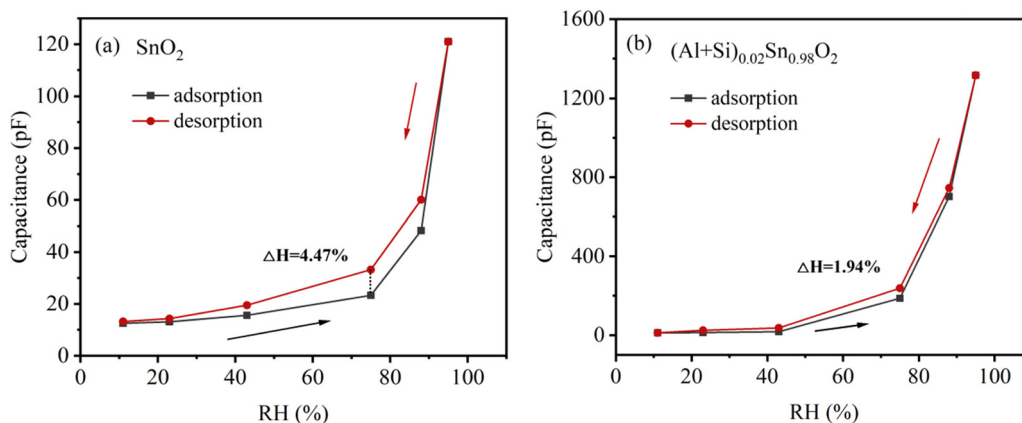


Fig. 12 Humidity hysteresis characteristics of (a) pure SnO₂ and (b) (Al + Si)_{0.02}Sn_{0.98}O₂ humidity sensors.

is as follows:

$$H(\%RH) = \frac{C_A - C_D}{S} \quad (10)$$

where C_A and C_D are the capacitance values obtained at the same RH in the desorption and adsorption process, respectively, and S is the sensitivity of the sensor. The maximum humidity hysteresis for pure SnO_2 and $(\text{Al} + \text{Si})_{0.02}\text{Sn}_{0.98}\text{O}_2$ are 4.47% and 1.94% RH, respectively. The $(\text{Al} + \text{Si})_{0.02}\text{Sn}_{0.98}\text{O}_2$ sensor exhibits a significantly reduced hysteresis compared to pure SnO_2 , which indicates that the addition of Al^{3+} and Si^{4+} ions accelerates the desorption process on the SnO_2 surface. However, it is important to note that the fabricated SnO_2 humidity sensor may encounter challenges related to variations in environmental humidity and temperature, which can impact the response and decay time of the device, leading to less than optimal results.

Fig. 13 illustrates the response/recovery time of the humidity sensors based on pure and Al–Si co-doped SnO_2 , covering a humidity range from 11% RH to 95% RH. The response/recovery time of the humidity sensor are defined as the duration required for sensor's capacitance variation to reach 90% of its total capacitance change. The $(\text{Al} + \text{Si})_{0.02}\text{Sn}_{0.98}\text{O}_2$ sensor exhibits a rapid response time of 25 s and a recovery time 5 s while the corresponding response/recovery times of $(\text{Al} + \text{Si})_{0.01}\text{Sn}_{0.99}\text{O}_2$ and pure SnO_2 are 37 s/6 s and 54 s/14 s. The fast response/recovery times of $(\text{Al} + \text{Si})_{0.02}\text{Sn}_{0.98}\text{O}_2$ are mainly due to the fact that the substitution of Al^{3+} and Si^{4+} into SnO_2 can enhance the adsorption activity of SnO_2 . It can be concluded that the recovery capability of the SnO_2 sensor depends on Al and Si doping concentrations. Table 2 presents a comparison of the sensing performance for the humidity sensors based on different sensing materials. The results highlight that the $(\text{Al} + \text{Si})_{0.02}\text{Sn}_{0.98}\text{O}_2$ humidity sensor exhibits several advantages, including faster response and recovery times, as well as lower hysteresis. These findings suggest that the inclusion of

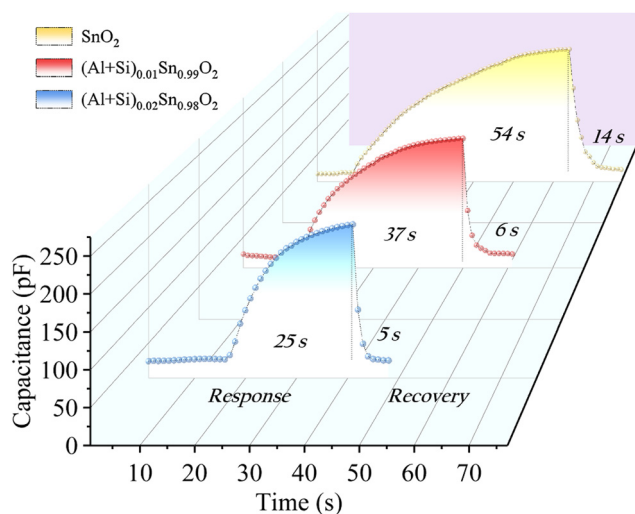


Fig. 13 Response/recovery time of pure and Al–Si co-doped SnO_2 humidity sensors at the humidity ranging from 11% to 95% RH.

Table 2 A comparison of humidity sensing performance in previously reported work

Material	Response time (s)	Recovery time (s)	Hysteresis (%)	Ref.
$\text{SnO}_2/\text{SiO}_2$	14	16	2	35
ZrP	57	9	5.2	36
Al/ SnO_2	100	88	—	37
$\text{Na}_{1/3}\text{Sr}_{1/3}\text{Tb}_{1/3}\text{Cu}_3\text{Ti}_4\text{O}_{12}$	179	220	10.3	38
$(\text{Al} + \text{Si})_{0.02}\text{Sn}_{0.98}\text{O}_2$	25	5	1.94	This work

Al–Si dopants plays a crucial role in enhancing the adsorption of water molecules on the SnO_2 surface, thus improving the overall performance of the sensor.

Respiratory detection plays a crucial role in the prevention of respiratory diseases and fitness tracking. Fig. 14(a)–(d) shows the response testing of pure SnO_2 and Al–Si co-doped SnO_2 sensors towards different breathing rates. The instantaneous capacitance of the humidity sensor was measured using the LCR testing instrument. The changes in capacitance were highly variable when the person breathed in different rates or depths and then according to it, the breathing was distinguished into shallow, medium and deep respiration. As seen from Fig. 14(b)–(d), the capacitance values of the Al–Si co-doped samples change more quickly than that of SnO_2 under different respiratory rates. For pure SnO_2 , the respiratory intervals for response/recovery time at shallow (20–250 pF), medium (250–400 pF) and deep (400–650 pF) breathing states were 4.7 s, 5.5 s and 6.3 s respectively. After increasing the content of Al–Si (as shown in Fig. 14(b)–(d)), the average response intervals decreased by approximately 1.8 seconds in different breathing states compared to pure SnO_2 . In the case of the $(\text{Al} + \text{Si})_{0.02}\text{Sn}_{0.98}\text{O}_2$ sensor, it was observed that the average response time in the shallow breathing state was shorter, indicating a quicker response. This suggests that the introduction of Al^{3+} and Si^{4+} into SnO_2 can enhance the response and recovery ability of the material. This finding demonstrates the promising potential of Al–Si co-doped SnO_2 for promptly monitoring breathing rates and depths. Consequently, the $(\text{Al} + \text{Si})_{0.02}\text{Sn}_{0.98}\text{O}_2$ sensor exhibited outstanding humidity sensing performance, further establishing its potential as an advanced respiratory sensor.

3.5 Humidity sensing mechanism

The chemical mechanisms for the enhancement in the humidity sensitivity induced by structural defects such as oxygen vacancies were proposed. As shown in Fig. 15, the introduction of dopant ions induces the formation of substitutional defects Al_{Sn} , Si_{Sn} and the oxygen vacancies in the crystalline structure of SnO_2 . The introduction of the Al–Si dopant ions leads to the generation of oxygen vacancies. This increased the presence of oxygen vacancy defects provides additional active surface adsorption sites for water molecules on the surface of Al–Si co-doped SnO_2 . The oxygen vacancies accelerate water adsorption and desorption reactions, which is beneficial for hopping transportation of protons on the SnO_2 surface.³⁹ The water molecules adsorption/desorption reaction formula on the surface of SnO_2 are as



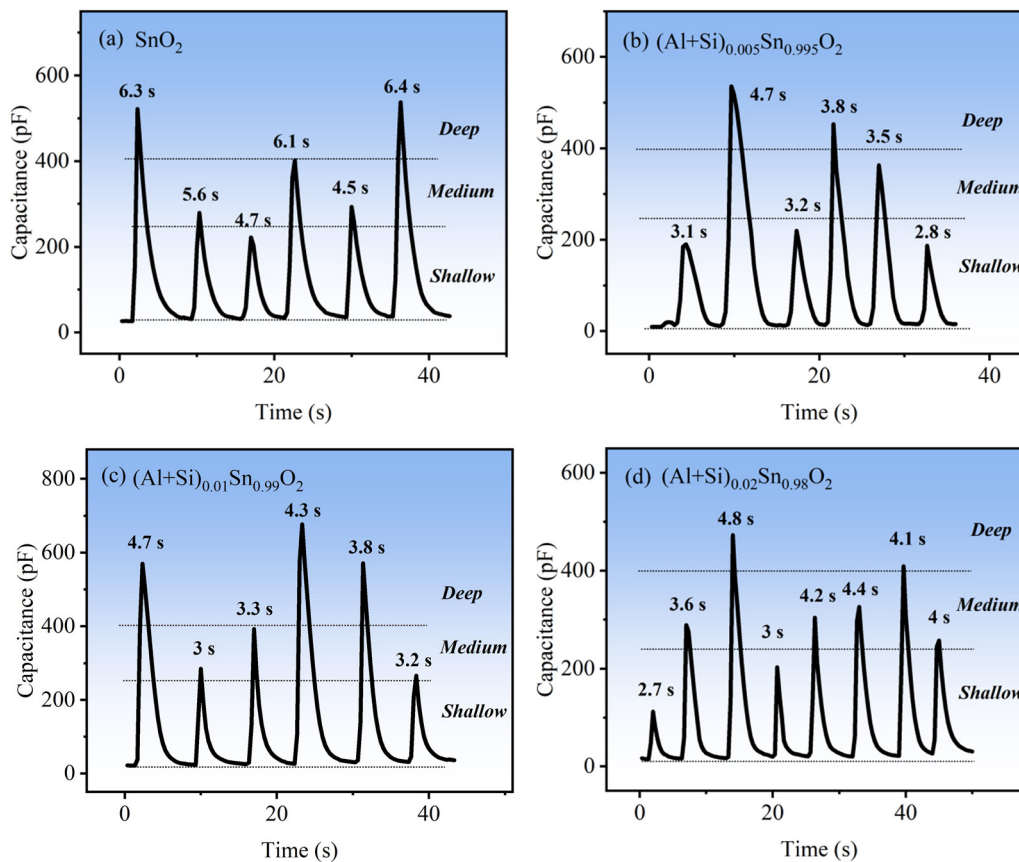


Fig. 14 The respiratory intervals of (a) pure and (b–d) Al–Si co-doped SnO₂ for response/recovery time at shallow, medium and deep breathing states.

follows:⁴⁰



where $\text{O}_s^{-\alpha}$ represents a surface adsorbed oxygen species with $\alpha = 1$ indicating singly ionized oxygen species or $\alpha = 2$ for doubly ionized oxygen species; e^- represents an electron in the conduction band surface; and S represents a surface adsorption site. In the case of Al–Si co-doping, the oxygen vacancies originating from Al and Si ions incorporated into SnO₂ can consume excess electrons, and

since then, the oxygen vacancies with one trapped electron increased significantly. Both the oxygen vacancies and the electrons can serve as charge carriers to facilitate electronic conduction and enhance the capacitance. As a result, the oxygen vacancies can accelerate the ionisation of water molecules into conductive H^+ and bind the water molecules near oxygen vacancies into H_3O^+ ($\text{H}_2\text{O} \rightarrow \text{H}^+ + \text{OH}^-$, $\text{H}^+ + \text{H}_2\text{O} \rightarrow \text{H}_3\text{O}^+$), thereby enhancing the sensors sensitivity at different humidity levels and rapidly increasing its capacitance.⁴¹ Hence, the introduction of Al and Si ions is responsible for the enhancement of the sensitivity and linearity of the sensor.

4. Conclusions

In this study, we successfully synthesized a novel capacitive humidity sensor utilizing acceptor–donor co-doped SnO₂ nanoparticles for the detection of ambient humidity and human respiration. The Raman spectra reveal an increased presence of bridging mode oxygen vacancies in $(\text{Al} + \text{Si})_{0.02}\text{Sn}_{0.98}\text{O}_2$. Additionally, the EPR results demonstrate a higher concentration of singly ionized oxygen vacancies following the introduction of Al–Si. Furthermore, DFT calculations provide evidence that Si 3s orbital and Al 3s orbital contribute to the band edge, confirming the formation of acceptor–donor complexes in Al–Si co-doped SnO₂. The humidity sensing experiment showed that the $(\text{Al} + \text{Si})_{0.02}\text{Sn}_{0.98}\text{O}_2$ humidity sensor exhibited high

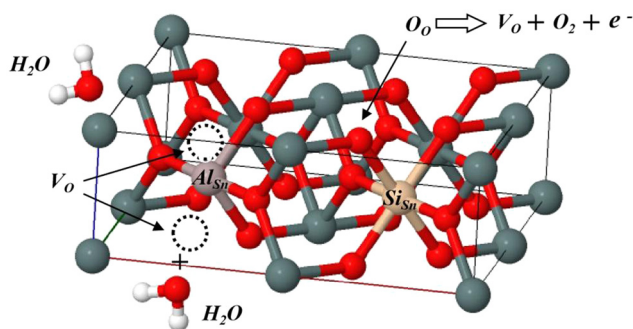


Fig. 15 Structure diagram of the defects $\text{Al}_{\text{Sn}} + \text{Si}_{\text{Sn}} + \text{V}_\text{O}$ reacting with water molecules.

sensitivity ($S = 839$), low hysteresis (1.94%), fast response/recovery times (25 s/5 s) and quick respiratory intervals at three breathing states. We also discussed the chemical mechanisms for the enhancement in the humidity sensitivity induced by oxygen vacancies in $(\text{Al} + \text{Si})_{0.02}\text{Sn}_{0.98}\text{O}_2$. Hence, the $(\text{Al} + \text{Si})_{0.02}\text{Sn}_{0.98}\text{O}_2$ sensor exhibits excellent humidity sensing characteristics for detecting ambient humidity and human respiratory rate.

Research data policy and data availability statements

All data generated or analysed during this study are included in this published article.

Author contributions

All authors contributed to the study conception and design. Yuchuan Ding performed material preparation, data collection, analysis, and the creation of new software used in the work. Yong Chen made substantial contributions to the conception and design of the work, and Mao-Hua Wang revised the work critically for important intellectual content. The first draft of the manuscript was written by Yuchuan Ding and all authors commented on the previous versions of the manuscript.

Conflicts of interest

The authors declare that they have no conflict of interest.

Acknowledgements

This research was partially supported by the grant from Changzhou University with KYCX20-2566.

References

- 1 Y. Su, C. Li, M. Li, H. Li, S. Xu and L. Qian, *et al.*, Surface acoustic wave humidity sensor based on three-dimensional architecture graphene/PVA/SiO₂ and its application for respiration monitoring, *Sens. Actuators, B*, 2020, **308**(0925–4005), 127693.
- 2 S. Kano, K. Kim and M. Fujii, Fast-Response and Flexible Nanocrystal-Based Humidity Sensor for Monitoring Human Respiration and Water Evaporation on Skin, *ACS Sens.*, 2017, **2**(6), 828–833.
- 3 H. Jin, T. P. Huynh and H. Haick, Self-Healable Sensors Based Nanoparticles for Detecting Physiological Markers via Skin and Breath: Toward Disease Prevention via Wearable Devices, *Nano Lett.*, 2016, **16**(7), 4194–4202.
- 4 H. Zhang, S. Yu, C. Chu, J. Zhang, J. Liu and P. Li, Effects on structure, surface oxygen defects and humidity performance of Au modified ZnO via hydrothermal method, *Appl. Surf. Sci.*, 2019, **486**(0169–4332), 482–489.
- 5 Q. Zhu, Y. Jin, W. Wang, G. Sun and D. Wang, Bioinspired Smart Moisture Actuators Based on Nanoscale Cellulose Materials and Porous, Hydrophilic EVOH Nanofibrous Membranes, *ACS Appl. Mater. Interfaces*, 2018, **11**(1), 1440–1448.
- 6 T. Y. Li, R. J. Si, J. Sun, S. T. Wang, J. Wang and R. Ahmed, *et al.*, Giant and controllable humidity sensitivity achieved in (Na + Nb) co-doped rutile TiO₂, *Sens. Actuators, B*, 2019, **293**(0925–4005), 151–158.
- 7 J. Wang, Y. M. Guo, S. T. Wang, L. Tong, J. Sun and G. B. Zhu, *et al.*, The effect of humidity on the dielectric properties of (In + Nb) co-doped SnO₂ ceramics, *J. Eur. Ceram. Soc.*, 2019, **39**(2–3), 323–329.
- 8 I. Paulowicz, V. Hrkac, S. Kaps, V. Cretu, O. Lupan and T. Braniste, *et al.*, Three-Dimensional SnO₂ Nanowire Networks for Multifunctional Applications: From High-Temperature Stretchable Ceramics to Ultraresponsive Sensors, *Adv. Electron. Mater.*, 2015, **1**(8), 1500081.
- 9 M. Eslamian, A. Salehi and E. Nadimi, The role of oxygen vacancies on SnO₂ surface in reducing cross-sensitivity between ambient humidity and CO: a first principles investigation, *Surf. Sci.*, 2021, **708**(0039–6028), 121817.
- 10 Q. Zhou, W. Chen, L. Xu, R. Kumar, Y. Gui and Z. Zhao, *et al.*, Highly sensitive carbon monoxide (CO) gas sensors based on Ni and Zn doped SnO₂ nanomaterials, *Ceram. Int.*, 2018, **44**(4), 4392–4399.
- 11 W. Zeng, T. Liu, Z. Wang, S. Tsukimoto, M. Saito and Y. Ikuhara, Selective Detection of Formaldehyde Gas Using a Cd-Doped TiO₂–SnO₂ Sensor, *Sensors*, 2009, **9**(11), 9029–9038.
- 12 M. Sik Choi, J. H. Ahn, M. Young Kim, A. Mirzaei, S. M. Choi and D. Won Chun, *et al.*, Changes in the crystal structure of SnO₂ nanoparticles and improved H₂S gas-sensing characteristics by Al doping, *Appl. Surf. Sci.*, 2021, **565**(0169–4332), 150493.
- 13 K. Suematsu, M. Sasaki, N. Ma, M. Yuasa and K. Shimano, Antimony-Doped Tin Dioxide Gas Sensors Exhibiting High Stability in the Sensitivity to Humidity Changes, *ACS Sens.*, 2016, **1**(7), 913–920.
- 14 Y. N. Sun, M. Goktas, L. Zhao, P. Adelhelm and B. H. Han, Ultrafine SnO₂ nanoparticles anchored on N,P-doped porous carbon as anodes for high performance lithium-ion and sodium-ion batteries, *J. Colloid Interface Sci.*, 2020, **572**(0021–9797), 122–132.
- 15 F. Mao, C. Z. Gao, F. Wang, C. Zhang and F. S. Zhang, Ab Initio Study of Ferromagnetism Induced by Electronic Hole Localization in Al-Doped α -SiO₂, *J. Phys. Chem. C*, 2017, **121**(41), 23055–23061.
- 16 D. Li, Y. Jiang, P. Zhang, D. Shan, J. Xu and W. Li, *et al.*, The phosphorus and boron co-doping behaviors at nanoscale in Si nanocrystals/SiO₂ multilayers, *Appl. Phys. Lett.*, 2017, **110**(23), 233105.
- 17 T. Zheng, W. He, L. Wang, J. Li and S. Zheng, Effect of different substrates on Si and Ta co-doped Ga₂O₃ films prepared by pulsed laser deposition, *J. Cryst. Grow.*, 2020, **533**, 125455.
- 18 T. Boucherka, M. Touati, A. Berbadj and N. Brihi, Al³⁺ doping induced changes of structural, morphology,

- photoluminescence, optical and electrical properties of SnO₂ thin films as alternative TCO for optoelectronic applications, *Ceram. Int.*, 2023, **49**(4), 5728–5737.
- 19 Z. Duan, J. Li, Z. Yuan, Y. Jiang and H. Tai, Capacitive humidity sensor based on zirconium phosphate nanoplates film with wide sensing range and high response, *Sens. Actuators, B*, 2023, **394**(0925–4005), 134445.
 - 20 C. Belkhaoui, N. Mzabi and H. Smaoui., Investigations on structural, optical and dielectric properties of Mn doped ZnO nanoparticles synthesized by co-precipitation method, *Mater. Res. Bull.*, 2019, **111**(0025–5408), 70–79.
 - 21 N. S. Ramgir, Y. Kyu Hwang, I. S. Mulla and J. S. Chang, Effect of particle size and strain in nanocrystalline SnO₂ according to doping concentration of ruthenium, *Solid State Sci.*, 2006, **8**(3–4), 359–362.
 - 22 N. Ahmad, S. Khan and M. M. Nizam Ansari, Exploration of Raman spectroscopy, dielectric and magnetic properties of (Mn,Co) co-doped SnO₂ nanoparticles, *Phys. B*, 2019, **558**(0921–4526), 131–141.
 - 23 L. Z. Liu, T. H. Li, X. L. Wu, J. C. Shen and P. K. Chu, Identification of oxygen vacancy types from Raman spectra of SnO₂ nanocrystals, *J. Raman Spectrosc.*, 2012, **43**(10), 1423–1426.
 - 24 L. Z. Liu, X. L. Wu, F. Gao, J. C. Shen, T. H. Li and P. K. Chu, Determination of surface oxygen vacancy position in SnO₂ nanocrystals by Raman spectroscopy, *Solid State Commun.*, 2011, **151**(11), 811–814.
 - 25 G. Zhang, C. Xie, S. Zhang, S. Zhang and Y. Xiong, Defect Chemistry of the Metal Cation Defects in the p- and n-Doped SnO₂ Nanocrystalline Films, *J. Phys. Chem. C*, 2014, **118**(31), 18097–18109.
 - 26 K. Pavithra and S. Murugesan, Embedding oxygen vacancies at SnO₂-CNT surfaces via a microwave polyol strategy towards effective electrocatalytic reduction of carbon-dioxide to formate, *Catal. Sci. Technol.*, 2020, **10**(5), 1311–1322.
 - 27 M. A. Paulin, G. Alejandro, D. G. Lamas, M. Quintero, R. O. Fuentes and J. E. Gayone, *et al.*, Oxygen vacancies and their role on the magnetic character of polycrystalline CeO₂, *Ceram. Int.*, 2023, **49**(3), 5146–5153.
 - 28 K. Thiyagarajan and K. Sivakumar, Oxygen vacancy-induced room temperature ferromagnetism in graphene-SnO₂ nanocomposites, *J. Mater. Sci.*, 2017, **52**(13), 8084–8096.
 - 29 L. Villamagua, R. Rivera, D. Castillo and M. Carini, A quantum chemical analysis of Zn and Sb doping and co-doping in SnO₂, *AIP Adv.*, 2017, **7**(10), 105010.
 - 30 J. Zhang, F. Xie, L. Yang, S. Guo, Y. Xiong and S. Zhang, Effect of Co doping on chemisorbed oxygen accumulation and gas response of SnO₂ under dynamic program cooling, *Sens. Actuators, B*, 2021, **340**(0925–4005), 129810.
 - 31 Y. Li, R. Deng, Y. Tian, B. Yao and T. Wu, Role of donor-acceptor complexes and impurity band in stabilizing ferromagnetic order in Cu-doped SnO₂ thin films, *Appl. Phys. Lett.*, 2012, **100**(17), 172402.
 - 32 Y. Ding, Y. Chen and M. Wang, Effects of Al incorporation on structural and humidity-sensing properties of SnO₂ sensor, *J. Mater. Sci.: Mater. Electron.*, 2024, **35**(2), 172.
 - 33 F. Li, P. Li and H. Zhang, Preparation and Research of a High-Performance ZnO/SnO₂ Humidity Sensor, *Sensors*, 2021, **22**(1), 293.
 - 34 M. Panday, G. K. Upadhyay and L. P. Purohit, Sb incorporated SnO₂ nanostructured thin films for CO₂ gas sensing and humidity sensing applications, *J. Alloys Compd.*, 2022, **904**(0925–8388), 164053.
 - 35 M. Parthibavarman, V. Hariharan and C. Sekar, High-sensitivity humidity sensor based on SnO₂ nanoparticles synthesized by microwave irradiation method, *Mater. Sci. Eng., C*, 2011, **31**(5), 840–844.
 - 36 Y. Zhu, J. Chen, H. Li, Y. Zhu and J. Xu, Synthesis of mesoporous SnO₂-SiO₂ composites and their application as quartz crystal microbalance humidity sensor, *Sens. Actuators, B*, 2014, **193**(0925–4005), 320–325.
 - 37 P. Pascariu, A. Airinei, N. Olaru, I. Petrila, V. Nica and L. Sacarescu, *et al.*, Microstructure, electrical and humidity sensor properties of electrospun NiO-SnO₂ nanofibers, *Sens. Actuators, B*, 2016, **222**(0925–4005), 1024–1031.
 - 38 S. Sriluarueang, B. Putasaeng, K. Sreejivungsa, N. Thanamoon and P. Thongbai, Giant dielectric response, nonlinear characteristics, and humidity sensing properties of a novel perovskite: Na_{1/3}Sr_{1/3}Tb_{1/3}Cu₃Ti₄O₁₂, *RSC Adv.*, 2023, **13**(42), 29706–29720.
 - 39 H. Zhang, H. Zhang, J. Man and C. Chen, Preparation of high performance Fe-doped SnO₂ humidity sensor and its application in respiration detection, *Sens. Actuators, A*, 2023, **362**(0924–4247), 114644.
 - 40 K. Grossmann, R. G. Pavelko, N. Barsan and U. Weimar, Interplay of H₂, water vapor and oxygen at the surface of SnO₂ based gas sensors – An operando investigation utilizing deuterated gases, *Sens. Actuators, B*, 2012, **166–167**(0925–4005), 787–793.
 - 41 J. Wu, Q. Huang, D. Zeng, S. Zhang, L. Yang and D. Xia, *et al.*, Al-doping induced formation of oxygen-vacancy for enhancing gas-sensing properties of SnO₂ NTs by electrospinning, *Sens. Actuators, B*, 2014, **198**(0925–4005), 62–69.