



Showcasing research from Professor Ujjwal Pal's laboratory, Department of Energy and Environmental Engineering, CSIR-Indian Institute of Chemical Technology, Hyderabad, India.

Surface engineering of a 2D CuFe-LDH/MoS₂ photocatalyst for improved hydrogen generation

We have showcased the synthesis of S-type heterojunctions in CuFe-LDH/MoS₂ composites with 2D/2D architectures through hydrothermal processes, with significantly enhanced photocatalytic hydrogen production performance.

As featured in:



See Ujjwal Pal *et al.*,
Mater. Adv., 2024, 5, 4159.

Cite this: *Mater. Adv.*, 2024,
5, 4159

Surface engineering of a 2D CuFe-LDH/MoS₂ photocatalyst for improved hydrogen generation†

Chandra Shobha Vennapoosa,^{ab} Sandip Prabhakar Shelake,^{bc} Bhavya Jaksani,^{ab}
Aparna Jamma,^{ab} B. Moses Abraham,^{id} d Annadanam V. Sesha Sainath,^{bc}
Mohsen Ahmadipour^e and Ujjwal Pal^{id} *^{ab}

Creating effective heterostructure photocatalysts with S-scheme-based charge-transfer dynamics enables efficient electron transfers, thereby enhancing visible-light-induced photocatalytic hydrogen production. In this report, we investigate a series of CuFe-LDH/MoS₂ composites synthesized by employing MoS₂ with CuFe-LDH through a self-assembled chemical method and an *in situ* hydrothermal process. The morphological features illustrate a consistent stacked nanosheet-like structure. The enhanced electronic and optical properties of the as-prepared CuFe-LDH/MoS₂ and their improved photocatalytic hydrogen evolution execution is credited to the S-scheme heterojunction preventing the recombination of photogenerated charge transporters and improving the fast charge transference and utilization. The CuFe-LDH/MoS₂ photocatalyst exhibits a superior photocatalytic H₂ creation rate of 3.4 mmol g⁻¹ h⁻¹ and an AQY of 1.3% compared to CuFe-LDH (1.3 mmol g⁻¹ h⁻¹; AQY:0.5%). DFT studies reveal that the synergistic effects of the CuFe-LDH/MoS₂ interface effectively enhance both the thermodynamics and kinetics of the rate-determining step for the hydrogen evolution reaction, which aligns with the experimental results. This design approach paves the way for creating highly efficient photocatalysts for future research in this promising domain.

Received 19th October 2023,
Accepted 13th February 2024

DOI: 10.1039/d3ma00881a

rsc.li/materials-advances

Introduction

Solar energy stands as an endless, environmentally friendly, and sustainable energy source on our planet. Generating hydrogen from water using solar energy is often considered one of the cleanest forms of energy production.^{1–3} Under solar irradiation, a photocatalyst instigates the activation of water molecules, leading to the generation of hydrogen and oxygen, thus efficiently transmuting solar energy into hydrogen.^{4–9} Nevertheless, the realm of photocatalysis presents numerous exigencies necessitating further investigation, including strategies for mitigating electron-hole pair recombination and addressing

photocatalyst photo-corrosion.^{10–12} Consequently, the imperative remains to cultivate a resilient and highly efficient photocatalyst.

LDH is categorized as a two-dimensional material (2D), characterized by positively charged layers where the positive charge is counterbalanced by different anions residing between the layers. Consequently, LDH as a whole remains electrically neutral and retains a contingent presence of H₂O molecules.^{13–15} The structural chemical formula for LDH can be expressed as [M_{1–x}²⁺M_x³⁺(OH)₂][X⁺A_{x/n}]^{n–m}H₂O, encompassing divalent metal cations such as Ni²⁺, Mg²⁺, Cu²⁺, and Zn²⁺ (with a valence of +2), and trivalent metal cations including Al³⁺, Fe³⁺, Cr³⁺, and Sc³⁺ (with a valence of +3).^{16,17} Owing to the advantageous characteristics of variable elemental composition, a substantial precise surface area, and robust stability exhibited by LDHs, their structural features can be readily tailored and controlled. Consequently, LDHs find extensive applications in the fields of photocatalysis and electrocatalysis.^{18–20} However, owing to the sluggish transference rate of photogenerated transporters produced by individual LDHs upon photo excitation; LDHs alone lack a pronounced impact on H₂ evolution.^{21–23} Hence, various strategies have been devised to enhance the H₂ evolution efficiency, such as the construction of heterojunctions or the reinforcement of coupling between two semiconductors. For instance, NiAl-LDH/CdS

^a Department of Energy & Environmental Engineering, CSIR-Indian Institute of Chemical Technology, Tarnaka, Hyderabad, Telangana 500007, India.

E-mail: upal03@gmail.com, ujjwalpal@iict.res.in

^b Academy of Scientific & Innovative Research (AcSIR), Ghaziabad, Uttar Pradesh 201002, India

^c Polymers and Functional Materials and Fluoro-Agrochemicals Department, CSIR-Indian Institute of Chemical Technology, Uppal Road, Hyderabad 500007, India

^d Department of Chemical Engineering, Indian Institute of Technology Kanpur, Kanpur 208016, India

^e Institute of Power Engineering, Universiti Tenaga Nasional, 43650 Serdang, Selangor, Malaysia

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3ma00881a>




promotes H₂ evolution by establishing S-schemes that consume superfluous e⁻ and h⁺.²⁴ The synthesis of CoAl-LDH/RGO nanocomposites through a solvothermal method effectively facilitates the transfer and separation of photogenerated charge carriers, thereby enhancing the composite properties.^{25,26}

In the field of photocatalysis, molybdenum sulfides (Mo sulfides), notably MoS₂, have become the most prospective platinum (Pt) substitutes.^{27,28} In contrast, MoS₂ is an intrinsically n-type semiconductor containing a sandwich-like stacked S–Mo–S fashion in a stack of planes that are closely filled in a hexagonal arrangement and have a van der Waals interaction between two adjacent planes. The indirect and direct band gaps are 1.2 eV, but MoS₂ lies within 1.9 eV, which is mostly employed in photocatalysis.²⁹ This material has garnered substantial attention within the photocatalysis community due to its wide availability, favorable electrical conductivity, and facile synthesis.³⁰ Moreover, MoS₂ exhibits exceptional photocatalytic performance attributed to its robust light absorption capabilities within the visible spectrum, chemical stability, and narrow band gap.³¹ MoS₂ has found extensive utility in photocatalysis, with notable examples including the TiO₂/MoS₂,³² MoS₂/g-C₃N₄,³³ and CuO@ZnO³⁴ systems, which leverage heterojunction construction to expedite the separation of photoinduced charge carriers and enhance H₂ production. To bolster the efficiency of photocatalytic water splitting, various heterojunction types, such as type Z, type I, and type II, can be engineered. The S-scheme heterojunction encompasses considerations of band bending, electrostatic interactions between semiconductor materials, and the creation of intrinsic electric fields, thus enriching the model conditions relative to alternative heterojunction configurations.^{35–37} Within this context, the S-scheme heterojunction achieved by combining CuFe-LDH and MoS₂ serves to not only suppress the recombination of photoinduced charge carriers but also enhance the production of H₂ gas.

In the current study, we have constructed an S-scheme photocatalyst by combining 2H-MoS₂ and CuFe-LDH, which act as the building blocks for constructing type-II CuFe-LDH/MoS₂ electrostatic heterostructures through hydrothermal processes, as detailed in Scheme 1. Initially, LDH exhibits limited charge carrier conductivity. Nevertheless, the establishment of a heterojunction with MoS₂ substantially elevates their conductivity by facilitating charge carrier transport. This enhancement proves advantageous for the promotion of more effective photocatalytic redox reactions. The persistent coverage of CuFe-LDH nanosheets with MoS₂ nanosheets reveals a highly efficient pathway for the transfer of holes from CuFe-LDH to the scavenger in the oxidation reaction, and the transfer of electrons from MoS₂ for the reduction reaction, as observed in the S-scheme charge separation mechanism. Furthermore, we investigated the photocatalytic efficacy of various composite catalysts, and it was established that the CuFe-LDH/MoS₂ photocatalyst exhibited superior photocatalytic performance. The formation of an S-scheme heterojunction reduced the recombination of photogenerated carriers, resulting in a notable enhancement of the transfer of photogenerated charges at the catalyst interface. Additionally, an in-depth investigation of the photochemical properties and intrinsic mechanisms of CuFe-LDH/MoS₂ was carried out. This research has effectively enhanced the photocatalytic hydrogen production capabilities of the catalyst through straightforward methods, thereby increasing its potential for significant advancement in the realm of photocatalytic hydrogen production.

Results and discussion

The crystallographic structures of the powders were initially synthesized *via* X-ray diffraction (XRD) analysis, as depicted in Fig. 1(a). The intrinsic diffraction features corresponding to the

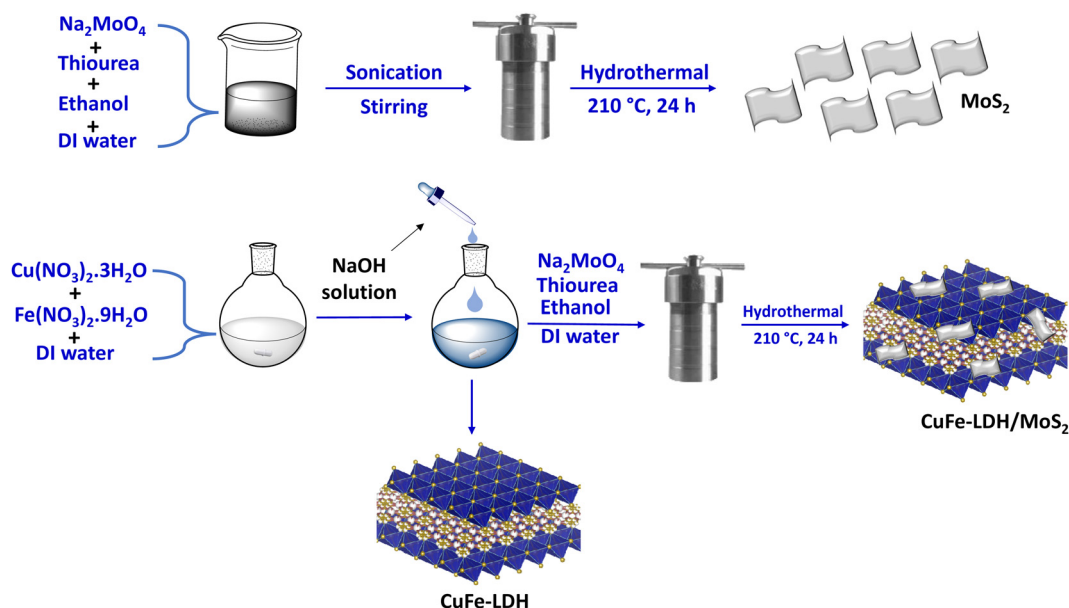

Scheme 1 Synthetic procedure of MoS₂, CuFe-LDH, and the CuFe-LDH/MoS₂ nanocomposite.



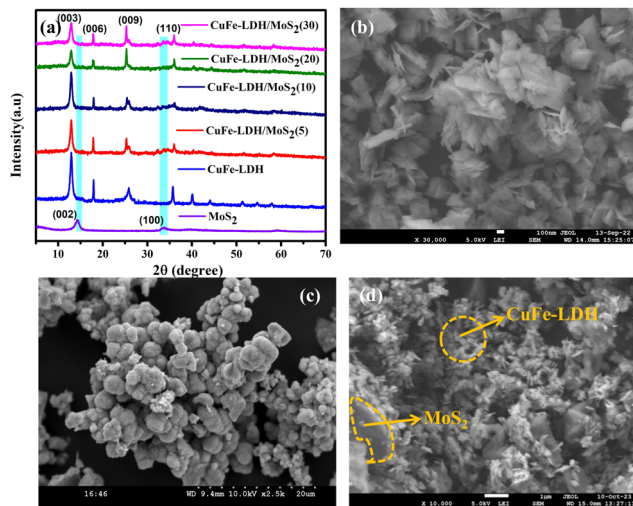


Fig. 1 (a) PXRD spectra, and FESEM images of (b) CuFe-LDH, (c) MoS₂, and (d) CuFe-LDH/MoS₂.

hydratalcrite-like structure were discernible in the XRD pattern of CuFe-LDH.³⁸ Specifically, the peaks observed at 2θ values of 13.1° , 23.7° , 34.2° , and 59.8° corresponded to the (003), (006), (009), and (110) planes of CuFe LDH, respectively (Fig. 1(a)). In the XRD patterns of MoS₂ and CuFe-LDH/MoS₂, three distinct diffraction peaks at 14.41° and 32.71° were associated with the (002), and (100) crystallographic planes of MoS₂, respectively.³⁹ The XRD patterns of the CuFe-LDH/MoS₂(x), which were fabricated with different levels of MoS₂ loading ($x = 5, 10, 20, 30$), are presented in Fig. 1(a). These profiles exhibited concurrent diffraction peaks attributable to both MoS₂ and CuFe-LDH, affirming that the introduction of MoS₂ did not perturb the chemical composition of CuFe-LDH throughout the synthesis of CuFe-LDH/MoS₂. This observation is consistent with the relatively trace amount of MoS₂ nanosheets in the composite, as shown in Fig. S1 (ESI[†]).³⁹ It's noteworthy that the diffraction peaks attributed to CuFe-LDH maintained their clarity in the composite photocatalysts, affirming that the initial introduction of MoS₂ did not interfere with the crystalline structure of MoS₂.

Fig. 1(b)–(d) presents typical field emission scanning electron microscopy (FESEM) images of CuFe-LDH, MoS₂, and CuFe-LDH/MoS₂(20). In Fig. 1(b), it is evident that the unmodified CuFe-LDHs exhibit a flaky nanosheet morphology, which is a characteristic feature of exfoliated LDH materials, as previously observed.⁴⁰ Fig. 1(c) illustrates the sheet-like morphology of MoS₂. The morphology depicted in Fig. 1(d) for CuFe-LDH/MoS₂(20) reveals the successful growth of hexagonal, flaky MoS₂ nanosheets on the CuFe-LDH sheets, in accordance with prior research findings.³⁹ These results indicate that CuFe-LDH effectively impedes the aggregation of MoS₂ nanoplatelets within CuFe-LDH/MoS₂(20), and conversely, electrostatic interactions between LDH and MoS₂ preserve their original nanosheet morphologies in CuFe-LDH/MoS₂(20) (Fig. 1(d)). In Fig. S3(a) and (b) (ESI[†]), the nitrogen (N₂) adsorption and desorption curves for the examined samples are presented.

Evidently, the CuFe-LDH/MoS₂(20) composite exhibits a characteristic type IV isotherm, accompanied by a specific surface area of $125.4 \text{ m}^2 \text{ g}^{-1}$ and a pore diameter of 11.19 nm, falling within the conventional mesoporous size range. Subsequently, upon comparative analysis of the respective images, it becomes apparent that CuFe-LDH/MoS₂(20) outperforms CuFe-LDH and MoS₂ in both specific surface area and pore diameter. This observation signifies the utilization of two-dimensional materials in augmenting the specific surface area of the composite catalyst and promoting the rate of H₂ evolution during the reaction.

The microstructural characteristics, chemical composition, and crystallographic features of the prepared MoS₂, CuFe-LDH, and CuFe-LDH/MoS₂(20) materials were further elucidated through transmission electron microscopy (TEM) and high-resolution TEM (HR-TEM) analyses, as depicted in Fig. 2. In Fig. 2(a), CuFe-LDH appeared as an aggregation of hexagonal nanosheets, with an average diameter ranging from 20 to 30 nm. The HR-TEM image of CuFe-LDH shown as an inset in Fig. S2(c) (ESI[†]) revealed distinct lattice fringes, signifying a clearly defined crystal structure. The lattice spacing was measured at 0.25 nanometers, corresponding to the (012) plane of hexagonal CuFe-LDH nanosheets, as reported previously.⁴⁰ The synthesized MoS₂ nanosheets exhibited interconnectivity, and formation of a self-organized assembly of exfoliated nanosheets with only a few layers, as illustrated in Fig. S2(a) (ESI[†]). The HR-TEM image displayed interlayer lattice fringes with a lattice spacing measuring 0.22 nm, corresponding to the (103) crystallographic orientations of MoS₂, as presented in Fig. S2(b) (ESI[†]).³⁹ In contrast to the LDHs, significant alterations in the morphological characteristics of CuFe-LDH/MoS₂(20) were observed, as depicted in Fig. 2(c) and (d). Notably, LDHs were effectively coated by MoS₂. Fig. 2(c) and (d) present TEM images of the heterostructured CuFe-LDH/MoS₂(20) nanocomposite, demonstrating uniform morphology across the heterostructure nanocomposites. Fig. 2(d) highlights the self-assembly of MoS₂ and CuFe-LDH nanosheets, leading to the creation of a structure with precise alignment in the opposing growth orientation of CuFe-LDH and MoS₂, resulting in heterointerfaces. Moreover, the HR-TEM image depicted in Fig. 2(c), which revealed interplanar lattice spacings of 0.22 nm and 0.25 nm, was associated with the (103) and (012) interplanar planes of a few-layered MoS₂ and CuFe-LDH, respectively. The presence of heterogeneous nanojunctions within the CuFe-LDH/MoS₂(20) nanocomposite was distinctly evident in the HR-TEM image. This image clearly depicted the development of lattice fringes in opposing directions and distinct barriers between MoS₂ and CuFe-LDH layers. This observation suggests that few-layer MoS₂, characterized by an interlayer spacing of 0.22 nm, establishes close contact with CuFe-LDH facilitating the formation of nanoscale interfaces, enabling efficiency for the separation and transfer of photoexcited exciton pairs, thereby enhancing catalytic performance. The elemental distribution of each metal constituent within the electrostatic heterostructure CuFe-LDH/MoS₂(20) nanocomposite was quantitatively assessed through EDX spectroscopy measurements (Fig. 2(d)–(i)). All elements,



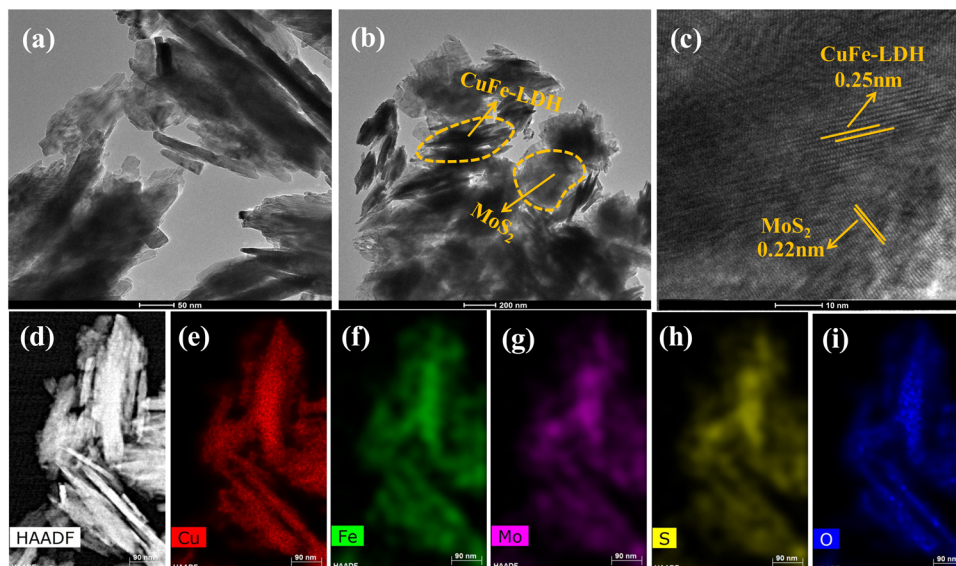


Fig. 2 TEM images of (a) CuFe-LDH, (b) CuFe-LDH/MoS₂(20), (c) HR-TEM image of CuFe-LDH/MoS₂(20) and (d)–(i) HAADF-STEM and elemental analysis of CuFe-LDH/MoS₂(20).

including Mo, S, Cu, Fe, S, and O, exhibited high-intensity signals, indicating a uniform distribution of each element throughout the few-layered CuFe-LDH/MoS₂(20) nanocomposite. During the growth process, the well-dispersed CuFe-LDH nanosheets offered active surfaces for the nucleation and expansion of MoS₂, playing a pivotal role in shaping the hierarchical structural arrangement. The development of heterostructures featuring edge-bound, thinly-layered MoS₂ and CuFe-LDH nanosheets resulted in enhanced chemical and physical characteristics, particularly in terms of photocatalytic

performance. The existence of additional basal edge sites, which contain unsaturated sulfur ions, efficiently constrained H⁺ ions within the close interface between MoS₂ and CuFe-LDH nanosheets, thereby enhancing exceptional redox reaction capabilities.⁴¹

Assessing catalyst performance and its responsiveness to visible light is a crucial aspect of catalytic studies. To investigate their light absorption capabilities, we conducted UV-visible diffuse reflectance spectroscopy (UV-vis DRS) on CuFe-LDH, MoS₂, and CuFe-LDH/MoS₂(20). As illustrated in Fig. 3(a), CuFe-LDH

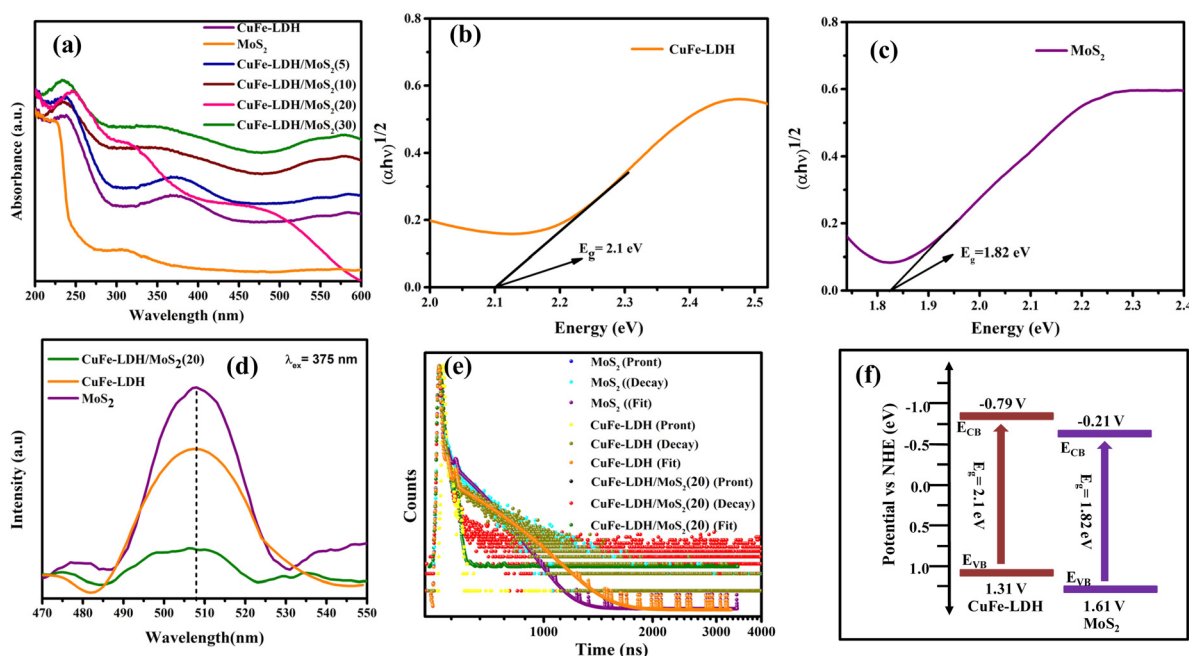


Fig. 3 (a) UV-vis DR spectral graph of the prepared samples and band gap energy values estimated through the Tauc plot of (b) CuFe-LDH, (c) MoS₂, (d) PL spectra, (e) TCSPS analysis of the MoS₂, CuFe-LDH, and CuFe-LDH/MoS₂(20) composites and (f) obtained band gap patterns of the materials.



exhibited three absorption bands within the visible light range. The absorption band in the 200–300 nm range can be attributed to ligand-to-metal charge transfer (from O 2p orbit to Cu 3d_{2g}), while the dual-band in the 300–500 nm range is associated with the octahedral structure (d–d transition of Cu²⁺), both characteristic of visible light absorption.⁴¹ Both MoS₂ and CuFe-LDH/MoS₂(-x) exhibited comprehensive light absorption throughout the visible light spectrum, a characteristic attributed to the utilization of black MoS₂ in the preparation process and the substantial proportion of MoS₂ content within the composite catalyst. The band gap energies of CuFe-LDH, MoS₂, and CuFe-LDH/MoS₂ were calculated from the corresponding Kubelka-Munk function and Tauc plot as follows (eqn (1)).⁴¹

$$(\alpha h\nu)^{1/n} = A(h\nu - E) \quad (1)$$

where “a” represents the absorption coefficient and “hν” is the photon energy. The band gap values for CuFe-LDH and MoS₂ are 2.1 eV and 1.82 eV, respectively (Fig. 3(b) and (c)).³⁹ As demonstrated in Fig. 3, the calculated optical band gap energy, “E_g” for CuFe-LDH was consistent with our previous findings, at approximately 2.1 eV. Additionally, the optical band gap of MoS₂ was established to be approximately 1.82 eV, following the direct band gap model. This result suggests that the MoS₂ heterostructure grown on CuFe-LDH more closely resembles MoS₂ thin layers. This finding aligns with TEM observations of the synthesized materials.

The intensity of the photoluminescence spectrum (PL) peaks serves as an indicator of the recombination rate of photogenerated electrons and holes within different catalysts. Notably, when subjected to excitation at a 375 nm wavelength, the samples exhibited maximum emission peaks at around 507 nm, as illustrated in Fig. 3(d). Furthermore, it was noted that the fluorescence intensity of the CuFe-LDH/MoS₂(20) composite was less pronounced in comparison to the pristine CuFe-LDH and MoS₂.⁴² This reduction can be attributed to the efficient separation and transfer of a significant number of electrons and holes within CuFe-LDH/MoS₂(20). Consequently, fewer opportunities for recombination arise, resulting in weaker fluorescence in CuFe-LDH/MoS₂(20). This phenomenon, in turn, facilitates photocatalytic reactions. The electron lifetimes of the photogenerated electrons were determined by analyzing time-resolved photoluminescence (TRPL) spectra, utilizing an excitation wavelength above 385 nm, which resulted in a pronounced emission peak at 578 nm. Additionally, photon count data were extracted from the TRPL spectra. For all photocatalysts examined, two distinct electron lifetimes were observed, with shorter and longer durations associated with surface emissions linked to defect generation and internal electron transfer, respectively. The average lifetimes for CuFe-LDH, MoS₂, and CuFe-LDH/MoS₂(20) were measured at 0.54 ns, 0.61 ns and 0.42 ns, as depicted in Fig. 3(e). These findings indicate that the diminished lifetime of the heterojunction photocatalyst is mainly attributed to non-radiative photo-decay, representing a pathway for electron transfer from the conduction band of MoS₂ to the valence band of LDH, effectively inhibiting the recombination of electron-hole pairs.

The arrangement of the heterojunction interface can impede exciton pair recombination and accelerate surface chemical reactions. The evaluation of junction properties is facilitated through the examination of the alignment of energy bands and energy states at the interface. To investigate these aspects, we employed high-resolution X-ray photoelectron spectroscopy (XPS) to examine the energy states of constituent elements within the CuFe-LDH/MoS₂ heterojunction interfaces. The XPS analysis revealed detectable signals corresponding to elements Mo, S, Cu, Fe, C, and O in a wide XPS spectrum, thus confirming the formation of heterostructure nanocomposites CuFe-LDH, MoS₂, and CuFe-LDH/MoS₂ (Fig. 4(a)). Furthermore, the transfer of electrons from the MoS₂ to the CuFe-LDH within the CuFe-LDH/MoS₂ system, facilitated through S-scheme charge transfer, was substantiated by XPS analysis of pristine MoS₂ and CuFe-LDH. In the pristine CuFe-LDH, the Cu 2p_{3/2} and Cu 2p_{1/2} spectrum (Fig. 4(b)) exhibited peaks at 931.2 and 951.0 eV corresponding to the primary Cu²⁺ state, along with two prominent shake-up satellite peaks observed at 940.2 and 960.5 eV, respectively.^{43,44} Additionally, the Cu 2p spectrum of CuFe-LDH/MoS₂ was subjected to peak-fitting analysis to elucidate the nature of the Cu phase and its interaction with MoS₂ (Fig. 4(b)). Following the formation of a heterostructure between CuFe-LDH and MoS₂, the Cu 2p peaks associated with CuFe-LDH/MoS₂ exhibited a noticeable blue shift towards higher binding energy (BE), with an energy shift of approximately 0.2 eV. The deconstructed Cu 2p XPS spectrum of CuFe-LDH/MoS₂ provided further validation of the presence of Cu²⁺ in the system. In Fig. 4(b), two pairs of spin-orbit peaks, observed at BEs of 931.4 and 951.2 eV, corresponded to Cu 2p_{3/2} and Cu 2p_{1/2}, respectively, and were accompanied by two satellite peaks at 940.2 and 960.7 eV. In the unmodified CuFe-LDH (Fig. 4(c)), distinctive peaks at 712.9 and 725.9 eV indicated the existence of Fe³⁺ species. In contrast, CuFe-LDH/MoS₂ displayed a 0.2 eV shift to higher energies in the Fe 2p peaks, with two primary peaks observed at 713.3 and 726.1 eV, corresponding to Fe 2p_{3/2} and Fe 2p_{1/2}, respectively.⁴⁵ The broader Fe 2p peaks observed in CuFe-LDH/MoS₂, as compared to pure CuFe-LDH, suggest a change in the chemical environment of iron, likely induced by interactions with MoS₂. This alteration is evident in the shifted peaks following the introduction of Fe into the CuFe-LDH matrix (formation of CuFe-LDH/MoS₂). The introduction of Fe significantly influences the chemical environment of CuFe-LDH/MoS₂, it is crucial to determine the valence state of the Fe species, as it could play a vital role in catalytic activity.⁴⁶ This observation suggests that Cu and Fe are present in the Cu²⁺ and Fe³⁺ oxidation states within the CuFe-LDH/MoS₂ nanocomposites, respectively. Furthermore, the appearance of a satellite peak and a higher BE shift in the Cu 2p primary line signifies the existence of octahedral geometry, specifically the [CuO₆] entities in CuFe-LDH/MoS₂. In the comparison of the decomposed O 1s spectrum of pure CuFe-LDH with that of CuFe-LDH/MoS₂, as demonstrated for pristine CuFe-LDH in Fig. 4(f), the high-resolution O 1s spectrum disclosed two XPS peaks at 530.6 eV (O I) and 530.2 eV (O II), attributing them to lattice



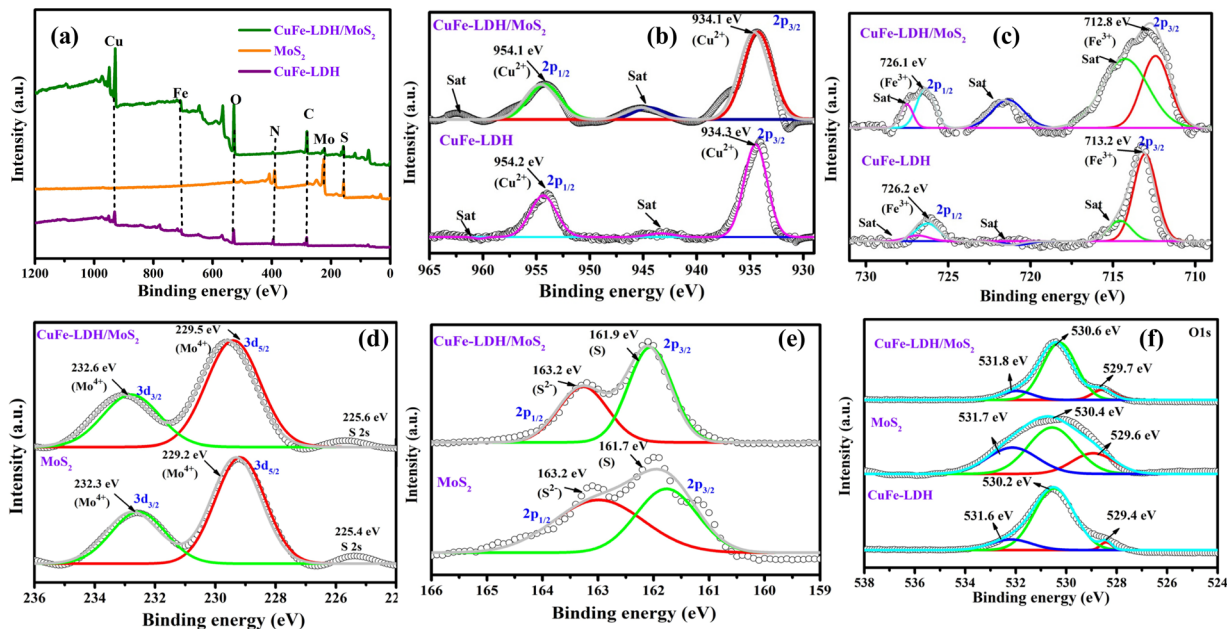


Fig. 4 The XPS spectra of CuFe-LDH, MoS₂, and CuFe-LDH/MoS₂: (a) survey spectra, (b) Cu 2p, (c) Fe 2p, (d) Mo 3d, (e) S 2p and (f) O 1s.

oxygen and surface hydroxyl groups bonded to metal centers. The spectra consisting of O 1s of MoS₂/CuFe-LDH (Fig. 4(f)) disclose three different peaks ascribed to the lattice oxygen of metal center-O_I (529.6 eV), surface hydroxyl groups of metal center-O_{II} (530.8 eV), and oxygen vacancies in lattice absorbed water O_{III} (531.3 eV).⁴¹ This is substantiated by the results of the XPS analysis of Mo 3d presented above.³⁷ These results reveal the p–n heterojunction impact of CuFe-LDH with MoS₂, and the effect was observed by the shifting of the O 1s peaks of the MoS₂/CuFe-LDH composite photocatalyst toward higher BE.

In Fig. 4(d), we offer a comparative analysis of the resolved Mo 3d spectrum, contrasting pure MoS₂ with the Mo component within CuFe-LDH/MoS₂. Within the Mo XPS peaks of unaltered MoS₂, we discerned a division into three peaks, with the two principal peaks situated at 232.6 eV (3d_{3/2}) and 229.5 eV (3d_{5/2}), signifying the Mo⁴⁺ oxidation state. Additionally, peaks at 232.3 and 229.2 eV were evident, indicating the presence of the Mo⁴⁺ oxidation state and the S 2s state. Furthermore, we scrutinized the high-resolution S 2p spectra of pure MoS₂ (Fig. 4(e)), which could be decomposed into two doublet peaks at 161.7 and 163.2 eV, corresponding to the 2p_{3/2} and 2p_{1/2} spin states of S 2p, confirming the S²⁻ oxidation state. Likewise, the high-resolution S 2p spectra of CuFe-LDH/MoS₂ displayed two doublet peaks at 161.9 and 163.2 eV, attributed to the 2p_{3/2} and 2p_{1/2} spin states of S 2p, validating the S²⁻ oxidation state. Fig. S4(a) and (b) (ESI[†]), which depicts the C1s and N1s spectra, provides compelling evidence for the establishment of a heterojunction between CuFe-LDH and MoS₂. These spectra distinctly reveal the presence of C–C and C–N moieties within the structural composition of this heterojunction.⁴¹

The XPS spectral findings presented above reveal notable shifts in the BE positions in both neat MoS₂ and CuFe-LDH upon the establishment of an S-scheme charge transfer

mechanism in CuFe-LDH/MoS₂. Specifically, MoS₂ experiences a blue shift in BE location, concurrent with a red shift observed in the BE location of CuFe-LDH. These shifts are accredited to the transference of electrons from CuFe-LDH to MoS₂, followed by the recombination of the gathered electrons from MoS₂ with the h⁺ within LDH. Consequently, this process leads to an enrichment of the e⁻ density within MoS₂ in the nanocomposite, resulting in fewer BEs for Mo and S, respectively. Simultaneously, the diminished e⁻ density within LDH in CuFe-LDH/MoS₂ induces an upward shift in the BE positions of Cu, Fe, and O. This reordering of the chemical environment delivers a compelling indication for the presence of a charge-transference-induced electric field and a vigorous electronic interface between LDH and MoS₂, facilitated by the creation of an S-scheme mode of charge pair departure. Consequently, the departure of photoinduced exciton pairs becomes more facile at advanced reduction and oxidation potentials, ultimately enhancing the photocatalytic performance.^{39–41} Moreover, following the hybridization of MoS₂ with CuFe-LDH, there is a notable increase in the proportion of active sulfur sites, as evidenced by Fig. 4. This observation aligns with the loading of MoS₂ onto CuFe-LDH nanosheets, further supporting the augmentation of sulfur active sites.

The photocatalytic generation of H₂ was evaluated in MoS₂, CuFe-LDH, and CuFe-LDH/MoS₂(-x) by exposing them to aqueous Na₂S and Na₂SO₃ solution (50 mL) under direct visible light ($\lambda \geq 400$ nm), as represented in Fig. 5(a). In the absence of a catalyst or light, no H₂ evolution was observed, underscoring the dependence of photocatalytic H₂ creation on the synergistic influence of both the catalyst and light.^{47–49} CuFe-LDH and MoS₂ exhibited H₂ formation rates of 1.3 and 0.6 mmol g⁻¹ h⁻¹, respectively. Notably, CuFe-LDH/MoS₂(-x), operating through the S-scheme charge-carrier-transference mechanism amid



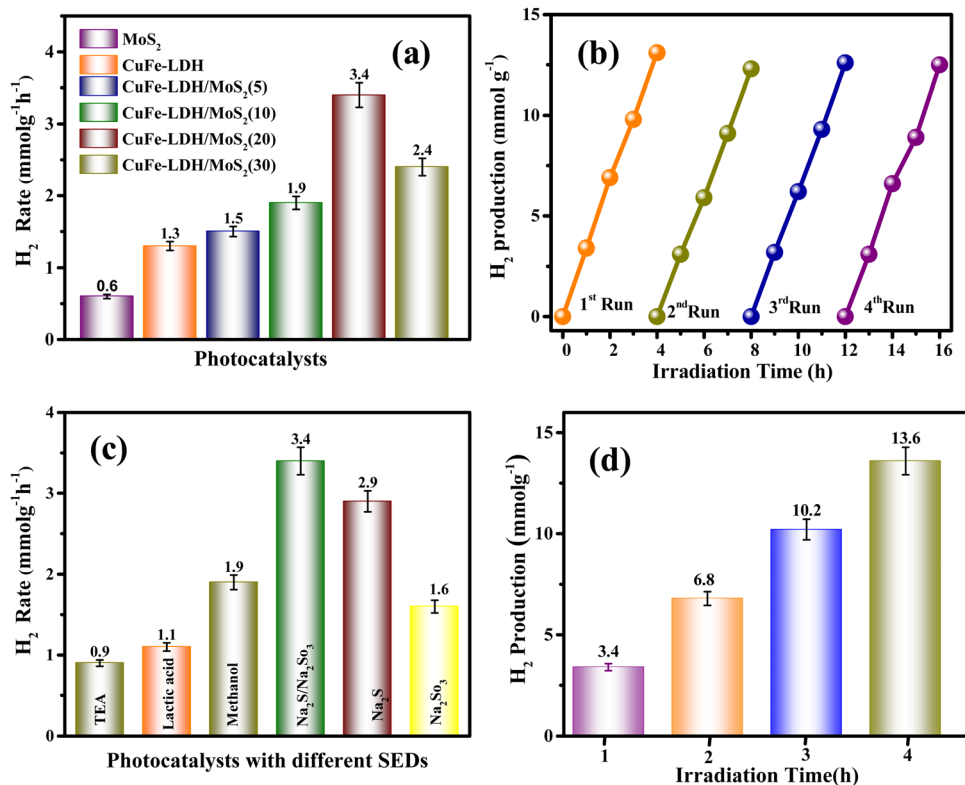


Fig. 5 (a) Histogram showing various photocatalysts' varying rates of H₂ creation, (b) reclaimable nature of CuFe-LDH/MoS₂(20), (c) various sacrificial agents employed to measure the H₂ creation rate for the CuFe-LDH/MoS₂(20) semiconductor and (d) time on stream of hydrogen yield up to 4 hours of CuFe-LDH/MoS₂(20).

CuFe-LDH and MoS₂, exhibited significantly enhanced H₂ formation performance compared to the individual CuFe-LDH and MoS₂.⁵⁰ As the weight percentage (wt%) of MoS₂ varied from 5 to 30 in CuFe-LDH/MoS₂(*x*), the H₂ formation rate increased from 1.5 mmol g⁻¹ h⁻¹ (CuFe-LDH/MoS₂(5)) to 1.9 mmol g⁻¹ h⁻¹ (CuFe-LDH/MoS₂(10)) and further to 3.4 mmol g⁻¹ h⁻¹ (CuFe-LDH/MoS₂(20)), before decreasing to 2.4 mmol g⁻¹ h⁻¹ (CuFe-LDH/MoS₂(30)), functioning optimally when exposed to visible light, indicating its high charge mobility (Table S1, ESI[†]). In contrast, single MoS₂ displayed negligible photocatalytic H₂ creation, likely due to inefficient charge separation or poor transport of charge transporters to the H₂ creation active sites. The observed enhancements in photocatalytic performance can be attributed to several factors within CuFe-LDH/MoS₂(20), including the quantum confinement effects, increased exposure of active edges, and light scattering phenomena resulting from the nanolayered MoS₂. These factors are thermodynamically favorable for promoting the H₂ creation reaction. However, excessive filling of MoS₂ led to a decline in photocatalytic performance. This decline can be attributed to MoS₂ acting as a shield within CuFe-LDH/MoS₂(20), which hinders the absorption of photons. The overall improvement in photocatalytic actions is primarily ascribed to the establishment of an S-scheme charge flow, achieved through the filling of MoS₂ onto CuFe-LDH, as exemplified in the CuFe-LDH/MoS₂(20) heterostructure.

Single MoS₂ exhibits a negligible amount of photocatalytic H₂ production either because of inefficient charge separation or because of the reduced transportation of the charge carriers to the hydrogen evolution active edges. The incremental photocatalytic performances are due to the increase in exposed active edges, quantum confinement, or light scattering effect of nanolayered MoS₂ in CuFe-LDH/MoS₂, which is thermodynamically feasible for the hydrogen evolution reaction. However, extra loading of MoS₂ resulted in the reduction of photocatalytic performance, which is owing to the shielding because of MoS₂ in CuFe-LDH/MoS₂ that creates hindrance for photon absorption.⁴¹ The augmentation in photocatalytic activities is attributed to the heterojunctions with the S-scheme charge existence of flow obtained due to the incorporation of MoS₂ on CuFe-LDH as in the CuFe-LDH/MoS₂ heterostructure.

The investigation of material recyclability is of paramount importance, considering the common occurrence of reduced catalytic effectiveness upon repeated utilization in a hydrated medium under exposure to normal sunshine or visible light. To assess the long-term photocatalytic constancy and recyclability of a semiconductor, we subjected the CuFe-LDH/MoS₂(20) heterostructure to four successive cycles of catalytic reactions for H₂ production. Additionally, Fig. 5(b) illustrates the results of catalytic recyclability tests for H₂ evolution, conducted over four distinct cycles. Notably, Fig. 5(b) highlights a consistent rate of H₂ recyclability throughout the repeated fourth cycle, indicating



the high stability of the CuFe-LDH/MoS₂(20) material in its photocatalytic H₂ evolution activity. This robust performance underscores the material's chemical stability and suitability for clean reusability in the process of photocatalytic H₂ formation. As revealed by the powder XRD, it (after the HER) shows weak peak intensity but no significant local structural change in the CuFe-LDH/MoS₂(20) catalyst was observed; this could be attributed to the presence of Na in the sample, as Na₂S and Na₂SO₃ are used as SEDs. The decrease in intensity may be related to the occupation of oxygen vacancies by Na ions. XPS results⁴⁹ are consistent with the XRD findings. As revealed by XPS, it shows nearly the same peaks before and after activity. The additional elemental peak of Na is observed at 1073 eV in the XPS result after activity, as shown in Fig. S5 (ESI[†]). This data highlights the long-term stability of the catalyst under experimental conditions. To provide a comprehensive overview of the catalytic performance, we present a comparative table (Table S2, ESI[†]) that juxtaposes the performance of CuFe-LDH/MoS₂(20) with materials discussed in the existing literature. Fig. 5(c) illustrates the performance of CuFe-LDH/MoS₂(20) concerning H₂ production efficiency when employing various sacrificial agents. The hydrogen evolution efficiencies for CuFe-LDH/MoS₂(20)/TEA, CuFe-LDH/MoS₂(20)/methanol, CuFe-LDH/MoS₂(20)/lactic acid, CuFe-LDH/MoS₂(20)/Na₂S/Na₂SO₃, CuFe-LDH/MoS₂(20)/Na₂S, and CuFe-LDH/MoS₂(20)/Na₂SO₃ were found to be 0.9 mmol g⁻¹ h⁻¹, 1.9 mmol g⁻¹ h⁻¹, 1.1 mmol g⁻¹ h⁻¹, 3.4 mmol g⁻¹ h⁻¹, 2.9 mmol g⁻¹ h⁻¹, and 1.6 mmol g⁻¹ h⁻¹, respectively. The maximum effective combination for H₂ creation was CuFe-LDH/MoS₂(20) in conjunction with Na₂S/Na₂SO₃ is 3.4 mmol g⁻¹ h⁻¹. This outcome is thinkable attributable to the enhanced charge transfer reactions within this system and a reduction

in electron-hole recombination. The efficiency of the evolution of H₂ was conducted over a time of four hours in Fig. 5(d).

To investigate interfacial transference and departure of photon-generated charge transporters within the photocatalysts, we conducted PEC property tests on MoS₂, CuFe-LDH, and CuFe-LDH/MoS₂(20). The curves for the transient photocurrent density of the composites are presented in Fig. 6(a). Under irregular light irradiation, the photocurrent responses of all catalysts exhibited variations, reflecting the inherent characteristics of each semiconductor catalyst. Subsequently, because of hole accumulation, the photocurrent density of the composites steadily declined. The comparatively lower photocurrent density observed for MoS₂ and CuFe-LDH can be accredited to the pronounced recombination of e⁻ and h⁺. In contrast, CuFe-LDH/MoS₂(20) exhibited the highest photocurrent response compared to MoS₂ and CuFe-LDH, indicating that the joining of CuFe-LDH significantly enhances the departure of photogenerated transporters on MoS₂. Obviously, the transient photocurrent of the MoS₂/CuFe-LDH composite was significantly enhanced. This was because the MoS₂/CuFe-LDH composite formed a direct S-scheme heterojunction, which resulted in the CB electrons of MoS₂ that transferred to the CuFe-LDH VB recombining with the holes under visible light and realizing the effective separation of the photogenerated electrons and holes. In general, during the photogenerated electron transfer process, the impedance is inversely proportional to the transient photocurrent.⁴⁰ This was beneficial to improve the photocatalytic H₂ evolution activity. This enhanced separation of photogenerated charges, along with the effective suppression of electron-hole recombination, can be attributed to the type-II and S-scheme heterojunction architecture.

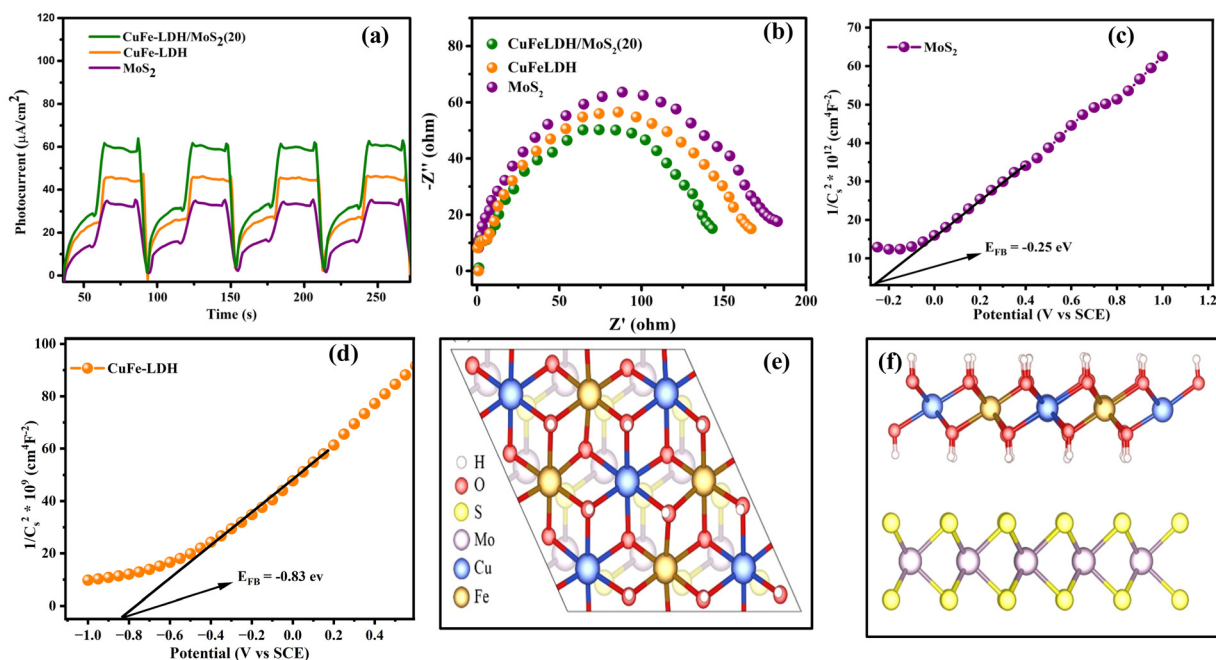


Fig. 6 (a) Response of transient photocurrent, (b) electrochemical impedance spectra of MoS₂, CuFe-LDH, and CuFe-LDH/MoS₂(20), (c), (d) Mott-Schottky plots of MoS₂ and CuFe-LDH, (e) top view and (f) side view of the CuFe-LDH/MoS₂ heterostructure.



CuFe-LDH/MoS₂(20) thus demonstrates excellent photocatalytic H₂ creation activity.

The area of arcs observed in electrochemical impedance spectroscopy (EIS) plots can serve as a valuable metric for investigating the charge transference resistance occurring amid the working electrode and electrolyte. In the context of open circuit potential conditions, the Nyquist plots for our composites are depicted in Fig. 6(b). Notably, due to its limited electric conduction, CuFe-LDH exhibits a bigger arc area in the Nyquist plot. Conversely, CuFe-LDH/MoS₂(20) displays a smaller circular arc area, indicative of its enhanced charge transference rate and superior electrical conductivity.⁵¹ This improved charge transference rate actively contributes to the acceleration of the photocatalytic reaction rate.

The assessment of CB positions in semiconductor materials is achieved using Mott–Schottky analysis. Both CuFe-LDH and MoS₂ display characteristics consistent with n-type semiconductors, as shown in Fig. 6(c) and (d). In contrast, the flat band potentials for CuFe-LDH and MoS₂ are measured at −0.25 and −0.83 V, respectively, relative to the standard calomel electrode (SCE).⁴⁶ The flat band potential (V_{fb}) of CuFe-LDH and MoS₂ is calculated following the (eqn (2)).³⁸

$$\frac{1}{c^2} = \left[\frac{2}{q\epsilon_0\epsilon N_d} \right] \left[V_{app} - V_{fb} - \frac{kT}{q} \right] \quad (2)$$

Typically, in the n-type semiconductors, the CB energy level (E_{CB}) is positioned approximately −0.1 to −0.2 V more negative compared to the flat band potential (E_{fb}). The theoretical E_{CB} values for MoS₂ and CuFe-LDH are −0.45 and −1.03 V vs. SCE, respectively. By applying (eqn (3)), the E_{CB} for MoS₂ and CuFe-LDH can be crudely assessed as −0.21 and −0.79 V, respectively, relative to the NHE. Comparing the conduction band position of MoS₂ (−0.21 V) to that of CuFe-LDH (−0.79 V) with respect to the standard hydrogen electrode, MoS₂ displays a

relatively more positive nature.⁵⁰ As a result, the combination of CuFe-LDH and MoS₂ found an auspicious thermodynamic path for the transference of photogenerated e[−]. These findings line up with the data obtained from photoluminescence spectroscopy.

$$E_{NHE} = E_{SCE} + 0.241 \quad (3)$$

In the realm of photocatalysis employing photocatalytic materials, the route of electron transference is mainly governed by the disparity in Fermi energy levels. MoS₂ features an energy band gap (E_g) of around 1.82 eV, along with CB (E_{CB}) and VB (E_{VB}) potentials of −0.21 and 1.61, respectively. Similarly, CuFe-LDH exhibits an E_g of around 2.1 eV, with corresponding E_{CB} and E_{VB} values of −0.79 and 1.31, respectively.⁵²

To illuminate the synergistic influences arising from the MoS₂/CuFe-LDH interface on catalytic H₂ creation, the significant reaction stages on the MoS₂ and CuFe-LDH catalysts as well as on the MoS₂/CuFe-LDH interface are investigated using DFT calculations. Theoretical frameworks for MoS₂ and CuFe-LDH were constructed, aiming to investigate the Gibbs energy in the MoS₂/CuFe LDH heterostructure, with their representations illustrated in Fig. 6(e) and (f). Fig. 7(a) provides a representation of the HER kinetics, incorporating both the initial H₂O splitting process *via* a transition state and the succeeding chemisorption of intermediates (H and OH). The splitting of H₂O into adsorbed H and OH on MoS₂ demands an input of approximately 0.52 eV, rendering it energetically endothermic and encountering a high energy barrier of 1.21 eV, making pure MoS₂ thermodynamically unfavorable for this process. In contrast to MoS₂, the water dissociation energy barrier decreases to 0.74 eV for CuFe-LDH and 0.45 for the MoS₂/CuFe-LDH interface, as shown in Fig. 7(b). This reduction accelerates the sluggish Volmer step and subsidiary energy barrier for OH–H bond breakage, ultimately facilitating water

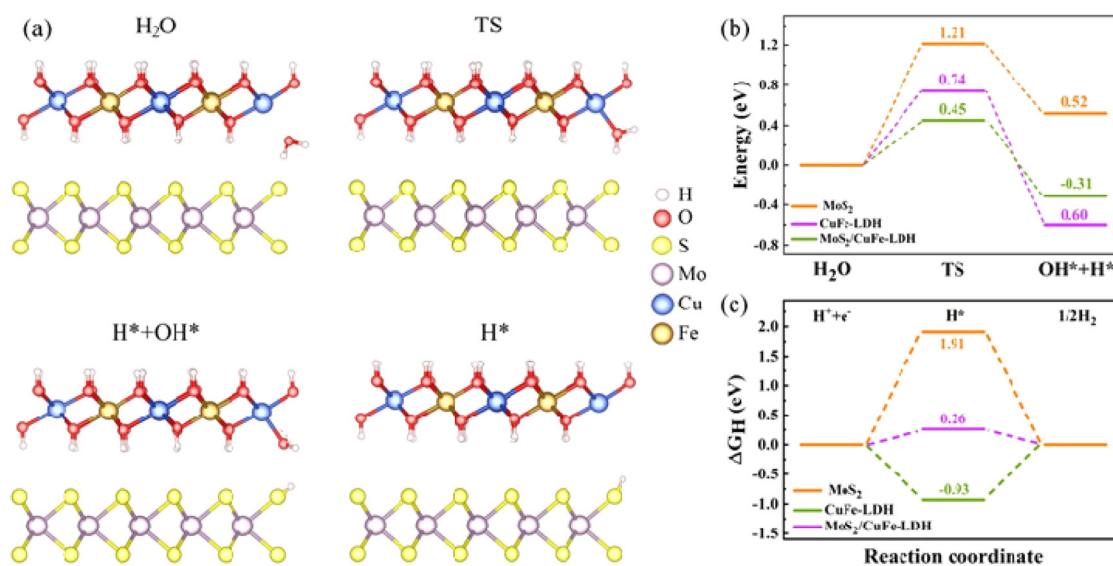


Fig. 7 (a) Optimized structural configurations of the water dissociation process on the CuFe-LDH/MoS₂ heterostructure, (b) computed reaction energy diagram of H₂O splitting on MoS₂, CuFe-LDH and the CuFe-LDH/MoS₂ complex, and (c) the associated free energy diagram of hydrogen evolution.



dissociation. Consequently, the hybridization of MoS₂ with CuFe-LDH effectively enhances both the thermodynamics and kinetics of the rate-determining step for the H₂ evolution reaction (HER), aligning with our experimental findings. In addition to the energy barrier associated with the initial H₂O dissociation, the Gibbs free energy (ΔG_H) of adsorbed hydrogen holds significant importance. Fig. 7(c) illustrates the ΔG_H amid the adsorbed *H atom and gassy H₂. It is evident that both MoS₂ (1.91 eV) and CuFe-LDH (-0.93 eV) exhibit large ΔG_H values, suggesting an unfavorable condition for the release of H₂ molecules. Meanwhile, CuFe-LDH/MoS₂ shows a smaller ΔG_H of 0.26 eV, approximate to the ideal 0 eV, indicating a balanced adsorption strength of H on the surface neither overly strong nor weak thus favoring the H-adsorption and subsequent release of H₂ molecules.⁴⁶ Therefore, the interfacial synergistic effect within CuFe-LDH/MoS₂ leads to an auspicious energy barrier during the initial H₂O dissociation step, ultimately facilitating the H₂ creation.

Based on the findings, we were able to ascertain the CB and VB energy levels for CuFe-LDH and MoS₂, as presented in Fig. 8. These two semiconductor materials, forming heterojunctions, can be categorized as either type II heterojunctions or S-scheme heterojunctions.^{39,51} For the hypothetical scenario of a type II heterojunction, photogenerated e⁻ and h⁺ would migrate to the places corresponding to CuFe-LDH and the VB and CB of MoS₂, respectively. However, it's worth noting that the CB energy level of MoS₂, is relatively low, approximately -0.21 eV, which provides an adequate driving force for hydrogen production. But the MoS₂ single unit cell possesses a negligible amount of hydrogen generation efficiency due to the lower charge transportation efficiency. Obviously, compared with that in MoS₂, the peak position of S 2p in CuFe-LDH/MoS₂ shifted to a higher position, and the peak position of Cu 2p and Fe 2p in CuFe-LDH/MoS₂ shifted to a lower position. These observations confirm the formation of an S-scheme heterojunction, indicating favorable electron transfer from MoS₂ to CuFe-LDH.⁵³⁻⁵⁷ In this S-scheme heterojunction, when the photocatalysts are in near contact, e⁻ naturally transfers from CuFe-LDH to MoS₂ due to coulombic forces. Owing to the differing +Ve and -Ve

characteristics of the two photocatalysts, an internal electric arena forms at the interface, leading to band bending resulting from the transference and buildup of e⁻. When exposed to visible light, the e⁻ in the MoS₂ CB is associated with the h⁺ in the CuFe-LDH VB, effectively eliminating surplus e⁻ and h⁺. Consequently, the hydrogen creation process takes place at the CuFe-LDH CB, with the reaction occurring at the MoS₂ VB.

According to the foregoing findings, the MoS₂/CuFe-LDH catalyst is suitable for photocatalytic activity. The following factors contribute to the enhanced photocatalytic activity and stability: (i) UV DRS and PL studies show that MoS₂ ions in the CuFe-LDH catalyst boosted light absorption and decreased photogenerated ion recombination, respectively.^{54,58} (ii) The sheet like-structure encourages interaction between the CuFe-LDH and MoS₂ catalyst and the reaction solution, resulting in rapid charge transport during the photocatalytic process. The inclusion of CuFe-LDH to MoS₂ frames adds more active sites, which helps with photocatalysis. (iii) DFT calculations also show a decline in the band gap of MoS₂ following doping with CuFe-LDH atoms, indicating increased electron conductivity and photocatalytic activity of MoS₂/CuFe-LDH. Overall, the MoS₂/CuFe-LDH hybrid has been considered a very efficient and stable photocatalyst for hydrogen production due to the synergetic effects of highly active CuFe-LDH and the sheet-like constitution of MoS₂.^{59,60} To gain further insights into the mechanism of photocatalytic H₂ generation and the separation of photogenerated electrons and holes in these MoS₂/CuFe-LDH heterostructures, we also performed EIS, PL emission spectroscopy, and transient photocurrent measurements. In that, EIS analysis was employed to evaluate the internal resistance of the charge-transfer process of the samples.

Conclusion

The CuFe-LDH/MoS₂ composites was successfully synthesized *via* a hydrothermal method, establishing an S-scheme heterojunction by the compatible band structures and electron transfer properties of MoS₂ and CuFe-LDH. The intimate proximity



Fig. 8 Mechanism of photocatalytic H₂ creation from the CuFe-LDH/MoS₂ system.



of MoS₂ and CuFe-LDH results in efficient charge transfer and a significant enhancement of photogenerated carrier transfer rates due to the generated internal electric field. This successful coupling not only expedites photogenerated carrier separation but also minimizes electron transfer resistance, preventing charge recombination between CuFe-LDH and MoS₂, and ultimately boosting hydrogen production efficiency. In comparison to CuFe-LDH and MoS₂, the CuFe-LDH/MoS₂ composite exhibited the highest photocatalytic hydrogen production, yielding 3.4 mmol g⁻¹ h⁻¹ in 4 hours and maintaining good stability over a 16-hour cycling test. In summary, this study offers a novel understanding of the building of S-type heterojunctions in 2D/2D spatially structured photocatalysts.

Conflicts of interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Acknowledgements

This work is supported by the CSIR-IICT (MLP-0082) and DST/TMD/HFC/2k18/60, DST INSPIRE fellowship (IF 180789). CSV thanks DST and SPS CSIR for research funding and ACSIR for their PhD enrolment. We are thankful to Dr D. Srinivasa Reddy, Director, Dr A. Gangagni Rao, HOD, DEEE in CSIR-IICT for all research facilities. BMA expresses his gratitude to HPC center, IIT Kanpur for providing the computational facilities. CSIR-IICT Communication no: IICT/Pubs./2023/367.

References

- 1 Y. Wang, H. Suzuki, J. Xie, O. Tomita, D. J. Martin, M. Higashi, D. Kong, R. Abe and J. Tang, Mimicking Natural Photosynthesis: Solar to renewable H₂fuelsynthesis by Z-Scheme water splitting systems, *Chem. Rev.*, 2018, **118**, 5201–5241.
- 2 I. Mondal, A. Mahata, H. Kim, U. Pal, F. D. Angelis and J. Y. Park, A combined experimental and theoretical approach revealing a direct mechanism for bifunctional water splitting on doped copper phosphide, *Nanoscale*, 2020, **12**, 17769–17779.
- 3 S. Gonuguntla, R. Kamesh, U. Pal and D. Chatterjee, Dye sensitization of TiO₂ relevant to photocatalytic hydrogen generation, *J. Photochem. Photobiol.*, 2023, **57**, 100621.
- 4 C. S. Gopinath and N. Nalajala, A scalable and thin film approach for solar hydrogen generation: a review on enhanced photocatalytic water splitting, *J. Mater. Chem. A*, 2021, **9**, 1353–1371.
- 5 J. Wang, G. Wang, B. Cheng, J. Yu and J. Fan, Sulfur-doped g-C₃N₄/TiO₂ S-scheme heterojunction photocatalyst for Congo Red Photodegradation, *Chin. J. Catal.*, 2021, **42**, 56–68.
- 6 A. Gautam, S. Sk and U. Pal, Recent advances in solution assisted synthesis of transition metal chalcogenides for photo-electrocatalytic hydrogen evolution, *Phys. Chem. Chem. Phys.*, 2022, **24**, 20638–20673.
- 7 L. Mohapatra and K. Parida, A review on the recent progress, challenges, and perspective of layered double hydroxides as promising photocatalysts, *J. Mater. Chem. A*, 2016, **4**, 10744–10766.
- 8 M. Laipan, H. Fu, R. Zhu1, L. Sun, J. Zhu and H. He, Converting Spent Cu/Fe Layered Double Hydroxide into Cr(vi) Reductant and Porous Carbon Material, *Sci. Rep.*, 2017, **7**, 1–11.
- 9 I. Mondal and U. Pal, Synthesis of MOF templated Cu/CuO@TiO₂ nanocomposites for synergistic hydrogen production, *Phys. Chem. Chem. Phys.*, 2016, **18**, 4780–4789.
- 10 W. Jiang, X. Zong, L. An, S. Hua, X. Miao, S. Luan, Y. Wen, F. F. Tao and Z. Sun, Consciously Constructing Heterojunction or Direct Z-Scheme Photocatalysts by Regulating Electron Flow Direction, *ACS Catal.*, 2018, **8**, 2209–2217.
- 11 W. Yin, L. Bai, Y. Zhu, S. Zhong, L. Zhao, Z. Li and S. Bai, Embedding Metal in the Interface of a p–n Heterojunction with a Stack Design for Superior Z-Scheme Photocatalytic Hydrogen Evolution, *ACS Appl. Mater. Interfaces*, 2016, **8**, 23133–23142.
- 12 C. S. Vennapoosa, A. Karmakar, Y. T. Prabhu, B. M. Abraham, S. Kundu and U. Pal, Rh-doped ultrathin NiFeLDH nanosheets drive efficient photocatalytic water splitting, *Int. J. Hydrogen Energy*, 2023, **52**, 371–384.
- 13 S. Sk, R. Madhu, D. S. Gavali, V. Bhasin, R. Thapa, S. N. Jha, D. Bhattacharyya, S. Kundu and U. Pal, An ultrathin 2D NiCo-LDH nanosheet decorated NH₂-UiO-66 MOF-nanocomposite with exceptional chemical stability for electrocatalytic water splitting, *J. Mater. Chem. A*, 2023, **11**, 10309–10318.
- 14 M. He, S. Hu, C. Feng, H. Wu, H. Liu and H. Mei, Interlaced rosette-like MoS₂/Ni₃S₂/NiFe-LDH grown on nickel foam: a bifunctional electrocatalyst for hydrogen production by urea-assisted electrolysis, *Int. J. Hydrogen Energy*, 2020, **45**, 23–35.
- 15 I. Mondal, S. Gonuguntla and U. Pal, Photo induced fabrication of Cu/TiO₂ core-shell heterostructure derived from Cu-MOF for solar hydrogen generation: the size of the Cu nanoparticle matters, *J. Phys. Chem. C*, 2019, **123**, 26073–26081.
- 16 M. Gong, Y. Li, H. Wang, Y. Liang, J. Z. Wu, J. Zhou, J. Wang, T. Regier, F. Wei and H. Dai, An Advanced Ni–Fe Layered Double Hydroxide Electrocatalyst for Water Oxidation, *J. Am. Chem. Soc.*, 2013, **135**, 8452–8455.
- 17 M. Gong, Y. Li, H. Wang, Y. Liang, J. Z. Wu, J. Zhou, J. Wang, T. Regier, F. Wei and H. Dai, An Advanced Ni–Fe Layered Double Hydroxide Electrocatalyst for Water Oxidation, *J. Am. Chem. Soc.*, 2013, **135**, 8452–8455.
- 18 D. Huang, J. Ma, L. Yu, D. Wu, K. Wang, M. Yang, D. Papoulis and S. Komarneni, AgCl and BiOCl Compositd with NiFe-LDH for Enhanced Photo-Degradation of Rhodamine B, *Sep. Purif. Technol.*, 2015, **156**, 789–794.



- 19 R. Boppella, C. H. Choi, J. Moon and D. Ha Kim, Spatial charge separation on strongly coupled 2D-Hybrid of rGO/La₂Ti₂O₇/NiFe-LDH heterostructures for highly efficient noble metal free photocatalytic hydrogen generation, *Appl. Catal., B*, 2018, **239**, 178–186.
- 20 S. C. Shit, I. Mondal, P. Saikiran, L. Bai, J. Y. Park and J. Mondal, MOF-derived bifunctional iron oxide and iron phosphide nanoarchitecture photo electrode for neutral water splitting, *ChemElectroChem*, 2018, **5**, 2842–2849.
- 21 L. Liu, S. Li, Y. An, X. Sun, H. Wu, J. Li, X. Chen and H. Li, Hybridization of nan diamond and CuFe-LDH as heterogeneous photo activator for visible-light driven photo-Fenton reaction: photocatalytic activity and mechanism, *Catalysts*, 2019, **9**, 118–129.
- 22 Y. Hou, R. M. Lohe, J. Zhang, S. H. Liu, X. D. Zhuang and X. L. Feng, Vertically oriented cobalt selenide/NiFe layered-double hydroxide nanosheets supported on exfoliated graphene foil: an efficient 3D electrode for overall water splitting, *Energy Environ. Sci.*, 2016, **9**, 478–483.
- 23 X. L. Ma, X. M. Li, A. D. Jagadale, X. G. Hao, A. Abudul and G. Q. Guan, Fabrication of Cu(OH)₂@NiFe-layered double hydroxide catalyst array for electrochemical water splitting, *Int. J. Hydrogen Energy*, 2016, **41**, 14553–14561.
- 24 A. Kumaresan, S. Yang, K. Zhao, N. Ahmad, J. Zhou, Z. Zheng, Y. Zhang, Y. Gao, H. Zhou and Z. Tang, Facile development of CoAl-LDHs/RGO nanocomposites as photocatalysts for efficient hydrogen generation from water splitting under visible-light irradiation, *Inorg. Chem. Front.*, 2019, **6**, 1753–1760.
- 25 J. Zhang, Q. Zhu, L. Wang, M. Nasir, S.-H. Cho and J. Zhang, g-C₃N₄/CoAl-LDH 2D/2D hybrid heterojunction for boosting photocatalytic hydrogen evolution, *Int. J. Hydrogen Energy*, 2020, **45**, 21331–21340.
- 26 Z. Jin, X. Wang, Y. Wang, T. Yan and X. Hao, Snowflake-like Cu₂S coated with NiAl-LDH forms a p–n heterojunction for efficient photocatalytic hydrogen evolution, *ACS Appl. Energy Mater.*, 2021, **4**, 14220–14231.
- 27 I. Mondal, S. Gonuguntla and U. Pal, Photoinduced fabrication of Cu/TiO₂core–shell heterostructures derived from Cu-MOF for solar hydrogen generation: the size of the Cu nanoparticle matters, *J. Phys. Chem. C*, 2019, **123**, 26073–26081.
- 28 G. Ye, Y. Gong, J. Lin, B. Li, Y. He, S. T. Pantelides, W. Zhou, R. Vajtai and P. M. Ajayan, Defects engineered monolayer MoS₂ for improved hydrogen evolution reaction, *Nano Lett.*, 2016, **16**, 1097–1103.
- 29 G. Swain, S. Sultana, J. Moma and K. Parida, Fabrication of hierarchical two-dimensional MoS₂ nanoflower decorated upon cubic CaIn₂S₄ micro flowers: facile approach to construct novel metal-free p–n heterojunction semiconductors with superior charge separation efficiency, *Inorg. Chem.*, 2018, **57**, 10059–10071.
- 30 C. Feng, Z. Chen, J. Hou, J. Li, X. Li, L. Xu, M. Sun and R. Zeng, Effectively enhanced photocatalytic hydrogen production performance of one-pot synthesized MoS₂ clusters/CdS nanorod heterojunction material under visible light, *Chem. Eng. J.*, 2018, **345**, 404–413.
- 31 A. Tiwari, A. Gautam, S. Sk, D. S. Gavali, R. Thapa and U. Pal, Controlled loading of MoS₂ on hierarchical porous TiO₂ for enhanced photocatalytic hydrogen evolution, *J. Phys. Chem. C*, 2021, **125**(22), 11950–11962.
- 32 A. Gautam, Y. T. Prabhu and U. Pal, Efficient charge transfer on the tunable morphology of TiO₂/MoS₂ photocatalyst for an enhanced hydrogen production, *New J. Chem.*, 2021, **45**, 10257–10267.
- 33 X. Liu, B. Wang, M. Liu, S. Liu, W. Chen, L. Gao and X. Li, In situ growth of vertically aligned ultrathin MoS₂ on porous g-C₃N₄ for efficient photocatalytic hydrogen production, *Appl. Surf. Sci.*, 2021, **554**, 149617–149624.
- 34 Y. T. Prabhu, V. N. Rao, M. V. Shankar, B. Sreedhar and U. Pal, The facile hydrothermal synthesis of CuO@ZnO heterojunction nanostructures for enhanced photocatalytic hydrogen evolution, *New J. Chem.*, 2019, **43**, 6794–6805.
- 35 A. Gautam, S. Sk, A. Jamma, B. M. Abraham, M. Ahmadipourd and U. Pal, Colloidal synthesis of a heterostructured CuCo₂S₄/g-C₃N₄/In₂S₃ nanocomposite for photocatalytic hydrogen evolution, *Energy Adv.*, 2023, **2**, 1512–1520.
- 36 C. Zhao, X. Li, L. Yue, S. Yuan, X. Ren, Z. Zeng, X. Hu, Y. Wu and Y. He, One-step preparation of novel Bi–Bi₂O₃/CdWO₄ Z-scheme heterojunctions with enhanced performance in photocatalytic NH₃ synthesis, *J. Alloys Compd.*, 2023, **968**, 171956.
- 37 Y. Jiuheng, C. Sumin, L. Baojun and T. Wei, Construction of MoS₂/NiFe-Ni foam p–n heterojunction as Photoanode for tetracycline degradation and simultaneous cathodic hydrogen evolution, *J. Environ. Chem. Eng.*, 2022, **10**, 108437.
- 38 M. Laipan, H. Fu, R. Zhu1, L. Sun, J. Zhu and H. He, Converting Spent Cu/Fe Layered Double Hydroxide into Cr(vi) Reductant and Porous Carbon Material, *Sci. Rep.*, 2017, **7**, 1–11.
- 39 X. Liu, J. Xu, L. Ma, Y. Liu and L. Hua, Nano-flower S-scheme heterojunction NiAl-LDH/MoS₂ for enhancing photocatalytic hydrogen production, *New J. Chem.*, 2022, **46**, 228–238.
- 40 Y. Sun, X. Wang, Q. Fu and C. Pan, Construction of Direct Z-Scheme Heterojunction NiFe-Layered Double Hydroxide (LDH)/Zn_{0.5}Cd_{0.5}S for Photocatalytic H₂ Evolution, *ACS Appl. Mater. Interfaces*, 2021, **13**, 39331–39340.
- 41 S. Nayak, G. Swain and K. Parida, Enhanced Photocatalytic Activities of RhB Degradation and H₂ Evolution from in Situ Formation of the Electrostatic Heterostructure MoS₂/NiFe LDH Nanocomposite through the Z-Scheme Mechanism via p–n Heterojunctions, *ACS Appl. Mater. Interfaces*, 2019, **11**, 20923–20942.
- 42 M. Rong, F. Yang, C. Yu, S. Wang, H. Zhong and Z. Cao, MoS₂/CoAl-LDH heterostructure for enhanced efficient of oxygen evolution reaction, *Colloids Surf., A*, 2020, **607**, 125419.
- 43 J. Shen, J. Liang, X. Fu, Y. Jiang, S. Yan, H. He and X. Ren, Facile Synthesis of CuMgFe Layered Double Hydroxides for Efficient Catalytic Phenol Hydroxylation under Mild Conditions, *ChemistrySelect*, 2020, **5**, 2835–2841.



- 44 C. S. Vennapoosa, S. Varangane, B. M. Abraham, V. Perupogu, S. Bojja and U. Pal, Controlled photoinduced electron transfer from g-C₃N₄ to CuCdCe-LDH for efficient visible light hydrogen evolution reaction, *Int. J. Hydrogen Energy*, 2022, **47**, 40227–40241.
- 45 S. Nayak, L. Mohapatra and K. Parida, Visible light-driven novel g-C₃N₄/NiFe-LDH composite photocatalyst with enhanced photocatalytic activity towards water oxidation and reduction reaction, *J. Mater. Chem. A*, 2015, **3**, 18622–18635.
- 46 H. Sun, W. Zhang, J. G. Li, Z. Li, X. Ao, K. H. Xue, K. K. Ostrikov, J. Tang and C. Wang, Rh-engineered ultrathin NiFe-LDH nanosheets enable highly-efficient overall water splitting and urea electrolysis, *Appl. Catal., B*, 2021, **284**, 119740.
- 47 T. Liu, K. Yang, H. Gong and Z. Jin, Visible-light driven S-scheme Mn_{0.2}Cd_{0.8}S/CoTiO₃ heterojunction for photocatalytic hydrogen evolution, *Renewable Energy*, 2021, **173**, 389–400.
- 48 J. Tao, X. Yu, Q. Liu, G. Liu and H. Tang, Internal electric field induced S-scheme heterojunction MoS₂/CoAl LDH for enhanced photocatalytic hydrogen evolution, *J. Colloid Interface Sci.*, 2021, **585**, 470–479.
- 49 C. S. Vennapoosa, S. Gonuguntla, S. Sk, B. M. Abraham and U. Pal, Ternary Cu(OH)₂/P(C₃N₄)/MoS₂ nanostructures for photocatalytic hydrogen production, *ACS Appl. Nano Mater.*, 2022, **5**, 4848–4859.
- 50 Y. Zou, D. Maa, D. Suna, S. Mao, C. Heb, Z. Wang, X. Jia and J. W. Shi, Carbon nanosheet facilitated charge separation and transfer between molybdenum carbide and graphitic carbon nitride toward efficient photocatalytic H₂ production, *Appl. Surf. Sci.*, 2019, **473**, 91–100.
- 51 C. Zheng, K. Kang, Y. Xie, X. Yang, L. Lana, H. Song and S. Bai, Competitive adsorption and selectivity of water vapor/R134a on activated carbon for indoor air purification, *Sep. Purif. Technol.*, 2023, **317**, 123741.
- 52 Y. Zhang and Z. Jin, Boosting Photocatalytic Hydrogen Evolution Achieved by NiS_x Coupled with g-C₃N₄@ZIF-67 Heterojunction, *J. Phys. Chem. C*, 2019, **123**, 18248–18263.
- 53 S. Yuan, J. Wang, C. Zhao, L. Yue, X. Ren, Z. Zeng, X. Hu, Y. Wu and Y. He, S-scheme Bi₂O₃/CdMoO₄ hybrid with highly efficient charge separation for photocatalytic N₂ fixation and tetracycline Degradation: Fabrication, catalytic Optimization, physicochemical studies, *Sep. Purif. Technol.*, 2023, **325**, 124665.
- 54 C. S. Vennapoosa, S. Varangane, S. Gonuguntla, B. M. Abraham, M. Ahmadipour and U. Pal, S-Scheme ZIF-67/CuFe-LDH Heterojunction for High-Performance Photocatalytic H₂ Evolution and CO₂ to MeOH Production, *Inorg. Chem.*, 2023, **62**, 16451–16463.
- 55 M. Hao, D. Wei and Z. Li, Rational Design of an Efficient S-Scheme Heterojunction of CdS/Bi₂WO₆-S Nanocomposites for Photocatalytic CO₂ Reduction, *Energy Fuels*, 2022, **36**, 11524–11531.
- 56 B. Su, H. Huang, Z. Ding, M. B. J. Roeffaers, S. Wang and J. Long, S-scheme CoTiO₃/Cd_{0.51}Zn_{0.49}S₁₀ heterostructures for visible-light driven photocatalytic CO₂ reduction, *J. Mater. Sci. Technol.*, 2022, **124**, 164–170.
- 57 S. Liu, K. Wang, M. Yang and Z. Jin, Rationally Designed Mn_{0.2}Cd_{0.8}S@CoAl-LDH S-Scheme Heterojunction for Efficient Photocatalytic Hydrogen Production, *Acta Phys.-Chim. Sin.*, 2022, **38**, 2109023.
- 58 K. Bhunia, M. Chandra, S. Khilari and D. Pradhan, Bimetallic PtAu alloy nanoparticles-integrated g-C₃N₄ Hybrid as a efficient photocatalyst for water-to-hydrogen conversion, *ACS Appl. Mater. Interfaces*, 2019, **11**, 478–488.
- 59 S. Li, M. Cai, Y. Liu, C. Wang, K. Lv and X. Chen, S-Scheme photocatalyst TaON/Bi₂WO₆ nanofibers with oxygen vacancies for efficient abatement of antibiotics and Cr(vi): Intermediate eco-toxicity analysis and mechanistic insights, *Chin. J. Catal.*, 2022, **43**, 2652–2664.
- 60 Y. Yang, X. Gu, K. Gong, S. Meng, J. Lei, X. Zheng, Y. Feng and S. Chen, Revealing the charge transfer mechanism and assessing product toxicity in the 2D/1D Bi₂O₂CO₃/Bi₈(CrO₄)O₁₁ heterostructure system, *Environ. Sci.: Nano*, 2023, **10**, 1867–1882.

