


Cite this: *Mater. Adv.*, 2024,  
5, 749

## 2D/2D Z-scheme WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunctions for photocatalytic organic pollutant degradation and nitrogen fixation†

Yasi Li <sup>a</sup> and Junkai Wang\*<sup>b</sup>

Two-dimensional/two-dimensional (2D/2D) Z-scheme WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunctions were successfully prepared by facile rapid calcination, which exhibited considerable photocatalytic performance in environmental application and energy application without any cocatalyst. The synthesized 2D/2D Z-scheme WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> significantly improved the visible-light photocatalytic degradation of tetracycline hydrochloride (TC-HCl), and 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> had the best photocatalytic degradation effect. 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> could also degrade rhodamine B (RhB), methylene blue (MB) and methyl orange (MO), and RhB was almost completely degraded after 20 min irradiation. •O<sub>2</sub><sup>-</sup> was the main active species in the degradation process of 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub>. The 2D/2D Z-scheme heterostructure enhanced the photogenerated electron–hole separation and transfer ability and possessed good photocatalytic stability. The 2D/2D Z-scheme WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunction system was first used in nitrogen fixation. 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> can simultaneously achieve photocatalytic nitrogen reduction reaction (NRR) and nitrogen oxidation reaction (NOR) to produce NH<sub>4</sub><sup>+</sup> and NO<sub>3</sub><sup>-</sup>, respectively, using air as a nitrogen source. However, in the presence of a hole sacrificial agent and N<sub>2</sub> as a nitrogen source, the photocatalytic nitrogen fixation reaction of 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> was dominated by NRR. The nitrogen fixation products and their possible mechanisms were also discussed. This study confirms that the designed 2D/2D Z-scheme WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunctions have great potential in the photocatalytic degradation of different-type organic pollutants and regulable photocatalytic NRR and NOR reactions.

Received 27th October 2023,  
Accepted 4th December 2023

DOI: 10.1039/d3ma00915g

rsc.li/materials-advances

### Introduction

Environmental safety and energy resources are among the primary needs for human survival and development. Photocatalysis is regarded as one of the most hopeful methods for environment remediation and energy conversion because of its mild reaction conditions, no secondary pollution, and low energy consumption.<sup>1–4</sup> Under light irradiation, the semiconductor photocatalysts are excited to produce photogenerated carriers, which can directly or indirectly participate in the oxidation–reduction reaction.<sup>1–4</sup> Among the visible-light catalytic materials, WO<sub>3</sub> and g-C<sub>3</sub>N<sub>4</sub> photocatalytic materials have the advantages of a suitable energy band structure, good visible-light response range, and relatively simple preparation process.<sup>5–7</sup> Therefore, WO<sub>3</sub> and g-C<sub>3</sub>N<sub>4</sub> are ideal materials for constructing efficient visible-light catalysts. Furthermore, if the

two materials are integrated to construct type-II or Z-scheme heterojunctions, the electrons (e<sup>-</sup>) and holes (h<sup>+</sup>) can be physically separated, favoring the redox reaction.<sup>19,20</sup> In addition, the Z-scheme can simultaneously use the more positive valence band (VB) of one semiconductor and the more negative conduction band (CB) of the other semiconductor, so it has a stronger redox capacity than the one-component semiconductor.<sup>8–16</sup> Two-dimensional/two-dimensional (2D/2D) composite structures have the largest interface contact area, which is conducive to photogenerated carrier transmission.<sup>9–16</sup> Therefore, 2D/2D Z-scheme heterojunctions can effectively enhance the performance of WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> photocatalysts. The reported 2D/2D Z-scheme WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunction systems had complex synthesis, insufficient application research, need for cocatalyst and other deficiencies to some degree.<sup>9–16</sup> Thus, it is necessary to further study the 2D/2D Z-scheme WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunction in more ways.

Industrial manufacturing, agricultural production, and daily life produce much wastewater. Organic pollutants in wastewater are toxic, accumulative, and challenging to degrade even at low concentrations, posing a serious threat to the water environment.<sup>17</sup> There are a variety of organic pollutants with

<sup>a</sup> Department of Mechanical Engineering, College of Engineering, Shantou University, Shantou 515063, China

<sup>b</sup> College of Chemistry and Chemical Engineering, Shantou University, Shantou 515063, China. E-mail: jkwang@stu.edu.cn

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d3ma00915g>



various properties in environmental water bodies, such as organic dyes, antibiotics, surfactants, and endocrine disruptors.<sup>17–19</sup> Tetracycline hydrochloride (TC-HCl) has been widely used in humans and animals as an inexpensive broad-spectrum antibiotics.<sup>20–23</sup> TC-HCl easily accumulates in water and soil systems because of its excellent water solubility and long half-life.<sup>20–23</sup> Organic dyes are common organic pollutants, and the same method has different removal effects on dyes with different properties.<sup>24</sup> The traditional removal methods of organic pollutants in the water include physical adsorption, chemical oxidation, and biodegradation. However, most of them have the disadvantages of poor efficiency, complicated methods, high cost, or easily causes secondary pollution.<sup>16,21–23</sup> The degradation of different-type organic pollutants in water is an urgent problem to be solved.

Moreover, nitrogen is an indispensable component of the biological structure.<sup>25–27</sup> It is found in proteins and nucleic acids, and most organisms except nitrogen-fixing microorganisms cannot directly use N<sub>2</sub>.<sup>25,28,29</sup> Nitrogen fixation is the conversion of N<sub>2</sub> to simple nitrogenous compounds (nitric oxide, ammonia and others), followed by the generation of more complex compounds that can be used by organisms.<sup>29,30</sup> In recent years, NH<sub>3</sub> has become a crucial raw material and green energy carrier.<sup>28</sup> Nevertheless, the traditional Haber–Bosch process remains the dominant industrial NH<sub>3</sub> production method, which consumes excessive fossil and releases harmful gases.<sup>25,28,30–33</sup> HNO<sub>3</sub> is also a vital raw material in agriculture, military, chemical industry and other areas.<sup>34,35</sup> However, the industrial HNO<sub>3</sub> is synthesized by the Ostwald process through catalytic oxidation of NH<sub>3</sub>, so this method is highly energy-consuming.<sup>31,32,34,35</sup> At present, most of the new methods of artificial nitrogen fixation are to reduce N<sub>2</sub> to produce NH<sub>3</sub>. However, there are few studies on the oxidation of N<sub>2</sub> to produce HNO<sub>3</sub> or N<sub>2</sub> disproportionation reaction. Therefore, developing eco-friendly and low-cost methods to fix N<sub>2</sub> by directly forming NH<sub>3</sub> and HNO<sub>3</sub> is of great interest.<sup>34,35</sup>

In this paper, 2D/2D Z-scheme WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunctions with different doping ratios were prepared using ice water bath ultrasonography and rapid calcination. The degradation effects on typical antibiotic organic pollutants (TC-HCl) and typical dye organic pollutants with different charge properties [amphoteric dye rhodamine B (RhB), cationic dye methylene blue (MB), and anionic dye methyl orange (MO)] were explored. The performance of photocatalytic nitrogen fixation (NRR and NOR) was investigated using two typical photocatalytic nitrogen fixation conditions. According to the experimental results, the possible mechanisms of the photocatalytic degradation and photocatalytic nitrogen fixation were proposed, which offered a reference for preparing 2D/2D Z-scheme heterojunction photocatalysts and photocatalytic degradation and nitrogen fixation.

## Experimental

### Materials

Sodium tungstate dihydrate (Na<sub>2</sub>WO<sub>4</sub>·2H<sub>2</sub>O), potassium sodium tartrate tetrahydrate (C<sub>4</sub>H<sub>4</sub>KNaO<sub>6</sub>·4H<sub>2</sub>O), and sodium hydroxide (NaOH) were obtained from Sinopharm Chemical Reagent Co.,

Ltd. Tetracycline hydrochloride (TC-HCl), rhodamine B (RhB), methylene blue (MB), methyl orange (MO), ammonium oxalate (AO), ammonium chloride (NH<sub>4</sub>Cl), potassium nitrate (KNO<sub>3</sub>) and potassium mercury iodide (K<sub>2</sub>HgI<sub>4</sub>) were acquired from Shanghai Maclin Biochemical Co., Ltd. Isopropyl alcohol (IPA), ethanol and methanol were obtained from Beijing Chemical Plant. 65% Nitric acid was derived from Beijing Chemical Plant. Melamine (chemically pure, content ≥ 98%) was purchased from Sigma Aldrich (Shanghai) Trading Co., Ltd. High purity nitrogen (content ≥ 99.999%) and compressed air were acquired from Beijing Millennium Capital Gas Co., Ltd. All solutions in this paper were prepared using ultra-pure water.

### Synthesis of 2D/2D Z-scheme WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunctions

400 mg of Na<sub>2</sub>WO<sub>4</sub>·2H<sub>2</sub>O was added into 300 mL of 4.8 M nitric acid at room temperature for 72 h, centrifugally washed and dried, and ground into a yellow powder as the WO<sub>3</sub>·2H<sub>2</sub>O precursor.<sup>34</sup> 10 g melamine was put into a covered crucible and calcined at 550 °C (heating rate: 5 °C min<sup>-1</sup>) in a muffle furnace for 4 h. After air cooling, it was ground into a light yellow powder as Bulk g-C<sub>3</sub>N<sub>4</sub>.<sup>36</sup>

500 mg of Bulk g-C<sub>3</sub>N<sub>4</sub> was mixed with WO<sub>3</sub>·2H<sub>2</sub>O of different masses in 20 mL ethanol, ultrasonicated in an ice water bath for 12 h, stirred for 1 hour, and completely dried. The sample underwent rapid calcination at 400 °C for 0.5 h, and was fully ground to obtain the 2D/2D Z-scheme WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunctions. WO<sub>3</sub> in the WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> composite is the final product of 10 wt.%, 20 wt.%, 30 wt.%, 40 wt.% and 50 wt.%, respectively. They were named as 10% WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub>, 20% WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub>, 30% WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub>, 40% WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> and 50% WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub>. Pure WO<sub>3</sub> and pure g-C<sub>3</sub>N<sub>4</sub> were prepared for comparison experiments.

### Photocatalytic degradation evaluation

The light source was a 300 W Xenon lamp (HX-UV300, Beijing NBET Technology Co., Ltd) equipped with a UVCUT420 (λ ≥ 420) UV cut-off filter. The optical power meter (CEL-NP2000) monitored the light intensity, and the light intensity was controlled at 100 mW cm<sup>-2</sup>.

This work used antibiotic organic pollutants TC-HCl and dye organic pollutants MB, RhB and MO as photocatalytic degradation targets. The characteristic peaks of TC-HCl, RhB, MB and MO were 357 nm, 554 nm, 664 nm and 463 nm,<sup>37–39</sup> respectively. The 30 mg photocatalyst was dispersed in 100 mL aqueous solution containing 10 mg L<sup>-1</sup> organic pollutants, and stirred away from light for 30 min to achieve the adsorption–desorption equilibrium. After the visible-light source was turned on, a 3 mL suspension was taken at certain intervals for centrifugation, and the absorbance of the organic pollutants after degradation was determined by UV-Vis spectrophotometer (YOKE T3202). The degradation efficiency (η) was calculated using the characteristic peak absorbance value. The η was calculated by the eqn (1):<sup>38</sup>

$$\eta = \frac{A_0 - A}{A_0} \times 100\% = \frac{C_0 - C}{C_0} \times 100\% \quad (1)$$



where  $A_0$  and  $A$  are the initial absorbance of the characteristic peak of organic pollutants and the absorbance after a certain reaction time, respectively. According to the Lambert–Beer law,  $C_0$  and  $C$  are the initial concentration of organic pollutants and the concentration after a certain time, respectively.

### Photocatalytic nitrogen fixation evaluation

Experiment 1 and Experiment 2 are two typical conditions of the photocatalytic nitrogen fixation reaction.<sup>34,40,41</sup> The light source was 300 W Xenon lamp (HSX-UV300).

Experiment 1: a 100 mg quantity of photocatalyst was dispersed in 100 mL ultra-pure water, and then ultrasonicated for 15 min. Air flowed into the above suspension at a rate of 100 mL min<sup>-1</sup>. The suspension was taken at set intervals to test the concentration of NH<sub>4</sub><sup>+</sup> and NO<sub>3</sub><sup>-</sup>.<sup>34,41</sup>

Experiment 2: a 100 mg quantity of photocatalyst was dispersed in 100 mL 20% methanol aqueous solution, and then ultrasonicated for 15 min. N<sub>2</sub> flowed into the above suspension at a rate of 100 mL min<sup>-1</sup>. The suspension was taken at set intervals to test the concentration of NH<sub>4</sub><sup>+</sup> and NO<sub>3</sub><sup>-</sup>.<sup>40,41</sup>

The concentration of NH<sub>4</sub><sup>+</sup> was determined by Nessler's reagent colorimetric method. The concentration of NO<sub>3</sub><sup>-</sup> was measured by ion chromatography (Shimadzu LC20Adsp, Shodex IC SI-52 4E). The above methods were referred to in our previous paper.<sup>41</sup>

## Results and discussion

### Photocatalyst characterization

X-ray diffraction spectra (XRD, Rigaku D/MAX-2550V) (Fig. 1(a)) and Fourier-transform infrared (FT-IR, BRUKER VERTEX70) spectra (Fig. 1(b)) were used to characterize the chemical composition and structure of the g-C<sub>3</sub>N<sub>4</sub>, WO<sub>3</sub> and WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> composites. In Fig. 1(a), the characteristic peaks at 13.1° and 27.4° belong to the (100) and (002) crystal faces of pure g-C<sub>3</sub>N<sub>4</sub> (JCPDS 87-1526),<sup>33,42</sup> respectively. The (002) peak is

attributed to the stacking structure of the conjugated aromatic rings, while the (100) peak is attributed to the interlayer stacking of g-C<sub>3</sub>N<sub>4</sub>.<sup>43,44</sup> Therefore, after g-C<sub>3</sub>N<sub>4</sub> was peeled off by ultrasonic treatment, the intensity of the (100) peak gradually broadened and weakened until it disappeared. The characteristic peaks of pure WO<sub>3</sub> are in accordance with JCPDS 83-0950, which belongs to monoclinic WO<sub>3</sub> (m-WO<sub>3</sub>).<sup>45</sup> The XRD results of WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> contain the characteristic peaks of g-C<sub>3</sub>N<sub>4</sub> and WO<sub>3</sub>. With the increase of WO<sub>3</sub> doping amount, the peaks of WO<sub>3</sub> become stronger, while the peaks of g-C<sub>3</sub>N<sub>4</sub> become weaker. The XRD results indicate that the WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> composites were prepared successfully. These materials maintain the complete crystal structure of the sheet-like g-C<sub>3</sub>N<sub>4</sub> and WO<sub>3</sub>.

As shown in Fig. 1(b), the FT-IR spectrum of pure WO<sub>3</sub> has a wide peak at 631 cm<sup>-1</sup> due to the stretching vibration of the O–W–O bond.<sup>46</sup> The peak of pure g-C<sub>3</sub>N<sub>4</sub> at 803 cm<sup>-1</sup> was ascribed to the out-of-plane bending vibration of the 3-*S*-triazine ring. The peaks at 1230 cm<sup>-1</sup>, 1313 cm<sup>-1</sup>, 1395 cm<sup>-1</sup>, 1537 cm<sup>-1</sup> and 1633 cm<sup>-1</sup> belong to the skeleton stretching vibration of the C–N heterocyclic ring.<sup>42</sup> All signals of g-C<sub>3</sub>N<sub>4</sub> can be seen in the FT-IR spectra of WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub>. With the increase of the WO<sub>3</sub> doping amount, the characteristic peaks of WO<sub>3</sub> gradually become stronger. This is consistent with the XRD results, and indicates the structural integrity of the WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> composite.

X-ray photoelectron spectroscopy (XPS, Thermo Fisher Scientific ESCALAB250Xi) was applied to study the surface element composition and valence information of the photocatalysts. Fig. 2(a) shows the XPS full spectrum of g-C<sub>3</sub>N<sub>4</sub>, WO<sub>3</sub> and 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub>. The XPS survey spectrum of 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> shows four elements (C, N, O and W), and no other impurities appear. The C and N are provided by g-C<sub>3</sub>N<sub>4</sub>, and O and W are provided by WO<sub>3</sub>. Fig. 2(b) is the high-resolution W 4f spectrum of WO<sub>3</sub> and 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub>. Compared with the two peaks of pure WO<sub>3</sub> (36.0 eV and 38.1 eV), the two peaks of 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> shift to lower binding energy (35.6 eV and 37.7 eV). The reason for this shift may be that the hydrogen

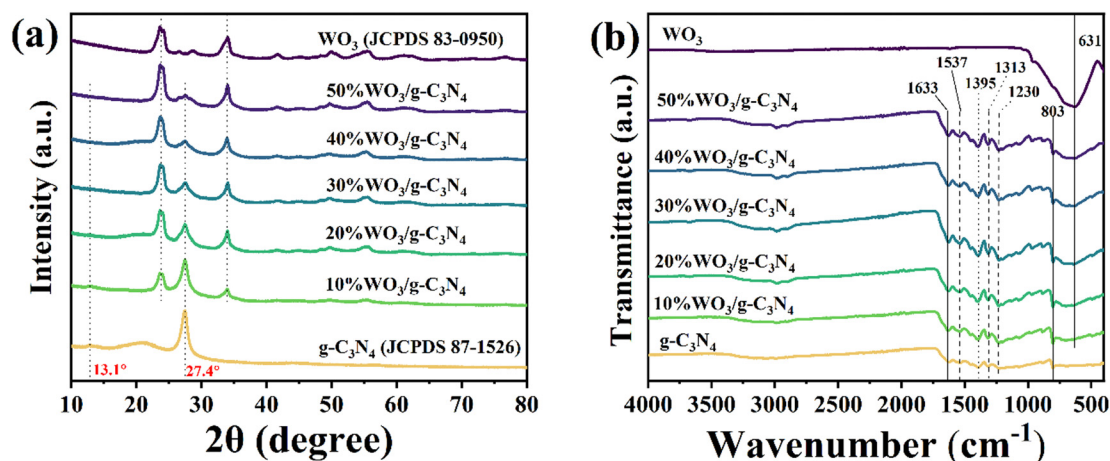


Fig. 1 (a) XRD and (b) FT-IR spectra of the g-C<sub>3</sub>N<sub>4</sub>, WO<sub>3</sub> and WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> composites.



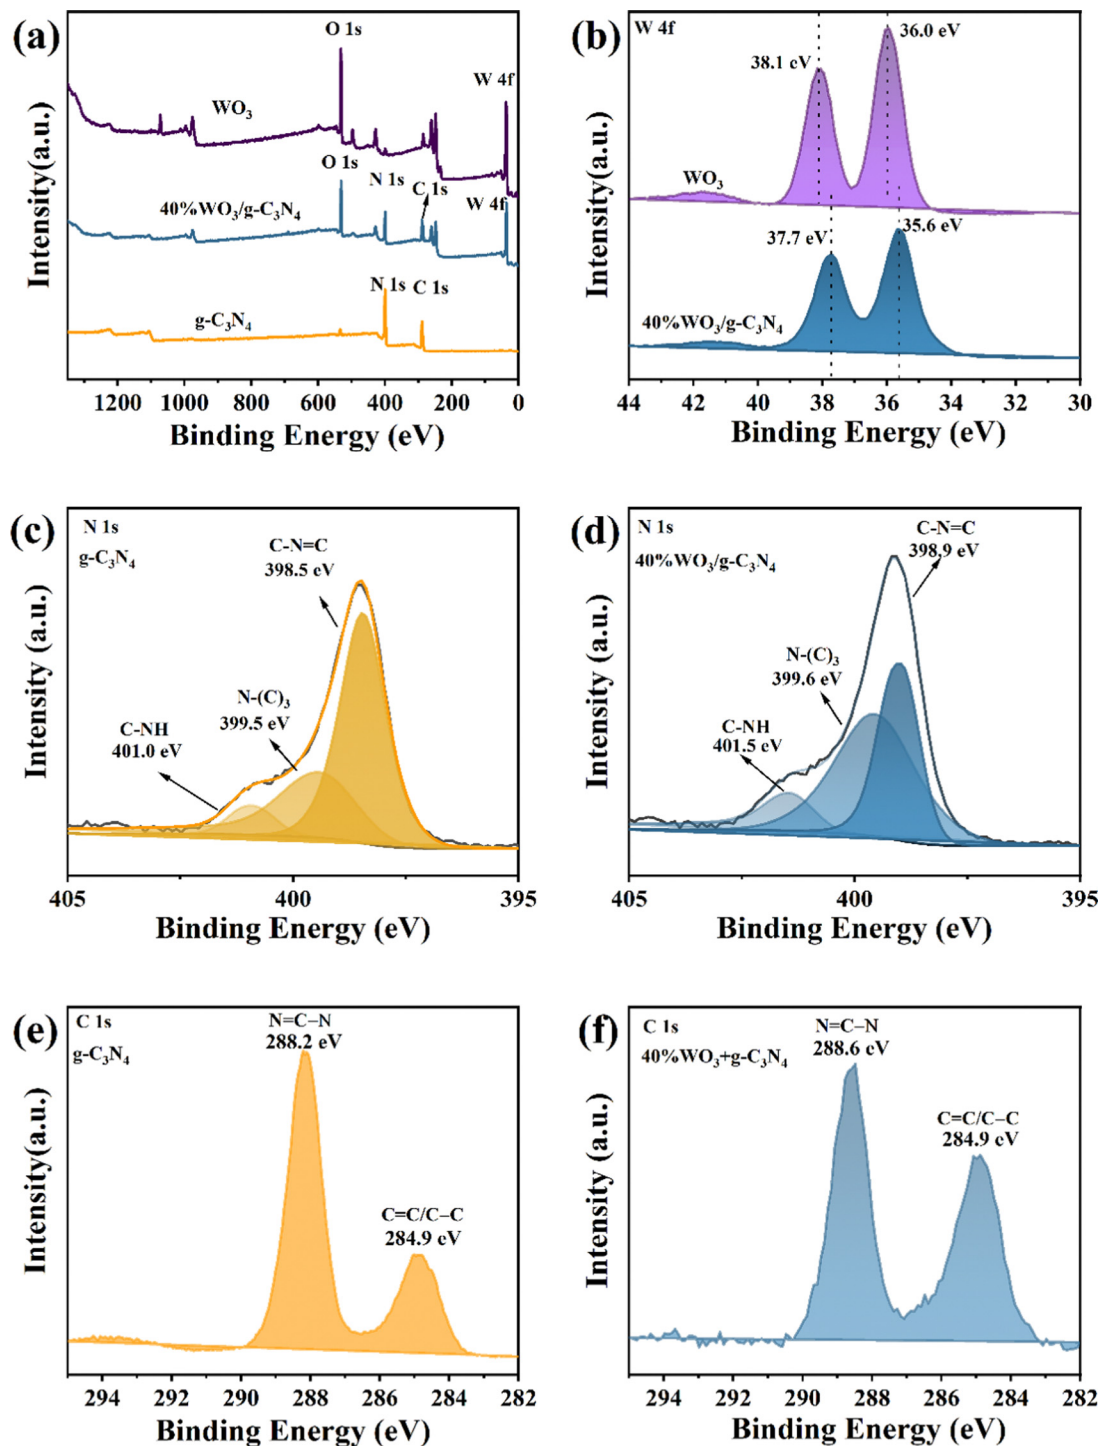


Fig. 2 (a) XPS survey spectra of  $g\text{-C}_3\text{N}_4$  and  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$ , (b) high-resolution W 4f spectra of  $\text{WO}_3$  and  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$ , (c) high-resolution N 1s spectra of  $g\text{-C}_3\text{N}_4$ , (d) high-resolution N 1s spectra of  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$ , (e) high-resolution C 1s spectra of  $g\text{-C}_3\text{N}_4$  and (f) high-resolution C 1s spectra of  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$ .

bond formed between the terminal  $\text{-NH}_2$  and  $\text{W-O}$  bond during the action of  $\text{WO}_3$  and  $g\text{-C}_3\text{N}_4$  will slightly weaken the  $\text{W-O}$  bond, thus reducing the binding energy value of W 4f in  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$ .<sup>47,48</sup> Fig. 2(c) and (d) show the high-resolution N 1s spectra of  $g\text{-C}_3\text{N}_4$  and  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$ , respectively. The positions of the three N 1s peaks of pure  $g\text{-C}_3\text{N}_4$  are 398.5 eV,

399.5 eV and 401.0 eV, which can be attributed to  $\text{C-N=C}$ ,  $\text{N-(C)}_3$  and  $\text{C-NH}$ ,<sup>49</sup> respectively. The N 1s peaks of  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$  are shifted towards higher binding energy due to the charge transfer at the interface of  $\text{WO}_3$  and  $g\text{-C}_3\text{N}_4$ .<sup>50</sup> This illustrates that a heterostructure is formed between  $g\text{-C}_3\text{N}_4$  and  $\text{WO}_3$ . Fig. 2(e) and (f) show the high-resolution C 1s



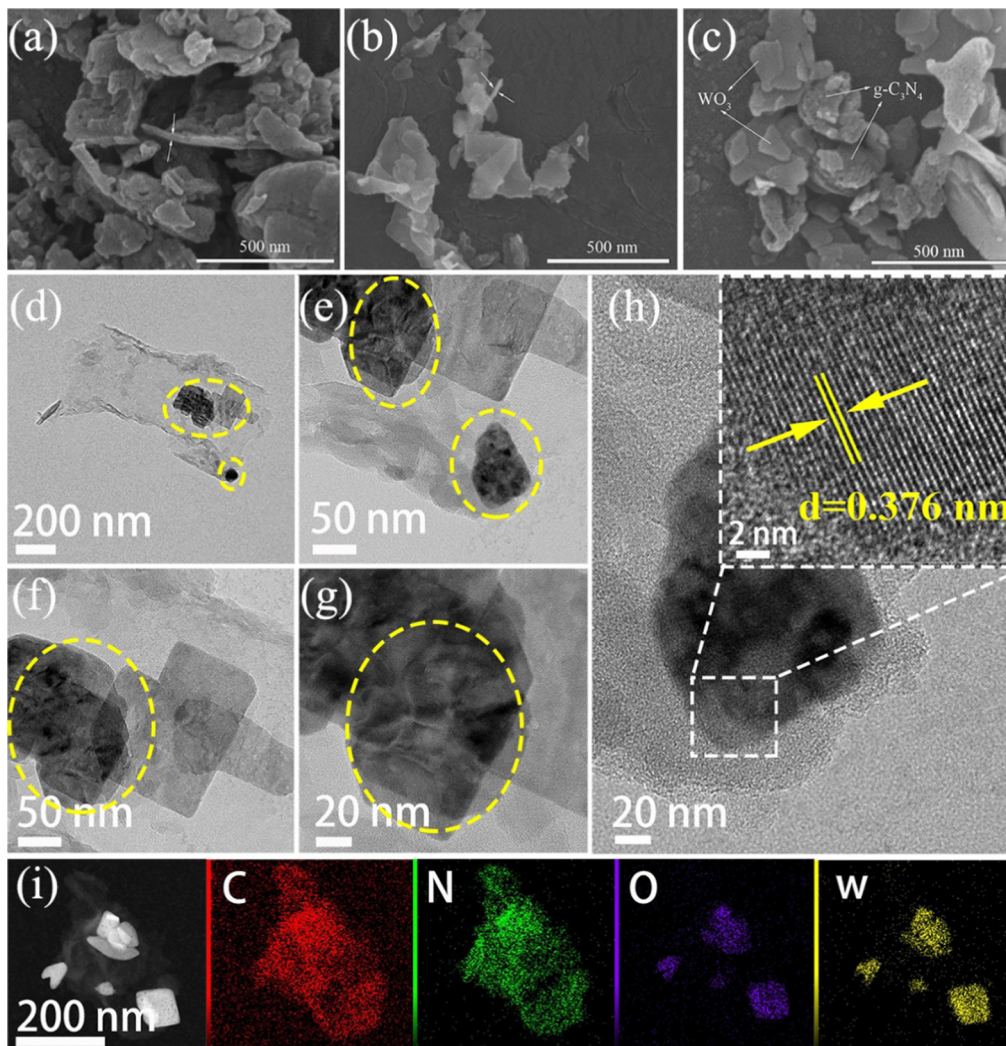


Fig. 3 SEM images of (a)  $g\text{-C}_3\text{N}_4$ , (b)  $\text{WO}_3$  and (c)  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$ ; (d)–(h) HRTEM images and (i) EDS mapping images of  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$ .

spectra of  $g\text{-C}_3\text{N}_4$  and  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$ , respectively.  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$  has two major C 1s peaks at 284.9 eV and 288.6 eV, corresponding to  $\text{sp}^2$  bonded carbon ( $\text{N}=\text{C}-\text{N}$ ) and aromatic carbon ( $\text{C}=\text{C}/\text{C}-\text{C}$ ),<sup>19</sup> while the corresponding peaks positions for pure  $g\text{-C}_3\text{N}_4$  are 284.9 eV and 288.2 eV, respectively. Compared to  $g\text{-C}_3\text{N}_4$ , the position of  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$  was slightly shifted by 0.4 eV.<sup>50</sup> This is consistent with the results of N1s, verifying the existence of the heterojunction.

The surface morphology of  $g\text{-C}_3\text{N}_4$ ,  $\text{WO}_3$  and  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$  can be visually displayed through scanning electron microscope (SEM, Hitachi SU8010) and high-resolution transmission electron microscope (HRTEM, JEOL JEM-F200) with an energy dispersive spectrometer (EDS). As shown by the white arrow in Fig. 3(a),  $g\text{-C}_3\text{N}_4$  is a stack of nanosheets with a thickness of less than 30 nm.  $\text{WO}_3$  is composed of  $\text{WO}_3$  nanosheets, which are indicated by the white arrow in Fig. 3(b). Fig. 3(c) shows that  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$  is a 2D composite structure formed by stacking  $g\text{-C}_3\text{N}_4$  nanosheets and  $\text{WO}_3$  nanosheets together.

Fig. 3(d)–(h) displays the HRTEM images of  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$ .  $\text{WO}_3$  is darker than  $g\text{-C}_3\text{N}_4$ , and  $\text{WO}_3$  is marked with

the yellow circle. The lattice plane of 0.376 nm corresponds to the (002) plane of  $\text{WO}_3$  (Fig. 3(h)).<sup>10</sup> The EDS mapping images of  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$  (Fig. 3(i)) demonstrates the existence and the location of the C, N, O and W elements. These results further prove the successful preparation of 2D/2D  $\text{WO}_3/g\text{-C}_3\text{N}_4$ .

The specific surface area and pore structure of the  $g\text{-C}_3\text{N}_4$  and  $\text{WO}_3/g\text{-C}_3\text{N}_4$  composites were studied by  $\text{N}_2$  adsorption-desorption isotherm (Fig. S1a, ESI<sup>†</sup>) using Micromeritics ASAP 2460. The pore size distribution diagram (Fig. S1b, ESI<sup>†</sup>) shows that the pore sizes of these six samples are mainly mesoporous. Among them, the pores of  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$  are mainly distributed in the 1.5–16 nm range, and there are few mesopores smaller than 2 nm.<sup>51</sup> Table S1 (ESI<sup>†</sup>) summarizes the data for the specific surface area and pore volume. The specific surface areas of the  $\text{WO}_3/g\text{-C}_3\text{N}_4$  composites are all smaller than that of pure  $g\text{-C}_3\text{N}_4$ , and  $20\%\text{WO}_3/g\text{-C}_3\text{N}_4$  ( $11.88\text{ m}^2\text{ g}^{-1}$ ) has the smallest specific surface area. The specific surface area sizes of  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$  ( $14.87\text{ m}^2\text{ g}^{-1}$ ) and  $50\%\text{WO}_3/g\text{-C}_3\text{N}_4$  ( $14.90\text{ m}^2\text{ g}^{-1}$ ) are similar. For the pore volume, the pure  $g\text{-C}_3\text{N}_4$  ( $0.49\text{ cm}^3\text{ g}^{-1}$ ) is still the largest, and  $20\%\text{WO}_3/g\text{-C}_3\text{N}_4$



( $0.04 \text{ cm}^3 \text{ g}^{-1}$ ) is the smallest. The specific surface area and pore volume can affect the number of active sites, and thus affect the adsorption and reaction effect in the catalytic process. However, the specific surface area and pore volume are not necessarily better with larger sizes. It is necessary to synthesize other properties to obtain the final catalytic performance. Table S1 (ESI<sup>†</sup>) also shows the zeta potential of the  $\text{g-C}_3\text{N}_4$  and  $\text{WO}_3/\text{g-C}_3\text{N}_4$  composites in water.

Fig. 4(a) shows the results from investigating the optical properties of the  $\text{g-C}_3\text{N}_4$ ,  $\text{WO}_3$  and  $\text{WO}_3/\text{g-C}_3\text{N}_4$  composites by ultraviolet and visible diffuse reflectance spectra (UV-Vis DRS, SHIMADZU UV-3600 Plus). Fig. 4(a) was converted into Fig. 4(b) using the Kubelka–Munk function, and the band gap ( $E_g$ ) of the  $\text{g-C}_3\text{N}_4$ ,  $\text{WO}_3$  and  $\text{WO}_3/\text{g-C}_3\text{N}_4$  composites was estimated.<sup>41</sup> The  $E_g$  values of pure  $\text{g-C}_3\text{N}_4$  and pure  $\text{WO}_3$  are 2.48 eV and 2.41 eV, respectively. The similar  $E_g$  of these two pure substances leads to the similar  $E_g$  of the  $\text{WO}_3/\text{g-C}_3\text{N}_4$  composites, which is why the  $\text{g-C}_3\text{N}_4$ ,  $\text{WO}_3$  and  $\text{WO}_3/\text{g-C}_3\text{N}_4$  composites are all yellow. The  $E_g$  of 40% $\text{WO}_3/\text{g-C}_3\text{N}_4$  and 50% $\text{WO}_3/\text{g-C}_3\text{N}_4$  is 2.43 eV, which is the smallest  $E_g$  among the five  $\text{WO}_3/\text{g-C}_3\text{N}_4$  composites and is more conducive to the absorption of visible light.

To further study the photogenerated carrier recombination probability of the  $\text{g-C}_3\text{N}_4$  and  $\text{WO}_3/\text{g-C}_3\text{N}_4$  composites, the photoluminescence (PL, HORIBA FluoroMax-4) spectra of the samples were tested. The weak PL peak intensity indicates the low recombination probability of the photogenerated carriers and high separation efficiency.<sup>43,52</sup> As shown in Fig. 4(c), the PL

peak intensity was ranked as  $\text{g-C}_3\text{N}_4 > 30\%\text{WO}_3/\text{g-C}_3\text{N}_4 > 10\%\text{WO}_3/\text{g-C}_3\text{N}_4 > 20\%\text{WO}_3/\text{g-C}_3\text{N}_4 > 50\%\text{WO}_3/\text{g-C}_3\text{N}_4 > 40\%\text{WO}_3/\text{g-C}_3\text{N}_4$ . The 40% $\text{WO}_3/\text{g-C}_3\text{N}_4$  photogenerated carrier recombination rate is the lowest in the above samples. Thus, the photogenerated  $\text{e}^- - \text{h}^+$  separation efficiency of 40% $\text{WO}_3/\text{g-C}_3\text{N}_4$  is the highest, which is conducive to improving its photocatalytic performance.

Electrochemical impedance spectroscopy (EIS, CHI660E Electrochemical Workstation) was used to further investigate the charge transfer capability of the  $\text{g-C}_3\text{N}_4$ ,  $\text{WO}_3$  and 40%  $\text{WO}_3/\text{g-C}_3\text{N}_4$  (Fig. 4(d)).<sup>41</sup> A smaller arc radius on the EIS Nyquist diagram corresponds to a smaller charge transfer resistance on the working electrode surface.<sup>41</sup> In Fig. 4(d), the arc radius of 40%  $\text{WO}_3/\text{g-C}_3\text{N}_4$  is smaller than that of  $\text{g-C}_3\text{N}_4$  and  $\text{WO}_3$ , illustrating that 40%  $\text{WO}_3/\text{g-C}_3\text{N}_4$  has better photogenerated electron-hole separation and transfer ability.

### Photocatalytic degradation performance

Firstly, the photocatalyst and TC-HCl were mixed away from light for 30 min ( $t$  is  $-30$  to  $0$  min in the corresponding Fig. 5(a)) to reach the adsorption-desorption equilibrium. The degradation efficiencies of the  $\text{g-C}_3\text{N}_4$ ,  $\text{WO}_3$  and  $\text{WO}_3/\text{g-C}_3\text{N}_4$  composites as a photocatalyst for the antibiotic organic pollutant TC-HCl are shown in Fig. 5(a). The adsorption efficiency of the  $\text{g-C}_3\text{N}_4$ ,  $\text{WO}_3$  and  $\text{WO}_3/\text{g-C}_3\text{N}_4$  composites for TC-HCl is about 7%. The adsorption rate of pure  $\text{WO}_3$  to TC-HCl is slower than that of the  $\text{g-C}_3\text{N}_4$  and  $\text{WO}_3/\text{g-C}_3\text{N}_4$  composites, while the adsorption of bulk  $\text{g-C}_3\text{N}_4$  to TC-HCl was almost zero. When  $t$  is 0 min, the visible light

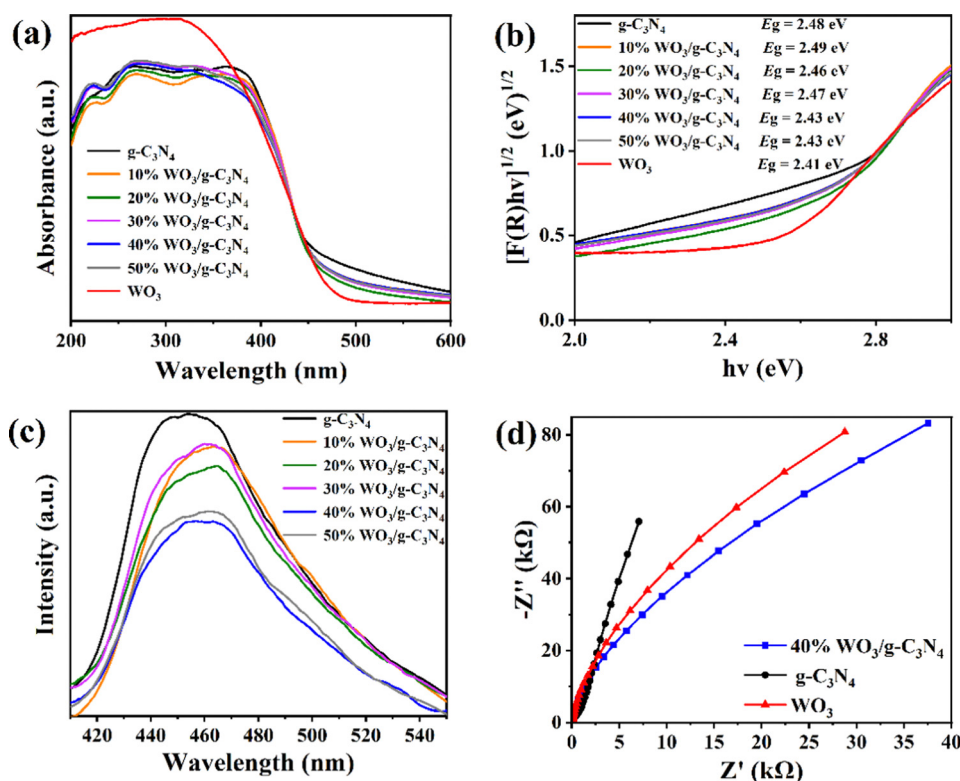


Fig. 4 (a) UV-vis DRS spectra, (b)  $E_g$  and (c) PL spectra of the  $\text{g-C}_3\text{N}_4$ ,  $\text{WO}_3$  and  $\text{WO}_3/\text{g-C}_3\text{N}_4$  composites; (d) EIS of 40% $\text{WO}_3/\text{g-C}_3\text{N}_4$ ,  $\text{g-C}_3\text{N}_4$  and  $\text{WO}_3$ .



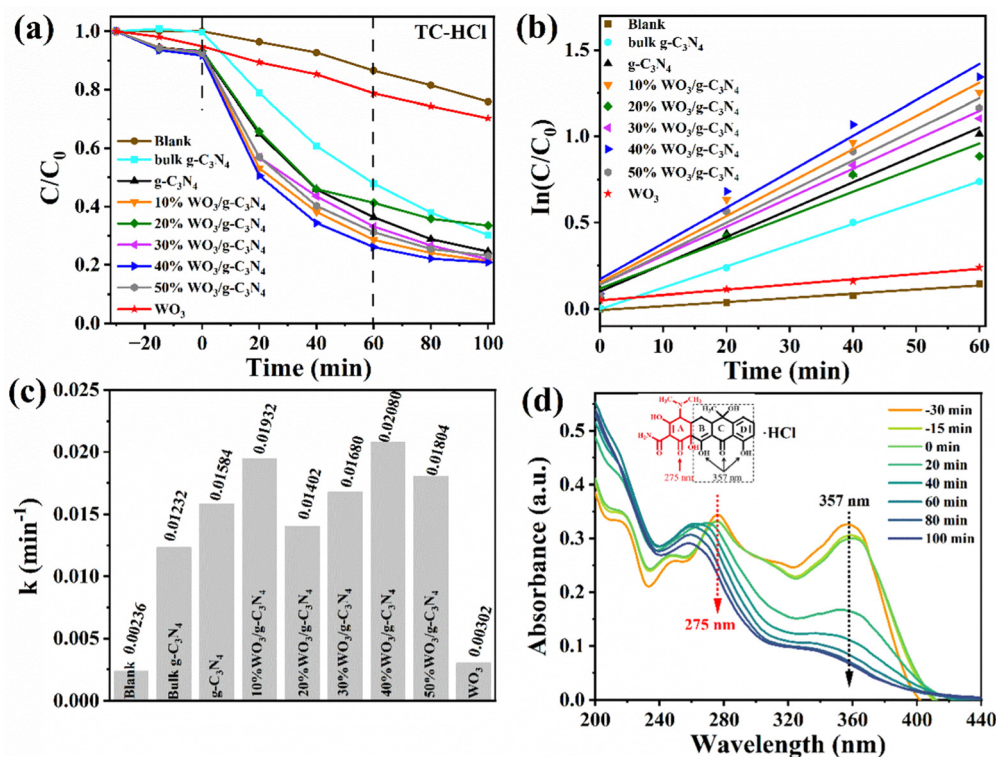


Fig. 5 (a) The photocatalytic degradation efficiency of TC-HCl by  $g\text{-C}_3\text{N}_4$ ,  $\text{WO}_3$  and  $\text{WO}_3/g\text{-C}_3\text{N}_4$  composites under visible light, (b) corresponding first-order kinetic fitting curves and (c) corresponding UV-vis absorption spectra during the degradation of TC-HCl by  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$ .

source was turned on to start the photocatalytic reaction. “Blank” is the blank control without any photocatalyst. The self-degradation rate of TC-HCl is 24.1% after 100 min visible-light irradiation. The removal efficiency of TC-HCl by bulk  $g\text{-C}_3\text{N}_4$ ,  $g\text{-C}_3\text{N}_4$ ,  $\text{WO}_3$ ,  $10\%\text{WO}_3/g\text{-C}_3\text{N}_4$ ,  $20\%\text{WO}_3/g\text{-C}_3\text{N}_4$ ,  $30\%\text{WO}_3/g\text{-C}_3\text{N}_4$ ,  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$  and  $50\%\text{WO}_3/g\text{-C}_3\text{N}_4$  are 69.8%, 75.4%, 29.7%, 78.8%, 66.6%, 78.1%, 79.1% and 76.9%, respectively. It shows that  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$  has the best degradation effect on TC-HCl. The degradation rate of the  $\text{WO}_3/g\text{-C}_3\text{N}_4$  composite became slow after the irradiation time  $t$  was 60 min, indicating that the maximum degradation efficiency was reached at 60 min. Therefore,  $t$  was 0–60 min for the first-order kinetic fitting (Fig. 5(b)). Fig. 5(a) shows the degradation process, and Fig. 5(b) shows the first-order kinetics fitting curve, which was calculated by eqn (2):

$$-\ln\left(\frac{C}{C_0}\right) = kt \quad (2)$$

where  $C_0$  and  $C$  are the concentrations of the organic pollutants ( $\text{mg L}^{-1}$ , ppm) in water at the initial concentration and time  $t$ , respectively. The term  $k$  is the apparent rate constant ( $\text{min}^{-1}$ ).

Fig. 5(c) is a histogram comparison of the apparent rate constant  $k$ . The  $k$  values of bulk  $g\text{-C}_3\text{N}_4$ ,  $g\text{-C}_3\text{N}_4$ ,  $\text{WO}_3$ ,  $10\%\text{WO}_3/g\text{-C}_3\text{N}_4$ ,  $20\%\text{WO}_3/g\text{-C}_3\text{N}_4$ ,  $30\%\text{WO}_3/g\text{-C}_3\text{N}_4$ ,  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$  and  $50\%\text{WO}_3/g\text{-C}_3\text{N}_4$  were  $0.00236 \text{ min}^{-1}$ ,  $0.01232 \text{ min}^{-1}$ ,  $0.01584 \text{ min}^{-1}$ ,  $0.00302 \text{ min}^{-1}$ ,  $0.01932 \text{ min}^{-1}$ ,  $0.01402 \text{ min}^{-1}$ ,  $0.01680 \text{ min}^{-1}$ ,  $0.02080 \text{ min}^{-1}$  and  $0.01804 \text{ min}^{-1}$ , respectively. Therefore, the introduction of the  $g\text{-C}_3\text{N}_4$  nanosheets is greatly enhanced the catalytic effect of  $\text{WO}_3$ . Among them,

$40\%\text{WO}_3/g\text{-C}_3\text{N}_4$  had the best degradation efficiency, which was 1.69 times, 1.31 times and 6.89 times of bulk  $g\text{-C}_3\text{N}_4$ ,  $g\text{-C}_3\text{N}_4$  and  $\text{WO}_3$ , respectively.

Fig. 5(d) shows the UV-visible absorption spectrum during the adsorption and degradation of TC-HCl by  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$ . TC-HCl has two characteristic peaks at 275 nm and 357 nm, as shown in Fig. 5(d). It has been reported that the peak at 275 nm is associated with the aromatic ring A structure, including the enolic hydroxyl, amide and ketone groups. The peak at 357 nm is from aromatic rings B, C, and D, comprising the extended chromophores.<sup>53</sup>  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$  can simultaneously destroy the rings B, C, D, and A, but the destructive effect on A is relatively weak under visible light. The slight shift in the location of the characteristic peak may be caused by the slight change in pH during the removal process.

Fig. 6(a) shows the removal process of  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$  as a photocatalyst for three typical dyes with different charge properties, cationic dye MB, amphoteric dye RhB, and anionic dye MO. After 30 min dark adsorption process, 11.4% MB, 24.6% RhB and 1.8% MO can be removed. According to Table S1 (ESI<sup>†</sup>),  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$  was negatively charged in water, so the adsorption effect of the anionic dye MO was poor. When the light source was turned on, RhB was almost completely degraded after 20 min. After 100 min, the total removal rate of MB reached 91.4%, while that of MO was only 49.6%. Therefore, it proves that  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$  has a good removal effect on MB and RhB.

Fig. 6(b) shows the recycling experiments of  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$ , where it can be seen that  $40\%\text{WO}_3/g\text{-C}_3\text{N}_4$  almost



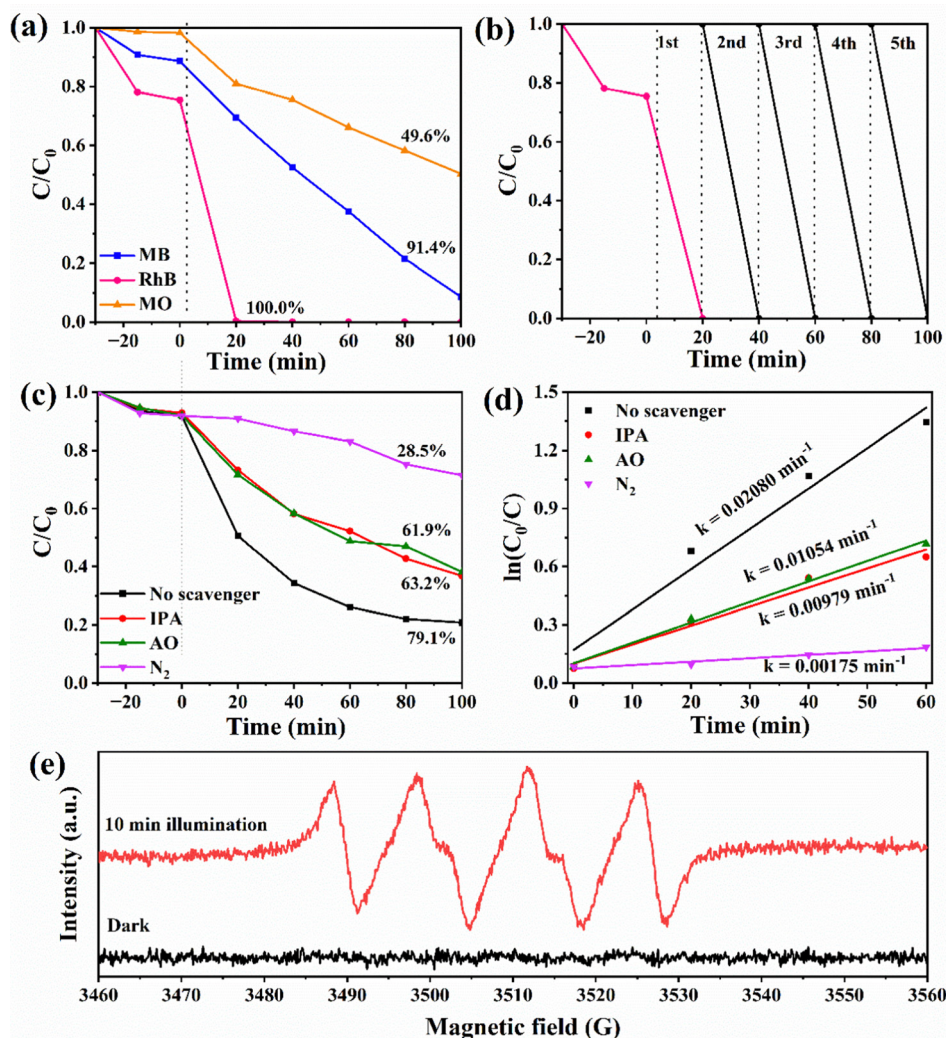


Fig. 6 (a) The removal process of MB, RhB and MO by 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub>. (b) Photodegradation cycle test of 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub>; (c) free radical capture experiments of the 0.3 g L<sup>-1</sup> 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> photocatalytic degradation of 10 mg L<sup>-1</sup> TC-HCl, and (d) their first-order kinetic fitting curves; and (e) EPR spectra of the DMPO-•O<sub>2</sub><sup>-</sup> adducts over 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> under dark condition and with 10 min illumination in methanol.

maintained its original degradation efficiency of RhB after 5 cycles. Therefore, 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> possessed good photocatalytic stability for the potential application.

### Photocatalytic degradation mechanism

It has been reported that the superoxide radical (•O<sub>2</sub><sup>-</sup>), hole (h<sup>+</sup>), and hydroxyl radical (•OH) are the main active species in photocatalytic oxidation reactions.<sup>54</sup> To study the photocatalytic degradation mechanism of the 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> photocatalyst, three trapping agents were applied to explore the active species in the photocatalytic reaction process. In this work, 1 mM ammonium oxalate (AO) was used to capture h<sup>+</sup>, and 1 mM isopropyl alcohol (IPA) was used to capture •OH. N<sub>2</sub> is used to remove O<sub>2</sub> in the reaction system. It blocked the generation of •O<sub>2</sub><sup>-</sup> from the root. Therefore, N<sub>2</sub> can be used as the trapping agent of •O<sub>2</sub><sup>-</sup>.<sup>55</sup> By adding different trapping agents in the reaction solution, the corresponding reactive species were removed. According to the change of photocatalytic efficiency,

the role of different active substances in the photocatalytic process can be determined. The device and process of the above capture experiment are the same as that of the photocatalytic performance test.

Fig. 6(c) shows the degradation process of 10 mg L<sup>-1</sup> TC-HCl by 0.3 g L<sup>-1</sup> 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> when IPA, AO and N<sub>2</sub> were added to the reaction system. The removal rate decreased from 79.1% to 63.2%, 61.9% and 28.5%, respectively. It indicated that N<sub>2</sub> has the greatest impact on the removal rate. Therefore, •O<sub>2</sub><sup>-</sup> was the main active species, while h<sup>+</sup> and •OH had similar effects as the minor active species. Fig. 6(d) shows the kinetic fitting curves for the photocatalytic process that is shown in Fig. 6(c). The first 60 min of the reaction process conforms to the first-order kinetic model. The apparent rate constants *k* decreased from 0.02080 min<sup>-1</sup> to 0.00979 min<sup>-1</sup>, 0.01054 min<sup>-1</sup> and 0.00175 min<sup>-1</sup>, respectively (Fig. 6(d)). This verifies that the role of the active species in this process is ranked as •O<sub>2</sub><sup>-</sup> > h<sup>+</sup> ≈ •OH.





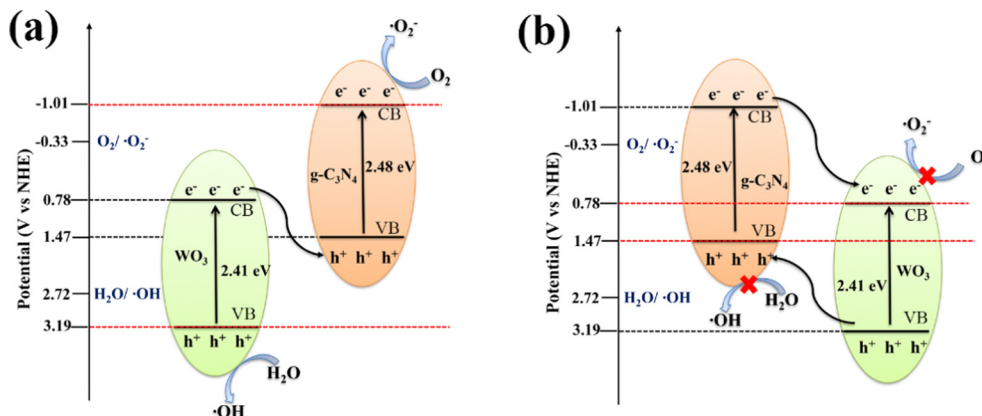


Fig. 7 The proposed mechanisms for the degradation of organic pollutants by 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> (a) Z-scheme heterojunction and (b) type-II heterojunction.

The valence band potential ( $E_{VB}$ ) and conduction band potential ( $E_{CB}$ ) of the semiconductor zero charge point ( $\text{pH}_{zpc}$ ) can be estimated by eqn (3) and (4):<sup>56–60</sup>

$$E_{VB} = X - E_e + 0.5E_g \quad (3)$$

$$E_{CB} = E_{VB} - E_g \quad (4)$$

where  $X$  is the geometric mean of the absolute electronegativity of the constituent atoms of the semiconductor,  $E_e$  is the energy of the free electron at the hydrogen scale, and  $E_g$  is the band gap. The  $X$  values of g-C<sub>3</sub>N<sub>4</sub> and WO<sub>3</sub> were 4.73 eV and 6.49 eV, respectively.<sup>54</sup> According to eqn (3) and (4), it can be estimated that the  $E_{CB}$  values of g-C<sub>3</sub>N<sub>4</sub> and WO<sub>3</sub> are  $-1.01$  eV and  $0.78$  eV, respectively. The  $E_{VB}$  values of g-C<sub>3</sub>N<sub>4</sub> and WO<sub>3</sub> are  $1.47$  eV and  $3.19$  eV, respectively.

Whether the  $\bullet\text{O}_2^-$  species are generated over 40% WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> under light irradiation offers an important clue to determining the transfer route of the charge carriers.  $\bullet\text{O}_2^-$  was detected using electron paramagnetic resonance (EPR, Bruker EMXplus-6/1). In Fig. 6(e), the apparent  $\bullet\text{O}_2^-$  characteristic peaks can be observed in the EPR spectrum of 5,5-dimethyl-1-pyrroline N-oxide (DMPO)  $\bullet\text{O}_2^-$  adduct over 40% WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> after 10 min light illumination, demonstrating the generation of  $\bullet\text{O}_2^-$ .<sup>61,62</sup>


According to the results of the above capture experiments and EPR, two possible reaction mechanisms are proposed in Fig. 7. The electron ( $e^-$ ) on the CB of WO<sub>3</sub> and  $h^+$  on VB of g-C<sub>3</sub>N<sub>4</sub> in the Z-scheme 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunction (Fig. 7(a)) are recombined. The CB of g-C<sub>3</sub>N<sub>4</sub> is more negative than O<sub>2</sub>/ $\bullet\text{O}_2^-$  ( $-0.33$  vs. NHE), and the VB of WO<sub>3</sub> is more positive than H<sub>2</sub>O/ $\bullet\text{OH}$  ( $2.72$  V vs NHE), which allows  $\bullet\text{O}_2^-$  and  $\bullet\text{OH}$  to be produced. If g-C<sub>3</sub>N<sub>4</sub> and WO<sub>3</sub> form a conventional type-II heterojunction (Fig. 7(b)), the CB of g-C<sub>3</sub>N<sub>4</sub> will transfer  $e^-$  to the CB of WO<sub>3</sub>, while the VB of WO<sub>3</sub> will transfer  $h^+$  to the VB of g-C<sub>3</sub>N<sub>4</sub>. However, in this case, the CB of WO<sub>3</sub> will be more positive than O<sub>2</sub>/ $\bullet\text{O}_2^-$ , so that the electrons on CB cannot reduce O<sub>2</sub> to generate  $\bullet\text{O}_2^-$ .<sup>47</sup> At the same time, the VB of g-C<sub>3</sub>N<sub>4</sub> will be more negative than H<sub>2</sub>O/ $\bullet\text{OH}$ , so that the  $h^+$  in VB cannot oxidize H<sub>2</sub>O to generate  $\bullet\text{OH}$ .<sup>47</sup> In conclusion, 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> is the Z-scheme heterojunction. This structure can improve the separation of the photogenerated  $e^-$  and  $h^+$ , and enhance the redox ability of the photogenerated  $e^-$  and  $h^+$ , as well as the catalytic performance of the photocatalyst.<sup>9–16</sup>

In addition, the comparison of almost all published 2D/2D Z-scheme WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunction systems is shown in Table 1, which indicates that the facile synthetic 2D/2D Z-scheme WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunctions in this work exhibit considerable photocatalytic performance in the environmental application and energy application without any cocatalyst.<sup>9–16</sup>

Table 1 Comparison of the 2D/2D Z-schemes of the WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunction photocatalyst systems

Photocatalyst	Synthesis	Environmental application	Energy application	Ref.
WO <sub>3</sub> -H <sub>2</sub> O/g-C <sub>3</sub> N <sub>4</sub>	Ultrasonic-assisted self-assembly	95% RhB degradation in 80 min	—	9
WO <sub>3</sub> /Ag/CN	Solvent evaporation and <i>in situ</i> calcination	96.2% RhB degradation in 40 min; ~90% TC degradation in 140 min	—	10
WO <sub>3</sub> /CNT/g-C <sub>3</sub> N <sub>4</sub>	Wet impregnation	92.3% MO degradation in 60 min	H <sub>2</sub> production	11
Pt-g-C <sub>3</sub> N <sub>4</sub> /H-WO <sub>3</sub>	Post-annealing	—	H <sub>2</sub> production	12
WO <sub>3</sub> /RGO/H-g-C <sub>3</sub> N <sub>4</sub>	Microwave-assisted hydrothermal method	~90% TC-HCl degradation in 60 min	—	13
WO <sub>3</sub> /g-C <sub>3</sub> N <sub>4</sub>	<i>In situ</i> construction	~100% RhB degradation in 40 min	—	14
Pt-WO <sub>3</sub> /g-C <sub>3</sub> N <sub>4</sub>	Reverse microemulsion	—	H <sub>2</sub> production	15
g-C <sub>3</sub> N <sub>4</sub> /Si-O/WO <sub>3</sub>	Wet chemical method	—	Aerobic alcohol oxidation	16
WO <sub>3</sub> /g-C <sub>3</sub> N <sub>4</sub>	<b>Rapid calcination</b>	<b>79.1% TC-HCl, 91.4% MB and 49.6% MO degradation in 100 min, respectively;</b> <b>~100% RhB degradation in 20 min</b>	<b>Nitrogen fixation (NNR and NOR)</b>	<b>This work</b>



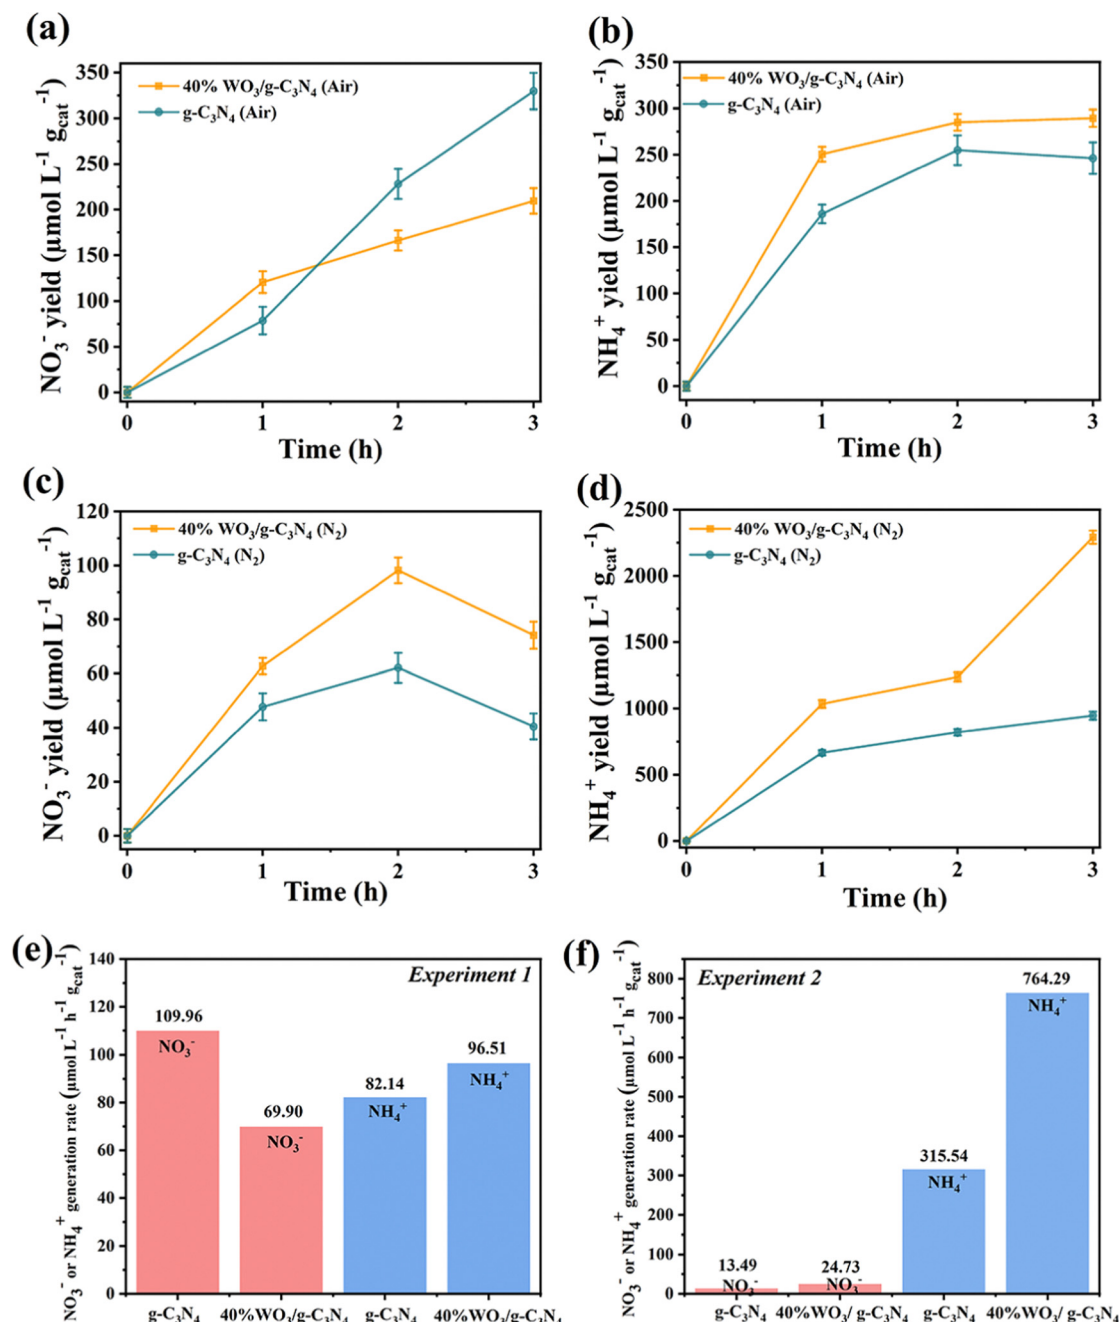

**Fig. 8** Photocatalytic nitrogen fixation performance of 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> and g-C<sub>3</sub>N<sub>4</sub>: (a) the yield of NO<sub>3</sub><sup>-</sup> in experiment 1, (b) the yield of NH<sub>4</sub><sup>+</sup> in Experiment 1, (c) the yield of NO<sub>3</sub><sup>-</sup> in experiment 2, and (d) the yield of NH<sub>4</sub><sup>+</sup> in Experiment 2. Error bars represent the standard deviation of three independent experiments. (e) The 3 h average NO<sub>3</sub><sup>-</sup> or NH<sub>4</sub><sup>+</sup> generation rate in Experiment 1 of g-C<sub>3</sub>N<sub>4</sub> and 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub>, and (f) the 3 h average NO<sub>3</sub><sup>-</sup> or NH<sub>4</sub><sup>+</sup> generation rate in Experiment 2 of g-C<sub>3</sub>N<sub>4</sub> and 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub>.

### Photocatalytic nitrogen fixation performance

Fig. 8(a), (b) and (e) show the generation of NO<sub>3</sub><sup>-</sup> and NH<sub>4</sub><sup>+</sup> in Experiment 1. As shown in Fig. 8(a), when the air was introduced into the aqueous suspension of 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> under Xenon lamp irradiation, the NO<sub>3</sub><sup>-</sup> concentration increased with the increase of the reaction time. After 1 h, the NO<sub>3</sub><sup>-</sup> yield decreased, and the amount of the NO<sub>3</sub><sup>-</sup> yield was lower than that of pure g-C<sub>3</sub>N<sub>4</sub>. As shown in Fig. 8(b), the yield of NH<sub>4</sub><sup>+</sup> first increased for 1 h and then gradually stabilized. At the same

time, the yield was always higher than that of pure g-C<sub>3</sub>N<sub>4</sub>. Fig. 8(e) shows that the 3 h average NO<sub>3</sub><sup>-</sup> yield of 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> was 69.90 μmol L<sup>-1</sup> h<sup>-1</sup> g<sub>cat</sub><sup>-1</sup>, and the 3 h average NH<sub>4</sub><sup>+</sup> yield was 96.51 μmol L<sup>-1</sup> h<sup>-1</sup> g<sub>cat</sub><sup>-1</sup>. Unlike pure g-C<sub>3</sub>N<sub>4</sub>, the yield of the nitrogen fixed product NO<sub>3</sub><sup>-</sup> in the N<sub>2</sub> disproportionation reaction of 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> was lower than that of NH<sub>4</sub><sup>+</sup>. The total nitrogen fixation efficiency of 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> was 166.41 μmol L<sup>-1</sup> h<sup>-1</sup> g<sub>cat</sub><sup>-1</sup>, which was lower than that of pure g-C<sub>3</sub>N<sub>4</sub> (192.10 μmol L<sup>-1</sup> h<sup>-1</sup> g<sub>cat</sub><sup>-1</sup>). Therefore, the



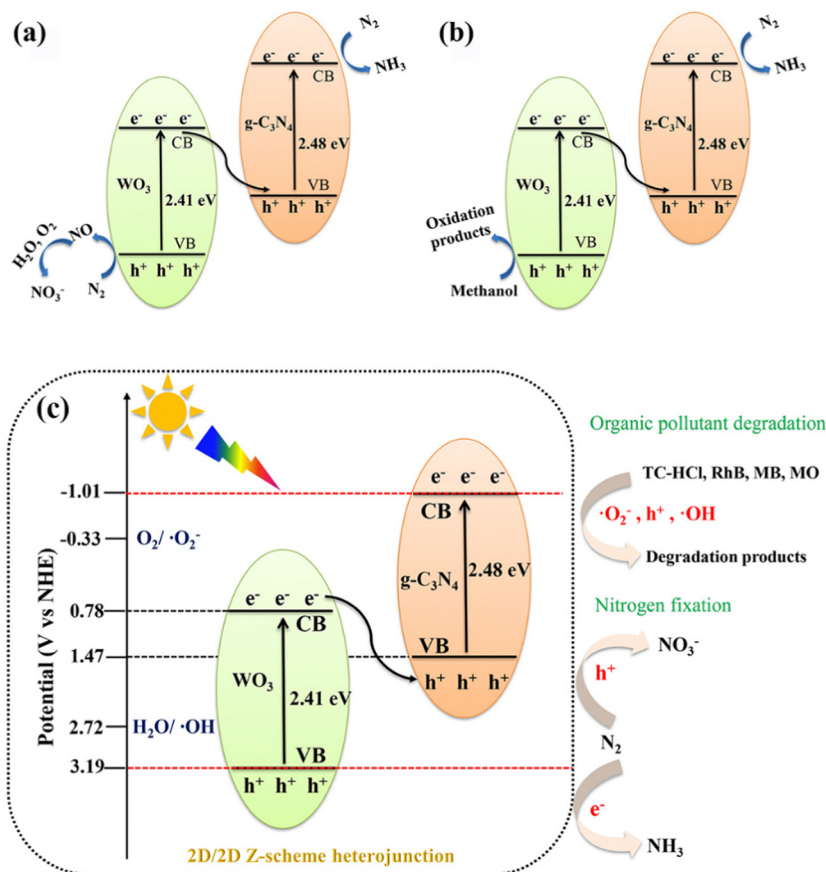


Fig. 9 The proposed photocatalytic nitrogen fixation mechanism of 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub>: (a) Experiment 1 and (b) Experiment 2; and (c) the proposed photocatalytic mechanism of the 2D/2D Z-scheme WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunctions in this work.

nitrogen disproportionation reaction efficiency of 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> in Experiment 1 was lower than that of pure g-C<sub>3</sub>N<sub>4</sub> and the NRR accounted for a larger proportion in the disproportionation reaction.

The generation of NO<sub>3</sub><sup>-</sup> and NH<sub>4</sub><sup>+</sup> in Experiment 2 is shown in Fig. 8(c), (d) and (f). When N<sub>2</sub> was introduced into a 20% methanol (as hole scavenger) aqueous suspension containing 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> under Xenon lamp irradiation, the NO<sub>3</sub><sup>-</sup> yield first increased and then decreased (Fig. 8(c)). In the 2 hours, a small amount of NO<sub>3</sub><sup>-</sup> was produced due to the removal of h<sup>+</sup>. After 2 hours, the e<sup>-</sup> reduce NO<sub>3</sub><sup>-</sup> and the NO<sub>3</sub><sup>-</sup> yield decreased. For Fig. 8(d), the NH<sub>4</sub><sup>+</sup> yield continued to increase. In addition, the NH<sub>4</sub><sup>+</sup> yield of 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> was 2.37 times higher than that of pure g-C<sub>3</sub>N<sub>4</sub>. Fig. 8(f) shows that the 3 h average NO<sub>3</sub><sup>-</sup> yield of 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> was 24.73 μmol L<sup>-1</sup> h<sup>-1</sup> g<sub>cat</sub><sup>-1</sup>, and the 3 h average NH<sub>4</sub><sup>+</sup> yield was 764.29 μmol L<sup>-1</sup> h<sup>-1</sup> g<sub>cat</sub><sup>-1</sup>. NH<sub>4</sub><sup>+</sup> was the main nitrogen fixation product. The total nitrogen fixation efficiency of 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> (789.02 μmol L<sup>-1</sup> h<sup>-1</sup> g<sub>cat</sub><sup>-1</sup>) was 2.40 times higher than that of the g-C<sub>3</sub>N<sub>4</sub> nanosheets (329.03 μmol L<sup>-1</sup> h<sup>-1</sup> g<sub>cat</sub><sup>-1</sup>). Experiment 2 showed that 40% WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> enhanced the NRR.

### Photocatalytic nitrogen fixation mechanism

A photocatalytic nitrogen fixation mechanism based on the 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> Z-scheme heterojunction was proposed, as

shown in Fig. 9(a) and (b). Under light irradiation, 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> generated photogenerated electron-hole (e<sup>-</sup>-h<sup>+</sup>) pairs on VB. Then, e<sup>-</sup> was transferred from VB to CB while leaving h<sup>+</sup> on VB. In Experiment 1 (Fig. 9(a)), the photogenerated e<sup>-</sup> on VB can be transferred to the surface *via* nitrogen vacancies. Then, e<sup>-</sup> can reduce N<sub>2</sub> (in the incoming air) to NH<sub>3</sub>. At the same time, the remaining photogenerated h<sup>+</sup> in VB can oxidize N<sub>2</sub> (in the incoming air) to NO. Then, NO further reacts with O<sub>2</sub> and H<sub>2</sub>O to generate NO<sub>3</sub><sup>-</sup>.<sup>31,34</sup>

In Experiment 1, N<sub>2</sub> underwent a disproportionation reaction to generate NH<sub>4</sub><sup>+</sup> and NO<sub>3</sub><sup>-</sup>. It has been reported that the disproportionation reactions are energetically more favorable than the individual oxidation or reduction reactions.<sup>31</sup> According to the law of charge conservation, the ratio of NO<sub>3</sub><sup>-</sup> to NH<sub>4</sub><sup>+</sup> generated in the N<sub>2</sub> dismutation reaction should be 3 : 5.<sup>31</sup> Nevertheless, the actual ratio of NO<sub>3</sub><sup>-</sup> to NH<sub>4</sub><sup>+</sup> is closer to 5 : 7. The slightly lower proportion of NH<sub>4</sub><sup>+</sup> is due to the competition from the hydrogen evolution reaction (HER). In Experiment 1, 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> with the Z-scheme heterojunction was not more effective than pure g-C<sub>3</sub>N<sub>4</sub>. This is because g-C<sub>3</sub>N<sub>4</sub> is beneficial to the adsorption and activation of N<sub>2</sub>, and the active ingredient of 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> is mainly on the VB of WO<sub>3</sub>. The adsorbed and activated N<sub>2</sub> on g-C<sub>3</sub>N<sub>4</sub> is far from h<sup>+</sup>, which results in reduced NOR efficiency.

However, in Experiment 2 (Fig. 9(b)), the photogenerated h<sup>+</sup> was consumed by the hole sacrifice agent, which highlighted



the advantage of the 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> Z-scheme heterojunction. A large amount of photogenerated e<sup>-</sup> could reduce N<sub>2</sub> to NH<sub>3</sub> and improve the NRR reaction efficiency. Therefore, 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> is suitable for photocatalytic nitrogen fixation, reducing N<sub>2</sub> to ammonia. The reaction conditions of nitrogen fixation have a great influence on the reaction products of nitrogen fixation.

## Conclusions

A series of 2D/2D Z-scheme WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> heterojunctions were prepared by facile rapid calcination, and the degradation effect of different WO<sub>3</sub> ratios on the typical antibiotic organic contaminant TC-HCl was explored. The photocatalytic degradation effect of 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> is 1.69, 1.31 and 6.89 times higher than that of bulk g-C<sub>3</sub>N<sub>4</sub>, g-C<sub>3</sub>N<sub>4</sub> and WO<sub>3</sub> nanosheets, respectively. The removal efficiency of RhB, MB and MO were 100%, 91.4% and 49.6%, respectively. The main reactive species of 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> in the degradation process was •O<sub>2</sub><sup>-</sup>. The 2D/2D Z-scheme WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> can realize photocatalytic nitrogen fixation. With the presence of a hole sacrifice agent and N<sub>2</sub> as the nitrogen source, the photocatalytic nitrogen fixation reaction of 40%WO<sub>3</sub>/g-C<sub>3</sub>N<sub>4</sub> was dominated by NRR, and the almost all product was NH<sub>4</sub><sup>+</sup> (764.29 μmol L<sup>-1</sup> h<sup>-1</sup> g<sub>cat</sub><sup>-1</sup>). The total nitrogen fixation efficiency was 2.40 times higher than that of pure g-C<sub>3</sub>N<sub>4</sub>. The results prove that the 2D/2D Z-scheme heterojunction enhanced the photogenerated electron-hole separation and transfer ability, which is very effective in both photocatalytic degradation and photocatalytic nitrogen fixation application scenarios (Fig. 9(c)). This work provides a reference for understanding the 2D/2D Z-scheme heterojunctions, photocatalytic NRR and NOR reactions, and the photocatalytic degradation process of antibiotics and organic pollutants with different charge properties.

## Author contributions

Yasi Li contributed to the experimental design, investigation, validation, and writing of the original draft. Junkai Wang performed the conceptualization, methodology, investigation, visualization, and funding acquisition.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

This work was funded by the Special Program for Science Research Foundation of the Higher Education Institutions of Guangdong Province (grant no. 2020ZDZX2052), and the Shantou University Scientific Research Foundation for Talents (grant no. NTF22004).

## References

- 1 J. Bai, R. Shen, Z. Jiang, P. Zhang, Y. Li and X. Li, *Chin. J. Catal.*, 2022, **43**, 359–369.
- 2 Y. Hu, X. Li, W. Wang, F. Deng, L. Han, X. Gao, Z. Feng, Z. Chen, J. Huang, F. Zeng and F. Dong, *Chin. J. Struct. Chem.*, 2022, **41**, 2206069.
- 3 G. M. Li, B. Wang and R. Wang, *Chin. J. Struct. Chem.*, 2020, **39**, 1675–1688.
- 4 Z. Jin, Y. Li and X. Hao, *Acta Phys.-Chim. Sin.*, 2021, **37**, 1912033.
- 5 X. Li, B. Wang, W. Yin, J. Di, J. Xia, W. Zhu and H. Li, *Acta Phys.-Chim. Sin.*, 2020, **36**, 17401.
- 6 L. Huang, H. Xu, Y. Li, H. Li, X. Cheng, J. Xia, Y. Xu and G. Cai, *Dalton Trans.*, 2013, **42**, 8606–8616.
- 7 Y. Y. Zhou, J. X. Zhang and D. F. Wu, *ChemistrySelect*, 2023, **8**, e202301237.
- 8 K. He, J. Xie, X. Luo, J. Wen, S. Ma, X. Li, Y. Fang and X. Zhang, *Chin. J. Catal.*, 2017, **38**, 240–252.
- 9 L. Li, D. Jiang, X. Wu, X. Sun, X. Qu, L. Shi and F. Du, *J. Mater. Sci.*, 2020, **55**, 4238–4250.
- 10 J. Chen, X. Xiao, Y. Wang and Z. Ye, *Appl. Surf. Sci.*, 2019, **467–468**, 1000–1010.
- 11 U. Bharagav, N. R. Reddy, V. N. K. Rao, P. Ravi, M. Sathish, D. Rangappa, K. Prathap, C. S. Chakra, M. V. Shankar, L. Appels, T. M. Aminabhavi, R. R. Kakarla and M. M. Kumari, *Chemosphere*, 2023, **311**, 137030.
- 12 D. Liu, S. Zhang, J. Wang, T. Peng and R. Li, *ACS Appl. Mater. Interfaces*, 2019, **11**, 27913–27923.
- 13 Y. Bao, H. Guo, L. Jiang, Z. Liu, J. Qu, C. Zhang, X. Jia and K. Chen, *Appl. Surf. Sci.*, 2019, **496**, 143639.
- 14 H. Zhang, Z. Cai, W. Xu, M. Huang and X. Liu, *New J. Chem.*, 2019, **43**, 17416.
- 15 S. Tang, Y. Ma, H. Wang, Y. Liang, X. Xu, D. Zhang, B. Cao, Q. Wang and W. Li, *ChemSusChem*, 2023, **16**, e202202184.
- 16 L. Sun, B. Li, X. Chu, N. Sun, Y. Qu, X. Zhang, I. Khan, L. Bai and L. Jing, *ACS Sustainable Chem. Eng.*, 2019, **7**, 9916–9927.
- 17 Z. B. Wu, X. Z. Yuan, J. Zhang, H. Wang, L. B. Jiang and G. M. Zeng, *ChemCatChem*, 2017, **9**, 41–64.
- 18 E. Forgacs, T. Cserhati and G. Oros, *Environ. Int.*, 2004, **30**, 953–971.
- 19 X. R. Yang, Z. Chen, W. Zhao, C. X. Liu, X. X. Qian, M. Zhang, G. Y. Wei, E. Khan, Y. H. Ng and Y. S. Ok, *Chem. Eng. J.*, 2021, **405**, 126806.
- 20 H. Yang, Z. C. Zhao, Y. P. Yang, Z. Zhang, W. Chen, R. Q. Yan, Y. X. Jin and J. Zhang, *Sep. Purif. Technol.*, 2022, **300**, 121846.
- 21 Y. X. Li, M. Fu, R. Q. Wang, S. W. Wu and X. M. Tan, *Chem. Eng. J.*, 2022, **444**, 136567.
- 22 J. Guo, T. T. Liu, H. Peng and X. G. Zheng, *Int. J. Mol. Sci.*, 2022, **23**, 9343.
- 23 F. D. Wu, J. C. Chen and J. P. Hu, *J. Environ. Chem. Eng.*, 2022, **10**, 107117.
- 24 S. Krobthong, T. Rungsawang and S. Wongrerkdee, *Toxics*, 2023, **11**, 266.
- 25 G. H. Dong, W. K. Ho and C. Y. Wang, *J. Mater. Chem. A*, 2015, **3**, 23435–23441.



- 26 J. H. Yang, H. Y. Bai, Y. Z. Guo, H. Zhang, R. B. Jiang, B. C. Yang, J. F. Wang and J. C. Yu, *Angew. Chem., Int. Ed.*, 2021, **60**, 927–936.
- 27 P. F. Xia, X. C. Pan, S. L. Jiang, J. G. Yu, B. W. He, P. M. Ismail, W. Bai, J. J. Yang, L. Yang, H. H. Zhang, M. Cheng, H. Y. Li, Q. Zhang, C. Xiao and Y. Xie, *Adv. Mater.*, 2022, **34**, 2200563.
- 28 M. Cheng, C. Xiao and Y. Xie, *J. Mater. Chem. A*, 2019, **7**, 19616–19633.
- 29 N. Cherkasov, A. O. Ibhadon and P. Fitzpatrick, *Chem. Eng. Process.*, 2015, **90**, 24–33.
- 30 X. Z. Chen, N. Li, Z. Z. Kong, W. J. Ong and X. J. Zhao, *Mater. Horiz.*, 2018, **5**, 9–27.
- 31 W. J. Ren, Z. W. Mei, S. S. Zheng, S. N. Li, Y. M. Zhu, J. X. Zheng, Y. Lin, H. B. Chen, M. Gu and F. Pan, *Research*, 2020, **2020**, 3750314.
- 32 Y. T. Wang, Y. F. Yu, R. R. Jia, C. Zhang and B. Zhang, *Natl. Sci. Rev.*, 2019, **6**, 730–738.
- 33 X. B. Chen, L. Liu, P. Y. Yu and S. S. Mao, *Science*, 2011, **331**, 746–750.
- 34 H. Tong, S. X. Ouyang, Y. P. Bi, N. Umezawa, M. Oshikiri and J. H. Ye, *Adv. Mater.*, 2012, **24**, 229–251.
- 35 X. C. Wang, K. Maeda, A. Thomas, K. Takanebe, G. Xin, J. M. Carlsson, K. Domen and M. Antonietti, *Nat. Mater.*, 2009, **8**, 76–80.
- 36 W. J. Ong, L. L. Tan, Y. H. Ng, S. T. Yong and S. P. Chai, *Chem. Rev.*, 2016, **116**, 7159–7329.
- 37 R. B. Xu, M. H. Su, Y. H. Liu, Z. B. Chen, C. Ji, M. L. Yang, X. Y. Chang and D. Y. Chen, *J. Cleaner Prod.*, 2020, **242**, 118366.
- 38 Y. S. Li, M. R. Ti, Z. Q. Li, Y. Zhang, L. Wu and Y. J. He, *J. Mater. Sci.: Mater. Electron.*, 2021, **32**, 2268–2282.
- 39 T. T. Xiao, Z. Tang, Y. Yang, L. Q. Tang, Y. Zhou and Z. G. Zou, *Appl. Catal., B*, 2018, **220**, 417–428.
- 40 Y. J. Xue, Y. C. Guo, Z. G. Liang, H. Z. Cui and J. Tian, *J. Colloid Interface Sci.*, 2019, **556**, 206–213.
- 41 Y. Li, M. Ti, D. Zhao, Y. Zhang, L. Wu and Y. He, *J. Alloys Compd.*, 2021, **870**, 159298.
- 42 Y. T. Xiao, G. H. Tian, W. Li, Y. Xie, B. J. Jiang, C. G. Tian, D. Y. Zhao and H. G. Fu, *J. Am. Chem. Soc.*, 2019, **141**, 2508–2515.
- 43 Y. J. Xue, X. K. Kong, Y. C. Guo, Z. Q. Liang, H. Z. Cui and J. Tian, *J. Materiomics*, 2020, **6**, 128–137.
- 44 X. Chen, J. Y. Li, Z. R. Tang and Y. J. Xu, *Catal. Sci. Technol.*, 2020, **10**, 6098–6110.
- 45 V. Luxmi and A. Kumar, *Mater. Sci. Semicond. Process.*, 2019, **104**, 104690.
- 46 S. Prabhu, S. Manikumar, L. Cindrella and O. J. Kwon, *Mater. Sci. Semicond. Process.*, 2018, **74**, 136–146.
- 47 W. Yu, J. Chen, T. Shang, L. Chen, L. Gu and T. Peng, *Appl. Catal., B*, 2017, **219**, 693–704.
- 48 J. Meng, X. Wang, Y. Liu, M. Ren, X. Zhang, X. Ding, Y. Guo and Y. Yang, *Chem. Eng. J.*, 2021, **403**, 126354.
- 49 H. Yu, R. Shi, Y. Zhao, T. Bian, Y. Zhao, C. Zhou, G. I. N. Waterhouse, L. Z. Wu, C. H. Tung and T. Zhang, *Adv. Mater.*, 2017, **29**, 1605148.
- 50 J. Fu, Q. Xu, J. Low, C. Jiang and J. Yu, *Appl. Catal., B*, 2019, **243**, 556–565.
- 51 Y. Wang, X. Di, X. Wu and X. Li, *J. Alloys Compd.*, 2020, **846**, 156215.
- 52 W. Ho, Z. Zhang, W. Lin, S. Huang, X. Zhang, X. Wang and Y. Huang, *ACS Appl. Mater. Interfaces*, 2015, **7**, 5497–5505.
- 53 Y. Quan, M. Liu, H. Wu, X. Tian, L. Dou and Z. Wang, *Appl. Surf. Sci.*, 2024, **642**, 158601.
- 54 S. Chen, Y. Hu, S. Meng and X. Fu, *Appl. Catal., B*, 2014, **150**, 564–573.
- 55 X. Liu, A. Jin, Y. Jia, T. Xia, C. Deng, M. Zhu, C. Chen and X. Chen, *Appl. Surf. Sci.*, 2017, **405**, 359–371.
- 56 M. Chatterjee, M. Mondal, T. Sukul, K. Ghosh and S. K. Pradhan, *J. Ind. Eng. Chem.*, 2023, **127**, 390–405.
- 57 S. Zwane, D. S. Dlamini, B. B. Mamba and A. T. Kuvarega, *Inorg. Chem. Commun.*, 2023, **151**, 110637.
- 58 M. Lv, H. Wang and H. Shi, *Colloids Surf., A*, 2023, **679**, 132579.
- 59 C. Mrabet, R. Jaballah, N. Mahdhi, A. Boukhachem and M. Amlouk, *J. Alloys Compd.*, 2023, **968**, 172252.
- 60 K. Li, J. Zhu, W. Zhou, L. Sun and S. Tian, *J. Alloys Compd.*, 2023, **968**, 171955.
- 61 L. Zhang, J. Qiu, G. Xia, D. Dai, X. Zhong and J. Yao, *J. Mater. Sci. Technol.*, 2023, **138**, 214–220.
- 62 X. Mo, X. Zhang, B. Lin, C. Ning, M. Li, H. Liao, Z. Chen and X. Wang, *J. Mater. Sci. Technol.*, 2023, **145**, 174–184.

