

# Polymer Chemistry

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: N. Braidi, A. Hernández, G. Scurani, F. Parenti, N. Badi and F. E. Du Prez, *Polym. Chem.*, 2024, DOI: 10.1039/D5PY00098J.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

# Synthesis of Triamine-Functionalized Rigid Crosslinkers for Material Science

*Niccolò Braidì,<sup>1\*</sup> Aitor Hernández,<sup>2</sup> Giulia Scurani,<sup>1</sup> Francesca Parenti,<sup>1</sup> Nezha Badf,<sup>2</sup> Filip E. Du Prez<sup>2\*</sup>*

<sup>1</sup> Department of Chemical and Geological Sciences, University of Modena and Reggio Emilia, via Campi 103, 41125, Modena, Italy

<sup>2</sup> Polymer Chemistry Research Group, Centre of Macromolecular Chemistry, Department of Organic and Macromolecular Chemistry, Faculty of Sciences, Ghent University, Krijgslaan 281 (S4), 9000 Ghent, Belgium

E-mails: [niccolo.braidì2@unibo.it](mailto:niccolo.braidì2@unibo.it); [filip.duprez@ugent.be](mailto:filip.duprez@ugent.be)

## KEYWORDS

Crosslinkers, Amines, ARGET ATRP, Styrene, Vinylogous Urethanes



## ABSTRACT

In this study, a primary amine-terminated star-shaped polystyrene (PS) was synthesized using an Activators Regenerated by Electron Transfer Atom Transfer Radical Polymerization (ARGET ATRP) protocol, yielding products with low dispersity ( $< 1.2$ ) and molar masses in the range of 2 to 12 kDa. The influence of the trifunctional initiator's reactivity on the resulting polymer topology was investigated. The bromo-terminated PS was efficiently converted to its azide-terminated counterpart as confirmed by online ATR FT-IR and NMR spectroscopy. The targeted amine-terminated PS was then obtained by a Staudinger reduction of the azide groups using tributylphosphine. To assess the applicability of these novel amine-terminated PS as well-defined trifunctional crosslinking agents, traditional epoxy thermoset networks and covalent adaptable networks (CANs) were synthesized using diepoxides or diacetoacetates, respectively. The resulting materials exhibited excellent thermal resistance, attributed to the high PS-content. Moreover, by making use of the option to tune the molar mass of such macromolecular crosslinkers, the network's crosslinking density could be tailored, enabling control over swelling degree, glass transition temperature, and, in the case of the obtained vinylogous urethane vitrimers, even reprocessability.



## INTRODUCTION

The role of amines in material science is prevalent, with applications spanning catalysis,<sup>1,2</sup> epoxy thermoset materials,<sup>3</sup> surface modification,<sup>4,5</sup> and carbon capture,<sup>6,7</sup> to name a few. Particularly in the field of polymer science, following the discovery of covalent adaptable networks (CANs),<sup>8-11</sup> multifunctional amine-terminated (macro)molecules have become crucial in the development of recyclable crosslinked materials based on various exchange chemistries. These include vinylogous urethanes,<sup>12-14</sup> dicarboxamide-imide,<sup>15,16</sup> imine-based,<sup>17-19</sup> and  $\beta$ -amino ester chemistries.<sup>20-22</sup> As a result, there is a considerable interest in creating novel multifunctional amines for their use as rigid crosslinkers in material science and replace for example the widely used tris(2-aminoethyl)amine (TREN) containing a tertiary amine moiety.

Given the ability of Atom Transfer Radical Polymerization (ATRP) to precisely control the macromolecular architecture<sup>23,24</sup> and, consequently, the mechanical properties of polymers, it is not surprising that the design of primary amine-terminated polymers derived from this technique has been widely investigated. This is particularly evident in the following examples, which summarize attempts to introduce amines at the polymer chain ends and highlight some of the challenges encountered in achieving these goals. Coessens and Matyjaszewski reported an unsuccessful attempt to obtain primary amine-terminated poly(methyl acrylate) by reacting the bromo-terminated precursor with ammonia.<sup>25</sup> In contrast, an excess of diamines (*e.g.*, hexamethylenediamine) reacted quantitatively, though this resulted in chain ends bearing both primary and secondary amine functionalities.<sup>26,27</sup> Another approach involves Gabriel's synthesis,




starting with nucleophilic substitution using potassium phthalimide, followed by cleavage via acid hydrolysis (or hydrazine in the Ing-Manske variant) to release the primary amine. Using this method, Monge *et al.* and subsequent researchers observed quantitative conversion on bromo-terminated polymers.<sup>28-33</sup> However, Postma *et al.* reported that  $\beta$ -elimination competed with nucleophilic substitution, decreasing the chain-end functionality of the heterotelechelic polystyrene employed.<sup>34, 35</sup> Furthermore, Weimer *et al.* tested the Ing-Manske procedure on hyperbranched polystyrene but encountered crosslinking, attributed to nucleophilic displacement of residual halides by the newly formed primary amines.<sup>36</sup> Another approach, offering arguably higher atom economy (depending on the reducing agent used), less harmful reagents than the Ing-Manske variant, and reduced susceptibility to  $\beta$ -elimination, involved the replacement of halogenated chain ends with azides (using sodium azide<sup>37-44</sup> or trimethylsilyl azide<sup>38, 45, 46</sup>), followed by reduction to obtain primary amine chain ends. While the first step has been frequently reported in the literature due to its use in azide-alkyne Huisgen cycloaddition,<sup>47, 48</sup> fewer reports describe the reduction of azide-terminated polymers. Matyjaszewski *et al.* reported the quantitative reduction of both heterotelechelic and telechelic azide-terminated polystyrene using  $\text{LiAlH}_4$ .<sup>45</sup> However, they observed gelation of the reaction mixture during the reduction of telechelic polymers, necessitating a larger solvent volume to complete the reaction. Given the drawbacks of the aforementioned procedures, the Staudinger reduction of azide-terminated polymers with triphenylphosphine, initially proposed by Coessens *et al.*, has been more widely applied.<sup>2, 41, 46</sup> The primary amine-terminated polymers obtained through this method have been used in copolymerizations,<sup>49</sup> (bio)conjugation,<sup>50</sup> membrane fabrication for (nano)filtration,<sup>31</sup> and catalyst



production.<sup>2</sup> However, to the best of our knowledge, they have not yet been tested as crosslinking agents.

Therefore, the objective of this study is twofold. First, the development of a synthetic pathway for rigid, star-shaped amino-terminated polystyrenes with variable molar mass (trisAminoPS). Second, the evaluation of these products as crosslinkers in both conventional epoxy networks and CANs (**Figure 1**).

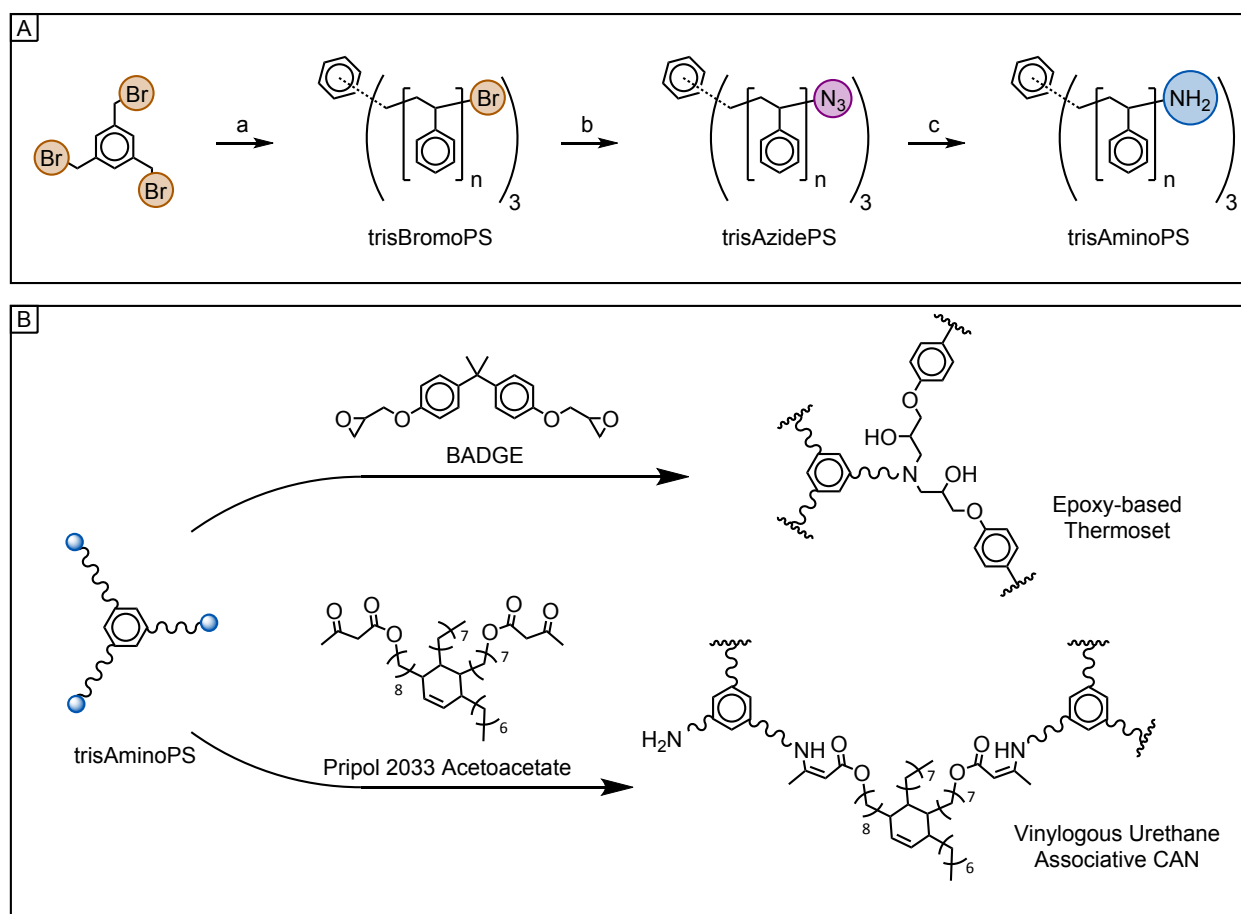

**Figure 1.** Overview of the reactions explored. **A)** Synthetic pathway yielding trifunctional primary amine-terminated polystyrene: **a)** ARGET ATRP of styrene initiated by 1,3,5-tris(bromomethyl)benzene, **b)** nucleophilic substitution with sodium azide, **c)** Staudinger reduction with tributylphosphine and water. **B)** Crosslinking process using bisphenol A diglycidyl ether



(BADGE) or Pripol 2033 acetoacetate to form a traditional epoxy-based network or a vinylogous urethane CAN, respectively.

The proposed synthetic pathway begins with the Activators Regenerated by Electron Transfer (ARGET)<sup>51-53</sup> ATRP of styrene using a trifunctional brominated initiator (1,3,5-tris(bromomethyl)benzene) for the design of trifunctional bromo-terminated polystyrenes (trisBromoPS) with inherently high glass transition temperature ( $T_g$ ). This is followed by nucleophilic substitution with sodium azide to yield trisAzidePS, and subsequent Staudinger reduction with tributylphosphine to obtain the trifunctional primary amine-terminated polystyrenes (trisAminoPS, **Figure 1A**). The latter macromolecular structures are then reacted with a diepoxide or a diacetoacetate electrophilic compound to form the targeted networks (**Figure 1B**).


## RESULTS AND DISCUSSION

The choice of ARGET among the advanced ATRP techniques<sup>54-58</sup> relies in the possibility to use mild organic bases such as 2,4,6-trimethylpyridine, in combination with a lipophilic derivative of ascorbic acid (5,6-isopropylidene-L-ascorbic acid). This allows precise tuning of the concentration of radicals, as discussed in a previous study,<sup>51</sup> which is crucial to minimize radical-radical termination reactions that could lead to branched or even crosslinked products when using a trifunctional initiator.<sup>59-61</sup> Since our previously reported reaction conditions were optimized for chlorinated initiators, some modifications were necessary to adapt them for brominated initiators, which yield more readily functionalizable polymers.<sup>62</sup> Specifically, the solvent was changed to anisole (instead of an ethyl acetate/ethanol solution) to prevent nucleophilic substitution of the ethoxide anion — generated in small quantities by ethanol in basic environment — on the more



labile brominated chain-ends.<sup>52</sup> Additionally, due to the altered polarity of the reaction mixture and thus to address solubility, a more lipophilic ligand, 4,4'-dinonyl-2,2'-dipyridyl, was employed instead of the previously used tris(2-pyridylmethyl)amine ligand.

By varying the amount of initiator used, a series of polymers with different chain lengths has been synthesized, by employing a volume of styrene ( $V_{\text{styrene}}$ ) of 20 mL. The number-average molar mass determined by gel permeation chromatography ( $M_n^{\text{GPC}}$ ) were found to closely match the targeted theoretical values ( $M_n^{\text{th}}$ ), as reported in **Table 1**. Note that the linear fit of  $M_n^{\text{GPC}}$  has a slope slightly lower than unity, leading to significant discrepancies between the two values at higher molar masses (**Figure 2A**).

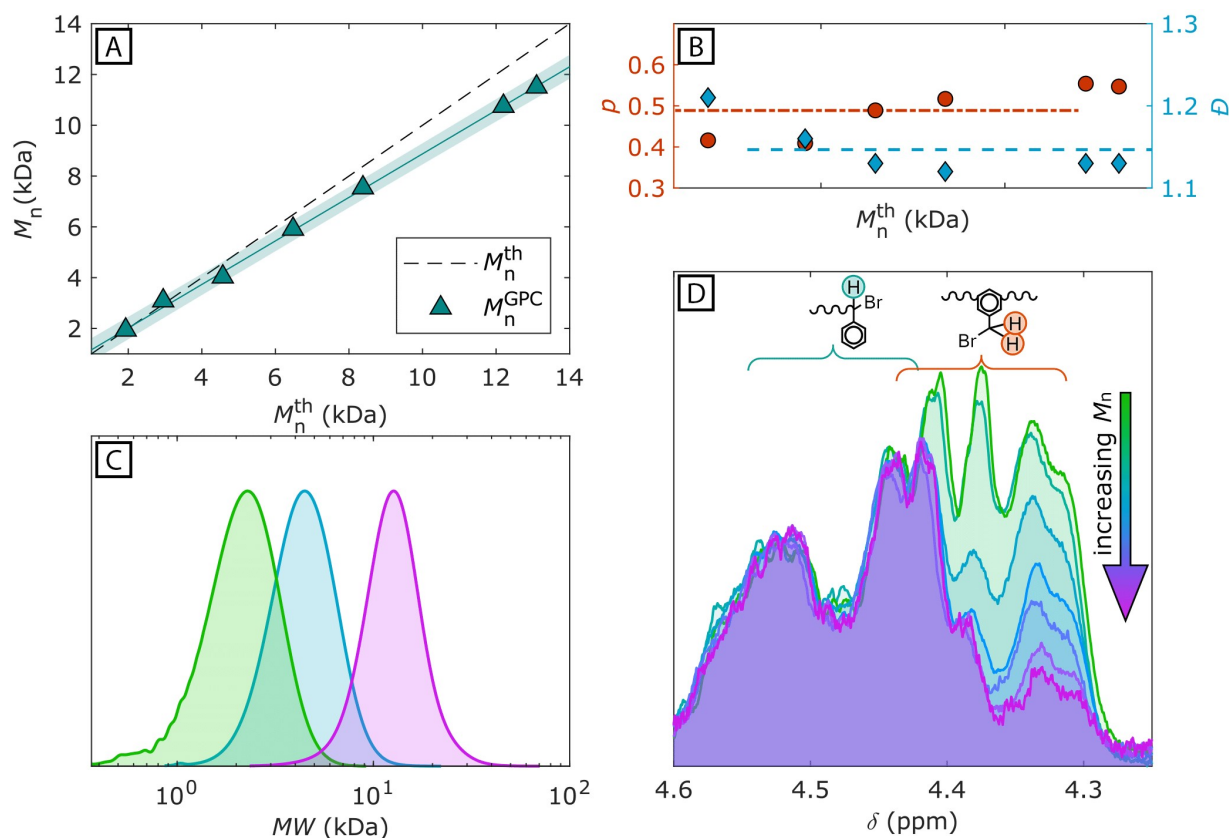

**Figure 2.** Characterizations of trisBromoPSs obtained via the ARGET ATRP of styrene initiated by 1,3,5-tris(bromomethyl)benzene. Reaction conditions:  $[\text{styrene}]_0 : [\text{CuBr}_2]/(4,4'\text{-dinonyl-2,2'-}$





dipyridyl)<sub>2</sub>]<sub>0</sub> : [5,6-isopropyl-idene-L-ascorbic acid]<sub>0</sub> : [2,6-dimethylpyridine]<sub>0</sub> = 100 : 0.0511 : 0.249 : 0.737 mol% (relative to styrene), with [1,3,5-tris(bromomethyl)benzene]<sub>0</sub> varied from 2.76 to 0.447 mol% to target different  $M_n^{\text{th}}$ ,  $V_{\text{styrene}} : V_{\text{anisole}} = 20 : 10$  v/v,  $T = 100$  °C, time = 14 h. **A**) Plot of  $M_n^{\text{GPC}}$  versus  $M_n^{\text{th}}$  (*green triangles*) with linear fitting, including the 95% confidence interval (*solid line* and *shaded area*, respectively),  $M_n^{\text{th}}$  versus  $M_n^{\text{th}}$  (*dashed line*); **B**) Plot of  $p$  versus  $M_n^{\text{th}}$  (*red circles, left ordinate*) with the mean value ( $p = 0.49$ , *red dashed line*), plot of  $\mathcal{D}$  versus  $M_n^{\text{th}}$  (*blue diamonds, right ordinate*) with the mean value ( $\mathcal{D} = 1.15$ , *blue dashed line*); **C**) MWDs of three trisBromoPSs with  $M_n = 1.94$ , 4.03, and 11.51 kDa (*green, blue, and magenta*, respectively); **D**) Overlaid <sup>1</sup>H-NMR spectra of trisBromoPSs, expanded in the  $\delta = 4.25$ -4.6 ppm region, normalized to  $\delta = 4.52$  ppm to highlight the decrease in intensity of the broad shoulder assigned to the pendant PS-Ph(CH<sub>2</sub>Br)-PS, relative to the broad peak assigned to the chain-end PS-CH(Ph)Br, as  $M_n^{\text{GPC}}$  increases.

This arises from the smaller radius of gyration of star polymers compared to the linear PS standards used for GPC calibration.<sup>63, 64</sup> Conversions ( $p$ ) higher than 0.4 were achieved, yielding products on a ten-gram scale with dispersities ( $\mathcal{D}$ ) below 1.2. Similarly low  $\mathcal{D}$  values were obtained when the reaction scale was increased fivefold, although this came at the expense of the yield (**entry 2, Table 1**). Moreover, targeting higher  $M_n^{\text{th}}$  gratifyingly resulted in higher  $p$  and lower  $\mathcal{D}$  values (**Figure 2B**). Notably, the narrow and monomodal molecular weight distributions (MWD) recorded indicate a minimal occurrence of radical-radical termination reactions, regardless of the targeted  $M_n^{\text{th}}$  (**Figure 2C**).

**Table 1.** Characterization of trisBromoPS, synthesized via the ARGET ATRP of styrene using 1,3,5-tris(bromomethyl)benzene as the initiator<sup>[a]</sup>

entry	[initiator] <sub>0</sub> (mol%)	$p$	$M_n^{\text{th}}$ [c] (kDa)	$M_n^{\text{GPC}}$ (kDa)	$\mathcal{D}$	$f$	$T_g$ (°C)
1	2.76	0.416	1.93	1.94	1.21	2.84	64.2
2 [b]	0.902	0.225	2.95	3.09	1.17	2.79	76.5
3	1.54	0.420	3.20	3.30	1.16	2.95	76.8



4	1.01	0.409	4.57	4.03	1.16	2.82	80.2
5	0.832	0.489	6.48	5.91	1.13	2.89	83.3
6	0.671	0.517	8.38	7.54	1.12	2.76	84.6
7	0.487	0.554	12.20	10.75	1.13	2.85	–
8	0.447	0.547	13.10	11.51	1.13	2.75	90.2

<sup>[a]</sup> Common conditions: [styrene]<sub>0</sub> : [CuBr<sub>2</sub>/(4,4'-dinonyl-2,2'-dipyridyl)<sub>2</sub>]<sub>0</sub> : [5,6-isopropyl-idene-L-ascorbic acid]<sub>0</sub> : [2,6-dimethylpyridine]<sub>0</sub> = 100 : 0.0511 : 0.249 : 0.737 mol% with respect to styrene,  $V_{\text{styrene}} : V_{\text{anisole}} = 20 : 10$  mL,  $T = 100$  °C,  $time = 14$  h.

<sup>[b]</sup> The amounts of monomer, solvent, and reagents were increased fivefold.

<sup>[c]</sup> Calculated with **Equation S1**.

Only a slight incidence of the expected  $\beta$ -elimination was observed, resulting in double bonds at some chain ends, as evidenced by the <sup>1</sup>H-NMR spectra (**Figure S1-S8**).<sup>34, 65, 66</sup> Consequently, across the explored  $M_n^{\text{th}}$  range, the average PS functionality ( $f$ , calculated with **Equation S3**) was found to be  $\bar{f}_{NMR} = 2.83 \pm 0.06$  instead of the ideal value of  $f = 3$ . These products do not possess perfect star-shaped structures because the bromides of 1,3,5-tris(bromomethyl)benzene are less reactive than those at the PS chain ends. This disparity arises from the fact that the bromides in the initiator are bound to primary carbons, whereas the chain-end bromides are attached to secondary carbons.<sup>67</sup> As a result, the radicals generated on the initiator are less stable than those at the chain ends, leading to incomplete arm initiation. Evidence for this is provided by the <sup>1</sup>H-NMR spectra of the trisBromoPS samples. When the spectra are overlaid and normalized at  $\delta = 4.52$  ppm, a decrease in the intensity of the broad signal attributed to the pendant PS-Ph(CH<sub>2</sub>Br)-PS, relative to the broad peak assigned to the chain-end PS-CH(Ph)Br, is apparent (**Figure 2D**). This effect becomes more pronounced at lower  $M_n^{\text{GPC}}$  values, where the



highest intensity of the PS-Ph(CH<sub>2</sub>Br)-PS signal was observed. In other words, the low  $M_n^{\text{GPC}}$  products are richer in telechelic structures with a pendant bromide in the middle compared to the desired three-arm star polymer. Accurate quantification of the three-arm star molar fraction ( $\chi_{\text{star}}$ ) is challenging due to significant overlap with the PS-CH(Ph)Br signal. However, this limitation could be readily addressed by using a more reactive initiator.<sup>67</sup>


Although the post-functionalization of bromo-terminated polystyrenes with sodium azide has been extensively reported, the procedures show a wide range of reaction times, spanning from a few<sup>38, 68</sup> to several<sup>2, 39, 41</sup> hours. Therefore, to monitor the progress of the azidation reaction, online ATR FT-IR was employed, specifically tracking the emergence of the azide stretching peak at 2096 cm<sup>-1</sup>.<sup>2, 39, 46, 69</sup> After only two hours of reaction at 30 °C, the intensity of this peak approached an asymptotic value (**Figure S9**). Quantitative conversion from bromide to azide was confirmed by <sup>1</sup>H-NMR analysis. As shown in previous studies,<sup>2, 39, 43, 45, 46</sup> the chemical shift of the chain-end methines moved up-field from 4.2–4.9 ppm for PS-CH(Ph)Br to 3.8–4.1 ppm for PS-CH(Ph)N<sub>3</sub> (**Figure S10-S16**). Notably, the peak attributed to PS-Ph(CH<sub>2</sub>N<sub>3</sub>)-PS ( $\delta = 4.1$ -4.2 ppm) was sharper and significantly less overlapped with the PS-CH(Ph)N<sub>3</sub> signal ( $\delta = 3.8$ -4.1 ppm). This assignment was further confirmed by an HSQC spectrum (**Figure S17**). Unlike the brominated precursor, this enabled the assessment of  $\chi_{\text{star}}$ , (calculated with **Equation S2**, Supplementary Information) which increased from 0.06 for the polymer with  $M_n^{\text{GPC}} = 2.22$  kDa to  $\chi_{\text{star}} = 0.80$  for the polymer with  $M_n^{\text{GPC}} = 11.20$  kDa (**Table S1**). The functionality value remained unchanged after the nucleophilic



substitution with sodium azide ( $\bar{f}_{NMR} = 2.84 \pm 0.06$ ). Additionally, the yields were consistently high for both low and high-molar mass polymers,  $\overline{yield} = (94.6 \pm 2.84)\%$ . Consequently, the  $M_n^{GPC}$  values of the azide-functionalized PS closely matched those of the brominated precursors, as reflected in the low mean percentage difference between the two,  $\overline{\Delta M_n^{GPC}} = (+3.36 \pm 5.29)\%$ .

During the final step of the proposed synthetic pathway (*i.e.*, the Staudinger reduction, step **c** in **Figure 1A**), tributylphosphine was chosen because of its reportedly lower hazard profile, ease of byproduct removal, and superior atom economy compared to the more commonly used triphenylphosphine.<sup>2, 41, 46</sup> Upon addition of the reagent to the trisAzidePS solution in THF, rapid nitrogen gas evolution was observed, corresponding to the formation of the iminophosphorane intermediate, which was subsequently cleaved upon the addition of water. As an example of this strategy, the reduction of a low-molar mass trisAzidePS (**entry 1, Table S2**) demonstrated quantitative chain-end reduction, as confirmed by <sup>1</sup>H-NMR analysis. The chemical-shift of the chain-end methines shifted up-field from  $\delta_{PS-CH(Ph)N_3} = 3.8-4.1$  ppm to  $\delta_{PS-CH(Ph)NH_2} = 3.3-3.9$  ppm (**Figure 3A**). This result was consistently observed across the entire series of triamine-functionalized PS (**Figure S18-S24**).



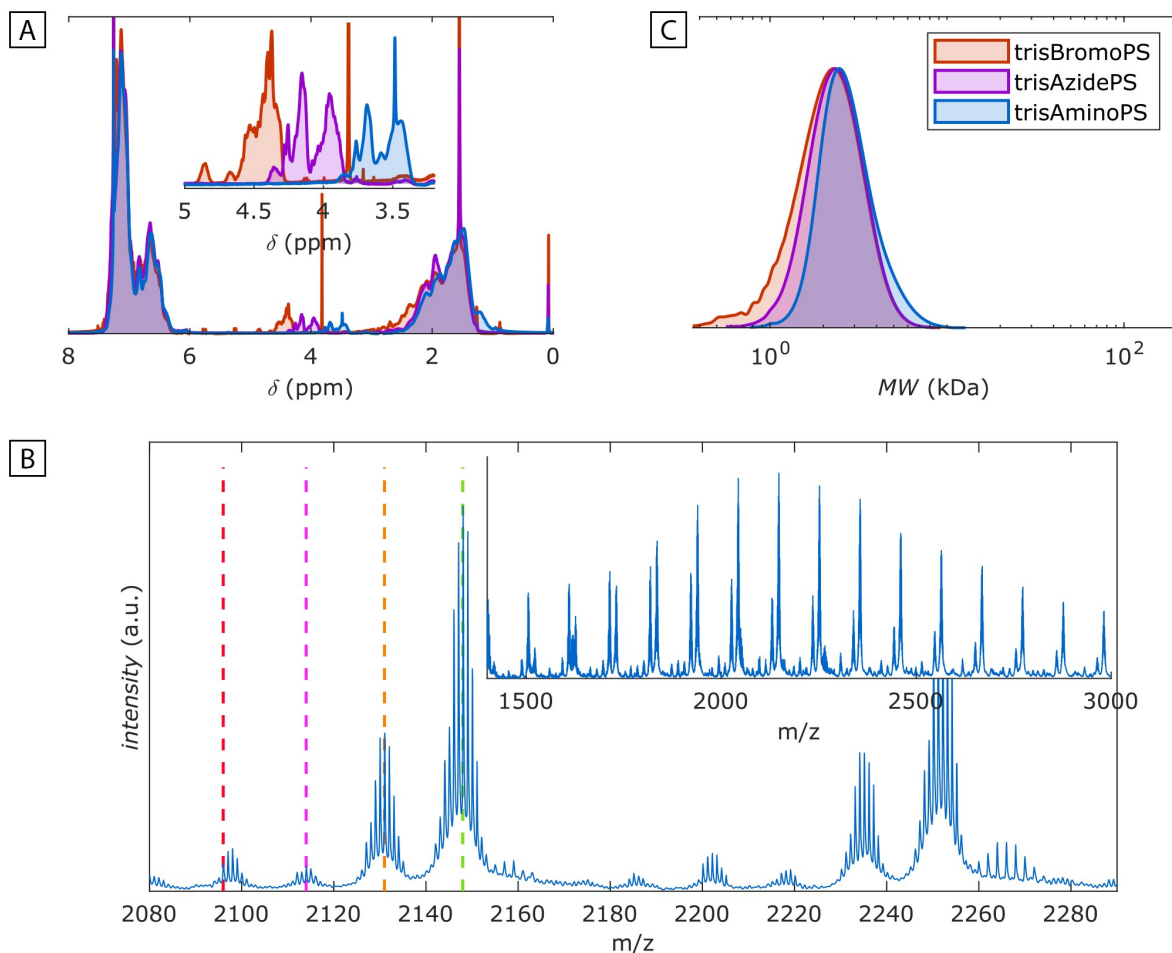

**Figure 3.** Characterization of a low-MW trisAminoPS (**entry 1, Table S2**) obtained by the reduction of trisAzidePS with tributylphosphine and water. Reaction conditions: tributylphosphine (2 eq. relative to the azide functionalities of the trisAzidePS),  $V_{\text{THF}} = 6 \text{ mL/g}$  with respect to  $w_{\text{trisAzidePS}}$ ,  $T = 60 \text{ }^\circ\text{C}$ ,  $\text{time} = 0.5 \text{ h}$ . Subsequently,  $V_{\text{H}_2\text{O}} = 0.6 \text{ mL/(g)}$  was added, and the reaction mixture was stirred at  $60 \text{ }^\circ\text{C}$  overnight. **A)** Superimposed  $^1\text{H-NMR}$  spectra of trisBromoPS (*orange*), trisAzidePS (*purple*), and trisAminoPS (*blue*). The inset highlights the chemical shift changes of the proton(s) geminal to the respective functionalities. **B)** MALDI-TOF MS spectrum of trisAminoPS measured using dithranol as the matrix and AgTFA as the ionizing salt. The main population appears at  $m/z = 2148 \pm n \cdot 104 \text{ u}$  (*green dashed line*), with progressively less intense populations observed at  $m/z = 2131$  (*orange*),  $2114$  (*magenta*), and  $2096$  (*red*)  $\pm n \cdot 104 \text{ u}$ . Assignments are discussed in the text. **C)** MWDs of the products.

This result was further confirmed by MALDI-TOF MS analysis (**Figure 3B**). The mass spectrum showed a main distribution with a peak at  $m/z = 2148 \text{ u}$ , corresponding to the calculated mass for trisAminoPS ( $n=18$  leading to  $[\text{C}_{153}\text{H}_{153}(\text{NH}_2)_3, \text{Ag}]^+ = 2148 \text{ u}$ ). A secondary distribution




shifted by  $-17$  u aligns with the expected polystyrene containing two amines and a dehydrohalogenated chain-end,  $[\text{C}_{153}\text{H}_{152}(\text{NH}_2)_2, \text{Ag}]^+ = 2131$  u. Only minor traces of products with one or no amine (from double or triple dehydrohalogenation) were detected, shifted by  $-34$  and  $-51$  u, respectively.

These findings support the quantitative conversion of azides to amines, suggesting, as previously reported,<sup>34, 65, 66</sup> that the primary cause of small functionality loss arises from the undesired dehydrohalogenation during the ARGET ATRP step. By comparing the peak intensities, the chain-end functionality determined by MALDI-ToF MS ( $f_{\text{MALDI}} = 2.69$ ), is consistent with the value obtained from  $^1\text{H-NMR}$  ( $f_{\text{NMR}} = 2.75$ ). As ARGET ATRP allows the synthesis of low-dispersity polymers with predetermined molar masses, it is crucial that the post-functionalization pathway does not compromise these properties. This requirement was fulfilled in the reduction step, where the low molar mass and dispersity of the starting trisBromoPS were maintained in the amine derivative (**Figure 3C**). A slight shift toward higher molar masses was observed, likely due to the precipitation-based purification process, which removed lower molar masses chains that dissolve in methanol. This explanation is further supported by the increase in yields as the  $M_n^{\text{GPC}}$  of the precursor increased (**Table S2**). While testing this synthetic step, a potential side reaction with high-molar mass azide-functionalized PSs was found. Specifically, a shoulder appeared at higher molar masses in the MWD, indicative of coupling reactions. This unwanted reaction was slightly more pronounced for longer precursors, as shown in the comparison between lower and higher  $M_n^{\text{GPC}}$  (**Figure 4A**). Notably, decreasing the reaction time between tributylphosphine and water addition significantly suppressed these side reactions. Specifically, waiting 0.5 instead of 3



h resulted in a less pronounced high-MW shoulder (Figure 4B). A possible explanation for this phenomenon is the formation of isocyanate through the reaction of iminophosphorane complexes with CO<sub>2</sub>.<sup>70</sup> Such isocyanates could then react further with the produced free-base amines, forming urea bridges. However, the significant impact of reaction conditions on this side reaction suggests that proper optimization could effectively mitigate it.

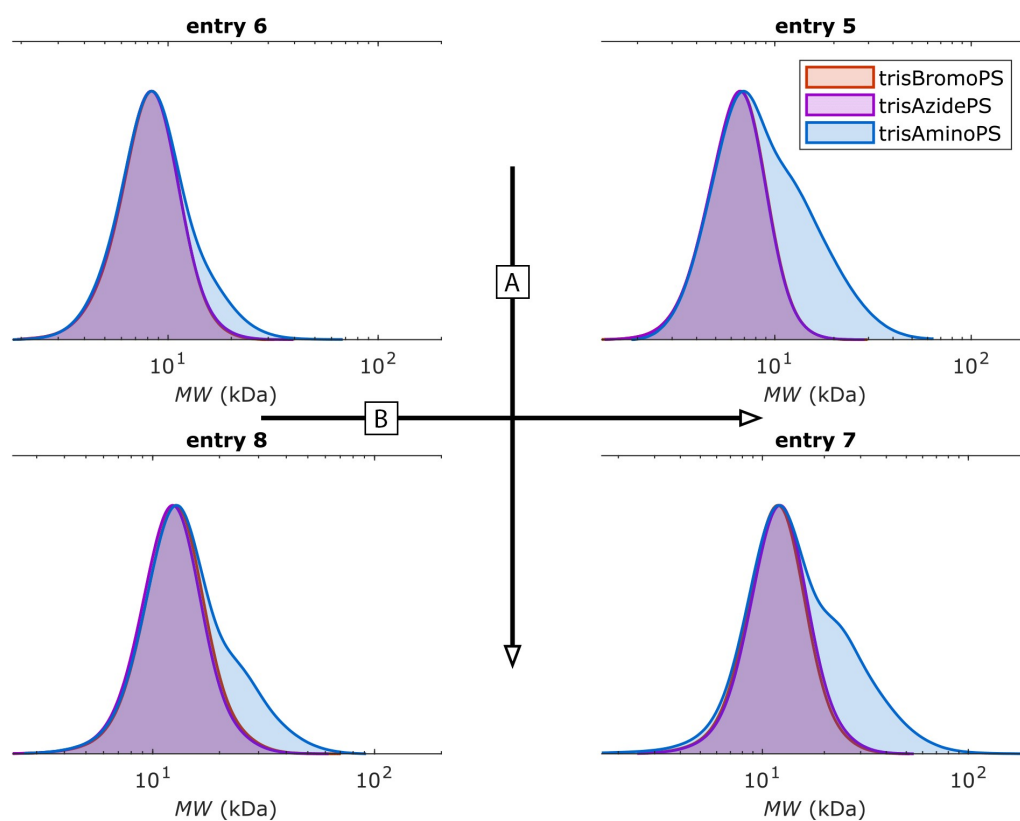

**Figure 4.** MWDs of **trisAminoPS** (*blue*) compared to their respective precursors (*purple*). The entries (referencing **Table S2**) differ in the molar mass of the precursor and the reaction time waited before the addition of water, while all other reaction conditions are kept constant. **A**) Variation in the  $M_n^{\text{GPC}}$  of the precursor: increase going from the first to the second row. **B**) Variation in the time waited between the addition of tributylphosphine and water: increase going from the first to the second column (0.5 to 3 h).

To evaluate the sustainability of the proposed synthetic pathway, the E-Factor has been calculated.

According to the first principle of green chemistry, this value should be as close to zero as possible,



indicating minimal waste generation.<sup>71, 72</sup> By definition, the E-Factor accounts for solvent waste, which typically constitutes 80–90% of the reaction mixture's weight. In industrial settings, solvent management is significantly more optimized than at the laboratory scale. As a result, the true E-Factor (i.e., the value achievable in an optimized industrial process) lies between a simplified E-Factor (sEF), assuming 100% solvent recovery, and a complete E-Factor (cEF), assuming total solvent waste. As a result of the additive nature of the E-Factor, the overall sEF for the multistep synthesis of trisAminoPS was calculated as 1.85 (0.76 + 0.11 + 0.98 for the first, second, and third synthetic steps, respectively), placing it within the range of bulk chemicals. In contrast, the cEF-value is 156, with the primary contribution arising from solvents used in product recovery and purification via precipitation. Excluding the purification steps, the E-Factor significantly decreases to 14, which highlights the main expected limitation of the proposed synthesis method, which is the waste generated during product recovery.

In the second part of this research, two examples have been selected as proof-of-concept to explore the potential applicability of trisAminoPSs as crosslinkers, namely for the synthesis of (1) traditional thermosets using bisphenol A diglycidyl ether (BADGE) following a 3:1 molar ratio relative to trisAminoPS, and (2) vinylogous urethane associative CANs (vitrimers)<sup>12</sup> using Pripol 2033 acetoacetate in a 3:2.1 molar ratio relative to trisAminoPS. Preliminary tests revealed that the latter reaction required demanding conditions to achieve significant conversion. Specifically, the reaction necessitated the use of a solvent (toluene), high reaction temperatures (100–140 °C), and extended reaction times (48 h). In contrast, while the BADGE-based thermoset also required elevated temperatures and prolonged reaction times, the synthesis could be done in bulk. These





overall demanding conditions for the crosslinking were attributed to two factors: the relatively low concentration of reactive groups (compared to small polyamine molecules) and the positioning of these groups on less accessible sites, *i.e.* on a secondary carbon or on a primary carbon located in the middle of the polymeric chain. Despite these challenges, the relatively low soluble fractions of the resulting networks, with a mean value of 5.3% w/w for the epoxy-based thermoset and 16.0% w/w for the acetoacetate-based CAN, show that trisAminoPS can effectively be used as a crosslinker (**Table 2**). Furthermore, the results revealed that tuning the  $M_n^{\text{GPC}}$  of the trisAminoPS can effectively influence the properties of the resulting networks. First, it was observed that increasing the  $M_n^{\text{GPC}}$  of the precursor leads to a progressive increase in the swelling ratio of the networks as expected. Specifically, swelling increased from 210% to 560% for the epoxy-based network and from 620% to 2140% for the acetoacetate-based one. This trend is attributed to a dilution of the crosslinking points caused by the higher number of repeating polystyrene units. Second, it was observed that the glass transition temperature ( $T_g$ ) of the networks decreases with increasing molar mass of the precursor. For the epoxy-based networks,  $T_g$  dropped from 109 to 74 °C, while for the acetoacetate-based networks,  $T_g$  decreased from 104 °C to 54 °C (**Figure S25** and **Table 2**). This was attributed to a progressive decrease in crosslink density, which appears to outweigh the inherent increase in  $T_g$  of the precursor associated with higher  $M_n^{\text{GPC}}$  (**Table S2**). For comparison, a previously reported Pripol-based network crosslinked with the common crosslinker TREN exhibited a low  $T_g$  of -24 °C (specifically, Pripol 2033 acetoacetate and TREN combined with Priamine 1074 at a ratio of 0.40:0.40:0.95 eq), resulting in elastomeric materials.<sup>13</sup> This shows that the PS-based crosslinkers significantly enhanced the rigidity of the networks, despite the use



of an elastomeric acetoacetate. Third, the rheological properties of the vinylogous urethane network were evaluated. The material was compression molded at 160 °C for 60 min under a pressure of 4 metric tons using a steel mold, resulting in pressed samples that exhibited optical transparency (**Figure S26**). Discs of the appropriate diameter were subsequently punched out for testing. Amplitude-sweep experiments were conducted to determine the optimal conditions for stress-relaxation experiments, which were set at an amplitude of 2% and a frequency of 1 Hz (**Figure S27**). From these experiments, relaxation times were extrapolated across a temperature range of 160–195 °C, and Arrhenius plots were constructed (**Figure S28**). These allowed calculation of the following activation energies:  $238.81 \pm 18.66$  kJ/mol (for the 4.69 kDa precursor) and  $182.05 \pm 6.12$  kJ/mol (for the 7.94 kDa precursor). As previously observed when macromolecules are employed as precursors for CANs,<sup>73, 74</sup> these values are significantly higher than those reported for vinylogous urethane networks derived from small molecules.<sup>12</sup> Moreover, a significant decrease in activation energy was observed with increasing  $M_n^{\text{GPC}}$  of the precursor. This trend was tentatively attributed to the synergic decrease in  $T_g$  and an increase in  $\chi_{\text{star}}$ , where the latter improves the accessibility of the amines as  $M_n^{\text{GPC}}$  of the precursor rises. These effects counteract the decrease in concentration of active moieties (*i.e.*, decreased dynamic crosslinking density), which has been previously reported to hinder the exchange dynamics.<sup>75</sup> It is noteworthy that the modulus of relaxation in both samples increased slightly from one temperature to another, which is attributable to incomplete curing of the product, as evidenced by their soluble fractions (>10 wt%). Additionally, the exceptionally high temperatures required to obtain relaxation times are clearly imputable to the pronounced rigidity of the product. In fact, these last two observations



prevent a reliable evaluation of the results in absolute terms. However, the comparison between the two samples highlights the significant influence of the PS-based precursor on the properties of the crosslinked product and thus its potential applicability in reprocessable materials with other dynamic chemistry platforms that make use of amine crosslinkers.<sup>18, 21</sup>



**Table 2.** Swelling and thermal properties of the crosslinked products obtained by reacting trisAminoPS with either BADGE or Pripol 2033 acetoacetate.<sup>[a]</sup>

Entry	<i>Bifunctional electrophile</i>	$M_n^{\text{GPC}}$ (kDa)	<i>Swelling ratio</i> (%)	<i>Soluble Fraction</i> (%)	$T_g$ (°C)	$w_{225\text{ °C}}^{\text{loss}}$ (%)	$T_{\text{onset d,air}}$ (°C) <sup>[b]</sup>
1	BADGE	2.58	207 ± 7	5.0 ± 0.3	109	–	–
2		4.69	300 ± 30	5.4 ± 5.3	71	1.46 <sup>[c]</sup>	217
3		7.46	395 ± 13	5.3 ± 0.3	99	–	–
4		7.94	511 ± 40	5.4 ± 2.3	75	3.94 <sup>[c]</sup>	277
5		12.18	556 ± 7	5.5 ± 0.4	74	–	–
6	Pripol 2033 acetoacetate	2.58	624 ± 95	10.3 ± 1.0	104	–	–
7		4.69	900 ± 50	13.7 ± 3.0	76	1.28 <sup>[d]</sup>	327
8		7.46	1202 ± 130	19.9 ± 3.6	72	–	–
9		7.94	1050 ± 60	12.7 ± 1.9	84	1.81 <sup>[d]</sup>	325
10		12.18	2140 ± 197	23.3 ± 2.9	54	–	–

<sup>[a]</sup> Common conditions: trisAminoPS and the electrophile were added to a glass vial, alongside toluene in the case of Pripol 2033 acetoacetate. The vial was loosely sealed, heated overnight (100 °C), and the resulting networks were dried in an oven at 120 °C and, under vacuum, 140 °C.

<sup>[b]</sup> Extrapolated at  $w^{\text{loss}} = 2.5\%$ .

<sup>[c]</sup> Extrapolated after two isotherms (160 °C for 1 h and 225 °C for 2 h).

<sup>[d]</sup> Extrapolated after one isotherm (225 °C for 2 h).

Finally, thermogravimetric analysis (TGA) was conducted on selected samples (**entry 2, 4, 7, and 9 in Table 2**). First, we compared the thermal behavior of the samples under a heating ramp in an air atmosphere (10 °C min<sup>-1</sup>). As observed from the overlaid curves and the data in **Table 2**, the VU-based networks exhibit inherently higher thermal resistance (**Figure S29**). Additionally, the peak in the first derivative appears slightly shifted to lower temperatures in networks



employing a lower molar mass precursor, which is a trend observed in both types of networks. Conversely, under isothermal degradation conditions, samples with a shorter precursor exhibit a lower overall weight loss (compare entry pairs **2** vs. **4** and **7** vs. **9**, **Table 2**). Overall, these relatively low weight losses, combined with high degradation onset temperatures—particularly for the VU-based networks—indicate good thermal stability of the materials. This thermal behavior aligns well with the composition of the networks, which consist of over 90% PS in weight.

## CONCLUSIONS

This study reported the development of a synthetic pathway for producing trifunctional amine-terminated polystyrenes and their potential use as crosslinking agents in both traditional and covalent adaptable networks. Specific attention was given to low molar mass products, demonstrating that the ARGET ATRP procedure produces bromide-bearing precursors in the 2–12 kDa range with low dispersities. The selection of the initiator was a critical factor as its reactivity was found to influence the topology of the resulting polymers.  $\beta$ -Elimination was identified as the primary source of functionality loss but in all cases an overall functionality above 2.8 was found. Post-functionalization with sodium azide was shown to be both highly effective, as confirmed by  $^1\text{H-NMR}$  analysis, and efficient as indicated by online ATR FT-IR. The quantitative reduction of trifunctional azide-terminated PS using tributylphosphine was demonstrated by  $^1\text{H-NMR}$  and MALDI-TOF MS. A potential side reaction was noticed, attributed to coupling due to isocyanate formation, and a strategy to minimize its occurrence by reducing the time waited before water addition was proposed. The scalability of the synthetic pathway was hinted by operating on



a multi-gram scale, with one example involving a fivefold increase in the quantities of reagents at all steps. Then, the resulting amine-terminated star-shaped PS, with varying molar masses and low dispersities, were successfully employed as crosslinkers to produce both traditional networks (using a diepoxide) and CANs (using a diacetoacetate molecule). This approach demonstrated how the precursor architecture (molar mass and topology) influences the properties of the resulting networks, including swelling degree, glass transition temperature, and, in the case of vinylogous urethane vitrimers, reprocessability. The final materials exhibited excellent thermal resistance, attributed to high PS content, further confirming the potential of this synthetic approach.

### Author contributions

The manuscript was written through contributions of all authors. All authors have given approval to the final version of the manuscript.

### Data availability

The data supporting this article have been included as part of the ESI.†

### Conflicts of interest

The authors declare no competing financial interest.

### Acknowledgements

The NMR expertise centre (Ghent University) is acknowledged for providing support and access to NMR infrastructure funded by a Research Foundation Flanders (FWO I006920N) and the Bijzonder Onderzoeksfonds (BOF.BAS. 2022.0023.01). N.B and F.D.P thank BOF-UGent for



GOA-funding (BOF21/GOA/007). A.T.'s PhD thesis was funded by the European Union's Horizon 2020 research and innovation program under the Marie Skłodowska-Curie Grant agreement No 860911.



## References

1. L.-W. Xu, J. Luo and Y. Lu, *Chem. Commun.*, 2009, 1807-1821.
2. S. Abraham, C.-S. Ha and I. Kim, *Macromol. Rapid Commun.*, 2006, **27**, 1386-1392.
3. F.-L. Jin, X. Li and S.-J. Park, *J. Ind. Eng. Chem.*, 2015, **29**, 1-11.
4. N. Bouazizi, J. Vieillard, B. Samir and F. Le Derf, *Polymers*, 2022, **14**, 378.
5. Y.-W. Jeong, S. Jung, J. J. Han, H.-J. Park, R. Y. Kim, B.-H. Kim and M.-S. Kook, *Materials*, 2019, **12**, 2581.
6. J. Hack, N. Maeda and D. M. Meier, *ACS Omega*, 2022, **7**, 39520-39530.
7. B. Dutcher, M. Fan and A. G. Russell, *ACS Appl. Mater. Interfaces*, 2015, **7**, 2137-2148.
8. J. M. Winne, L. Leibler and F. E. Du Prez, *Polym. Chem.*, 2019, **10**, 6091-6108.
9. F. Van Lijsebetten, T. Debsharma, J. M. Winne and F. E. Du Prez, *Angew. Chem. Int. Ed.*, 2022, **61**, e202210405.
10. C. N. Bowman and C. J. Kloxin, *Angew. Chem. Int. Ed.*, 2012, **51**, 4272-4274.
11. C. J. Kloxin, T. F. Scott, B. J. Adzima and C. N. Bowman, *Macromolecules*, 2010, **43**, 2643-2653.
12. W. Denissen, G. Rivero, R. Nicolaÿ, L. Leibler, J. M. Winne and F. E. Du Prez, *Adv. Funct. Mater.*, 2015, **25**, 2451-2457.
13. W. Denissen, M. Droesbeke, R. Nicolaÿ, L. Leibler, J. M. Winne and F. E. Du Prez, *Nat. Commun.*, 2017, **8**, 14857.
14. F. Van Lijsebetten, K. De Bruycker, Y. Spiesschaert, J. M. Winne and F. E. Du Prez, *Angew. Chem. Int. Ed.*, 2022, **61**, e202113872.
15. F. Van Lijsebetten, Y. Spiesschaert, J. M. Winne and F. E. Du Prez, *J. Am. Chem. Soc.*, 2021, **143**, 15834-15844.
16. H. Zhang, A. van Hertrooij, T. Schnitzer, Y. Chen, S. Majumdar, R. A. T. M. van Benthem, R. P. Sijbesma and J. P. A. Heuts, *Macromolecules*, 2023, **56**, 6452-6460.
17. S. K. Schoustra, V. Asadi, H. Zuilhof and M. M. J. Smulders, *Eur. Polym. J.*, 2023, **195**, 112209.
18. S. K. Schoustra, V. Asadi and M. M. J. Smulders, *ACS Appl. Polym. Mater.*, 2024, **6**, 79-89.
19. A. Liguori and M. Hakkarainen, *Macromol. Rapid Commun.*, 2022, **43**, 2100816.
20. L. T. Nguyen, C. Mertens and F. E. Du Prez, *Macromolecules*, 2024, **57**, 4817-4825.
21. L. T. Nguyen, F. Portone and F. E. Du Prez, *Polym. Chem.*, 2024, **15**, 11-16.
22. L. Stricker, C. Taplan and F. E. Du Prez, *ACS Sustain. Chem. Eng.*, 2022, **10**, 14045-14052.
23. T. G. Ribelli, F. Lorandi, M. Fantin and K. Matyjaszewski, *Macromol. Rapid Commun.*, 2019, **40**, 1800616.
24. K. Matyjaszewski, *Chem. Mater.*, 2024, **36**, 1775-1778.
25. V. Coessens and K. Matyjaszewski, *J. Macromol. Sci. Chem., A*, 1999, **36**, 811-826.
26. J. Babin, D. Taton, M. Brinkmann and S. Lecommandoux, *Macromolecules*, 2008, **41**, 1384-1392.





27. B. Lepoittevin, A. Elhiri, L. Bech, J. Bellenev, J.-P. Baltaze, I. Capron, V. Planchot and P. Roger, *Carbohydr. Polym.*, 2011, **83**, 1174-1179.
28. S. Monge, O. Giani, E. Ruiz, M. Cavalier and J.-J. Robin, *Macromol. Rapid Commun.*, 2007, **28**, 2272-2276.
29. X. Zhang, O. Giani, S. Monge and J.-J. Robin, *Eur. Polym. J.*, 2008, **44**, 3676-3687.
30. R. P. Johnson, Y.-I. Jeong, E. Choi, C.-W. Chung, D. H. Kang, S.-O. Oh, H. Suh and I. Kim, *Adv. Funct. Mater.*, 2012, **22**, 1058-1068.
31. Q. Yang, H. H. Himstedt, M. Ulbricht, X. Qian and S. Ranil Wickramasinghe, *J. Membr. Sci.*, 2013, **430**, 70-78.
32. H. H. Himstedt, Q. Yang, L. P. Dasi, X. Qian, S. R. Wickramasinghe and M. Ulbricht, *Langmuir*, 2011, **27**, 5574-5581.
33. T. Itoh, T. Iwai, E. Ihara and K. Inoue, *Polym. J.*, 2007, **39**, 853-860.
34. A. Postma, T. P. Davis, G. Moad and M. S. O'Shea, *React. Funct. Polym.*, 2006, **66**, 137-147.
35. C. Shi, L. Lin, Y. Yang, W. Luo, M. Deng and Y. Wu, *e-Polymers*, 2020, **20**, 317-327.
36. M. W. Weimer, J. M. J. Fréchet and I. Gitsov, *J. Polym. Sci. Part A: Polym. Chem.*, 1998, **36**, 955-970.
37. L. Li, C. Wang, Z. Long and S. Fu, *J. Polym. Sci. Part A: Polym. Chem.*, 2000, **38**, 4519-4523.
38. V. Coessens, Y. Nakagawa and K. Matyjaszewski, *Polym. Bull.*, 1998, **40**, 135-142.
39. W.-B. Zhang, Y. Tu, R. Ranjan, R. M. Van Horn, S. Leng, J. Wang, M. J. Polce, C. Wesdemiotis, R. P. Quirk, G. R. Newkome and S. Z. D. Cheng, *Macromolecules*, 2008, **41**, 515-517.
40. H.-X. Wu, W.-M. Cao, R.-F. Cai, Y.-L. Song and L. Zhao, *J. Mater. Sci.*, 2007, **42**, 6515-6523.
41. L. Chen, X. Wang, R. Hou, H. Lu, Z. He, X. Zhou, W. Zhang and X. Wang, *Polym. Chem.*, 2023, **14**, 4659-4670.
42. A. P. Vogt and B. S. Sumerlin, *Macromolecules*, 2006, **39**, 5286-5292.
43. Q. Liu and Y. Chen, *J. Polym. Sci. Part A: Polym. Chem.*, 2006, **44**, 6103-6113.
44. S. Abraham, C.-S. Ha and I. Kim, *J. Polym. Sci. Part A: Polym. Chem.*, 2006, **44**, 2774-2783.
45. K. Matyjaszewski, Y. Nakagawa and S. G. Gaynor, *Macromol. Rapid Commun.*, 1997, **18**, 1057-1066.
46. E. Cloutet, J.-L. Fillaut, D. Astruc and Y. Gnanou, *Macromolecules*, 1999, **32**, 1043-1054.
47. F.-A. Teng, Y. Guo, J. He, Y. Zhang, Z. Han and H. Li, *Des. Monomers Polym.*, 2017, **20**, 283-292.
48. H. Gao, G. Louche, B. S. Sumerlin, N. Jahed, P. Golas and K. Matyjaszewski, *Macromolecules*, 2005, **38**, 8979-8982.
49. K. R. Brzezinska and T. J. Deming, *Macromol. Biosci.*, 2004, **4**, 566-569.
50. Y. Sasaki, N. Konishi, M. Kohri, T. Taniguchi, K. Kishikawa and T. Karatsu, *Colloid. Polym. Sci.*, 2022, **300**, 319-331.



51. N. Braidı, F. Parenti, G. Scurani, F. Tassinari, M. Buffagni, L. Bonifaci, G. Cavalca, N. Pettenuzzo and F. Ghelfi, *Polym. Chem.*, 2023, **14**, 1567-1576.
52. N. Braidı, M. Buffagni, F. Ghelfi, F. Parenti, A. Gennaro, A. A. Isse, E. Bedogni, L. Bonifaci, G. Cavalca, A. Ferrando, A. Longo and I. Morandini, *J. Macromol. Sci. Chem., A*, 2021, **58**, 376-386.
53. N. Braidı, N. Porcelli, F. Roncaglia, A. Mucci and F. Tassinari, *Macromol. Rapid Commun.*, 2025, **46**, 2400564.
54. M. Flejszar, P. Chmielarz, J. Smenda and K. Wolski, *Polymer*, 2021, **228**, 123905.
55. G. Gazzola, S. Pasinato, M. Fantin, N. Braidı, C. Tubaro, C. Durante and A. A. Isse, *Molecules*, 2022, **27**.
56. G. Damonte, I. Zaborniak, M. Klamut, D. Di Lisa, L. Pastorino, K. Awsiuk, K. Wolski, P. Chmielarz and O. Monticelli, *Int. J. Biol. Macromol.*, 2024, **273**, 132768.
57. J. Wang, L. Zhang, D. Chen, C. Wang, Z. Ren and Z. Wang, *Macromolecules*, 2024, **57**, 6267-6274.
58. C. Wang, H. Deng and H. Zhao, *Giant*, 2022, **11**, 100114.
59. S. Angot, K. S. Murthy, D. Taton and Y. Gnanou, *Macromolecules*, 1998, **31**, 7218-7225.
60. K. Ohno, B. Wong and D. M. Haddleton, *J. Polym. Sci. Part A: Polym. Chem.*, 2001, **39**, 2206-2214.
61. Y. Gnanou and D. Taton, *Macromol. Symp.*, 2001, **174**, 333-341.
62. V. Coessens and K. Matyjaszewski, *J. Macromol. Sci. Chem., A*, 1999, **36**, 667-679.
63. W. Radke, J. Gerber and G. Wittmann, *Polymer*, 2003, **44**, 519-525.
64. J. Gerber, W. Radke and G. Wittmann, *Int. J. Polym. Anal. Charact.*, 2004, **9**, 39-52.
65. J.-F. Lutz and K. Matyjaszewski, *J. Polym. Sci. Part A: Polym. Chem.*, 2005, **43**, 897-910.
66. K. Matyjaszewski, K. Davis, T. E. Patten and M. Wei, *Tetrahedron*, 1997, **53**, 15321-15329.
67. W. Tang, Y. Kwak, W. Braunecker, N. V. Tsarevsky, M. L. Coote and K. Matyjaszewski, *J. Am. Chem. Soc.*, 2008, **130**, 10702-10713.
68. H. Gao, D. J. Siegwart, N. Jahed, T. Sarbu and K. Matyjaszewski, *Des. Monomers Polym.*, 2005, **8**, 533-546.
69. D. Yang, L. Li and C. Wang, *Mater. Chem. Phys.*, 2004, **87**, 114-119.
70. D. Carnaroglio, K. Martina, G. Palmisano, A. Penoni, C. Domini and G. Cravotto, *Beilstein J. Org. Chem.*, 2013, **9**, 2378-2386.
71. R. A. Sheldon, *Green Chem.*, 2023, **25**, 1704-1728.
72. T. V. T. Phan, C. Gallardo and J. Mane, *Green Chem.*, 2015, **17**, 2846-2852.
73. J. Tellers, R. Pinalli, M. Soliman, J. Vachon and E. Dalcanale, *Polym. Chem.*, 2019, **10**, 5534-5542.
74. Y. Nishimura, J. Chung, H. Muradyan and Z. Guan, *J. Am. Chem. Soc.*, 2017, **139**, 14881-14884.
75. Y. Spiesschaert, C. Taplan, L. Stricker, M. Guerre, J. M. Winne and F. E. Du Prez, *Polym. Chem.*, 2020, **11**, 5377-5385.



- The data supporting this article have been included as part of the Supplementary Information.

