


 Cite this: *RSC Adv.*, 2024, 14, 6374

# Achieving high molecular weight alternating copolymers of 1-octene with methyl acrylate *via* Lewis acid catalyzed copolymerization†

Jiefan Wan, Yi Dan, Yun Huang and Long Jiang \*

The radical (co)polymerization of long-chain  $\alpha$ -olefins ( $C_{4+}$ ) to produce high molecular weight ( $M_w$ ) polymers is of great importance. However, this process is currently faced with significant challenges due to the presence of less reactive allylic radicals during radical (co)polymerization, leading to oligomers or polymers with extremely low  $M_w$  (less than  $1 \times 10^4 \text{ g mol}^{-1}$ ). Using copolymerization of 1-octene with methyl acrylate (MA) as a proof-of-concept for addressing this challenge, we present a feasible method for synthesizing high  $M_w$   $\alpha$ -olefin copolymers *via* scandium trifluoromethanesulfonate ( $\text{Sc}(\text{OTf})_3$ )-mediated radical copolymerization. In this case, copolymers of 1-octene and MA (poly(1-octene-*alt*-MA)) with a  $M_w$  exceeding  $3 \times 10^4 \text{ g mol}^{-1}$  were successfully synthesized in the presence of  $\text{Sc}(\text{OTf})_3$ . Meanwhile, the presence of alternating 1-octene–MA sequential structures was observed. To further enhance the  $M_w$  of poly(1-octene-*alt*-MA), a difunctional comonomer, 1,7-octadiene, was introduced to copolymerize with 1-octene and MA. The results indicate that the incorporation of difunctional comonomer leads to a significant increase in the  $M_w$  of the copolymers synthesized. The addition of 1 mol% of 1,7-octadiene resulted in a copolymer with a remarkably high  $M_w$  of up to  $13.45 \times 10^4 \text{ g mol}^{-1}$  while still maintaining a high degree of the alternating 1-octene–MA sequence (41%). The influence of polymerization parameters on the molecular weight were also investigated. Increasing the monomer concentration, reducing the dosage of initiator, and lowering the polymerization temperature have been found to be advantageous in enhancing the molecular weight. This approach has also been successfully applied to the synthesis of high molecular weight alternating copolymers of other long-chain  $\alpha$ -olefins, including 1-hexene, 1-decene and 1-tetradecane, with methyl acrylate. In summary, this study provides a feasible method for converting “less activated”  $\alpha$ -olefins into high  $M_w$  olefin copolymers. This approach holds significant potential for the production of value-added polyolefins, thus offering promising prospects for future applications.

 Received 7th January 2024  
 Accepted 13th February 2024

DOI: 10.1039/d4ra00165f

[rsc.li/rsc-advances](https://rsc.li/rsc-advances)

## 1 Introduction

In recent decades, the production of polyethylene has consistently accounted for approximately 30% of the overall global plastic production due to the continuous growth in demand for PE products.<sup>1–5</sup> Consequently, there has been a substantial increase in the production capacity of ethylene, which currently reaches a total of 120 million tons per year.<sup>6,7</sup> However, the ethylene cracking process also results in the generation of a significant quantity of low-value by-products, including hexene, octene, and other long chain  $\alpha$ -olefins ( $C_{4+}$ ). Although these  $\alpha$ -olefins are valuable non-renewable petrochemical resources,<sup>8–12</sup> their chemical inertness poses a significant

challenge when attempting to broaden their applications.<sup>13,14</sup> In fact, a portion of these olefins are presently being combusted, leading to a substantial waste of precious petroleum resources and a rise in carbon emissions.<sup>2,15</sup> To enhance the efficient utilization of non-renewable petrochemical resources and achieve carbon neutrality, it is crucial for the petrochemical industry to develop value-added strategies for the utilization of these low-value by-products. Radical copolymerization of  $\alpha$ -olefins with functional monomers to produce high-performance polymers has been proposed as a promising strategy to reduce the depletion of non-renewable petrochemical resources and enables their efficient and valuable utilization.

High molecular weight is a crucial determinant for high-performance polymer materials. However, the synthesis of high molecular weight  $\alpha$ -olefin (co)polymers through radical polymerization is challenging, mainly attributed to the existence of allyl hydrogens.<sup>16</sup> The allyl hydrogens are readily abstracted by the active radicals during the chain growth,

State Key Laboratory of Polymer Materials Engineering of China (Sichuan University), Polymer Research Institute of Sichuan University, Chengdu 610065, China. E-mail: [jianglong@scu.edu.cn](mailto:jianglong@scu.edu.cn)

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d4ra00165f>



leading to the formation of allylic radicals with extremely low reaction activity. The consequence of this is the incapacity to generate high molecular weight polymers. Although poly( $\alpha$ -olefins) can be synthesized through coordination polymerization, such as homo-polymerization for isotactic polypropylene or copolymerization for functional polyolefins,<sup>17,18</sup> the simultaneous improvement of catalytic efficiency and copolymer molecular weight remains an unattained goal.<sup>13,19</sup> Furthermore, the incorporation of functional monomers, particularly polar monomers, into olefin copolymers is restricted by the limited tolerance of coordination polymerization catalysts towards polar monomers.<sup>20,21</sup> Unlike coordination polymerization, free radical polymerization exhibits less stringent limitation regarding the suitability of monomer types. However, the differences in reactivity ratios of non-polar  $\alpha$ -olefins (0.0016) and polar acrylates (92) are large, leading to notably low integration ratio of  $\alpha$ -olefin units in the copolymer produced through radical copolymerization.<sup>22,23</sup> In recent decades, considerable efforts have been undertaken to address the issue of the relatively low reactivity exhibited radical polymerization of  $\alpha$ -olefins.<sup>16,17,24,25</sup> Techniques such as “living” radical polymerization have been devised to improve the activity of  $\alpha$ -olefins by maintaining a dynamic equilibrium of free radicals in the reaction system.<sup>26,27</sup> The molecular weight of polymers is typically controlled by polymerization parameters such as initiator dosage, monomer concentration, and branching structure, *etc.*<sup>28,29</sup> Furthermore, it is essential to account for the impact of changes in the reaction environment on the polymerization mechanism. For instance, the inhibition of cationic polymerization is advantageous for the production of polymers with higher molecular weight polymers, particularly in the presence of Lewis acid.<sup>30</sup>

In addition to increasing the molecular weight, there has been significant research interest in controlling the sequence structure of  $\alpha$ -olefin copolymers,<sup>31</sup> since well-defined sequence structures promise great potential for developing advanced polymer materials, such as self-healing,<sup>32</sup> molecular data storage and cryptography,<sup>33</sup> superior adhesion performance,<sup>34</sup> and high ion conduction.<sup>35</sup> Up to now, various state-of-the-art methods have been developed to synthesize alternating copolymers, including introducing of specific recognition sites,<sup>36</sup> iterative coupling through repeated cyclization,<sup>37</sup> and using bulky protection groups.<sup>38</sup> While the sequence controlled radical copolymerization of commodity monomers including acrylate, styrene, and acrylamide has made great progress,<sup>39–41</sup> the synthesis of sequence-controlled  $\alpha$ -olefin copolymers still presents enormous challenges. This is due to the extremely low reactivity of  $\alpha$ -olefins and the significant difference in reactivity ratios between  $\alpha$ -olefins and commodity co-monomers such as acrylates and styrene. The most promising protocol for synthesizing sequence-defined  $\alpha$ -olefin copolymers is the Lewis acid-catalyzed alternating copolymerization of  $\alpha$ -olefins with acrylates.<sup>42–44</sup> In this protocol, Lewis acids (LA), including  $\text{BF}_3$ ,<sup>45</sup> ethylaluminum dichloride,<sup>46</sup>  $\text{ZnCl}_2$ ,<sup>47</sup> and scandium triflate ( $\text{Sc}(\text{OTf})_3$ )<sup>48</sup> *etc.*, exhibit unique property for altering the reactivity of the acrylates through the formation of acrylate-LA complexes. The acrylate-LA complex exhibits extremely low

propensity toward homo-polymerization but has the capability to copolymerize with ethylene<sup>49</sup> and propylene,<sup>50</sup> leading to the formation of alternating copolymers. Inspired by these pioneering works, our group has succeeded in the synthesis of alternating copolymers containing long-chain  $\alpha$ -olefin units by using  $\text{AlCl}_3$  as Lewis-acid catalyst.<sup>51,52</sup> However, for LA catalyzed alternating copolymerization, a higher than stoichiometric dosage of LA was essential for forming nearly alternating copolymers, leading to a high-cost purification process and a large amount of waste water containing toxic ions.

In the study, a feasible radical copolymerization technique was developed to synthesize alternating  $\alpha$ -olefin copolymer with high molecular weight by using a catalytic dosage of  $\text{Sc}(\text{OTf})_3$  as the Lewis acid catalyst and 1-octene as a representative of  $\alpha$ -olefins to copolymerize with methyl acrylate. Although  $\text{Sc}(\text{OTf})_3$  have been well applied in catalyzing (meth)acrylate/nonpolar alkene radical copolymerizations,<sup>44,48,53</sup> few efforts have been made to quantitatively demonstrate the influence of the polymerization parameters on the molecular weight of the resulting copolymers. In addition, strategy to further enhance the molecular weight of the copolymers is lacking. Herein, the impact of initiator dosage, solvent, monomer concentration and polymerization temperature on copolymer sequence, molecular weight, and molecular weight distribution were studied. To further improve the molecular weight, a difunctional comonomer was introduced to copolymerize with 1-octene and methyl acrylate, and the impact of the difunctional comonomers on the sequence structure were also investigated.

## 2 Experimental section

### 2.1 Materials and chemicals

Methyl acrylate (MA, 99%) and 1-octene (99%) from Shanghai Titan Technology Co. Ltd (Shanghai, China) were purified by distillation under reduced pressure and stored under  $\text{N}_2$  before use. 2,2'-Azobis(2-methylpropionitrile) (AIBN, 99%), 2,2'-azobis(2,4-dimethylvaleronitrile) (ABVN, 98%), scandium triflate ( $\text{Sc}(\text{OTf})_3$ , 99%), methylene chloride ( $\text{CH}_2\text{Cl}_2$ , 99.5%), 1,4-dioxane (99.7%) and chlorobenzene (PhCl, 98.0%) purchased from Shanghai Titan Technology Co. Ltd (Shanghai, China) and 1,7-octadiene (98.5%) purchased from Thermo Fisher Scientific (China) Co. Ltd (Shanghai, China) were stored under  $\text{N}_2$ . Methanol purchased from Shanghai Titan Technology Co. Ltd (Shanghai, China), ethanol purchased from Chengdu Jinshan Chemical Co. Ltd (Chengdu, China) and acetone purchased from Chengdu Kelon Chemicals Co. Ltd (Chengdu, China) was used as received.

### 2.2 Polymerization

**2.2.1 Copolymerization of 1-octene with MA in the presence of  $\text{Sc}(\text{OTf})_3$ .** Firstly, the initiator (ABVN or AIBN) was dissolved in an organic solvent ( $\text{CH}_2\text{Cl}_2$ , PhCl, 1,4-dioxane, 10 ml) to obtain the initiator solution. Afterwards, the catalyst scandium trifluoromethanesulfonate (2.77 mmol, 1.363 g), organic solvent (20 ml, 40 ml), and methyl acrylate (27.7 mmol, 2.5 ml) were added to the reaction vessel in an oxygen free



environment, and stirred for 15–20 minutes to achieve sufficient complexation between the catalyst and methyl acrylate. Then 1-octene (79.6 mmol, 12.5 ml) and initiator solution were added to the reaction vessel, and then the reaction vessel was sealed. Finally, the sealed reaction vessel was placed in a water bath and reacted under heating conditions for 8 hours to obtain a polymer solution. The subsequent procedure involved the addition of the polymer solution to a mixture of deionized water and methanol (50 ml of deionized water and 400 ml of methanol) to induce precipitation and isolate the polymer. Following a 24 hours drying period, the polymer was dissolved in acetone and subsequently precipitated once more using the deionized water/methanol mixture. After drying under vacuum at 70 °C, the resulting purified product, which was colorless (or slightly yellow), soft, and rubber-like, was then collected and weighted to determine the copolymer yield.

**2.2.2 Sc(OTf)<sub>3</sub>-catalyzed copolymerization of 1-octene with MA in the presence of 1,7-octadiene.** After introducing different dosage of 1,7-octadiene, the Sc(OTf)<sub>3</sub>-catalyzed copolymerization of 1-octene with MA in the presence of 1,7-octadiene were conducted under the identical polymerization conditions as shown in Section 2.2.1. Generally, 1-octene (79.6 mmol, 12.5 ml), 1,7-octadiene (0.277 mmol, 0.831 mmol, 1.108 mmol, 1.385 mmol) and initiator solution were added to the reaction vessel, and then the reaction vessel was sealed. Finally, the sealed reaction vessel was placed in a water bath and reacted under heating conditions for 8 hours to complete the polymerization. The separation and purification of the resultant copolymers were carried out following the same method as shown in Section 2.2.1.

**2.2.3 Copolymerization of other  $\alpha$ -olefins with MA.** The Sc(OTf)<sub>3</sub>-catalyzed copolymerization of other  $\alpha$ -olefins with MA in the presence of 1,7-octadiene were conducted under the identical polymerization conditions as shown in Section 2.2.1. Generally, 1-hexene (81.5 mmol) or 1-decene (79.3 mmol) or 1-tetradecane (78.9 mmol), as well as 1,7-octadiene (0.277 mmol) and initiator solution were added to the reaction vessel, and then the reaction vessel was sealed. Finally, the sealed reaction vessel was placed in a water bath and reacted under heating conditions for 8 hours to complete the polymerization. The separation and purification of the resultant copolymers were carried out following the same method as shown in Section 2.2.1.

### 2.3 Characterization, calculation, and instrumentation

Complexation between monomer MA and Sc(OTf)<sub>3</sub> was characterized by detecting the wavelength of carbonyl absorbance peak in the UV-vis absorption spectra recorded on a UV-2600 spectrophotometer (Shimadzu Instruments (Suzhou) Co. Ltd) at a scanning speed of 400 nm min<sup>-1</sup> in the range of 185 to 400 nm. In addition, nuclear magnetic resonance carbon spectroscopy can be used to analyze the chemical shift of carbon after the complexation of methyl acrylate with different dosages of Sc(OTf)<sub>3</sub>.

NMR spectroscopies (<sup>1</sup>H NMR and <sup>13</sup>C NMR) were used to investigate the composition of the obtained copolymer by the

integration of the methoxy protons *versus* all the aliphatic resonances excluding hydrogen contribution of MA unit (<sup>1</sup>H NMR), and the sequence structure of the copolymer chains (<sup>13</sup>C NMR). The NMR (<sup>1</sup>H NMR, 400 MHz; <sup>13</sup>C NMR, 400 MHz) spectra were recorded on Bruker AV II-400 MHz using deuteriochloroform as solvent and tetramethylsilane as internal standard at ambient temperature. The productivity was defined and calculated as the ratio of copolymer's yield to monomer's amount. The equation for calculating the composition of the obtained copolymer is as follows.

$$F_{\text{MA}} = \frac{S_{11}/3}{S_{11}/3 + (S_{1-10} - S_{11})/16} \times 100\% \quad (1)$$

$$F_{1\text{-octene}} = 1 - F_{\text{MA}} \quad (2)$$

$F_{\text{MA}}$ : molar content of MA units in the copolymer,  $F_{1\text{-octene}}$ : molar content of 1-octene units in the copolymer,  $S_{11}$  represents the integrated area of H on C<sub>11</sub>, and  $S_{1-10}$  represents the integrated area of H on C<sub>1</sub>–C<sub>10</sub>.<sup>51</sup>

The relative molecular weight ( $M_n$ ) of copolymer was measured using a gel permeation chromatography (GPC, Waters 1515, America) equipped with three columns (Styragel® HR 5 THF 7.8 × 300 mm, Styragel® HR 4 THF 7.8 × 300 mm, and Styragel® HR 3 THF 7.8 × 300 mm) in series taking THF as an eluent at ambient temperature. The flow rate was set at 1  $\mu\text{L min}^{-1}$ . The polymer concentration in THF solvent was 2 mg ml<sup>-1</sup>, where the polymer was dissolved for more than 10 h in order to get a complete dissolution. Polystyrene was used as a calibration standard.

Thermo-gravimetric analyzer (Netzsch 209F1 Iris, Netzsch Instruments, Germany) was used to test and analyze the thermal weight loss process of the copolymer (temperature range: 30–600 °C, heating rate of 10 °C min<sup>-1</sup>, N<sub>2</sub> atmosphere), in order to evaluate the heat resistance of the copolymer. Differential scanning calorimeter (TA Q250, American TA Instrument) was used to test and analyze the glass transition temperature of copolymers (temperature range: –70–140 °C, heating rate: 10 °C min<sup>-1</sup>).

The product obtained by introducing the polymerization scheme of 1,7-octadiene contains a part of acetone insoluble polymer gel. After filtering out the gel, wrap it with filter paper and put it into Soxhlet extractor. After extracting with boiling acetone solution for 2 h, vacuum dry it at 70 °C for 24 h, and the weight was recorded.

## 3 Results and discussions

### 3.1 Synthesis of alternating 1-octene–MA copolymer in the presence of Sc(OTf)<sub>3</sub>

The formation of the Sc(OTf)<sub>3</sub> MA complex is essential for synthesizing alternating 1-octene–MA copolymer. Therefore, the interaction between Sc(OTf)<sub>3</sub> and MA was initially analyzed using <sup>13</sup>C NMR spectroscopy, and the results were shown in Fig. 1 and Table S1 in the ESI.† As shown in Fig. 1, in comparison with pristine MA solution, introducing far less than stoichiometric dosage of Sc(OTf)<sub>3</sub>, only about 0.1× the MA



molar content, the chemical shifts of  $C_{1'}$  and  $C_{2'}$  in MA increase by 1.31 ppm and decrease by 0.39 ppm respectively, and the chemical shifts of  $C_{3'}$  increase by 1.09 ppm. These changes clearly suggest that the electron cloud moves from  $C_{1'}$  to  $C_{2'}$  and  $Sc(OTf)_3$  has successfully complexed with MA. As the molar ratio of  $Sc(OTf)_3$  to MA increases from 0.1 to 0.3, a larger downfield shifts in the chemical shift of  $C_{1'}$  ( $\Delta\delta = 3.52$  ppm) and  $C_{3'}$  ( $\Delta\delta = 3.04$  ppm) accompanied by a larger upfield shift in the chemical shift of  $C_{2'}$  ( $\Delta\delta = 0.92$  ppm) can be observed, suggesting that increasing  $Sc(OTf)_3$  dosage can enhance the complexation strength between  $Sc(OTf)_3$  and MA.<sup>54</sup>

The complex between  $Sc(OTf)_3$  and MA were investigated by UV-vis absorption spectra, as shown in Fig. 2. As the molar ratio of  $Sc(OTf)_3$  to MA increases, the absorption peaks of the UV-vis absorption spectra of MA exhibit a red shift. This suggests that the addition of  $Sc(OTf)_3$  will decrease the  $\pi \rightarrow \pi^*$  transition energy of the lone pair electrons of carbonyl oxygen in MA molecules, increase the density of carbonyl electron clouds, and consequently decrease the density of carbon=carbon double bond electron clouds.<sup>55</sup> However, the magnitude of the red shift is not positively correlated to the  $Sc(OTf)_3/MA$  ratio. During the test, we found that at high  $Sc(OTf)_3$  dosage ( $n(Sc(OTf)_3)/n(MA) \geq 0.3$ ), the dissolution of  $Sc(OTf)_3$  in solvent gradually deteriorates with the increase in  $Sc(OTf)_3$  dosage, and the degree of redshift of the absorption peak in the UV-visible absorption spectrum of MA is lower than that with a  $Sc(OTf)_3/MA$  ratio of 0.1, and it continuously decreases with the increase of  $Sc(OTf)_3/MA$ . This suggests that an excessive dosage of  $Sc(OTf)_3$  may disrupt its complexation with MA, interfering with existing complexation. Overall, when the  $Sc(OTf)_3/MA$  ratio is 0.1, there is an effective complexation between  $Sc(OTf)_3$  and MA, which will benefit the alternating copolymerization of 1-octene with MA.

According to the above analysis, the dosage of catalyst  $Sc(OTf)_3$  for 1-octene and MA copolymerization was set to  $n(Sc(OTf)_3)/n(MA) = 0.1$ . Fig. 3 exhibits the  $^1H$  NMR spectrum of the resultant copolymer. The chemical shift of the methoxy

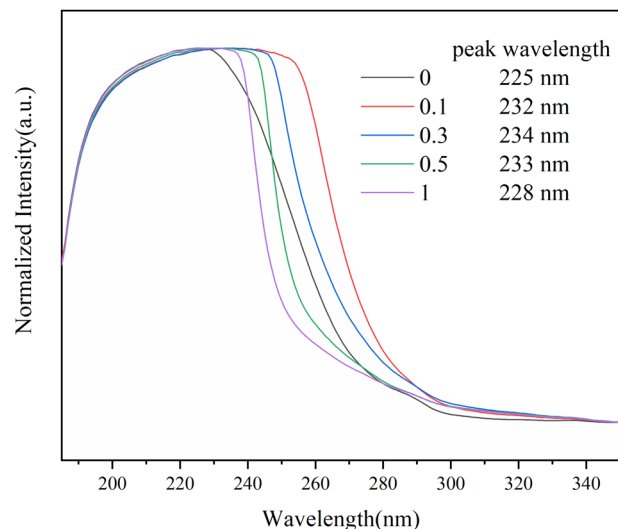


Fig. 2 UV-vis absorption spectra of  $Sc(OTf)_3/MA$  systems with different molar ratios of  $Sc(OTf)_3$  to MA in  $CH_2Cl_2$ .

protons in MA unit can be observed at 3.58 ppm, while the chemical shifts of protons in back-bone chain and 1-octene unit present as a wide multiple peaks in the range between 0.50 ppm and 2.59 ppm. According to eqn (1) and (2), the proportion of 1-octene and MA units in the copolymer could be calculated from the  $^1H$  NMR spectrum, and the result was listed in Table 1 (entry 2). The result demonstrates that the resultant copolymer contains 45.04 mol% of 1-octene unit ( $F_{1-octene}$ ) and 54.96 mol% of MA unit, suggesting the formation of nearly 1 : 1 alternating microstructure.  $^{13}C$  NMR analysis were further carried out to verify the sequence structure of the copolymer, and the result is shown in Fig. 4. Neither the chemical shift of MA-MA sequence at 35 ppm nor the chemical shift of octene-octene sequence at 43 ppm were observed, clearly demonstrate the formation of the sequence structure in this case.<sup>44,51,56</sup> We further analyzed the

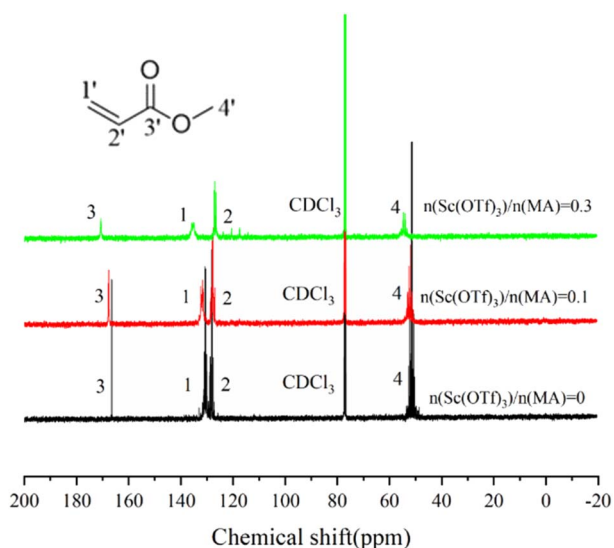


Fig. 1  $^{13}C$  NMR spectra of MA complexed with  $Sc(OTf)_3$  in  $CDCl_3$ .

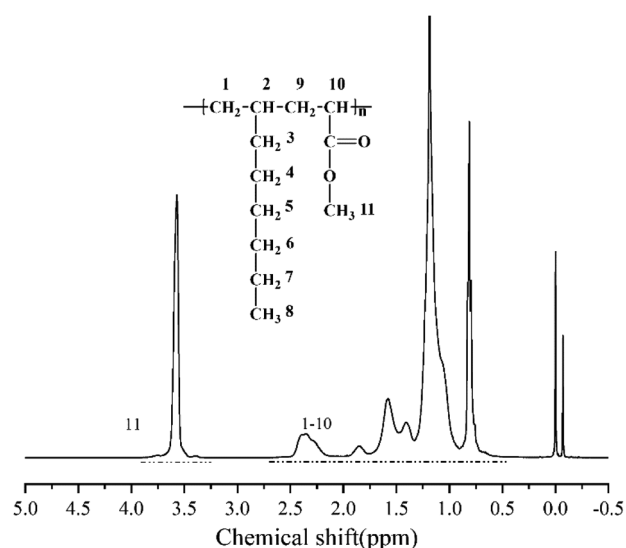


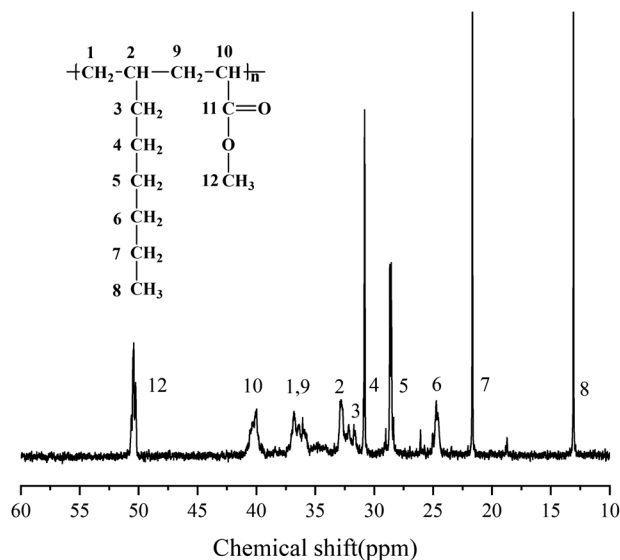
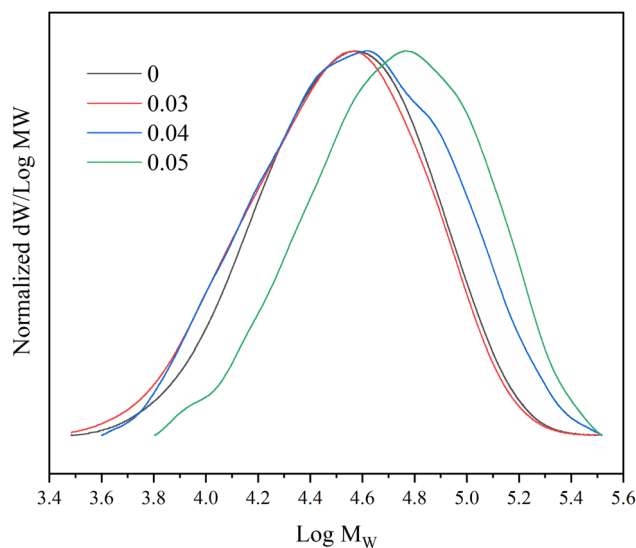
Fig. 3  $^1H$  NMR spectrum of copolymer of MA and 1-octene in  $CDCl_3$ .



Table 1 The constitutions of copolymers synthesized in the presence of Sc(OTf)<sub>3</sub>

| # <sup>a</sup> | $\phi^b$ | Integration of methoxy protons | Integration aliphatic protons | $F_{1\text{-octene}}$ | $F_{\text{MA}}$ | $M_n \times 10^{-4}$ (g mol <sup>-1</sup> ) | $M_w \times 10^{-4}$ (g mol <sup>-1</sup> ) | PDI <sup>c</sup> |
|----------------|----------|--------------------------------|-------------------------------|-----------------------|-----------------|---|---|------------------|
| 1              | 0.005    | 1.000                          | 5.440                         | 45.43                 | 54.57           | 1.79  | 3.20  | 1.79             |
| 2              | 0.003    | 1.000                          | 5.370                         | 45.04                 | 54.96           | 2.16  | 3.82  | 1.77             |
| 3              | 0.001    | 1.000                          | 6.023                         | 48.50                 | 51.50           | 2.59  | 4.34  | 1.68             |

<sup>a</sup> Reaction conditions:  $n(1\text{-octene})/n(\text{MA}) = 2.87$ ;  $n(\text{Sc}(\text{OTf})_3)/n(\text{MA}) = 0.1$ ; 45 °C. <sup>b</sup>  $\phi$  value is the molar ratio of ABVN based on total amount of monomers. <sup>c</sup> Molecular weight distribution.

Fig. 4 <sup>13</sup>C NMR spectrum of copolymer of MA and 1-octene in CDCl<sub>3</sub>.Fig. 5 Molecular weight distribution curves of copolymers with different 1,7-octadiene/MA molar ratio. Reaction conditions:  $n(\text{Sc}(\text{OTf})_3)/n(\text{MA}) = 0.1$ ;  $n(1\text{-octene})/n(\text{MA}) = 2.87$ ;  $n(\text{ABVN})/n(\text{Monomer}) = 0.001$ ; temperature 45 °C.

molecular weight and its distribution (PDI) of the resultant alternating copolymer by GPC, and the result was listed in Table 1. The  $M_n$  of the resultant 1-octene-MA copolymer is  $1.79 \times 10^4$  g mol<sup>-1</sup> with a PDI of 1.79, which is far enough to satisfy the practical requirements as a high-performance polymer.

Following the successful synthesis of the alternating 1-octene-MA copolymer, we further attempted to increase its molecular weight by reducing the dosage of initiator, and the results are shown in Table 1. As the initiator dosage decreases from 0.5 mol% to 0.1 mol%, the molecular weight ( $M_n$ ) of the copolymer increases from  $1.79 \times 10^4$  g mol<sup>-1</sup> to  $2.59 \times 10^4$  g mol<sup>-1</sup>, while the molecular weight distribution is slightly

decreased from 1.79 to 1.68. It is noteworthy that nearly 1 : 1 alternating copolymers have been consistently achieved in all cases, as indicated by ratio of 1-octene unit ( $F_{1\text{-octene}}$ ) to MA unit ( $F_{\text{MA}}$ ) in the copolymer. From the above results it can rationally conclude that: (1) in comparison to traditional LA catalysts, which requires a stoichiometric amount of LA for alternating copolymerization, catalytic amount of Sc(OTf)<sub>3</sub> ( $n(\text{Sc}(\text{OTf})_3)/n(\text{MA}) = 0.1$ ) is adequate for catalyzing the alternating copolymerization of 1-octene with MA in our case;<sup>51</sup> (2) the molecular weight of the 1-octene-MA copolymer could be significantly

Table 2 The constitutions of copolymers of MA, 1-octene and 1,7-octadiene. <sup>a</sup>

| # <sup>b</sup> | $n(1,7\text{-octadiene})/n(\text{MA})$ | $n(\text{AIBN})/n(\text{Monomer})$ (%) | $F_{1\text{-octene}}$ (%) | $F_{\text{MA}}$ (%) | $M_n \times 10^{-4}$ (g mol <sup>-1</sup> ) | $M_w \times 10^{-4}$ (g mol <sup>-1</sup> ) | PDI <sup>c</sup> |
|----------------|--|--|---------------------------|---------------------|---|---|------------------|
| 1              | 0.01                                   | 0.2                                    | 40.10                     | 59.26               | 3.24  | 7.37  | 2.28             |
| 2              | 0.03                                   | 0.1                                    | 40.18                     | 59.60               | 4.48  | 9.60  | 2.14             |
| 3              | 0.03                                   | 0.5                                    | 39.80                     | 60.06               | 3.86  | 8.65  | 2.24             |
| 4              | 0.04                                   | 0.5                                    | 38.15                     | 60.31               | 2.93  | 8.37  | 2.86             |
| 5              | 0.05                                   | 0.5                                    | 38.83                     | 60.14               | 3.56  | 8.82  | 2.48             |

<sup>a</sup> The equations for calculating the composition of the obtained copolymer is eqn S1 in the ESI. <sup>b</sup> Reaction conditions:  $n(1\text{-octene})/n(\text{MA}) = 2.87$ ;  $n(\text{Sc}(\text{OTf})_3)/n(\text{MA}) = 0.1$ ; temperature 60 °C. <sup>c</sup> Molecular weight distribution.



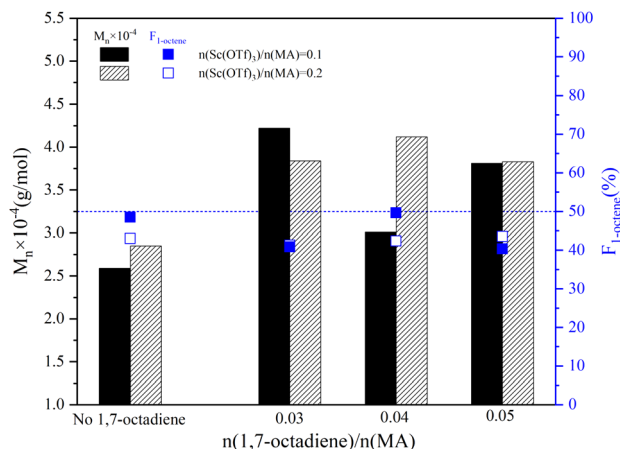


Fig. 6 The effect of the 1,7-octadiene on the molecular weight and its distribution. Reaction conditions:  $n(1\text{-octene})/n(\text{MA}) = 2.87$ ;  $n(\text{ABVN})/n(\text{monomer}) = 0.001$ ; temperature  $45\text{ }^{\circ}\text{C}$ .

improved by reducing the initiation dosage, however, further reducing initiator dosage may lead to an extremely low polymerization rate and unsatisfactory productivity. Hence, improving the molecular weight of 1-octene–MA copolymer in an efficient way remains a challenge.

### 3.2 The effect of the difunctional comonomer 1,7-octadiene on the molecular weight and its distribution

To increase the molecular weight of the copolymer, the difunctional comonomer 1,7-octadiene was introduced to copolymer with methyl acrylate and 1-octene in the presence of  $\text{Sc}(\text{OTf})_3$ . Since both of the ene-groups can participate in the polymerization, 1,7-octadiene, the difunctional comonomer, can be served as “chain extender” to get a significant increase in molecular weight of the resulting copolymer. The polymerization parameters and conditions for  $\text{Sc}(\text{OTf})_3$  catalyzed copolymerization in the presence of different dosage of 1,7-octadiene were listed in Table 2. Under different polymerization

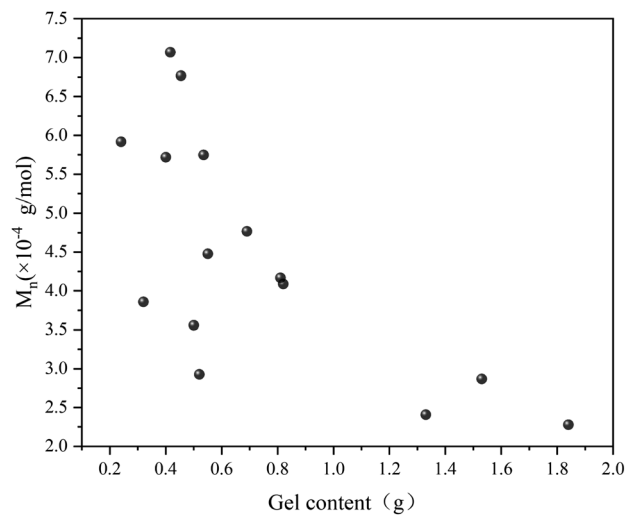


Fig. 8 Correlation between molecular weight and gel content in  $\text{Sc}(\text{OTf})_3$ -catalyzed 1-octene–MA copolymerization system in the presence of 1,7-octadiene. Reaction conditions are in Table S3 in the ESI.†

conditions, the introduction of 1,7-octadiene can increase the molecular weight ( $M_n$ ) of the copolymer from  $2.59 \times 10^4 \text{ g mol}^{-1}$  to  $4.48 \times 10^4 \text{ g mol}^{-1}$ , and the molecular weight distribution is increased from 1.68 to 2.14. The results indicate that the incorporation of difunctional comonomer leads to a significant increase in the molecular weight ( $M_n$ ) and its distribution of the copolymers synthesized.

In addition, with the increase of the proportion of 1,7-octadiene in the monomer, the PDI of the copolymer increases, and the molecular weight distribution curve shows a widening phenomenon (Fig. 5). This suggests that the molecular chains in the polymer undergo branching, resulting in an increase in molecular weight. The results of the obtained copolymer GPC confirm that the 1,7-octadiene unit in the copolymerization system are involved in the copolymerization.<sup>52,57</sup>

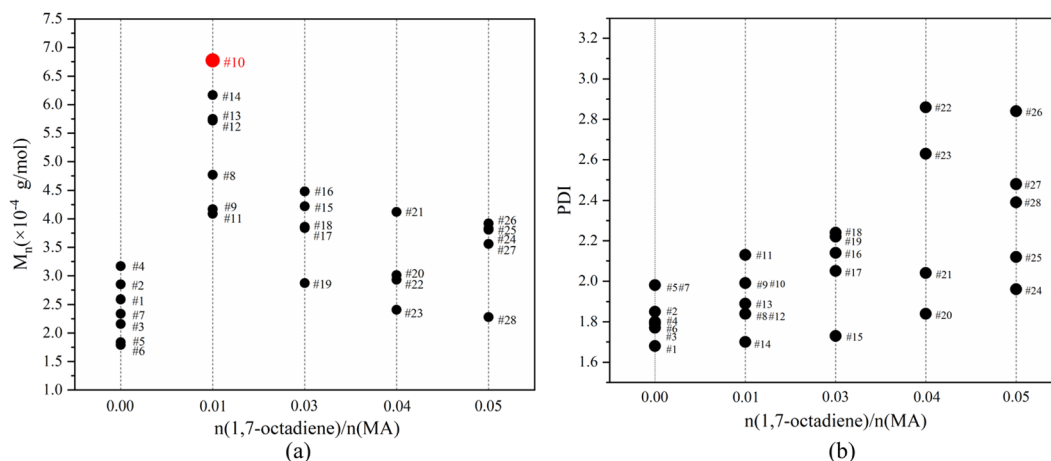


Fig. 7 The influence of 1,7-octadiene/MA molar ratio on the molecular weight (a) and PDI (b) of copolymers. The data points were labeled with entry numbers that align with the corresponding experiments listed in Table S2 in the ESI.†



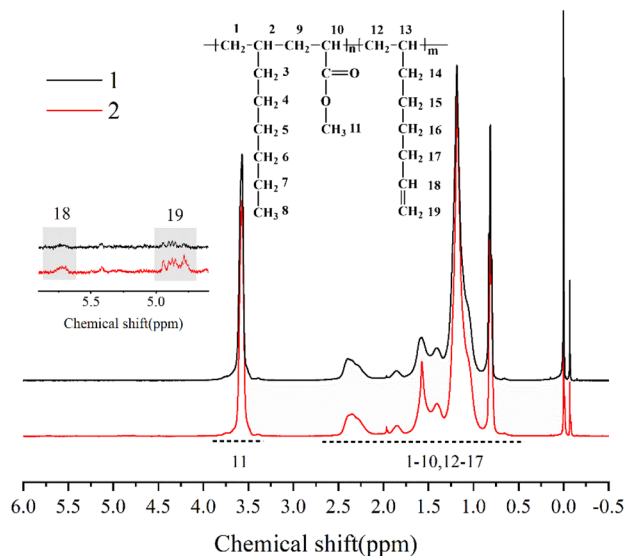


Fig. 9  $^1\text{H}$  NMR spectrum of copolymer of MA, 1-octene and 1,7-octadiene in  $\text{CDCl}_3$ . Reaction conditions:  $n(1\text{-octene})/n(\text{MA}) = 2.87$ ;  $n(\text{Sc}(\text{OTf})_3)/n(\text{MA}) = 0.1$ ; temperature  $60^\circ\text{C}$ ; curve 1:  $n(1,7\text{-octadiene})/n(\text{MA}) = 0.01$ , AIBN 0.2 mol%, curve 2:  $n(1,7\text{-octadiene})/n(\text{MA}) = 0.03$ , AIBN 0.1 mol%.

The impact of 1,7-octadiene on the sequence structures of the resultant copolymers was examined. Compared the proportion of 1-octene ( $F_{1\text{-octene}}$ ) of copolymers synthesized in the absence of 1,7-octadiene (as shown in Table 1) and in the presence of 1,7-octadiene (as shown in Table 2), it can be found that  $F_{1\text{-octene}}$  slightly decreased from 40–50% to 35–45% as 1,7-octadiene were introduced. This can be rationally attributed to the reaction activity of 1,7-octadiene, which is stronger than that of 1-octene.<sup>58,59</sup> Thus, 1,7-octadiene will compete with 1-octene to copolymerize with MA- $\text{Sc}(\text{OTf})_3$  complex.

The influence of  $\text{Sc}(\text{OTf})_3$  dosage on the sequence structure and the molecular weight of 1-octene–MA copolymer synthesized in the presence of varying dosages of 1,7-octadiene were presented in Fig. 6. As the ratio of  $n(\text{Sc}(\text{OTf})_3)/n(\text{MA})$  increased to 0.2, the proportion of 1-octene units in copolymers with different dosages of 1,7-octadiene remained consistent within the range of 40% to 50%. The copolymer obtained exhibits an alternating microstructure close to 1:1, similar to the copolymer synthesized under conditions of  $n(\text{Sc}(\text{OTf})_3)/n(\text{MA}) = 0.1$  (refer to Fig. S1 in the ESI $^\dagger$ ). This observation indicates that the presence of 1,7-octadiene does not impede the catalytic activity of  $\text{Sc}(\text{OTf})_3$ . In comparison to the copolymer synthesized in the absence of 1,7-octadiene, introducing 0.03–0.05 stoichiometric

amount of 1,7-octadiene (based on MA) could significantly increase the molecular weight of the resultant copolymers. The maximum  $M_n$  of  $4.12 \times 10^4 \text{ g mol}^{-1}$  and  $M_w$  of  $8.40 \times 10^4 \text{ g mol}^{-1}$  were achieved under the conditions of 42.34%. Meanwhile, it is evident from Fig. 6 that the dosage of  $\text{Sc}(\text{OTf})_3$  has a minimal effect on the molecular weight. Considering that increasing  $\text{Sc}(\text{OTf})_3$  dosage did not result in a substantial improvement in the proportion of 1-octene unit in copolymers or the molecular weight of copolymers, the  $\text{Sc}(\text{OTf})_3$  dosage was set at  $n(\text{Sc}(\text{OTf})_3)/n(\text{MA}) = 0.1$  for the subsequent studies.

Fig. 7 illustrates the influence of 1,7-octadiene dosage on  $M_n$  and PDI of the resultant copolymers. The  $M_n$  and PDI presented in Fig. 7 are derived from 28 sets of copolymerization experiments conducted under different 1,7-octadiene dosages, with polymerization parameters and conditions are listed in Table S2, $^\dagger$  and each data point in the figure corresponds to each entry in the table. Compared to copolymers synthesized in the absence of 1,7-octadiene, introducing 1 mol% of 1,7-octadiene (based on the amount of MA) to the copolymerization system could increase the molecular weight by 2 times, as shown in Fig. 7a. However, if the dosage of 1,7-octadiene exceeds 1 mol%, the molecular weight of the resultant copolymer decreases, accompanied by a broadening of PDI (Fig. 7b). Meanwhile, gels were generated during the polymerization, and a negative relationship between the gel content and the molecular weight was observed, as shown in Fig. 8 and Table S3. $^\dagger$  The phenomenon clearly indicates the dual functions of 1,7-octadiene: serving as the branching site to extend the kinetic chain length and as the crosslinking agent causing irreversible gels. The optimal balance between chain extension and crosslinking is achieved at  $n(1,7\text{-octadiene})/n(\text{MA})$  ratio of 0.01. Under the optimal conditions, a copolymer with the highest  $M_n$  of ca.  $6.77 \times 10^4 \text{ g mol}^{-1}$  and  $M_w$  of ca.  $13.45 \times 10^4 \text{ g mol}^{-1}$  was obtained, while also maintaining a high degree of the alternating 1-octene–MA sequence ( $F_{1\text{-octene}} = 41\%$ ).

Compared to the copolymers obtained from coordination polymerization and traditional Lewis acid catalytic systems,  $\text{Sc}(\text{OTf})_3$ -catalyzed polymerization of MA and 1-octene can achieve an increase in molecular weight to above  $10 \times 10^4 \text{ g mol}^{-1}$  while maintaining alternating structures.<sup>19,60</sup>

The chemical structure of the copolymer synthesized in the presence of 1,7-octadiene was characterized using  $^1\text{H}$  NMR spectroscopy. The  $^1\text{H}$  NMR spectra (Fig. 9) demonstrate the identification of chemical shifts from 1-octene, MA, and 1,7-octadiene units, confirming the successful copolymerization of 1,7-octadiene with 1-octene and MA. Furthermore, it is noteworthy to observe the presence of residual double bonds in 1-

Table 3 Constitutions of copolymers synthesized in different solvent<sup>a</sup>

| # <sup>a</sup> | Solvent     | $F_{1\text{-octene}}$ (%) | $F_{\text{MA}}$ (%) | $M_n \times 10^{-4}$ ( $\text{g mol}^{-1}$ ) | $M_w \times 10^{-4}$ ( $\text{g mol}^{-1}$ ) | PDI <sup>b</sup> |
|----------------|-------------|---------------------------|---------------------|--|--|------------------|
| 1              | PhCl        | 38.14                     | 61.86               | 5.25   | 11.84  | 2.25             |
| 2              | 1,4-Dioxane | 35.43                     | 64.57               | 6.17   | 10.50  | 1.70             |

<sup>a</sup> Reaction conditions:  $n(1\text{-octene})/n(\text{MA}) = 2.87$ ;  $n(\text{Sc}(\text{OTf})_3)/n(\text{MA}) = 0.1$ ; Solvent: 30 ml; temperature  $40^\circ\text{C}$ ;  $n(\text{Initiator})/n(\text{Monomer}) = 0.001$ ;  $n(1,7\text{-octadiene})/n(\text{MA}) = 0.01$ . <sup>b</sup> Molecular weight distribution.



Table 4 Copolymer constitutions at different monomers concentration <sup>a</sup>

| # | [Monomers]<br>(mmol ml <sup>-1</sup> ) | Temp. (°C) | F <sub>1-octene</sub> (%) | F <sub>MA</sub> (%) | M <sub>n</sub> × 10 <sup>-4</sup> (g mol <sup>-1</sup> ) | M <sub>w</sub> × 10 <sup>-4</sup> (g mol <sup>-1</sup> ) | PDI <sup>b</sup> |
|---|--|------------|---------------------------|---------------------|--|--|------------------|
| 1 | 1.651                                  | 60         | 38.47                     | 61.53               | 4.09   | 8.72   | 2.13             |
| 2 | 2.384                                  | 60         | 38.53                     | 61.47               | 4.17   | 8.32   | 1.99             |
| 3 | 1.651                                  | 50         | 37.46                     | 62.54               | 5.72   | 10.53  | 1.84             |
| 4 | 2.384                                  | 50         | 38.34                     | 61.66               | 7.07   | 14.25  | 2.02             |

<sup>a</sup> Reaction conditions:  $n(1\text{-octene})/n(\text{MA}) = 2.87$ ;  $n(\text{Sc}(\text{OTf})_3)/n(\text{MA}) = 0.1$ ;  $n(\text{Initiator})/n(\text{Monomer}) = 0.001$ ; Initiator: AIBN;  $n(1,7\text{-octadiene})/n(\text{MA}) = 0.01$ . <sup>b</sup> Molecular weight distribution.

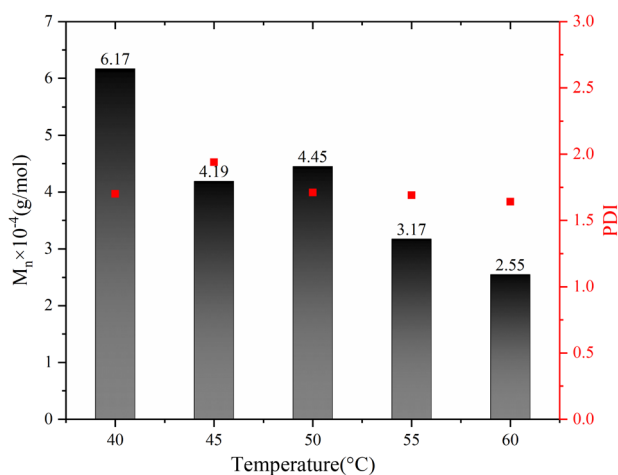


Fig. 10 The molecular weights and their distribution of the copolymers with polymerization temperature. Reaction conditions:  $n(1\text{-octene})/n(\text{MA}) = 2.87$ ;  $n(\text{Sc}(\text{OTf})_3)/n(\text{MA}) = 0.1$ ;  $n(\text{Initiator})/n(\text{Monomer}) = 0.001$ ;  $n(1,7\text{-octadiene})/n(\text{MA}) = 0.01$ .

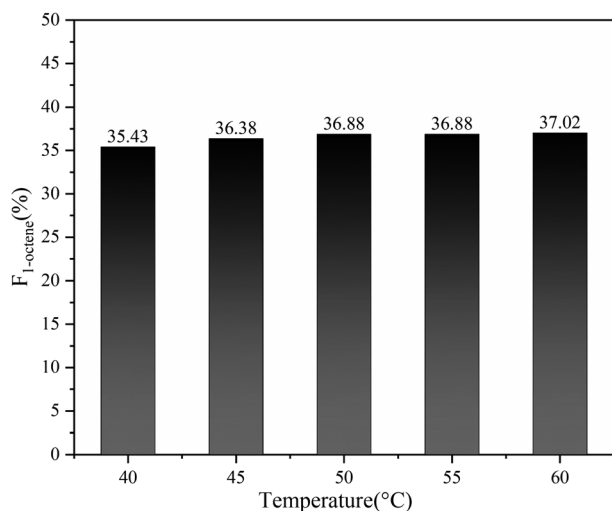


Fig. 11 The mole fractions of 1-octene unit (F<sub>1-octene</sub>) of copolymers with polymerization temperature. Reaction conditions:  $n(1\text{-octene})/n(\text{MA}) = 2.87$ ;  $n(\text{Sc}(\text{OTf})_3)/n(\text{MA}) = 0.1$ ;  $n(\text{Initiator})/n(\text{Monomer}) = 0.001$ ;  $n(1,7\text{-octadiene})/n(\text{MA}) = 0.01$ .

octene-MA-1,7-octadiene copolymers. The chemical shifts of 4.8 ppm and 5.7 ppm correspond to the H connected to C=C, suggesting that a portion of 1,7-octadiene contributes only one

ene-group for copolymerization with 1-octene and MA, while another ene-group remains available as a crosslinkable site.<sup>61-63</sup>

### 3.3 Influence of polymerization parameters on Sc(OTf)<sub>3</sub>-Catalyzed 1-octene/MA copolymerization

In order to gain a deeper understanding of the Sc(OTf)<sub>3</sub>-catalyzed 1-octene/MA copolymerization, a systematic investigation was conducted to examine the impact of polymerization parameters such as solvent, monomer concentration, and temperature. Moreover, copolymerization of  $\alpha$ -olefins with different chain lengths including 1-hexene, 1-decene and 1-tetradecane was also carried out to confirm the universality of this strategy.

Chlorobenzene and 1,4-dioxane, which are good solvent of Sc(OTf)<sub>3</sub>, were employed as solvents to carry out the Sc(OTf)<sub>3</sub>-catalyzed 1-octene/MA copolymerization. As shown in Table 3, Sc(OTf)<sub>3</sub>-catalyzed 1-octene/MA copolymerization has good suitability toward various solvents. However, it is noteworthy that the proportion of 1-octene units (F<sub>1-octene</sub>) slightly decreased in comparison to copolymer synthesized in DCM (F<sub>1-octene</sub> = 41%). This phenomenon may be attributed to the cation- $\pi$  interaction between Sc<sup>3+</sup> and the benzene ring in PhCl, or the coordination between Sc(OTf)<sub>3</sub> and the ether group in 1,4-dioxane. Such solvent effect could potentially weaken the MA-Sc(OTf)<sub>3</sub> complex, thereby resulting in an increase in the formation of MA-MA units in the resultant copolymers, and consequently causing the deviation of F<sub>MA</sub>/F<sub>1-octene</sub> from 1 : 1.

The impact of monomer concentration on the copolymerization was shown in Table 4. When the monomer concentration increased, the molecular weight of the copolymer increased and the molecular weight distribution remained relatively stable. The proportion of 1-octene in the copolymer composition remains relatively stable without obvious change. When the polymerization temperature is increased, the same law also applies. Higher monomer concentration can increase the collision probability between comonomer molecules, which is beneficial for chain growth and thus increases the molecular weight of the copolymer.<sup>64,65</sup> The good complexation between Sc(OTf)<sub>3</sub> and MA can satisfy the transfer of Sc(OTf)<sub>3</sub> from MA units in copolymer chain to MA monomer, facilitating the formation of alternating octene-MA structure and inhibiting the formation of homopolymer units.

The impact of polymerization temperature on the Sc(OTf)<sub>3</sub>-catalyzed 1-octene/MA copolymerization behaviors is shown Fig. 10 and 11. From Fig. 10, it can be seen that the molecular





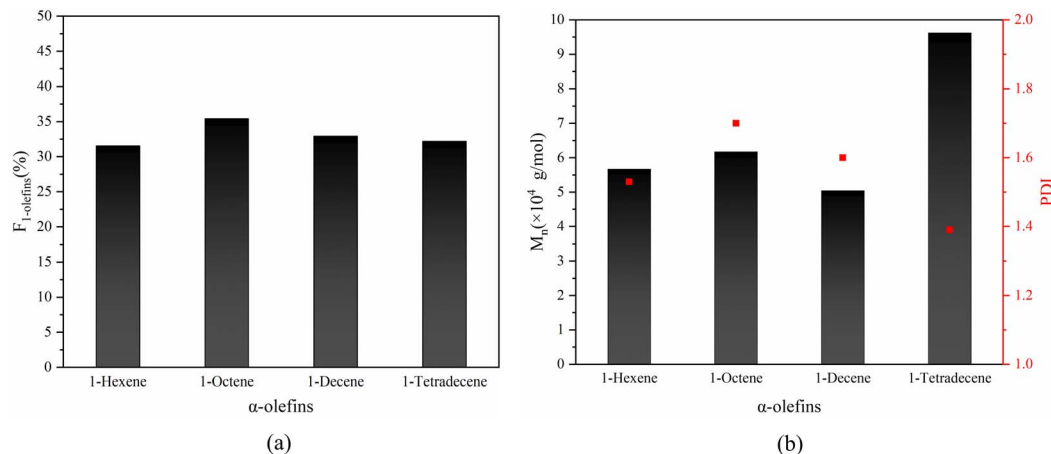


Fig. 12 The influence of different types  $\alpha$ -olefins on the mole fractions of  $\alpha$ -olefins unit ( $F_{1-\text{olefins}}$ ) (a) and the molecular weight/PDI (b) of copolymers. Reaction conditions:  $n(\text{Sc}(\text{OTf})_3)/n(\text{MA}) = 0.1$ ;  $n(\text{Initiator})/n(\text{Monomer}) = 0.001$ ;  $n(1,7\text{-octadiene})/n(\text{MA}) = 0.01$ ; temperature  $40^\circ\text{C}$ .

weight of the copolymer increased sharply with decreasing polymerization temperature, while the PDI remains relatively stable within the range of 1.60 to 1.95. The average molecular weight of the copolymer at a polymerization temperature of  $40^\circ\text{C}$  ( $6.17 \times 10^4$  g mol $^{-1}$ ) exceeds twice that of copolymer synthesized at a polymerization temperature of  $60^\circ\text{C}$  ( $2.55 \times 10^4$  g mol $^{-1}$ ). This result can be rationally explained as follows: The low temperature during the polymerization process helps to reduce the concentration of free radicals, which inhibits chain termination and transfer processes, thereby increasing the lifespan of free radicals.<sup>66–68</sup>

In addition, benefiting from the excellent capability of  $\text{Sc}(\text{OTf})_3$  in controlling the alternating sequence, 1-octene–MA copolymers synthesized at temperatures between  $40$ – $60^\circ\text{C}$  display a notably high proportion of 1-octene units, all exceeding 35%, as shown in Fig. 11.<sup>69,70</sup>

Based on the success in the synthesis of alternating 1-octene–MA copolymer,  $\alpha$ -olefins with different chain lengths such as 1-hexene, 1-decene and 1-tetradecene were also employed to copolymer with MA in the presence of  $\text{Sc}(\text{OTf})_3$ .

The  $^1\text{H}$  NMR spectrums of copolymer and equations for calculating the composition of the obtained copolymer are shown in Fig. S2–S4 $^\dagger$  and eqn (2) and S4 in the ESI. $^\dagger$  The results are shown in Fig. 12, the proportion of  $\alpha$ -olefins in the copolymer is above 30%, and the molecular weight reaches over  $5 \times 10^4$  g mol $^{-1}$ . This suggests that MA after complexing with  $\text{Sc}(\text{OTf})_3$  can copolymerize with different olefin monomers and maintain an alternating sequence structure of the copolymer. The strategy of increasing the molecular weight of copolymers mentioned earlier has universality for different long chain olefins.

Based on the successful synthesis of alternating 1-octene–MA copolymer,  $\alpha$ -olefins with varying chain lengths such as 1-hexene, 1-decene, and 1-tetradecene were also employed to copolymerize with MA in the presence of  $\text{Sc}(\text{OTf})_3$ . As depicted in Fig. 12, the proportion of  $\alpha$ -olefins in the copolymer exceeds 30%, and the molecular weight exceeds  $5 \times 10^4$  g mol $^{-1}$ . This indicates that MA, upon complexing with  $\text{Sc}(\text{OTf})_3$ , has the ability to copolymerize with various olefin monomers while preserving an alternating sequence structure in the resulting

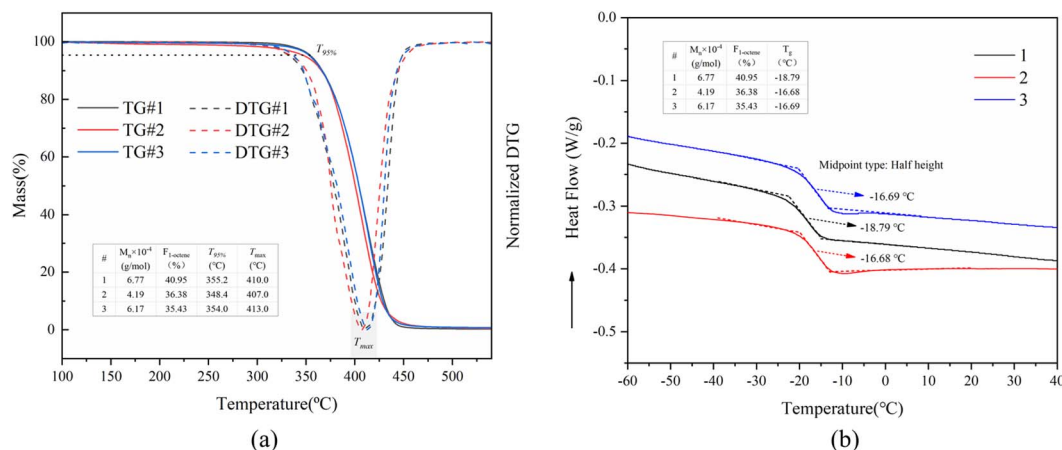


Fig. 13 TGA and DTG curves (a) and DSC curves (b) for poly(1-octene-*alt*-MA) copolymers with different mole fractions of 1-octene unit and molecular weight.



copolymer. The strategy of increasing the molecular weight of copolymers, as discussed previously, exhibits universality towards various  $\alpha$ -olefins.

Moreover, the impact of molecular weight ( $M_w$ ) and the proportion of 1-octene units ( $F_{1\text{-octene}}$ ) in poly(1-octene-*alt*-MA) copolymers on their thermal properties, specifically heat resistance and glass transition temperature ( $T_g$ ), was examined. The investigation involved analyzing the thermal decomposition performance of copolymers with varying  $M_w$  and  $F_{1\text{-octene}}$ . The results were shown in Fig. 13a, which indicate that the initial thermal decomposition temperature (temperature at 5% weight loss,  $T_{95\%}$ ) of poly(1-octene-*alt*-MA) is more responsive to changes in  $M_w$  than  $F_{1\text{-octene}}$ . An increase in  $M_w$  was observed to result in a noticeable rise in  $T_{95\%}$ , from 348.4 °C ( $4.19 \times 10^4$  g mol<sup>-1</sup>, curve 3 in Fig. 13a) to 355.2 °C ( $6.77 \times 10^4$  g mol<sup>-1</sup>, curve 1 in Fig. 13a) or 354.0 °C ( $6.17 \times 10^4$  g mol<sup>-1</sup>, curve 2 in Fig. 13). Furthermore, the influence of  $M_w$  and  $F_{1\text{-octene}}$  on the  $T_g$  of poly(1-octene-*alt*-MA) was investigated using DSC measurement. The findings revealed that  $T_g$  is more sensitive to changes in  $F_{1\text{-octene}}$  than  $M_w$ . Notably, an increase in the proportion of 1-octene unit led to a decrease in  $T_g$ , aligning with the expectation that a higher proportion of 1-octene unit enhances the flexibility of the molecular chain, thereby reducing  $T_g$ .<sup>74,72</sup> In conclusion, maintaining a high proportion of 1-octene and increasing the molecular weight of the copolymer are beneficial for expanding the potential temperature range for the practical application of poly(1-octene-*alt*-MA).

## 4 Conclusions

With the goal of developing a practical method to convert low-value  $\alpha$ -olefins, by-products of ethylene cracking process, into high-performance polymers, we successfully conducted alternating radical copolymerization of olefins with methyl acrylate using 1-octene as the representative of olefins. The control of the alternating sequence and molecular weight has been achieved by optimizing the polymerization parameters, such as monomer concentration and initiator dosage,  $n(\text{Sc}(\text{OTf})_3)/n(\text{MA})$  ratio, temperature, and copolymerizing with a difunctional comonomer. The results indicate that:

(1) A catalytic dosage  $\text{Sc}(\text{OTf})_3$  ( $n(\text{Sc}(\text{OTf})_3)/n(\text{MA}) = 0.1$ ) is sufficient to catalyze the alternating radical copolymerization of 1-octene and MA.

(2) Introducing 1,7-octadiene as “chain extender” to copolymerization with 1-octene and MA is an efficient way to significant increase the molecular weight, although its loading dosage needs to be finely controlled to avoid gelation. In addition, the carbon=carbon double bonds in 1,7-octadiene units not participating in the copolymerization can serve as crosslinking sites for further vulcanization.

(3) As the 1,4-dioxane is used as a solvent, the copolymer can completely dissolve while ensuring high molecular weight and almost alternating sequence structure, making it a more favorable solvent for subsequent material development. The molecular weight of the copolymer increases with the increase of monomer concentration and polymerization temperature.

(4) The strategy of maintaining the alternating sequence structure of copolymers and increasing the molecular weight of

copolymers is universal for different long chain  $\alpha$ -olefins such as 1-hexene and 1-decene.

(5) The initial decomposition temperature of the copolymer shows an upward trend with the increase of molecular weight. And the glass transition temperature of copolymers is generally below -16 °C, which decreases with the increase of the proportion of 1-octene in the copolymer.

This study has the potential to create new opportunities for producing high-performance polymers from  $\alpha$ -olefins, by-products of ethylene cracking process. This could help reduce the depletion of non-renewable petrochemical resources and enable their efficient and valuable utilization.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

We acknowledge the financial support from the Natural Science Foundation of Sichuan Province (No. 2023NSFSC0307).

## References

- 1 R. Geyer, J. R. Jambeck and K. L. Law, *Sci. Adv.*, 2017, **3**, e1700782.
- 2 C. W. S. Yeung, J. Y. Q. Teo, X. J. Loh and J. Y. C. Lim, *ACS Mater. Lett.*, 2021, **3**, 1660–1676.
- 3 C. Jehanno, J. W. Alty, M. Roosen, S. De Meester, A. P. Dove, E. Y.-X. Chen, F. A. Leibfarth and H. Sardon, *Nature*, 2022, **603**, 803–814.
- 4 G. Zanchin and G. Leone, *Prog. Polym. Sci.*, 2021, **113**, 101342.
- 5 Y. Xiao, P. Liu, W.-J. Wang and B.-G. Li, *Macromolecules*, 2021, **54**, 10381–10387.
- 6 L. Chen and Z. Lin, Polyethylene: Properties, Production and Applications, in *2021 3rd IEEE International Academic Exchange Conference on Science and Technology Innovation*, 2021, pp. 1191–1196.
- 7 D. Jubinville, E. Esmizadeh, S. Saikrishnan, C. Tzoganakis and T. Mekonnen, *Sustainable Mater. Technol.*, 2020, **25**, e00188.
- 8 M. Alabdullah, A. Rodriguez-Gomez, T. Shoinkhorova, A. Dikhtiarenko, A. D. Chowdhury, I. Hita, S. R. Kulkarni, J. Vittenet, S. M. Sarathy, P. Castaño, A. Bendjeriou-Sedjerari, E. Abou-Hamad, W. Zhang, O. S. Ali, I. Morales-Osorio, W. Xu and J. Gascon, *Nat. Catal.*, 2021, **4**, 233–241.
- 9 T. Ren, S. Liu, H. Li, A. Zhang, X. Li, W. Yuan and X. Gao, *Sep. Purif. Technol.*, 2022, **282**, 120012.
- 10 L. Guo, W. Chen, W. Wang, W. An, S. Gao, Y. Zhao, M. Luo, G. He and T. Liu, *J. Catal.*, 2022, **413**, 8–19.
- 11 G. Leone, M. Mauri, I. Pierro, G. Ricci, M. Canetti and F. Bertini, *Polymer*, 2016, **100**, 37–44.
- 12 A. Gollwitzer, T. Dietel, W. P. Kretschmer and R. Kempe, *Nat. Commun.*, 2017, **8**, 1226.
- 13 N. Patel, V. Valodkar and G. Tembe, *Polym. Chem.*, 2023, **14**, 2542–2571.



- 14 X.-Y. Wang, Y. Gao and Y. Tang, *Prog. Polym. Sci.*, 2023, **143**, 101713.
- 15 B. Young, T. R. Hawkins, C. Chiquelin, P. Sun, U. R. Gracida-Alvarez and A. Elgowainy, *J. Cleaner Prod.*, 2022, **359**, 131884.
- 16 J. Merna, P. Vlcek, V. Volkis and J. Michl, *Chem. Rev.*, 2016, **116**, 771–785.
- 17 C. Tan, C. Zou and C. Chen, *Macromolecules*, 2022, **55**, 1910–1922.
- 18 A. Schöbel, M. Winkenstette, T. M. J. Anselment and B. Rieger, *Copolymerization of Alkenes and Polar Monomers by Early and Late Transition Metal Catalysts*, 2012, vol. 3, pp. 779–823.
- 19 H. Zheng, Z. Qiu, D. Li, L. Pei and H. Gao, *J. Polym. Sci.*, 2023, **61**, 2987–3021.
- 20 C. Tan, M. Chen and C. Chen, *Trends Chem.*, 2023, **5**, 147–159.
- 21 Y. Zhang and Z. Jian, *Polym. Chem.*, 2022, **13**, 4966–4972.
- 22 S. Kawauchi, A. Akatsuka, Y. Hayashi, H. Furuya and T. Takata, *Polym. Chem.*, 2022, **13**, 1116–1129.
- 23 Z. Wu, Z. Wang, B.-W. Wang, C.-H. Peng and X. Fu, *Macromolecules*, 2020, **53**, 212–222.
- 24 M. Li, X. Wang, Y. Luo and C. Chen, *Angew. Chem., Int. Ed.*, 2017, **56**, 11604–11609.
- 25 T. Rünzi, D. Fröhlich and S. Mecking, *J. Am. Chem. Soc.*, 2010, **132**, 17690–17691.
- 26 Y.-N. Zhou, J.-J. Li, T.-T. Wang, Y.-Y. Wu and Z.-H. Luo, *Prog. Polym. Sci.*, 2022, **130**, 101555.
- 27 N. Corrigan, K. Jung, G. Moad, C. J. Hawker, K. Matyjaszewski and C. Boyer, *Prog. Polym. Sci.*, 2020, **111**, 101311.
- 28 X. Wang and H. Gao, *Polymers*, 2017, **9**, 188.
- 29 F. Li, F. Zhou, D. Romano and S. Rastogi, *Macromolecules*, 2023, **56**, 1995–2008.
- 30 A. Destephen, L. Lezama and N. Ballard, *Polym. Chem.*, 2020, **11**, 5757–5766.
- 31 J. Jiang, W.-J. Wang, B.-G. Li and S. Zhu, *Ind. Eng. Chem. Res.*, 2019, **58**, 18997–19008.
- 32 H. Lai, C. Jin, J. Park, R. Ikura, Y. Takashima and M. Ouchi, *Angew. Chem., Int. Ed.*, 2023, **62**, e202218597.
- 33 Z. Huang, Q. Shi, J. Guo, F. Meng, Y. Zhang, Y. Lu, Z. Qian, X. Li, N. Zhou and Z. Zhang, *Nat. Commun.*, 2019, **10**, 1918.
- 34 K. G. Goswami, S. Mete, S. S. Chaudhury, P. Sar, E. Ksendzov, C. D. Mukhopadhyay, S. V. Kostjuk and P. De, *ACS Appl. Polym. Mater.*, 2020, **2**, 2035–2045.
- 35 S. Han, P. Wen, H. Wang, Y. Zhou, Y. Gu, L. Zhang, Y. Shao-Horn, X. Lin and M. Chen, *Nat. Mater.*, 2023, 1–8.
- 36 S. Ida, M. Ouchi and M. Sawamoto, *J. Am. Chem. Soc.*, 2010, **132**, 14748–14750.
- 37 Y. Hibi, M. Ouchi and M. Sawamoto, *Nat. Commun.*, 2016, **7**, 11064.
- 38 M. Ouchi, *Polym. J.*, 2020, **53**, 239–248.
- 39 C. Yang, K. B. Wu, Y. Deng, J. Yuan and J. Niu, *ACS Macro Lett.*, 2021, **10**, 243–257.
- 40 X. Xia, R. Suzuki, T. Gao, T. Isono and T. Satoh, *Nat. Commun.*, 2022, **13**, 163.
- 41 J.-F. Lutz, M. Ouchi, D. R. Liu and M. Sawamoto, *Science*, 2013, **341**, 6146.
- 42 A. L. Logothetis and J. M. McKenna, *J. Polym. Sci., Polym. Chem. Ed.*, 2003, **15**, 1431–1439.
- 43 A. L. Logothetis and J. M. McKenna, *J. Polym. Sci., Polym. Chem. Ed.*, 2003, **15**, 1441–1455.
- 44 Y. Chen and A. Sen, *Macromolecules*, 2009, **42**, 3951–3957.
- 45 A. L. Logothetis and J. M. McKenna, *J. Polym. Sci., Polym. Lett. Ed.*, 2003, **12**, 131–137.
- 46 M. Hirooka, H. Yabuuchi, S. Morita, S. Kawasumi and K. Nakaguchi, *J. Polym. Sci., Part B: Polym. Lett.*, 2003, **5**, 47–55.
- 47 M. Imoto, T. Otsu, B. Yamada and A. Shimizu, *Macromol. Chem. Phys.*, 1965, **82**, 277–280.
- 48 M. Nagel, D. Poli and A. Sen, *Macromolecules*, 2005, **38**, 7262–7265.
- 49 S. Akita and K. Nozaki, *Polym. J.*, 2021, **53**, 1057–1060.
- 50 H. Fan, Y. Liao and S. Dai, *Polymer*, 2022, **254**, 125076.
- 51 C. Xiao, Y. Yu, L. Jiang and Y. Dan, *Ind. Eng. Chem. Res.*, 2018, **57**, 16604–16614.
- 52 C. Xiao, L. Jiang and Y. Dan, *Ind. Eng. Chem. Res.*, 2019, **58**, 7857–7865.
- 53 R. Luo and A. Sen, *Macromolecules*, 2007, **40**, 154–156.
- 54 J. Otera, *Modern Carbonyl Chemistry*, John Wiley & Sons, 2008.
- 55 J. E. Gautrot, P. Hodge, D. Cupertino and M. Helliwell, *New J. Chem.*, 2006, **30**, 1801–1807.
- 56 S. Kaur, G. Singh and V. K. Gupta, *J. Polym. Sci., Part A: Polym. Chem.*, 2009, **47**, 2156–2162.
- 57 T. Zhao, Y. Zheng, J. Poly and W. Wang, *Nat. Commun.*, 2013, **4**, 1873.
- 58 R. Chanerika, M. L. Shoji, M. Prato and H. B. Friedrich, *Catalysts*, 2023, **13**, 746.
- 59 A. Ali, M. K. Tufail, M. I. Jamil, W. Yaseen, N. Iqbal, M. Hussain, A. Ali, T. Aziz, Z. Fan and L. Guo, *Molecules*, 2021, **26**, 2037.
- 60 Y. Wang, R. Gao, Q. Gou, J. Lai, R. Zhang, X. Li and Z. Guo, *Eur. Polym. J.*, 2022, **181**, 111693.
- 61 Y. Liu, Y. Qin and J.-Y. Dong, *Ind. Eng. Chem. Res.*, 2020, **59**, 12038–12047.
- 62 H. Chen and J. Kong, *Polym. Chem.*, 2016, **7**, 3643–3663.
- 63 H. Li, G. Rojas and K. B. Wagener, *ACS Macro Lett.*, 2015, **4**, 1225–1228.
- 64 R. Han, S. Lu, Y. Wang, X. Zhang, Q. Wu and T. He, *Electrochim. Acta*, 2015, **173**, 796–803.
- 65 R. Ye, X. Sun, X. Mao, F. S. Alfonso, S. Baral, C. Liu, G. W. Coates and P. Chen, *Nat. Chem.*, 2024, **16**, 210–217.
- 66 L. Sollka and K. Lienkamp, *Macromol. Rapid Commun.*, 2020, **42**, 2000546.
- 67 J. M. Kaiser and B. K. Long, *Coordin. Chem. Rev.*, 2018, **372**, 141–152.
- 68 T. Pirman, M. Oceppek and B. Likozar, *Ind. Eng. Chem. Res.*, 2021, **60**, 9347–9367.
- 69 L. Zhong, H. Zheng, C. Du, W. Du, G. Liao, C. S. Cheung and H. Gao, *J. Catal.*, 2020, **384**, 208–217.
- 70 R. Kalepu and S. Mishra, *Chem. Sci. J.*, 2020, **132**, 48.
- 71 Y. Kametani and M. Ouchi, *ACS Polym. Au*, 2021, **1**, 10–15.
- 72 C.-C. Huang, M.-X. Du, B.-Q. Zhang and C.-Y. Liu, *Macromolecules*, 2022, **55**, 3189–3200.

