

Cite this: *Chem. Sci.*, 2024, 15, 18896

All publication charges for this article have been paid for by the Royal Society of Chemistry

Received 7th May 2024  
Accepted 5th October 2024

DOI: 10.1039/d4sc02995j

rsc.li/chemical-science

# Quantitative analysis of air-oxidation reactions of thiolate-protected gold nanoclusters†

Wataru Suzuki,<sup>‡a</sup> Ryo Takahata,<sup>‡ab</sup> Yoshiyuki Mizuhata,<sup>‡abc</sup>  
Norihiro Tokitoh,<sup>‡abc</sup> Songlin Xue<sup>‡d</sup> and Toshiharu Teranishi<sup>‡\*ab</sup>

The interaction of dioxygen (O<sub>2</sub>) with inorganic nanomaterials is one of the most essential steps to understanding the reaction mechanism of O<sub>2</sub>-related reactions. However, quantitative analyses for O<sub>2</sub>-binding processes and subsequent oxidation reactions on the surface are still elusive, whereas the reaction of O<sub>2</sub> with molecules such as transition metal complexes has been widely explored. Herein, we have quantitatively evaluated reaction processes of air-oxidation reactions of atomically precise thiolate-protected Au<sub>25</sub> nanoclusters ([Au<sub>25</sub>(SR)<sub>18</sub>]<sup>−</sup>) as a model of O<sub>2</sub> activation by inorganic nanomaterials. Kinetic analyses on the air-oxidation reaction of [Au<sub>25</sub>(SR)<sub>18</sub>]<sup>−</sup> revealed a controlling factor for O<sub>2</sub>-activation processes, which could be finely tunable by the protecting thiolate ligands.

## Introduction

Dioxygen (O<sub>2</sub>) activation in O<sub>2</sub> reduction and aerobic oxidations is one of the most fundamental and crucial reaction processes in chemistry. So far, many catalysts for O<sub>2</sub> activation have been developed by employing molecular catalysts<sup>1–3</sup> and inorganic nanomaterials, including metal nanoparticles (MNPs)<sup>4–6</sup> and metal nanoclusters (MNCs).<sup>7–9</sup> An understanding of the reaction mechanisms of O<sub>2</sub>-activation processes at the atomic level is essential to develop more efficient catalysts. Hence, mechanistic insights into O<sub>2</sub> activation have also been investigated.<sup>10–13</sup> For molecular catalysts such as Fe, Co and Cu complexes or organocatalysts such as porphyrinoids, O<sub>2</sub>-activation processes, including O<sub>2</sub>-binding and subsequent reduction to form reactive O<sub>2</sub> species, were experimentally well-revealed through structural<sup>10</sup> and kinetic<sup>11</sup> analyses based on experimental evidence. In contrast, because reaction systems with MNPs are relatively complicated due to the distributions of size and composition of MNPs, the understanding of the reaction mechanisms for the O<sub>2</sub>-activation process at the atomic level is quite a difficult challenge. Thus, estimations of such a reaction mechanism have mainly relied on theoretical analysis until now.<sup>12</sup>

Compared with MNPs, MNCs with sizes of less than 2 nm are considered a desirable model to reveal detailed reaction mechanisms at the atomic level owing to their atomically precise structures.<sup>14</sup> Among various MNCs, gold nanoclusters (AuNCs), such as thiolate-protected gold clusters (denoted as Au<sub>n</sub>(SR)<sub>m</sub>, SR = thiolate), are appropriate candidates to perform atomically precise analyses on O<sub>2</sub>-activation processes using inorganic nanomaterials because of their tunable reactivities, easy preparation and good stability.<sup>7,15,16</sup> For example, the thiolate-protected Au<sub>25</sub> cluster anion ([Au<sub>25</sub>(SR)<sub>18</sub>]<sup>−</sup>) exhibited reactivity towards O<sub>2</sub>, as seen in the catalytic oxygen reduction reaction (ORR).<sup>17</sup> The catalytic activity of [Au<sub>25</sub>(SR)<sub>18</sub>]<sup>−</sup> in the ORR could be tuned by the type of thiolate ligand<sup>17a</sup> and heteroatom doping.<sup>17b</sup> In addition, [Au<sub>25</sub>(SR)<sub>18</sub>]<sup>−</sup> which shows higher reactivity than other AuNCs with different sizes<sup>17c</sup> is a promising material for practical use. Together with the ORR, the reactions of [Au<sub>25</sub>(SR)<sub>18</sub>]<sup>−</sup> with O<sub>2</sub> are also important in the reductive activation of O<sub>2</sub> for substrate oxidation, which was seen in the aerobic oxidation of thiols to form disulfide in Au<sub>25</sub> polymer films.<sup>18</sup> In both cases, the interaction of O<sub>2</sub> on the surface of the Au<sub>25</sub> cluster and reduction of O<sub>2</sub>, namely Au<sub>25</sub> cluster oxidation,<sup>19,20</sup> are proposed to be crucial processes as an initial step for O<sub>2</sub> activation. However, whereas some reports demonstrated the interaction between O<sub>2</sub> and [Au<sub>25</sub>(SR)<sub>18</sub>]<sup>−</sup> using mass spectrometry<sup>21</sup> or theoretical analysis,<sup>13d,f,17d</sup> experimental evidence for the O<sub>2</sub> binding and/or activation by AuNCs is still limited. In particular, the air-oxidation reaction of [Au<sub>25</sub>(SR)<sub>18</sub>]<sup>−</sup> was analysed just qualitatively,<sup>22</sup> but quantitative analysis for O<sub>2</sub> activation by AuNCs, which is important to systematically evaluate the reactivities of AuNCs, has yet to be reported.

Herein, we report quantitative analyses of the air-oxidation reactions of AuNCs based on kinetic analysis for the first time. For a model of AuNCs, we chose [Au<sub>25</sub>(SR)<sub>18</sub>]<sup>−</sup> because of

<sup>a</sup>Institute for Chemical Research, Kyoto University, Uji, Kyoto, 611-0011, Japan. E-mail: teranishi@scl.kyoto-u.ac.jp

<sup>b</sup>Graduate School for Science, Kyoto University, Uji, Kyoto, 611-0011, Japan


<sup>c</sup>Integrated Research Consortium on Chemical Sciences, Uji, Kyoto, 611-0011, Japan

<sup>d</sup>School of Chemistry and Chemical Engineering, Jiangsu University, 301 Xuefu Road, Zhenjiang 212013, China

† Electronic supplementary information (ESI) available. CCDC 2299526. For ESI and crystallographic data in CIF or other electronic format see DOI: <https://doi.org/10.1039/d4sc02995j>

‡ Present Address: University of Hyogo, Himeji, 671-2280, Japan.



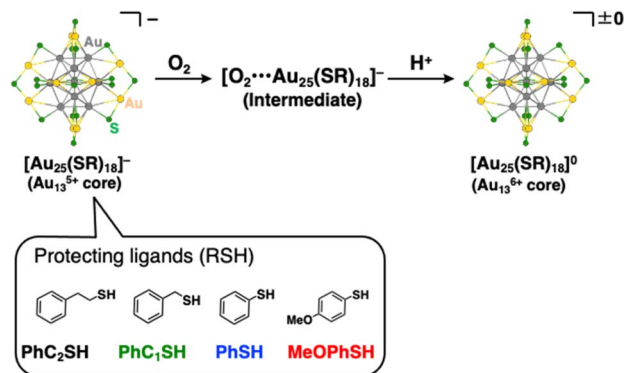

Scheme 1 Reaction scheme for air-oxidation reactions of  $[\text{Au}_{25}(\text{SR})_{18}]^-$  employed in this work. R groups were omitted for clarity. Atom labels: grey: gold in the Au<sub>13</sub> core, yellow: gold on the staple, and green: sulfur.

its reversible redox properties<sup>20</sup> and a variety of choices for protecting ligands.<sup>14,23</sup> The Au<sub>25</sub> cluster anions are composed of an Au<sub>13</sub><sup>5+</sup> core surrounded by six  $[\text{Au}_2(\text{SR})_3]^-$  units, and the oxidation reactions of the gold cluster occur in the Au<sub>13</sub> core rather than in staple moieties.<sup>19b</sup> Evaluations of the reactivities of  $[\text{Au}_{25}(\text{SR})_{18}]^-$  with O<sub>2</sub> were conducted in the presence of protons (Scheme 1). The addition of protons can promote the electron transfer reaction to reduce O<sub>2</sub> through proton-coupled electron transfer (PCET)<sup>24</sup> and this reaction system has a big advantage of facile quantitative analysis of the reactivity, as seen in the mechanistic analysis of O<sub>2</sub> reduction by organic molecules<sup>3c,25</sup> or transition metal complexes.<sup>26</sup> We have controlled redox potentials and O<sub>2</sub>-affinities of  $[\text{Au}_{25}(\text{SR})_{18}]^-$  by changing the thiolate (SR) ligands and revealed controlling factors in air-oxidation reactions of  $[\text{Au}_{25}(\text{SR})_{18}]^-$  to form neutral  $[\text{Au}_{25}(\text{SR})_{18}]^0$ .

## Results and discussion

### Synthesis and characterisation of thiolate-protected Au<sub>25</sub> cluster anions

Synthesis of the phenylethanethiolate-protected Au<sub>25</sub> cluster anion ( $\text{TOA}^+[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$ , TOA<sup>+</sup> = tetraoctylammonium) was conducted through the reduction of Au(I)-thiolate complexes according to the previous report.<sup>27</sup> Other Au<sub>25</sub> clusters ( $\text{TOA}^+[\text{Au}_{25}(\text{SR})_{18}]^-$ ) with different thiolate ligands (phenylmethanethiol (**PhC<sub>1</sub>SH**), thiophenol (**PhSH**) and 4-methoxythiophenol (**MeOPhSH**)) were synthesized using ligand-exchange reactions. Phenylmethanethiolate-protected Au<sub>25</sub> cluster anions ( $\text{TOA}^+[\text{Au}_{25}(\text{SC}_1\text{Ph})_{18}]^-$ ) were successfully synthesized through the ligand-exchange reaction of  $\text{TOA}^+[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$  with excess amounts of **PhC<sub>1</sub>SH** in CH<sub>2</sub>Cl<sub>2</sub>.  $\text{TOA}^+[\text{Au}_{25}(\text{SPh})_{18}]^-$  and  $\text{TOA}^+[\text{Au}_{25}(\text{SPhOMe})_{18}]^-$  were prepared by the ligand-exchange reaction of the cyclohexanethiolate-protected Au<sub>23</sub> cluster ( $\text{TOA}^+[\text{Au}_{23}(\text{SCy})_{16}]^-$ , SCy = cyclohexanethiolate) with **PhSH** or **MeOPhSH** (see the ESI<sup>†</sup> for detailed synthetic methods).<sup>28</sup> A series of thiolate-protected Au<sub>25</sub> cluster anions were characterised using UV-vis absorption spectroscopy, <sup>1</sup>H NMR, ESI-MS and X-ray

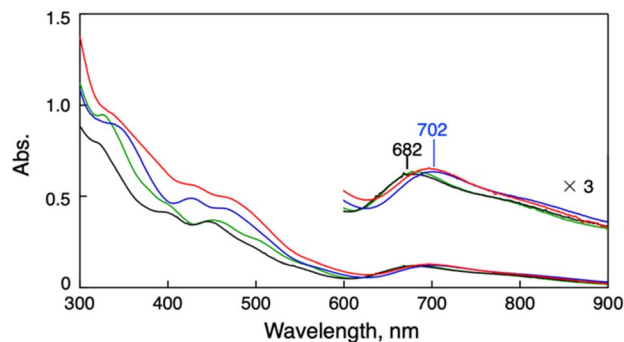


Fig. 1 UV-vis spectra of  $\text{TOA}^+[\text{Au}_{25}(\text{SR})_{18}]^-$  (0.010 mM) in THF. SR = SC<sub>2</sub>Ph (black), SC<sub>1</sub>Ph (green), SPh (blue) and SPhOMe (red).

absorption fine structure (XAFS) measurements (Fig. 1 and S1–S6<sup>†</sup>). In negative-mode ESI-MS spectra (Fig. S1<sup>†</sup>) of  $\text{TOA}^+[\text{Au}_{25}(\text{SR})_{18}]^-$ , peaks from  $[\text{Au}_{25}(\text{SR})_{18}]^-$  were clearly observed as well as the results of <sup>1</sup>H NMR spectroscopy (Fig. S2–S5<sup>†</sup>), supporting the high purity of the products. UV-vis absorption spectra of all products in tetrahydrofuran (THF) showed similar spectral features with a thiolate-protected Au<sub>25</sub> cluster anion,<sup>22</sup> that is, the absorption bands at around 400 nm and 700 nm and a shoulder peak at ca. 800 nm (Fig. 1). The absorption peak at around 700 nm, which is mainly derived from a Au<sub>13</sub> core-to-core transition,<sup>29</sup> was slightly red-shifted from  $\text{TOA}^+[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$  (682 nm) to  $\text{TOA}^+[\text{Au}_{25}(\text{SPh})_{18}]^-$  (702 nm). These shifts of absorption bands were caused by the differences in the electronic effects of thiolate ligands.<sup>30</sup> By contrast, the shape of absorption bands in the higher energy region was clearly different depending on the SR ligands because of the direct contribution of protecting ligands to the electronic transitions.<sup>29</sup> The structural features of a series of Au<sub>25</sub> cluster anions were compared using Au-L<sub>3</sub> edge XAFS measurements at 10 K with transmission mode (Fig. S6 and Table S1<sup>†</sup>). Extended XAFS (EXAFS) analysis showed that structures of all Au<sub>25</sub> cluster anions employed in this work showed similar structural parameters (Table S1<sup>†</sup>). Moreover,

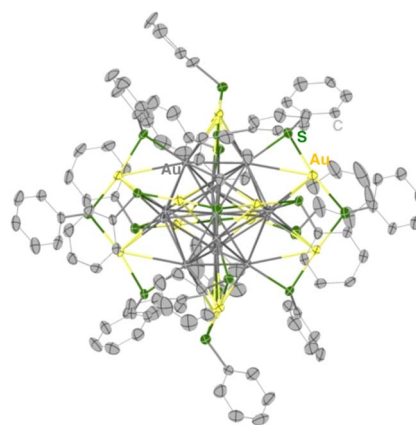


Fig. 2 A thermal ellipsoid plot (50% probability) of  $\text{TOA}^+[\text{Au}_{25}(\text{SPh})_{18}]^-$ . The TOA cation, solvent molecules, and hydrogen atoms were omitted for clarity. Atom labels: grey: gold in the Au<sub>13</sub> core, yellow: gold on the staple, green: sulfur, and light grey: carbon.



the solid-state structure of  $\text{TOA}^+[\text{Au}_{25}(\text{SPh})_{18}]^-$  was clarified using single-crystal X-ray crystallographic analysis (Fig. 2 and S7†). The anionic part in  $\text{TOA}^+[\text{Au}_{25}(\text{SPh})_{18}]^-$  has a  $\text{Au}_{13}$  icosahedral core ( $\text{Au}_{13}^{5+}$ ) with six dimeric staple moieties ( $[\text{Au}_2(\text{SR})_3]^-$ ), which are typical components for the  $\text{Au}_{25}$  cluster anion. The average Au–Au and Au–S bond lengths, summarized in Table S2,† were comparable to those of previously reported  $\text{TOA}^+[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$ .<sup>16</sup>

To determine the redox potentials of  $\text{Au}_{25}$  clusters, cyclic voltammetry (CV) and differential pulse voltammetry on a series of  $\text{Au}_{25}$  cluster anions were performed in THF containing TBAPF<sub>6</sub> as an electrolyte (Fig. S8†). The cyclic voltammogram of  $\text{TOA}^+[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$  showed two reversible redox waves at  $E_{1/2} = +0.06$  V and  $+0.41$  V vs. SCE (Fig. S8a†). These two redox waves could be assigned to the redox couples of  $\text{Au}_{25}^-/\text{Au}_{25}^0$  and  $\text{Au}_{25}^0/\text{Au}_{25}^+$ , respectively.<sup>20</sup> The first  $E_{1/2}$  values were positively shifted with decreasing electron-donating abilities of thiolate ligands;<sup>30</sup> for  $\text{TOA}^+[\text{Au}_{25}(\text{SC}_1\text{Ph})_{18}]^-$ , the first oxidation wave was observed at  $+0.16$  V vs. SCE owing to the weaker electron-donating ability of  $\text{SC}_1\text{Ph}$  than that of  $\text{SC}_2\text{Ph}$ . The largest shift of  $E_{1/2}$  ( $=+0.26$  V vs. SCE) was seen for  $\text{TOA}^+[\text{Au}_{25}(\text{SPh})_{18}]^-$  (Fig. S8d†) with the weakest electron-donating ligands in this work. It should be noted that the  $E_{1/2}$  value in the redox couple of  $\text{Au}_{25}^-/\text{Au}_{25}^0$  for  $\text{TOA}^+[\text{Au}_{25}(\text{SPhOMe})_{18}]^-$  ( $E_{1/2} = +0.17$  V vs. SCE) is almost the same as that for  $\text{TOA}^+[\text{Au}_{25}(\text{SC}_1\text{Ph})_{18}]^-$  (Table 1 and Fig. S8b, c†). As well as the redox properties of  $[\text{Au}_{25}(\text{SR})_{18}]^-$ , the affinity with  $\text{O}_2$  should be one of the essential factors to determine reactivities with  $\text{O}_2$ . The  $\text{O}_2$ -affinities of inorganic nanomaterials would be affected by surface environments including structures of protecting ligands. Thus, the two kinds of  $[\text{Au}_{25}(\text{SR})_{18}]^-$ , with the same redox potentials but different surface ligands, could provide meaningful insights into the correlation between the  $\text{O}_2$ -affinity and the reactivities of  $\text{Au}_{25}$  clusters.

### Air-oxidation reactions of thiolate-protected $\text{Au}_{25}$ clusters

Air-oxidation reactions of  $\text{TOA}^+[\text{Au}_{25}(\text{SR})_{18}]^-$  were monitored by UV-vis spectroscopic measurements. First, we evaluated the stability of  $\text{TOA}^+[\text{Au}_{25}(\text{SR})_{18}]^-$  (0.010 mM) in air-saturated THF at 298 K for 24 h (Fig. S9†). The lack of spectroscopic changes indicates that all  $\text{TOA}^+[\text{Au}_{25}(\text{SR})_{18}]^-$  are highly stable in the absence of any proton sources. Jin and co-workers reported photo-mediated oxidation reactions of  $[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$  under ambient light exposure,<sup>13d</sup> but such oxidation reactions were not observed in our reaction system. Thus, the light irradiation from the UV-vis spectroscopic device could not induce the

photo-induced oxidation reaction and we have excluded the light-mediated effect from our reaction system. By contrast, in the presence of a Brønsted acid like trifluoroacetic acid (TFA, 0.25 mM), the absorption at 445 nm and around 800 nm of  $\text{TOA}^+[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$  slightly decreased and a new absorption band at around 630 nm appeared (Fig. 3a). In addition, the absorption peak at around 400 nm became sharper. Such spectral change was also observed even in the presence of a small amount of TFA (0.050 mM, Fig. S10†). The UV-vis absorption feature of the final product indicates the formation of  $[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^0$ , a one-electron oxidized product of  $[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$  (eqn (1)).<sup>22</sup> The formation of  $[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^0$  was also confirmed by <sup>1</sup>H NMR (Fig. S11†) and CV measurements of  $[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$  (Fig. S12†). In the <sup>1</sup>H NMR spectrum, air-oxidation of  $\text{TOA}^+[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$  in THF-*d*<sub>8</sub> gave a new peak at 5.17 ppm (Fig. S11a and b†), which was in good agreement with that from  $[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^0$  (Fig. S11c†), supporting the formation of an one-electron-oxidized  $\text{Au}_{25}$  cluster. In the electrochemical measurements on  $\text{TOA}^+[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$ , the open circuit potential (OCP) was determined to be  $-0.03$  V vs. SCE in the absence of TFA, which was more negative than  $E_{1/2}$  ( $\text{Au}_{25}^-/\text{Au}_{25}^0$ ) of  $[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$  ( $+0.06$  V vs. SCE). Upon addition of TFA, OCP shifted to  $+0.21$  V vs. SCE, which was positioned between  $E_{1/2}$  ( $\text{Au}_{25}^-/\text{Au}_{25}^0$ ) and  $E_{1/2}$  ( $\text{Au}_{25}^0/\text{Au}_{25}^+$ ). Moreover, the negative potential sweep from  $+0.21$  V showed a clear reduction wave assigned with the reduction of

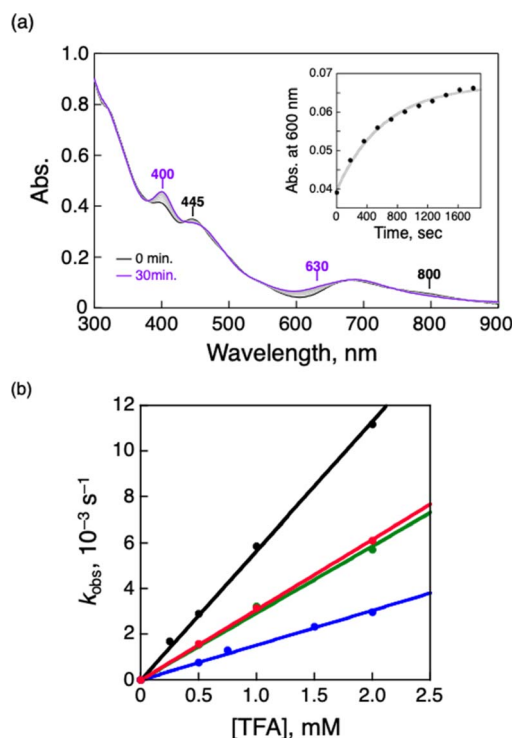



Fig. 3 (a) UV-vis spectral change of  $\text{TOA}^+[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$  (0.010 mM) in air-saturated THF containing TFA (0.25 mM) at 298 K. Inset: the time profile of absorbance at 600 nm. (b) [TFA] dependence of  $k_{\text{obs}}$  in the air-oxidation reaction of  $\text{TOA}^+[\text{Au}_{25}(\text{SR})_{18}]^-$  in air-saturated THF at 298 K. SR =  $\text{SC}_2\text{Ph}$  (black),  $\text{SC}_1\text{Ph}$  (green),  $\text{SPhOMe}$  (red) and  $\text{SPh}$  (blue).  $[\text{O}_2] = 2.2$  mM.<sup>31</sup>

Table 1 Summary of redox potentials of  $\text{TOA}^+[\text{Au}_{25}(\text{SR})_{18}]^-$  in THF containing 0.1 M TBAPF<sub>6</sub> under Ar

SR	$E_{1/2}$ ( $\text{Au}_{25}^-/\text{Au}_{25}^0$ ) V, vs. SCE	$E_{1/2}$ ( $\text{Au}_{25}^0/\text{Au}_{25}^+$ ) V, vs. SCE
<b>SC<sub>2</sub>Ph</b>	+0.06	+0.41
<b>SC<sub>1</sub>Ph</b>	+0.16	+0.50
<b>SPhOMe</b>	+0.17	+0.41
<b>SPh</b>	+0.26	+0.54



$[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^0$  to  $[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$ . This electrochemical evidence strongly supports the formation of the neutral  $\text{Au}_{25}$  cluster. The resulting  $[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^0$  formed under UV-vis spectroscopic conditions could be reduced to  $[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$  quantitatively (Fig. S13†) by reductants such as sodium borohydride ( $\text{NaBH}_4$ ). The reversible behaviour of  $\text{Au}_{25}^-/\text{Au}_{25}^0$  conversion was also observed even at a high TFA concentration (10 mM, Fig. S14†). This complete reversibility indicates that no side reactions such as decompositions of  $\text{Au}_{25}$  clusters occur, suggesting that  $[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$  is desirable as a highly durable redox catalyst.



$$\begin{aligned} d[\text{Au}_{25}(\text{SR})_{18}]/dt &= k_{\text{obs}}[\text{Au}_{25}(\text{SR})_{18}]^- \\ &= k[\text{TFA}][[\text{Au}_{25}(\text{SR})_{18}]^-] \end{aligned} \quad (2)$$


To perform the kinetic analysis in the formation of  $[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^0$ , the pseudo-first-order rate constant ( $k_{\text{obs}}$ ) was determined to be  $(1.6 \pm 0.1) \times 10^{-3} \text{ s}^{-1}$  at 298 K from the time course of the UV-vis spectral change at 600 nm (Fig. 3a, inset). A linear correlation was observed between the TFA concentration and  $k_{\text{obs}}$  (Fig. 3b, black), indicating that only one proton was involved in the oxidation reaction. The second-order rate constant ( $k$  in eqn (1) and (2)) could be determined to be  $(5.65 \pm 0.06) \text{ M}^{-1} \text{ s}^{-1}$  from the slope. It should be noted that no oxidation reaction of  $[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$  occurred in deaerated THF (Fig. S15†). Therefore,  $\text{O}_2$  should be an oxidant for  $[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$  in this reaction system. In addition, no change in optical properties of  $[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$  upon addition of TFA under the degassed conditions suggests no interaction between the  $\text{Au}_{25}$  cluster and TFA (Fig. S15†). Therefore, TFA should play a role in acceleration of  $\text{Au}_{25}$  cluster air-oxidation, namely  $\text{O}_2$  reduction through PCET, in which an electron transfer from  $[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$  to  $\text{O}_2$  and a proton comes from a Brønsted acid.<sup>24</sup> Other  $\text{TOA}^+[\text{Au}_{25}(\text{SR})_{18}]^-$  ( $\text{SR} = \text{SC}_1\text{Ph}$ ,  $\text{SPh}$  and  $\text{SPhOMe}$ ) were also oxidized to form corresponding neutral  $[\text{Au}_{25}(\text{SR})_{18}]^0$  in air-saturated THF containing TFA, as observed by the UV-vis spectral change (Fig. S16†). In addition, each  $[\text{Au}_{25}(\text{SR})_{18}]^0$  could be fully recovered to the corresponding anionic species by the addition of  $\text{NaBH}_4$ , indicating high durability of these  $\text{Au}_{25}^-/\text{Au}_{25}^0$  redox reaction systems (Fig. S17†). Kinetic analyses were performed to determine  $k$  values (Fig. 3b), which are

Table 2 Summary of rate constants ( $k$  and  $k_2$ ) and equilibrium constants ( $K$ ) in the air oxidation of  $\text{TOA}^+[\text{Au}_{25}(\text{SR})_{18}]^-$  in THF in the presence of TFA<sup>a</sup>

SR	$k, \text{M}^{-1} \text{s}^{-1}$	$k_2, \text{s}^{-1}$	$K, \text{mM}^{-1}$
$\text{SC}_2\text{Ph}$	$5.65 \pm 0.06$	$9.9 \pm 0.3$	$0.20 \pm 0.01$
$\text{SC}_1\text{Ph}$	$2.93 \pm 0.08$	$4.2 \pm 0.1$	$0.26 \pm 0.03$
$\text{SPhOMe}$	$3.19 \pm 0.01$	$3.67 \pm 0.03$	$0.34 \pm 0.01$
$\text{SPh}$	$1.51 \pm 0.02$	$1.35 \pm 0.01$	$0.55 \pm 0.01$

<sup>a</sup> At 298 K.  $[\text{Au}_{25}(\text{SR})_{18}]^- = 0.010 \text{ mM}$ .

summarized in Table 2. The oxidation reaction of  $[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$  with the lowest one-electron oxidation potential (+0.06 V vs. SCE, Table 1) showed the highest  $k$  value, whereas the lowest  $k$  value was confirmed in  $\text{TOA}^+[\text{Au}_{25}(\text{SPh})_{18}]^-$  with the highest  $E_{1/2}$  among  $\text{TOA}^+[\text{Au}_{25}(\text{SR})_{18}]^-$  in this work. The reactivities of  $\text{TOA}^+[\text{Au}_{25}(\text{SC}_1\text{Ph})_{18}]^-$  and  $\text{TOA}^+[\text{Au}_{25}(\text{SPhOMe})_{18}]^-$  were almost the same despite the different types of SR moieties (benzylic and aromatic thiolate, respectively). Considering the similar  $E_{1/2}$  values between  $\text{TOA}^+[\text{Au}_{25}(\text{SC}_1\text{Ph})_{18}]^-$  and  $\text{TOA}^+[\text{Au}_{25}(\text{SPhOMe})_{18}]^-$  (Table 1), the redox potential of  $\text{TOA}^+[\text{Au}_{25}(\text{SR})_{18}]^-$  should be one of the main controlling factors to determine the reactivities with  $\text{O}_2$ .



$$k_{\text{obs}} = \frac{k_2 K [\text{O}_2]}{1 + K [\text{O}_2]} \quad (4)$$

Häkkinen and co-workers demonstrated that small molecules such as  $\text{O}_2$  were able to access the surface of ligand-protected AuNCs, which would play an important role in small molecule activation.<sup>32</sup> Then, to examine the interaction of the surface of  $[\text{Au}_{25}(\text{SR})_{18}]^-$  with  $\text{O}_2$  during air-oxidation reactions, kinetic analyses were performed by changing the concentration of  $\text{O}_2$  in THF (Fig. 4). The pseudo-first-order rate constants ( $k_{\text{obs}}$ ) of the air-oxidation reaction of  $\text{TOA}^+[\text{Au}_{25}(\text{SR})_{18}]^-$  showed saturation behaviour on increasing the concentration of  $\text{O}_2$ , suggesting the existence of a pre-equilibrium between  $\text{TOA}^+[\text{Au}_{25}(\text{SR})_{18}]^-$  and  $\text{O}_2$  (eqn (3)). Based on eqn (4),<sup>33</sup> pre-equilibrium constants ( $K$ ), namely  $\text{O}_2$  binding constants with  $\text{Au}_{25}$  cluster anions, and second-order rate constants ( $k_2$ ) were determined and are summarized in Table 2. In the case of  $\text{TOA}^+[\text{Au}_{25}(\text{SC}_2\text{Ph})_{18}]^-$ ,  $k_2$  and  $K$  were  $(9.9 \pm 0.3) \text{ s}^{-1}$  and  $(0.20 \pm 0.01) \text{ mM}^{-1}$  at  $[\text{TFA}] = 0.50 \text{ mM}$ , respectively. When changing the concentration of TFA to 2.0 mM, the  $K$  value was retained ( $0.18 \pm 0.04 \text{ mM}^{-1}$ ), whereas the  $k_2$  value increased ( $(44 \pm 4) \text{ s}^{-1}$ ) (Fig. S18†). No influence of

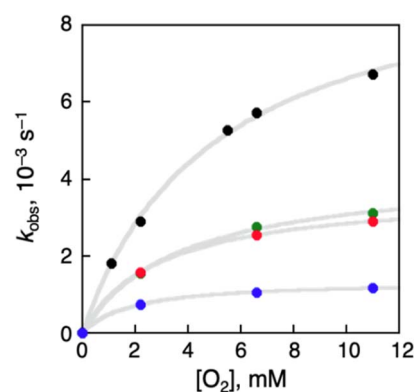


Fig. 4  $[\text{O}_2]$  dependence of  $k_{\text{obs}}$  in oxidation reactions of  $\text{TOA}^+[\text{Au}_{25}(\text{SR})_{18}]^-$  in THF ( $[\text{TFA}] = 0.50 \text{ mM}$ ) at 298 K. SR =  $\text{SC}_2\text{Ph}$  (black),  $\text{SC}_1\text{Ph}$  (green),  $\text{SPhOMe}$  (red) and  $\text{SPh}$  (blue).



the acid concentration on the  $O_2$  binding constant suggests that protons are not involved in the pre-equilibrium between the  $Au_{25}$  cluster and  $O_2$  (eqn (3)). The highest  $O_2$  binding constant ( $0.55 \pm 0.01 \text{ mM}^{-1}$ ) was observed in the air-oxidation reaction of  $TOA^+[Au_{25}(SPh)_{18}]^-$ , whereas  $TOA^+[Au_{25}(SC_2Ph)_{18}]^-$  showed the lowest  $O_2$ -binding properties ( $0.20 \pm 0.01 \text{ mM}^{-1}$ ). In other words,  $Au_{25}$  cluster anions protected by rigid aromatic thiolate ligands showed higher  $O_2$  binding constants than those with flexible aliphatic thiolate ligands. The affinity of  $O_2$  would be regulated by the electronic effects and/or the steric effects of **R** moieties of thiolate ligands. In mononuclear metal complexes, more electron-donating ligands increased the  $O_2$ -binding constants,<sup>34</sup> whereas an opposite tendency was observed in our system, in that more electron-donating ligands such as **SC<sub>2</sub>Ph** gave reduced  $K$  values. This difference between MNCs and transition metal complexes would be caused by the binding position of  $O_2$ : in mononuclear metal complexes, because both the  $O_2$ -binding and the redox reactions generally take place at the same sites, namely the metal centres (Fig. 5a), the affinity of  $O_2$  should be affected by the electronic states of metal centres. Although experimental evidence for  $O_2$  binding sites is insufficient due to the weak electronic interaction between  $O_2$  and  $AuNCs$ <sup>13d</sup> and further spectral and structural analyses for  $O_2$ -bound  $Au_{25}$  clusters are needed, some theoretical reports discussed that  $O_2$  would bind with the gold atom of staple  $Au_2(SR)_3$  moieties of  $[Au_{25}(SR)_{18}]^-$  in an end-on coordinating fashion rather than the  $Au_{13}$  icosahedral core.<sup>13d,17d</sup> It should be noted that the one-electron oxidation of  $[Au_{25}(SR)_{18}]^-$  occurs at the  $Au_{13}$  core, not at the staple  $Au_2(SR)_3$  units.<sup>19b</sup> Therefore, we could think that the  $O_2$ -binding and the redox sites are different in the ligand-protected MNCs, suggesting almost no electronic effects on the  $O_2$  affinity (Fig. 5b). To evaluate the steric effects of protecting ligands, ligand flexibility such as free rotation of alkyl chains should also be considered.<sup>35</sup> We compared the half cone angles ( $\theta$ ) of  $[Au_{25}(SC_2Ph)_{18}]^-$  and  $[Au_{25}(SPh)_{18}]^-$  based on the atomic structures revealed by X-ray analysis. The  $\theta$  value is defined as the averaged C–Au–S angle, where C is the carbon atom at the *ortho*-position of the phenyl ring of **SC<sub>2</sub>Ph** or **SPh** ligands (Fig. S19†). The  $\theta$  ( $63.2^\circ$ ) for  $[Au_{25}(SC_2Ph)_{18}]^-$  is larger

than that for  $[Au_{25}(SPh)_{18}]^-$  ( $50.3^\circ$ ), indicating the sterically more crowded environment on the surface of  $[Au_{25}(SC_2Ph)_{18}]^-$ . Based on the above discussion, it would be reasonable to explain that the steric effects of thiolate moieties, their bulkiness or flexibility, are dominant factors in determining the  $O_2$ -affinity with a  $Au_{25}$  cluster anion. This conclusion suggests that  $O_2$  would be favourably bound at a less steric gold(I) ion at the staple moiety rather than at sterically crowded metal-core gold atoms, which does not contradict with the theoretical analysis.<sup>13d,17d</sup>

Finally, we considered the controlling factors in determining the reactivities of  $Au_{25}$  clusters. As seen in the comparison of the kinetic parameters ( $K$  and  $k_2$ ) of  $[Au_{25}(SC_2Ph)_{18}]^-$  with those of  $[Au_{25}(SPh)_{18}]^-$  (Table 2), the electronic effects of  $Au_{25}$  clusters, evaluated using redox potentials ( $E_{1/2}$ ), are a dominant factor in regulating the reaction with  $O_2$ . Indeed, a linear relationship was observed between  $k_2$  values and  $E_{1/2}$  ( $Au_{25}^-/Au_{25}^0$ ), as shown in Fig. S20.† However, interestingly, a different aspect could be seen when the influences of  $O_2$  affinity on the reactivities were extracted from the kinetic parameters of  $TOA^+[Au_{25}(SC_1Ph)_{18}]^-$  and  $TOA^+[Au_{25}(SPhOMe)_{18}]^-$ : a higher  $K$  value ( $0.34 \pm 0.01 \text{ mM}^{-1}$ ) was observed in  $TOA^+[Au_{25}(SPhOMe)_{18}]^-$ , whereas the  $k_2$  value of  $TOA^+[Au_{25}(SPhOMe)_{18}]^-$  ( $3.67 \pm 0.03 \text{ s}^{-1}$ ) was slightly lower than that of  $TOA^+[Au_{25}(SC_1Ph)_{18}]^-$  ( $4.2 \pm 0.1 \text{ s}^{-1}$ ), resulting in comparable reactivities of these two  $Au_{25}$  clusters. Thus, the steric effects of protecting ligands could also contribute to tuning the reactivities of the  $Au_{25}$  clusters against  $O_2$ . For *ca.* 3 nm gold nanoparticles, the reactivities with  $O_2$  were simply correlated with  $O_2$ -binding constants in pre-equilibrium,<sup>12c</sup> which were regulated using the accessibility to active sites. In contrast, the oxidation reactivities of  $[Au_{25}(SR)_{18}]^-$  with  $O_2$  could be controlled over both steric and electronic effects. This dual effect on the reactivity enables us to construct finely tunable reaction systems by protecting ligand design, which should be important for precisely controlled catalytic systems based on inorganic nanomaterials.

## Conclusions

We have compared the air-oxidation reactivities of a series of thiolate-protected  $Au_{25}$  nanoclusters bearing different ligands. Kinetic analysis for the oxidation of  $Au_{25}^-$  to  $Au_{25}^0$  has quantitatively revealed that the  $O_2$ -affinity was regulated by the accessibility of surface gold atoms surrounded by protecting ligands, similar to other inorganic nanomaterials. On the other hand, the total reactivities with  $O_2$  can also be tuned by the electronic states of  $Au_{25}$  clusters such as transition metal complexes. This duality in controlling factors for reactivities allows us to construct precisely controlled reaction systems based on metal nanoclusters, which can be achieved by the rational design of protecting ligands. These results shed new light on ligand-protected MNCs with sizes of less than 2 nm to construct finely tunable reaction systems, in contrast to the case of reaction systems based on larger MNPs. Ligand designs, considering ligand–ligand or ligand–substrate interactions, should be effective for more precise control over the reactivities of MNCs.

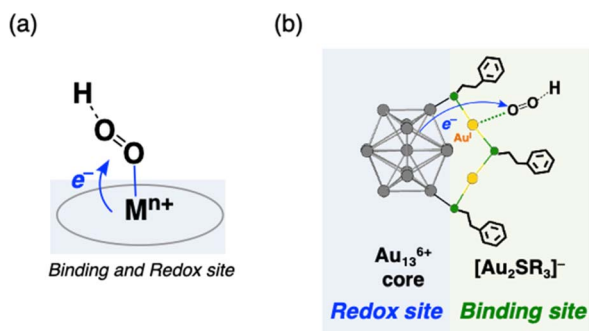


Fig. 5 Schematic illustrations of the interaction and reduction of  $O_2$  with (a) transition metal complexes and (b)  $[Au_{25}(SR)_{18}]^-$  through PCET. In (b), only one staple moiety ( $Au_2SR_3$  unit) is shown for clarity. Atom labels: grey: gold in the  $Au_{13}$  core, yellow: gold on the staple, and green: sulfur.



## Data availability

Additional experimental data supporting this article are included in the ESI.† Reasonable requests for additional information can be made to the corresponding authors.

## Author contributions

W. S. designed the research, performed the synthesis and characterisation and wrote the manuscript. R. T. performed EXAFS measurements using the synchrotron. Y. M. and N. T. performed single crystal X-ray diffraction measurement and analysis. S. X. contributed to the discussion and editing the manuscript. T. T. supervised the research. All authors have approved the manuscript.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

XAFS measurements were performed at the BL01B1 of SPring-8 with the approval of the Japan Synchrotron Radiation Research Institute (JASRI). This work was financially supported by the MEXT/Japan Society for the Promotion of Science (JSPS), KAKENHI, for Scientific Research (S) (grant no. JP19H05634 and JP24H00053) (T. T.), a JSPS Research Fellowship (grant no. 20J01921), JSPS KAKENHI for Early-Career Scientists (grant no. JP23K13765), International Collaboration Research Project of the Institute for Chemical Research, Kyoto University (grant no. 2024-119), and the Tokuyama Science Foundation (W. S.). We thank Ian McNaught, PhD, from Edanz (<https://jp.edanz.com/ac>) for editing a draft of this manuscript.

## References

- (a) M. L. Peigs, C. F. Wise, D. J. Martin and J. M. Mayer, *Chem. Rev.*, 2018, **118**, 2340–2391; (b) H. Sterckx, B. Morel and B. U. W. Maes, *Angew. Chem., Int. Ed.*, 2019, **58**, 7946–7970.
- (a) D. J. Martin, C. F. Wise, M. L. Peigs and J. M. Mayer, *Acc. Chem. Res.*, 2020, **53**, 1056–1065; (b) A. Rana, Y.-M. Lee, X. Li, R. Cao, S. Fukuzumi and W. Nam, *ACS Catal.*, 2021, **11**(5), 3073–3083; (c) S. Fukuzumi, L. Tahsini, Y.-M. Lee, K. Ohkubo, W. Nam and K. D. Karlin, *J. Am. Chem. Soc.*, 2012, **134**, 7025–7035.
- (a) I. Hatay, B. Su, M. A. Méndez, C. Corminboeuf, T. Khoury, C. P. Gross, M. Bourdillon, M. Meyer, J.-M. Barbe, M. Ersoz, S. Zálší, Z. Samec and H. H. Girault, *J. Am. Chem. Soc.*, 2010, **132**, 13733–13741; (b) K. Mase, K. Ohkubo, Z. Xue, H. Yamada and S. Fukuzumi, *Chem. Sci.*, 2015, **6**, 6496–6504; (c) E. Aoki, W. Suzuki, H. Kotani, T. Ishizuka, H. Sakai, T. Hasobe and T. Kojima, *Chem. Commun.*, 2019, **55**, 4925–4928.
- (a) Y. Zhang, X. Cui, F. Shi and Y. Deng, *Chem. Rev.*, 2012, **112**, 2467–2505; (b) C. Xie, Z. Niu, D. Kim, M. Li and P. Yang, *Chem. Rev.*, 2020, **120**, 1184–1249.
- M. Haruta, T. Kobayashi, H. Sano and N. Yamada, *Chem. Lett.*, 1987, 405–408.
- (a) M. K. Carpenter, T. E. Moylan, R. S. Kukreja, M. H. Atwan and M. M. Tessema, *J. Am. Chem. Soc.*, 2012, **134**, 8535–8542; (b) M. Daka, M. Ferrara, M. Bevilacqua, P. Pengo, P. Rajak, R. Ciancio, T. Montini, L. Pasquato and P. Fornasiero, *ACS Appl. Nano Mater.*, 2022, **5**, 4710–4720.
- (a) Y. Du, H. Sheng, D. Astruc and M. Zhu, *Chem. Rev.*, 2020, **120**, 526–622; (b) R. Jin, G. Li, S. Sharma, Y. Li and X. Du, *Chem. Rev.*, 2021, **121**, 567–648.
- (a) Y. Zhu, H. Qian, M. Zhu and R. Jin, *Adv. Mater.*, 2010, **22**, 1915–1920; (b) K. Harano, S. Takano and T. Tsukuda, *Chem. Commun.*, 2019, **55**, 15033–15036; (c) S. Tian, Y. Cao, T. Chen, S. Zang and J. Xie, *Chem. Commun.*, 2020, **56**, 1163–1174; (d) S. Zhuang, D. Chen, W.-P. Ng, D. Liu, L.-J. Liu, M.-Y. Sun, T. Nawaz, X. Wu, Y. Zhang, Z. Li, Y.-L. Huang, J. Yang and J. He, *JACS Au*, 2022, **2**, 2617–2626.
- (a) H. Tsunoyama, A. Ohnuma, K. Takahashi, A. Velloth, M. Ehara, N. Ichikuni, M. Tabuchi and A. Nakajima, *Chem. Commun.*, 2019, **55**, 12603–12606; (b) T. Kawawaki, N. Shimizu, K. Funai, Y. Mitomi, S. Hossain, S. Kikkawa, D. J. Osborn, S. Yamazoe, G. F. Metha and Y. Negishi, *Nanoscale*, 2021, **13**, 14679–14687.
- (a) R. R. Jacobson, Z. Tyeklar, A. Farooq, K. D. Karlin, S. Liu and J. Zubieta, *J. Am. Chem. Soc.*, 1988, **110**, 3690–3692; (b) T. Chishiro, Y. Shimazaki, F. Tani, Y. Tachi, Y. Naruta, S. Karasawa, S. Hayami and Y. Maeda, *Angew. Chem., Int. Ed.*, 2003, **42**, 2788–2791; (c) J. Cho, R. Sarangi, H. Y. Kang, J. Y. Lee, M. Kubo, T. Ogura, E. I. Solomon and W. Nam, *J. Am. Chem. Soc.*, 2010, **132**, 16977–16986.
- (a) H. Kotani, T. Yagi, T. Ishizuka and T. Kojima, *Chem. Commun.*, 2015, **51**, 13385–13388; (b) C. W. Anson, S. Ghosh, S. Hammes-Schiffer and S. S. Stahl, *J. Am. Chem. Soc.*, 2016, **138**, 4186–4193; (c) W. Suzuki, H. Kotani, T. Ishizuka and T. Kojima, *J. Am. Chem. Soc.*, 2019, **141**(14), 5987–5994; (d) W. Suzuki, H. Kotani, T. Ishizuka and T. Kojima, *Chem.–Eur. J.*, 2020, **26**(46), 10480–10486.
- (a) A. Abad, A. Corma and H. García, *Chem.–Eur. J.*, 2008, **14**, 212–222; (b) C. Shang and Z.-P. Liu, *J. Am. Chem. Soc.*, 2011, **133**, 9938–9947; (c) C. G. Long, J. D. Gilbertson, G. Vijayaraghavan, K. J. Stevenson, C. J. Pursell and B. D. Chandler, *J. Am. Chem. Soc.*, 2008, **130**, 10103–10115.
- (a) A. Sanchez, S. Abbet, U. Heiz, W.-D. Schneider, H. Häkkinen, R. N. Barnett and U. Landman, *J. Phys. Chem. A*, 1999, **103**, 9578; (b) H. Tsunoyama, N. Ichikuni, H. Sakurai and T. Tsukuda, *J. Am. Chem. Soc.*, 2009, **131**, 7086–7093; (c) Y. Zhu, H. Qian and R. Jin, *Chem.–Eur. J.*, 2010, **16**, 11455–11462; (d) D. R. Kauffman, D. Alfonso, C. Matranga, G. Li and R. Jin, *J. Phys. Chem. Lett.*, 2013, **4**, 195–202; (e) Z. Wu, G. Hu, D. Jiang, D. R. Mullins, Q.-F. Zhang, L. F. Allard Jr, L.-S. Wang and S. H. Overbury, *Nano Lett.*, 2016, **16**, 6550–6567; (f) D. A. Pichugina, N. A. Nikitina and N. E. Kuzmenko, *J. Phys. Chem. C*, 2020, **124**, 3080–3086.
- (a) Y. Negishi, T. Nakazaki, S. Malola, S. Takano, Y. Niihori, W. Kurashige, S. Yamazoe, T. Tsukuda and H. Häkkinen, *J. Am. Chem. Soc.*, 2015, **137**, 1206–1212; (b) S. Yamazoe,



- S. Takano, W. Kurashige, T. Yokoyama, K. Nitta, Y. Negishi and T. Tsukuda, *Nat. Commun.*, 2016, **7**, 10414; (c) I. Chakraborty and T. Pradeep, *Chem. Rev.*, 2017, **117**, 8208–8271.
- 15 (a) G. Li, H. Abroshan, C. Liu, S. Zhuo, Z. Li, Y. Xie, H. J. Kim, N. L. Rosi and R. Jin, *ACS Nano*, 2016, **10**, 7998–8005; (b) R. R. Nasaruddin, Q. Yao, T. Chen, M. J. Hülsey, N. Yan and J. Xie, *Nanoscale*, 2018, **10**, 23113–23121; (c) Q. Yao, Z. Wu, Z. Liu, Y. Lin, X. Yuan and J. Hie, *Chem. Sci.*, 2021, **12**, 99–127; (d) H. Shan, J. Shi, T. Chen, Y. Cao, Q. Yao, H. An, Z. Yang, Z. Wu, Z. Jiang and J. Xie, *ACS Nano*, 2023, **17**, 2368–2377.
- 16 (a) M. Zhu, C. M. Aikens, F. J. Hollander, G. C. Schatz and R. Jin, *J. Am. Chem. Soc.*, 2008, **130**, 5883–5885; (b) M. W. Heaven, A. Dass, P. S. White, K. M. Holt and R. W. Murray, *J. Am. Chem. Soc.*, 2008, **130**, 3754–3755.
- 17 (a) Y. Lu, Y. Jiang, X. Gao and W. Chen, *Chem. Commun.*, 2014, **50**, 8464–8467; (b) B. Kumar, T. Kawawaki, N. Shimizu, Y. Imai, D. Suzuki, S. Hossain, L. V. Nair and Y. Negishi, *Nanoscale*, 2020, **12**, 9969–9979; (c) W. Chen and S. Chen, *Angew. Chem., Int. Ed.*, 2009, **48**, 4386–4389; (d) F. Sun, C. Deng, S. Tian and Q. Tang, *ACS Catal.*, 2021, **11**, 7957–7969.
- 18 Y. Saito, Y. Shichibu and K. Konishi, *Nanoscale*, 2021, **13**, 9971–9977.
- 19 (a) T. A. Dreier, O. A. Wong and C. J. Aikens, *Chem. Commun.*, 2015, **51**, 1240–1243; (b) M. Zhu, C. M. Aikens, M. P. Hendrich, R. Gupta, H. Qian, G. C. Schatz and R. Jin, *J. Am. Chem. Soc.*, 2009, **131**, 2490–2492.
- 20 (a) S. Antonello, A. H. Holm, E. Instuli and F. Maran, *J. Am. Chem. Soc.*, 2007, **129**, 9836–9837; (b) S. Antonello, N. V. Perera, M. Ruzzi, J. A. Gascón and F. Maran, *J. Am. Chem. Soc.*, 2013, **135**, 15585–15594; (c) S. Antonello, G. Arrigoni, T. Dainese, M. De Nardi, G. Parisio, L. Perotti, A. René, A. Venzo and F. Maran, *ACS Nano*, 2014, **8**, 2788–2795; (d) K. Kwak and D. Lee, *Acc. Chem. Res.*, 2019, **52**, 12–22.
- 21 S. Bhat, R. Pradeep, N. Ananya, P. Chakraborty, G. Paramasivam, R. R. J. Methikkalam, A. Nag, G. Natarajan and T. Pradeep, *J. Phys. Chem. C*, 2018, **122**, 19455–19462.
- 22 M. Zhu, W. T. Eckenhoff, T. Pintauer and R. Jin, *J. Phys. Chem. C*, 2008, **112**, 14221–14224.
- 23 (a) X. Yuan, N. Goswami, W. Chen, Q. Yao and J. Xie, *Chem. Commun.*, 2016, **52**, 5234–5237; (b) Z. Lei, J.-J. Li, Z.-A. Nan, Z.-G. Jiang and Q.-M. Wang, *Angew. Chem., Int. Ed.*, 2021, **60**, 14415–14419; (c) W. Suzuki, R. Takahata, Y. Chiga, S. Kikkawa, S. Yamazoe, Y. Mizuhata, N. Tokitoh and T. Teranishi, *J. Am. Chem. Soc.*, 2022, **144**, 12310–12320.
- 24 (a) D. R. Weinberg, C. J. Gagliardi, J. F. Hull, C. F. Murphy, C. A. Kent, B. C. Westlake, A. Paul, D. H. Ess, D. G. McCafferty and T. J. Meyer, *Chem. Rev.*, 2012, **112**, 4016–4093; (b) S. Fukuzumi, Y.-M. Lee and W. Nam, *ChemCatChem*, 2018, **10**, 9–28.
- 25 W. Suzuki, H. Kotani, T. Ishizuka and T. Kojima, *Chem.–Eur. J.*, 2020, **26**, 10480–10486.
- 26 K. Mase, K. Ohkubo and S. Fukuzumi, *J. Am. Chem. Soc.*, 2013, **135**, 2800–2808.
- 27 J. F. Parker, J. E. F. Weaver, F. McCallum, C. A. Fields-Zinna and R. W. Murray, *Langmuir*, 2010, **26**(16), 13650–13654.
- 28 M. P. Maman, A. S. Nair, A. M. A. H. Nazeer, B. Pathak and S. Mandal, *J. Phys. Chem. Lett.*, 2020, **11**, 10052.
- 29 C. M. Aikens, *J. Phys. Chem. Lett.*, 2010, **1**, 2594–2599.
- 30 (a) R. Guo and R. W. Murray, *J. Am. Chem. Soc.*, 2005, **127**, 12140–12143; (b) Z. Liu, Y. Li, E. Kahng, S. Xue, X. Du, S. Li and R. Jin, *ACS Nano*, 2022, **16**, 18448–18458.
- 31 D. Das, Y.-M. Lee, K. Ohkubo, W. Nam, K. D. Karlin and S. Fukuzumi, *J. Am. Chem. Soc.*, 2013, **135**, 2825–2834.
- 32 (a) X. Chen and H. Häkkinen, *J. Am. Chem. Soc.*, 2013, **135**, 12944–12947; (b) O. Lopez-Acevedo, K. A. Kacprzak, J. Akola and H. Häkkinen, *Nat. Chem.*, 2010, **2**, 329–334.
- 33 T. Ishizuka, S. Ohzu, H. Kotani, Y. Shiota, K. Yoshizawa and T. Kojima, *Chem. Sci.*, 2014, **5**, 1429–1436.
- 34 M. L. Pegis, B. A. McKeown, N. Kumar, K. Lang, D. J. Wasylenko, X. P. Zhang, S. Rauegi and J. M. Mayer, *ACS Cent. Sci.*, 2016, **2**, 850–856.
- 35 J. A. Bilbrey, A. H. Kazez, J. Locklin and W. D. Allen, *J. Comput. Chem.*, 2013, **34**, 1189–1197.

