

Cite this: *Chem. Sci.*, 2024, 15, 14778 All publication charges for this article have been paid for by the Royal Society of Chemistry

Customizing dumbbell-shaped heterostructured artificial photosystems steering versatile photoredox catalysis†

Peng Su,^a Xian Yan^a and Fang-Xing Xiao  *^{ab}

Benefiting from their excellent light-capturing ability, suitable energy band structure and abundant active sites, transition metal chalcogenides (TMCs) have been attracting widespread attention in heterogeneous photocatalysis. Nonetheless, TMCs still suffer from sluggish charge transfer kinetics, a rapid charge recombination rate and poor stability, rendering the construction of high-performance artificial photosystems challenging. Here, a ternary dumbbell-shaped CdS/MoS₂/CuS heterostructure with spatially separated catalytically active sites has been elaborately designed. In such a heterostructured nanoarchitecture, MoS₂ clusters, selectively grown on both ends of the CdS nanowires (NWs), act as terminal electron collectors, while CuS nanolayers, coated on the sidewalls of CdS NWs through ion exchange, form a P–N heterojunction with the CdS NW framework, which accelerates the migration of holes from CdS to CuS, effectively suppressing the oxidation of sulfide ions and improving the stability of CdS NWs. The well-defined dumbbell-shaped CdS/MoS₂/CuS ternary heterostructure provides a structural basis for spatially precise regulation of the charge migration pathway, where photogenerated electrons and holes directionally migrate to the MoS₂ and CuS catalytic sites, respectively, ultimately achieving efficient carrier separation and significantly enhancing photoactivity for both photocatalytic hydrogen generation and selective organic transformation under visible light. Moreover, we have also ascertained that such ion exchange and interface configuration engineering strategies are universal. Our work features a simple yet efficient strategy for smartly designing multi-component heterostructures to precisely modulate spatially vectorial charge separation at the nanoscale for solar-to-hydrogen conversion.

Received 21st July 2024
Accepted 14th August 2024

DOI: 10.1039/d4sc04838e

rsc.li/chemical-science

1. Introduction

With the rapid increase in global energy demand, energy and environmental issues have become increasingly prominent, driving the rapid development of sustainable clean energy.^{1–3} The advantages of solar energy, including abundance, sustainability and environmental friendliness, render solar-driven photocatalysis a viable solution to the aforementioned challenges.^{4,5} In the past few decades, photocatalysis technology has been thrivingly developed including photocatalytic hydrogen production, CO₂ reduction and nitrogen fixation, selective organic transformation, and environmental remediation.^{6–8} However, its development is retarded by the confined light absorption scope, poor photostability, and high electron–hole recombination rate of semiconductor materials, reducing the

solar energy conversion efficiency and posing significant challenges in constructing robust and sustainable artificial photocatalytic systems.^{9–11}

Among the diverse semiconductor materials, transition metal chalcogenides (TMCs) have been widely explored due to their suitable energy band structure, outstanding light-capturing ability and enriched active sites.^{12,13} However, widespread applications of TMCs in heterogeneous photocatalysis are still hindered by sluggish charge transfer kinetics, severe photo-corrosion and a rapid charge recombination rate. To solve these problems, multifarious strategies have thus been proposed to optimize the photocatalytic efficiency of TMC photosystems, such as metal or non-metal element doping, co-catalyst loading and heterojunction engineering.^{14–16} Among them, co-catalyst modification represents a simple and feasible method for constructing high-efficiency TMC photocatalytic systems by providing abundant surface catalytically active sites and reducing the activation energy of surface redox reactions.^{17–20} Nevertheless, it should be emphasized that the interfacial integration mode between TMCs and co-catalysts is of paramount importance for the effective separation of photogenerated charge carriers, which is heavily dependent on

^aCollege of Materials Science and Engineering, Fuzhou University, New Campus, Minhou, Fujian Province, 350108, China

^bState Key Laboratory of Structural Chemistry, Fujian Institute of Research on the Structure of Matter, Chinese Academy of Sciences, Fuzhou, Fujian 350002, P. R. China. E-mail: fxxiao@fzu.edu.cn

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d4sc04838e>



applicable interface engineering techniques, aimed at meticulously constructing directional charge transfer pathways.

Constructing TMC heterostructure photosystems *via* exquisite, easily accessible, and tunable interface configuration regulation provides a feasible and efficient approach to enhance the photoactivities by maximizing the synergy of ingredients for enhanced interfacial charge transport and separation. In such a well-designed nanoarchitecture, favorable energy level alignment among the building blocks, decent interface integration fashion, and increased active sites concurrently enhance the carrier transport kinetics, prolong the carrier lifetime, and enhance the stability of heterostructure photosystems.^{21–23} Apart from heterojunction engineering, spatially precise co-catalyst loading on heterostructure photocatalysts provides an additional efficacious route to further strategically mediate charge migration by remarkably reducing the activation energy, providing charge trapping sites, and reinforcing charge flow impetus. Inspired by the structural merits of one-dimensional (1D) TMCs, which feature spatially unidirectional high-efficiency charge transport along the 1D framework, we believe that selectively positioning appropriate co-catalysts at both ends and sidewalls of 1D TMCs for designing a dumbbell-shaped composite photocatalyst is beneficial for engendering spatially separated vectorial charge migration channels. In this way, carrier migration pathways over the customized dumbbell-shaped heterostructure can be precisely modulated, which significantly diminishes the charge accumulation and enhances the charge separation.

In this work, a ternary dumbbell-shaped CdS/MoS₂/CuS heterostructure photosystem was designed *via* progressive interface modulation. Specifically, as a proof-of-concept investigation, CdS nanowires (NWs) are selected as a quintessential TMC substrate, and then a dumbbell-shaped CdS/MoS₂ binary nanocomposite was prepared by selectively growing MoS₂ clusters at both ends of CdS NWs through a hydrothermal reaction. Subsequently, CuS was uniformly coated on the sidewall of CdS NWs through a facile ion exchange strategy. The thus-formed P–N heterojunction at the contact interface between CdS and CuS promotes electron transfer from CuS to CdS, while holes migrate from CdS to CuS under the driving force of the built-in electric field, avoiding the accumulation of holes. At the same time, MoS₂ clusters at both ends of CdS provide abundant reactive sites to quickly trap the electrons for photoreduction catalysis including photocatalytic hydrogen generation and photoreduction of aromatic nitro compounds to amino derivatives under visible light. The synergistic effect of MoS₂ and CuS concomitantly promotes the charge separation/migration of the CdS/MoS₂/CuS ternary heterostructure. Our work conceptually demonstrates the smart design of robust, stable and well-defined heterostructure photocatalysts with spatially separated charge transport pathways for solar energy conversion.

2. Experimental section

2.1. Preparation of CdS nanowires (NWs)

CdS NWs were fabricated *via* a hydrothermal method. The detailed synthesis procedures are provided in the ESI.†

2.2. Preparation of the CdS/MoS₂ nanodumbbell binary nanocomposite

CdS/MoS₂ nanodumbbells were prepared by a hydrothermal method using CdS NWs as the substrate. The detailed information on the synthesis procedures is provided in the ESI.†

2.3. Preparation of CdS/MoS₂/CuS nanodumbbell ternary nanocomposites

CdS/MoS₂/CuS nanodumbbell heterostructures were synthesized through a cation exchange strategy using CdS/MoS₂ (CM²) nanodumbbells as the precursor. Specifically, 100 mg of CM² nanodumbbell catalyst was dispersed in 100 mL deionized water under ultrasonic treatment. Then, a certain amount of CuCl₂·2H₂O aqueous solution (0.1 M) was added to the above suspension and vigorously stirred for 1 h. The samples were precipitated, centrifuged, washed and dried overnight at 60 °C. The loading percentage of CuS was controlled by adjusting the volume of CuCl₂·2H₂O aqueous solution, and samples incorporating 0.2 mL, 0.4 mL, 1.2 mL, 2 mL, and 3.2 mL of 0.1 M CuCl₂·2H₂O aqueous solution were designated as CM²Cu^{0.5}, CM²C¹, CM²C³, CM²C⁵, and CM²C⁸, respectively.

2.4. Characterization

The crystal phase was explored by X-ray diffraction (XRD, X'Pert Pro MPD, Philips, Holland). Morphologies were probed by field emission scanning electron microscopy (FESEM, Supra55, Carl Zeiss, Germany). Transmission electron microscopy (TEM) images were recorded using a TEM microscope system (JEOL-2010). X-ray photoelectron spectroscopy (XPS) spectra were collected on a photoelectron spectrometer (ESCALAB 250, Thermo Scientific, America), for which the binding energy (B.E.) of all tested elements was calibrated using the B.E. of C 1s (284.80 eV). Fourier transform infrared (FTIR) spectra were collected using an infrared spectrophotometer (TJ270-30A, Tianjin, China). Raman spectra were studied using a Raman spectrometer (Dxr-2xi, Thermo Scientific, America). Ultraviolet-visible (UV-vis) light diffuse reflectance spectroscopy (DRS) was performed on a UV-vis spectrophotometer (Cary 7000, Varian, America), for which the reflectance background is BaSO₄ ranging from 200 nm to 800 nm. Photoluminescence (PL) spectra were recorded on a Varian Cary Eclipse spectrometer.

2.5. Photocatalytic hydrogen evolution

Photocatalytic hydrogen evolution measurements were conducted using a 300 W Xe lamp (PLSSXE300D, Beijing Perfect Light Co. Ltd, China) equipped with an optical cutoff filter ($\lambda > 420$ nm) as the light source. Specifically, 10 mg of the catalyst was dispersed in 5 mL Na₂S/Na₂SO₃ (Na₂S : Na₂SO₃ = 0.25 mol : 0.35 mol) solution and stirred throughout the reaction. Photocatalytic activities were evaluated based on the H₂ evolution amount in the first 2 h of the reaction. The H₂ amount was analyzed on an online gas chromatograph (Shimadzu GC-8A). Cyclic photocatalytic H₂ evolution measurements were carried out as follows: the photocatalytic reaction system was thoroughly degassed after the first run reaction without separating



the photocatalysts or supplementing $\text{Na}_2\text{S}/\text{Na}_2\text{SO}_3$ and, subsequently, the thoroughly degassed reaction system was irradiated again under the same conditions.

The apparent quantum yield (A.Q.Y) of the reaction was defined by the following equation:

$$\begin{aligned} \text{A.Q.Y}(100\%) &= \frac{\text{number of reacted electrons}}{\text{number of incident photons}} \times 100\% \\ &= \frac{\text{number of evolved hydrogen molecules} \times 2}{\text{number of incident photons}} \times 100\% \end{aligned} \quad (1)$$

2.6. Photocatalytic reduction performances

In a typical photoreduction reaction, a 300 W Xe lamp (PLS-SXE300D, Beijing Perfect Light Co. Ltd, China) equipped with a 420 nm cut-off filter ($\lambda > 420$ nm) was used as the irradiation source. 10 mg of catalyst and 40 mg of ammonium formate (NH_4HCO_2) were added to 30 mL of nitroaromatics aqueous solution (20 ppm), which was saturated with N_2 bubbling under ambient conditions. Before visible light illumination, the above suspension was stirred in the dark for 1 h to ensure the establishment of adsorption-desorption equilibrium between the sample and reactant. During the process of the reaction, 2 mL of sample solution was collected at a certain time interval and centrifuged to remove the catalyst completely at 12 000 rpm and the supernatant was analyzed using a UV-vis absorption spectrophotometer (Thermal Genesis). Photoreduction of other aromatic nitro compounds was also carried out under identical conditions. The photoactivities of the samples are defined by the following formula.

$$\text{Conversion}\% = \frac{C_0 - C}{C_0} \times 100\% \quad (2)$$

where C_0 represents the initial concentration of nitroaromatics and C is the concentration after visible light irradiation for a certain time.

2.7. PEC measurements

PEC water oxidation measurements were carried out on an electrochemical workstation (CHI 660E, CHI Shanghai, Inc.) using a standard three-electrode configuration and 0.5 M Na_2SO_4 (pH = 7) aqueous solution as the electrolyte. Pure CdS NWs, CM^2 and CM^2C^1 (1×1 cm) were used as the working electrodes, and Pt foil and an Ag/AgCl (KCl) electrode served as the counter electrode and reference electrode, respectively. A 300 W Xe lamp (FX300, Beijing Perfect Light Co. Ltd, China) equipped with a UV-cutoff filter for visible light ($\lambda > 420$ nm) was applied as the light source for visible light irradiation. The potentials of the electrodes are corrected against the reversible hydrogen electrode (RHE) *via* the calibration equation as shown below:

$$E_{\text{RHE}} = E_{\text{Ag/AgCl}} + 0.059\text{pH} + E_{\text{Ag/AgCl}}^{\circ} \quad (3)$$

$$(E_{\text{Ag/AgCl}}^{\circ} = 0.1976 \text{ V at } 25 \text{ }^{\circ}\text{C})$$


3. Results and discussion

3.1. Characterization of heterostructures

Scheme 1 illustrates the preparation process of a dumbbell-shaped CdS/MoS₂/CuS ternary heterostructure. CdS NWs were first prepared by a hydrothermal method using ethylenediamine as a chelating agent. Due to the increased surface energy, there is a difference in reactivity between the tip and the rod body of CdS NWs, and the selectivity of the tip is higher than that of the rod body, leading to preferential axial growth. Subsequently, a secondary hydrothermal reaction was carried out to introduce a molybdenum source, and MoS₂ clusters were grown at both ends to prepare the dumbbell-shaped CdS/MoS₂ binary nanocomposite. The MoS₂ clusters at both ends of CdS NWs serve as electron-capturing sites, promoting charge transfer along the axial direction of CdS NWs and accelerating carrier separation. Finally, considering that CuS (6.3×10^{-36})²⁴ has a smaller K_{sp} value than CdS (8.0×10^{-27}),²⁵ and the MoS₂ clusters at both ends of CdS are insoluble in water, Cu²⁺ ions can be used to replace the Cd²⁺ of CdS through a ion exchange strategy, forming a well-defined CdS/CuS P-N heterostructure on the CdS sidewall of binary dumbbell-shaped CdS/MoS₂ nanomaterials. The MoS₂ clusters at both ends are not replaced by Cu²⁺ ions but rather remain as hydrogen evolution active sites. It should be stressed that the internal electric field formed on the sidewall of the CdS in the heterostructure promotes the hole migration from CdS to CuS, enhancing the stability of the CdS NW substrate. The innovative design of such a ternary dumbbell-shaped CdS/MoS₂/CuS heterostructure ensures the spatial separation of reduction and oxidation sites, thereby significantly reducing the charge recombination rate and enhancing the photoactivity.

The morphology evolution of the catalyst was probed by field emission scanning electron microscopy (FESEM) measurements. Fig. 1a shows the FESEM image of CdS, which demonstrates a typical rod-shaped structure with a relatively smooth surface, and the diameter of the nanowires is about 30–50 nm. Fig. 1b shows the morphology of the CM^2 binary composite, from which it is apparent that MoS₂ clusters selectively grow at both ends of the CdS NWs, forming a dumbbell-like structure. Subsequently, a ternary dumbbell shaped CM^2C^1 heterostructure was constructed by cation exchange (replacing Cd²⁺ with Cu²⁺ ions) on the CdS sidewall of the dumbbell-shaped CdS/MoS₂ binary composite. As displayed in Fig. 1c, it is evident that replacement of Cd²⁺ with Cu²⁺ ions does not inflict damage on the MoS₂ clusters situated at both ends, and the CM^2C^1 heterostructure still maintains the dumbbell-shaped structure. The structural characteristics of CM^2C^1 were further confirmed by transmission electron microscopy (TEM). Fig. 1d indicates that MoS₂ at both ends demonstrates a clear cluster structure. The microstructure and morphology of the dumbbell-shaped CM^2C^1 ternary heterostructure were further analyzed by HRTEM (Fig. 1e). From the locally enlarged HRTEM image (Fig. 1f and g), lattice fringes of 0.357 nm and 0.325 nm corresponding to the (100) and (110) crystal planes of CdS and CuS



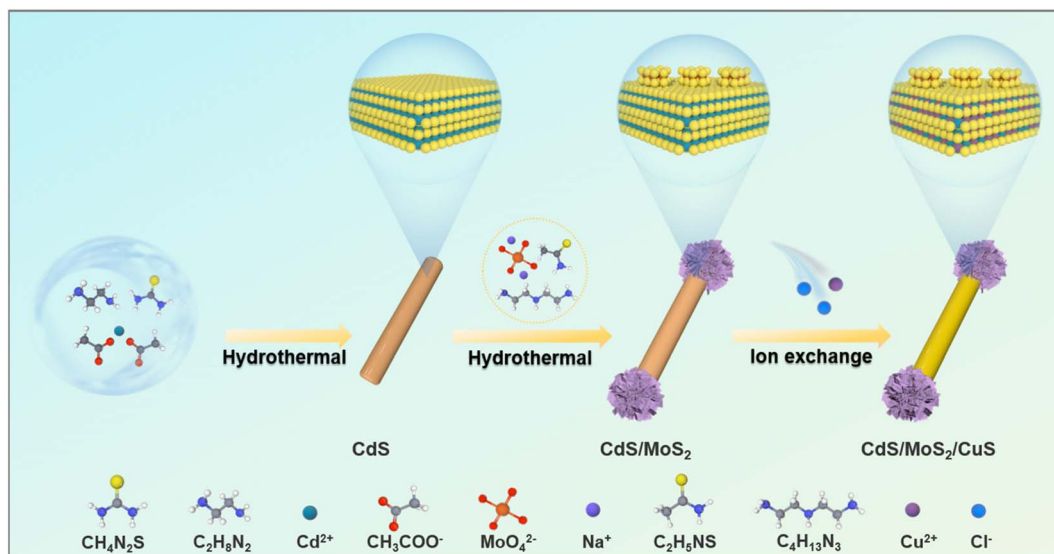

Scheme 1 Schematic illustration depicting the construction of the CdS/MoS₂/CuS nanodumbbell heterostructure.

are clearly observed.^{26–28} To precisely determine the integration sites between CdS and CuS, TEM elemental mapping analysis was performed on CM²C¹ (Fig. 1h–m). It was observed that Mo element was concentrated at the ends of the CdS NWs, further confirming the selective growth of MoS₂ clusters at the ends of the CdS NWs. Additionally, the distributions of Cu and Cd elements are consistent, both concentrating on the nanowire framework of CdS, indicating that CuS is accurately coated onto the CdS NWs through an ion exchange strategy. The above results indicate that a spatially controlled CdS/MoS₂/CuS ternary heterostructure has been successfully fabricated. The synergistic effect of MoS₂ clusters positioned at both ends and the ultrathin CuS layer coated on the CdS sidewalls provides a structural basis for the precise control of carrier transfer.

In addition to the intuitive morphology analysis, X-ray diffraction (XRD) is used to analyze the crystal structure of the sample. As shown in Fig. S1a,† pure CdS corresponds to a hexagonal phase (JCPDS No. 65-3414).²⁹ Only characteristic diffraction peaks of CdS are detected in the dumbbell-shaped CM^x ($x = 1, 2, 3, 4$) binary nanocomposite, and no characteristic diffraction peaks of MoS₂ are detected (Fig. S1b†), which is related to the low crystallinity (Fig. S1c†) and high dispersion of MoS₂. Moreover, it was revealed that the growth of MoS₂ at both ends of CdS NWs does not influence the crystal structure of CdS. Similarly, no characteristic peaks of MoS₂ and CuS are observed in the XRD pattern of the CM²C¹ heterostructure, which is caused by the low content of CuS generated through cation exchange (Fig. 2a). Raman spectroscopy was employed to conduct further analysis on the structures of CdS, CM² and CM²C¹ materials. As displayed in Fig. 2b, apparent vibrational peaks at 302 cm⁻¹ and 605 cm⁻¹ are observed, which are attributed to the 1 LO longitudinal optical and 2 LO phonon modes of hexagonal CdS,²⁶ respectively. It is worth noting that after selectively growing MoS₂ clusters at both ends of CdS NWs to construct dumbbell-shaped CM² composite materials, the

Raman peaks of 1 LO and 2 LO show negative shifts. This is associated with the lattice strain induced by the selective growth of MoS₂ clusters at the ends of CdS NWs, where the bond length of the CdS lattice is stretched at the interface between CdS and MoS₂.³⁰ The Raman spectrum of the CM²C¹ ternary heterostructure retains the 1 LO and 2 LO peaks of CdS, but these peaks are further negatively shifted compared with CM², which is related to the selective substitution of Cd²⁺ with Cu²⁺ ions on the sidewalls of CdS in the dumbbell-shaped CdS/MoS₂ binary composite. The above analysis confirms the successful construction of a dumbbell-shaped CM-Cu¹ heterostructure through the gradual introduction of MoS₂ and CuS. Fig. 2c shows the FTIR spectra of CdS, CM², and CM²C¹, wherein the peak at 3435 cm⁻¹ is attributed to the stretching vibration mode of the –NH group on the CdS surface.³¹ The decreased peak intensity of CM² and CM²C¹ at 3435 cm⁻¹ indicates that the introduction of MoS₂ and CuS shields the –NH peak.^{26,29} The optical properties of the samples were investigated by diffuse reflectance spectroscopy (DRS). As shown in Fig. 2d, the absorption band edge of pure CdS is approximately at 526 nm, which correlates with the photoexcitation of CdS. Compared with CdS, dumbbell-shaped CM² exhibits significantly enhanced light absorption in the visible light range, which is related to the selective growth of MoS₂ clusters at both ends of CdS NWs. The absorption capacity of the ternary dumbbell-shaped CM²C¹ heterostructure in the visible light range is further enhanced, which can be attributed to the *in situ* formation of CuS with a narrower band gap on the sidewall of CdS, substantially boosting the light absorption capacity of the CM²C¹ heterostructure. The loading of MoS₂ and CuS significantly enhances the light-capturing capability of CdS, laying the foundation for efficient photocatalytic reactions. As shown in Fig. 2e, the band gaps (E_g) of CdS, CM² and CM²C¹ are determined to be 2.4, 2.37 and 2.34 eV, respectively, indicating that MoS₂ and CuS loading exerts limited influence on the E_g of CdS.



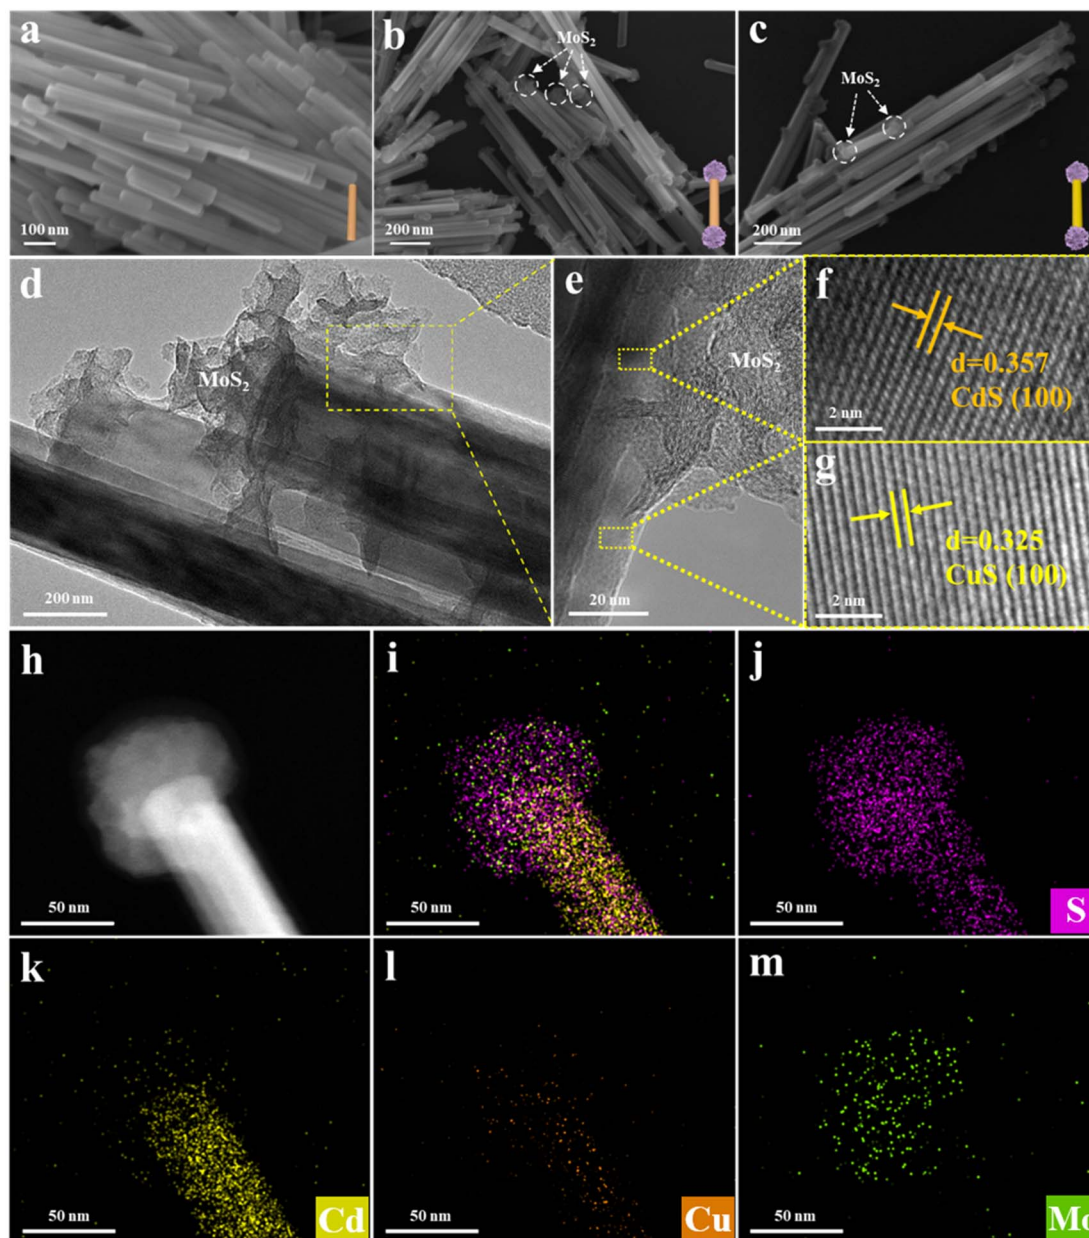


Fig. 1 SEM images of (a) CdS, (b) CM^2 and (c) CM^2C^1 . (d) TEM and (e–g) HRTEM images of the CM^2C^1 nanodumbbell heterostructure, and elemental mapping results of (h–m) CM^2C^1 .

The surface elemental composition and chemical state of the catalyst were analyzed by X-ray photoelectron spectroscopy (XPS). Fig. S2† shows the survey spectra of CdS and CM^2C^1 with the appearance of Cd, S, Mo and Cu signals in CM^2C^1 , wherein Cd and S elements originate from CdS NWs, while Mo and Cu elements stem from MoS_2 and CuS, respectively. The high-resolution S 2p spectrum of pure CdS (Fig. 2f) shows two peaks at 162.6 eV (S 2p_{1/2}) and 161.37 eV (S 2p_{3/2}) corresponding to the S²⁻ species,^{29,30} respectively. As shown in Fig. 2g, the peaks at 411.89 eV (Cd 3d_{3/2}) and 405.16 eV (Cd 3d_{5/2}) in the high-resolution Cd 3d spectrum of pure CdS correspond to the Cd²⁺ species,³² respectively. Compared with CdS, the binding energies of S 2p (Fig. 2f) in CM^2C^1 exhibit a red shift, indicating

a strong electronic interaction between MoS_2 and CuS with CdS. Fig. 2h shows the high-resolution Cu 2p spectrum of CM^2C^1 , wherein the peaks at 933.13 eV (Cu 2p_{3/2}) and 953.07 eV (Cu 2p_{1/2}) are attributed to the Cu²⁺ species.³³ The high-resolution Mo 3d spectrum of CM^2C^1 is shown in Fig. 2i, wherein the peaks at 229 eV (Mo 3d_{5/2}) and 232.63 eV (Mo 3d_{3/2}) correspond to the Mo⁴⁺ species of MoS_2 , and the peaks at 235.88 eV (Mo 3d_{3/2}) correspond to the Mo⁶⁺ species, which may be caused by Mo oxidation.^{34,35} In addition, a peak at 225.87 eV corresponding to S 2s species is observed in the Mo 3d spectrum, which is associated with the Mo–S bonds of MoS_2 .³⁶ The specific surface areas of CdS NWs, CM^2 and CM^2C^1 are determined to be approximately 14.47, 14.79, and 20.00 m² g⁻¹, respectively (Fig. S3 and



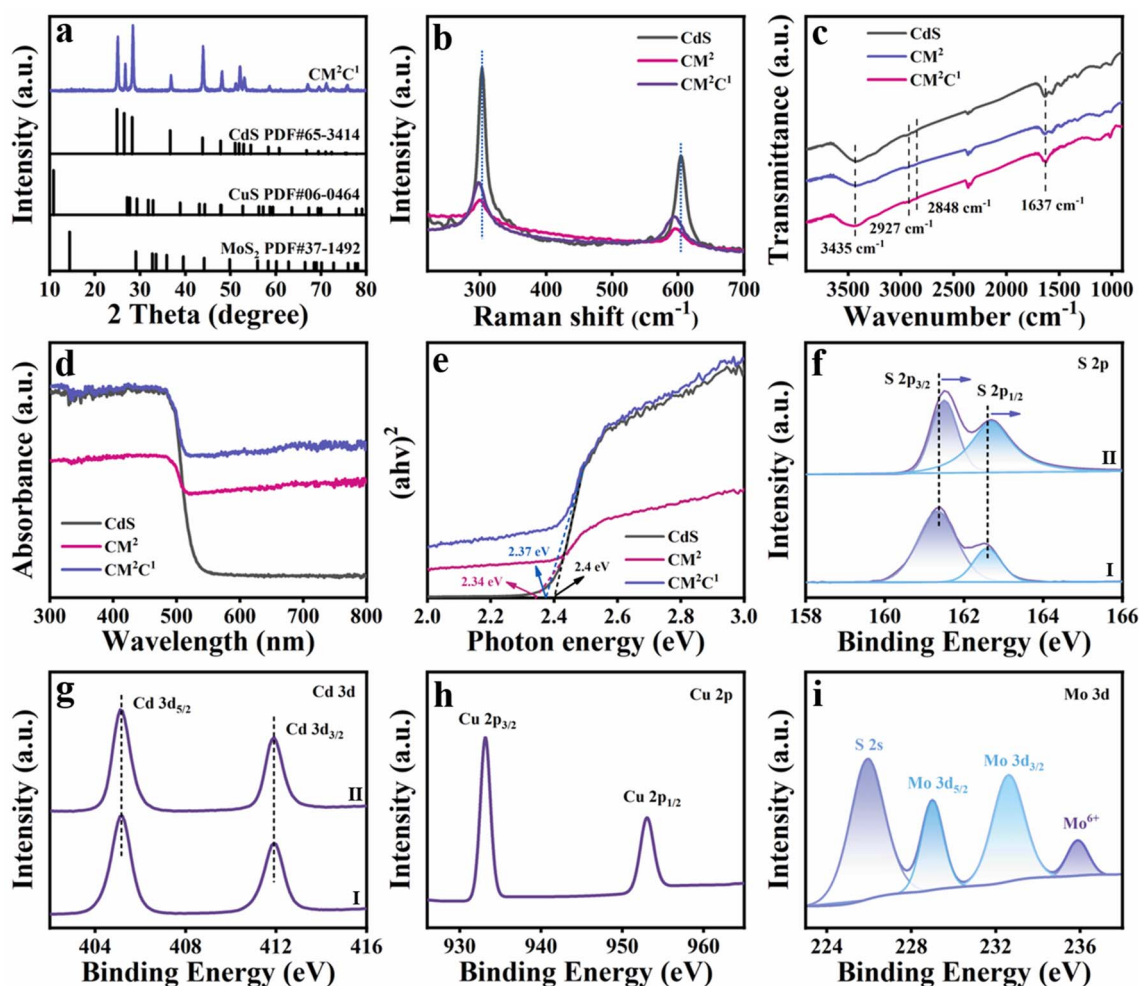


Fig. 2 (a) XRD patterns of the CM^2C^1 nanodumbbell heterostructure; (b) Raman, (c) FTIR, (d) DRS and (e) band-gap determination results of CdS, CM^2 and CM^2C^1 ; high-resolution (f) S 2p and (g) Cd 3d of (I) CdS and (II) CM^2C^1 ; high-resolution (h) Cu 2p and (i) Mo 3d of CM^2C^1 .

Table S3†), indicating that the introduction of MoS_2 and CuS has no significant effect on the specific surface area of the nanocomposites.

3.2. Photocatalytic performances

The photocatalytic hydrogen generation performances of the samples were explored under visible light irradiation. As shown in Fig. 3a, pure CdS exhibits low photocatalytic hydrogen evolution activity due to severe photo-corrosion. Notably, its photoactivity is significantly enhanced after the introduction of MoS_2 , with CM^2 displaying the highest hydrogen evolution activity, which is 16.7 times as high as that of pure CdS. We speculate that the MoS_2 clusters at both ends of CdS NWs serve as electron collectors, facilitating the charge migration from the CdS NWs to MoS_2 and then effectively reducing the recombination rate of charge carriers photoexcited over CdS. At the same time, the MoS_2 at both ends offers abundant reaction sites to further enhance the photocatalytic hydrogen evolution reaction, greatly improving the hydrogen evolution activity. With further adjustment of the amount of molybdenum source added, it was observed that the photocatalytic hydrogen

evolution activity of CM^3 quickly decreases. This is due to the fact that introducing more MoS_2 inevitably forms carrier recombination centers on the surface of CdS NWs, which fails to effectively facilitate the directional migration of electrons along CdS NWs. This confirms the crucial role of selectively growing MoS_2 at both ends of CdS NWs in promoting charge transfer. The photoactivity of CM^4 is almost equivalent to that of pure CdS, indicating that the introduced amount of MoS_2 greatly exceeds the loading capacity of CdS, resulting in a shielding effect that is unfavorable for the participation of photoexcited electrons from CdS in the catalytic reaction. Fig. 3b shows the photocatalytic hydrogen evolution rate of the dumbbell-shaped CM^2C^x ($x = 0.5, 1, 2, 3, 4$) ternary heterostructures, among which CM^2C^1 exhibits the highest hydrogen evolution rate that is 3.4 times larger than that of CM^2 . By selectively integrating MoS_2 and CuS onto CdS NWs, the synergistic effect of MoS_2 and CuS can be fully utilized, greatly enhancing the photocatalytic activity of the CM^2C^x photo-system. Meanwhile, to verify the superiority of selective loading of MoS_2 and CuS on CdS NWs, we prepared control samples of CdS/CuS/ MoS_2 (C/C/M) and CdS-CuS- MoS_2 (C-C-M) ternary



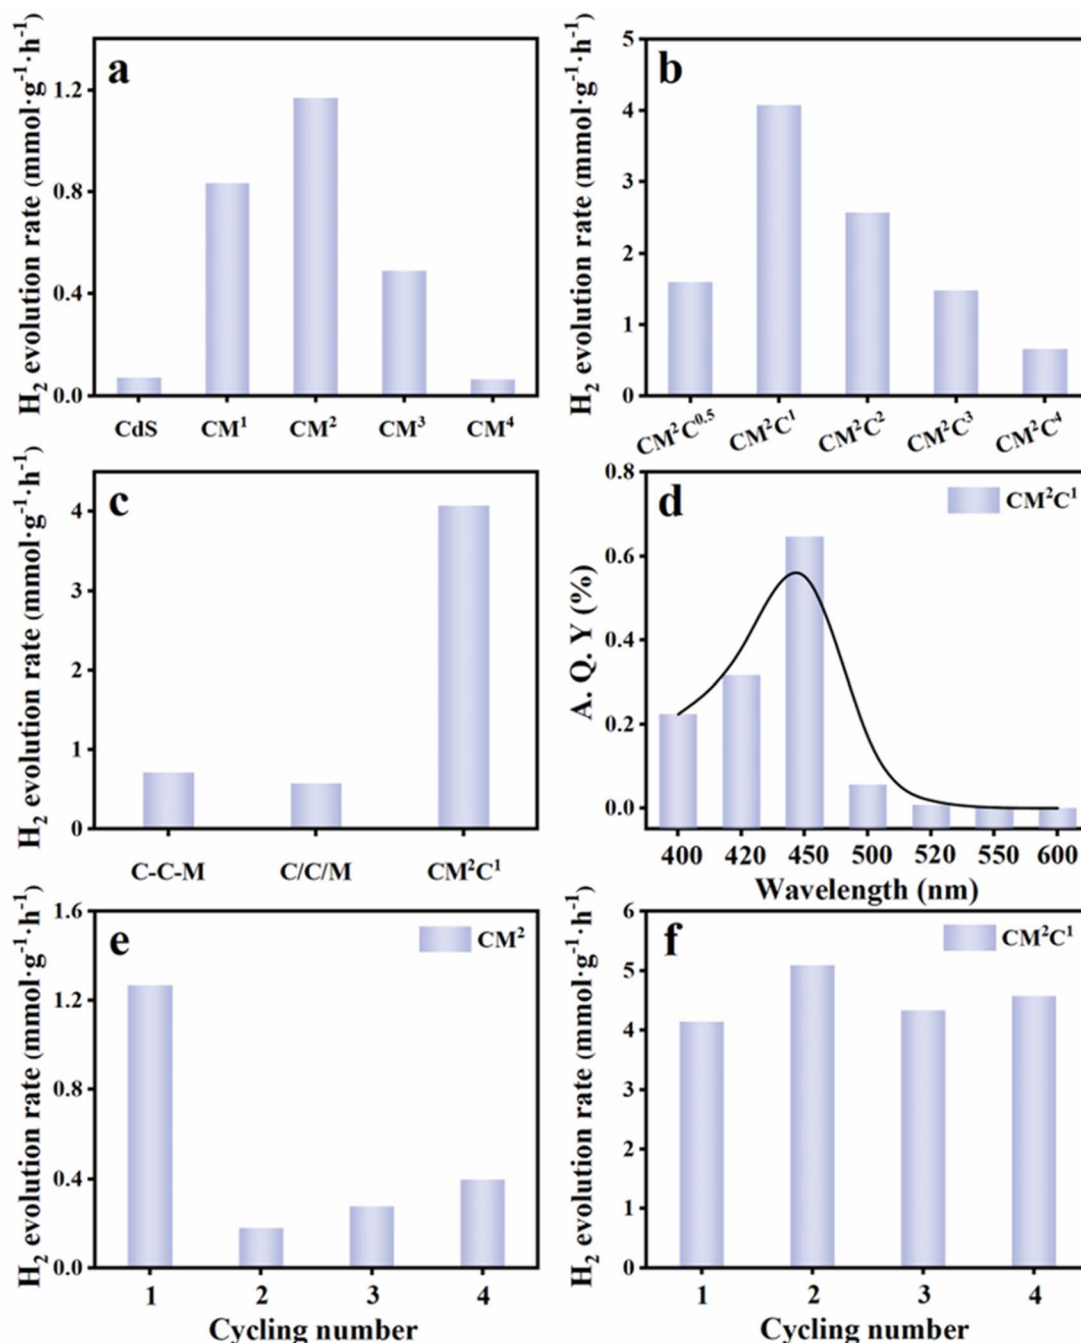


Fig. 3 Photocatalytic hydrogen evolution performances of (a) CdS and CM^x (x = 1, 2, 3, 4), and (b) CM²C^x (x = 0.5, 1, 2, 3, 4). (c) Photocatalytic hydrogen evolution performances of C-C-M, C/C/M and CM²C¹; (d) A.Q.Y. result of CM²C¹ under monochromatic light irradiation; photostability measurements of (e) CM² and (f) CM²C¹.

nanocomposites and analyzed their photocatalytic hydrogen production performance (Fig. 3c). Through ion exchange, CuS is *in situ* generated on the surface of CdS, followed by the loading of an equal amount of MoS₂ to construct the C/C/M composite. In addition, during the *in situ* generation of CuS on the surface of CdS through the ion exchange strategy, an equal amount of MoS₂ was added, wherein MoS₂ and CuS are randomly loaded onto CdS NWs to construct the C-C-M composite. The photoelectron transfer models of CdS/MoS₂/CuS, C-C-M, and C/C/M

heterostructures are shown in Fig. S4a–c.† CdS/MoS₂/CuS exhibits a unique dumbbell-shaped structure (Fig. S4a†), where MoS₂ clusters play an important role as electron collectors to withdraw the electrons from CdS, and simultaneously, CuS enables the formation of a p–n heterojunction with the CdS substrate to enhance hole transfer. Under the synergistic effect of MoS₂ clusters and CuS, photoinduced electrons and holes over CdS directionally migrate to the catalytic sites of MoS₂ and CuS, respectively, thus achieving efficient charge separation. In



contrast, the control sample C-C-M, with randomly loaded MoS₂ and CuS onto CdS NWs, lacked the ability for directional carrier migration. The random distribution of MoS₂ and CuS on CdS NWs cannot fully utilize the spatial unidirectional high-efficiency charge transport characteristics of the one-dimensional CdS NWs and is prone to forming electron-hole recombination centers, which are detrimental to carrier separation and migration (Fig. S4b†). Meanwhile, the control sample C/C/M, constructed by *in situ* generation of CuS on the CdS surface through ion exchange and then loading an equivalent amount of MoS₂, also lacks the efficient directional carrier migration capability. As shown in Fig. S4c,† the CuS/CdS P-N heterojunction on the CdS surface blocks the electron transfer pathway from CdS to MoS₂, hindering rapid separation and migration of carriers. Therefore, the photocatalytic activity of the control samples C-C-M and C/C/M is significantly lower than that of CM²C¹, further confirming the crucial role of selective loading of MoS₂ and CuS on CdS NWs in finely tuning carrier migration and suppressing carrier recombination. As shown in Fig. 3d, the dumbbell-shaped CM²C¹ heterostructure demonstrates the highest apparent quantum yield (A.Q.Y) at 450 nm, which is consistent with the DRS result, indicating the predominant role of photoexcitation of CdS NWs. Additionally, it was found from Fig. S5† that the photocatalytic hydrogen evolution rate of CM²C¹ increases with increasing light intensity, confirming that it is indeed a photocatalytic process. Moreover, as shown in Fig. 3e, the photocatalytic activity of the dumbbell-shaped CM² binary nanocomposite decreases substantially after the first reaction run, indicating that the MoS₂ clusters at both ends of CdS NWs as charge collectors are conducive to the separation of charge carriers, but the holes accumulating on the sidewalls of CdS NWs oxidize the lattice sulfide ions, leading to photo-corrosion and reduced photoactivity. In contrast, the dumbbell-shaped CM²C¹ ternary heterostructure still exhibits good photoactivity after four cycles (Fig. 3f), indicating that CuS coating on the sidewalls of CdS NWs for constructing a CdS/CuS P-N heterojunction is beneficial for stabilizing CM²C¹. Under the driving force of a built-in electric field provided by the P-N heterojunction, hole migration from CdS to CuS is accelerated, which prevents the hole oxidation of the CdS NWs and thus improves the photostability. Furthermore, the good photostability of CM²C¹ was consistently confirmed by the XRD (Fig. S6†), Raman (Fig. S7†), SEM (Fig. S8†), and XPS (Fig. S9†) results after the cyclic reaction. Additionally, as shown in Table S4,† the photocatalytic activity of the dumbbell-shaped CM²C¹ reported in our work outperforms previously documented catalysts associated with CdS.

In addition, the photocatalytic activity of the dumbbell-shaped CM²C¹ heterostructure for the reduction of aromatic nitro compounds was also investigated under visible light. Control experiments were conducted without light exposure and without adding the CM²C¹ catalyst to verify that the selective reduction of 4-nitroaniline (4-NA) to 4-phenylenediamine (4-PDA) is a photocatalytic reaction (Fig. S10†). Fig. 4a shows the photocatalytic activities of CdS NWs, CM² and CM²C¹ for the photoreduction of 4-NA under visible light irradiation. The low photoreduction activity of pure CdS is related to the rapid

recombination of photogenerated charge carriers. It is noteworthy that the photoactivity of CM² is significantly enhanced after the selective growth of MoS₂ clusters at both ends of CdS NWs, indicating that the MoS₂ clusters act as electron collectors to promote the directed migration of photogenerated electrons and suppress the recombination of photogenerated charge carriers. Compared with CdS NWs and CM², CM²C¹ demonstrates optimal photocatalytic activity, indicating that the construction of CdS/CuS P-N heterojunctions on the sidewall of CdS NWs promotes the directional migration of holes from CdS to CuS, achieving the spatial separation of electrons and holes and effectively enhancing photocatalytic activity. Meanwhile, CM²C¹ also exhibits similar optimal photocatalytic activities for the reduction of 3-nitroaniline (3-NA) (Fig. 4b), 2-nitroaniline (2-NA) (Fig. 4c), 4-nitrophenol (4-NP) (Fig. 4d), 3-nitrophenol (3NP) (Fig. 4e), and 2-nitrophenol (2-NP) (Fig. 4f). The photocatalytic performances of C-C-M, C/C/M and CM²C¹ were also probed under the same conditions (Fig. S11 and S12†). Taking the photoreduction of 4-NA as an example, it was found that the photocatalytic activity of CM²C¹ is always higher than those of C-C-M (Fig. 4g) and C/C/M (Fig. 4h), further validating the significant role of selectively integrating MoS₂ and CuS on CdS NWs in finely tuning carrier transport and suppressing carrier recombination. As shown in Fig. 4i, without the addition of a hole scavenger, the photocatalytic activity of CM²C¹ is markedly reduced, confirming the vital role of ammonium formate in quenching holes and inhibiting carrier recombination. Furthermore, the photocatalytic performances of CM²C¹ with and without adding an electron scavenger were probed (AgNO₃) (Fig. S13†). When the electron scavenger AgNO₃ was added to the reaction system, CM²C¹ showed no photocatalytic activity, effectively confirming the crucial role of electrons in stimulating the photoreduction catalysis.

3.3. PEC performances

The photoelectrochemical (PEC) performances of CdS, CM² and CM²C¹ were probed to evaluate the interfacial charge separation efficiency. The transient photocurrent responses of CdS NWs, CM², and CM²C¹ under periodic on-off illumination conditions ($\lambda > 420$ nm) were recorded. As displayed in Fig. 5a, compared with pure CdS NWs, CM² exhibits a higher photocurrent density, indicating that selective growth of MoS₂ clusters at both ends of CdS NWs can effectively promote the spatial separation and migration of charge carriers. It is worth noting that CM²C¹ exhibits a higher photocurrent response compared with CM², which indicates that the synergistic effect between the electron-withdrawing capability of MoS₂ clusters and P-N heterojunctions of Cu/CdS plays a significant role in finely tuning carrier migration and suppressing carrier recombination. The electrochemical impedance spectroscopy (EIS) results of CdS NWs, CM² and CM²C¹ are shown in Fig. 5b. Compared with CdS NWs and CM², CM²C¹ demonstrates the smallest arc radius, which confirms that CM²C¹ shows the lowest carrier transfer resistance, inhibiting the recombination of photogenerated electron-hole pairs. In addition, the charge recombination dynamics of CdS NWs, CM² and CM²C¹ were investigated



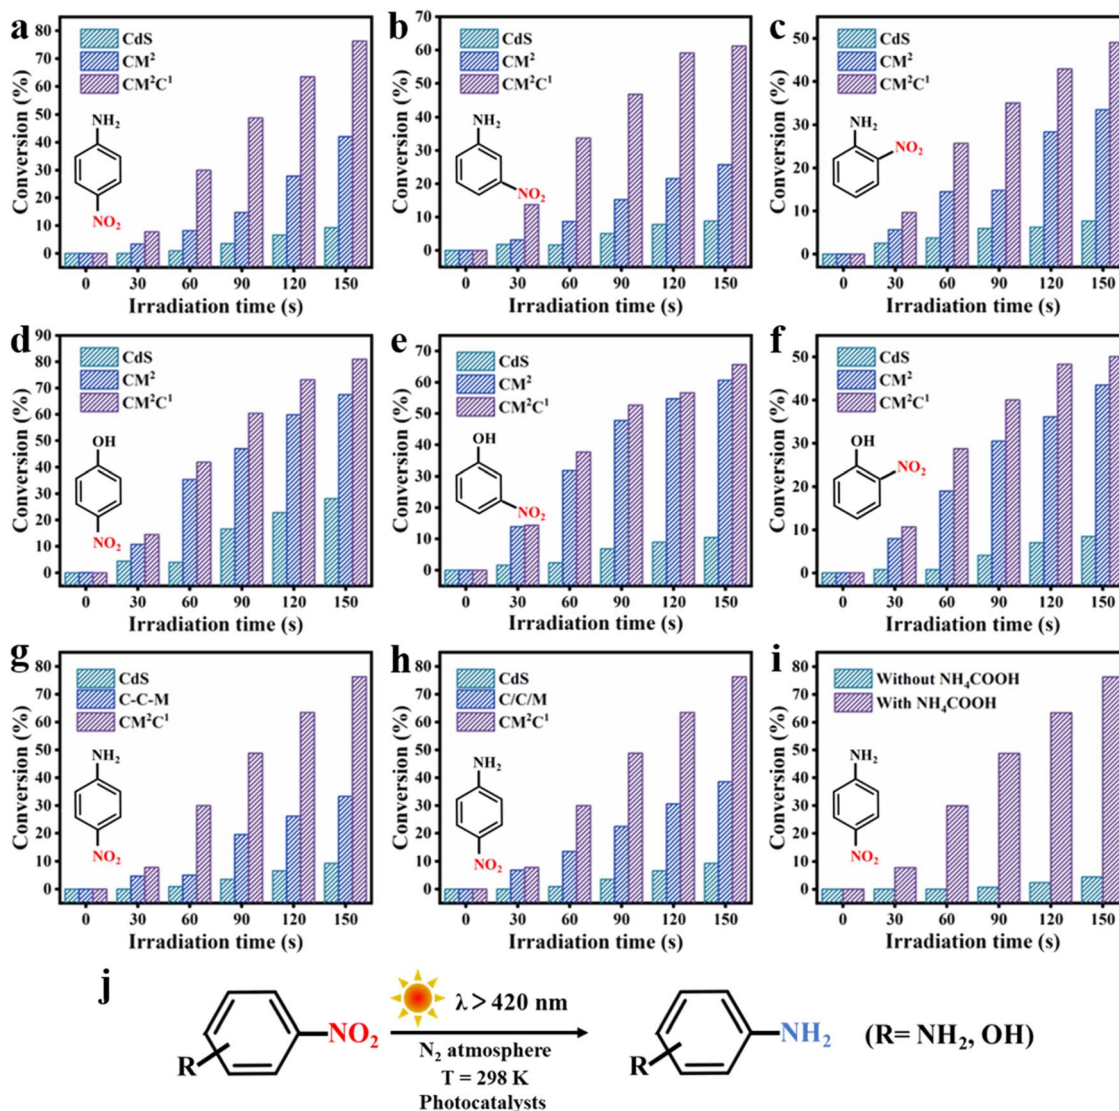


Fig. 4 Photoactivities of CdS, CM² and CM²C¹ for the photoreduction of nitroaromatics including (a) 4-NA, (b) 3-NA, (c) 2-NA, (d) 4-NP, (e) 3-NP, and (f) 2-NP. Photoactivities of CdS, C-C-M, and CM²C¹ for the photoreduction of (g) 4-NA, photocatalytic activities of CdS, C/C/M and CM²C¹ for the photoreduction of (h) 4-NA, and photocatalytic performances of CM²C¹ for the photoreduction of (i) 4-NA with and without adding NH₄COOH. The typical reaction model (j) under the current experimental conditions.

through open circuit voltage decay (OCVD) measurement. As shown in Fig. 5c, CM²C¹ exhibits the highest photovoltage and longest electron lifetime (Fig. 5d). This suggests that constructing a dumbbell-shaped CM²C¹ heterostructure by selectively loading MoS₂ and CuS on CdS NWs effectively facilitates the separation and migration of carriers. Besides, charge transfer kinetics were additionally investigated by steady-state photoluminescence spectroscopy (PL) (Fig. 5e), wherein CM²C¹ shows the lowest PL intensity compared with CdS NWs and CM², once again verifying the most efficient charge separation over CM²C¹.

On the other hand, since the K_{sp} values of CuS (6.3×10^{-36}) and Ag₂S (6.3×10^{-50})²⁵ are smaller than that of CdS (8.0×10^{-27}) and both CuS and Ag₂S are p-type semiconductors,³⁷ they can form a built-in electric field with the n-type semiconductor

CdS, thus promoting charge separation. Therefore, a dumbbell-shaped CdS/MoS₂/Ag₂S (CMA) ternary heterostructure photocatalyst was synthesized through a similar method to validate the universal role of the dumbbell-shaped heterostructure in finely tuning carrier transport. As illustrated in Fig. S14,† CMA not only retains the dumbbell-shaped structure but also shows deposition of Ag₂S nanoparticles on the sidewall of CdS NWs. It can be visually observed that MoS₂ and Ag₂S are selectively integrated onto the CdS NWs to construct a ternary dumbbell-shaped CMA heterostructure. By conducting HRTEM tests on ternary CMA composite catalysts, the integration of Ag₂S and MoS₂ on CdS NWs was further analyzed (Fig. S15†). It was observed that distinct MoS₂ clusters appeared at the ends of the CdS NWs. Additionally, lattice stripes of 0.242 and 0.357 nm are identified on the CdS NWs, corresponding to the (013) crystal



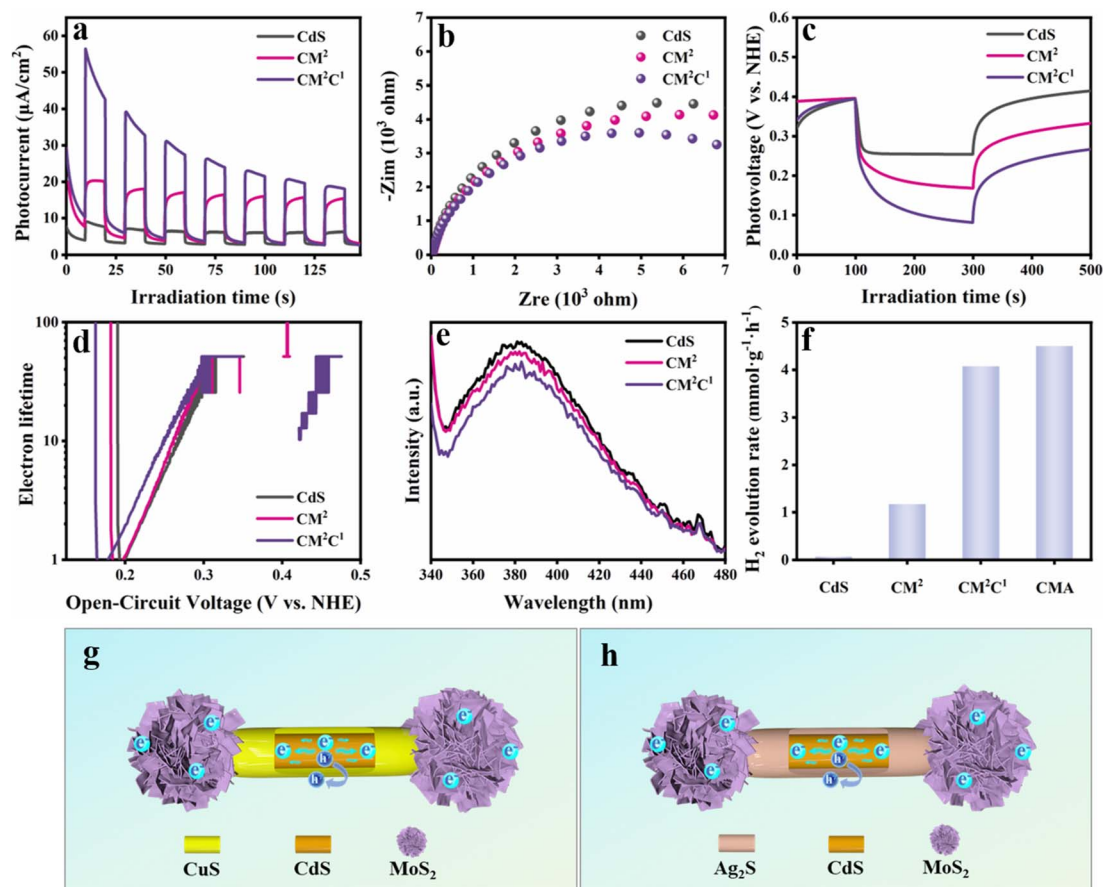


Fig. 5 (a) $I-t$, (b) EIS, (c) OCVD and (d) electron lifetime of CdS, CM^2 and CM^2C^1 under visible light ($\lambda > 420$ nm) irradiation. (e) PL results of CdS, CM^2 and CM^2C^1 , (f) photocatalytic hydrogen evolution performances of CdS, CM^2 and CMA, and schematic diagram of photoelectron transfer over the (g) CdS/MoS₂/CuS and (h) CdS/MoS₂/Ag₂S heterostructure.


plane of Ag₂S and the (100) crystal plane of CdS, respectively. Furthermore, by analyzing the high-resolution Ag 3d spectrum in CMA (Fig. S16c[†]), it can be found that the peaks at 368.04 (Ag 3d_{5/2}) and 374.03 (Ag 3d_{3/2}) eV correspond to the Ag⁺ species in Ag₂S, respectively.^{38,39} These results confirm the successful integration of Ag₂S and MoS₂ on the CdS NWs to construct a dumbbell-shaped CMA ternary heterostructure. In addition, the charge transfer models of CMC and CMA heterostructures are shown in Fig. 5g and h, respectively. Compared with those of CdS and CM^2 , the photocatalytic activities of the CMA and CM^2C^1 ternary dumbbell-shaped heterostructures have been significantly enhanced (Fig. 5f), indicating the synergy of MoS₂ and Ag₂S in promoting the separation and migration of charge carriers. Furthermore, the photocatalytic stability of CMA was verified by cyclic reaction (Fig. S17b[†]), XRD (Fig. S18[†]) and Raman (Fig. S19[†]) results. Similarly, as shown in Fig. S20,[†] the PEC results of CMA agree well with the photocatalytic activity. Specifically, compared with CdS and CM^2 , CMA exhibits optimal photocurrent density and the lowest interfacial charge transfer resistance. This indicates that selective loading of MoS₂ and Ag₂S on the CdS NWs effectively enhances the separation and migration of charge carriers, thereby resulting in enhanced photoactivity. These results further validate the universal role of

the dumbbell-shaped heterostructure in finely tuning the dynamics of charge carriers.

3.4. Photocatalytic mechanism

Based on the above results, the photocatalytic mechanism of the dumbbell-shaped CdS/MoS₂/CuS heterostructure was proposed (Scheme 2). The conduction band (CB) and valence band (VB) potentials of CdS and CuS were determined based on the DRS and M–S results. The CB and VB potentials of CdS are determined to be -1.17 and 1.3 eV (*vs.* NHE) (Fig. S21[†]), respectively, while those of CuS are 0.56 and 1.79 eV (*vs.* NHE) (Fig. S22[†]), respectively. It is worth noting that the positive M–S slope of CdS indicates that it is a typical n-type semiconductor (Fig. S21a[†]), whereas the negative M–S slope of CuS indicates that it is a typical p-type semiconductor (Fig. S22a[†]). The Fermi level of the n-type semiconductor CdS is close to its CB, while the Fermi level of the p-type semiconductor CuS is close to its VB, making the Fermi level of CdS more negative than that of CuS. Due to the difference in Fermi levels, when CdS contacts CuS, the free electrons on CdS migrate towards CuS until they reach the same Fermi level, forming a P–N heterojunction at the contact interface (Fig. S23[†]). When the CdS/MoS₂/CuS heterostructure is photoexcited by visible light, the built-in electric



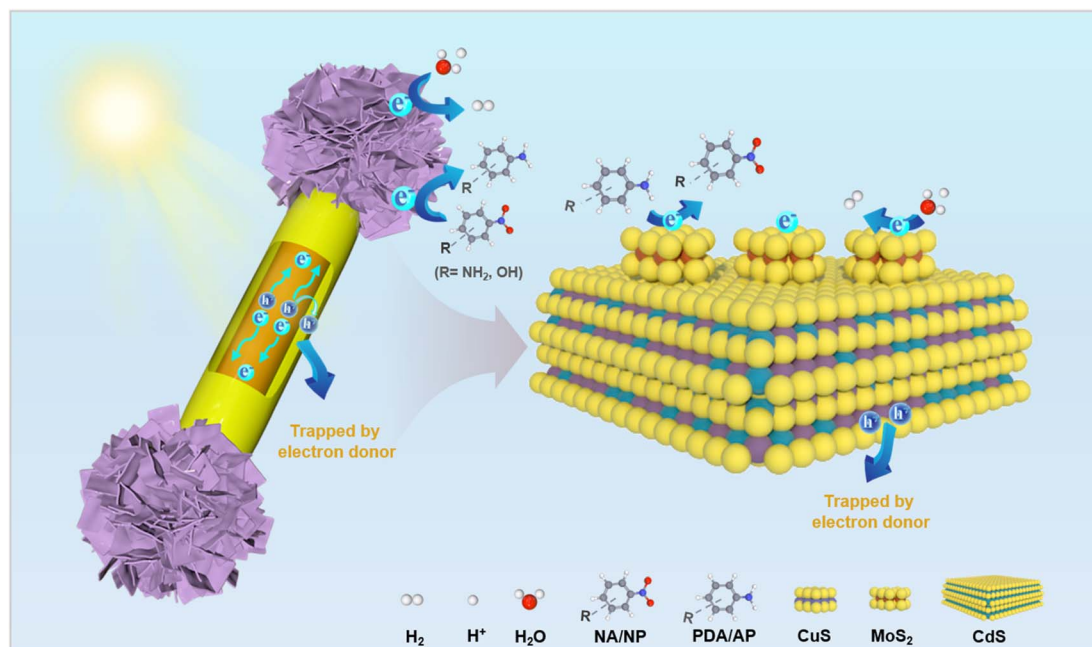

Scheme 2 Schematic illustration of the photocatalytic mechanism of the CdS/MoS₂/CuS heterostructure.

field (electric field direction from CdS to CuS) promotes the migration of CB electrons from CuS to CdS and eventually to MoS₂ clusters for a reduction reaction. Meanwhile, the migration of VB holes from CdS to CuS is stimulated and ultimately quenched by a sacrificial reagent (Fig. S24[†]). Through this charge transfer pathway, photogenerated electron-hole pairs on CdS are effectively separated, and the electrons on CdS are quickly transferred to MoS₂ clusters to reduce H⁺/H₂O to hydrogen, and simultaneously, the holes on CuS are quenched by sacrificial reagents (S²⁻ and SO₃²⁻). For the photoreduction of aromatic nitro compounds, hole scavengers (ammonium formate) are added to the reaction system to ensure that electrons are the only active species. The electrons trapped by the terminal MoS₂ clusters convert aromatic nitro compounds into amino derivatives, while the VB holes in CuS are completely quenched by the electron donor or hole scavenger. Consequently, the unique integration mode of the dumbbell-shaped CdS/MoS₂/CuS heterostructure effectively promotes the directed migration of photogenerated electrons/holes through the synergistic effect of CuS and MoS₂, significantly improving the photocatalytic performances.

4. Conclusions

In summary, a ternary heterostructure photocatalyst, CdS/MoS₂/CuS, with a distinctive dumbbell-shaped structure was crafted through a simple hydrothermal reaction coupled with a cation exchange strategy. The unique integration mode endows the CdS/MoS₂/CuS heterostructure with abundant reaction active sites, good stability and efficient vectorial carrier transport efficiency. Under the influence of synergy stemming from the unique integration mode between CuS and MoS₂, electrons and holes photoexcited over CdS are rapidly

transferred to the electron collector (MoS₂) and hole capture sites (CuS), respectively, to participate in photoredox reactions. These unique structural advantages endow the CdS/MoS₂/CuS ternary heterostructure with significantly enhanced photocatalytic performances for hydrogen evolution and selective reduction of nitroaromatic to amino derivatives under visible light. Our work provides an effective strategy for designing and developing multi-component heterostructures to regulate vectorial charge transfer at the nanoscale.

Data availability

All data supporting the findings of this study are available within the paper and its ESI[†] files. Source data are provided with this paper.

Author contributions

Peng Su performed the experiments, analyzed all data, and drafted the manuscript. Xian Yan helped review the manuscript. Fang-Xing Xiao guided this work and corrected the manuscript. All the authors contributed to critical discussions on the data and manuscript.

Conflicts of interest

The authors declare no competing interests.

Acknowledgements

The support provided by the Award Program for Minjiang Scholar Professorship is greatly acknowledged. This work was financially supported by the National Natural Science



Foundation of China (no. 21703038 and 22072025). The financial support from the State Key Laboratory of Structural Chemistry, Fujian Institute of Research on the Structure of Matter, Chinese Academy of Sciences is acknowledged (no. 20240018).

References

- 1 X. Lin, S. Xu, Z. Q. Wei, S. Hou and F. X. Xiao, Selective organic transformation over a self-assembled all-solid-state Z-scheme core-shell photoredox system, *J. Mater. Chem. A*, 2020, **8**, 20151–20161.
- 2 L. Zhang, X. Jiang, Z. Jin and N. Tsubaki, Spatially Separated Catalytic Sites Supplied with CdS-MoS₂-In₂O₃ Ternary Dumbbell S-scheme heterojunction For Enhanced Photocatalytic Hydrogen Production, *J. Mater. Chem. A*, 2022, **10**, 10715–10728.
- 3 Y. G. Hu, F. Zhan, Q. Wang, Y. J. Sun, C. Yu, X. Zhao, H. Wang, R. Long, G. Z. Zhang, C. Gao, W. K. Zhang, J. Jiang, Y. Tao and Y. J. Xiong, Tracking Mechanistic Pathway of Photocatalytic CO₂ Reaction at Ni Sites Using Operando, Time-Resolved Spectroscopy, *J. Am. Chem. Soc.*, 2020, **142**, 5618–5626.
- 4 Q. Zhu, Z. Xu, B. Qiu, M. Xing and J. Zhang, Emerging Cocatalysts on g-C₃N₄ for Photocatalytic Hydrogen Evolution, *Small*, 2021, **17**, 2101070.
- 5 G. G. Zhang, Z. A. Lan and X. C. Wang, Conjugated Polymers: Catalysts for Photocatalytic Hydrogen Evolution, *Angew. Chem., Int. Ed.*, 2016, **55**, 15712–15727.
- 6 X. Yan, J. H. Dong, J. Y. Zheng, Y. Wu and F. X. Xiao, Customizing precise, tunable, and universal cascade charge transfer chains towards versatile photoredox catalysis, *Chem. Sci.*, 2024, **15**, 2898–2913.
- 7 X. Yan, M. Yuan, Y. L. Yuan, P. Su, Q. Chen and F. X. Xiao, Photocarrier tunneling triggering CO₂ photocatalysis, *Chem. Sci.*, 2024, **15**, 10625–10637.
- 8 P. Rong, Y. F. Jiang, Q. Wang, M. Gu, X. L. Jiang and Q. Yu, Photocatalytic degradation of methylene blue (MB) with Cu1-ZnO single atom catalysts on graphene-coated flexible substrates, *J. Mater. Chem. A*, 2022, **10**, 6231–6241.
- 9 V. Polliotto, S. Livraghi, A. Krukowska, M. V. Dozzi, A. Zaleska-Medynska, E. Selli and E. Giamello, Copper-Modified TiO₂ and ZrTiO₄: Cu Oxidation State Evolution during Photocatalytic Hydrogen Production, *ACS Appl. Mater. Interfaces*, 2018, **10**, 27745–27756.
- 10 W. Yang, M. Xu, K. Y. Tao, J. H. Zhang, D. C. Zhong and T. B. Lu, Building 2D/2D CdS/MOLs Heterojunctions for Efficient Photocatalytic Hydrogen Evolution, *Small*, 2022, **18**, 2200332.
- 11 S. Q. Luo, H. W. Lin, Q. Wang, X. H. Ren, D. Hernández-Pinilla, T. Nagao, Y. Xie, G. L. Yang, S. J. Li, H. Song, M. Oshikiri and J. H. Ye, Triggering Water and Methanol Activation for Solar-Driven H₂ Production: Interplay of Dual Active Sites over Plasmonic ZnCu Alloy, *J. Am. Chem. Soc.*, 2021, **143**, 12145–12153.
- 12 F. X. Xiao, J. W. Miao, H. Y. Wang and B. Liu, Self-assembly of hierarchically ordered CdS quantum dots-TiO₂ nanotube array heterostructures as efficient visible light photocatalysts for photoredox applications, *J. Mater. Chem. A*, 2013, **1**, 12229–12238.
- 13 X. F. Gao, H. B. Li, W. T. Sun, Q. Chen, F. Q. Tang and L. M. Peng, CdTe Quantum Dots-Sensitized TiO₂ Nanotube Array Photoelectrodes, *J. Phys. Chem. C*, 2009, **113**, 7531–7535.
- 14 S. R. Xu, J. L. Li, Q. L. Mo, K. Wang, G. Wu, Y. Xiao, X. Z. Ge and F. X. Xiao, Steering Photocatalytic CO₂ Conversion over CsPbBr₃ Perovskite Nanocrystals by Coupling with Transition-Metal Chalcogenides, *Inorg. Chem.*, 2022, **61**, 17828–17837.
- 15 R. J. Feng, K. W. Wan, X. Y. Sui, N. Zhao, H. X. Li, W. Y. Lei, J. G. Yu, X. F. Liu, X. H. Shi, M. L. Zhai, G. Liu, H. Wang, L. R. Zheng and M. H. Liu, Anchoring single Pt atoms and black phosphorene dual co-catalysts on CdS nanospheres to boost visible-light photocatalytic H₂ evolution, *Nano Today*, 2021, **37**, 101080.
- 16 G. W. Wang, G. K. Zhang, X. X. Ke, X. Y. Chen, X. Chen, Y. S. Wang, G. Y. Huang, J. C. Dong, S. Q. Chu and M. L. Sui, Direct Synthesis of Stable 1T-MoS₂ Doped with Ni Single Atoms for Water Splitting in Alkaline Media, *Small*, 2022, **18**, 2107238.
- 17 K. N. Li, S. S. Zhang, Y. H. Li, J. J. Fan and K. L. Lv, MXenes as noble-metal-alternative co-catalysts in photocatalysis, *Chin. J. Catal.*, 2021, **42**, 3–14.
- 18 K. L. He, E. Campbell, Z. M. Huang, R. C. Shen, Q. Li, S. Q. Zhang, Y. L. Zhong, P. Zhang and X. Li, Metal Carbide-Based Cocatalysts for Photocatalytic Solar-to-Fuel Conversion, *Small Struct.*, 2022, **3**, 2200104.
- 19 D. Ding, Z. Jiang, D. Ji, N. V. Myung and L. Zan, Bi₂O₂Se as a novel co-catalyst for photocatalytic hydrogen evolution reaction, *Chem. Eng. J.*, 2020, **400**, 125931.
- 20 J. Zander and R. Marschall, Ni₂FeS₄ as a highly efficient earth-abundant co-catalyst in photocatalytic hydrogen evolution, *J. Mater. Chem. A*, 2023, **11**, 17066–17078.
- 21 J. Xiong, J. Di and H. Li, Interface engineering in low-dimensional bismuth-based materials for photoreduction reactions, *J. Mater. Chem. A*, 2021, **9**, 2662–2677.
- 22 H. Li, Q. Song, S. Wan, C. W. Tung, C. Liu, Y. Pan, G. Luo, H. M. Chen, S. Cao, J. Yu and L. Zhang, Atomic Interface Engineering of Singl-Atom Pt/TiO₂-Ti₃C₂ for Boosting Photocatalytic CO₂ Reduction, *Small*, 2023, **19**, 2301711.
- 23 X. Hao, Y. Fan, W. Deng and Z. Jin, *In situ* XPS demonstrated efficient charge transfer of ohmic junctions based on graphdiyne (g-C_nH_{2n-2}) nanosheets coupled with porous nanoflowers Ni₅P₄ for efficient photocatalytic H₂ evolution, *Carbon*, 2024, **218**, 118752.
- 24 Q. Zhao, Z. Tang, Y. Pan, J. Han, J. Yang, Y. Guo, X. Lai, Z. Yang and G. Li, The Ksp gap enabled precipitation transformation reactions from transition metal hydroxides to sulfides for alkali metal ion storage, *Inorg. Chem. Front.*, 2023, **10**, 3406–3414.
- 25 C. Lu, S. Du, Y. Zhao, Q. Wang, K. Ren, C. Li and W. Dou, Efficient visible-light photocatalytic H₂ evolution with heterostructured Ag₂S modified CdS nanowires, *RSC Adv.*, 2021, **11**, 28211–28222.



- 26 K. Wang, X. Z. Ge, Q. L. Mo, X. Yan, Y. Xiao, G. Wu, S. R. Xu, J. L. Li, Z. X. Chen and F. X. Xiao, Steering bi-directional charge transfer *via* non-conjugated insulating polymer, *J. Catal.*, 2022, **416**, 92–102.
- 27 L. F. Luo, Y. D. Wang, S. P. Huo, P. Lv, J. Fang, Y. Yang and B. Fei, Cu-MOF assisted synthesis of CuS/CdS(H)/CdS(C): Enhanced photocatalytic hydrogen production under visible light, *Int. J. Hydrogen Energy*, 2019, **44**, 30965–30973.
- 28 C. Lai, M. M. Zhang, B. S. Li, D. L. Huang, G. M. Zeng, L. Qin, X. G. Liu, H. Yi, M. Cheng, L. Li, Z. Chen and L. Chen, Fabrication of CuS/BiVO₄ (040) binary heterojunction photocatalysts with enhanced photocatalytic activity for Ciprofloxacin degradation and mechanism insight, *Chem. Eng. J.*, 2019, **358**, 891–902.
- 29 B. Qiu, L. Cai, N. Zhang, X. Tao and Y. Chai, A Ternary Dumbbell Structure with Spatially Separated Catalytic Sites for Photocatalytic Overall Water Splitting, *Adv. Sci.*, 2020, **7**, 1903568.
- 30 X. X. Lu, W. J. Chen, Y. Yao, X. M. Wen, J. N. Hart, C. Tsounis, C. Y. Toe, J. Scott and Y. H. Ng, Photogenerated charge dynamics of CdS nanorods with spatially distributed MoS₂ for photocatalytic hydrogen generation, *Chem. Eng. J.*, 2021, **420**, 127709.
- 31 X. Y. Fu, Y. B. Li, M. H. Huang, T. Li, X. C. Dai, S. Hou, Z. Q. Wei and F. X. Xiao, Partially Self-Transformed Transition-Metal Chalcogenide Interim Layer: Motivating Charge Transport Cascade for Solar Hydrogen Evolution, *Inorg. Chem.*, 2020, **59**, 2562–2574.
- 32 Y. Li, Q. Zhao, Y. Zhang, Y. Li, L. Fan, F.-t. Li and X. Li, In-situ construction of sequential heterostructured CoS/CdS/CuS for building “electron-welcome zone” to enhance solar-to-hydrogen conversion, *Appl. Catal., B*, 2022, **300**, 120763.
- 33 Y. L. Han, X. F. Dong and Z. B. Siang, Synthesis of Mn_xCd_{1-x}S nanorods and modification with CuS for extraordinarily superior photocatalytic H₂ production, *Catal. Sci. Technol.*, 2019, **9**, 1427–1436.
- 34 G. Eda, H. Yamaguchi, D. Voiry, T. Fujita, M. W. Chen and M. Chhowalla, Photoluminescence from Chemically Exfoliated MoS₂, *Nano Lett.*, 2011, **11**, 5111–5116.
- 35 S. Huang, C. Chen, H. Tsai, J. Shaya and C. Lu, Photocatalytic degradation of thiobencarb by a visible light-driven MoS₂ photocatalyst, *Sep. Purif. Technol.*, 2018, **197**, 147–155.
- 36 R. Gusain, N. Kumar, F. Opoku, P. P. Govender and S. S. Ray, MoS₂ Nanosheet/ZnS Composites for the Visible-Light-Assisted Photocatalytic Degradation of Oxytetracycline, *ACS Appl. Nano Mater.*, 2021, **4**, 4721–4734.
- 37 W. Zhao, B. Dai, F. Zhu, X. Tu, J. Xu, L. Zhang, S. Li, D. Y. C. Leung and C. Sun, A novel 3D plasmonic p-n heterojunction photocatalyst: Ag nanoparticles on flower-like p-Ag₂S/n-BiVO₄ and its excellent photocatalytic reduction and oxidation activities, *Appl. Catal., B*, 2018, **229**, 171–180.
- 38 L. Deng, D. Yin, K. K. Khaing, S. Xiao, L. Li, X. Guo, J. Wang and Y. Zhang, The facile boosting sunlight-driven photocatalytic performance of a metal-organic-framework through coupling with Ag₂S nanoparticles, *New J. Chem.*, 2020, **44**, 12568–12578.
- 39 C. Chen, Z. Li, H. Lin, G. Wang, J. Liao, M. Li, S. Lv and W. Li, Enhanced visible light photocatalytic performance of ZnO nanowires integrated with CdS and Ag₂S, *Dalton Trans.*, 2016, **45**, 3750–3758.

