

## PAPER

[View Article Online](#)  
[View Journal](#) | [View Issue](#)Cite this: *J. Mater. Chem. A*, 2024, **12**, 26890Realizing high-stability anodes for rechargeable magnesium batteries *via in situ*-formed nanoporous Bi and nanosized Sn†Dachong Gu,<sup>a</sup> Yuan Yuan,<sup>id</sup> \*<sup>abc</sup> Xianhao Peng,<sup>a</sup> Dajian Li,<sup>id</sup> <sup>a</sup> Liang Wu,<sup>id</sup> <sup>a</sup> Guangsheng Huang,<sup>a</sup> Jingfeng Wang<sup>a</sup> and Fusheng Pan<sup>ab</sup>

Rechargeable magnesium batteries (RMBs) are regarded as potential next-generation energy storage technologies, thanks to their high theoretical specific capacity and abundance of magnesium resources. However, magnesium anodes tend to form passivating surface films, which hinder the reversible transport of  $\text{Mg}^{2+}$  ions and narrow the selection of suitable electrolytes. Herein, the Bi–Sn alloy loaded with  $\text{SnO}_2$  (Bi–Sn@ $\text{SnO}_2$ ) is synthesized to be the anode for RMBs and improve diffusion kinetics of  $\text{Mg}^{2+}$  ions. The Bi–Sn@ $\text{SnO}_2$  anode delivers a reversible capacity of  $314 \text{ mA h g}^{-1}$  at  $50 \text{ mA g}^{-1}$ . In addition, the Bi–Sn@ $\text{SnO}_2$  anode exhibits high rate performance ( $297 \text{ mA h g}^{-1}$  at  $500 \text{ mA g}^{-1}$ ) and long cycle life ( $148 \text{ mA h g}^{-1}$  at  $1 \text{ A g}^{-1}$  after 300 cycles) due to the *in situ* formation of nanoporous Bi and nanosized Sn by the synergistic effect of Bi–Sn phase separation, defects and the  $\text{Mg}^{2+}$  insertion/extraction reaction. The loading of  $\text{SnO}_2$  on the Bi–Sn alloy surface can restrict the growth of alloy particles and reduce the decomposition of electrolytes. Noticeably, the Bi–Sn@ $\text{SnO}_2$  anode shows good compatibility with the chloride-free  $\text{Mg}(\text{TFSI})_2/\text{G2}$  electrolyte.

Received 19th July 2024  
Accepted 3rd September 2024

DOI: 10.1039/d4ta04998e

[rsc.li/materials-a](https://rsc.li/materials-a)

## 1 Introduction

The demand for battery storage systems in terms of low cost, high safety and high energy density is increasing with the development of intermittent energy storage, electric vehicles and portable devices. Lithium-ion batteries are facing a cost rise due to the limited Li and Co resources and safety issues, especially in large-scale applications.<sup>1–6</sup> Recently, as an alternative to lithium-ion batteries, RMBs have attracted much attention owing to their high volumetric capacity ( $3833 \text{ mA h cm}^{-3}$ ), low cost and fewer dendrite problems.<sup>7–12</sup> However, the poor compatibility between the conventional electrolyte components (magnesium salts and solvents) and the Mg metal anode still hinders the development of the RMBs. The reduction products of conventional electrolytes on the Mg surface cannot conduct  $\text{Mg}^{2+}$  ions, hence blocking the electrochemical reaction.<sup>13–15</sup> Some electrolytes have been applied to avoid Mg anode–electrolyte passivation reactions, which involve halide-ion-containing electrolytes with high corrosiveness and poor

anodic stability<sup>16–19</sup> and borohydride-based electrolytes<sup>20–22</sup> with a complex preparation process.

Since the alloy electrode potential is around 0.1–0.5 V higher than that of Mg metal, using alloy-type anodes may result in better compatibility with simple salt electrolytes, which is considered to be another feasible strategy to bypass the passivation problem.<sup>23</sup> Currently, Bi and Bi-based alloys are very attractive as anodes for RMBs because of the relatively high capacity ( $385 \text{ mA h g}^{-1}$  and  $3783 \text{ mA h cm}^{-3}$ ) based on the alloying reaction  $3\text{Mg}^{2+} + 2\text{Bi} + 6\text{e}^- \rightleftharpoons \text{Mg}_3\text{Bi}_2$  and fast  $\text{Mg}^{2+}$  kinetics.<sup>24–26</sup> The electrochemical activity of electrodeposited Bi anodes with the  $\text{Mg}(\text{TFSI})_2/\text{AN}$  electrolytes was first demonstrated in a three-electrode cell in 2012.<sup>27</sup> Meng *et al.*<sup>28</sup> constructed a  $\text{Mg}_3\text{Bi}_2/\text{S}$  battery prototype with high specific capacity and long-cycle life ( $400 \text{ mA h g}^{-1}$  at a rate of C/2 after 30 cycles) in  $\text{Mg}(\text{TFSI})_2/\text{DME}$  electrolytes. Notably, the magnesiation and demagnesiation of Bi anodes will lead to the detachment of Bi fragment from the Bi electrodes and capacity loss due to the 100% volume change.<sup>29</sup> Wang *et al.*<sup>30</sup> prepared Bi nanoparticles encapsulated in nitrogen-doped carbon (Bi@NC) through the carbonisation of  $\text{Bi}_2\text{O}_3\text{CO}_3\text{@PDA}$ . The specific capacity of Bi@NC was observed to be  $289.4 \text{ mA h g}^{-1}$  in  $\text{Mg}(\text{PFTB})_2$  electrolyte at  $200 \text{ mA g}^{-1}$ , with a capacity retention of 74.7% after 300 cycles. Structural control (such as Bi nanocrystals,<sup>31</sup> mesoporous Bi<sup>32</sup> and Bi nanotubes<sup>33</sup>) and alloying (Bi–Sn,<sup>34–36</sup> Bi–Sb,<sup>37</sup> Bi–Pb,<sup>38</sup> Bi–Sb–Sn,<sup>39</sup> *etc.*) strategies are used to mitigate the huge volume change, improve the cycling stability and increase the specific capacity. In addition, Bi-based

<sup>a</sup>National Engineering Research Center for Magnesium Alloys, College of Materials Science and Engineering, Chongqing University, Chongqing, 400000, China. E-mail: yuanyuan17@cqu.edu.cn; yuan.yuan.er@gmail.com

<sup>b</sup>Chongqing Institute of New Energy Storage Materials and Equipment, Chongqing, 401122, China

<sup>c</sup>School of Materials Science and Engineering, Central South University, Changsha, 410083, China

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d4ta04998e>

alloys have been employed in the fabrication of magnesium anode interfacial protection layers based on their rapid  $\text{Mg}^{2+}$  ion diffusion kinetics. Chai *et al.*<sup>40</sup> employed the electrodeposition method to prepare a Mg–Sn–Bi ternary alloy interphase layer on Mg foil (Mg–Sn–Bi@Mg). The Mg–Sn–Bi@Mg anode facilitates the rapid deposition and stripping of  $\text{Mg}^{2+}$ , exhibiting a low overpotential of 39.4 mV and a cycle life exceeding 2000 hours.


Sn alloying with Mg ( $2\text{Mg}^{2+} + \text{Sn} + 4\text{e}^- \rightarrow \text{Mg}_2\text{Sn}$ ) leads to a high theoretical capacity of  $903 \text{ mA h g}^{-1}$  and a low plateau of 0.2 V (*vs.*  $\text{Mg}^{2+}/\text{Mg}$ ).<sup>41</sup> Earlier studies have demonstrated sluggish  $\text{Mg}^{2+}$  ion kinetics in bulk Sn. Additionally, the Sn anode experiences a 214% volume change in cycling, resulting in poor electrochemical performance.<sup>42,43</sup> Parent *et al.*<sup>44</sup> pointed out that the particle size of the Sn anode should be <40 nm for excellent reversible Mg-storage and they prepared SnSb/graphene composites to form nano-Sn *in situ* which can deliver a reversible capacity of  $\sim 470 \text{ mA h g}^{-1}$  (calculated by using the pure-Sn nanodomains). However, due to the low reactivity of Sb, the mass of the electrode increases and the energy density of the battery decreases.

In the present work, we propose a facile thermo-reduction (deoxygenation) method to prepare a Bi–Sn alloy loaded with  $\text{SnO}_2$  (Bi–Sn@ $\text{SnO}_2$ ) anode, which is suitable for large-scale production. The  $\text{SnO}_2$  particles can limit the growth of Bi–Sn alloy particles and can reduce the decomposition of the electrolyte according to the *ex situ* XPS analysis. Additionally, defects in Bi–Sn@ $\text{SnO}_2$  can cause lattice distortion and internal stresses to form amorphous Mg–Bi. The obtained Bi–Sn@ $\text{SnO}_2$  anode delivers a high reversible capacity of  $148 \text{ mA h g}^{-1}$  after 300 cycles at a current density of  $1 \text{ A g}^{-1}$ . The exceptional performance is attributed to nanoporous Bi and nanosized Sn formed *in situ* in the presence of defects during cycling, effectively alleviating volume change and enhancing alloy anode reactivity.

## 2 Results and discussion



### 2.1 Microstructures and components

The synthesis process of the Bi–Sn@ $\text{SnO}_2$  (BSS-600) alloy material is briefly exhibited in Fig. 1a. Firstly,  $\text{Bi}_2\text{Sn}_2\text{O}_7$  (BSO)

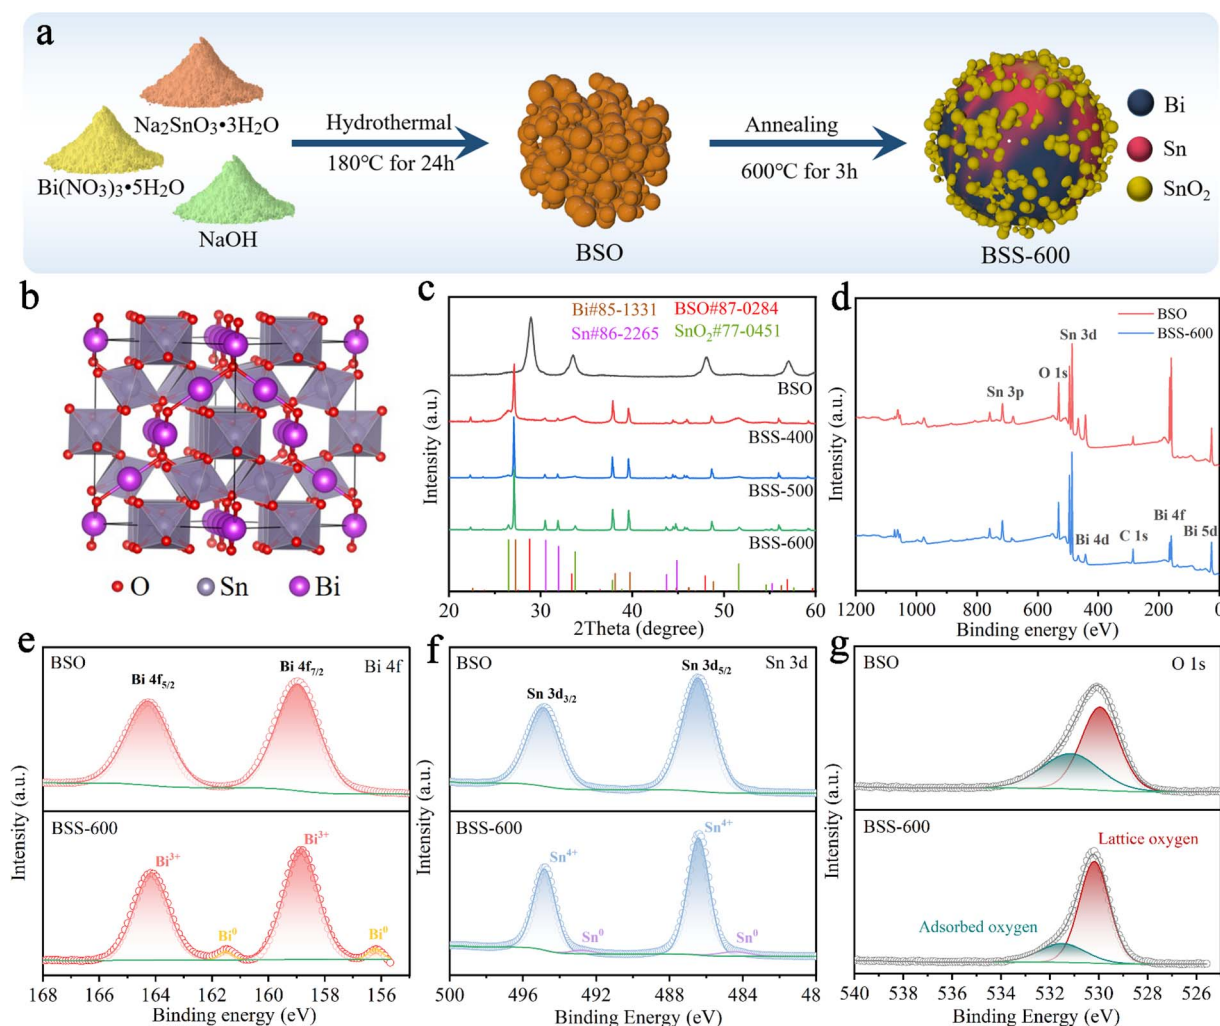

**Fig. 1** (a) Schematic diagram of the preparation process of BSS-600. (b) Crystal structure of BSO. (c) XRD patterns of BSO, BSS-400, BSS-500 and BSS-600. (d) XPS full spectrum of BSO and BSS-600 and high-resolution (e) Bi 4f, (f) Sn 3d, and (g) O 1s XPS spectra.

was obtained by the hydrothermal reaction of  $\text{Bi}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$  and  $\text{Na}_2\text{SnO}_3 \cdot 3\text{H}_2\text{O}$  under alkaline conditions. The obtained BSO emphasizes the interpenetration of  $\text{SnO}_6$  octahedral sublattices and  $\text{Bi}_2\text{O}$  tetrahedral sublattices (Fig. 1b). Secondly, BSO is annealed under an Ar and  $\text{H}_2$  atmosphere for 3 h. XRD patterns of the as-prepared samples are shown in Fig. 1c, and the strong diffraction peaks presented at  $28.8^\circ$ ,  $33.4^\circ$ ,  $47.9^\circ$  and  $56.9^\circ$  can be assigned to the  $\gamma\text{-Bi}_2\text{Sn}_2\text{O}_7$  phase. The broadened peaks of BSO can be attributed to the nanosized particles. To compare the diffraction peaks of the larger BSO particles with those of pristine BSO, the latter was held at  $800^\circ\text{C}$  for 3 hours under an Ar gas flow. The size of the obtained BSO is increased to about 200 nm without a phase transition, proving that BSO has high thermal stability. Simultaneously, the corresponding characteristic peaks of BSO in the XRD pattern become sharper, which demonstrates that the wide peaks of pristine BSO are related to the particle size (Fig. S1†). After annealing in an Ar/ $\text{H}_2$  atmosphere at  $400^\circ\text{C}$  and  $500^\circ\text{C}$ , the peak belonging to BSO disappeared and an obvious Bi phase can be observed with major peaks at  $27.3^\circ$ ,  $38.1^\circ$  and  $39.7^\circ$ . As the reaction temperature increases, the intensity of the peaks corresponding to the Sn phase ( $30.6^\circ$  and  $32.0^\circ$ ) increases gradually. The broad characteristic peaks of BSS-400 and BSS-500 at  $26.6^\circ$  and  $33.9^\circ$  corresponding to  $\text{SnO}_2$  can be related to the low crystallinity of  $\text{SnO}_x$  mixed phases ( $0 < x < 3.5$ ). When the temperature further increased to  $600^\circ\text{C}$ , the obtained product is composed of the Bi phase, Sn phase and  $\text{SnO}_2$  phase owing to more complete thermal reduction. It can be concluded that the thermal reduction reaction of BSO can be summarized as follows:



X-ray photoelectron spectroscopy (XPS) is utilised for the analysis of the chemical status of the BSO and BSS-600 samples. Fig. 1d presents the overall elemental spectrum, which reveals signals from the Bi, Sn, O and C elements. In comparison to BSO, the Sn and O peaks of BSS-600 remain consistent, while the Bi peaks are observed to be weaker. This phenomenon can be attributed to the partial coverage of Bi by  $\text{SnO}_2$  in the BSS-600 sample, which has resulted in a reduction in the peak intensity of Bi. The peak signals observed at 158.9 eV and 164.3 eV are attributed to the  $\text{Bi } 4f_{7/2}$  and  $\text{Bi } 4f_{5/2}$  states of  $\text{Bi}_2\text{O}_3$ , respectively (Fig. 1e). The peaks at 486.4 eV and 494.7 eV correspond to the binding energies of  $\text{Sn } 3d_{5/2}$  and  $\text{Sn } 3d_{3/2}$  states of  $\text{SnO}_2$  (Fig. 1f). The XPS signals of pure Bi (156.2 eV) and Sn (484.4 eV) are demonstrated in the BSS-600 sample in comparison to the BSO sample. However, the binding energy of Bi and Sn is lower than their equilibrium binding energy (157.0 eV for Bi and 485.0 eV for Sn). This observation demonstrates an increase in the electron density of Bi and Sn, which can be attributed to the generation of defects during the thermal reduction process (deoxygenation process). Oxygen species were also detected by O 1s XPS, as shown in Fig. 1g. Two typical XPS peaks at  $\sim 530.2$  and

$531.5$  eV can be attributed to lattice oxygen and adsorbed oxygen species, respectively.<sup>45</sup>

According to the SEM image, the BSO particles aggregate to form a porous bulk material (Fig. 2a). The transmission electron microscopy (TEM) image of BSO is illustrated in Fig. S2†. The BSO bulk is formed by the connection of the nanoparticles, which are approximately 40 nm in size. The morphology of the obtained particles at different annealing temperatures was characterized. At  $400^\circ\text{C}$  and  $500^\circ\text{C}$ , the thermal reduction products of BSO show a mixture of bulks and alloy particles due to the limited reduction reaction (Fig. 2b and c). As the reaction temperature increased to  $600^\circ\text{C}$ , microspheres (2–5  $\mu\text{m}$ ) with irregular particles on the surface were obtained (BSS-600), which are believed to be bismuth–tin alloy spheres loaded with  $\text{SnO}_2$  on the surface. When the annealing time is halved to 1.5 hours, the alloy exhibits a relatively elevated  $\text{SnO}_2$  content and a diminished Sn concentration, accompanied by the emergence of micropores on the surface of the alloy particles (Fig. S3†). This observation indicates that deoxygenation of BSO may result in the preferential formation of Bi and that incomplete thermal reduction of  $\text{SnO}_2$  may restrict the flow of molten Bi-metal and form micropores on the alloy surface. No  $\text{SnO}_2$  was detected in the obtained products when the annealing temperature of BSO was increased to  $650^\circ\text{C}$ , based on the SEM image and XRD analysis (Fig. S4†). Meanwhile, the size of the alloy particles increased to around 50  $\mu\text{m}$ , suggesting that  $\text{SnO}_2$  could limit the growth of the alloy particles during the cooling process of preparation. The aforementioned investigation of process time and temperature also indicates that annealing at  $600^\circ\text{C}$  for 3 hours is an appropriate method.

The  $\text{N}_2$  adsorption and desorption curves of BSO, BSS-400 and BSS-500 are typical IV isotherms, as shown in Fig. 2e. BSO is a porous block stacked by particles with a high Brunauer–Emmett–Teller (BET) surface area of  $52.0 \text{ m}^2 \text{ g}^{-1}$  (Fig. 2f and Table S1†). The  $\text{N}_2$  adsorption–desorption isotherm of BSS-600 shows no obvious H3 hysteresis loop and the specific surface area is measured to be  $3.3 \text{ m}^2 \text{ g}^{-1}$ . Both the larger pore size and BET surface of BSS-400 and BSS-500 indicate the incomplete reaction of BSO after the thermal reduction treatment. The high-angle annular dark field (HAADF) image and the corresponding elemental mapping images (Fig. 2h) indicate the Bi–Sn core and the uniform distribution of Sn and O on its surface. The HRTEM image of BSS-600 shows lattice spacings measured for the particles on the alloy surface to be approximately 0.335 nm and 0.176 nm in Fig. 2g, corresponding to the (110) and (211) lattice planes of  $\text{SnO}_2$ . The interplanar spacings of 0.227 nm and 0.206 nm for the core can be indexed to the (110) and (220) lattice planes of Bi and Sn. The above results additionally demonstrate the structure of the Bi–Sn alloy loaded with  $\text{SnO}_2$  particles.

The results of SEM and elemental mapping of the pristine BSS-600 electrode are shown in Fig. 3a. In the BSS-600 alloy material, Bi-dominated regions can be distinguished from Sn-dominated regions according to the elemental mapping. Since the melting point of Bi is  $271.4^\circ\text{C}$ , slightly higher than that of Sn ( $231.9^\circ\text{C}$ ), the Bi phase nucleates and grows during the annealing process and separates from the Sn phase. After the



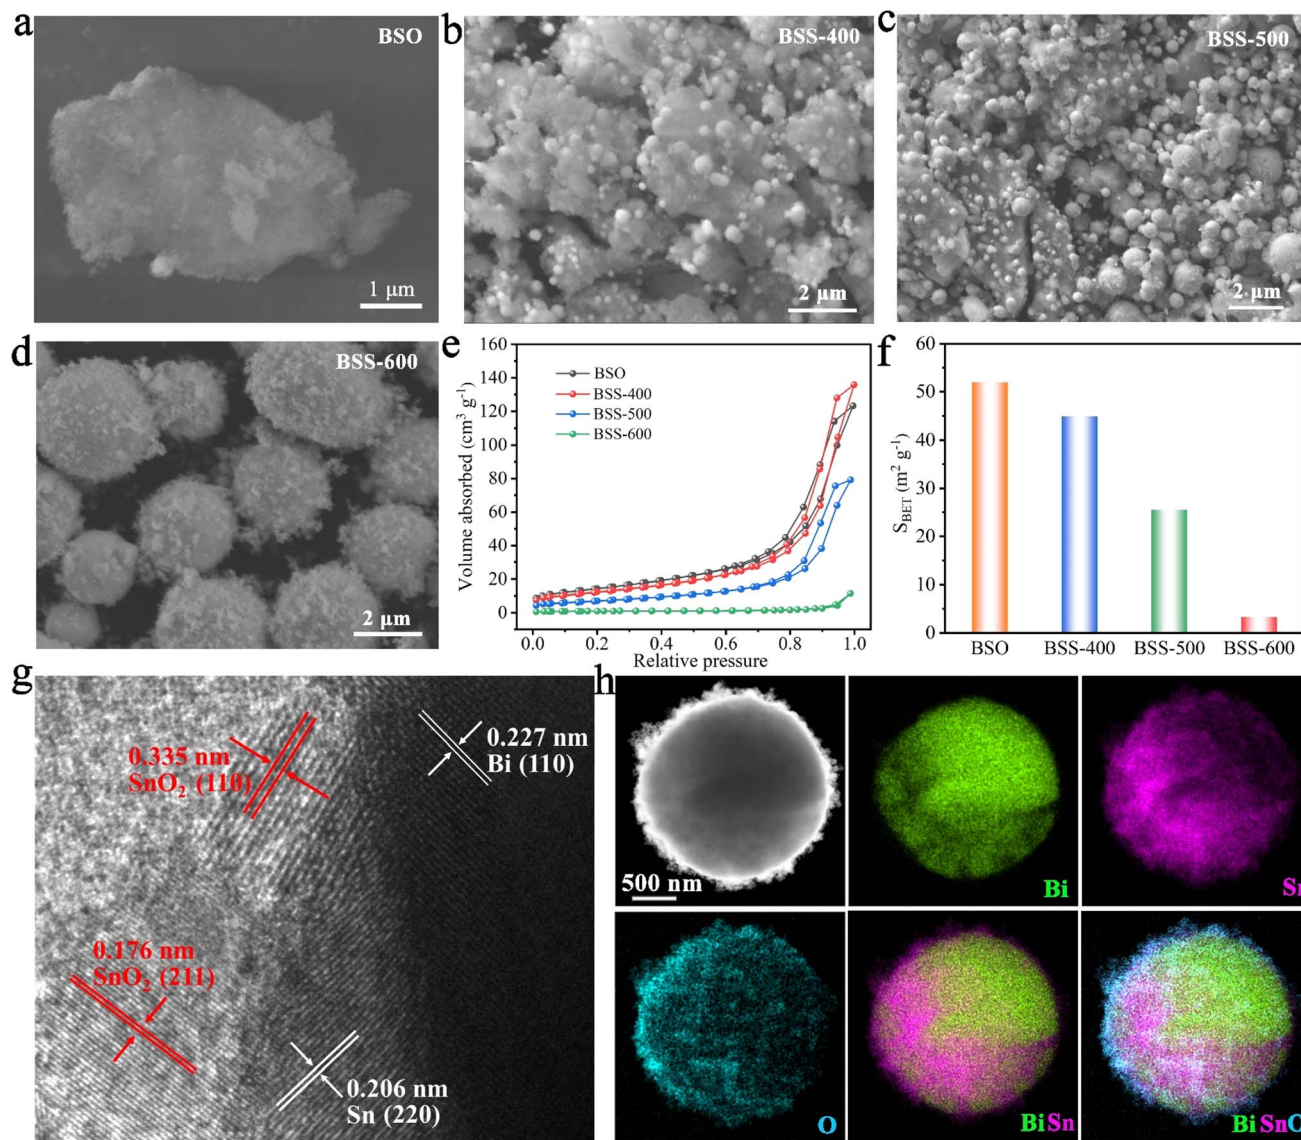


Fig. 2 (a–d) SEM images of BSO, BSS-400, BSS-500 and BSS-600; (e and f) N<sub>2</sub> adsorption–desorption isotherms and BET surface areas. (f) HRTEM-image of BSS-600. (g and h) HADDF-STEM image of BSS-600 and the corresponding elemental color mapping for Bi, Sn, and O.

first three cycles, the BSS-600 electrode forms *in situ* porous Bi and Sn as in the SEM image and elemental mappings of the activated BSS-600 electrode (Fig. 3b), which can be associated with the irreversible volume expansion in Mg<sup>2+</sup> embedding and subsequent Mg<sup>2+</sup> stripping, as well as the presence of defects. The formation of the porous alloy enhances the electrode's specific surface area, which is more conducive to electrochemical reactions. The huge changes in the morphology of the BSS-600 electrodes reflect the presence of large internal stresses during Mg<sup>2+</sup> ion intercalation/extraction. Following 20 cycles, the porous alloy undergoes further nanosizing to form a nanoporous alloy, which has been proven to be advantageous in increasing the contact surface area between the anode and electrolyte and shortening the diffusion path of Mg<sup>2+</sup> ions. This process can facilitate the improvement of electrode performance and accommodate internal stresses, ensuring a stable

cycling capacity. The elemental mappings display a more pronounced Bi signal and a partially overlapping Sn signal, which indicates the combination of nanoporous Bi and nano-Sn. The lattice spacings of the nanoporous alloy are measured to be approximately 0.328 nm and 0.376 nm (Fig. 3d), which correspond to the (012) and (101) lattice planes of Bi. The interplanar spacing of 0.326 nm can be indexed to the (012) lattice plane and the major peak at 27.3° of Bi. It is worth noting that a few defects were identified in larger grains, which can be associated with the formation of vacancies during the deoxygenation process. The continuous nanoporous alloy can be believed to be nanoporous Bi. Significant variations in particle size, from ~5 μm in pristine BSS-600 to ~50 nm in the cycled BSS-600 can be attributed to phase separation, defects and the volume change in Mg<sup>2+</sup> embedding/stripping. The SEM images and corresponding elemental mappings (Fig. 3 and S5†)

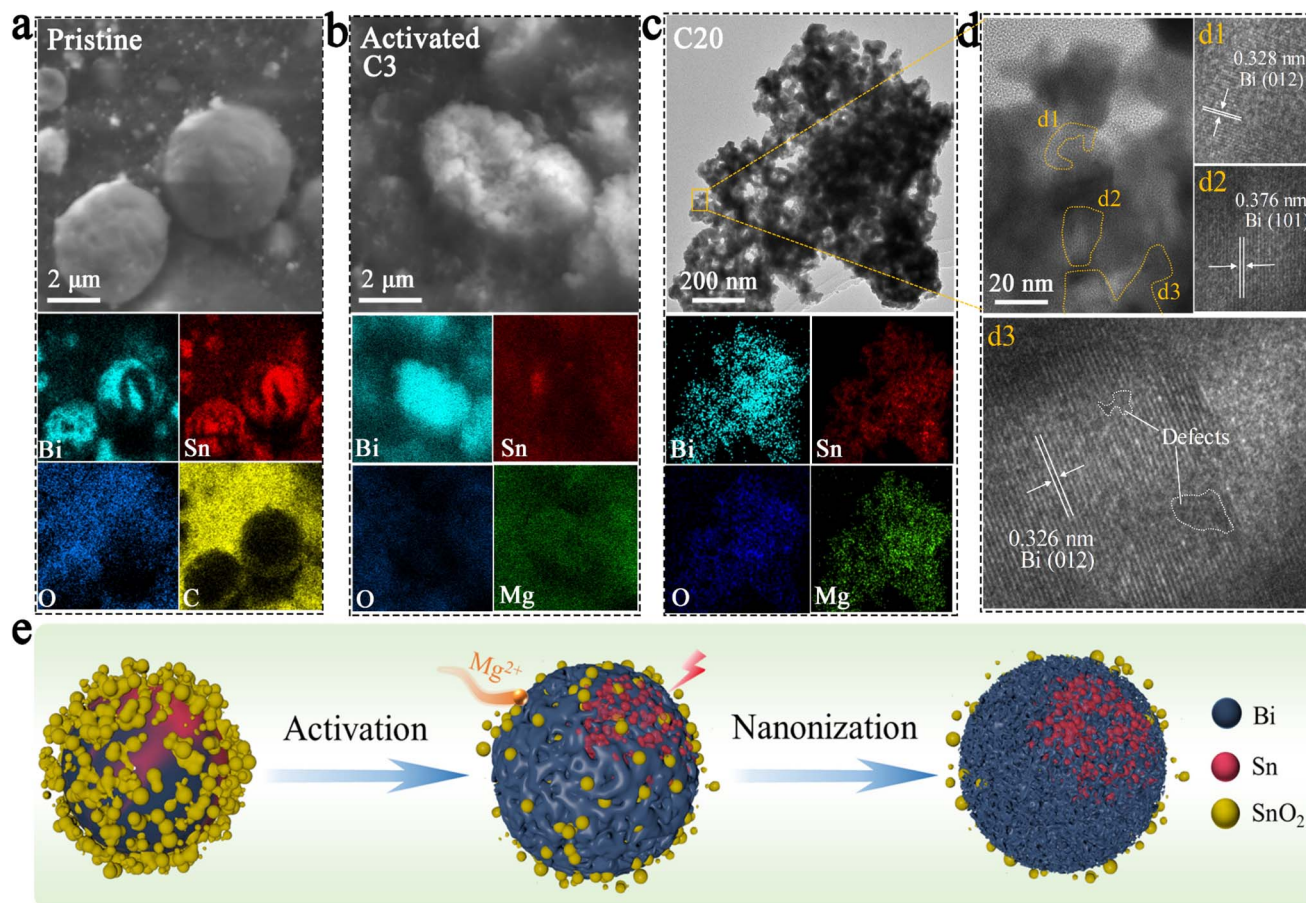


Fig. 3 SEM images and elemental mappings of the (a) pristine BSS-600 electrode and (b) activated BSS-600 electrode. (c) TEM image and elemental mappings, and (d) HRTEM image of the BSS-600 electrode after the 20<sup>th</sup> charge. (e) Schematic illustration of morphological evolution of the BSS-600 electrode during cycles.

indicate that nanosized Sn rather than nanoporous Sn is obtained. The structural differences between Bi and Sn can be attributed to the magnitude of the volume change that occurs during the embedding and stripping of  $\text{Mg}^{2+}$ . In comparison to the 100% volume change during Bi magnesiation, the 214% volume change during Sn magnesiation can be excessive for the formation of a continuous nanoporous alloy structure.

## 2.2 Electrochemical performance and kinetic analyses

The cycling performance of as-prepared samples was tested at a current density of  $50 \text{ mA g}^{-1}$ . The two initial cycles demonstrated obvious irreversible capacity in the first-cycle reactions for the BSO, BSS-400, and BSS-500 samples. For the BSO ( $\text{Bi}_2\text{Sn}_2\text{O}_7$ ) sample, a capacity of up to  $958 \text{ mA h g}^{-1}$  in the initial discharge decayed rapidly in the subsequent discharges as shown in Fig. 4a. Additionally, the 0.8–0.2 eV plateau observed in the initial discharge curve disappeared in the subsequent discharge (Fig. S6†). It can be assumed that the irreversible capacity loss and low stability observed in the BSO sample without thermal reduction (deoxygenation) are related to the formation of MgO (one of the components of the passivation film), which impedes the reversible insertion/extraction of  $\text{Mg}^{2+}$

ions. For the BSS-400 and BSS-500 samples, the initial capacity of the BSS-400 and BSS-500 electrodes was 185 and  $216 \text{ mA h g}^{-1}$ , respectively, which subsequently decreased to 125 and  $180 \text{ mA h g}^{-1}$  during the 2<sup>nd</sup> discharge (Fig. 4a). The corresponding charge/discharge curves for the two initial cycles are shown in Fig. 4b. The sloping platform from 0.6–0.1 V is observed at the first cycle, which can be related to the irreversible reaction of  $\text{SnO}_x$  (one of the phase components of BSS-400 and BSS-500 samples based on the XRD analysis above,  $0 < x < 3.5$ ) and lead to irreversible capacity loss. For the BSS-600 sample, the capacity decay behavior is not observed. In the initial discharge of the BSS-600 electrode, the voltage drops to  $\sim 20 \text{ mV}$  and then increases again (Fig. 4b). The characteristic potential drop during the initial discharge is also observed in other alloy anodes<sup>46,47</sup> for RMBS, which is related to the adsorption and aggregation of  $\text{Mg}^{2+}$  ions on the surface of alloy particles. To further investigate the first cycle, GITT curves of the as-prepared samples (Fig. S7†) were obtained at  $20 \text{ mA g}^{-1}$ . The GITT curves show the sloping discharge plateau at 0.8–0.2 V in BSO, BSS-400 and BSS-500 samples, which might be related to  $\text{SnO}_x + \text{Mg}^{2+} \rightarrow \text{Mg}_y\text{SnO}_2$ . The demagnesiation of  $\text{Mg}_y\text{SnO}_2$  occurs during charging at  $20 \text{ mA g}^{-1}$  (Fig. S7†), not at  $50 \text{ mA g}^{-1}$  (Fig. 4b), which suggests that the reaction has kinetics



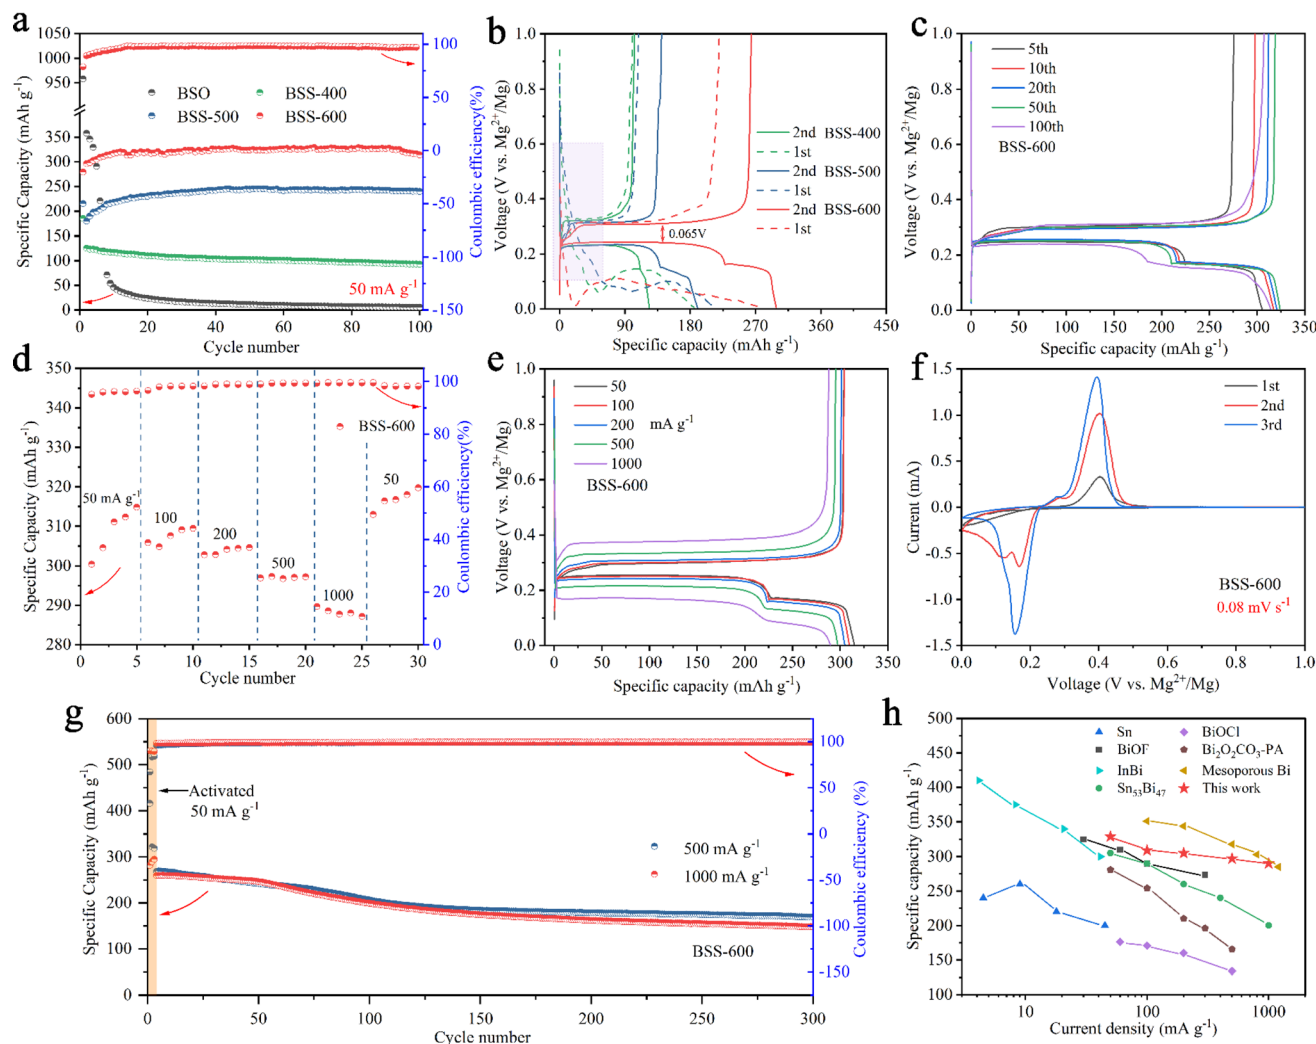


Fig. 4 (a) Cycling performance of the as-prepared samples at  $50 \text{ mA g}^{-1}$ . (b) The first two discharge/charge curves of BSS-400, BSS-500 and BSS-600 corresponding to (a). (c) Discharge/charge profiles of the BSS-600 electrode after different cycles. (d) Rate performance and (e) corresponding discharge/charge curves of the BSS-600 electrode at different current densities. (f) CV curves of the BSS-600 electrode and (g) cycling performance of the BSS-600 electrode at  $500 \text{ mA g}^{-1}$  and  $1 \text{ A g}^{-1}$ . (h) The comparison of rate performance in this work with the reported data in the literature.

limitations. The GITT curve of the BSS-600 electrode exhibits two voltage plateaus related to the magnesiation reactions of Bi and Sn without the plateau reaction of  $\text{SnO}_2$  with  $\text{Mg}^{2+}$  ions, indicating that  $\text{SnO}_2$  can be considered an inactive material.

The cycle performance of BSS-400 is stable from the second cycle, with a capacity retention rate of 74.4% after 100 cycles. In contrast, BSS-500 and BSS-600 exhibit a significant increase in specific capacities during the first 10 cycles. This observation is in accordance with the structural alterations of electrode particles during the cycling process (Fig. 3), which can be attributed to the process whereby the alloy particles undergo cracking and further nanosizing to form the nanoporous Bi and nano-Sn. After 100 cycles, the capacity of BSS-600 and BSS-500 can reach  $314 \text{ mA h g}^{-1}$  and  $240 \text{ mA h g}^{-1}$ , respectively. As shown in Fig. 4b, the discharge/charge curves of the second cycle of the prepared samples exhibit a distinct plateau during the discharge process. The voltage platform at  $\sim 0.24 \text{ V}$

corresponds to the magnesiation of Bi to form  $\text{Mg}_3\text{Bi}_2$  ( $\text{Bi} + 1.5\text{Mg}^{2+} + 3\text{e}^- \rightarrow 0.5\text{Mg}_3\text{Bi}_2$ ) and the voltage platform at  $\sim 0.17 \text{ V}$  corresponds to the magnesiation of Sn to form  $\text{Mg}_2\text{Sn}$  ( $\text{Sn} + 2\text{Mg}^{2+} + 4\text{e}^- \rightarrow \text{Mg}_2\text{Sn}$ ) according to the related literature.<sup>39,48,49</sup> The discharge/charge platforms of BSS-600 show a minimum voltage polarization of  $0.065 \text{ V}$ . Therefore, the following electrochemical tests focus on the BSS-600 alloy.

The discharge/charge profiles of the BSS-600 electrode after different cycles are shown in Fig. 4c. The capacity based on the magnesiation of Sn at  $\sim 0.17 \text{ V}$  increases, while the capacity based on the magnesiation of Bi at  $\sim 0.24 \text{ V}$  decreases with increasing cycles according to the discharge plateaus. The decrease in magnesiation capacity provided by Bi can be related to the electronic disconnection of Bi fragment resulting from particle pulverization. Additionally, magnesiation capacity corresponding to the contribution of  $\text{Mg}_2\text{Sn}$  increases, which can be attributed to the *in situ* formation of nanosized Sn to improve

the electrochemical reactivity. Fig. 4d and e show the rate performance of the BSS-600 electrode at various current densities from 50 to 1000 mA g<sup>-1</sup> and the corresponding discharge/charge profiles. The BSS-600 electrode exhibits an initial discharge capacity of 289 mA h g<sup>-1</sup> at 50 mA g<sup>-1</sup>, which gradually increases to 315 mA h g<sup>-1</sup> in subsequent cycles. This increase is mainly attributed to the enhanced reactivity and specific surface area of the active material resulting from the cracking of the alloy particles. The BSS-600 electrode exhibits excellent rate capacity, with specific capacities of 297 mA h g<sup>-1</sup> at 500 mA h g<sup>-1</sup> and 290 mA h g<sup>-1</sup> at 1 A g<sup>-1</sup>. The specific capacity of BSS-600 can reach 320 mA h g<sup>-1</sup> when the current density returns to 50 mA g<sup>-1</sup>, suggesting its excellent current adaptability. The first three CV curves of BSS-600 are shown in Fig. 4f. It shows that two pairs of redox peaks have been formed in the second cycle. The redox potentials at ~0.16/0.40 V vs. Mg<sup>2+</sup>/Mg are associated with the magnesiation of Bi and demagnesiation of Mg<sub>3</sub>Bi<sub>2</sub>. The redox potentials at ~0.12/0.29 V vs. Mg<sup>2+</sup>/Mg are associated with the magnesiation of Sn and demagnesiation of Mg<sub>2</sub>Sn. The peak intensity increases as the

cycling progresses, which demonstrates that the reaction reactivity of Bi and Sn increases during cycling. Furthermore, the cycling performance of the BSS-600 electrodes was evaluated at 500 mA g<sup>-1</sup> and 1000 mA g<sup>-1</sup>. Prior to testing, an activation process consisting of three formation cycles at 50 mA g<sup>-1</sup> was conducted. The specific capacity of the activated BSS-600 electrode is 260 mA h g<sup>-1</sup> and the specific capacity remains 148 mA h g<sup>-1</sup> after 300 cycles at a current density of 1000 mA g<sup>-1</sup>. At 500 mA g<sup>-1</sup>, the BSS-600 electrode exhibits a capacity of 170 mA h g<sup>-1</sup> after 300 cycles, representing a retention rate of 63.4% in comparison to the initial cycle capacity (268 mA h g<sup>-1</sup>) following activation. The discharge capacity decreases from 416 mA h g<sup>-1</sup> to 322 mA h g<sup>-1</sup> during the first two cycles of activation, which can be attributed to the presence of partially unreduced SnO<sub>x</sub> (0 < x < 3.5) in the test sample, as evidenced by the reaction plateau of 0.6–0.1 V in the first discharge curve (Fig. S8†). Fig. 4h shows a comparison of the rate performance of BSS-600 with the reported data in the literature.<sup>32,36,41,47,50–52</sup> Xu *et al.*<sup>32</sup> reported the synthesis of mesoporous Bi through the etching of BiOI nanosheets grown on

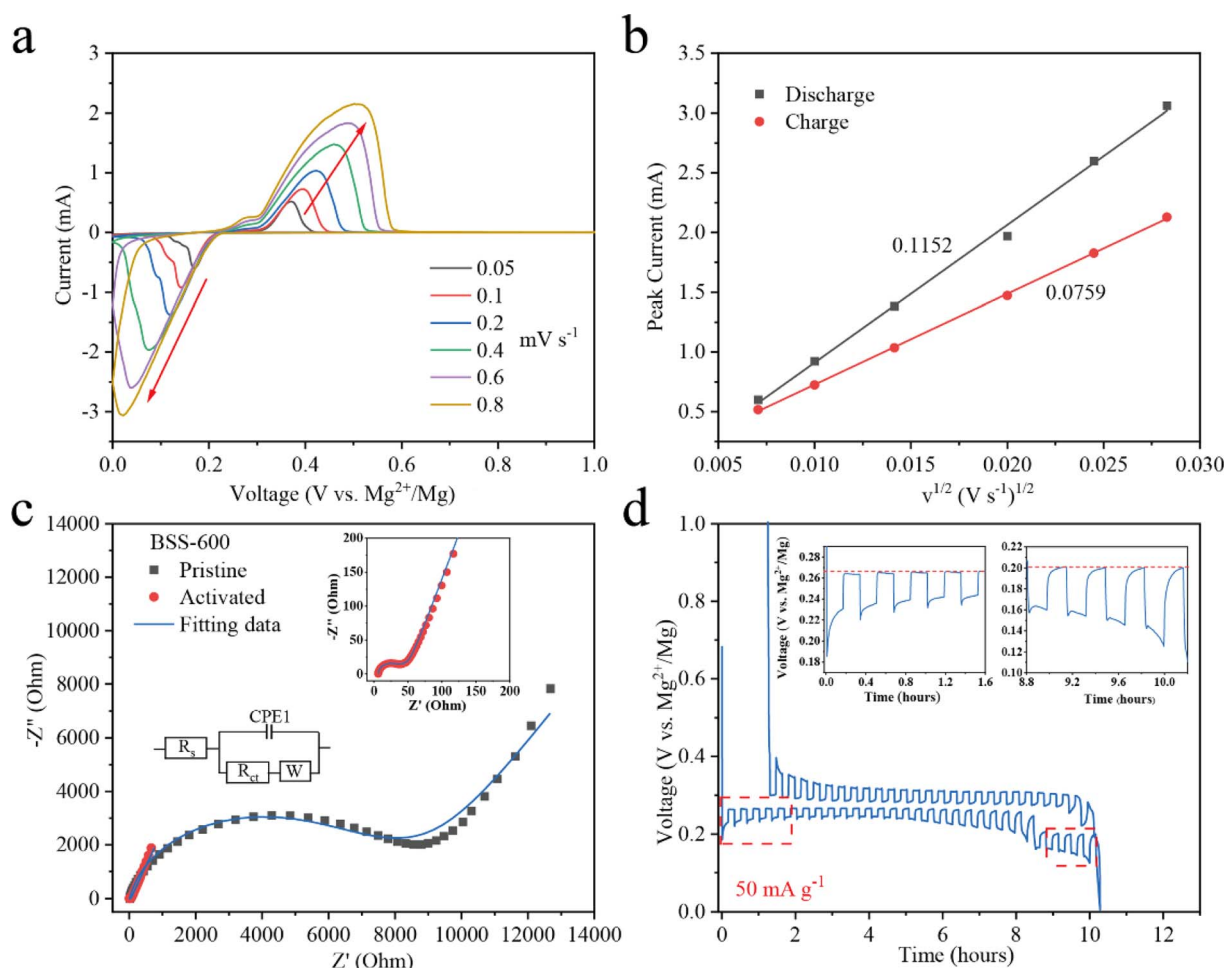


Fig. 5 (a) The CV curves of the BSS-600 electrodes at different scan rates from 0.005 to 0.8 mV s<sup>-1</sup> and (b) a linear fitting for the relationship between the peak current (*I*<sub>p</sub>) and the scan rate *v*<sup>1/2</sup> from the CV curves. (c) Nyquist plots for pristine BSS-600 and activated BSS-600. The insets show the equivalent circuit for the fitting of impedance and the magnified region of pristine BSS-600. (d) GITT curve obtained from a BSS-600//Mg battery, with 10 min of reduction/oxidation at 50 mA g<sup>-1</sup> followed by 10 min of relaxation at the OCV.

carbon cloth (BiOI-CC, obtained by a hydrothermal reaction) with  $\text{Na}(\text{BH})_4$ . Inspired by the reduction of Bi-based compounds, the Bi-Sn@ $\text{SnO}_2$  alloy materials presented in this study were obtained through the thermal reduction of  $\text{Bi}_2\text{Sn}_2\text{O}_7$ , a process that combines Bi and Sn alloys and results in the formation of defects in the binary alloy. Nanoporous Bi and nano-Sn were obtained by Bi-Sn phase separation, defects and  $\text{Mg}^{2+}$  insertion/extraction, which contributes to the achievement of high rate performance ( $297 \text{ mA h g}^{-1}$  at  $500 \text{ mA g}^{-1}$ ) and cycle stability ( $148 \text{ mA h g}^{-1}$  at  $1 \text{ A g}^{-1}$  after 300 cycles). The BSS-600 electrode demonstrates excellent transport properties for  $\text{Mg}^{2+}$  ions among these reported anode materials.

To evaluate the order of magnitude of the apparent diffusion coefficients of  $\text{Mg}^{2+}$  ( $D_{\text{Mg}^{2+}}$ ), cyclic voltammetry (CV) at various scan rates was conducted.<sup>53,54</sup> As the scan rate increases, the peak current ( $I_p$ ) grows stronger as shown in Fig. 5a. The peaks corresponding to the redox reactions between Bi and  $\text{Mg}^{2+}$  ions were chosen to show the linear relationship between the  $I_p$  and the square root of the scanning rate (Fig. 5b). The  $D_{\text{Mg}^{2+}}$  values related to Bi according to the Randles-Sevcik equation (ESI†), are  $2.51 \times 10^{-15}$  and  $1.38 \times 10^{-15} \text{ cm}^2 \text{ s}^{-1}$  ( $n = \sim 1.689$ , obtained based on the 20<sup>th</sup> discharge profile in Fig. 4b and corresponding to the plateau reaction  $\text{Bi} + 1.5\text{Mg}^{2+} + 3\text{e}^- \rightarrow$

$0.5\text{Mg}_3\text{Bi}_2$  at  $\sim 0.24 \text{ eV}$ ) in the  $\text{Mg}^{2+}$  insertion and extraction processes, respectively. Electrochemical impedance spectroscopy (EIS) of the BSS-600 electrode was conducted to further evaluate the  $D_{\text{Mg}^{2+}}$ . EIS of the pristine and activated BSS-600 electrodes is also performed to measure the apparent diffusion coefficient of  $\text{Mg}^{2+}$  in the electrode. From Fig. 5c, the internal resistance ( $R_s$ ) of  $\text{Mg}/\text{BSS-600}$  cells decreases from  $12.96$  to  $6.54 \Omega$  after activation. These impedance spectra comprise a semicircle in the high-frequency region, corresponding to the charge-transfer resistance ( $R_{ct}$ ) at the electrode/electrolyte interface, and an inclined line in the low-frequency region. The  $R_{ct}$  is regarded as a crucial factor in determining the rate performance of electrodes. Activated BSS-600 has a much lower  $R_{ct}$  value ( $22.15 \Omega$ ) compared to pristine BSS-600 ( $5989 \Omega$ ), which might be due to the breakdown of alloy particles and the improved electronic conductivity. At a low frequency, the inclined line was related to the Warburg impedance associated with the diffusion of  $\text{Mg}^{2+}$  ions in the electrode materials.  $D_{\text{Mg}^{2+}}$  values calculated from EIS are  $1.17 \times 10^{-15}$  vs.  $5.88 \times 10^{-17} \text{ cm}^2 \text{ s}^{-1}$  for activated and pristine BSS-600 electrodes, respectively (Table S2†). A GITT study was carried out to better understand the mechanism of Mg insertion and de-insertion in activated BSS-600 anodes. The approach allows

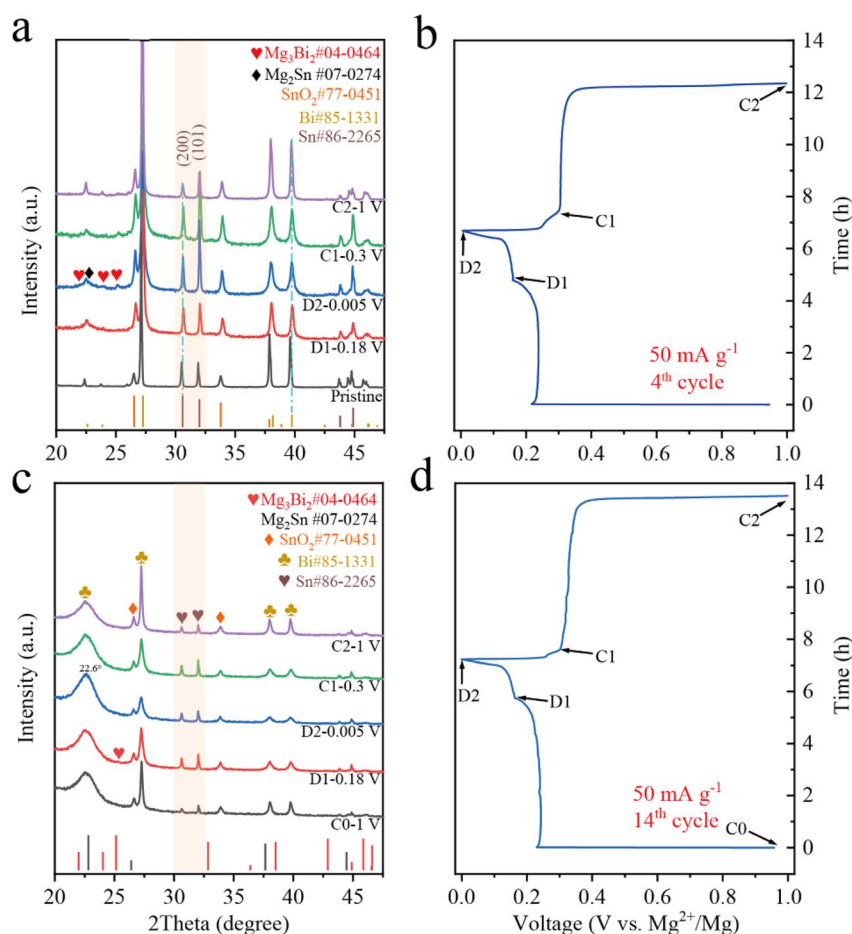


Fig. 6 The *ex situ* XRD patterns and corresponding the discharge/charge curves of the BSS-600 electrodes in the varied states of the 4<sup>th</sup> cycle (a and b) and the 14<sup>th</sup> cycle (c and d).



the electrode to reach its equilibrium potential while also providing insights into kinetics phenomena. The thermodynamic potential is stable at  $\sim 0.27$  V for the magnesiation of Bi and at  $\sim 0.2$  V for the magnesiation of Sn (see the inset of Fig. 5d). It is noted that the OCV potential is reached after fast relaxation, especially the magnesiation of Bi, showing high ion kinetics during the alloying reaction.

### 2.3 Compositional changes and surface chemistry

The electrochemical reactions of the BSS-600 electrode in different discharge/charge stages of the 4<sup>th</sup> cycle are investigated by *ex situ* XRD (Fig. 6a and b). Referring to PDF cards Bi #85-1331 and Sn #86-2265, the diffraction peaks of the Bi and Sn phases in the pristine BSS-600 electrode have shifted to a lower angle by  $\sim 0.1^\circ$ , which can be attributed to the presence of oxygen vacancies in the pristine BSS-600 electrode according to eqn (1) and (2). When being discharged to the end of the first plateau, the diffraction peaks of hexagonal  $\text{Mg}_3\text{Bi}_2$  appear and the peaks corresponding to the Bi phase weaken. It can be concluded that the voltage plateau at 0.24 V is associated with the alloying of Mg with Bi to form  $\text{Mg}_3\text{Bi}_2$ . After completely discharging to 0.005 V, the diffraction peaks of the cubic  $\text{Mg}_2\text{Sn}$  phase are recognized. However, the peaks belonging to the Sn phase strengthen, which could be associated with the exposed Sn phase in the inner part of the BSS-600 particles as the particles crack. Specifically, the peak intensity of the Sn phase at  $32.0^\circ$ , corresponding to its (101) plane, unexpectedly increases and even exceeds its strongest peak at  $30.6^\circ$  corresponding to its (200) plane, which is not observed in other Bi-Sn alloy anodes<sup>34,35</sup> and can be attributed to the Sn-SnO<sub>2</sub> interface favouring the growth of the (101) plane of Sn. To further verify the discharge/charge process, the XRD patterns of the BSS-600

electrode at various states of the 14<sup>th</sup> cycle are shown in Fig. 6c and d. When discharged to 0.18 V, the intensity of the Sn phase diffraction peak increases and that of the Bi phase decreases, which suggests that the magnesiation of Bi could cause the separation of Sn from the Bi-Sn alloy to generate fresh Sn. However, only a weak peak at  $25.1^\circ$  belonging to the  $\text{Mg}_3\text{Bi}_2$  phase is observed, which is inconsistent with the electrochemical profile and the high capacity contribution at 0.24 V. It can be believed that the amorphous Mg-Bi phase is generated. The defects in Bi-Sn@SnO<sub>2</sub> can cause lattice distortion and internal stresses to form amorphous Mg-Bi. In addition,  $\text{Mg}^{2+}$  insertion to Bi with large internal strain during the atomic rearrangement process can hinder the formation of crystalline  $\text{Mg}_3\text{Bi}_2$ . The sharp peak at  $25.1^\circ$  belonging to crystalline  $\text{Mg}_3\text{Bi}_2$  is significantly observed after the 20<sup>th</sup> discharge to 0.18 V (Fig. S9<sup>†</sup>), indicating a gradual reduction of defects and release of stresses with increasing cycling. The formation of nanoporous Bi and nano-Sn is accompanied by the magnesiation reaction of Bi to form  $\text{Mg}_3\text{Bi}_2$ . With discharge from 0.18 V to 0.005 V, the peaks corresponding to the Bi phase and Sn phase diminish. It is worth noting that the peak of the Bi phase at  $22.5^\circ$  is close to the peak of the  $\text{Mg}_2\text{Sn}$  phase at  $22.7^\circ$ , whereas these two peaks merge at  $22.6^\circ$  and strengthen at full magnesiation (D2). These results indicate the magnesiation of Sn to form mainly  $\text{Mg}_x\text{Sn}$  ( $0 < x \leq 2$ ). In subsequent charge in stage C1, the peaks corresponding to the Bi phase and the Sn phase strengthen and the peak intensities return to stage D1, showing the demagnesiation of  $\text{Mg}_x\text{Sn}$  and partial Mg-Bi alloy. With continuous charge to 1 V, the intensity of peaks belonging to the Bi phase increases, suggesting Mg dealloying from the Mg-Bi alloy. The dips in the relative peak signal of Sn may be caused by the considerably higher Bi content in the electrode surface layer, which is induced by phase separation during

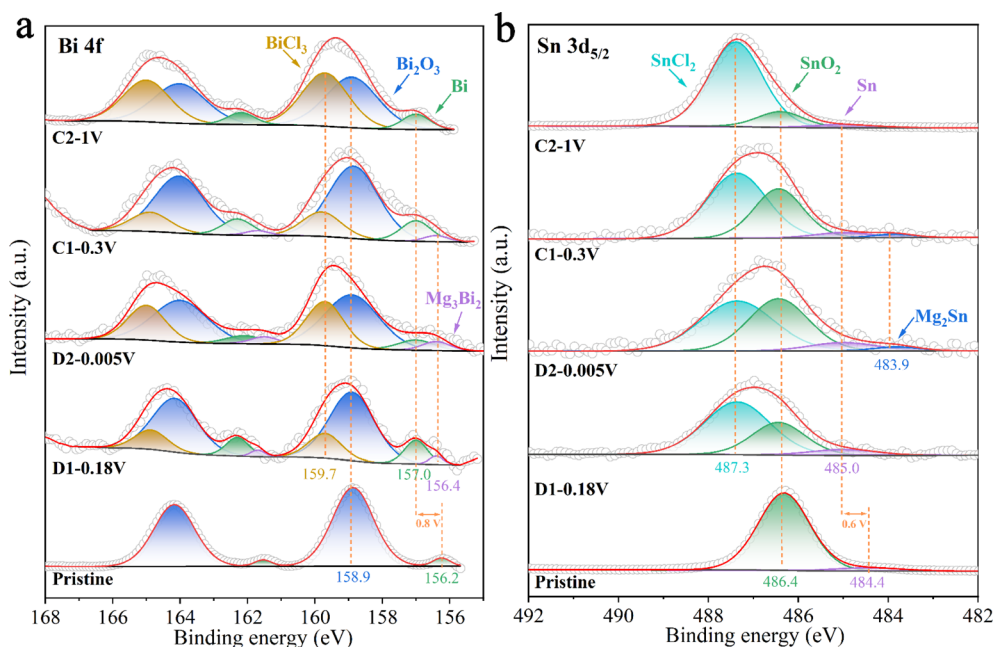


Fig. 7 The *ex situ* XPS spectra at (a) Bi 4f and (b) Sn 3d<sub>5/2</sub> regions at different discharge/charge stages in the 4<sup>th</sup> cycle.

demagnesiation of the Mg–Bi alloy. Therefore, the peak intensity of Sn is reduced in a certain range of the detection area. The XRD pattern of the BSS-600 electrode in stage C2 (Fig. 6c) exhibits a weaker peak for amorphous Mg–Bi and a stronger peak for Bi in comparison to that of stage C0, indicating an irreversible decrease in amorphous Mg–Bi and fast  $\text{Mg}^{2+}$  ion transport in  $\text{Mg}_3\text{Bi}_2$  with the formation of nanoporous Bi during cycling, as evidenced by Mg diffusion calculations for amorphous Mg–Bi and crystalline  $\text{Mg}_3\text{Bi}_2$ .<sup>55</sup>

*Ex situ* XPS was used to investigate the formation and composition of the surface film on the BSS-600 anode resulting from interfacial reactions with the electrolyte during the formation process in the 4<sup>th</sup> cycle. Fig. 7 summarizes the results of curve fitting conducted on the Bi 4f peaks at 168–155 eV and the broad Sn 3d<sub>5/2</sub> peaks at 492–482 eV to determine the relative concentrations of various Bi and Sn species. The surface of the pristine anode contains Sn and Bi metals, which are attributed to the partial amounts of Bi and Sn that were not covered by  $\text{SnO}_2$  on the BSS-600 anode surface. The binding energies of Bi and Sn are 156.2 and 484.4 eV, lower than their corresponding equilibrium binding energies of 157.0 and 485.0 eV, respectively. The peaks of Bi and Sn have exhibited a shift to the equilibrium binding energy position at various discharge/charge states in the 4<sup>th</sup> cycle, in comparison to the pristine anode. This phenomenon could be related to the occurrence of

defects in the pristine particles, which are produced by a suitable degree of deoxygenation and are associated with small amounts of  $\text{SnO}_2$ . During the discharge/charge process, the defects gradually disappear and a porous alloy is formed as a result of the phase transition and atomic rearrangement associated with  $\text{Mg}^{2+}$  insertion/extraction. This observation is in accordance with the *ex situ* XRD analysis of the BSS-600 electrode above. However, the relatively high surface content of  $\text{Bi}_2\text{O}_3$ , with the binding energy always at 158.9 eV, is likely due to surface contamination of the BSS-600 anode with air. The presence of  $\text{SnCl}_2$  and  $\text{BiCl}_3$  at 487.2 and 159.7 V in Fig. 7 is due to the Cl-transfer in the APC electrolyte to Bi and Sn as suggested in the previous reports.<sup>42,56</sup> In particular, the proportions of  $\text{SnCl}_2$  and  $\text{BiCl}_3$  gradually dominated with the end of charging, indicating the occurrence of anode–electrolyte interface reactions. In addition, the Sn content of the BSS-600 electrode surface tends to decrease with the charging process, especially in stage C2 where the relative content is extremely low. As the source of  $\text{SnCl}_2$ , Sn is reduced by the formation of  $\text{SnCl}_2$ , which also explains the reduced XRD peak signal when charged to 1 V. The results indicate that the reaction  $\text{Sn} - \text{e}^- + \text{Cl}^- \rightarrow \text{SnCl}_2$  occurs during the charging process. Meanwhile, the presence of inactive  $\text{SnO}_2$  particles may reduce the reaction at the anode–electrolyte interface. Although  $\text{SnCl}_2$  is soluble in THF, its formation and dissolution can affect the changes in the

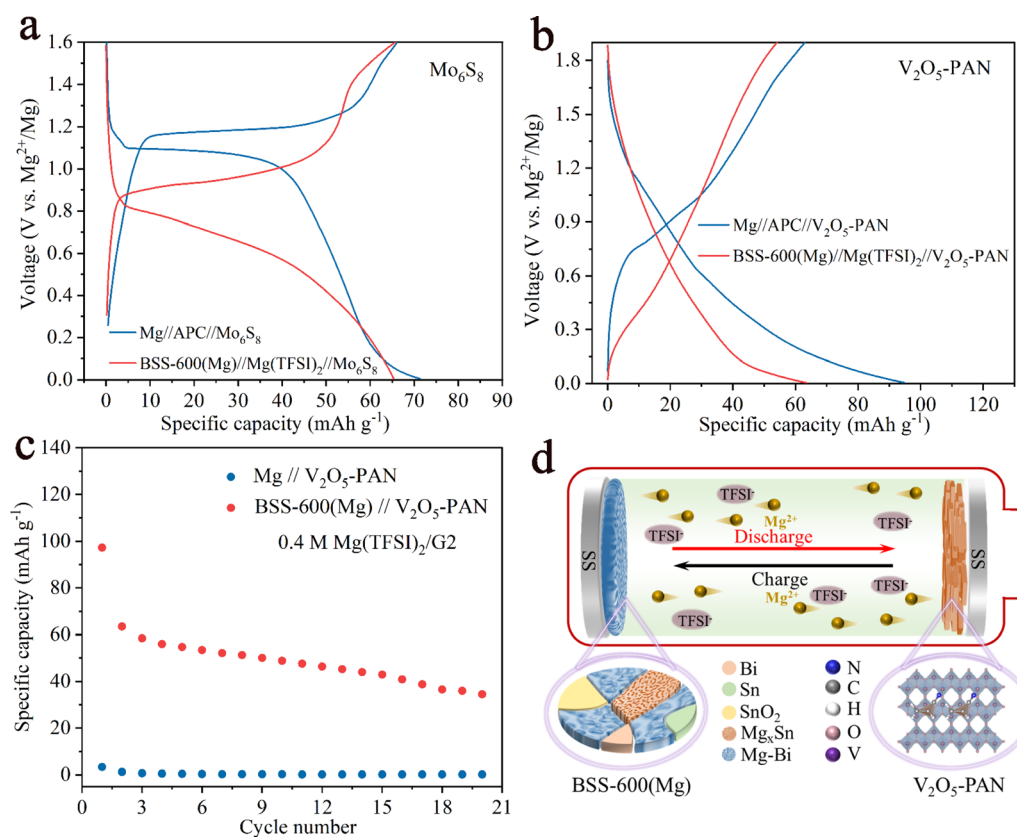


Fig. 8 Full-cell discharge/charge curves for the (a)  $\text{Mo}_6\text{S}_8$  and (b)  $\text{V}_2\text{O}_5\text{-PAN}$  cathode system at  $50 \text{ mA g}^{-1}$ . (c) Comparison of cycling performance of the Mg// $\text{V}_2\text{O}_5\text{-PAN}$  and BSS-600(Mg)// $\text{V}_2\text{O}_5\text{-PAN}$  full cells using Mg(TFSI)<sub>2</sub>/G2 electrolyte. (d) Schematic diagram of the full cell with a BSS-600 anode of the rechargeable magnesium batteries.

anode surface structure and electrochemical performance. The relatively low  $\text{SnO}_2$  content is noted in stage C2, which appears to be  $\text{SnO}_2$  being buried by surface  $\text{SnCl}_2$ . The Mg 1s spectrum (Fig. S10†) of pristine appears upon discharge, which is in agreement with the signal of  $\text{Mg}_3\text{Bi}_2$  in the Bi 4f spectrum and  $\text{Mg}_2\text{Sn}$  in the Sn  $3d_{5/2}$  spectrum. At full demagnesiumation, the Mg signal decreases but does not disappear entirely and the signals from  $\text{Mg}_3\text{Bi}_2$  and  $\text{Mg}_2\text{Sn}$  are not detected, which may be due to the presence of MgO and  $\text{MgCO}_3$ . Above all, the initial several cycles are thought to be required for the BSS-600 electrode to activate the material from the surface to bulk and produce a stable solid electrolyte interface at the anode surface.

## 2.4 Compatibility with conventional electrolytes

Full cells were assembled with a pre-magnesiumated (Mg) BSS-600 anode and cathode ( $\text{Mo}_6\text{S}_8$  and  $\text{V}_2\text{O}_5$ -PAN) coupling the chloride-free  $\text{Mg}(\text{TFSI})_2$  electrolytes. For comparison, we also assembled full cells with 0.4 M APC electrolytes, which are known to be corrosive and have a low-voltage window. For the  $\text{Mo}_6\text{S}_8$  cathode, the discharge/charge curves of the two full cells at 50  $\text{mA g}^{-1}$  are displayed in Fig. 8a. Despite a decrease in the discharge potential of approximately 0.4 V in the full cells, the cathode-limited cells can still deliver a capacity of 65  $\text{mA h g}^{-1}$  when using the  $\text{Mg}(\text{TFSI})_2/\text{G2}$  electrolytes. The first five discharge/charge profiles of BSS-600(Mg)// $\text{Mg}(\text{TFSI})_2/\text{Mo}_6\text{S}_8$  in the potential range of 0–1.8 V at a current density of 50  $\text{mA g}^{-1}$  are presented in Fig. S11.† The overpotential of the full cell gradually reduces, which indicates that the BSS-600 electrode has good compatibility with the  $\text{Mg}(\text{TFSI})_2/\text{G2}$  electrolyte. Fig. 8b illustrates the discharge/charge curves of the  $\text{V}_2\text{O}_5$ -PAN full cells. The BSS-600(Mg)// $\text{Mg}(\text{TFSI})_2/\text{V}_2\text{O}_5$ -PAN full cell has a lower discharge potential than the Mg//APC/ $\text{V}_2\text{O}_5$ -PAN full cell, which proves that the BSS-600 anode engages in a reversible alloying reaction with  $\text{Mg}^{2+}$  ions, not simple Mg adsorption or deposition. According to Fig. 8c, it is shown that the BSS-600(Mg)// $\text{Mg}(\text{TFSI})_2/\text{V}_2\text{O}_5$ -PAN full cell delivers a capacity of 63  $\text{mA h g}^{-1}$  at 50  $\text{mA g}^{-1}$  while the Mg// $\text{Mg}(\text{TFSI})_2/\text{V}_2\text{O}_5$ -PAN full cell shows negligible capacity. In the  $\text{Mg}(\text{TFSI})_2/\text{G2}$  electrolyte, the BSS-600 anode can store  $\text{Mg}^{2+}$  ions through phase transition reactions, as schematically illustrated in Fig. 8d, while the Mg metal anode cannot transport  $\text{Mg}^{2+}$  ions due to the formation of a passivation layer on the Mg surface. These results suggest that using alloy anodes is a practical solution for the passivation issue between magnesium metal anodes and conventional electrolytes.

## 3 Conclusions

In summary, the design of the Bi-Sn@ $\text{SnO}_2$  alloy anode involves alloying and structure control. The Bi-Sn@ $\text{SnO}_2$  alloy was fabricated by annealing the  $\text{Bi}_2\text{Sn}_2\text{O}_7$  precursor at 600 °C for 3 h (BSS-600). The obtained BSS-600 anode can deliver a reversible capacity of 148  $\text{mA h g}^{-1}$  at a current density of 1000  $\text{mA g}^{-1}$  for 300 cycles and exhibit superior rate performance, which could be attributed to the *in situ* formation of nanoporous Bi and nanosized Sn resulting from Bi-Sn phase separation, defects

and  $\text{Mg}^{2+}$  insertion/extraction. The nanostructured Bi and Sn could mitigate volume change and deliver high reversible magnesium storage capacity.  $\text{SnO}_2$  on the Bi-Sn alloy surface can limit the growth of alloy particles and diminish the decomposition of electrolytes. More importantly, the BSS-600 anodes display good compatibility with the Cl-free simple salt  $\text{Mg}(\text{TFSI})_2/\text{G2}$  electrolytes.

## Data availability

Data can be made available on request.

## Conflicts of interest

There are no conflicts of interest to declare.

## Acknowledgements

This work was supported by the National Key R&D Program of China (2023YFB3809500) and the National Natural Science Foundation of China (52171100).

## References

- 1 D. J. Li, Y. Yuan, J. W. Liu, M. Fichtner and F. S. Pan, *J. Magnesium Alloys*, 2020, **8**, 963–979.
- 2 P. Canepa, G. S. Gautam, D. C. Hannah, R. Malik, M. Liu, K. G. Gallagher, K. A. Persson and G. Ceder, *Chem. Rev.*, 2017, **117**, 4287–4341.
- 3 J. W. Choi and D. Aurbach, *Nat. Rev. Mater.*, 2016, **1**, 16013.
- 4 X. B. Cheng and Q. Zhang, *J. Mater. Chem. A*, 2015, **3**, 7207–7209.
- 5 Z. G. Yang, J. L. Zhang, M. C. W. Kintner-Meyer, X. C. Lu, D. W. Choi, J. P. Lemmon and J. Liu, *Chem. Rev.*, 2011, **111**, 3577–3613.
- 6 J. C. Wang, L. L. Zhao, N. Zhang, P. F. Wang and T. F. Yi, *Nano Energy*, 2024, **123**, 109361.
- 7 H. D. Yoo, I. Shterenberg, Y. Gofer, G. Gershinsky, N. Pour and D. Aurbach, *Energy Environ. Sci.*, 2013, **6**, 2265–2279.
- 8 N. Singh, T. S. Arthur, O. Tutusaus, J. Li, K. Kisslinger, H. L. L. Xin, E. A. Stach, X. D. Fan and R. Mohtadi, *ACS Appl. Energ. Mater.*, 2018, **1**, 4651–4661.
- 9 O. Crowther and A. C. West, *J. Electrochem. Soc.*, 2008, **155**, A806–A811.
- 10 M. Matsui, *J. Power Sources*, 2011, **196**, 7048–7055.
- 11 C. H. Chen, J. Liu, M. E. Stoll, G. Henriksen, D. R. Vissers and K. Amine, *J. Power Sources*, 2004, **128**, 278–285.
- 12 A. El Kharbachi, O. Zavorotynska, M. Latroche, F. Cuevas, V. Yartys and M. Fichtner, *J. Alloys Compd.*, 2020, **817**, 153261.
- 13 S. B. Son, T. Gao, S. P. Harvey, K. X. Steirer, A. Stokes, A. Norman, C. S. Wang, A. Cresce, K. Xu and C. M. Ban, *Nat. Chem.*, 2018, **10**, 532–539.
- 14 Z. Lu, A. Schechter, M. Moshkovich and D. Aurbach, *J. Electroanal. Chem.*, 1999, **466**, 203–217.
- 15 R. Attias, M. Salama, B. Hirsch, Y. Goffer and D. Aurbach, *Joule*, 2019, **3**, 27–52.



- 16 I. Shterenberg, M. Salama, Y. Gofer and D. Aurbach, *Langmuir*, 2017, **33**, 9472–9478.
- 17 T. D. Gregory, R. J. Hoffman and R. C. Winterton, *J. Electrochem. Soc.*, 1990, **137**, 775–780.
- 18 D. Aurbach, Z. Lu, A. Schechter, Y. Gofer, H. Gizbar, R. Turgeman, Y. Cohen, M. Moshkovich and E. Levi, *Nature*, 2000, **407**, 724–727.
- 19 D. Aurbach, G. S. Suresh, E. Levi, A. Mitelman, O. Mizrahi, O. Chusid and M. Brunelli, *Adv. Mater.*, 2007, **19**, 4260.
- 20 D. Samuel, C. Steinhauser, J. G. Smith, A. Kaufman, M. D. Radin, J. Naruse, H. Hiramatsu and D. J. Siegel, *ACS Appl. Mater. Interfaces*, 2017, **9**, 43755–43766.
- 21 H. M. Xu, Z. H. Zhang, J. J. Li, L. X. Qiao, C. L. Lu, K. Tang, S. M. Dong, J. Ma, Y. J. Liu, X. H. Zhou and G. L. Cui, *ACS Appl. Mater. Interfaces*, 2018, **10**, 23757–23765.
- 22 R. Mohtadi, M. Matsui, T. S. Arthur and S. J. Hwang, *Angew. Chem., Int. Ed.*, 2012, **51**, 9780–9783.
- 23 J. Z. Niu, Z. H. Zhang and D. Aurbach, *Adv. Energy Mater.*, 2020, **10**, 2000697.
- 24 W. Jin, Z. J. Li, Z. G. Wang and Y. Q. Fu, *Mater. Chem. Phys.*, 2016, **182**, 167–172.
- 25 S. C. Jung and Y. K. Han, *J. Phys. Chem. C*, 2018, **122**, 17643–17649.
- 26 Z. G. Liu, J. Lee, G. L. Xiang, H. F. J. Glass, E. N. Keyzer, S. E. Dutton and C. P. Grey, *Chem. Commun.*, 2017, **53**, 743–746.
- 27 T. S. Arthur, N. Singh and M. Matsui, *Electrochem. Commun.*, 2012, **16**, 103–106.
- 28 Z. Meng, D. Foix, N. Brun, R. Dedryvère, L. Stievano, M. Morcrette and R. Berthelot, *ACS Energy Lett.*, 2019, **4**, 2040–2044.
- 29 J. Z. Niu, H. Gao, W. S. Ma, F. K. Luo, K. B. Yin, Z. Q. Peng and Z. H. Zhang, *Energy Storage Mater.*, 2018, **14**, 351–360.
- 30 J. Wang, R. Yu, J. Wang, J. Long, F. Qiao, L. Zhang, G. He, Q. An and L. Mai, *J. Magnesium Alloys*, 2023, **11**, 4181–4188.
- 31 K. V. Kravchyk, L. Piyeteau, R. Caputo, M. He, N. P. Stadie, M. I. Bodnarchuk, R. T. Lechner and M. V. Kovalenko, *ACS Nano*, 2018, **12**, 8297–8307.
- 32 X. Xu, D. L. Chao, B. Chen, P. Liang, H. Li, F. X. Xie, K. Davey and S. Z. Qiao, *Angew. Chem., Int. Ed.*, 2020, **59**, 21728–21735.
- 33 Y. Y. Shao, M. Gu, X. L. Li, Z. M. Nie, P. J. Zuo, G. S. Li, T. B. Liu, J. Xiao, Y. W. Cheng, C. M. Wang, J. G. Zhang and J. Liu, *Nano Lett.*, 2014, **14**, 255–260.
- 34 J. Z. Niu, K. B. Yin, H. Gao, M. J. Song, W. S. Ma, Z. Q. Peng and Z. H. Zhang, *Nanoscale*, 2019, **11**, 15279–15288.
- 35 M. J. Song, J. Z. Niu, K. B. Yin, H. Gao, C. Zhang, W. S. Ma, F. K. Luo, Z. Q. Peng and Z. H. Zhang, *Nano Res.*, 2019, **12**, 801–808.
- 36 M. J. Song, T. B. Zhang, J. Z. Niu, H. Gao, Y. J. Shi, Y. Zhang, W. S. Ma and Z. H. Zhang, *J. Power Sources*, 2020, **451**, 227735.
- 37 F. Murgia, D. Laurencin, E. T. Weldekidan, L. Stievano, L. Monconduit, M. L. Doublet and R. Berthelot, *Electrochim. Acta*, 2018, **259**, 276–283.
- 38 M. J. Song, J. Z. Niu, H. Gao, T. Y. Kou, Z. K. Wang and Z. H. Zhang, *J. Mater. Chem. A*, 2020, **8**, 13572–13584.
- 39 D. C. Gu, Y. Yuan, J. W. Liu, D. J. Li, W. B. Zhang, L. Wu, F. Y. Cao, J. F. Wang, G. S. Huang and F. S. Pan, *J. Power Sources*, 2022, **548**, 232076.
- 40 X. Chai, H. Xie, T. T. Zhang, Y. Xin, F. Zhang, B. He, H. Xie, L. Yu and H. Tian, *Energy Storage Mater.*, 2024, **70**, 103460.
- 41 N. Singh, T. S. Arthur, C. Ling, M. Matsui and F. Mizuno, *Chem. Commun.*, 2013, **49**, 149–151.
- 42 D. T. Nguyen, X. M. Tran, J. Kang and S. W. Song, *Chemelectrochem*, 2016, **3**, 1813–1819.
- 43 F. Nacimiento, M. Cabello, C. Pérez-Vicente, R. Alcántara, P. Lavela, G. Ortiz and J. Tirado, *Nanomaterials*, 2018, **8**, 501.
- 44 L. R. Parent, Y. W. Cheng, P. V. Sushko, Y. Y. Shao, J. Liu, C. M. Wang and N. D. Browning, *Nano Lett.*, 2015, **15**, 1177–1182.
- 45 W. Fan, H. Li, F. Zhao, X. Xiao, Y. Huang, H. Ji and Y. Tong, *Chem. Commun.*, 2016, **52**, 5316–5319.
- 46 X. Peng, Y. Yuan, D. Gu, X. Zheng, D. Li, L. Wu, G. Huang, J. Wang and F. Pan, *Small*, 2024, 2400967.
- 47 F. Murgia, L. Monconduit, L. Stievano and R. Berthelot, *Electrochim. Acta*, 2016, **209**, 730–736.
- 48 M. Song, T. Zhang, J. Niu, H. Gao, Y. Shi, Y. Zhang, W. Ma and Z. Zhang, *J. Power Sources*, 2020, **451**, 227735.
- 49 F. Zhang, Y. Shen, H. Xu and X. Zhao, *ACS Appl. Mater. Interfaces*, 2023, **15**, 23353–23360.
- 50 S. Chen, Y. B. Du, H. P. Ma, Z. T. Wang, S. Fan, W. M. Zhang and H. Y. Yang, *Nano Lett.*, 2023, **23**, 9788–9795.
- 51 W. Wang, L. Liu, P. F. Wang, T. T. Zuo, Y. X. Yin, N. Wu, J. M. Zhou, Y. Wei and Y. G. Guo, *Chem. Commun.*, 2018, **54**, 1714–1717.
- 52 C. X. Zhu, Y. K. Tang, L. Liu, X. Bai, Y. Y. Xu, Y. Nuli and J. L. Wang, *Mater. Horiz.*, 2023, **10**, 1719–1725.
- 53 W. Wang, L. Liu, P. F. Wang, T. T. Zuo, Y. X. Yin, N. Wu, J. M. Zhou, Y. Wei and Y. G. Guo, *Chem. Commun.*, 2018, **54**, 1714–1717.
- 54 L. Yang, L. Guo, D. Yan, Y. Wang, T. Shen, D. S. Li, M. E. Pam, Y. Shi and H. Y. Yang, *ACS Nano*, 2023, **17**, 6754–6769.
- 55 S. C. Jung and Y. K. Han, *J. Phys. Chem. C*, 2018, **122**, 17643–17649.
- 56 D. Aurbach, I. Weissman, Y. Gofer and E. Levi, *Chem. Rec.*, 2003, **3**, 61–73.