

Cite this: *Dalton Trans.*, 2025, **54**, 487Received 15th November 2024,
Accepted 4th December 2024

DOI: 10.1039/d4dt03198a

rsc.li/dalton

Ring-opening polymerization of ϵ -caprolactone with a macrocyclic tetracarbene indium complex†

Henry R. Brothers,^a Raju Chambenahalli,^b Gary S. Nichol,^b
Jennifer A. Garden^b and David M. Jenkins^a

The first chiral tetracarbene indium(III) complexes have been synthesized by employing a rigid dianionic macrocyclic tetra-NHC ligand. The macrocyclic indium tetra-NHC bromide and ethoxide complexes are structurally similar to analogous salen complexes. The indium ethoxide complex effectively promotes living ring-opening polymerization of ϵ -caprolactone at room temperature.

Neutral auxiliary ligands that are ubiquitous for transition-metal catalysts, such as N-heterocyclic carbenes (NHCs),^{1,2} have found limited application in p-block metal catalysis.^{3,4} Main group metals' preference for ligands with anionic character has limited NHCs to a single donor ligand (as a Lewis base) in most cases,^{5–7} which has curtailed utilization of polydentate NHCs as supporting ligands.⁸ Indeed, to circumvent this mismatch, two primary strategies have been adopted to include an anionic component to the NHCs. Preparation of NHC ligand precursors which contain hydroxyl or amino functionality gives rise to main group metal–NHC complexes with anionic linkages to the NHC motif *via* alkoxy or amido tethers, respectively.^{9,10} Alternatively, inclusion of borate groups within NHC ligand precursors is an effective strategy towards main group metal–NHC complexes which are stabilized by the anionic contributions from distal borate moieties instead of anionic tethers.^{11,12} While these two strategies have been effectively employed for metals such as germanium and tin, there are very few reports of tethered or borate-containing NHCs on group 13 metals such as gallium,^{10,12} indium,¹¹ or thallium.

This lack of effective NHC ligands for indium is disappointing since indium catalysis has been demonstrated to be

effective and selective for organic transformations such as directed carbonyl–ene reactions,¹³ catalytic alcohol dehydration for S_N1 reactions,¹⁴ and catalytic alkyne hydrofunctionalization reactions.¹⁵ Beyond these molecular processes, indium catalysis has particularly shined in the development of ring opening polymerization processes, especially for the polymerization of cyclic esters.^{16,17} Recently, the Williams,^{6,18} Rieger,¹⁹ Carpentier,^{20,21} and Mehrkhodavandi^{22–24} research groups have all independently developed effective indium catalysts for synthesis of polylactic acid (PLA) or polycaprolactone (PCL). Notably, the auxiliary ligands for these systems are often Schiff bases that are based on a tetradentate salen-type motif.

Our group has developed extensive chemistry for anionic tetradentate NHC ligands which are structurally analogous to salen-type ligands.^{25,26} These ligands are highly effective at supporting iron catalysts for catalytic $C_2 + N_1$ aziridination reactions.²⁷ Recently, we reported an approach to synthesize a D_2 -symmetric variant of this ligand with enhanced structural rigidity.²⁸ However, to our knowledge no anionic borate-based NHCs have been employed for catalysis with p-block metals.

In this manuscript, we showcase the syntheses of stable indium complexes supported by a chiral anionic tetracarbene macrocyclic ligand. The absolute stereochemistries of the complexes were confirmed by single crystal X-ray diffraction. An indium complex with ethoxide as an axial ligand efficiently promotes living polymerization of ϵ -caprolactone at room temperature.


Results and discussion

We have previously described the synthesis of the chiral macrocyclic ligand (^(S,S)-1,2-Cy,BMe₂TC^H), **1**, and its iron and palladium complexes.²⁸ To prepare the indium complex of **1**, we employed a similar ligation strategy. Compound **1** was deprotonated with ⁿBuLi at –35 °C in THF before addition of indium(III) bromide at room temperature (Scheme 1). Repeated extraction and filtration of the crude product with benzene efficiently

^aDepartment of Chemistry, The University of Tennessee, Knoxville, Tennessee 37996, USA. E-mail: jenkins@ion.chem.utk.edu

^bSchool of Chemistry, University of Edinburgh, West Mains Road, Edinburgh, EH9 3FJ, UK. E-mail: J.Garden@ed.ac.uk

† Electronic supplementary information (ESI) available: Full experimental details and characterization for all compounds is provided, including NMR spectra, IR spectra, UV-Vis spectra, and X-ray diffraction data. CCDC 2401889 and 2401890. For ESI and crystallographic data in CIF or other electronic format see DOI: <https://doi.org/10.1039/d4dt03198a>

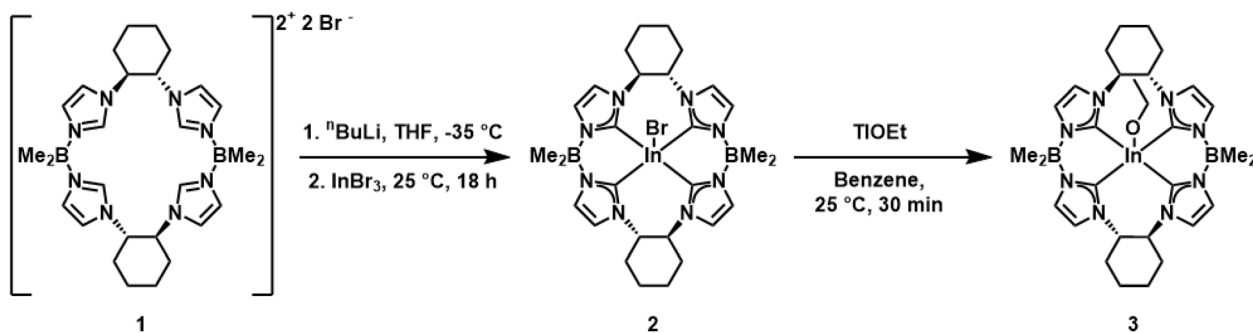

Scheme 1 Synthesis of indium complexes 2 and 3.

removes residual lithium bromide salts. (S,S) -1,2-Cy,BMe₂TC^HInBr, 2, was crystallized by diluting a concentrated benzene solution with *n*-pentane, affording colorless needles of 2 in 43% yield. Unlike our previously reported tetracarbenyl complex of indium, 2 is stable in air free environments, which is likely due to the improved steric protection of the chiral pocket.¹¹

The ¹H NMR spectrum for 2 shows a C₂-symmetric complex with resonances broadly similar to square planar (S,S) -1,2-Cy,BMe₂TC^HPd (Fig. S1†).²⁸ Two separate ¹H NMR signals are observed for protons bound to the chiral carbons and there are four vicinal doublets that correspond to the imidazolylidene protons. Like similar diamagnetic five coordinate tetracarbenyl complexes that we have reported previously, the protons from the methyl groups attached to the borate moieties are diastereotopic and locked into a single conformation.^{26,28,29} Finally, the ¹³C NMR spectrum for 2 gives two carbene resonances at 179.36 ppm and 178.15 ppm (Fig. S2†).²⁸

Single crystal X-ray diffraction for (S,S) -1,2-Cy,BMe₂TC^HInBr shows that the complex adopts a slightly distorted square pyramidal geometry (Fig. 1A). The In–C bond distances are inequivalent with In–C₁ (2.20(2) Å) and In–C₃ (2.20(2) Å) being shorter than In–C₂ (2.29(2) Å) and In–C₄ (2.28(2) Å). Likewise, the *trans* angles across the macrocycle are also not equivalent, where C₁–In–C₃ is 153.3(7)° while C₂–In–C₄ is 140.0(8)°. These tight angles move the indium atom out of the macrocycle's plane much more than the achiral variant, (Et) ,BMe₂TC^HInBr, which we previously reported.¹¹

We were interested in synthesizing an indium alkoxide complex since alkoxide ligands are effective initiators for ring-opening polymerization of cyclic esters.^{6,18} Since 2 bears a single axial bromide ligand, we thought that ligand metathesis could allow for preparation of a macrocyclic tetra-NHC indium (III) alkoxide complex. Indeed, treating a benzene solution of 2 with thallium ethoxide resulted in immediate precipitation of pale yellow TlBr salt and afforded (S,S) -1,2-Cy,BMe₂TC^HIn(OEt), 3, in 67% yield after crystallization (Scheme 1).

The NMR spectra for 3 are similar to 2, but feature additional resonances related to the ethoxide ligand, with diagnostic ¹H NMR resonances at 4.01 and 1.23 ppm for the ethoxide ligand (Fig. S6†). Furthermore, the triplet-of-doublet

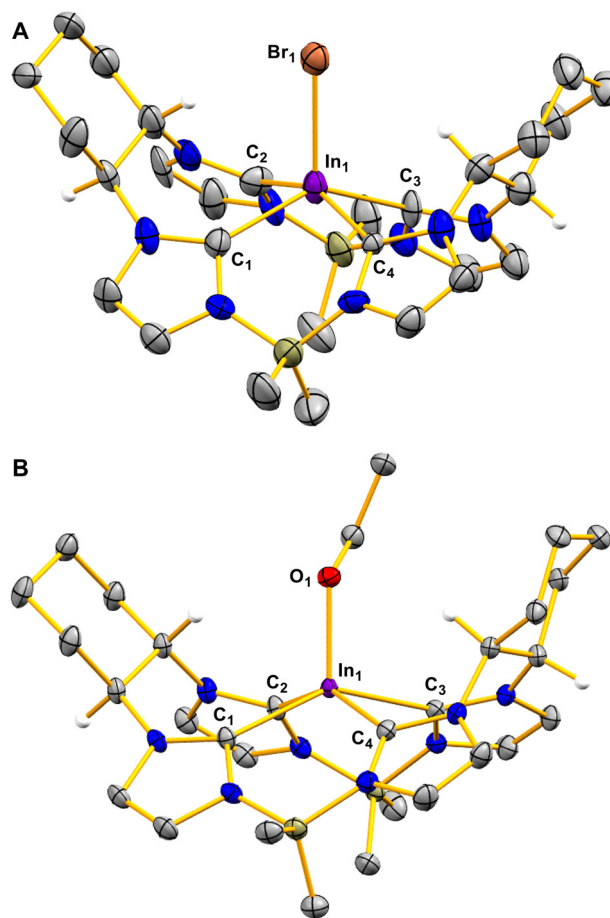


Fig. 1 X-Ray crystal structures of 2 (A) and 3 (B). Purple, olive, blue, orange, red, grey, and white ellipsoids (50% probability) represent indium, boron, nitrogen, bromine, oxygen, carbon, and hydrogen atoms, respectively. Solvent molecules and H-atoms on non-stereogenic carbons are omitted for clarity. One conformer from the asymmetric unit cell of both 2 and 3 are shown. Selected bond distances (Å) and angles (°) are as follows: for 2, In₁–C₁, 2.20(2); In₁–C₂, 2.29(2); In₁–C₃, 2.20(2); In₁–C₄, 2.28(2); In₁–Br₁, 2.583(3); C₁–In₁–C₃, 153.3(7); C₂–In₁–C₄, 140.0(8). For 3, In₁–C₁, 2.326(2); In₁–C₂, 2.221(2); In₁–C₃, 2.343(2); In₁–C₄, 2.235(2); In₁–O₁, 2.07(1); C₁–In₁–C₃, 145.73(6); C₂–In₁–C₄, 149.16(6).

resonances related to diastereotopic protons on the stereogenic cyclohexane carbons are shifted upfield to 6.00 and 4.21 ppm relative to those in the ^1H NMR spectrum for **2** (6.39 and 4.31 ppm). The ^{13}C NMR spectrum for **3** gives two carbene carbon resonances at 181.77 ppm and 180.39 ppm in addition to two new resonances at 63.14 and 23.65 ppm which correspond to ethoxide carbons (Fig. S7†).

Crystals of suitable quality for SCXRD were obtained *via* vapor diffusion of *n*-pentane into a benzene solution of **3**. Like **2**, a distorted square pyramidal geometry is observed in the crystal structure for **3** with $\text{C}_1\text{-In-C}_3$ as $145.73(6)^\circ$ while $\text{C}_2\text{-In-C}_4$ is $149.16(6)^\circ$ (Fig. 1B). The In-C_{NHC} bond lengths for **3** between 2.221(2) Å and 2.343(2) Å are longer compared to those for **2**. The In-O_1 bond distance (2.07(1) Å) is comparable to the few other examples of monomeric indium alkoxides.^{6,30}

Ring opening polymerization (ROP) of ϵ -caprolactone (CL) promoted by **2** and **3** was examined to determine the effectiveness of **1** as an auxiliary ligand *versus* similarly structured tetradentate ligands.^{18,19,24} As such, the reactivities of complexes **2** and **3** with CL were tested under conditions similar to previous reported methods: 1 mmol CL, 0.01 mmol complex (7.5 mM, benzene), at 25 °C. The PCL products were analyzed using size exclusion chromatography (SEC). Reaction kinetics were monitored by quenching aliquots at specified time intervals before ^1H NMR analysis.

Synthesis of PCL was attempted first with **2** as initiator. These reactions quickly produced extremely viscous mixtures that gave inconsistent kinetic data and afforded PCL products with unexpectedly high molecular weights and high dispersity

values. These observations suggest poor initiation efficiency from the In-Br unit, which affects poor molecular weight control over PCL products.³¹ These results prompted the synthesis of **3** so that an efficient and unambiguous initiator for CL ROP could be prepared.

When complex **3** was used as the initiator for CL ROP, kinetic experiments showed rapid consumption of CL consistent with a first-order reaction rate (Fig. 2A), albeit with a slight induction period. The linear correlation between the polymer number-averaged molecular weight (M_n) and monomer conversion suggests that **3** promotes living CL ROP (Fig. 2B and Table S1†). Strict molecular weight control was maintained over the PCL products that were made using **3**; dispersity values were narrowed from 1.24 to 1.08 as monomer conversion increased, which indicates single site activation (Fig. 2B). Efficient, living CL ROP by **3** is further evidenced by the monomodal molecular weight distributions observed throughout the reaction (Fig. 2C).

Matrix-assisted laser desorption ionization time-of-flight mass spectrometry (MALDI-TOF-MS) analysis of PCL samples prepared using **3** showed only one series, which was identified as PCL with ethoxy end groups (Fig. 2D). The identity of the end groups is further evidenced in the ^1H NMR spectrum for purified PCL samples prepared using **3** (Fig. S12†), which gives signals of requisite integration as a quartet (4.20 ppm) and a triplet (1.32 ppm). These signals are consistent with reported spectra for PCL produced with metal ethoxide initiators.^{32,33} Considering the first-order reaction kinetics, narrow molecular weight distribution, and observed end group fidelity, we

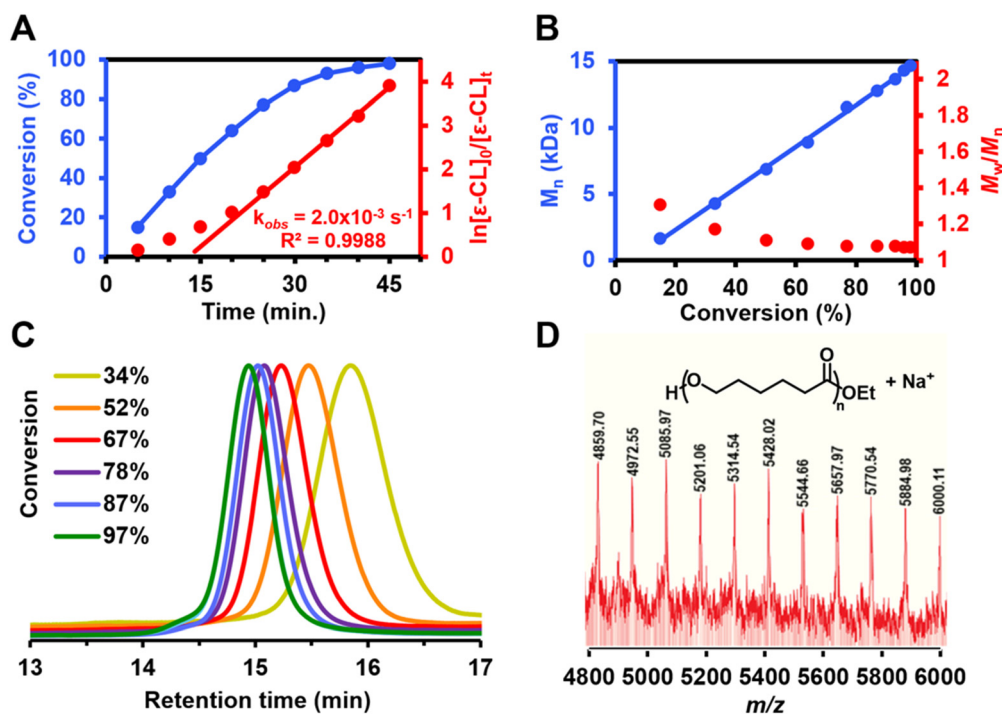


Fig. 2 (A) Kinetic plots for polymerization of ϵ -caprolactone (CL) using **3** as initiator ([initiator]:[CL] = 1:100, [M] = 0.075 M in benzene). (B) Molecular weight ($M_{n,SEC}$) and dispersity correlation with CL conversion for polycaprolactone (PCL) synthesized using **3**. (C) SEC traces for PCL synthesized using **3** at different CL conversions. (D) MALDI-TOF mass spectrum of PCL synthesized using **3**.

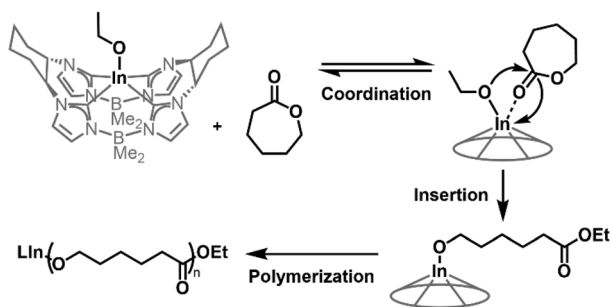


Fig. 3 Proposed coordination–insertion mechanism for CL ROP promoted by **3**.

propose an ethoxy-initiated coordination–insertion mechanism for CL ROP with **3** as initiator (Fig. 3).^{32,33}

Conclusions

We have synthesized two C_2 -symmetric indium complexes that are supported by chiral macrocyclic tetracarbenes. These complexes were characterized by multinuclear NMR, HRMS, and SCXRD. Switching from a bromide to an ethoxide axial ligand enabled living polymerization of ϵ -caprolactone at room temperature with preserved ethoxy end groups. These results highlight a new platform for indium catalysis that is not based on salen/half-salen derivatives for CL ROP, but instead on NHCs as supporting ligands. This study increases the diversity of ligand structures that can be used to support In-catalysed CL polymerisation. Future research will focus on developing other cyclic ester polymerizations that take advantage of the chiral pocket on these main group complexes.

Author contributions

H. R. B. synthesized the ligands and indium complexes and conducted polymerization reactions. H. R. B. conducted NMR studies on all molecules, including kinetic studies on polymers, and SCXRD analysis for **3**. R. C. conducted polymer characterization including SEC measurements and MALDI-TOF MS. G. S. N. conducted SCXRD analysis for **2**. J. A. G. and D. M. J. designed and supervised the project. The manuscript was written by H. R. B. and D. M. J. with additional editing provided by R. C. and J. A. G.

Data availability

The data supporting this article have been included as part of the ESI.†

Conflicts of interest

There are no conflicts to declare.

Acknowledgements

H. R. B. and D. M. J. thank the National Science Foundation (NSF CHE-2154697) for support. Any opinions, findings, and conclusions expressed in this material are those of the authors and do not necessarily reflect the views of the National Science Foundation. R. C. and J. A. G. gratefully acknowledge the EPSRC (EP/V049003/1 and EP/X028208/1), and J. A. G. also thanks the UKRI Future Leaders Fellowship (MR/T042710/1) and the Royal Society (Royal Society (RSG\R1\180101)).

References

- G. G. Zámbo, J. F. Schlagintweit, R. M. Reich and F. E. Kühn, *Catal. Sci. Technol.*, 2022, **12**, 4940–4961.
- C. Romain, S. Bellemin-Laponnaz and S. Dagorne, *Coord. Chem. Rev.*, 2020, **422**, 213411.
- V. Nesterov, D. Reiter, P. Bag, P. Frisch, R. Holzner, A. Porzelt and S. Inoue, *Chem. Rev.*, 2018, **118**, 9678–9842.
- S. Goswami, P. Mandal, S. Sarkar, M. Mukherjee, S. Pal, D. Mallick and D. Mukherjee, *Dalton Trans.*, 2024, **53**, 1346–1354.
- I. Jain and P. Malik, *Eur. Polym. J.*, 2021, **150**, 110412.
- N. Yuntawattana, T. M. McGuire, C. B. Durr, A. Buchard and C. K. Williams, *Catal. Sci. Technol.*, 2020, **10**, 7226–7239.
- C. Fliedel, G. Schnee, T. Avilés and S. Dagorne, *Coord. Chem. Rev.*, 2014, **275**, 63–86.
- A. Neshat, P. Mastroianni and A. Mousavizadeh Mobarakeh, *Molecules*, 2022, **27**, 95.
- P. L. Arnold and A. C. Scarisbrick, *Organometallics*, 2004, **23**, 2519–2521.
- P. Horeglad, O. Ablialimov, G. Szczepaniak, A. M. Dabrowska, M. Dranka and J. Zachara, *Organometallics*, 2014, **33**, 100–111.
- S. A. Cramer, F. L. Sturgill, P. P. Chandrachud and D. M. Jenkins, *Dalton Trans.*, 2014, **43**, 7687–7690.
- L. P. Ho, L. Anders and M. Tamm, *Chem.–Asian J.*, 2020, **15**, 845–851.
- J.-F. Zhao, H.-Y. Tsui, P.-J. Wu, J. Lu and T.-P. Loh, *J. Am. Chem. Soc.*, 2008, **130**, 16492–16493.
- M. Yoshimatsu, H. Goto, R. Saito, K. Iguchi, M. Kikuchi, H. Wasada and Y. Sawada, *Commun. Chem.*, 2023, **6**, 279.
- A. Da Lama, J. Pérez Sestelo, L. A. Sarandeses and M. M. Martínez, *J. Org. Chem.*, 2024, **89**, 16015–16021.
- E. Fazekas, P. A. Lowy, M. Abdul Rahman, A. Lykkeberg, Y. Zhou, R. Chambenahalli and J. A. Garden, *Chem. Soc. Rev.*, 2022, **51**, 8793–8814.
- J. Gao, D. Zhu, W. Zhang, G. A. Solan, Y. Ma and W.-H. Sun, *Inorg. Chem. Front.*, 2019, **6**, 2619–2652.
- D. Myers, A. J. P. White, C. M. Forsyth, M. Bown and C. K. Williams, *Angew. Chem., Int. Ed.*, 2017, **56**, 5277–5282.
- J. Bruckmoser, D. Henschel, S. Vagin and B. Rieger, *Catal. Sci. Technol.*, 2022, **12**, 3295–3302.

- 20 M. Normand, V. Dorcet, E. Kirillov and J.-F. Carpentier, *Organometallics*, 2013, **32**, 1694–1709.
- 21 S. Dagonne, M. Normand, E. Kirillov and J.-F. Carpentier, *Coord. Chem. Rev.*, 2013, **257**, 1869–1886.
- 22 C. Goonesinghe, H.-J. Jung, H. Roshandel, C. Diaz, H. A. Baalbaki, K. Nyamayaro, M. Ezhova, K. Hosseini and P. Mehrkhodavandi, *ACS Catal.*, 2022, **12**, 7677–7686.
- 23 H.-J. Jung, K. Nyamayaro, H. A. Baalbaki, C. Goonesinghe and P. Mehrkhodavandi, *Inorg. Chem.*, 2023, **62**, 1968–1977.
- 24 I. Yu, A. Acosta-Ramírez and P. Mehrkhodavandi, *J. Am. Chem. Soc.*, 2012, **134**, 12758–12773.
- 25 J. F. DeJesus, R. W. Kerr, D. A. Penchoff, X. B. Carroll, C. C. Peterson, P. L. Arnold and D. M. Jenkins, *Chem. Sci.*, 2021, **12**, 7882–7887.
- 26 M. R. Anneser, G. R. Elpitiya, J. Townsend, E. J. Johnson, X. B. Powers, J. F. DeJesus, K. D. Vogiatzis and D. M. Jenkins, *Angew. Chem.*, 2019, **131**, 8199–8202.
- 27 P. P. Chandrachud, H. M. Bass and D. M. Jenkins, *Organometallics*, 2016, **35**, 1652–1657.
- 28 J. F. DeJesus and D. M. Jenkins, *Chem. – Eur. J.*, 2020, **26**, 1429–1435.
- 29 M. R. Anneser, G. R. Elpitiya, X. B. Powers and D. M. Jenkins, *Organometallics*, 2019, **38**, 981–987.
- 30 D. C. Aluthge, J. M. Ahn and P. Mehrkhodavandi, *Chem. Sci.*, 2015, **6**, 5284–5292.
- 31 J. W. J. Hughes, D. J. Babula, F. Stowers-Veitch, K. Yuan, M. Uzelac, G. S. Nichol, M. J. Ingleson and J. A. Garden, *Dalton Trans.*, 2023, **52**, 17767–17775.
- 32 F. Peprah, G. E. Tarantola, A. S. Plaman, E. L. Vu, A. B. Huynh and C. B. Durr, *Dalton Trans.*, 2024, **53**, 7073–7080.
- 33 A. Buchard, M. G. Davidson, G. Gobius du Sart, M. D. Jones, G. Kociok-Köhn, S. N. McCormick and P. McKeown, *Inorg. Chem.*, 2023, **62**, 15688–15699.