

# Dalton Transactions

An international journal of inorganic chemistry

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: E. Topic, J. Sarjanovi, D. Musija, M. Mandari, A. Cocut, T. Hrenar, D. Agustin, J. Pisk and V. Vrdoljak, *Dalton Trans.*, 2025, DOI: 10.1039/D5DT00105F.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

## ARTICLE

# Influence of ancillary ligands on the formation and functionality of oxovanadium(V) metallocsupramolecular assemblies: advanced computational and catalytic analysis

Edi Topić,<sup>a</sup> Josipa Sarjanović,<sup>a</sup> Danijela Musija,<sup>b</sup> Mirna Mandarić,<sup>a</sup> Andrea Cocut,<sup>a</sup> Tomica Hrenar,<sup>a</sup> Dominique Agustin,<sup>c,d</sup> Jana Pisk,<sup>\*a</sup> and Višnja Vrdoljak<sup>\*a</sup>

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Coordination-driven self-assembly approach offers opportunity for designing metallocsupramolecular architectures with tailored properties. Applying this strategy, we present the synthesis and detailed characterization of tetranuclear and polynuclear vanadium(V) compounds with an aroylhydrazone ligand. These assemblies were obtained using the 3-methoxy-2-hydroxybenzaldehyde isonicotinoyl hydrazone ligand (H<sub>2</sub>VIH) and NH<sub>4</sub>VO<sub>3</sub> in presence of primary aliphatic alcohols of increasing carbon chain length (from one to five carbon atoms). Reactions in lower alcohols selectively yielded metallocyclic compounds [VO(VIH)(OR)]<sub>4</sub> (**1**, **2**, and **3**, where R = CH<sub>3</sub>, C<sub>2</sub>H<sub>5</sub>, and C<sub>3</sub>H<sub>7</sub>, respectively), while reactions in higher alcohols afforded infinite zig-zag chain polymers [VO(VIH)(OR)]<sub>n</sub> (**4** and **5**, where R = C<sub>4</sub>H<sub>9</sub> and C<sub>5</sub>H<sub>11</sub>, respectively). Their formation was studied experimentally and computationally. Quantum chemical calculations using density functional theory provided valuable insights into the stability of both cyclic and chain assemblies. The solid-state structures of **1–5** and pseudopolymorphs of [VO<sub>2</sub>(HVIH)] (**6-0.5H<sub>2</sub>O-0.5CH<sub>3</sub>OH** and **6-2H<sub>2</sub>O**) were confirmed using single-crystal and powder X-ray diffraction methods. The oxovanadium(V) species were tested as catalysts for cyclooctene and benzyl alcohol oxidation, with results correlated to those for analogous molybdenum complexes [MoO<sub>2</sub>(VIH)]<sub>4</sub> (**7**) and [MoO<sub>2</sub>(VIH)(C<sub>2</sub>H<sub>5</sub>OH)] (**8**). The influence of the metal centre, nuclearity, and ancillary ligand identity on catalytic performance was also investigated, revealing that the vanadium metal center influences the catalytic activity due to its capacity to form robust structures.

## Introduction

Transition metal oxo complexes in high oxidation states, particularly those of Group 5 and 6, play significant roles in various chemical and biological processes. Complexes containing V<sup>IV,V</sup>,<sup>1-7</sup> Mo<sup>VI</sup>,<sup>8-11</sup> and W<sup>VI</sup>,<sup>12-14</sup> are commonly used as (pre)catalysts in oxidation reactions with oxidants such as O<sub>2</sub>, H<sub>2</sub>O<sub>2</sub>, or *tert*-butyl hydroperoxide (TBHP). Notably, related discrete metal complexes can feature multiple coordination pockets which further enhance their catalytic versatility.<sup>15-17</sup>

Alternatively, {Mo<sup>VI</sup>O<sub>2</sub>}<sup>2+</sup> metallocsupramolecular complexes are gaining attention for their effectiveness as epoxidation catalysts.<sup>18-22</sup> Metal-organic frameworks STA-12(Co), STA-12(Ni), and STA12(Ni+20% Co) effectively catalyse the oxidation of benzylic alcohols.<sup>23</sup> Zn-based MOF (ZIF-8), and its Co(II)- and Cu(II)-modified assemblies, also showed good catalytic activity.<sup>24</sup> Moreover, an Fe(phthalocyanine) complex demonstrated high effectiveness for alcohol oxidation using TBHP and H<sub>2</sub>O<sub>2</sub> without organic solvents.<sup>25</sup>

However, reports on oxovanadium(V) metallocsupramolecular architectures, involving polydentate organic ligands and {VO}<sup>3+</sup> units remain relatively rare. The complex [VO<sub>2</sub>(2,2'-bpy)]<sub>2</sub>(tp)<sub>n</sub> is the first 1D vanadium(V) coordination polymer containing bipyridine and terephthalate ligands.<sup>26</sup> Rare examples of V<sup>IV</sup>O assemblies include the cyclic complex [VO(3HPA)]<sub>4</sub> (3HPA = 3-hydroxypicolinic acid), and coordination polymers [VO(dod)<sub>2</sub>]<sub>2</sub>X<sub>2</sub> (dod=1,4-diazoniabicyclo[2,2,2] octane-1-4-diacetate).<sup>27,28</sup> A compelling example is interconvertible vanadium-seamed hexameric pyrogallol[4]arene nanocapsules.<sup>29</sup> To the best of our knowledge, oxovanadium(V) complexes with isonicotinoyl or nicotinoyl moiety represent rare examples where the hydrazone ligand coordinates two metal centres to form a polymer.<sup>30-32</sup>

<sup>a</sup> University of Zagreb, Faculty of Science, Department of Chemistry, Horvatovac 102a, 10000 Zagreb, Croatia; E-mail: jana.pisk@chem.pmf.hr, visnja.vrdoljak@chem.pmf.hr

<sup>b</sup> University of Zagreb, School of Medicine, Department of Chemistry and Biochemistry, Šalata 3, 10000 Zagreb, Croatia.

<sup>c</sup> LCC-CNRS (Laboratoire de Chimie de Coordination), 205 Route de Narbonne, BP44099, CEDEX 4, 31077 Toulouse, France

<sup>d</sup> Department of Chemistry, IUT Paul Sabatier, Université Paul Sabatier, University of Toulouse, Av. G. Pompidou, CS20258, 81104 Castres, France


† Electronic Supplementary Information (ESI) available: (1) powder diffraction patterns, (2) additional figures for compounds, (3) tables of selected bond distances and angles and of hydrogen bonds parameter, (4) UV-Vis spectra, (5) NMR spectra ATR-IR spectra, (6) TGA curves, (7) Crystallographic data sets for the structures **1–5**, **6-0.5H<sub>2</sub>O-0.5CH<sub>3</sub>OH**, **6-2H<sub>2</sub>O**, and **8** are available through the Cambridge Structural Data base with deposition numbers CCDC 2335829–2335837, 2400624. For ESI and crystallographic data in CIF format see DOI: 10.1039/x0xx00000x



A coordination-driven self-assembly method is a powerful tool for developing metallosupramolecular architectures.<sup>33-37</sup> The assembly outcomes are influenced by a variety of factors, including the metal ion's coordination geometry, ligands' denticity spacer unit flexibility, and donor atom positions.<sup>38,39</sup> The process involves reversible metal-ligand bond formation and cleavage,<sup>40,41</sup> resulting in diverse supramolecular isomers, from discrete entities to complex networks. Structures that maximize metal-ligand bonding interactions typically have increased enthalpy, while smaller assemblies may benefit from entropic effects,<sup>42-45</sup> allowing for the design of functional materials with tailored properties.

Building on our prior research,<sup>21,22,46-49</sup> we aimed to develop vanadium-based assemblies utilizing coordination-driven self-assembly method. We selected 3-methoxy-2-hydroxybenzaldehyde isonicotinoyl hydrazone (H<sub>2</sub>VIH, Scheme 1) to link vanadium mononuclear building units into higher dimensional structures. We aimed to determine whether primary alcohols ROH (C<sub>n</sub>H<sub>2n+1</sub>OH, n = 1–5) could facilitate the assembly of specific supramolecular structure. We conducted quantum chemical calculations to evaluate the stability of cyclic tetramer complexes and compared them to chain configurations. By examining their unique structural properties and interactions, we aimed to uncover their potential applications in various fields, including catalysis.

The preliminary evaluations of their catalytic potential were conducted through two oxidation reactions: cyclooctene epoxidation and benzyl alcohol oxidation. The production of epoxides is crucial in industry, especially in production of plastics, adhesives and coatings, highlighting their significance in a variety of applications.<sup>50,51</sup> On the other hand, benzaldehyde, utilized in fragrances and pharmaceuticals<sup>52,53</sup> is often produced through conventional synthesis methods that tend to generate harmful by-products.<sup>54,55</sup> Therefore, exploring more sustainable synthesis pathways is essential for minimizing environmental impact while meeting industrial needs.

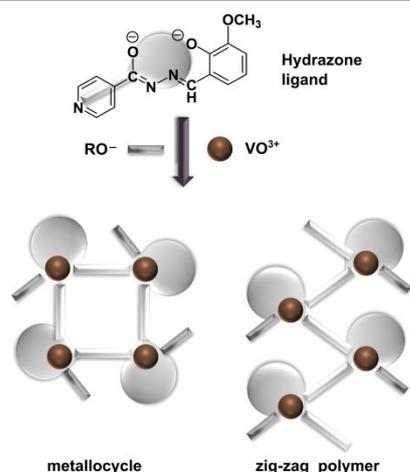

**Scheme 1** A schematic presentation of doubly deprotonated ligand  $\text{VIH}^{2-}$ , ancillary ligand  $\text{OR}^-$ , and metallosupramolecular assemblies  $[\text{VO}(\text{VIH})(\text{OR})]_4$  (**1**, **2**, and **3**, where  $\text{R} = \text{CH}_3$ ,  $\text{C}_2\text{H}_5$ , and  $\text{C}_3\text{H}_7$ , respectively) and  $[\text{VO}(\text{VIH})(\text{OR})]_n$  (**4** and **5**, where  $\text{R} = \text{C}_4\text{H}_9$  and  $\text{C}_5\text{H}_{11}$ , respectively).

## Results and discussion

View Article Online

DOI: 10.1039/D5DT00105F


### Metallosupramolecular assemblies

We have previously reported the synthesis of the 3-methoxy-2-hydroxybenzaldehyde isonicotinoyl hydrazone (H<sub>2</sub>VIH) as part of our work on a series of aroylhydrazones.<sup>56</sup> Refluxing a slight excess of H<sub>2</sub>VIH with one equivalent of  $\text{NH}_4\text{VO}_3$  in the corresponding alcohol (C<sub>n</sub>H<sub>2n+1</sub>OH, n = 1–5) led to the isolation of dark red, almost black crystalline solids. These coordination assemblies were characterized by X-ray crystallography along with spectral and analytical methods. They were identified as metallosupramolecular tetranuclear  $[\text{VO}(\text{VIH})(\text{OR})]_4$  (**1**, **2**, and **3**, where  $\text{R} = \text{CH}_3$ ,  $\text{C}_2\text{H}_5$ , and  $\text{C}_3\text{H}_7$ , respectively) and polymeric products  $[\text{VO}(\text{VIH})(\text{OR})]_n$  (**4** and **5**, where  $\text{R} = \text{C}_4\text{H}_9$  and  $\text{C}_5\text{H}_{11}$ , respectively), Scheme 1.

The three tetranuclear complexes **1**, **2**, and **3** crystallize in the tetragonal space group  $I4_1/a$  and exhibit remarkably similar crystal structures, as evidenced by powder patterns (see ESI<sup>†</sup>, Fig. S1) as well as the obtained structural model (Fig. 1a1, Table S1, Fig. S2a-c, see ESI<sup>†</sup>). Crystal structure of **2** has been reported previously (refcode: CAZVIM).<sup>57</sup> Each tetranuclear unit in these compounds consists of four  $[\text{VO}(\text{VIH})]$  monomers linked through oxovanadium-pyridyl  $\text{V}-\text{N}_{\text{py}}$  coordination bonds, which are oriented approximately perpendicular to the chelation plane. This arrangement yields a robust metallocycle, representing a unique structure among the oxovanadium(V) compounds.

In contrast, compounds **4** and **5**, which feature disordered *n*-butoxy and *n*-pentoxy ancillary ligands, assemble differently. These compounds crystallize in orthorhombic  $Pca2_1$  space group, and form isostructural 1D coordination polymers (Fig. 1b1, Table S2, Fig. S2d-e, see ESI<sup>†</sup>), albeit with similar overall geometry and connectivity to observed metallocycles – differing only by the relative orientation of the neighbouring monomers. The chains can be described with ubiquitous 2C1 topology, *i.e.* 2-node one-dimensional periodic net (Fig. 1b2).<sup>58</sup> Among the tetranuclear complexes, complex **1** is particularly noteworthy due to its significant porosity (Fig. 1a2, Fig. S3, see ESI<sup>†</sup>). The spherical probe pore volume is approximately 30 Å<sup>3</sup> per monomer unit, corresponding to about 9.2% of the unit cell volume.<sup>59</sup> This substantial pore space within the methoxy complex suggests a possible potential for guest inclusion or adsorption, although the nature of included chemical species in the measured crystal could not be conclusively determined from the diffraction data. This pore volume contrasts with the more compact structures observed in compounds **2–5**, which lack notable porosity, indicating that the smallest alkoxy ligand uniquely supports this open framework structure. Alongside, an interesting trend is noticed when observing monomer volumes and pore volumes for the whole series – while monomer volumes increased approximately linearly with the number of carbon atoms in the ancillary ligand, the pore volume decreased exponentially (Fig. 1d).



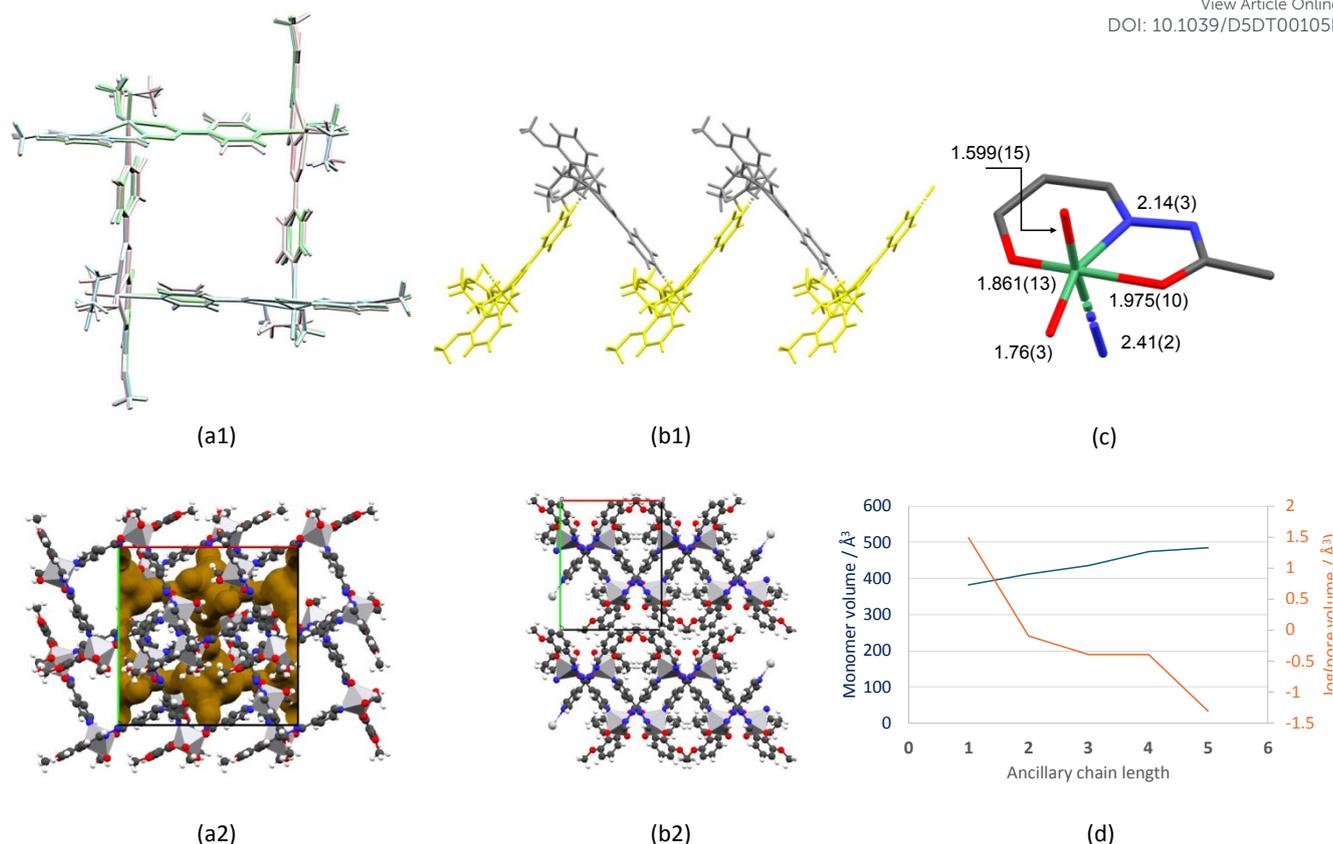

**Fig. 1** a1) Structure overlay of tetranuclear  $[\text{VO}(\text{VIH})(\text{OR})]_4$  species **1** (light green), **2** (light red) and **3** (light blue). a2) Packing of tetramers in **1**, showing significant crystal voids. b1) Infinite polymeric chains found in **4**. b2) Packing of infinite polymeric chains of **4**. c) Coordination environment of vanadium(V) core with mean and standard deviations of relevant bond lengths across compounds **1–5**. d) Monomer volume and logarithm of spherical probe pore volume per monomer across in relation to ancillary chain length for compounds **1–5**. Packing of molecules/polymeric chains in (a) **1**, (b) **4**, shown in polyhedral style. Voids in **1** are represented by the yellow surface.

The relevant metal–ligand distances in the oxovanadium core (Fig. S4, see ESI<sup>†</sup>) remain fairly consistent regardless of the selected ancillary ligand (Fig. 1c), with bond lengths varying by only a few percent from the mean values, reflecting the well-known robustness of the *ONO* coordination environment of the doubly deprotonated ligand in enolato-imino tautomeric form (Fig. S5, see ESI<sup>†</sup>). However, in the tetranuclear complex **1**, two specific deviations stand out: the vanadium–methoxy oxygen bond distance is notably shorter than in the other compounds, while the vanadium–hydrazonato nitrogen bond distance is elongated. One factor that appears to be correlated with formation of discrete over polymeric compounds is the torsion angle between the pyridyl and aryl rings of the  $\text{VIH}^{2-}$  ligand. For complexes **1**, **2**, and **3**, the interring torsion angles are  $9^\circ$ ,  $24^\circ$ , and  $14^\circ$ , respectively, suggesting a relatively small degree of distortion that enables the formation of compact, closed assembly. In contrast, the polymers **4** and **5** exhibit significantly larger interring torsion angles of approximately  $44^\circ$  and  $40^\circ$ . This increased torsional angle, probably mediated by the bulk of the ancillary ligand, might favour an open chain-like polymeric structure.

Regarding intermolecular interactions, no significant hydrogen bonding is observed within these structures – all potential hydrogen bond donors are lost through ligand deprotonation and coordination. However, numerous  $\text{C–H}\cdots\text{O}$  contacts are

observed throughout the crystal structures, particularly in the 1D polymers, where these contacts contribute to stabilize the extended framework.


**Quantum chemical calculations.** To further understand the factors that lead to the formation of distinct assemblies, extensive quantum chemical calculations were performed. To analyze the stability of tetramer complexes, experimental structures from **1**, **2** and **3** were taken and geometry optimizations together with harmonic frequency calculations were performed. For complexes with butoxy and pentoxy groups where there are no appropriate experimental structures, equivalent geometries were created and calculations were performed. The standard Gibbs binding energies for tetramer models were calculated as a difference from tetramer energy to 4 monomer energies where in monomer the last binding place was filled up with a pyridine molecule.

$$\Delta_b G^\circ(\text{tetramer}) = \Delta_f G^\circ(\text{tetramer}) - 4\Delta_f G^\circ(\text{monomer,py}) + 4\Delta_f G^\circ(\text{py})$$



**Table 1** Standard Gibbs binding energies for tetramer models calculated at the B3LYP-D3BJ/6-311++G(d,p) level of the theory

Ligand	$\Delta_b G^\circ$ (tetramer) / kJ mol <sup>-1</sup>
OCH <sub>3</sub>	-20.36
OC <sub>2</sub> H <sub>5</sub>	-23.24
OC <sub>3</sub> H <sub>7</sub>	-24.78
OC <sub>4</sub> H <sub>9</sub>	-32.97
OC <sub>5</sub> H <sub>11</sub>	-31.29

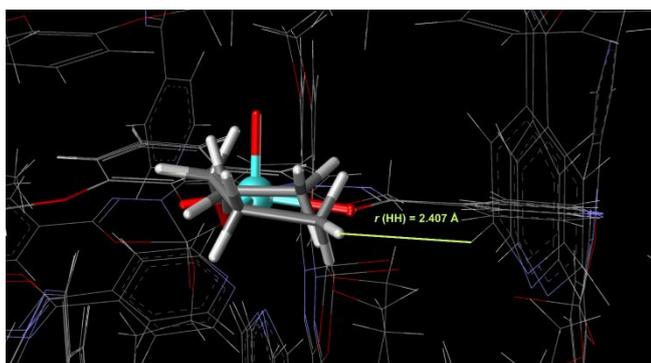**Fig. 2** Overlaid crystal structures of **1**, **2**, and **3** where the distance from the hydrogen atom of the propyl group to the nearest atom is highlighted. Extension in the alkoxy group with an additional methylene –CH<sub>2</sub>– group in the same configuration is impossible due to the steric repulsions.

According to the calculated standard Gibbs energies of binding (in Table 1), tetramers for all structures should exist. But, besides electronic effects, steric effects of packing should also be considered. The overlay of crystal structures for **1**, **2**, and **3** is presented in Fig. 2. It is clear that the smallest distance between hydrogen atoms in the crystal structure of **3** is 2.407 Å. The addition of another methylene –CH<sub>2</sub>– group would cause steric repulsion, confirming that steric reasons are the most important for the crystal packing.

Stability was also cross-checked according to the chain polymer models. For each ligand, a chain tetramer model where the last binding place was filled up with a pyridine molecule was created. The difference in standard Gibbs energies of tetramer formation  $\Delta\Delta_f G^\circ$  (cyclic – chain) was calculated as

$$\Delta\Delta_f G^\circ (\text{cyclic} - \text{chain}) = \Delta_f G^\circ (\text{cyclic}) - \Delta_f G^\circ (\text{chain}) + \Delta_f G^\circ (\text{py})$$

**Table 2** Difference in standard Gibbs energies of tetramer cyclic vs chain formation  $\Delta\Delta_f G^\circ$  (cyclic – chain) calculated at the B3LYP-D3BJ/6-311++G(d,p) level of the theory

Ligand	$\Delta\Delta_f G^\circ$ (cyclic – chain) / kJ mol <sup>-1</sup>
OCH <sub>3</sub>	-35.23
OC <sub>2</sub> H <sub>5</sub>	-29.55
OC <sub>3</sub> H <sub>7</sub>	-26.35
OC <sub>4</sub> H <sub>9</sub>	-46.62
OC <sub>5</sub> H <sub>11</sub>	-35.78

Corresponding differences in standard Gibbs energies of tetramer formation are presented in Table 2. In each case, the cyclic tetramer structures were lower in energy reflecting the fact that cyclic tetrameric structures with all ligands should exist. Therefore, the only possible explanation for different crystal packing remains steric reasons.

### Mononuclear complexes

The reaction carried out in methanol at room temperature produced a dark-coloured solution after two weeks. Evaporation of the solution in an airstream yielded orange crystals of [VO<sub>2</sub>(HVIH)]·0.5H<sub>2</sub>O·0.5CH<sub>3</sub>OH (**6·0.5H<sub>2</sub>O·0.5CH<sub>3</sub>OH**). Upon prolonged exposure of the filtrate to air, a few crystals of [VO<sub>2</sub>(HVIH)]·2H<sub>2</sub>O (**6·2H<sub>2</sub>O**) also formed.

The two pseudopolymorphs were characterized by SCXRD (ESI, Table S3, Fig. S1f-g). The dihydrate **6·2H<sub>2</sub>O** crystallizes in *P*1 space group forming an intriguing supramolecular chain mediated by V=O···water···water···N<sub>py</sub> hydrogen bonds (ESI, Fig. S6). On the other hand, hemihydrate hemimethanolate **6·0.5H<sub>2</sub>O·0.5CH<sub>3</sub>OH** crystallizes in the monoclinic space group *Cc* with four symmetrically inequivalent molecules of [VO<sub>2</sub>(HVIH)] in the asymmetric unit. The relative orientation and difference density map between the neighbouring pyridyl fragments suggest partial protonation of the pyridyl moieties, forming a hydrogen bond between the pairs of neighbouring [VO<sub>2</sub>(HVIH)] molecules. Although the structure of solvent molecules could not be determined satisfactorily, electron density of refined solvent mask suggests the aforementioned composition. More precise conclusions about the nature of hydrogen bonding in the **6·0.5H<sub>2</sub>O·0.5CH<sub>3</sub>OH** would require a structural probe more sensitive to hydrogen atom position. However, the molecular structures of the complexes are in line with the expectations – {VO<sub>2</sub>}<sup>+</sup> core coordinated by *ONO* chelating pocket of a deprotonated ligand, in an enolato-imino form (Fig. S5, see ESI<sup>†</sup>).


### Molybdenum(VI) assemblies

For comparison purpose in the catalytic part of this research, we prepared molybdenum complexes [MoO<sub>2</sub>(VIH)]<sub>4</sub> (**7**) and [MoO<sub>2</sub>(VIH)(C<sub>2</sub>H<sub>5</sub>OH)] (**8**), known from our previous study.<sup>46</sup> The crystal structure of [MoO<sub>2</sub>(VIH)(C<sub>2</sub>H<sub>5</sub>OH)] (**8**), not reported previously, has been described in short in ESI (Fig. S6, see ESI<sup>†</sup>).

### Principal component analysis

Next, we focused on gaining a deeper understanding of this reaction system. The reaction between NH<sub>4</sub>VO<sub>3</sub> and H<sub>2</sub>VIH (with the initial concentrations of the reactants being 4.0×10<sup>-5</sup> mol dm<sup>-3</sup>) was studied in methanol at room temperature by time-dependent UV-Vis spectrophotometry.



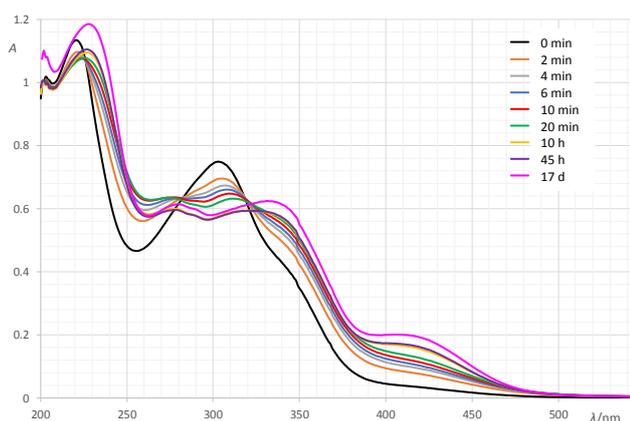

**Fig. 3** Time-dependent UV-Vis spectra of a reaction mixture of  $\text{NH}_4\text{VO}_3$  and  $\text{H}_2\text{VIH}$  in methanol at room temperature.

Time-dependent UV-Vis spectra (Fig. 3) were decomposed using the 2<sup>nd</sup>-order tensor decomposition tool principal component analysis. The obtained results showed that the original dataset (389 spectra) could be correctly represented using only 2 principal components. These two components described 98% of the variance in the original data. The first principal component was responsible for 74.04% of the total variance and describes a major reaction involving the coordination of the hydrazone ligand to vanadium. The second component describes 23.88% of the total variance and represents a secondary reaction in the system (Fig. 4). The analysis of the UV-Vis spectra of the V-hydrazone complex (Fig. S7, see ESI<sup>†</sup>) revealed a final transformation of the initially formed hydrazone complex into the corresponding dioxovanadium(V) species in the very diluted  $\text{CH}_3\text{OH}$  solutions.

### Spectroscopic characterization


**UV-Vis spectra.** The UV-Vis spectra of  $\text{H}_2\text{VIH}$  and complexes **1–8** were recorded in both methanol and acetonitrile (Fig. S8–S10, see ESI<sup>†</sup>). The spectral data ( $\lambda_{\text{max}}$  and  $\epsilon$ ) are given in Table S5, see ESI<sup>†</sup>. In methanol,  $\text{H}_2\text{VIH}$  gives absorption maxima at 221 nm, 304 nm and a shoulder around 342 nm that are ascribed to transitions  $\pi \rightarrow \pi^*$  of the aromatic rings,  $\pi \rightarrow \pi^*$  and  $n \rightarrow \pi^*$  of the azomethine and carbonyl moieties, respectively.<sup>60,61</sup> In the spectra of complexes **1–8** these absorption bands are red-shifted, indicating enolization and deprotonation of hydrazone ligand.<sup>60</sup> For example, in the spectrum of methanolic solution of **1**, they are present at 231 and 315 nm with the shoulder at

approximately 340 nm and attributed to intraligand  $\pi \rightarrow \pi^*$  and  $n \rightarrow \pi^*$  transitions, respectively.<sup>6,60,61</sup> Two additional bands appearing in the spectrum at 425 nm and 272 nm are assigned to ligand-to-metal charge-transfer (LMCT) transitions. The band at 425 nm can be attributed to charge transfer from the coordinated hydrazone ligand to vanadium(V) while the character of the band at 272 nm is mainly LMCT for coordinated hydrazone, methoxy and oxo ligands and to some extent  $\pi \rightarrow \pi^*$  of hydrazone ligand.<sup>6,60,62</sup>

In the UV-Vis spectrum of methanolic solution of **7**, the intraligand  $\pi \rightarrow \pi^*$  transitions are observed at 225 nm and 317 nm and  $n \rightarrow \pi^*$  at 365 nm, while the bands appearing at 280 nm and 420 nm can be assigned to LMCT transitions.<sup>6,63</sup>

**NMR spectra.** The complexes are diamagnetic, and the NMR spectra in  $\text{CD}_3\text{OD}$  show the expected signals for the  $\text{VIH}^{2-}$  ligand.  $^1\text{H}$  and  $^{13}\text{C}$  NMR chemical shifts of  $\text{H}_2\text{VIH}$ ,  $[\text{VO}(\text{VIH})(\text{OCH}_3)]_4$ , and  $[\text{MoO}_2(\text{VIH})]_4$  (Table S6, Scheme S1, Fig. S11–S14, see ESI<sup>†</sup>) are assigned by  $^1\text{H}$ , APT, HMQC, and HMBC NMR experiments in  $\text{CD}_3\text{OD}$ . Due to the very low solubility of samples, the quaternary carbon signals were detected in some cases from the well-resolved cross peaks in 2D spectra. Complexes **1–5** display similar spectra, suggesting complete  $\text{RO}^-$  alkoxo ligand exchange in  $\text{CD}_3\text{OD}$  solution. Signals belonging to the corresponding alcohol were also detected in  $^1\text{H}$  NMR spectra of complexes **1–5**. Table S6 therefore lists the  $^1\text{H}$  and  $^{13}\text{C}$  NMR data for  $[\text{VO}(\text{VIH})(\text{OCH}_3)]_4$ . Singlets at 8.83 ppm and 3.92 ppm are assigned to  $\text{CH}=\text{N}$  and  $\text{OCH}_3$  groups, respectively. The signals at 8.07 ppm and 8.68 ppm are due to isonicotinoyl protons (H6, H10 and H7, H9, respectively), whereas those in the range 7.26–6.91 ppm are assigned to aromatic ring protons. The most significant coordination-induced difference between signals is noticed for imine  $\text{CH}=\text{N}$ , up to 0.18 ppm. A similar observation was also noted in the spectrum of the molybdenum complexes, showing greater differences in chemical shifts (up to 0.27 ppm for imine  $\text{CH}=\text{N}$ ).

In the  $^{13}\text{C}$  NMR spectra, the chemical shifts for C1, C4, and C12 carbons experience deshielding effects up to 4.28 ppm, 6.78 ppm, and 6.84 ppm, respectively. The signals for the isonicotinoyl carbons C5–C10 do not exhibit appreciable change in chemical shifts when compared to those of the free ligand (max  $\Delta\delta = 0.64$  ppm), confirming that the metallosupramolecular nature of complexes found in the crystal structures is not retained in very diluted  $\text{CD}_3\text{OD}$  solutions.

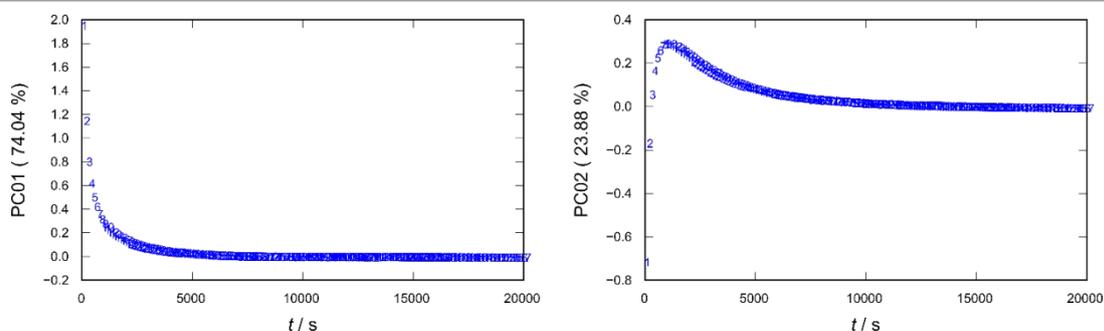

**Fig. 4** Principal component scores for the reaction of  $\text{NH}_4\text{VO}_3$  and  $\text{H}_2\text{VIH}$  in methanol at room temperature monitored in time by UV-Vis spectrophotometry.



Unfortunately, the low solubility of all investigated compounds prevented a detailed NMR analysis in non-coordinated solvents. The  $^1\text{H}$  NMR spectra of the partially dissolved complexes in  $\text{CDCl}_3$  show characteristic resonances for the  $\text{V}-\text{OCH}_3$  or  $\text{V}-\text{OCH}_2$  protons on the alkoxide ligand. They are significantly shifted compared to the signals of the corresponding free alcohols. Specifically, the resonances are at 5.38 ppm for **1**, 5.63 ppm for **2**, 5.58 ppm for **3**, 5.63 ppm for **4**, and 5.62 ppm for **5**.<sup>30</sup> A representative  $^1\text{H}$  NMR spectrum of **3**, partially dissolved in  $\text{CDCl}_3$  after 24 hours, is shown in Fig. S15, see ESI<sup>†</sup>.

**ATR-IR spectra.** In the ATR-IR spectra of the hydrazone, the two bands observed at  $3202\text{ cm}^{-1}$  and  $1688\text{ cm}^{-1}$  respectively correspond to the  $\text{N}-\text{H}$  and  $\text{C}=\text{O}$  stretches.<sup>56</sup> These bands are absent in the spectra of the complexes (Fig. S16, see ESI<sup>†</sup>), suggesting the occurrence of hydrazone tautomerization  $\text{N}-\text{NH}-\text{C}=\text{O} \rightleftharpoons \text{N}=\text{N}-\text{C}-\text{OH}$  and deprotonation. Moreover, the bands belonging to  $\text{C}-\text{O}_{\text{phenolato}}$  (at  $1260\text{ cm}^{-1}$ ),  $\text{C}=\text{N}_{\text{imine}}$  (at  $1615\text{ cm}^{-1}$ ), and  $\text{C}-\text{O}_{\text{hydrazone}}$  (at  $1350\text{ cm}^{-1}$ ) indicate ligand coordination to vanadium through *ONO* donor atoms.<sup>18–20</sup> Weaker intensity bands for  $\text{V}-\text{N}_{\text{imine}}$  at  $780\text{ cm}^{-1}$ ,  $\text{V}-\text{O}_{\text{hydrazone}}$  at  $580\text{ cm}^{-1}$ , and  $\text{V}-\text{O}_{\text{phenolato}}$  at  $570\text{ cm}^{-1}$ , corroborate the *ONO* ligand coordination on the vanadium. The formation of metallosupramolecular assemblies is suggested by the emergence of a new absorption band at  $710\text{ cm}^{-1}$  for the  $\text{V}-\text{N}_{\text{py}}$  bond, which results from the isonicotinoyl nitrogen atom binding on the vanadium-free site of the neighbouring complex. Additionally, the coordination of alkoxide is confirmed by a newly observed band in the range of  $1034\text{--}1064\text{ cm}^{-1}$  for  $\text{C}-\text{O}_{\text{OR}}$ ,<sup>64</sup> as well as a band for  $\text{V}-\text{O}_{\text{OR}}$  at  $590\text{ cm}^{-1}$ . All assignments are supported by high level quantum chemical calculations.

The spectra also show a very intense peak at  $962\text{ cm}^{-1}$  (for **1**, **2**, and **3**) and  $957\text{ cm}^{-1}$  (for **4** and **5**), indicating the presence of  $\{\text{V}=\text{O}\}^{3+}$  core.<sup>65</sup> It is noteworthy that these bands of vanadium(V) complexes are found at higher frequencies compared to those of the corresponding molybdenum(VI) compounds.<sup>18–20</sup> Additionally, the presence of the dioxovanadium(V)  $\text{VO}_2^+$  group is inferred from the band at  $930\text{ cm}^{-1}$  and  $890\text{ cm}^{-1}$  for **6**,<sup>66</sup> which is attributed to  $\text{V}=\text{O}$  stretching.<sup>6,67,68</sup>

### Thermogravimetric analyses

The compounds were thermally analysed in an oxygen stream. The gases that evolved during the analysis were monitored in real time using FT-IR. Fig. S17–S21 (see ESI<sup>†</sup>) present the thermograms of compounds **1** and **5** along with a 3D graphical representation of the TG–FT-IR spectra. The thermograms of crystalline samples revealed a two-step decomposition for compounds **1–5**. The temperature at which the alkoxide oxidation occurs, ( $198\text{ }^\circ\text{C}$  for **1**,  $183\text{ }^\circ\text{C}$  for **2**,  $166\text{ }^\circ\text{C}$  for **3**,  $185\text{ }^\circ\text{C}$  for **4**, and  $162\text{ }^\circ\text{C}$  for **5**), suggests the stability of alkoxide OR ligands which decreases with alkyl chain length in the metallocyclic and polymeric series. The thermograms clearly demonstrate the correlation between the release of gaseous products and the observed mass loss. Gaseous compound

identification was facilitated through a library search based on the obtained FT-IR spectrum. The presence of the corresponding aldehyde was indicated by the main band found at approximately  $1760\text{ cm}^{-1}$ . These results are consistent with theoretical calculations published for the thermal decomposition of vanadium alkoxo complex.<sup>69</sup>

Furthermore, the partial decomposition of formaldehyde in the case of compound **1** was detected, likely due to the gas carrier tube being at  $200\text{ }^\circ\text{C}$ . In the second step, residuals **1\*–5\*** exhibited significant mass loss with decomposition temperatures ranging from  $229\text{ }^\circ\text{C}$  to  $244\text{ }^\circ\text{C}$ . In all the cases, the final residual corresponds well with the formation of  $\text{V}_2\text{O}_5$ .

For **6-0.5CH<sub>3</sub>OH-0.5H<sub>2</sub>O**, the thermal gravity curve displays three distinct steps. The initial two steps indicate the loss of methanol and water (the onset temperatures are  $25\text{ }^\circ\text{C}$  and  $63\text{ }^\circ\text{C}$ , respectively). The most significant mass loss, occurring between  $158\text{ }^\circ\text{C}$  and  $409\text{ }^\circ\text{C}$ , is attributed to the decomposition of hydrazone.

### Catalytic studies

The initial screening of catalytic activity involved vanadium catalysts **1–6** in cyclooctene epoxidation, using TBHP in decane as oxidant. This reaction was selected based on our prior work on epoxidation reactions with tetranuclear molybdenum-based catalysts derived from aroylhydrazones.<sup>18,21</sup> The oxidant choice was supported based on previous investigation with similar vanadium catalysts, prioritising high selectivity and yields towards the desired epoxide, and high catalytic turnover.<sup>49</sup> In this study, the performance of the vanadium catalysts was compared with the molybdenum analogue catalysts **7** and **8**.

As expected, cyclooctene conversion and selectivity towards the corresponding epoxide were higher with TBHP in decane, approximately 10% greater than with TBHP in water. According to the nature of the mixture, water might lower the reactivity since it can compete with TBHP by coordinating the vanadium center, then slowing the oxygen transfer process. Regardless of the oxidant used, the measured parameters for all vanadium catalysts were relatively consistent (Fig. S22, see ESI<sup>†</sup>). Cyclooctene conversion with TBHP in decane ranged from 80% to 85%, being the highest for catalyst **2** and lowest for catalysts **3** and **5**, while in water, it ranged from 76% (catalyst **1**) to 81% (catalyst **4**). Epoxide selectivity with TBHP in decane was between 63 (catalysts **2** and **3**) and 76% (catalyst **6**), compared to 64% (catalyst **2**) to 72% (catalysts **4** and **5**) with TBHP in water. To compare with Mo catalyst **7**, it is obvious that the conversion for **7** is higher either with TBHP in decane (93%) or in water (71%), while the selectivity towards epoxide is around 85% no matter the oxidant used. Catalytic profiles for V catalysts, with TBHP in decane are presented in Fig. S23, see ESI<sup>†</sup>. Catalyst **2** exhibits the slowest conversion to catalytically active species, whereas catalyst **6** converts the fastest, presumably linked to the nature of the coordination between molecular species, as discussed above.

The presented results with the catalyst **6** can be correlated to investigation performed previously, with  $\text{V}^{\text{V}}$  mononuclear compounds obtained by the pyridoxal-based ligands.<sup>49</sup> Given




that the catalyst loading was ten times less in the previous investigation, a corresponding decrease in catalytic performance was anticipated. This is reflected in the observed 31% conversion of cyclooctene and a notably lower epoxide selectivity of 10%. Furthermore, the presented investigation included different mechanistic pathways for the catalyzed oxygen atom transfer to olefins that were systematically investigated using density functional theory (DFT) calculations. Among the examined pathways, two were identified as energetically feasible. Notably, one of these pathways exhibited a lower energy span, corresponding to an H-bond-assisted oxygen transfer mechanism to an external olefin. A similar mechanism has been previously explored in the context of Mo<sup>VI</sup> systems, but its applicability to V<sup>V</sup> systems has not been investigated prior to the published study (Fig. S25, see ESI<sup>†</sup>).

The catalytic potential of vanadium catalysts **1–6** was further investigated towards benzyl alcohol oxidation. The study examined the effect of different oxidizing agents, including TBHP (commercially available in decane or water) and H<sub>2</sub>O<sub>2</sub> (with acetonitrile addition). The use of H<sub>2</sub>O<sub>2</sub> as an oxidant, without addition of acetonitrile, was also explored. However, the results were negligible, with minimal catalytic activity and selectivity towards the desired product observed under these conditions. Due to the lack of significant outcomes, these results are not included in the present study. Reactions using TBHP as oxidant were monitored for 5 hours. In contrast, when H<sub>2</sub>O<sub>2</sub> with MeCN was employed as the oxidant, the reactions were followed for only 50 minutes due to rapid conversion of the aldehyde into benzoic acid, a by-product of the studied reaction. The obtained results are compiled on Figure 5 and Table 3. The comparison of benzyl alcohol conversion and selectivity towards benzaldehyde, as presented in Fig. 5 is discussed at two key time points: 20 minutes from the reaction start and at the end of the reaction. A reaction time of 20 min was chosen because alcohol conversion reaches its peak at this point, then decreases over time, suggesting a subsequent conversion to other by-products of the reaction. The benzyl alcohol conversions using TBHP, whether dissolved in decane or water, exhibit very similar trends. Across all vanadium catalysts (**1–6**), the conversion values exceed 80% at 300 min and approach 60% or more at 20 min of the reaction.

It can be concluded that the water, obtained by decomposition of H<sub>2</sub>O<sub>2</sub>, influences the reaction environment. Increased water

content seems to hinder benzyl alcohol oxidation. On the other side, during the reaction, TBHP decomposes into tert-butanol, an organic solvent, meaning it is less likely to interfere the oxidation reaction and might even act as co-solvent.<sup>21,49</sup>

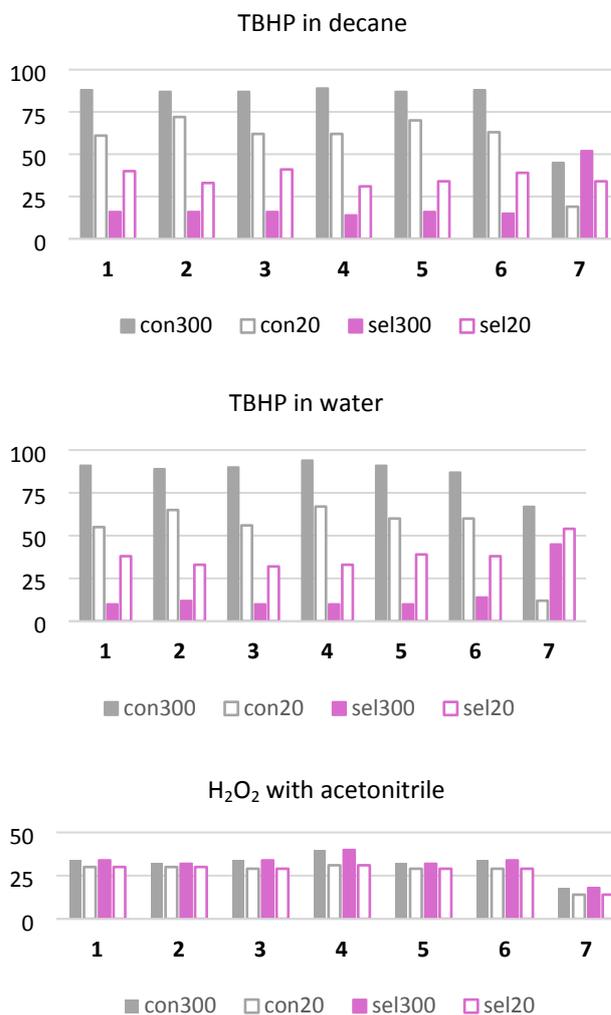

**Fig 5** Comparison of alcohol conversion (grey-edged bar) and aldehyde selectivity (pink-edged bar) after 300 min (full-coloured bar) and 20 min (white-coloured bar) with vanadium and molybdenum-analogue catalysts, with different oxidants applied.

**Table 3** Catalytic results of benzyl alcohol oxidation. Reaction conditions: time, 5 h; temperature, 80 °C,  $n(\text{catalyst})/n(\text{cyclooctene})/n(\text{oxidant}) = 0.1 \text{ mmol}/20 \text{ mmol}/40 \text{ mmol}$

Catalyst	Oxidant											
	TBHP in decane				TBHP in water				H <sub>2</sub> O <sub>2</sub> with CH <sub>3</sub> CN			
	Con <sup>a</sup> / %		Sel <sup>b</sup> / %		Con <sup>a</sup> / %		Sel <sup>b</sup> / %		Con <sup>a</sup> / %		Sel <sup>b</sup> / %	
	Reaction time / min											
	300	20	300	20	300	20	300	20	50	20	50	20
[VO(VIH)(OCH <sub>3</sub> ) <sub>4</sub> ] ( <b>1</b> )	88	61	16	40	91	55	10	38	34	30	34	30
[VO(VIH)(OC <sub>2</sub> H <sub>5</sub> ) <sub>4</sub> ] ( <b>2</b> )	87	72	16	33	89	65	12	33	32	30	32	30
[VO(VIH)(OC <sub>3</sub> H <sub>7</sub> ) <sub>4</sub> ] ( <b>3</b> )	87	62	16	41	90	56	10	32	34	29	34	29
[VO(VIH)(OC <sub>4</sub> H <sub>9</sub> ) <sub>n</sub> ] ( <b>4</b> )	89	62	14	31	94	67	10	33	40	31	40	31
[VO(VIH)(OC <sub>5</sub> H <sub>11</sub> ) <sub>n</sub> ] ( <b>5</b> )	87	70	16	34	91	60	10	39	32	29	32	29
[VO <sub>2</sub> (HVIH)] ( <b>6</b> )	88	63	15	39	87	60	14	38	34	29	34	29
[MoO <sub>2</sub> (VIH)] <sub>4</sub> ( <b>7</b> )	45	19	52	34	67	12	45	54	18	14	18	14



<sup>a</sup> alcohol consumed at 20 min and at the end of reaction. <sup>b</sup>  $n(\text{alcohol}) \text{ transformed} / n(\text{catalyst}) / \text{time}(\text{h})$  at 20 min and at the end of the reaction.

View Article Online


DOI: 10.1039/D5DT00105F

Benzaldehyde selectivity demonstrates a different trend. At 300 minutes, the selectivity values are approximately 16% with TBHP in decane and 10% with TBHP in water. These values are lower compared to those at 20 minutes, where selectivity ranges from 30 to 40% with TBHP in decane and 32–39% with TBHP in water, and around 30% with H<sub>2</sub>O<sub>2</sub>, across all vanadium catalysts (1–6), implying that after 20 min of the reaction benzaldehyde is slowly converted to the corresponding carboxylic acid, confirmed by characteristic peak in chromatogram.


It seems that the organic solvent presence in the system facilitates the formation of the desired product by enhancing the solubility of the reactants and stabilizing catalytic intermediates. In contrast, the water content adversely impacts the reaction by potentially disrupting catalyst activity, and reducing the efficiency of substrate-catalyst interactions. The exact amount of benzoic acid was not quantified due to the instrumentation limitations. This phenomenon is more pronounced when employing hydrogen peroxide as oxidizing agent. The conversion parameter remains largely consistent between 20 and 50 minutes, indicating a plateau in the kinetic profile is established. Meanwhile, in contrast to catalysts 1–6, catalysts 7 and 8 exhibit a different pattern. While the benzyl alcohol conversion with TBHP as an oxidant is much lower

compared to vanadium catalysts 1–6, the selectivity towards benzaldehyde is significantly higher, reaching approximately 50% for catalyst 7, but very low for 8. Conversely, Mo catalysts perform poorly with H<sub>2</sub>O<sub>2</sub> as the oxidant, which is in contrast to the reported data with a similar class of ligands.<sup>70,71</sup> As observed in Fig. 6, all vanadium catalysts (1–6) exhibit very similar kinetic profiles, achieving over 50% conversion at the onset of the reaction and improving further as the reaction progresses. Initial conversion values range from 55% for catalyst 1 to 67% for catalyst 4, indicating the highest TOF<sub>20min</sub> for catalyst 4 (404) and the lowest TOF<sub>20min</sub> for catalyst 1 (327). This further implies that all catalysts follow a similar reaction mechanism, transitioning to catalytically active species at comparable rates, depending on the alcohol coordinated to the vanadium metal centre. By the end of the reaction, all catalysts achieve conversion rates within a narrow range of 89–93%, resulting in similar TON values across all catalysts (176–190), Fig. 7.

Fig. 6 and S24 (see ESI<sup>†</sup>) illustrate that the kinetic profiles for catalysts 1–6 are remarkably similar, irrespective of whether TBHP is used in decane or water, respectively. The TOF<sub>20min</sub> values are slightly elevated when TBHP is employed in water, with catalyst 2 exhibiting the highest TOF<sub>20min</sub> at 432, and catalyst 6 the lowest at 366. By the end of the reaction, the TON values range from 160 to 183, Fig. 7.

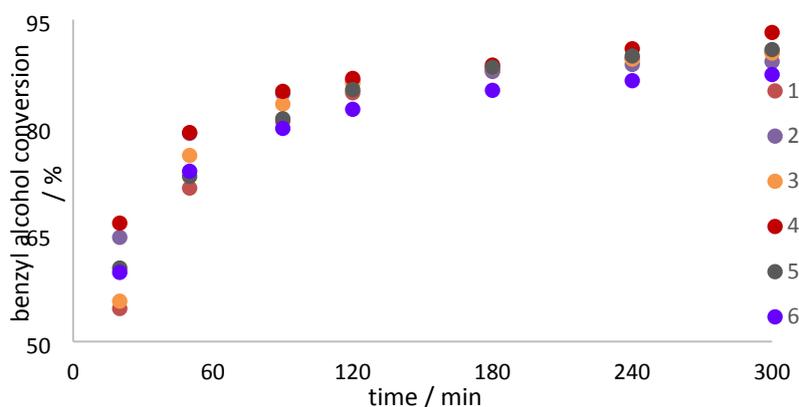

**Fig. 6** Kinetic profiles of benzyl alcohol conversion with V catalysts. The reaction temperature was 80 °C and TBHP in decane was used as the oxidizing agent. Reaction conditions: time, 5 h; temperature, 80 °C,  $n(\text{catalyst})/n(\text{cyclooctene})/n(\text{oxidant}) = 0.1 \text{ mmol}/20 \text{ mmol}/40 \text{ mmol}$ .

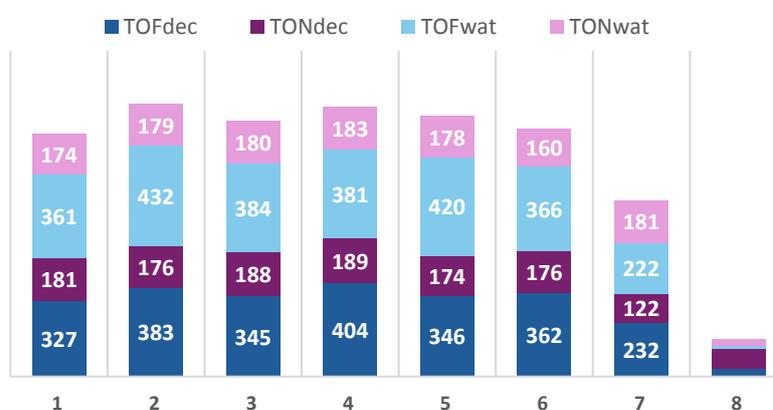

**Fig. 7** Comparison of TOF<sub>20min</sub> and TON values for V catalysts **1–6** and Mo catalysts **7** and **8**, with TBHP in decane and water as the oxidizing agent, for the benzyl alcohol oxidation. [View Article Online](#)  
DOI: 10.1039/D5DT00105F

In comparison to Mo catalysts, **7** and **8**, all vanadium catalysts **1–6** have higher TOF<sub>20min</sub> values, no matter the media in which TBHP is available. However, for catalyst **7**, TON of 122 in decane is lower in comparison to TON 181 in water, while the values for the catalyst **8** are extremely low.

We extended our investigation to evaluate the catalytic potential of [VO(acac)<sub>2</sub>] and V<sub>2</sub>O<sub>5</sub> as reference systems specifically for benzyl alcohol oxidation. The results from these reference systems are detailed in the Supplementary Material section (Table S7, see ESI<sup>†</sup>). The results obtained using [VO(acac)<sub>2</sub>] as a catalyst with TBHP in water or H<sub>2</sub>O<sub>2</sub> in MeCN as oxidants closely mirror those achieved with vanadium catalysts **1–6**. However, when employing TBHP in decane, the catalytic performance differed significantly. In this case, the benzyl alcohol conversion reached only 72% after 300 minutes of reaction, with a conversion of just 22% observed at the 20-minute mark. These findings suggest that the catalytic system requires a longer activation than catalysts **1–6**. Interestingly, the aldehyde selectivity was initially high at 71% after 20 minutes but decreased substantially to 37% by the end of the reaction. This trend further supports the hypothesis that TBHP is a more effective oxidant for this reaction than hydrogen peroxide, likely due to its superior ability to activate the catalyst and sustain high selectivity during the reaction. Furthermore, the results obtained with V<sub>2</sub>O<sub>5</sub> as a catalyst, regardless of the oxidant employed, yielded outcomes that are consistent with those observed for catalysts **1–6**. This indicates that V<sub>2</sub>O<sub>5</sub> exhibits comparable catalytic efficiency and selectivity under similar reaction conditions.

The mechanistic pathway for benzyl alcohol oxidation has not been addressed in this manuscript and remains a focal point for future investigations.

## Experimental

### General details

3-methoxy-2-hydroxybenzaldehyde isonicotinoyl hydrazone (H<sub>2</sub>VIH),<sup>56</sup> [VO(acac)<sub>2</sub>],<sup>72</sup> [MoO<sub>2</sub>(acac)<sub>2</sub>] (acac = acetylacetonate),<sup>73</sup> [MoO<sub>2</sub>(VIH)]<sub>4</sub>,<sup>46</sup> and [MoO<sub>2</sub>(VIH)(C<sub>2</sub>H<sub>5</sub>OH)]<sub>4</sub>,<sup>46</sup> were synthesised following the previously published procedures. 3-Methoxy-2-hydroxybenzaldehyde and isonicotinyl hydrazine were commercially available. All chemicals and solvents were used without further purification. They were purchased from Alfa Aesar or Aldrich. Additional characterization details (elemental and thermal analyses, ATR-IR, UV-Vis, NMR, PXRD, and SCXRD methods), and figures as noted in the text can be found in the supporting information.

### Synthesis of [VO(VIH)(OR)]<sub>4</sub> (**1**, **2**, and **3**) and [VO(VIH)(OR)]<sub>n</sub> (**4** and **5**).

NH<sub>4</sub>VO<sub>3</sub> (0.023 g, 0.2 mmol) was added to a solution of H<sub>2</sub>VIH (0.057 g, 0.21 mmol) in alcohol (30 mL). The reaction mixture was refluxed for 3 h and left overnight. The solution was concentrated under reduced pressure to a third of its volume and left

to stand at room temperature. Dark red-black crystals formed over one week were isolated by filtration and dried in vacuo.

**[VO(VIH)(OCH<sub>3</sub>)]<sub>4</sub> (**1**):** The complex was prepared in methanol. Yield: 0.036 g; 49%. Anal. Calcd. for C<sub>60</sub>H<sub>56</sub>N<sub>12</sub>O<sub>20</sub>V<sub>4</sub> (1468.921): C, 49.06; H, 3.84; N, 11.44. Found: C, 48.94; H, 3.63; N, 11.27%. TG: CH<sub>3</sub>O, 8.53 (Calcd. 8.45%); V<sub>2</sub>O<sub>5</sub>, 24.51% (Calcd. 24.76%). Selected IR data (cm<sup>-1</sup>): 1616 (C=N)<sub>imine</sub>, 1596 (C=N), 1350 (C-O<sub>hydrazone</sub>), 1262 (C-O<sub>phenolato</sub>), 1043 (C-O<sub>alkoxo</sub>), 970 (N-N), 962 (V=O), 750 (V-N<sub>imine</sub>), 708 (V-N<sub>py</sub>), 602 (V-O<sub>alkoxo</sub>), 580 (V-O<sub>hydrazone</sub>), 571 (V-O<sub>phenolato</sub>).

**[VO(VIH)(OC<sub>2</sub>H<sub>5</sub>)]<sub>4</sub> (**2**):** The complex was prepared in ethanol (30 mL). Yield: 0.063 g; 82%. Anal. Calcd. for C<sub>64</sub>H<sub>64</sub>N<sub>12</sub>O<sub>20</sub>V<sub>4</sub> (1525.027): C, 50.40; H, 4.23; N, 11.02. Found: C, 50.23; H, 4.19; N, 10.89%. TG: C<sub>2</sub>H<sub>5</sub>O, 12.13 (Calcd. 11.82%); V<sub>2</sub>O<sub>5</sub>, 23.67% (Calcd. 23.85%). Selected IR data (cm<sup>-1</sup>): 1615 (C=N)<sub>imine</sub>, 1595 (C=N), 1349 (C-O<sub>hydrazone</sub>), 1262 (C-O<sub>phenolato</sub>), 1034 (C-O<sub>alkoxo</sub>), 971 (N-N), 961 (V=O), 751 (V-N<sub>imine</sub>), 710 (V-N<sub>py</sub>), 600 (V-O<sub>alkoxo</sub>), 578 (V-O<sub>hydrazone</sub>), 569 (V-O<sub>phenolato</sub>).

**[VO(VIH)(OC<sub>3</sub>H<sub>7</sub>)]<sub>4</sub> (**3**):** The complex was in *n*-propanol (30 mL). Yield: 0.061 g; 77%. Anal. Calcd. for C<sub>17</sub>H<sub>18</sub>N<sub>3</sub>O<sub>5</sub>V (1581.132): C, 51.65; H, 4.59; N, 10.63. Found: C, 51.51; H, 4.46; N, 10.47%. TG: C<sub>3</sub>H<sub>7</sub>O, 14.12 (Calcd. 14.95%); V<sub>2</sub>O<sub>5</sub>, 22.87% (Calcd. 23.01%). Selected IR data (cm<sup>-1</sup>): 1614 (C=N)<sub>imine</sub>, 1594 (C=N), 1350 (C-O<sub>hydrazone</sub>), 1261 (C-O<sub>phenolato</sub>), 1060 (C-O<sub>alkoxo</sub>), 971 (N-N), 962 (V=O), 751 (V-N<sub>imine</sub>), 707 (V-N<sub>py</sub>), 598 (V-O<sub>alkoxo</sub>), 574 (V-O<sub>hydrazone</sub>), 570 (V-O<sub>phenolato</sub>).

**[VO(VIH)(OC<sub>4</sub>H<sub>9</sub>)]<sub>n</sub> (**4**):** The complex was prepared in *n*-butanol (30 mL). Yield: 0.075 g; 91%. Anal. Calcd. for C<sub>18</sub>H<sub>20</sub>N<sub>3</sub>O<sub>5</sub>V (409.31): C, 52.82; H, 4.93; N, 10.27. Found: C, 52.70; H, 4.78; N, 10.03%. TG: C<sub>4</sub>H<sub>9</sub>O, 17.17 (Calcd. 17.86%); V<sub>2</sub>O<sub>5</sub>, 22.00% (Calcd. 22.22%). Selected IR data (cm<sup>-1</sup>): 1616 (C=N)<sub>imine</sub>, 1598 (C=N), 1351 (C-O<sub>hydrazone</sub>), 1258 (C-O<sub>phenolato</sub>), 1064 (C-O<sub>alkoxo</sub>), 974 (N-N), 957 (V=O), 756 (V-N<sub>imine</sub>), 708 (V-N<sub>py</sub>), 599 (V-O<sub>alkoxo</sub>), 574 (V-O<sub>hydrazone</sub>), 565 (V-O<sub>phenolato</sub>).

**[VO(VIH)(OC<sub>5</sub>H<sub>11</sub>)]<sub>n</sub> (**5**):** The complex was prepared in *n*-pentanol (30 mL). Yield: 0.064 g; 74%. Anal. Calcd. for C<sub>19</sub>H<sub>22</sub>N<sub>3</sub>O<sub>5</sub>V (423.336): C, 53.91; H, 5.24; N, 9.93. Found: C, 53.77; H, 5.04; N, 9.76%. TG: C<sub>5</sub>H<sub>11</sub>O, 20.09 (Calcd. 20.58%); V<sub>2</sub>O<sub>5</sub>, 21.51% (Calcd. 21.48%). Selected IR data (cm<sup>-1</sup>): 1615 (C=N)<sub>imine</sub>, 1598 (C=N), 1351 (C-O<sub>hydrazone</sub>), 1256 (C-O<sub>phenolato</sub>), 1067 (C-O<sub>alkoxo</sub>), 972 (N-N), 958 (V=O), 756 (V-N<sub>imine</sub>), 709 (V-N<sub>py</sub>), 599 (V-O<sub>alkoxo</sub>), 574 (V-O<sub>hydrazone</sub>), 565 (V-O<sub>phenolato</sub>).

### Synthesis of [VO<sub>2</sub>(HVIH)]·0.5CH<sub>3</sub>OH·0.5H<sub>2</sub>O (**6**·0.5·0.5H<sub>2</sub>O)

NH<sub>4</sub>VO<sub>3</sub> (0.023 g, 0.2 mmol) was added to a solution of H<sub>2</sub>VIH (0.057 g, 0.21 mmol) in methanol (30 mL). The reaction mixture was left to stand at room temperature for two weeks. The solution was concentrated in an airstream to a third of its



volume and left to stand in a refrigerator. An orange powdered product formed over one week. Complex **6-0.5CH<sub>3</sub>OH-0.5H<sub>2</sub>O** was isolated by filtration and dried. Upon further evaporation, a few crystals of [VO<sub>2</sub>(HVIH)]·2H<sub>2</sub>O (**6-2H<sub>2</sub>O**) also formed.

### [VO<sub>2</sub>(HVIH)]·0.5CH<sub>3</sub>OH·0.5H<sub>2</sub>O (**6-0.5CH<sub>3</sub>OH·0.5H<sub>2</sub>O**):

Yield: 0.027 g; 35%. Anal. Calcd. for C<sub>14</sub>H<sub>12</sub>N<sub>3</sub>O<sub>5</sub>V (388,227): C, 47.61; H, 3.42; N, 11.90. Found: C, 47.45; H, 3.12; N, 11.64%. TG: CH<sub>3</sub>OH, 3.70 (Calcd. 3.92%); TG: H<sub>2</sub>O, 3.70 (Calcd. 3.92%); V<sub>2</sub>O<sub>5</sub>, 22.13% (Calcd. 22.28%). Selected IR data (cm<sup>-1</sup>): 1608 (C=N)<sub>imine</sub>, 1599 (C=N), 1348 (C-O<sub>hydrazone</sub>), 1249 (C-O<sub>phenolate</sub>), 973 (N-N), 930, 890 (V=O), 756 (V-N<sub>imine</sub>), 579 (V-O<sub>hydrazone</sub>), 572 (V-O<sub>phenolate</sub>).

### Quantum chemical calculations

Optimizations of geometries for all computed complexes were performed using the hybrid functional B3LYP<sup>74</sup> with the D3 version of Grimme's dispersion<sup>75</sup> and Becke-Johnson dumping in combination with the Def2TZVP<sup>76</sup> basis set. Initial geometries were taken from crystallographically determined structures. To confirm that the obtained geometries were local minima, harmonic frequency calculations were performed.<sup>77,78</sup> The standard Gibbs energies of formation were calculated at  $T = 298.15$  K and  $p = 101\,325$  Pa. Strengths of the intramolecular interactions were estimated by the calculation of relative differences in the standard Gibbs energies of binding  $\Delta_b G^\circ$ . All quantum chemical calculations were carried out using the Gaussian 16 program package.<sup>79</sup>

### Principal component analysis

Data obtained by time-dependent UV-Vis spectrophotometry of the monitored chemical reaction were exported to the ASCII format and arranged in the matrix (numbers written in a free format). Thus obtained 2<sup>nd</sup>-order data tensor with dimensions number-of-spectra×number-of-wavelengths was decomposed using the 2<sup>nd</sup>-order tensor reduction tool principal component analysis (PCA). PCA enables one to find the best linear projections for a high dimensional set of data in the least-squares sense. Scores represent projections of the original sample points on the principal component (PC) direction and can be used for representation of reactions in a reduced space. Therefore, each point in the score plots represents one sample UV-Vis spectra. Data were mean-centered and PCA of covariance matrix was performed using a NIPALS algorithm implemented in our own program moonee.<sup>77,80</sup>

### Conclusions

This study explores the synthesis, characterization, and catalytic activity of a series of vanadium(V) metallosupramolecular complexes with an aroylhydrazone ligand, demonstrating the potential of these complexes in oxidation reactions. Employing 3-methoxy-2-hydroxybenzaldehyde isonicotinoyl hydrazone (H<sub>2</sub>VIH) and NH<sub>4</sub>VO<sub>3</sub> with primary alcohols, we successfully synthesized and characterized both tetranuclear metallocycles and one-dimensional polymeric chains—resulting from varying the alkoxy ligand.

Through quantum chemical calculations, we assessed the stability of these assemblies, providing insights into the energetic favorability of cyclic versus polymeric forms and identifying key structural influences, such as the torsion angle between ligand rings and metal–ligand bond lengths. These findings indicate that ligand steric influence and torsional flexibility can significantly impact the formation and stability of these supramolecular structures, suggesting avenues for tuning structural properties through ligand modification.

Catalytic testing of the vanadium complexes in the epoxidation of cyclooctene and the oxidation of benzyl alcohol revealed their efficacy and consistency, with minor variations in conversion and selectivity depending on the specific vanadium complex and oxidant used. When compared with molybdenum analogues, the vanadium catalysts demonstrated competitive activity, though molybdenum retained a slight advantage in conversion and selectivity. Additionally, mechanistic studies using time-dependent UV-Vis spectrophotometry and principal component analysis allowed us to monitor reaction intermediates and transformations, revealing that the primary reaction pathway involved hydrazone ligand coordination to vanadium, followed by the formation of stable dioxo species under dilute conditions.

The findings in the described series of oxovanadium(V) coordination compounds illustrate how subtle changes in ancillary ligand size and flexibility can dictate not only the dimensionality of the structures, but also influence critical geometric and packing features, as well as catalytic performance. Expanding the studies to even longer or branched alkoxy ancillary ligands might provide a way to control the assembly of the monomers into tailor-made discrete or polymeric species as even more performant functional materials.

### Data availability

The data supporting this article have been included as part of the ESI. Crystallographic data for **1**, **2**, **3**, **4**, **5**, **6-2H<sub>2</sub>O**, **6-0.5CH<sub>3</sub>OH·0.5H<sub>2</sub>O** and **8** have been deposited at the Cambridge Structural Data base under with deposition numbers CCDC 2367618–2367624, 2400624.

### Author Contributions

Edi Topić: investigation, writing – original draft preparation, review and editing. Josipa Sarjanović: investigation and formal analysis. Danijela Musija: investigation and formal analysis, and writing – original draft preparation. Mirna Mandarić: investigation and formal analysis. Andrea Cocut: quantum chemical calculation. Tomica Hrenar: quantum chemical calculation, chemometric analysis, data curation, and writing – original draft preparation, visualization. Dominique Agustin: supervision, review and editing. Jana Pisk: investigation, supervision, formal analysis, writing – original draft preparation. Višnja Vrdoljak: conceptualization, supervision, funding acquisition, investigation, writing – original draft preparation, visualization, review and editing.



## Conflicts of interest

There are no conflicts to declare.

View Article Online  
DOI: 10.1039/D5DT00105F

## Acknowledgments

This work was supported by the Croatian Science Foundation under the project number HRZZ-IP-2022-10-7368. We acknowledge the support of project CluK co-financed by the Croatian Government and the European Union through the European Regional Development Fund-Competitiveness and Cohesion Operational Programme (Grant KK.01.1.1.02.0016.). LCC CNRS and Chemistry Dept of IUT Paul Sabatier are acknowledged for providing the equipment and chemicals for catalytic experiments considering cyclooctene epoxidation reactions.

Open Access Article. Published on 26 February 2025. Downloaded on 2/26/2025 10:18:01 PM.  
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.



## Notes and references

- 1 I. Gryca, K. Czerwińska, B. Machura, A. Chrobok, L. S. Shul'pina, M. L. Kuznetsov, D. S. Nesterov, Y. N. Kozlov, A. L. Pombeiro, I. A. Varyan and G. B. Shul'pin, High Catalytic Activity of Vanadium Complexes in Alkane Oxidations with Hydrogen Peroxide: An Effect of 8-Hydroxyquinoline Derivatives as Noninnocent Ligands, *Inorg. Chem.*, 2018, **57**, 4, 1824–1839.
- 2 D. Dragancea, N. Talmaci, S. Shova, G. Novitchi, D. Darvasiova, P. Rapta, M. Breza, M. Galanski, J. Kožíšek, N. M. R. Martins, L. M. D. R. S. Martins, A. J. L. Pombeiro and V. B. Arion, Vanadium(V) Complexes with Substituted 1,5-bis(2-hydroxybenzaldehyde)carbohydrazones and Their Use As Catalyst Precursors in Oxidation of Cyclohexane, *Inorg. Chem.*, 2016, **55**, 9187–9203.
- 3 J.-Q. Wu and Y.-S. Li, Well-defined vanadium complexes as the catalysts for olefin polymerization, *Coord. Chem. Rev.* 2011, **255**, 2303-2314.
- 4 G. B. Shul'pin and Y. N. Kozlov, Kinetics and mechanism of alkane hydroperoxidation with tert-butyl hydroperoxide catalysed by a vanadate anion, *Org. Biomol. Chem.*, 2003, **1**, 2303–2306.
- 5 M. Sutradhar, L. M. D. R. S. Martins, M. F. C. G. da Silva and A. J. L. Pombeiro, Vanadium complexes: Recent progress in oxidation catalysis, *Coord. Chem. Rev.* 2015, **301–302**, 200–239.
- 6 W. Trakarnpruk and P. Hoonsart, Oxidation of Alcohols over Vanadium Catalysts, *Chin. J. Catal.*, 2007, **28**, 290–292.
- 7 M. R. Maurya, N. Jangra, F. Avecilla, N. Ribeiro and I. Correia, Vanadium(V) and Molybdenum(VI) Complexes Containing ONO Tridentate Schiff Bases and Their Application as Catalysts for Oxidative Bromination of Phenols, *ChemistrySelect*, 2019, **4**, 12743-12756.
- 8 J. Pisk, B. Prugovečki, D. Matković-Čalogović, R. Poli, D. Agustin and V. Vrdoljak, Charged dioxomolybdenum(VI) complexes with pyridoxal thiosemicarbazone ligands as molybdenum(V) precursors in oxygen atom transfer process and epoxidation (pre)catalysts, *Polyhedron*, 2012, **33**, 441-449.
- 9 J. Pisk, D. Agustin, V. Vrdoljak and R. Poli, Epoxidation Processes by Pyridoxal Dioxomolybdenum(VI) (Pre)Catalysts Without Organic Solvent, *Adv. Synth. Catal.*, 2011, **353**, 2910-2914.
- 10 R. Bikas, V. Lippolis, N. Noshiranzadeh, H. Farzaneh-Bonab, A. J. Blake, M. Siczek, H. Hosseini-Monfared and T. Lis, Electronic Effects of Aromatic Rings on the Catalytic Activity of Dioxidomolybdenum(VI)–Hydrazone Complexes, *Eur. J. Inorg. Chem.*, 2017, 999-1006.
- 11 M. R. Maurya, L. Rana and F. Avecilla, Catalytic oxidation of internal and terminal alkenes by oxidoperoxidomolybdenum(VI) and dioxidomolybdenum(VI) complexes, *Inorg. Chim. Acta*, 2015, **429**, 138-147.
- 12 L. J. McCormick, B. F. Abrahams, B. A. Boughton, M. J. Grannas, T. A. Hudson and R. Robson, Synthesis, Structure and Cation-Binding Properties of Some [4 + 4] Metallocyclic MO<sub>2</sub><sup>2+</sup> (M = Mo or W) Derivatives of 9-Phenyl-2,3,7-trihydroxyfluor-6-one. *Inorg. Chem.* 2014, **53**, 1721–1728.
- 13 V. Vrdoljak, J. Pisk, D. Agustin, P. Novak, J. P. Vuković and D. Matković-Čalogović, Dioxomolybdenum (VI) and dioxotungsten (VI) complexes chelated with the ONO tridentate hydrazone ligand: synthesis, structure and catalytic epoxidation activity, *New J. Chem.* 38 (12), 6176-6185.
- 14 M. Z. Čorović, F. Wiedemaier, F. Belaj and N. C. Mösch-Zanetti, Replacement of Molybdenum by Tungsten in a Biomimetic Complex Leads to an Increase in Oxygen Atom Transfer Catalytic Activity, *Inorg. Chem.* 2022, **61**, 12415–12424.
- 15 E. Topić, V. Damjanović, K. Pičuljan, M. Rubčić, Dinuclear Molybdenum(VI) Complexes Based on Flexible Succinyl and Adipoyl Dihydrazones, *Crystals* 2024, **14**, 135.
- 16 M. Sutradhar, N. V. Shvydkiy, M. F. C. G. da Silva, M. V. Kirillova, Y. N. Kozlov, A. J. L. Pombeiro and G. B. Shul'pin, A new binuclear oxovanadium(v) complex as a catalyst in combination with pyrazinecarboxylic acid (PCA) for efficient alkane oxygenation by H<sub>2</sub>O<sub>2</sub>, *Dalton Trans.*, 2013, **42**, 11791-11803.
- 17 M. R. Maurya, N. Kumar and F. Avecilla, Controlled Modification of Triaminoguanidine-Based μ<sub>3</sub> Ligands in Multinuclear [V<sup>VO</sup>]/[V<sup>VO</sup>O<sub>2</sub>] Complexes and Their Catalytic Potential in the Synthesis of 2-Amino-3-cyano-4H-pyrans/4H-chromenes, *Inorg. Chem.* 2024, **63**, 2505–2524.
- 18 V. Vrdoljak, M. Mandarić, T. Hrenar, I. Đilović, J. Pisk, G. Pavlović, M. Cindrić and D. Agustin, Geometrically Constrained Molybdenum(VI) Metallosupramolecular Architectures: Conventional Synthesis versus Vapor and Thermally Induced Solid-State Structural Transformations, *Cryst. Growth Des.*, 2019, **19**, 3000-3011.
- 19 D. Cvijanović, J. Pisk, G. Pavlović, D. Šišak-Jung, D. Matković-Čalogović, M. Cindrić, D. Agustin and V. Vrdoljak, Discrete mononuclear and dinuclear compounds containing a MoO<sub>2</sub><sup>2+</sup> core and 4-aminobenzhydrazone ligands: synthesis, structure and organic-solvent-free epoxidation activity, *New. J. Chem.* 2019, **43**, 1791-1802.
- 20 J. Pisk, M. Rubčić, D. Kuzman, M. Cindrić, D. Agustin and V. Vrdoljak, Molybdenum(VI) complexes of hemilabile aroylhydrazone ligands as efficient catalysts for greener cyclooctene epoxidation: an experimental and theoretical approach, *New J. Chem.* 2019, **43**, 5531-5542.
- 21 J. Pisk, D. Agustin and V. Vrdoljak, Tetranuclear molybdenum(VI) hydrazone-to epoxidation (pre)catalysts: Is water always the best choice? *Catal. Commun.* 2020, **142**, 106027.
- 22 M. Mandarić, E. Topić, D. Agustin, J. Pisk and V. Vrdoljak, Preparative and Catalytic Properties of Mo<sup>VI</sup> Mononuclear and Metallosupramolecular Coordination Assemblies Bearing Hydrazone-to Ligands, *Int. J. Mol. Sci.* 2024, **25**, 1503.
- 23 A. Farrokhi, M. Jafarpour and R. Najafzade, Phosphonate-based Metal Organic Frameworks as Robust Heterogeneous Catalysts for TBHP Oxidation of Benzylic Alcohols. *Catalysis Letters*, 2017, **147**, 1714-1721.
- 24 U. S. F. Arrozi, R. Pratama, F. Soraya, Y. Permana, S. Hartina, E. Salduna, W. W. Lestari, W. Ciptonugroho and Y. P. Budiman, Solvent-Free Oxidation of Benzyl Alcohol Using Modified Zeolitic Imidazolate Frameworks-8 (ZIF-8) Catalysts, *Chemistry Select*, 2024, **9**, e202304882.
- 25 B. M. Peterson, M. E. Herried, R. L. Neve and R. W. McGaff, Oxidation of primary and secondary benzylic alcohols with hydrogen peroxide and tert-butyl hydroperoxide catalyzed by a “helmet” phthalocyaninato iron complex in the absence of added organic solvent, *Dalton Trans.* 2014, **43**, 17899-17903.
- 26 M. Y. Enbo, W. Ying, L. Shutao, W. Yangguang, L. Wang and C. Hu, A novel chain-like binuclear vanadium(V) coordination polymer containing mixed ligands: hydrothermal synthesis and crystal structure of [VO<sub>2</sub>(2,2'-bipy)]<sub>2</sub>(tp)<sub>2</sub> (tp=terephthalate), *Inorg. Chim. Acta*, 2003, **344**, 257-261.
- 27 E. Kiss, A. Benyei and T. Kiss, VO(IV) complexes of 3-hydroxypicolinic acid: a solution study and the structure of a supramolecular assembly in the solid state. *Polyhedron* 2003, **22** 27-33.
- 28 X.-M. Zhang, M. Liang Tong, H. Kay Lee and X.-M. Chen, The First Noncluster Vanadium(IV) Coordination Polymers: Solvothermal Syntheses, Crystal Structure, and Ion Exchange. *J. Solid. State Chem.* 2001, **160**, 118–122.
- 29 K. Su, M. Wu, D. Yuan and M. Hong, Interconvertible vanadium-seamed hexameric pyrogallol[4]arene nanocapsules, *Nat. Commun.* 2018, **9**, 4941.
- 30 S. P. Dash, A. K. Panda S. Pasayat, R. Dinda, A. Biswas, E. R. T. Tiekink, S. Mukhopadhyay, S. K. Bhutia, W. Kaminsky and E. Sinn, Oxidovanadium(v) complexes of aroylhydrazones incorporating heterocycles: synthesis, characterization and study of DNA binding, photo-induced DNA cleavage and cytotoxic activities, *RSC Adv.*, 2015, **5**, 51852–51867.
- 31 L. Zhang, Z. You and H.-Y. Qian, Synthesis, characterization and crystal structure of a novel tetranuclear oxidovanadium(V)



- complex derived from *N'*-(2-hydroxy-3-methoxybenzylidene)isonicotinohydrazide with catalytic property, *Inorg. Nano-Metal Chem.* 2022, 1–5,
- 32 H. Kargar, A. Kaka-Naeini, M. Fallah-Mehrjardi, R. Behjatmanesh-Ardakani, H. Amiri Rudbari and K. Shahzad Munawar, Oxovanadium and dioxomolybdenum complexes: synthesis, crystal structure, spectroscopic characterization and applications as homogeneous catalysts in sulfoxidation, *J. Coord. Chem.*, 2021, **74**, 1563–1583.
- 33 C. Lescop, Coordination-Driven Syntheses of Compact Supramolecular Metallacycles toward Extended Metallo-organic Stacked Supramolecular Assemblies, *Acc. Chem. Res.* 2017, **50**, 885–894.
- 34 B. H. Northrop, H.-B. Yang and P. J. Stang, Coordination-driven self-assembly of functionalized supramolecular metallacycles, *Chem. Commun.* 2008, 5896–5908.
- 35 T. R. Cook and P. J. Stang, Recent Developments in the Preparation and Chemistry of Metallacycles and Metallacages via Coordination, *Chem. Rev.* 2015, **115**, 7001–7045.
- 36 S. Leininger, B. Olenyuk and P. J. Stang, Self-assembly of discrete cyclic nanostructures mediated by transition metals. *Chem. Rev.* 2000, **100**, 853–908.
- 37 B. H. Northrop, Y.-R. Zheng, K.-W. Chi and P. J. Stang, Self-Organization in Coordination-Driven Self-Assembly, *Acc. Chem. Res.* 2009, **42**, 1554–1563.
- 38 M. Ahmadi and S. Seiffert, Coordination Geometry Preference Regulates the Structure and Dynamics of Metallo-Supramolecular Polymer Networks, *Macromolecules* 2021, **54**, 1388–1400.
- 39 R. L. Borkar, M. Bhol, B. Shankar, J. Karges and M. Sathiyendiran, Solvent-Directed Rhenium(I) Metallocyclic Tubes, Dimeric Capsule, and Intercalated Dimers, *Cryst. Growth Des.* 2024, **24**, 1987–1999.
- 40 M. S. McCreedy and R. J. Puddephatt, Self-assembly of isomeric clamshell dimers of platinum(II), *Dalton Trans.*, 2012, **41**, 12378–12385.
- 41 C. H. Li and J. L. Zuo, Self-Healing Polymers Based on Coordination Bonds, *Adv. Mater.* 2019, 1903762.
- 42 N. Giuseppone, J. L. Schmitt and J. M. Lehn, Driven Evolution of a Constitutional Dynamic Library of Molecular Helices Toward the Selective Generation of [2 × 2] Gridlike Arrays under the Pressure of Metal Ion Coordination. *J. Am. Chem. Soc.* 2006, **128**, 16748–16763.
- 43 C. Dietrich-Buchecker, B. Colasson, M. Fujita, A. Hori, N. Geum, S. Sakamoto, K. Yamaguchi and J. P. Sauvage, Quantitative Formation of [2]Catenanes Using Copper(I) and Palladium(II) as Templating and Assembling Centers: The Entwining Route and the Threading Approach, *J. Am. Chem. Soc.* 2003, **125**, 5717–5725.
- 44 V. Berl, I. Huc, R. G. Khoury, M. J. Krische and J. M. Lehn, Interconversion of single and double helices formed from synthetic molecular strands, *Nature* 2000, **407**, 720–723.
- 45 A. A. Levchenko, C. K. Yee, A. N. Parikh and A. Navrotsky, Energetics of Self-Assembly and Chain Confinement in Silver Alkanethiolates: Enthalpy–Entropy Interplay, *Chem. Mater.* 2005, **17**, 5428–5438.
- 46 V. Vrdoljak, B. Prugovečki, D. Matković-Čalogović, R. Dreos, P. Siega and C. Tavagnacco, Zigzag Chain, Square Tetranuclear, and Polyoxometalate-Based Inorganic–Organic Hybrid Compounds - Molybdenum vs Tungsten, *Cryst. Growth Des.* 2010, **10**, 1373–1382.
- 47 V. Vrdoljak, B. Prugovečki, D. Matković-Čalogović, J. Pisk, R. Dreos and P. Siega, Supramolecular Hexagon and Chain Coordination Polymer Containing the  $\text{MoO}_2^{2+}$  Core: Structural Transformation in the Solid State, *Cryst. Growth Des.* 2011, **11**, 1244–1252.
- 48 V. Vrdoljak, B. Prugovečki, D. Matković-Čalogović, T. Hrenar, R. Dreos and P. Siega, Three Polymorphic Forms of a Monomeric Mo(VI) Complex: Building Blocks for Two Metal–Organic Supramolecular Isomers. Intermolecular Interactions and Ligand Substituent Effects, *Cryst. Growth Des.* 2013, **13**, 3773–3784.
- 49 J. Pisk, J.-C. Daran, R. Poli and D. Agustin, Pyridoxal based ONS and ONO vanadium(V) complexes: Structural analysis and catalytic application in organic solvent free epoxidation, *J. Mol. Cat. A: Chem.*, 2015, **403**, 52–63.
- 50 R. A. Sheldon and J. K. Kochi, in *Metal-Catalyzed Oxidations of Organic Compounds*, Academic Press, New York, 1981. 9.
- 51 L. C. Hill, in *Advances in Oxygenated Processes*, ed. A. L. Baumstark, JAI Press Inc., London, 1988, vol. 1
- 52 R. J. J. Jachuck, D. K. Selvaraj and R. S. Varma, Process intensification: oxidation of benzyl alcohol using a continuous isothermal reactor under microwave irradiation, *Green Chem.* 2006, **8**, 29–33.
- 53 C. Ragupathi, J. J. Vijaya, S. Narayanan, S. K. Jesudoss and L. J. Kennedy, Highly selective oxidation of benzyl alcohol to benzaldehyde with hydrogen peroxide by cobalt aluminate catalysis: a comparison of conventional and microwave methods, *Ceram. Int.*, 2015, **41**, 2069–2080.
- 54 C. Lu, J. Hu, M. Y. N. Meng, A. D. Zhou, F. Zhang and Z. B. Zhang, The synergistic effect of benzyl benzoate on the selective oxidation of toluene to benzaldehyde, *Chem. Eng. Res. Des.* 2019, **141**, 181–186.
- 55 C. Miao, H. Zhao, Q. Zhao, C. Xia and W. Sun, NHPI and ferric nitrate: a mild and selective system for aerobic oxidation of benzylic methylenes, *Catal. Sci. Technol.* 2016, **6**, 1378–1383.
- 56 J. Pisk, T. Hrenar, M. Rubčić, G. Pavlović, V. Damjanović, J. Lovrić, M. Cindrić, V. Vrdoljak, Comparative studies on conventional and solvent-free synthesis toward hydrazones: application of PXRD and chemometric data analysis in mechanochemical reaction monitoring, *CrystEngComm*, 2018, **20**, 1804–1817.
- 57 L. Zhang, Z. You and H.-Y. Qian, Synthesis, characterization and crystal structure of a novel tetranuclear oxidovanadium(V) complex derived from *N'*-(2-hydroxy-3-methoxybenzylidene)isonicotinohydrazide with catalytic property, *Inorg. Nano-Met. Chem.*, 2022, **54**, 282–286.
- 58 Blatov V. A., Shevchenko A. P., Proserpio D. M. Applied topological analysis of crystal structures with the program package ToposPro, *Cryst. Growth Des.*, 2014, **14**, 3576–3586.
- 59 As implemented in CCDC Mercury software. C. R. Groom, I. J. Bruno, M. P. Lightfoot and S. C. Ward, The Cambridge Structural Database, *Acta Cryst.*, 2016, **B72**, 171–179.
- 60 S. Y. Ebrahimpour, M. Mohamadi, I. Sheikhshoae, S. Suárez, R. Baggio and M. Khaleghi, A novel oxido-vanadium(V) Schiff base complex: synthesis, spectral characterization, crystal structure, electrochemical evaluation, and biological activity, *Res. Chem. Intermed.*, 2016, **42**, 611–623.
- 61 Y.-H. Lu, Y.-W. Lu, C.-L. Wu, Q. Shao, X.-L. Chen and R. N. B. Bimbong, UV–visible spectroscopic study of the salicylaldehyde benzoylhydrazone and its cobalt complexes, *Spectrochim. Acta A*, 2006, **65**, 695–701. <https://doi.org/10.1016/j.saa.2005.12.032>
- 62 H. Hosseini-Monfared, S. Alavi, R. Bikas, M. Vahedpour and P. Mayer, Vanadiumoxo–aroylhydrazone complexes: Synthesis, structure and DFT calculations, *Polyhedron*, 2010, **29**, 3355–3362.
- 63 R. Dinda, P. Sengupta, S. Ghosh, H. Mayer-Figge and W. S. Sheldrick, A family of mononuclear molybdenum-(VI), and -(IV) oxo complexes with a tridentate (ONO) ligand, *J. Chem. Soc., Dalton Trans.*, 2002, 4434–4439.
- 64 L. M. Martínez-Prieto, P. Palma, E. Álvarez, J. Cámpora, Nickel Pincer Complexes with Frequent Aliphatic Alkoxo Ligands [(<sup>18</sup>P)PCP]Ni-OR (R = Et, *n*Bu, *i*Pr, 2-hydroxyethyl). An Assessment of the Hydrolytic Stability of Nickel and Palladium Alkoxides, *Inorg. Chem.*, 2017, **56**, 21, 13086–13099.
- 65 S. R. Patra, S. Mondal, D. Sinha and K. K. Rajak, Mono Versus Dinuclear Vanadium(V) Complexes: Solvent Dependent



- Structural Versatility and Electro Syntheses of Mixed-Valence Oxovanadium(IV/V) Entities in Solution, *ACS Omega*, 2022, **7**, 11710-11721.
- 66 J. A. Bonadies and C. J. Carrano, Vanadium phenolates as models for vanadium in biological systems. 1. Synthesis, spectroscopy, and electrochemistry of vanadium complexes of ethylenebis[*o*-hydroxyphenyl]glycine] and its derivatives, *J. Am. Chem. Soc.* 1986, **108**, 4088–4095.
- 67 M. R. Maurya, S. Khurana, C. Schulzke and D. Rehder, Dioxo- and Oxovanadium(V) Complexes of Biomimetic Hydrazone *ONO* Donor Ligands: Synthesis, Characterisation, and Reactivity, *Eur. J. Inorg. Chem.* **2001**, 779–788.
- 68 M. R. Maurya, B. Sarkar, F. Avecilla and I. Correia, Vanadium Complexes Derived from Acetyl Pyrazolone and Hydrazides: Structure, Reactivity, Peroxidase Mimicry and Efficient Catalytic Activity for the Oxidation of 1-Phenylethanol, *Eur. J. Inorg. Chem.* 2016, 4028–4044.
- 69 J. Döbler, M. Pritzsche and J. Sauer, Oxidation of Methanol to Formaldehyde on Supported Vanadium Oxide Catalysts Compared to Gas Phase Molecules, *J. Am. Chem. Soc.* 2005, **127**, 10861-10868.
- 70 L. Balapoor, R. Bikas, M. Dargahi, Catalytic oxidation of benzyl-alcohol with H<sub>2</sub>O<sub>2</sub> in the presence of a dioxidomolybdenum(VI) complex, *Inorg. Chim. Acta* 2020, **510**, 119734.
- 71 S. L. Pandhare, R. R. Jadhao, V. G. Puranik, P. V. Joshi, F. Capet, M. K. Dongare, S. B. Umbarkar, C. Michon, F. Agbossou-Niedercorn, Molybdenum(VI) dioxo complexes for the epoxidation of allylic alcohols and olefins, *J. Organomet. Chem.* 2014, **772–773**, 271-279.
- 72 B. E. Bryant, W. C. Fernelius, D. H. Busch, R. C. Stoufer and W. Stratton, Vanadium(IV) Oxy(acetylacetonate), In *Inorganic Syntheses*; Ed. T. Moeller, John Wiley & Sons, Inc, 1957; 5, pp 113–116. <https://doi.org/10.1002/9780470132364.ch30>
- 73 J.-J. Chen, J. W. McDonald and W. E. Newton, Synthesis of molybdenum(IV) and molybdenum(V) complexes using oxo abstraction by phosphines, Mechanistic implications, *Inorg. Chem.*, 1976, **15**, 2612. <https://doi.org/10.1021/ic50165a008>
- 74 (a) C. Lee, W. Yang and R. G. Parr, *Phys. Rev. B*, 1998, **37**, 785; (b) R. Peverati and D. G. Truhlar, *Phys. Chem. Chem. Phys.*, 2021, **14**, 16187.
- 75 S. Grimme, S. Ehrlich and L. Goerigk, "Effect of the damping function in dispersion corrected density functional theory," *J. Comp. Chem.* **32** (2011) 1456-65.
- 76 (a) F. Weigend and R. Ahlrichs, "Balanced basis sets of split valence, triple zeta valence and quadruple zeta valence quality for H to Rn: Design and assessment of accuracy," *Phys. Chem. Chem. Phys.*, **7** (2005) 3297–3305. (b) F. Weigend, "Accurate Coulomb-fitting basis sets for H to Rn," *Phys. Chem. Chem. Phys.*, **8** (2006) 1057-1065.
- 77 T. Hrenar, I. Primožič, D. Fijan, M. Majerić Elenkov, Conformational analysis of spiro-epoxides by principal component analysis of molecular dynamics trajectories, *Phys. Chem. Chem. Phys.* 2017, **19**, 31706–31713.
- 78 I. Primožič, T. Hrenar, K. Baumann, L. Krišto, I. Križič, S. Tomić, "Mechanochemical and Conformational Study of N-heterocyclic Carbonyl-Oxime Transformations" *Croat. Chem. Acta* 2014, **87**, 153–160.
- 79 M. J. Frisch, G. W. Trucks, H. B. Schlegel, G. E. Scuseria, M. A. Robb, J. R. Cheeseman, G. Scalmani, V. Barone, G. A. Petersson, H. Nakatsuji, X. Li, M. Caricato, A. V. Marenich, J. Bloino, B. G. Janesko, R. Gomperts, B. Mennucci, H. P. Hratchian, J. V. Ortiz, A. F. Izmaylov, J. L. Sonnenberg, D. Williams-Young, F. Ding, F. Lipparini, F. Egidi, J. Goings, B. Peng, A. Petrone, T. Henderson, D. Ranasinghe, V. G. Zakrzewski, J. Gao, N. Rega, G. Zheng, W. Liang, M. Hada, M. Ehara, K. Toyota, R. Fukuda, J. Hasegawa, M. Ishida, T. Nakajima, Y. Honda, O. Kitao, H. Nakai, T. Vreven, K. Throssell, J. A. Montgomery, Jr., J. E. Peralta, F. Ogliaro, M. J. Bearpark, J. J. Heyd, E. N. Brothers, K. N. Kudin, V. N. Staroverov, T. A. Keith, R. Kobayashi, J. Normand, K. Raghavachari, A. P. Rendell, J. C. Burant, S. S. Iyengar, J. Tomasi, M. Cossi, J. M. Millam, M. Klene, C. Adamo, R. Cammi, J. W. Ochterski, R. L. Martin, K. Morokuma, O. Farkas, J. B. Foresman and D. J. Fox, Gaussian 16, Revision A.03, Gaussian, Inc., Wallingford CT, 2016.
- 80 O. Jović, T. Smolić, I. Primožič, T. Hrenar, "Spectroscopic and Chemometric Analysis of Binary and Ternary Edible Oil Mixtures: Qualitative and Quantitative Study", *Anal. Chem.* **88** (2016) 4516–4524.



## Data availability statement

View Article Online  
DOI: 10.1039/D5DT00105F

The data supporting this article have been included as part of the Supplementary Information.

Crystallographic data sets for the structures **1–5**, **6·0.5H<sub>2</sub>O·0.5CH<sub>3</sub>OH**, **6·2H<sub>2</sub>O**, and **8** are available through the Cambridge Structural Data base with deposition numbers CCDC 2335829–2335837, 2400624.

