

Dalton Transactions

An international journal of inorganic chemistry

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: J. Medina, Y. Wang, H. Bourakhouadar, M. Köller, A. J. Corkett, D. Ensling, T. Jüstel and R. Dronskowski, *Dalton Trans.*, 2025, DOI: 10.1039/D5DT01003A.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Thermometer or Freezer: Dual Functionality in a 2D Mixed-Anion Terbium (III) Oxide Carbodiimide

Juan Medina-Jurado,^a YiXu Wang,^a Hicham Bourakhouadar,^a Moritz Köller,^a Alex J. Corkett,^b David Enseling,^c Thomas Jüstel^c, and Richard Dronskowski^{*a}

^a Chair of Solid-State and Quantum Chemistry, Institute of Inorganic Chemistry, RWTH Aachen University, 52056 Aachen, Germany

^b Jülich Center for Neutron Science-2 (JCNS), Forschungszentrum Jülich GmbH, 52425 Jülich, Germany

^c Department of Chemical Engineering, FH Münster University of Applied Sciences, 48565 Steinfurt, Germany

E-mail: drons@HAL9000.ac.rwth-aachen.de

<http://www.ssc.rwth-aachen.de>

Abstract

Advances in the chemistry of compounds containing the NCN^{2-} complex anion are leading to the discovery of new materials with interesting and promising properties. Here we present a comprehensive investigation of the optical and magnetic properties of the 2D *phosphor* $\text{Tb}_2\text{O}_2\text{NCN}$ whose structure presents a double layer of Tb-triangular lattices separated from each other by the NCN^{2-} anion, offering a conjunction of luminescent thermometry and magnetocaloric effect. Temperature-dependent luminescence studies reveal the typical behavior of thermal quenching, but when the temperature increases, a mechanism of direct relaxation to the 5D_4 levels of Tb^{3+} ions is activated, thereby giving rise to an anti-thermal quenching effect. This peculiar feature has prompted us to explore the characteristics of $\text{Tb}_2\text{O}_2\text{NCN}$ in temperature sensing, using the classical approach of optical ratiometric thermometry as well as an approach based on linear transformations (i.e., principal component analysis). The latter, by employing the entire emission spectrum, offers better sensitivity leading to more accurate temperature values. The magnetic properties of $\text{Tb}_2\text{O}_2\text{NCN}$ reveal a long-range antiferromagnetic ordering below $T_N = 6.5$ K as well as first-order field-induced metamagnetic transitions. The absence of hysteresis and its high magnetic density make $\text{Tb}_2\text{O}_2\text{NCN}$ a fine candidate for magnetic refrigeration, with a surprisingly large value of $-\Delta S_M = 11.7 \text{ J kg}^{-1} \text{ K}^{-1}$ at 5 T, much more promising than those reported for other Tb-comprising compounds.



Introduction

View Article Online
DOI: 10.1039/D5DT01003A

In recent years, layered crystal structures incorporating the NCN^{2-} anion have been shown to display a wide variety of desirable optical properties, as well as finding applications in electrochemistry and photochemistry.^[1] Among the most prominent examples are the MNCN ($M = \text{Zn, Mn, Fe, Co}$) binary carbodiimide compounds, which exhibit outstanding performance as anodes in lithium- and sodium-ion batteries, and also silver cyanamide, Ag_2NCN , which has been used as a catalyst for water oxidation.^[2–8] One area in which NCN -based compounds stand out is that of luminescence, however, as they are able to incorporate many of the most common activators into their crystal structure, such as lanthanide ions Ln^{3+} ($\text{Ln} = \text{Ce, Tb, Pr, Eu}$) or Mn^{2+} and Eu^{2+} divalent cations.^[9–20] Several *phosphor* materials have been synthesized by substitution using as host lattice NCN -based structures such as those based on binary carbodiimides, for example $\text{CaNCN}:\text{Mn}^{2+}$, $\text{SrNCN}:\text{Eu}^{2+}$, and $\text{Gd}_2\text{NCN}_3:\text{Tb}^{3+}$, or those synthesized based on ternary cyanamides, such as $\text{LiIn}(\text{NCN})_2:\text{Tb}^{3+}$ or the recent work on the alkaline-mixed compound $\text{Li}_x\text{Na}_{1-x}\text{Tb}(\text{NCN})_2$.^[21,22] Nonetheless, the mixed-anion oxide carbodiimides, $\text{Ln}_2\text{O}_2\text{NCN}$, currently constitute the largest family of host lattices suitable for the preparation of luminescent materials.

The crystal structure of $\text{Ln}_2\text{O}_2\text{NCN}$ ($\text{Ln} = \text{Sm–Yb}$, $P\bar{3}m1$) is composed of alternating layers of $[\text{Ln}_2\text{O}_2]^{2+}$ and NCN^{2-} stacked along the c -axis as shown in Figure 1.^[23,24] The structure of the cationic layer is formed by a block (or double-layer) of Ln^{3+} ions composed of two sheets with a triangular Ln–Ln network extending throughout the ab -plane. The geometry of the crystal sublattice of the Ln^{3+} ions is such that the distance between sheets within the same block, d_{intra} , is much smaller than the distance between sheets of different blocks, d_{inter} , so that the distance arrangement between the Ln^{3+} ionic planes is $d_{\text{intra}}-d_{\text{inter}}-d_{\text{intra}}-d_{\text{inter}}-\dots$ along the stacking axis, making it a structure that can be understood as being two-dimensional. Luminescent materials of this family have been developed, such as the substituted compounds $\text{Y}_2\text{O}_2\text{NCN}:\text{Eu}^{3+}$ and $\text{Gd}_2\text{O}_2\text{NCN}:\text{Eu}^{3+}, \text{Tb}^{3+}$.^[25,26] As in the case of the other luminescent compounds based on the NCN group, however, the description of the optical properties is limited



to the study of the excitation/emission spectra and radiative decay curves but potential uses as a functional material have not yet been explored in depth.

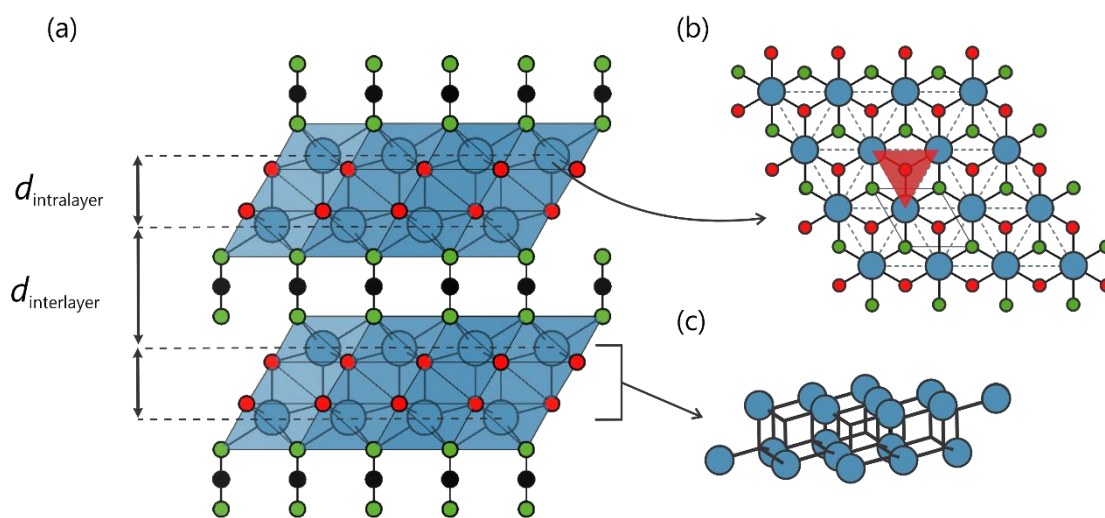


Figure 1. (a) Crystal structure of Tb₂O₂NCN with two different spacings between layers. (b) The terbium atoms (blue) are arranged in a double layer consisting of two sheets of triangular nets (in red) of terbium cations. (c) Arrangement of Tb³⁺ ions in shifted triangular lattice layers.

An application field receiving increased attention recently is that of optical thermometry, where the temperature can be determined by the emission characteristics of a luminescent center present in the material hence called “thermometric”.^[27–37] Thus, by analyzing thermally induced changes in specific spectroscopic parameters of the *phosphor*, a direct correlation between said parameters and temperature can be established. Accordingly, luminescent thermometry has been developed on the basis of photoluminescent properties such as the intensity of an emission band, spectral position, bandwidth, radiative decay time, or, most importantly, the *ratio* of the emission intensity (dubbed “ratiometric”) of two different bands.^[27,28,38,39] The latter is the most frequently employed approach, since this type of thermometry is not affected by changes in the experimental conditions under which the emission intensities are obtained.^[28,40–42]

Typically, in a ratiometric-thermometric material, two luminescent centers with different temperature response are required.^[39,43,44] The design usually involves a lanthanide ion (Ln^{3+}) acting as a reference and a transition-metal ion (M^{2+}) to detect the signal.



This type of configuration is particularly effective given the difference in the responsible ions' thermal quenching mechanism (i.e., how the emission of the centers is affected with respect to temperature).^[45–48] In this way, one will obtain thermometers with good accuracy (δT) and thermal sensitivity (S_T). This technique still has some limitations, however, mainly related to the need to spectroscopically resolve the bands involved which is not always simple as there may be band overlap. In addition, a good thermometric material should be as thermally and chemically stable as possible while its preparation process should be robust enough to reproduce the results of luminescence evaluation.^[27,28,31,38,49]

Hereby, we present the inorganic solid-state mixed-anion *phosphor* terbium (III) oxide carbodiimide ($\text{Tb}_2\text{O}_2\text{NCN}$) as a candidate multifunctional material, coupling magnetism and photosensitivity in the same compound. The temperature-dependent photoluminescence exhibits typical thermal-quenching behavior at low temperatures but reveals, at moderate temperatures, an antithermal-quenching mechanism, so as to establish ratiometric thermometry with only *one* luminescent center. This peculiar characteristic, together with the fact that $\text{Tb}_2\text{O}_2\text{NCN}$ presents high chemical, thermal and mechanical stability and a facile solid-state synthesis process, make it a promising material for thermal sensing at cryogenic temperatures. In addition, we present an approach to thermometry, which is receiving increasing attention, based on dimensional reduction through principal component analysis (PCA): not only the emission of two bands but the *complete data* of the emission spectrum (high dimensional space) are considered for the treatment of the information, thus eliminating problems related to spectral overlap or changes in the shape of the emission spectrum.^[51–55]

$\text{Tb}_2\text{O}_2\text{NCN}$ also exhibits a temperature-dependent magnetic behavior demonstrating a giant magnetocaloric effect (MCE) such that it is also a promising candidate for a low-temperature refrigerant. The large ground-state spin of Tb^{3+} ions and the high magnetic density in $\text{Tb}_2\text{O}_2\text{NCN}$ lead to a large magnetic entropy change ($-\Delta S_M$) manifesting its role for magnetic refrigeration.^[56,57] Finally, this compound exhibits slow magnetic relaxation as a consequence of the inherent anisotropy in the ions' magnetic ordering, thus demonstrating a strong structure-property relation; the geometry of the crystal



structure determines the processes related to the energy migration of the photoluminescence as well as the magnetic interaction between the Tb^{3+} ions.

Results and Discussion

The fully inorganic 2D $\text{Tb}_2\text{O}_2\text{NCN}$ was synthesized via solid-state metathesis by heating a solid, homogenized mixture of Li_2NCN and TbOCl to 600 °C under argon flow, as described recently.^[58] The powder X-ray diffraction pattern reveals high phase purity (Figure 2a) with hexagonal lattice parameters $a = 3.75 \text{ \AA}$ and $c = 8.20 \text{ \AA}$. Details of the Rietveld refinement, crystallographic information and atomic positions are available in the Supplementary Information (Figure S1, Tables S1 and S2). The structure of $\text{Tb}_2\text{O}_2\text{NCN}$ ($P\bar{3}m1$, No. 164) is composed of a double-layer of Tb^{3+} ions with a bipyramidal-type coordination environment, i.e., three NCN^{2-} units on one side and three oxygen atoms on the opposite side, plus an additional oxygen atom forming a $\text{Tb}-\text{O}$ bond along the c -stacking axis (Figure 2b). Each of the TbN_3O_4 polyhedra shares an edge with six other polyhedra in the same layer and with three others in the next layer. The terbium cations within the double-layer are bridged to each other by O^{2-} anions, while the connection between terbium atoms in different layers relies on NCN^{2-} anions. The arrangement of the Tb^{3+} magnetic ions in each sheet of the double-layer forms an equilateral triangular lattice with distances $d_{\text{intrasheet}} \approx 3.75 \text{ \AA}$ and $d_{\text{intralayer}} \approx 3.65 \text{ \AA}$ (Figure 2b). An important characteristic is that these triangular Tb motifs are displaced from each other in such a way that the Tb^{3+} ion in one layer is above/below the center of the triangle formed by the terbium ions in the next layer of the double-layer, as shown in Figure 2c. Thus, the triangular layers alternate with the NCN^{2-} anion in a stacking with an $AB\text{-NCN-AB-NCN-AB}$ arrangement and an interlayer distance $d_{\text{interlayer}} \approx 5.69 \text{ \AA}$, so that we can expect a behavior characteristic for a two-dimensional system.



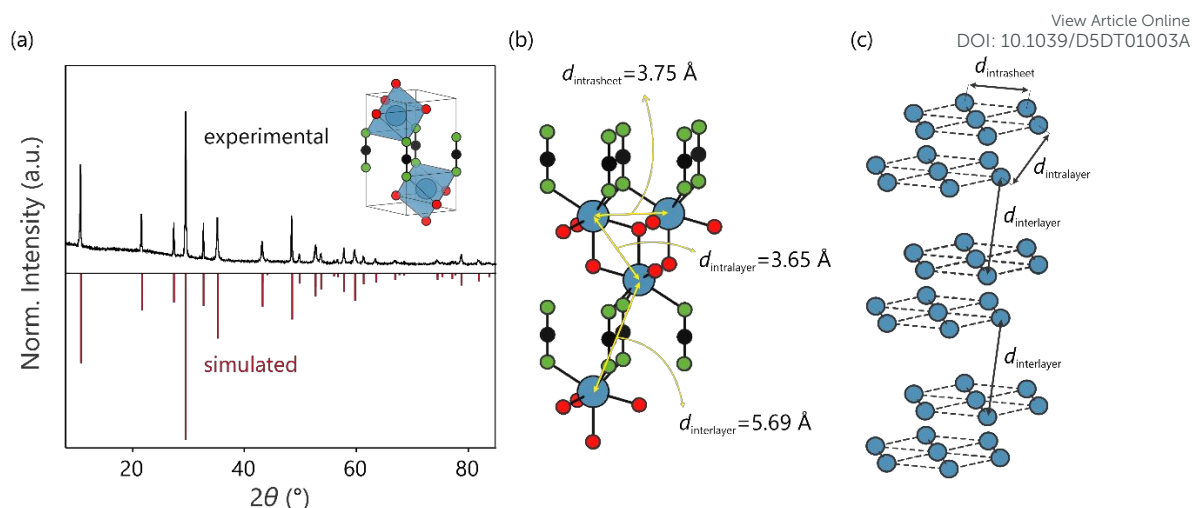


Figure 2. (a) Powder X-ray diffraction pattern of $\text{Tb}_2\text{O}_2\text{NCN}$ and simulated reflections based on the previously reported model. (b) Connection between terbium atoms within the double layer revealing two different spacings, $d_{\text{intrasheet}} = 3.75$ and $d_{\text{intralayer}} = 3.65$ Å, as well as the communication between atoms of different layers at a distance of $d_{\text{interlayer}} = 5.69$ Å. (c) Topological arrangement of Tb^{3+} ions highlighting the three most important distances: intrasheet, intralayer and interlayer.

To investigate the optical properties of $\text{Tb}_2\text{O}_2\text{NCN}$, photoluminescence emission spectra were recorded in the temperature range of 3–320 K (Figure 3a). Upon excitation at 270 nm the oxide carbodiimide exhibits typical Tb^{3+} luminescence with narrow and well-resolved emission bands. The spectrum consists of multiple bands along five regions centered around 487, 543, 583, 621, and 658 nm corresponding to the $[\text{Xe}]4f^8 - [\text{Xe}]4f^8$ intraconfigurational transitions of the Tb^{3+} ions from the 5D_4 level towards the 7F_J levels with $J = 6, 5, 4, 3$, and 2 , respectively. The temperature dependence of the emission spectra of $\text{Tb}_2\text{O}_2\text{NCN}$ is provided in Figure 3b and reveals two types of behavior. First, as the temperature increases from 3 to 140 K, the intensity of the main emission (at 543 nm) decreases to about 55 % of the intensity at 3 K, which typically is due to the thermal activation of non-radiative decay mechanisms, an observation well-known as thermal quenching. Quite surprisingly, however, starting at 140 K the intensity *increases* progressively with temperature up to 320 K, an increase of about 200 % compared to the intensity at 140 K, thus demonstrating an anti-thermal quenching behavior.



To facilitate the analysis of the thermal and anti-thermal quenching of the $^5D_4 \rightarrow ^7F_J$ transitions, we segmented the emission spectrum into five different regions: R_1 ($J = 6$, 480–500 nm), R_2 ($J = 5$, 535–555 nm), R_3 ($J = 4$, 577–602 nm), R_4 ($J = 3$, 613–629 nm), and R_5 ($J = 2$, 656–660 nm). The behavior of the intensities (expressed as integrated area) of the five R_i regions with temperature, as well as the total emission, are shown in Figure 3c. Clearly, the intensity of the regions R_1 , R_2 (related to the main emission at 543 nm) and R_3 mirror the thermal and antithermal quenching behavior, although the effect is not as pronounced in the R_1 case. In contrast, the intensity of the R_4 region is not strongly affected by temperature until 200 K at which point the intensity starts to increase up to 150% at $T = 320$ K compared to the value at 3 K. The R_5 region looks practically unaffected. Thus, the anti-thermal quenching effect becomes dominant in four out of five regions from $T = 200$ K onwards.

This temperature behavior can be explained by two different processes. A first mechanism takes place at low temperatures, where under excitation at 270 nm the electrons pass directly from the ground state to the 5d levels (Figure 3d), where by non-radiative processes they populate the 5D_J levels and emit light mainly by $^5D_4 \rightarrow ^7F_J$ transitions. Thus, as the temperature increases, the non-radiative transfer process becomes more dominant and the intensity of the emission decreases, which constitutes the thermal-quenching effect. This is observed in the intensity behavior of regions R_2 and R_3 where the intensity clearly decreases as the temperature increases. Nonetheless, the fact that the intensity in the R_1 region (transition $^5D_4 \rightarrow ^7F_6$) is not so strongly affected by temperature can be explained by a compensation effect resulting from Tb–Tb energy transfer through a cross-relaxation mechanism between the $^5D_3 \rightarrow ^7F_0$ and $^7F_6 \rightarrow ^5D_4$ transitions. At moderate temperatures, as the temperature increases multiple vibration states above the 5d levels are formed. If they are energetically close enough to the Tb–NCN charge-transfer state, the 5d electrons relax directly towards the 5D_4 levels, thereby increasing the intensity of all radiative emissions towards the 7F_J levels and explaining the anti-thermal quenching effect, as shown in Figure 3e (violet line). Therefore, in this temperature regime, this second mechanism compensates and exceeds the intensity reduction originating from the intrinsic thermal-quenching effect, so all the intensities of the R_i regions increase. If the temperature continues to increase, i.e., the compound is over-heated, electrons could



be thermally induced from the Tb–NCN state to the ground state without light emission, thus increasing the non-radiative energy loss (Figure 3e yellow line).

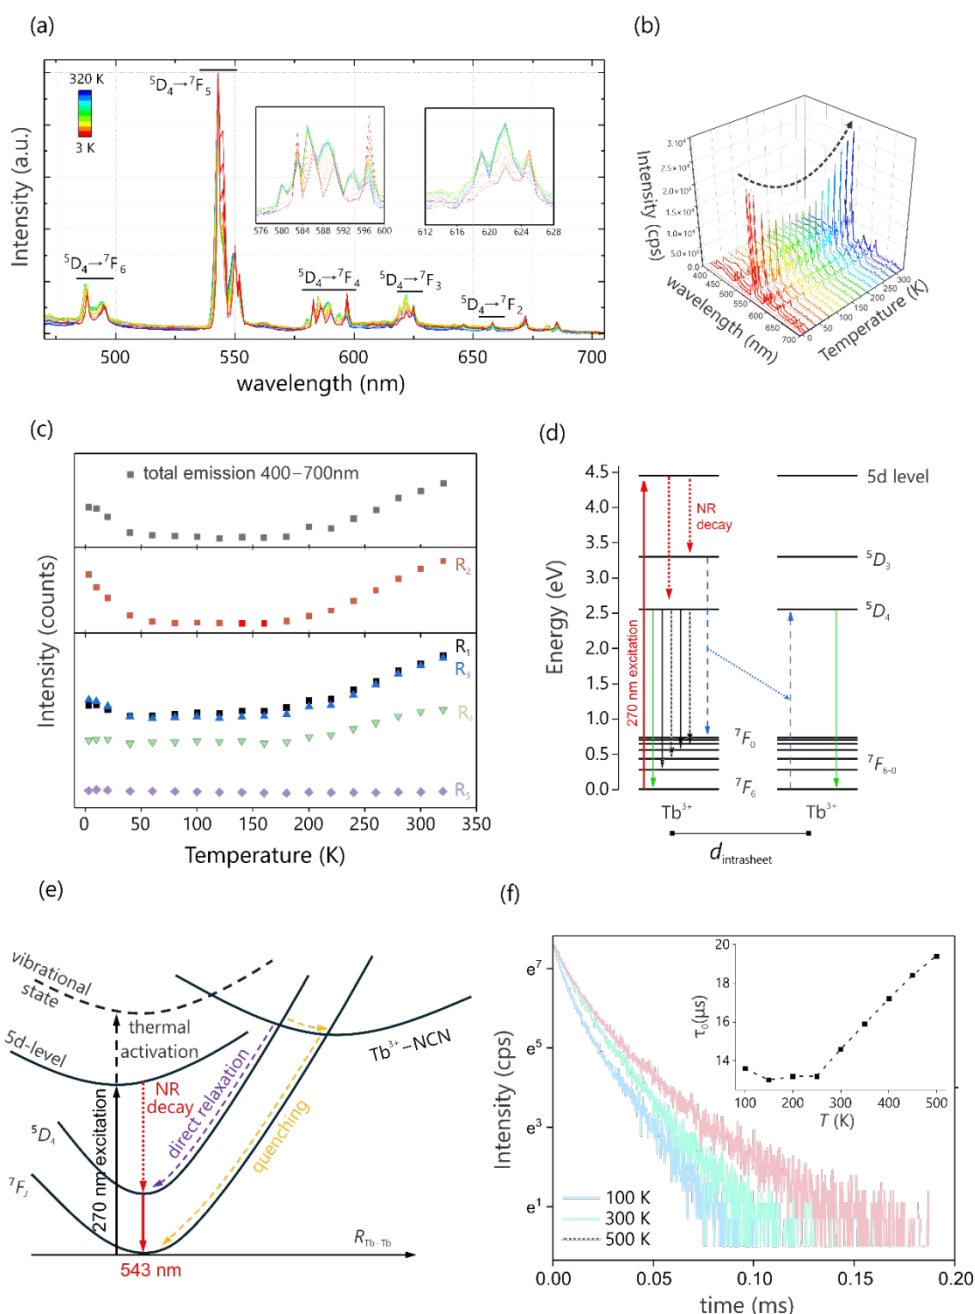


Figure 3. (a) Emission spectra of Tb₂O₂NCN under $\lambda_{\text{exc}} = 270$ nm in the temperature range between 3 and 320 K, resulting in the transitions $^5D_4 \rightarrow ^7F_J$. (b) Temperature-dependent emission spectra showing the anti-thermal quenching effect for the main emission at 543 nm. (c) Temperature-dependence of integrated intensities for the total emission and $^5D_4 \rightarrow ^7F_J$ transitions, R_1 ($J = 6$), R_2 ($J = 5$), R_3 ($J = 4$), R_4 ($J = 3$) and R_5 ($J = 2$). (d) Schematic energy



diagram of the cross-relaxation process between $^5D_3 \rightarrow ^7F_0$ and $^7F_6 \rightarrow ^5D_4$ (e). Suggested configurational coordinate diagram for the anti-thermal quenching process in Tb_2O_2NCN (f). Decay curves for the transition $^5D_4 \rightarrow ^7F_5$ at 100, 300, and 500 K. Inset: Temperature-dependence of the experimental radiative lifetime (τ_0). For the excitation spectrum of Tb_2O_2NCN , please see ref. [58].

To obtain information about the energy transfer process between Tb^{3+} ions, time-dependent luminescence measurements ($\lambda_{exc} = 270$ nm) were carried out for the $^5D_4 \rightarrow ^7F_5$ transition in the 100–500 K range, as depicted in Figure 3f. In all cases, the decay curves do not show mono-exponential behavior but the long-time part follows the mono-exponential decay model: $I = I_0 \exp(-t/\tau_0)$. By fitting the experimental data with this equation, an experimental radiative lifetime of $\tau_0 = 13.6$ μs at $T = 100$ K is obtained, which increases to 19.4 μs at 500 K, revealing that the energy migration process slows with temperature and is consistent with the thermal intensity behavior in the emission spectrum. Now, it is known that the probability (or rate) of energy transfer (P) can be expressed as $P = C \exp(-2R/L)$, where R is the distance between the luminescent centers, C is an interaction constant between them, and L is the effective average Bohr radius (≈ 0.30 Å for Tb^{3+} ions). Since in the Tb_2O_2NCN structure the intrasheet distance (≈ 3.75 Å) is considerably smaller than the interlayer distance (≈ 5.69 Å) the energy-migration rate is dominant along the Tb^{3+} ion double-layer ($P_{intrasheet} / P_{interlayer} \approx 8 \times 10^5$). To investigate the nature of these short-distance interactions, the value of the critical transfer distance (R_C) compared to the Tb–Tb distance in the triangular network ($d_{intrasheet} \approx 3.75$ Å) has been evaluated. This very critical distance can be calculated according to $R_C = 2 \left(\frac{3V}{4\pi x_C n} \right)^{1/3}$ where V is the unit-cell volume, n is the number of activators per unit cell, and x_C is the activator concentration (1.0 for Tb_2O_2NCN , a stoichiometric compound fully occupied by Tb^{3+} ions). Thus, one obtains $R_C \approx 4.57$ Å $> d_{intrasheet}$, indicating that the energy-migration process is favored through an exchange interaction mechanism.

In an attempt to take advantage of the particular thermal behavior of the emission spectrum, Tb_2O_2NCN was tested for ratiometric thermometry. We found that the thermal variation of the intensities (expressed as integrated area, I_{λ}^{area}) of the emission peaks in regions R_2 and R_3 provide good combinations suitable for thermometric parameters, $\Delta = I_{\lambda_2}^{area} / I_{\lambda_1}^{area}$. The choice of λ_1 and λ_2 is made so that one of the



intensities is strengthened at low temperatures (cold band) while the other is weakened (hot band). In this way, we have explored the temperature behavior of two thermometric parameters $\Delta_{552/580} = I_{552\text{ nm}}^{\text{area}} / I_{580\text{ nm}}^{\text{area}}$ and $\Delta_{597/594} = I_{597\text{ nm}}^{\text{area}} / I_{594\text{ nm}}^{\text{area}}$ as shown in Figure 4. The experimental data can be appropriately described according to the Mott–Seitz equation^[59,60] according to which $\Delta_T = \Delta_0 / [1 + \alpha_1 \exp(-\Delta E_1/k_B \cdot T) + \alpha_2 \exp(-\Delta E_2/k_B \cdot T)]$, where Δ_0 , α_1 and α_2 are fitting parameters and ΔE_1 and ΔE_2 are the activation energies for the emissions. Fitting the model yields that for thermometry based on $\Delta_{552/580}$ only one channel is required (i.e., $\Delta E_2 \approx 0$) so that $\Delta E_1 \approx 37$ K while for the thermometric parameter $\Delta_{597/594}$ values of $\Delta E_1 \approx 225$ K and $\Delta E_2 \approx 38$ K (see Supplementary Information for details) are obtained. Small values in the activation energy could be related to a multiphonon quenching mechanism while the higher value would be associated with the thermal crossover mechanism described in Figure 3. Moreover, as shown in Figure 4, the values of $\Delta_{552/580}$ decrease exponentially with temperature, which explains the presence of only one non-radiative decay channel, while $\Delta_{597/594}$ shows an “S-shaped” decrease, making the presence of two channels ΔE_1 and ΔE_2 with a considerable energy difference understandable.

The performance analysis of both thermometric curves was performed by inspecting the relative thermal sensitivity, $S_r = |\partial \Delta_T / \partial T| / \Delta$, and temperature uncertainty, $\delta T = |\delta \Delta / \Delta| / S_r$.^[27,28,38] This evaluation reveals that the wavelengths chosen provide good values of S_r and δT (i.e., $S_r > 1\%$ K⁻¹ and $\delta T < 1$ K) at relatively low temperatures. The thermometric parameter $\Delta_{552/580}$ offers an operating range between 10 and 140 K with a maximum sensitivity $S_r = 2.42\%$ K⁻¹ at 20 K while $\Delta_{597/594}$ provides a maximum sensitivity $S_r = 1.13\%$ K⁻¹ also at 20 K but with a wider temperature reading range between 10 and 180 K. Similar results can also be obtained with the intensities associated with the maximum emission (Figure S2). Furthermore, it is possible to establish a direct linear correlation between temperature and the thermometric parameters $\Delta_{594/597}$ and $\Delta_{580/597}$, involving wavelengths of the transition $^5D_4 \rightarrow ^7F_4$, in addition to $\Delta_{622/597}$ related to the transitions $^5D_4 \rightarrow ^7F_3$ and $^5D_4 \rightarrow ^7F_4$, respectively. Hence, the thermometry appears in three different temperature regimes: cryogenic (10–120 K), low (80–200 K) and medium (180–320 K) as shown in Figure 5. This type of thermometry is simpler, more robust and reliable, and it does not require any additional



calibration. In addition, large values in the slopes demonstrate a high sensitivity indicating that $\text{Tb}_2\text{O}_2\text{NCN}$ is an excellent self-referencing luminescent thermometer. DOI: 10.1039/D5DT00003A

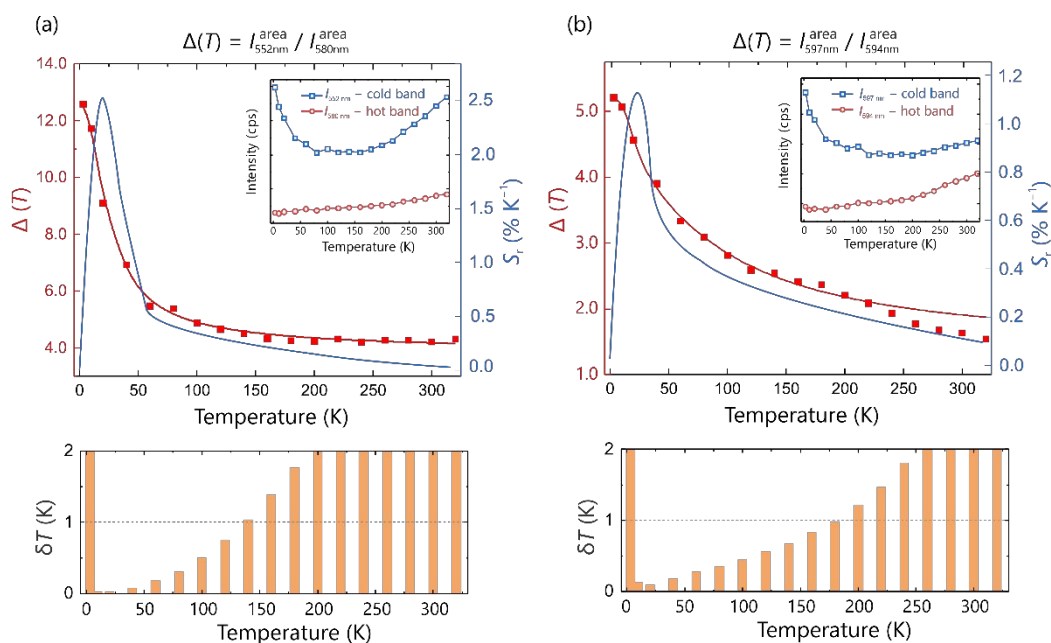


Figure 4. Top: Thermometric calibration curves $\Delta(T)$ involving the integrated areas for the peaks (inset) and relative sensitivity dependence, $S_r(T)$. Red squares are experimental data while solid curves are the best fit to the Mott–Seitz model. Bottom: temperature uncertainty curves $\delta T(T)$.

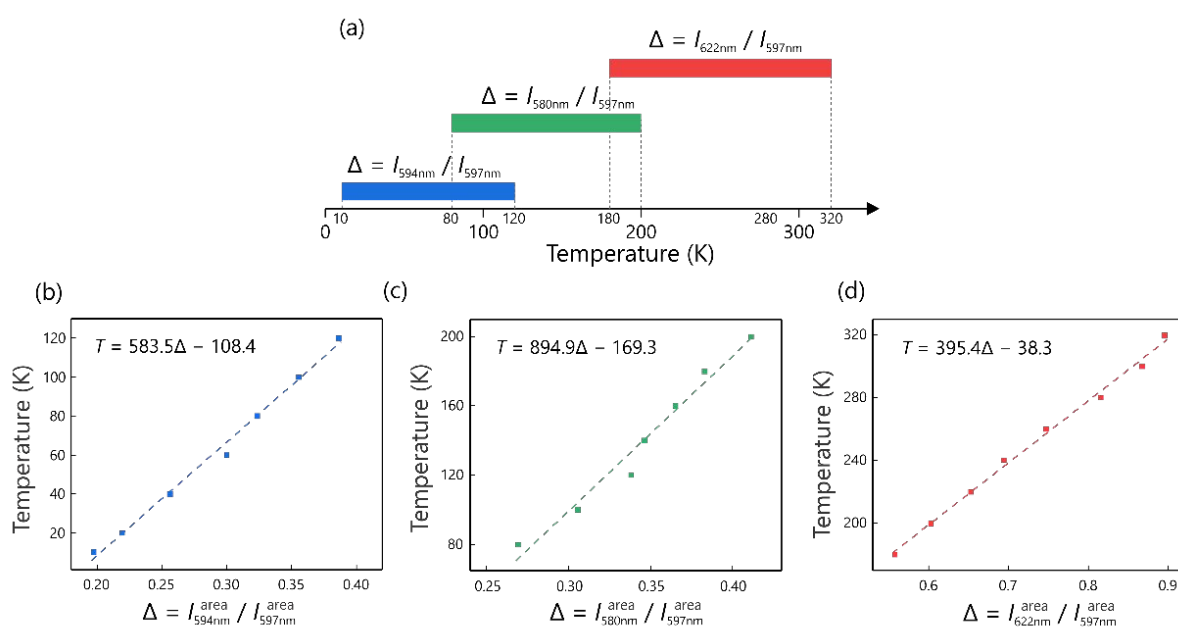


Figure 5. (a) Relation between thermometric parameters and the temperature ranges offering the best performance for linear thermometry. Temperature-dependence of the ratiometric parameters $\Delta_{594/597}$ (b), $\Delta_{580/597}$ (c) and $\Delta_{622/597}$ (d). Solid squares represent the experimental data and dashed lines correspond to the best fit to a linear equation.

One of the biggest challenges related to ratiometric thermometry is to extract intensities reliably and easily. In the case of $\text{Tb}_2\text{O}_2\text{NCN}$, the wavelengths offering the best results in sensitivity (S_r) and precision (δT) involve the $^5D_4 \rightarrow ^7F_J$ transitions ($J = 4$ and 3), which involve a high degree of complexity due to the splitting of the emissions by the crystal field, and this could hinder a future real application. For this reason, we have explored the option of a thermometry involving, during the analysis, information from the *entire* emission spectrum and not just part of it, thereby eliminating any error upon intensity extraction. To do so, we propose a multivariate thermometry based on principal component analysis (PCA), a statistical dimensionality-reduction method used to find combinations of variables describing the behavior of large datasets. In this way, the collected data were arranged in a 18×251 matrix X where the number of rows corresponds to the number of observations (i.e., the different temperatures in the range 3–320 K) while the number of columns represents the number of variables, in our case the intensities at the wavelengths of the emission spectrum between 450–700 nm. Thus, the PCA was performed on this matrix X , producing a set of new variables, or principal components (PC_i), which are related to the original intensities $I(\lambda_j)$ at a given temperature, by means of $PC_i = \sum c_i(\lambda_j)I(\lambda_j)$ where $c_i(\lambda_j)$ represents the coefficients describing the behavior of each principal component.^[54,55]

After applying PCA to our experimental datasets, we found that only three principal components are sufficient to describe more than 90% of the variance of the original data. In addition, the coefficients associated with each of the three principal components reproduce the emission spectrum in considerable detail (Figure 6a), showing a shape and variability very close to the original information in the regions of interest R_i (that is, where the transitions $^5D_4 \rightarrow ^7F_J$ occur) while in the areas outside their contribution is basically null, so that our principal components are not only statistically relevant but also have physical meaning. As a result, temperature was related to these new variables by multivariate linear regression, obtaining a good correlation as shown in Figure 6b. In order to evaluate the performance parameters, the linear regression equation was used as a basis $T_{\text{calc}} = \beta_0 + \sum \beta_i PC_i$ obtaining sensitivity values (S_r) well



above 1.0% as shown in Figure 6b and a precision (δT) of ≈ 1.0 K (see Supplementary Information for details). It is rather obvious that PCA-thermometry offers better performance results since it uses the entire experimental dataset to identify the parameters that correlate with temperature, without the need to pre-select regions or specific thermometric parameters.

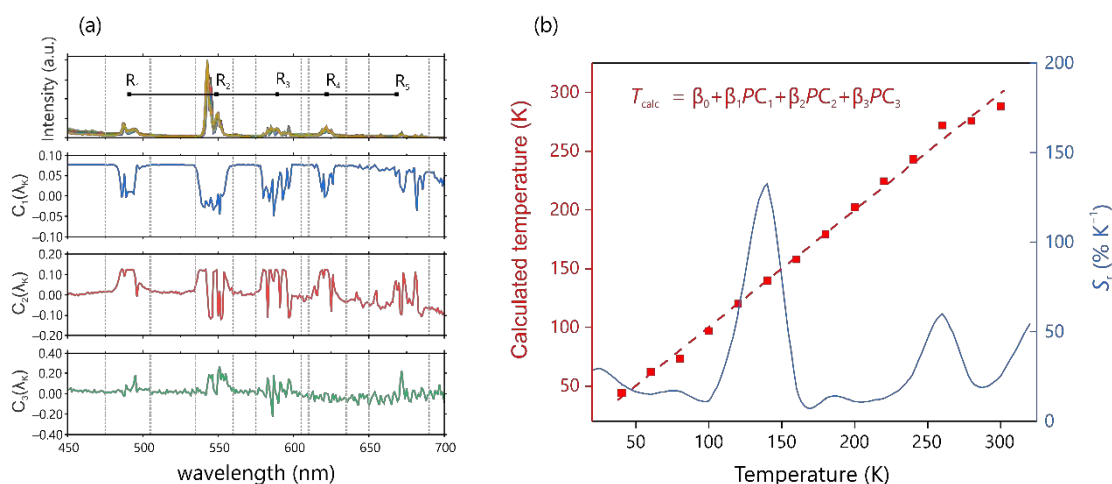


Figure 6. (a) Photoluminescent emission spectrum of Tb₂O₂NCN and the corresponding coefficients for the first three principal components: PC_1 explains 65.7% of the original data's variance while PC_2 and PC_3 have values of 25.29% and 2.06%. (b) Relation between temperature and calculated temperature by multivariate regression using principal components as input. Solid squares represent the experimental data while the dashed line represents the best fit to a linear equation. In addition, the relative sensitivity dependence $S_r(T)$ is shown on the right axis.

The magnetic behavior of μ -crystalline Tb₂O₂NCN was investigated by susceptibility measurements using a SQUID magnetometer. The value of the magnetic susceptibility $\chi_M T$ at room temperature is 22.4 cm³ K mol⁻¹ in good agreement with the theoretical value of 23.6 cm³ K mol⁻¹ expected for two isolated Tb³⁺ ions ($J = 6$, $g_L = 3/2$).^[37,61–63] Upon cooling, $\chi_M T$ remains practically constant up to about 150 K, from where, due to the depopulation of the excited levels of the ⁷F₆ ground multiplet, it starts to decrease to a value of 2.1 cm³ K mol⁻¹ at 3 K as shown in Figure 7a. In the temperature range between 50–300 K the susceptibility χ_M follows the Curie Weiss law $\chi = \frac{C}{T - \theta_{CW}}$ quite well, so that by fitting a $1/\chi_M$ vs. T curve the parameters $\theta_{CW} = -16.6$ K and $C = 23.75$ cm³ K mol⁻¹ are obtained. The negative value of θ_{CW} indicates predominantly



antiferromagnetic interactions between Tb^{3+} ions in the paramagnetic state, while the effective magnetic moment calculated from C yields $13.98 \mu_{\text{B}}$ (i.e., $9.70 \mu_{\text{B}}$ per Tb^{3+} ion), in agreement with the expected theoretical value ($\mu_{\text{eff}} = g_L \sqrt{J(J+1)} = 9.72 \mu_{\text{B}}$ per Tb^{3+} ion).^[37,64] Under 50 K, the curve $\chi(T)$ clearly shows the characteristic peak for a paramagnetic transition to long-range antiferromagnetic order at $T_N \approx 6.5$ K (Figure 7b). This low ordering temperature reflects the Tb–Tb interactions: as already mentioned, the arrangement of the Tb^{3+} in $\text{Tb}_2\text{O}_2\text{NCN}$ corresponds to three Tb–Tb distances: $d_{\text{intrasheet}} \approx 3.75 \text{ \AA}$, $d_{\text{intralayer}} \approx 3.65 \text{ \AA}$, and $d_{\text{interlayer}} \approx 5.69 \text{ \AA}$. For our analysis we may ignore the intralayer interactions in the same double-layer because (Figure 7c) this interaction (J_2) should be small since a positional shift in the triangular network frustrates the intralayer magnetic coupling. Therefore, we will limit ourselves to comparing the $d_{\text{intrasheet}}$ (J_1) and $d_{\text{interlayer}}$ (J_3) interactions. Given that the NCN^{2-} anion is between the Tb^{3+} ions in different layers, these are relatively far away from each other, so a small value of J_3 can be expected compared to J_1 . In fact, this can be seen if comparing the scale of the dipolar interactions^[65–68] $D = \frac{-\mu_0 \mu_{\text{eff}}^2}{4\pi R^3}$ (here R is the Tb–Tb distance) from which $D_1 / D_3 = 6.01 \text{ K} / 1.72 \text{ K} = 3.49$ is obtained, reinforcing the idea of a two-dimensional system with magnetic moments located on the triangular lattice. Furthermore, the frustration index $f = |\theta_{\text{CW}} / T_N| = 2.55$ of $\text{Tb}_2\text{O}_2\text{NCN}$ reflects a geometrically frustrated system according to the criteria established by Ramirez.^[69,70] Given that magnetic ordering is observed at low temperature, however, we can conclude that such geometrical frustration does not completely hinder the emergence of magnetic ordering in $\text{Tb}_2\text{O}_2\text{NCN}$.

Isothermal magnetization measurements (Figure 8a) in the range of $\mu_0 H = 0\text{--}9$ T at various temperatures show a lack of saturation, indicative of magnetocrystalline anisotropy. The slow relaxation dynamics of $\text{Tb}_2\text{O}_2\text{NCN}$ was studied by AC susceptibility measurements at 2 K. In a zero DC field with an AC field of 5 Oe in the frequency range of 10–10000 Hz, a clear dependence of the out-of-phase component of the susceptibility (χ'') on the frequency is revealed, although without the presence of any maximum in the measurement range. Fitting simultaneously χ' and χ'' to a generalized Debye model^[71–74] (see Supplementary Information for more details) allows us to extract (Figure 8b and 8c) the characteristic magnetic relaxation time of $\tau_0 \approx 5.7 \mu\text{s}$ and a parameter $\alpha = 0.01$, indicating that the relaxation of the magnetic



configurations takes place simultaneously. Additionally, the curves $M(H)$ at temperatures between 2.5–8 K show a slope change at ≈ 1.8 T that becomes evident when comparing the behavior at low and high magnetic fields, clearly observed in the $\partial M/\partial H$ plot of Figure 8a, which typically suggests a metamagnetic transition. To confirm and determine the nature of the magnetic transition, the $M-H$ data were converted into $M^2-\mu_0 H/M$ curves (Arrott plot) depicted in Figure 8d. According to the Banerjee criterion,^[75] a negative slope in the Arrott plot would indicate a first-order magnetic transition.

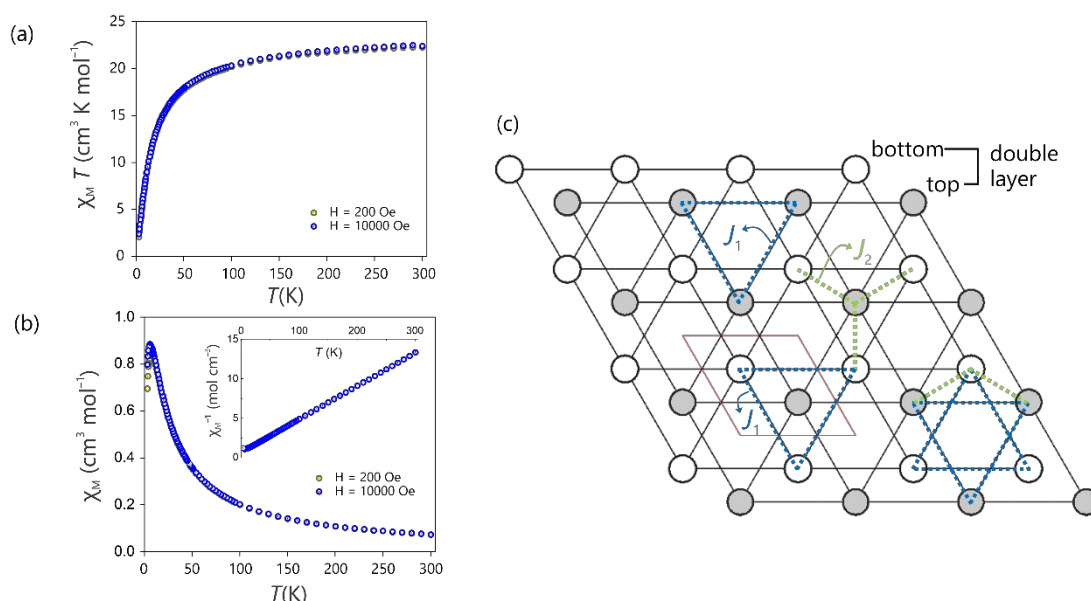


Figure 7. (a) Temperature dependence of $\chi_M T$ for $\text{Tb}_2\text{O}_2\text{NCN}$ at $H = 200$ Oe and 10 kOe. (b) Magnetic susceptibility vs. temperature under an applied field of 200 Oe and 10 kOe. Inset: inverse of susceptibility (χ^{-1}) showing Curie–Weiss behavior. (c) Projection of the double-layer down the c -axis showing only terbium atoms. Empty and filled circles represent the Tb on the different sheets of the double layer, bottom and top, respectively. The unit cell is shown in red. The Tb–Tb intrasheet (J_1) and intralayer (J_2) magnetic interactions are indicated in blue and green, respectively.



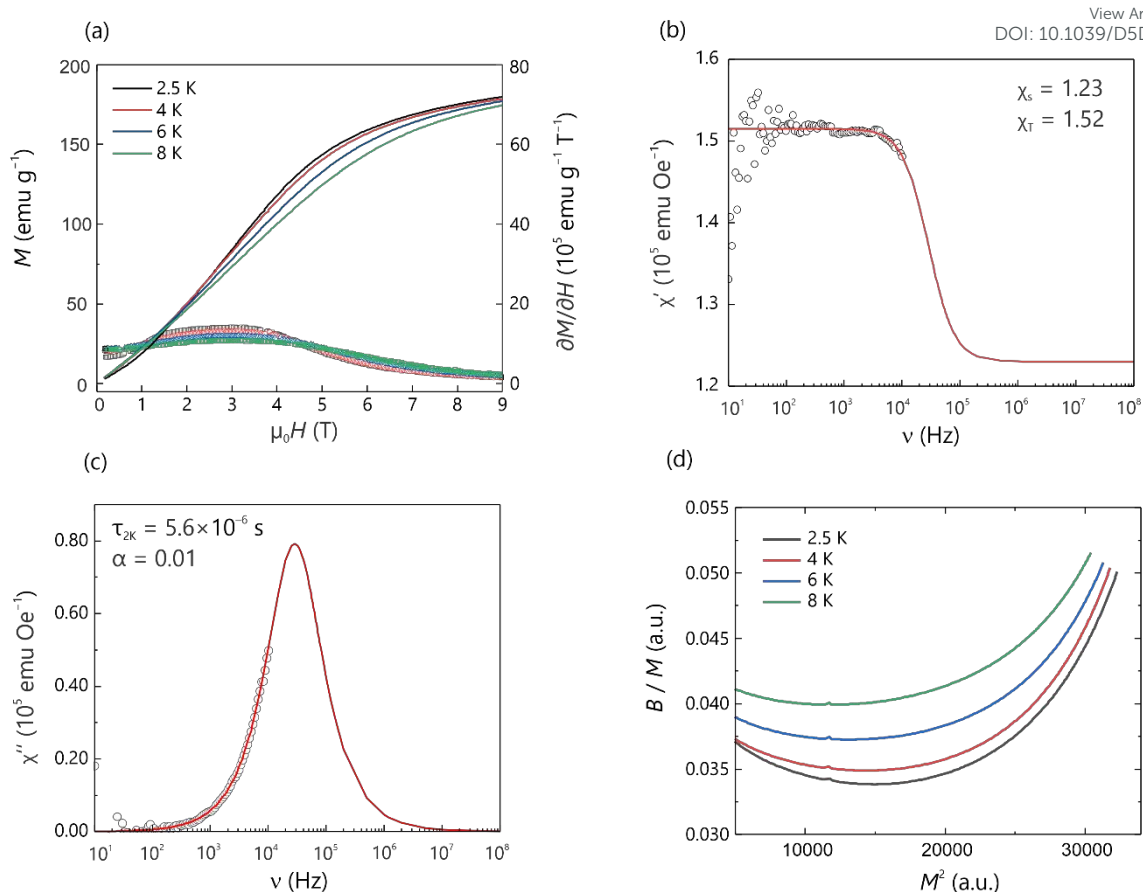


Figure 8. (a) Field-dependent magnetization curves of $\text{Tb}_2\text{O}_2\text{NCN}$ at various temperatures. The right ordinate axis represents $\partial M/\partial H$ as a function of the field, revealing the metamagnetic transition at ≈ 1.8 T. Frequency dependence of the in-phase, χ' (b) and out-of-phase, χ'' (c) magnetic susceptibility at 2 K. Solid lines correspond to the best fit to the Debye generalized model. (d) Arrott plots calculated from the M – H curves.

These characteristics in the behavior of the $M(H)$ curves, together with the fact that $\text{Tb}_2\text{O}_2\text{NCN}$ has a high magnetic density ($2 \times M_{\text{Tb}} / M_{\text{w}} = 0.82$) and is also magnetically reversible (no magnetic hysteresis, see Figure S3), make it particularly attractive for magnetic refrigeration applications. The magnetocaloric performance was evaluated by means of the magnetic entropy change ($-\Delta S_{\text{M}}$), calculated from the isothermal magnetization curves using the Maxwell equation $\Delta S_{\text{M}} = \mu_0 \int_0^H \left(\frac{\partial M}{\partial T} \right)_H dH$.^[76–80] Figure 9a depicts the magnetic entropy change curves as a function of temperature in the 1–7 T range. The maximum $-\Delta S_{\text{M}}$ at low field (3 T) reaches a value of $\approx 3.6 \text{ J kg}^{-1} \text{ K}^{-1}$ while in high field (7 T) a maximum of $\approx 21.1 \text{ J kg}^{-1} \text{ K}^{-1}$ is observed, but still far from the theoretical maximum of $-\Delta S_{\text{M}} = nR \ln(2J + 1) / M_{\text{w}} \approx 109.0 \text{ J kg}^{-1} \text{ K}^{-1}$ (here, n is the number of magnetic centers, R is the gas constant and M_{w} represents the formula



weight).^[57] A comparison of the magnetocaloric performance of $\text{Tb}_2\text{O}_2\text{NCN}$ with other Tb-based compounds is summarized in Table 1, together with sketches of the magnetic sublattices in Figure 9b. These compounds can be grouped according to the dimensionality of the connected terbium ions. In the group of compounds with 3D ordering, TbCrO_4 stands out: the TbO_8 polyhedra are arranged in the tetragonal zircon (ZrSiO_4) structure, with $\text{Tb-Tb} \approx 3.9 \text{ \AA}$ and a maximum magnetic entropy change of $16.2 \text{ J kg}^{-1} \text{ K}^{-1}$ at 23 K .^[81] In turn, in TbBO_3 , 2D triangular nets of Tb^{3+} are observed forming monolayers with intra- and inter-layer distances of 3.8 \AA and 4.4 \AA , respectively, with a value of $-\Delta S_M$ of $5.97 \text{ J kg}^{-1} \text{ K}^{-1}$ at 2 K .^[82] In $\text{LiTbP}_4\text{O}_{12}$, terbium ions form 1D channels with intra- and inter-channel distances of 5.6 \AA and 6.4 \AA , the maximum value of $-\Delta S_M$ being $15.9 \text{ J kg}^{-1} \text{ K}^{-1}$ at 2 K .^[83] $\text{Tb}_2\text{O}_2\text{NCN}$, however, with a double layer arrangement and intra- and inter-layer distances of 3.75 \AA and 5.69 \AA , far surpasses all their performances under the same applied field and temperature. Apparently, the effect of magnetic frustration compensation on Tb-Tb interactions in this type of structure plays an important role. We conclude that $\text{Tb}_2\text{O}_2\text{NCN}$ would be an excellent candidate for practical application as a cryogenic refrigerant.

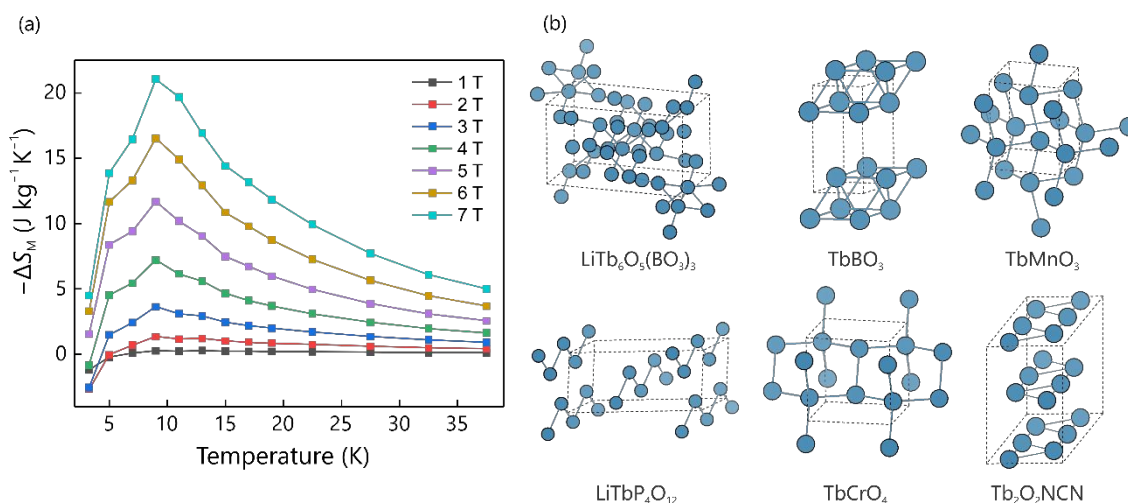


Figure 9. (a) Magnetic entropy change ($-\Delta S_M$) as a function of temperature at several magnetic field changes in the range 1–7 T. (b) Selected Tb-based magnetic refrigeration materials with Tb–Tb networks showing 1D, 2D, and 3D structural dimensionality.



Table 1. Structural characteristics and magnetic features of selected Tb-based compounds

Material	θ_{CW} (K)	T_{N} (K)	$-\Delta S_{\text{M}}$ (J kg ⁻¹ K ⁻¹) at 5 T ^[a]	Tb-arrangement
TbCrO ₄ ^[81]	-	22.1	16.2 ($T = 23$ K)	3D framework
TbBO ₃ ^[82]	-11.0	< 2	5.97 ($T = 2$ K)	2D layers
LiTbP ₄ O ₁₂ ^[83]	0.86	< 2	15.9 ($T = 2$ K)	1D channels
LiTb ₆ O ₆ (BO ₃) ₃ ^[84]	-12.4	< 2	6.58 ($T = 4$ K)	3D framework
TbMnO ₃ ^[85]	-	7.0	6.75 ($T = 16$ K)	3D framework
Tb ₂ O ₂ NCN ^[b]	-16.6	6.5	11.7 ($T = 9$ K)	2D double layers

^[a] At 2 T for LiTb₆O₆(BO₃)₃^[b] This work.

At this point, it is clear that the arrangement of Tb³⁺ ions in the Tb₂O₂NCN structure plays a key role in determining the properties even though it is not only the arrangement: the interatomic communication may perhaps be even more decisive. Hence, the density of states (DOS) and crystal orbital Hamilton population (COHP) for the interactions involving Tb were calculated to analyze the electronic structure of Tb₂O₂NCN (Figure 10). From the local DOS, the expected, dominant contribution of the N 2p and O 2p levels is seen at the valence band maximum (VBM) between -2.5 and 0 eV, while the conduction band minimum (CBM), between 3.75 and 5 eV, is Tb-centered. The Crystal Orbital Hamilton Populations (COHP) for Tb–X (X = Tb, O, N) interactions shows that Tb–O bonds are stronger than Tb–N bonds (a higher value in the integrated COHP), while, curiously, Tb–Tb interactions show a bonding character in the empty conduction band, unlike Tb–O and Tb–N interactions. This suggests that under excitation at 270 nm (≈ 4.45 eV) Tb–Tb communication (i.e., the energy migration process in luminescence) would take place directly (attractively in terms of Tb–Tb but not necessarily reducing terbium) and not through O²⁻ or NCN²⁻. In contrast, the strong bonding character of the Tb–N bond near the Fermi level (E_{F}) indicates that Tb–Tb magnetic interactions will occur through the NCN²⁻ unit, thus explaining the communication of the triangular nets of different layers when long-range magnetic order is established.



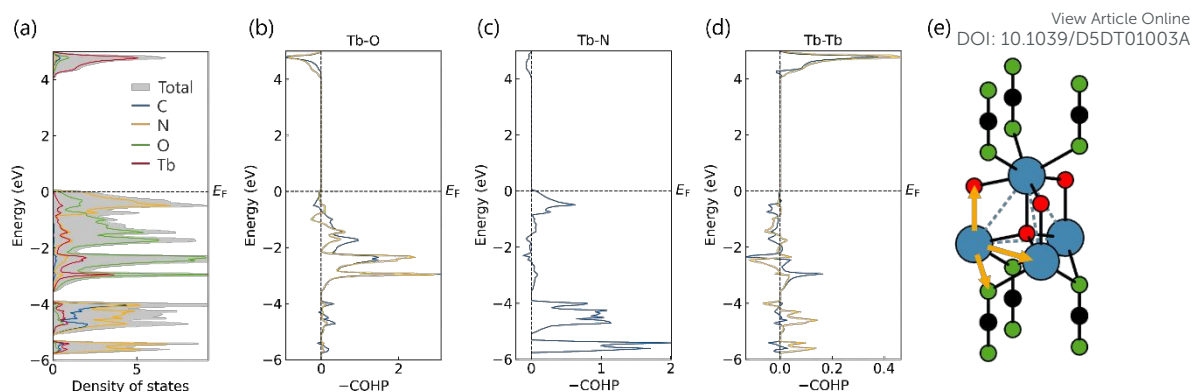


Figure 10. (a) Total and local density of states of Tb₂O₂NCN. The Fermi level (E_F) is set to zero. COHP for Tb–Tb (b), Tb–O (c) and Tb–N (d) interactions. In all cases blue and orange lines represent interactions between nearest and second-nearest neighbours, respectively. (e) Possible communication pathways between terbium atoms: direct or via oxygen or the N of the NCN²⁻ unit.

Conclusions

Both spectroscopic and magnetic investigations on solid-state Tb₂O₂NCN have allowed us to explore its potential for luminescent thermometry and magnetic refrigeration applications at low temperatures. The crystal structure can be understood as a two-dimensional system, formed by alternating layers of the extended NCN²⁻ anion and [Tb₂O₂]²⁺ which, in turn, consist of a double-layer of Tb triangular lattice, all stacked along the [001] direction. Thanks to its anti-thermal quenching behavior, Tb₂O₂NCN is suitable for optical thermometry using appropriate thermometric parameters offering good sensitivity ($S_r > 1\% \text{ K}^{-1}$) and precision ($\delta T > 1 \text{ K}$). In addition, the option of an instantaneous, linear and simple thermometry has been explored that allows covering a wider temperature range thanks to dimensionality reduction (PCA) offering better performance. In turn, magnetic investigations show that Tb₂O₂NCN contains magnetic frustration between Tb³⁺ ions. This frustration is topological, a consequence of the arrangement geometry, since the Tb-triangular lattices are shifted from each other in the double-layer, separated by the large NCN²⁻ anion. Given the comparatively large Tb³⁺ magnetic moment, however, the frustration is insufficient to suppress the magnetic order observed from $T_N = 6.5 \text{ K}$. Furthermore, magnetocalorics of Tb₂O₂NCN was investigated, thanks to first-order metamagnetic transitions taking place at around 1.8 T. The maximum for the magnetic entropy change achieves $-\Delta S_M \approx 21.1 \text{ J kg}^{-1} \text{ K}^{-1}$ at 7 T. Furthermore, $-\Delta S_M \approx 11.7 \text{ J kg}^{-1} \text{ K}^{-1}$ at 5 T is considerably



larger than those reported for other materials incorporating trivalent terbium under the same magnetic field change and temperature. These excellent results establish that $\text{Tb}_2\text{O}_2\text{NCN}$ is an extremely promising material for applications in thermometry and magnetic refrigeration.

Experimental Section

Synthesis

Preparation of $\text{Tb}_2\text{O}_2\text{NCN}$

The stoichiometric terbium oxide carbodiimide, $\text{Tb}_2\text{O}_2\text{NCN}$, was prepared on a 0.4 g scale by solid-state metathesis reaction between TbOCl and Li_2NCN in a 2 : 1 molar ratio under argon protective atmosphere. The mixture was homogenized using a mortar and pestle agate, transferred into an open dry glass capillary and loaded into a glass ampoule. The sample was heated in a horizontal tubular furnace at 600 °C under flowing argon for 18 h, with heating and cooling rates of 2 °C/min. The product is an air-stable powder which was washed several times with water and acetone to remove the LiCl metathesis salt, finally dried in air at 100 °C.

Powder X-ray diffraction analysis

Powder X-ray diffraction data of washed $\text{Tb}_2\text{O}_2\text{NCN}$ were collected employing a STOE STADI-P powder diffractometer with a flat sample holder ($\text{Cu-K}_{\alpha 1}$, linear PSD, $2\theta = 4\text{--}120^\circ$ with individual steps of 0.015°). Rietveld refinement was performed using GSAS II.^[86] In the final cycles of least-squares refinement, lattice parameters, fractional coordinates, site-occupancy factors and isotropic thermal displacement parameters (U_{iso}) were refined for all atoms with a constrained U_{iso} for chemically reasonable sorts of atoms, in particular all C and N atoms.

Luminescence Spectroscopy

Excitation and emission spectra of $\text{Tb}_2\text{O}_2\text{NCN}$ sample were recorded using a fluorescence spectrometer FLS920 (Edinburgh Instruments) equipped with a 450 W xenon discharge lamp (OSRAM) as the radiation source. For the data collection, a R2658P single-photon-counting photomultiplier tube from Hamamatsu was used. For temperature adjustment a cryostat "MicrostatN" from Oxford Instruments had been



mounted on the spectrometer. Liquid nitrogen was used as a cooling agent. The photoluminescence decay curves were also recorded on the FLS920 spectrometer, while a 270 nm laser diode from Edinburgh Instruments was used as an excitation source.

Magnetic measurements

Magnetic susceptibility measurements of powderous $\text{Tb}_2\text{O}_2\text{NCN}$ were performed using a Quantum Design SQUID MPMS-XL magnetometer. Samples were placed in PTFE containers and data were recorded in the temperature range 4–300 K in a field of 200 Oe. Magnetization data were collected at several temperatures in the field range $0 \leq \mu_0 H(\text{T}) \leq 9$. The AC magnetic susceptibility measurements were performed in a PPMS-DynaCool system using the vibrating sample magnetometry option in an oscillating AC field of 5 Oe with frequencies from 10 Hz to 10 kHz in a zero-DC field. The magnetic susceptibilities were corrected for the sample holder and the intrinsic diamagnetic contribution of the compound ($\chi_{\text{M,dia}} = -1.95 \times 10^{-4} \text{ cm}^3 \text{ mol}^{-1}$).

Dimensionality reduction

Before performing the PCA, the data in the X matrix (18 observations \times 251 wavelengths) were pre-processed. First, each observation (i.e., each row) was normalized using the intensity maximum, and subsequently each column was adjusted to the normal distribution by the transformation $z = \frac{x-\mu}{\sigma}$. The resulting matrix Z served as input for PCA. In overall, PCA is a technique that transforms a set of correlated variables p in a new set of independent variables q , denominated as principal components. The first stage involves the calculation of the covariance matrix and then, the eigenvalues and eigenvectors are determined, sorted in descending order according to their eigenvalues. The number of principal components was determined by using the scree plot as criterion (Figure S4).

Computational details

Density-functional theory calculations were performed using the Vienna *ab initio* simulation package (VASP, version 6.1.1).^[87,88] Projector augmented wave pseudopotentials with Perdew-Burke-Ernzerhof (PBE)^[89] parameterization were used. The generalized gradient approximation (GGA)^[90] scheme was chosen for treating



both electron exchange and correlation. 800 eV was set as the cutoff for the plane wave basis set. A Γ -centered Monkhorst-Pack k point mesh was used throughout for sampling the first Brillouin zone, the distance between two adjacent k points being always below $2\pi \times 0.02 \text{ \AA}^{-1}$. The experimentally obtained structure was first optimized on this level of theory until energy and force differences between consecutive iterations fell below thresholds of 10^{-8} eV and $10^{-6} \text{ eV \AA}^{-1}$, respectively. Gaussian smearing with 0.02 eV as the smearing width was set to treat partial occupancies for each orbital. It is worth noting that, due to the well-known self-interaction errors, the 4f orbitals of Tb were downfolded in the core, and a special “trivalent” GGA potential (designated Tb_3) was used. Following the structure optimization, self-consistent field (SCF) calculations were carried out. Only time-reversal symmetry was considered during the SCF calculations and tetrahedron method with Blöchl corrections^[91] was utilized for Brillouin zone integration. Wavefunctions were written out by the end of SCF calculations. Subsequently, a reciprocal space unitary transformation^[92] was performed by using the Local-Orbital Basis Suite Towards Electronic Structure Reconstruction (LOBSTER, version 5.1.1)^[93,94] suite to extract both density of states (DOS) and chemical-bonding information. The outputs from LOBSTER were automatically postprocessed by LOBSTER’s postprocessor (LOPOSTER).^[95]

Supplementary Information

Supplementary information is available free of charge at xxxxx.

Author Contributions

All authors have accepted responsibility for the entire content of this submitted manuscript and approved the submission.

Conflict of Interest

The authors declare no conflicts of interest regarding this article.

Acknowledgments

We thank Mr T. Storp for his assistance with PXRD measurements and Ms C. Houben for her assistance with magnetic measurements. J. Medina-Jurado is grateful for the



financial support from Deutscher Akademischer Austauschdienst (DAAD). A. Corkett is indebted to the Deutsche Forschungsgemeinschaft (DFG) for funding (project number 441856704).

Keywords

oxide carbodiimide, terbium, thermometry, thermal quenching, magnetocaloric effect, dimensionality reduction.

References

- [1] A. J. Corkett, O. Reckeweg, R. Pöttgen and R. Dronskowski, *Chem. Mater.*, 2024, **36**, 9107–9125.
- [2] M. Becker and M. Jansen, *Acta Crystallogr.*, 2001, **C57**, 347–348.
- [3] X. Liu, M. Krott, P. Müller, C. Hu, H. Lueken and R. Dronskowski, *Inorg. Chem.*, 2005, **44**, 3001–3003.
- [4] X. Liu, R. Dronskowski, R.K. Kremer, M. Ahrens, C. Lee and M.-H. Whangbo, *J. Phys. Chem. C*, 2008, **112**, 11013–11017.
- [5] X. Liu, L. Stork, M. Speldrich, H. Lueken and R. Dronskowski, *Chem. Eur. J.*, 2009, **15**, 1558–1561.
- [6] M. Krott, X. Liu, B.P.T. Fokwa, M. Speldrich, H. Lueken and R. Dronskowski, *Inorg. Chem.*, 2007, **46**, 2204–2207.
- [7] S.K. Deb and A.D. Yoffe, *Trans. Faraday Soc.*, 1959, **55**, 106–113.
- [8] M. Becker, J. Nuss and M. Jansen, *Z. Naturforsch.*, 2000, **55b**, 383–385.
- [9] E. Leysour de Rohello, Y. Suffren, O. Merdignac-Conanec, O. Guillou, C. Calers and F. Chevre, *J. Solid State Chem.*, 2021, **300**, 122240.



- [10] M. Kubus, C. Castro, D. Enseling and T. Jüstel, *Opt. Mater.*, 2016, **59**, 126– 129
- [11] M. Krings, G. Montana, R. Dronskowski and C. Wickleder, *Chem. Mater.*, 2011, **23**, 1694– 1699
- [12] Y. Masubuchi, S. Nishitani, A. Hosono, Y. Kitagawa, J. Ueda, S. Tanabe, H. Yamane, M. Higuchi and S. Kikkawa, *J. Mater. Chem. C*, 2018, **6**, 6370– 6377.
- [13] D. Dutczak, M. Ströbele, D. Enseling, T. Jüstel and H.-J. Meyer, *Eur. J. Inorg. Chem.*, 2016, **25**, 4011– 4016.
- [14] J. Glaser, L. Unverfehrt, H. Bettentrup, G. Heymann, H. Huppertz, T. Jüstel and H.-J. Meyer, *Inorg. Chem.*, 2008, **47**, 10455– 10460.
- [15] D. Dutczak, A. Siai, M. Ströbele, D. Enseling, T. Jüstel, and H.-J. Meyer, *Eur. J. Inorg. Chem.*, 2020, **41**, 3954– 3958.
- [16] E. Säilynoja, M. Lastusaari, J. Hölsä and P. Porcher, *J. Lumin.*, 1997, **72**, 201– 203.
- [17] J. Hölsä, R.-J. Lamminmäki, M. Lastusaari, P. Porcher and E. Säilynoja, *J. Alloys Compd.*, 1998, **275**, 402–406.
- [18] J. Hölsä, R.-J. Lamminmäki, M. Lastusaari, E. Säilynoja, P. Porcher, P. Dereñ and W. Stręk, *Spectrochim. Acta, Part A*, 1998, **13**, 2065–2069.
- [19] M. Takahashi, Y. Hashimoto, S.I. Kikkawa and H. Kobayashi, *J. Soc. Mater. Sci.*, 2000, **11**, 1230–1234.
- [20] T. Takeda, N. Hatta and S. Kikkawa, *Chem. Lett.*, 2006, **9**, 988– 989.
- [21] M. Kubus, R. Heinicke, M. Ströbele, D. Enseling, T. Jüstel, and H.-J. Meyer, *Mater. Res. Bull.*, 2015, **62**, 37–41.



- [22] J. Medina-Jurado, H. Bourakhouadar, Y. Wang, A.J. Corkett, D. Enseling, T. Jüstel and R. Dronskowski, *Chem. Mater.*, 2025, **37**, 2506–2515.
- [23] Y. Hashimoto, M. Takahashi, S. Kikkawa and F. Kanamaru, *J. Solid State Chem.*, 1996, **125**, 37.
- [24] M. Li, W. Yuan, J. Wang and C. Gu, *Powder Diffr.*, 2007, **22**, 59.
- [25] J. Sindlinger, J. Glaser, H. Bettentrup, T. Jüstel and H.-J. Meyer, *Z. Anorg. Allg. Chem.*, 2007, **633**, 1686–1690.
- [26] L. Wang, S. Yuan, Y. Yang, F. Chevre, F. Tessier and G. Chen, *Opt. Mater. Express*, 2015, **5**, 2616–2624.
- [27] A. Ansari, A. Parchur, M.K. Nazeeruddin and M. Tavakoli, *Coord. Chem. Rev.*, 2021, **444**, 214040.
- [28] M. D. Dramićanin, *J. Appl. Phys.*, 2020, **128**, 040902.
- [29] Y. Shen, X. Han, S. Wang, H. Yu and H. Zhang, *Inorg. Chem.*, 2025, **64**, 133–141.
- [30] R.M. Diaz-Rodriguez, D.A. Gálico, D. Chartrand, E.A. Sutura and M. Murugesu, *J. Am. Chem. Soc.*, 2022, **144**, 912–921.
- [31] D.K. Amarasinghe and F.A. Rabuffetti, *Chem. Mater.*, 2019, **31**, 10197–10204.
- [32] M. Suta, Ž. Antić, V. Đorđević, S. Kuzman, M.D. Dramićanin and A. Meijerink, *Nanomater.*, 2020, **10**, 543.
- [33] X. Liu, A. Skripka, Y. Lai, Y. *et al.*, *Nat Commun*, 2021, **12**, 6401.
- [34] S. Wang, Y. Xu, T. Chen, W. Jiang, J. Liu, X. Zhang, W. Jiang and L. Wang, *Chem. Eng. J.*, 2021, **404**, 125912.



- [35] P. Dang, W. Wang, H. Lian, G. Li and J. Lin, *Adv. Optical Mater.*, 2022, **10**, 2102287.
- [36] K. Karachousos-Spiliotakopoulos, V. Tangoulis, N. Panagiotou, A. Tasiopoulos, V. Nastopoulos, E. Moreno-Pineda, W. Wernsdorfer, M. Schulze, A. M.P. Botas and L.D. Carlos, *Inorg. Chem.*, 2022, **61**, 18629–18639.
- [37] J. Wang, J. J. Zakrzewski, M. Zychowicz, Y. Xin, H. Tokoro, S. Chorazy and S.-I. Ohkoshi, *Angew. Chem. Int. Ed.*, 2023, **62**, e202306372.
- [38] C. D. S. Brites, R. Marin, M. Suta, A. N. Carneiro-Neto, E. Ximendes, D. Jaque and L. D. Carlos, *Adv. Mater.*, 2023, **35**, 2302749.
- [39] Y. Ma, A. Aierken, Y. Wang and A. Meijerink, *J. Colloid Interface Sci.*, 2023, **638**, 640–649.
- [40] Y. Wang, L. Lei, R. Ye, G. Jia, Y. Hua, D. Deng and S. Xu, *ACS Appl. Mater. Interfaces*, 2021, **13**, 23951–23959.
- [41] K. Elzbieciak-Piecka and L. Marciniak, *Sci Rep*, 2022, **12**, 16364.
- [42] G. Brunet, R. Marin, M.-J. Monk, U. Resch-Genger, D. A. Gállico, F.A. Sigoli, E.A. Suturina, E. Hemmer and M. Murugesu, *Chem. Sci.*, 2019, **10**, 6799–6808.
- [43] Y. Cui, H. Xu, Y. Yue, Z. Guo, J. Yu, Z. Chen, J. Gao, Y. Yang, G. Qian and B. Chen, *J. Am. Chem. Soc.*, 2012, **134**, 3979–3982.
- [44] X. Shi, Y. Xue, Q. Mao, L. Pei, X. Li, M. Liu, Q. Zhang and J. Zhong, *Inorg. Chem.*, 2023, **62**, 893–903.
- [45] M. Back, J. Ueda, H. Nambu, M. Fujita, A. Yamamoto, H. Yoshida, H. Tanaka, M. Brik and S. Tanabe, *Adv. Opt. Mater.*, 2021, **9**, 2100033.



[46] J. Stefańska, A. Bednarkiewicz and L. Marciniak, *J. Mater. Chem. C*, 2022, **10**, 5744–5782. View Article Online
DOI: 10.1039/D1TD01003A

[47] Y.H. Wang, S. Yang, Q.F. Xu, C.L. Yang, S.F. Zhang, S. Y.J. Yu and M.M. Jiao, *J. Phys. Chem. C*, 2022, **126**, 15517–15527.

[48] P. Du, X. Huang and J. Yu, *Inorg. Chem. Front.*, 2017, **4**, 1987–1995.

[49] K. M. N. de Souza, R. N. Silva, J. A. B. Silva, C. D. S. Brites, B. Francis, R. A. S. Ferreira, L. D. Carlos and R. L. Longo, *Adv. Optical Mater.*, 2022, **10**, 2200770.

[50] Z. Liang, J. Wu and Y. Cui, *Light Sci Appl*, 2023, **12**, 36.

[51] K. Trejgis, K. Ledwa, K. Maciejewska *et al.*, *Sci Rep*, 2022, **12**, 5847.

[52] I.E. Kolesnikov, D.V. Mamonova, M.A. Kurochkin, M.A. Khodasevich, V.A. Medvedev, E.Y. Kolesnikov and A.A. Manshina, *J. Mater. Chem. C*, 2023, **11**, 14814–14825.

[53] Š. Dragutin *et al.*, *Tehnika*, 2020, **75**, 279–283.

[54] E. Ximendes, R. Marin, L.D. Carlos *et al.*, *Light Sci Appl*, 2022, **11**, 237.

[55] A. Rajčić, Z. Ristić, Z. J. Periša, B. Milićević, S. Aldawood, A.N. Alodhayb, Ž. Antić and M.D. Dramićanin, *Technologies*, 2024, **12**, 131.

[56] Z. Li, A. Arauzo, J.G. Planas and E. Bartolomé, *Dalton Trans.*, 2024, **53**, 8969–8979.

[57] B. Wang, X. Liu, F. Hu, J. Wang, J. Xiang, P. sun, J. Wang, J. Sun, T. Zhao, Z. Mo, J. Shen, Y. Chen, Q. Huang and B. Shen, *J. Am. Chem. Soc.*, 2024, **146**, 35016–35022.



- [58] J. Medina-Jurado, H. Bourakhouadar, A.J. Corkett, D. Enseling, T. Jüstel and R. Dronskowski, *Z. Anorg. Allg. Chem.*, 2025, e202400212. View Article Online
DOI: 10.1039/D5DT01003A
- [59] C. D. S. Brites, P. P. Lima, N. J. O. Silva, A. Millán, V. S. Amaral, F. Palacio and L. D. Carlos, *Nanoscale*, 2012, **4**, 4799–4829.
- [60] D. V. Lapaev, V. G. Nikiforov, V. S. Lobkov, A. A. Knyazev and Y. G. Galyametdinov, *J. Mater. Chem. C*, 2018, **6**, 9475–9481.
- [61] C. Ritchie, E.G. Moore, M. Speldrich, P. Kögerler and C. Boskovic, *Angew. Chem., Int. Ed.*, 2010, **49**, 7702.
- [62] K. Katoh, S. Yamashita, N. Yasuda, Y. Kitagawa, B.K. Breedlove, Y. Nakazawa and M. Yamashita, *Angew. Chem., Int. Ed.*, 2018, **57**, 9262.
- [63] H. Wang, Z. Zhu, L. La Droite, W. Liao, O. Cador, B. Le Guennic and J. Tang, *Chem. Sci.*, 2023, **14**, 7208.
- [64] S. Mugiraneza and A.M. Hallas, *Commun. Phys.*, 2022, **5**, 1.
- [65] N.P. Raju, M. Dion, M.J.P. Gingras, T.E. Mason and J.E. Greedan, *Phys. Rev. B*, 1999, **59**, 14489.
- [66] S.E. Palmer and J.T. Chalker, *Phys. Rev. B*, 2000, **62**, 488.
- [67] M.J.P. Gingras, C. Lacroix, P. Mendels and F. Mila, *Introduction to Frustrated Magnetism*. Springer: Berlin, 2011.
- [68] O.A. Petrenko and D. McK. Paul, *Phys. Rev. B*, 2000, **63**, 024409.
- [69] V. Biondo, P.C.W. Sarvezuk, F.F. Ivashita, K.L. Silva, A. Paesano Jr. and O. Isnard, *Mater. Res. Bull.*, 2014, **54**, 41–47.
- [70] A.P. Ramirez, *Ann. Rev. Mater. Sci.*, 1994, **24**, 453.



- [71] P.V. Madduri, S. Sen, B. Giri, D. Chakrabartty, S. Manna, S. Parkin and A. Nayak, *Phys. Rev. B*, 2020, **102**, 174402.
- [72] O. Pastukh, P. Konieczny, M. Laskowska, Ł. Laskowski, *Magnetochemistry*, 2021, **7**, 122.
- [73] M. Balanda, *Acta Phys. Polym.*, 2013, **124**, 964.
- [74] C.V. Topping and S.J. Blundell, *J. Phys.: Condens. Matter*, 2019, **31**, 013001.
- [75] B.K. Banerjee, *Phys. Lett.*, 1964, **12**, 16.
- [76] K.P. Shinde, S.H. Jang, J.W. Kim, M. Ranot and K.C. Chung, *Dalton Trans.*, 2015, **44**, 20386–20391.
- [77] M. Kumar, L. Li, J.K. Zareba, L. Tashi, S.C. Sahoo, M. Nyk, S. Liu and H. Sheikh, *Cryst. Growth Des.*, 2020, **20**, 6430–6452.
- [78] S.-J. Liu, S.-D Han, J.-P. Zhao, J. Xu and X.-H. Bu, *Coord. Chem. Rev.*, 2019, **394**, 39–52.
- [79] S.-J. Liu, C. Cao, S.-L. Yao, T.-F. Zheng, Z.-X. Wang, C. Liu, J.-S. Liao, J.-L. Chen, Y.-W. Li and H.R. Wen, *Dalton Trans.*, 2017, **46**, 64–70.
- [80] Y. Wang, H. Zhang, M.-L. Wu, K. Tao, Y.-W. Li, T. Yan, K.-W. Long, T. Long, Z. Pang and Y. Long, *Chinese Physics B*, 2016, **25**, 127104.
- [81] E. Palacios, M. Castro, J. Romero de Paz, J.M. Gallardo-Amores and R. Sáez-Puche, *J. Solid State Chem.*, 2022, **314**, 123356.
- [82] P. Mukherjee, Y. Wu, G.I. Lampronti and S.E. Dutton, *Mater. Res. Bull.*, 2018, **98**, 173–179.



- [83] D.N. Petrov, P.T. Long, Y.S. Koshkid'Ko, J. Ćwik and K. Nenkov, *J. Phys. D: Appl. Phys.*, 2020, **53**, 495005. View Article Online
DOI:10.1039/D5DP01003A
- [84] Y. Chen, W. Liu, J. Feng, R. Guo, F. Fan, J. Shen, G. Zhang and H. Tu, *Cryogenics*, 2022, **124**, 103476.
- [85] M. Staruch, K. Luna, A. McDannald and M. Jain, *J. Magn. Magn. Mater.*, 2015, **377**, 117–120.
- [86] B. Toby, *J. Appl. Crystallogr.*, 2001, **34**, 210.
- [87] G. Kresse and J. Furthmüller, *Phys. Rev. B*, 1996, **54**, 11169–11186.
- [88] G. Kresse and J. Furthmüller, *Comput. Mater. Sci.*, 1996, **6**, 15–50.
- [89] J.P. Perdew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, **77**, 3865–3868.
- [90] J.P. Perdew, J.A. Chevary, S.H. Vosko, K.A. Jackson, M.R. Pederson, D.J. Singh and C. Fiolhais, *Phys. Rev. B*, 1992, **46**, 6671–6687.
- [91] P.E. Blöchl, O. Jepsen and O.K. Andersen, *Phys. Rev. B*, 1994, **49**, 16223–16233.
- [92] S. Maintz, V.L. Deringer, A.L. Tchougréeff and R. Dronskowski, *J. Comput. Chem.*, 2013, **34**, 2557–2567.
- [93] S. Maintz, V.L. Deringer, A.L. Tchougréeff and R. Dronskowski, *J. Comput. Chem.*, 2016, **37**, 1030–1035.
- [94] R. Nelson, C. Ertural, J. George, V.L. Deringer, G. Hautier and R. Dronskowski, *J. Comput. Chem.*, 2020, **41**, 1931–1940.
- [95] Y. Wang, P.C. Müller, D. Schnieders and R. Dronskowski, in preparation.



Open Access Article. Published on 26 May 2025. Downloaded on 6/1/2025 5:02:18 AM.
This article is licensed under a Creative Commons Attribution 3.0 Unported Licence.



The data supporting this article have been included as part of the [Supplementary Information](#). [View Article Online](#)
DOI: 10.1039/D5DT01003A

