


# Energy & Environmental Science

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: Y. Wu, Z. chen, K. Shi, Y. Wang, X. Li, Z. Zhao, Q. Zhuang, J. Wang and M. Chen, *Energy Environ. Sci.*, 2025, DOI: 10.1039/D4EE06035K.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

## Broader context

In the rapidly evolving fields of battery technology and energy storage, polymer-based electrolytes are gaining extensive attention for achieving high-energy-density lithium metal batteries (LMBs) with high safety owing to their exceptional flexibility and manufacturability. However, for the inorganic filler, most studies focus on the simple mixture with polymer to decrease the crystallinity of polymer to reach higher ion conductivity. Meanwhile, seldom attentions have been paid on the interfacial ion transfer, which leads to higher barrier. In this work, as a proof-of-concept, an innovative conductive inorganic filler has been proposed to optimize the electrochemical performance of the quasi-solid-state polymer electrolytes of poly(vinylidene fluoride-co-hexafluoropropylene) (PVDF-HFP). More importantly, the lithiated phase transformation of inorganic filler into a lithiated  $\text{Li}_x\text{TiN}$  layer helps to accelerate the lithium salt dissociation, enhance the  $\text{Li}^+$  transport kinetics, and improve the interface compatibility, providing new insights for the design of advanced polymer electrolytes for high-performance LMBs.



## ARTICLE

# Fast Li<sup>+</sup> Transport Kinetics Enabled by TiN Nanofiber in Hybrid Polymer-based Electrolyte for Long-life Li Metal Batteries

Yixin Wu,<sup>a</sup> Zhen Chen,<sup>\*a</sup> Kai Shi,<sup>b,c</sup> Yang Wang,<sup>a</sup> Xian-Ao Li,<sup>a</sup> Ziqi Zhao,<sup>a</sup> Quan Zhuang,<sup>\*d</sup> Jian Wang,<sup>\*b,c</sup> and Minghua Chen<sup>\*a</sup>Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Polymer-based solid-state electrolytes exhibit superior advantages in flexibility, lightweight, and large-scale processability, rendering them promising for high-performance solid-state lithium metal batteries (SSLMBs) with enhanced safety. However, challenges like poor structural uniformity, sluggish Li<sup>+</sup> transport kinetics, and inferior interface compatibility hinder their practical applications. Herein, a hybrid quasi-solid-state electrolyte (PHLT) composed of titanium nitride (TiN) fibrous nanofiller and poly(vinylidene fluoride-co-hexafluoropropylene)/lithium bis(trifluoromethanesulfonyl)imide (PVDF-HFP/LiTFSI) matrix was developed. The inorganic filler could decrease the crystallinity of PVDF-HFP, propel the polar transformation of the polymer, as well as adsorb and immobilize the TFSI<sup>-</sup> anions, significantly enhancing Li-ion transport kinetics. Further, the in-situ generated fast Li-ion conductor, i.e., Li<sub>x</sub>TiN, derived from lithiated TiN, along with a smooth but dense LiF interphase, effectively bridges the electrolyte|electrode interface and suppresses Li dendrite growth. Consequently, the as-fabricated Li|PHLT|LiFePO<sub>4</sub> cells achieve exceptional cycling stability over 3000 cycles at 2 C with superior average Coulombic efficiency of 99.8%. Notably, this strategy also enables great compatibility with matching high-loading cathodes (9.5 mg cm<sup>-2</sup>), moreover, delivers impressive performance in large areal pouch cells as well as bilayer stacking cells. This work provides an innovative approach to constructing solid-state electrolyte with enhanced diffusion kinetics and interface compatibility, paving the way for practical SSLMB applications.

## Introduction

The increasing prevalence of lithium-ion batteries (LIBs) in electric vehicles and large-scale energy storage systems has led to surging demand for high energy density, safety standards, and long life. Compared to the commercial graphite anode, lithium metal anode exhibits an exceptionally high theoretical capacity (3860 mAh g<sup>-1</sup>) and the lowest reduction potential (-3.04 V vs. standard hydrogen electrode), rendering it the optimal choice for high-energy-density lithium metal batteries (LMBs).<sup>1-4</sup> However, the failures of LMBs have shown that metallic Li cannot operate safely and stably in traditional liquid electrolyte and polyolefin separator systems. The main issue can be attributed to the growth of lithium dendrites that lead to short circuits and possible thermal runaway or even explosions. Furthermore, traditional organic liquid electrolytes are plagued by high flammability and serious side reactions with active metallic Li.<sup>5,6</sup> As an alternative, solid-state electrolytes or quasi-solid-state electrolytes exhibit high mechanical strength and stability, inhibit the lithium dendrite growth, expand the

operating temperature range of batteries, and fundamentally eliminate the risk of electrolyte leakage.<sup>7,8</sup> Consequently, this advancement is expected to enable the realization of high energy density and high safety in LMBs.

Compared to the hard and brittle inorganic sulfide or oxides-based electrolytes, polymer-based electrolytes such as polyethylene oxide,<sup>9</sup> polyvinylidene fluoride (PVDF),<sup>10</sup> poly(vinylidene fluoride-co-hexafluoropropylene) (PVDF-HFP),<sup>11</sup> polyacrylonitrile,<sup>12</sup> exhibit superior flexibility and toughness as well as the ease of large-scale fabrication, attracting extensive attention and investigations. Among them, the PVDF-HFP stands out for its high dielectric constant ( $\epsilon_r$ : ~8–12), low crystallinity and superior thermal stability, making it highly suitable for a wide range of practical applications.<sup>13</sup> Nevertheless, there are still some limitations to be overcome, such as low ionic conductivity at room temperature, non-compact structure and interfacial parasitic reactions, which restrict their further development.

To address the above-mentioned challenges, numerous research approaches have been proposed including the utilization of electrolyte additives,<sup>14</sup> the regulation of electrolyte composition,<sup>15</sup> the grafting of polymer,<sup>6</sup> in-situ polymerization strategy,<sup>16</sup> and the incorporation of inorganic fillers.<sup>17</sup> Among these strategies, the integration of inorganic fillers has demonstrated the potential to harmonize the electrochemical properties and mechanical strength of the electrolyte. Currently, the main inorganic fillers focus on oxides, while few attentions are paid on utilizing nitride materials such

<sup>a</sup> Key Laboratory of Engineering Dielectric and Applications (Ministry of Education), School of Electrical and Electronic Engineering, Harbin University of Science and Technology, Harbin 150080, Heilongjiang, China

<sup>b</sup> Helmholtz Institute Ulm (HIU), 89081 Ulm, Germany

<sup>c</sup> Karlsruhe Institute of Technology (KIT), 76021 Karlsruhe, Germany

<sup>d</sup> Inner Mongolia Key Laboratory of Carbon Nanomaterials, Nano Innovation Institute (NII), College of Chemistry and Materials Science, Inner Mongolia Minzu University, Tongliao 028000, China



as BN, which shows exceptional insulating properties.<sup>18</sup> Meanwhile, the research on conductive transition metal nitride fillers remains scarce, likely due to concerns about their high electronic conductivity potentially compromising the insulating properties of electrolytes. However, recent studies have reported that the inclusion of conductive fillers does not necessarily impair the electronic insulation of electrolytes.<sup>19</sup> Instead, the surface polarization effect of conductive fillers can facilitate the dissociation of lithium salt in a manner analogous to high dielectric fillers.<sup>20</sup> The polarization phenomenon redistributes the interfacial electric field, weakens the Coulombic interaction between cations and anions, and amplifies the local electric field strength within the polymer matrix. Therefore, incorporating metal-based nitride fillers can effectively enhance Li salt dissociation, increase carrier concentration, and improve the electrochemistry performance of electrolytes. Furthermore, the gradual conductive-dielectric transition significantly promotes fast ion transport, enabling superior performance of the LMBs.

Herein, as a “proof-of-concept”, a dielectric PVDF-HFP based quasi-solid-state polymer electrolyte (QPE) integrating optimized TiN nanofiber fillers was proposed. The TiN fillers possess superior mechanical property, thermal conductivity, exceptional chemical/electrochemical stability, and metallic-like conductivity, effectively enhancing the comprehensive properties of the electrolyte. In this design, as exhibited in Fig. 1A, the incorporation of TiN nanofibers greatly promotes the dissociation of  $\text{LiN}(\text{SO}_2\text{CF}_3)_2$  (LiTFSI) and accelerates Li-ion kinetics through several aspects: 1) The stronger adsorption of TFSI<sup>-</sup> anions on the TiN (111) surface provides an “anchor effect” to restrict anion mobility; 2) TiN facilitates the phase transformation of PVDF into its  $\beta$ -phase, which features with a higher dielectric constant enabling reduced dissociation barrier; and 3) The surface of TiN is in-situ lithiated to form  $\text{Li}_x\text{TiN}$  layer during cycling, further enhancing Li-ion transport dynamics alongside the heterogeneous interfaces. Additionally, the high aspect ratio of fibrous TiN increases the proportion of organic-inorganic interfaces. Combined with the contribution from favored  $\beta$ -phase transformation, continuous and shortened Li-ion transport pathways are created for uniform and fast Li-ion flux, yielding substantially enhanced Li<sup>+</sup> transport kinetics. Consequently, these advantages enable stable operation of the Li||Li symmetric cells and Li||LiFePO<sub>4</sub> full cells. More impressively, the bipolar stacking cells and pouch cells also demonstrate excellent safety and stability, showcasing the practical feasibility of this design.

## Results and discussion

### Theoretical simulations of TiN fillers on the dissociation behavior of LiTFSI

Firstly, density functional theory (DFT) calculations were conducted to gain insights into the interactions and dissociation ability of LiTFSI on both the pristine PVDF-HFP chain segments and the TiN (111) crystal plane. Fig. 1B illustrates that the adsorption energy of TFSI<sup>-</sup> anions on PVDF-HFP is minimal at


only 0.02 eV. Conversely, TiN exhibits significantly stronger adsorption energy as high as 4.74 eV (Fig. 1C). Such adsorption is conducive to limiting the free movement of anions, thereby increasing the Li<sup>+</sup> transference number and reducing the polarization of the electrolyte. The charge density difference plots between LiTFSI/TFSI<sup>-</sup> and Ti atoms further reveal the interaction between TiN and TFSI<sup>-</sup> anions (Fig. 1D, E), evidenced by the charge accumulations between TFSI<sup>-</sup> and the O atoms. The interactions can also be corroborated by the projected density of states (PDOS) and crystal orbital Hamilton population (COHP) analyses. The hybridization between the electronic orbitals of O and Ti atoms is evident, aligning well with the COHP results, which show fully occupied bonding states for the Ti–O bonds. This suggests strong anion confining by TiN (Fig. 1F and S1). The bonding strength can be quantified by the integral COHP (ICOHP), which measures the energy-weighted population of bonding wave functions between two atomic orbitals. The larger absolute value of ICOHP reflects stronger bonding. For LiTFSI/TFSI<sup>-</sup> adsorption on the TiN (111) surface, two and five Ti–O bonds are formed with average length of 2.26 Å and 2.38 Å, corresponding well with the absolute ICOHP values of 1.67 and 1.34.

Due to the strong attraction exerted by TiN, the dissociation barrier for lithium salts is significantly reduced to 1.72 eV (Fig. 1G), which is considerably lower than that of the PVDF-HFP (5.71 eV, Fig. 1H)—approximately one-third of the barrier in the pristine polymer matrix. The above investigations and findings reveal that TiN is more conducive to decoupling LiTFSI and acting as an “anchor” for TFSI<sup>-</sup> as well, thereby reducing the interaction between Li<sup>+</sup> and TFSI<sup>-</sup>. Consequently, the utilization of TiN as a modified filler is anticipated to facilitate the dissociation of lithium salts, liberating a substantial amount of Li<sup>+</sup> ions, which in turn enhances the electrochemical properties of the electrolyte. Simultaneously, the confinement of TFSI<sup>-</sup> anions further contributes to improved ionic transport and stability, making TiN an effective additive for advancing solid-state lithium-ion battery performance.

### Structural characterizations of TiN nanofibers and electrolyte membranes

The TiN nanofibers retain the fibrous morphology, similar to the precursor (Fig. S2), with a diameter of approximately 500 nm (Fig. S3A). The structure is consistent with the X-ray diffraction (XRD) pattern of the Osbornite TiN phase (PDF #06-0642) (Fig. S3B). Ionic conductivity test demonstrates that the solid-state electrolyte incorporating 5 wt% TiN (denoted as PHLT) exhibits the highest ionic conductivity, ca., 1.29 mS cm<sup>-1</sup> (Fig. S4), which is four times higher than that of the PVDF-HFP electrolyte without fillers (PHL, 0.29 mS cm<sup>-1</sup>). As exhibited in Fig. 2A, the as-synthesized PHLT membrane appears much smoother and more compact, indicating the potential for tight electrolyte/electrode contact. Cross-sectional SEM images show that the thicknesses of PHL and PHLT are approximately 55 and 53 μm, respectively (Fig. 2B, S5). Notably, the long fibrous structure facilitates superior dispersibility of filler within the polymer matrix (Fig. S6).



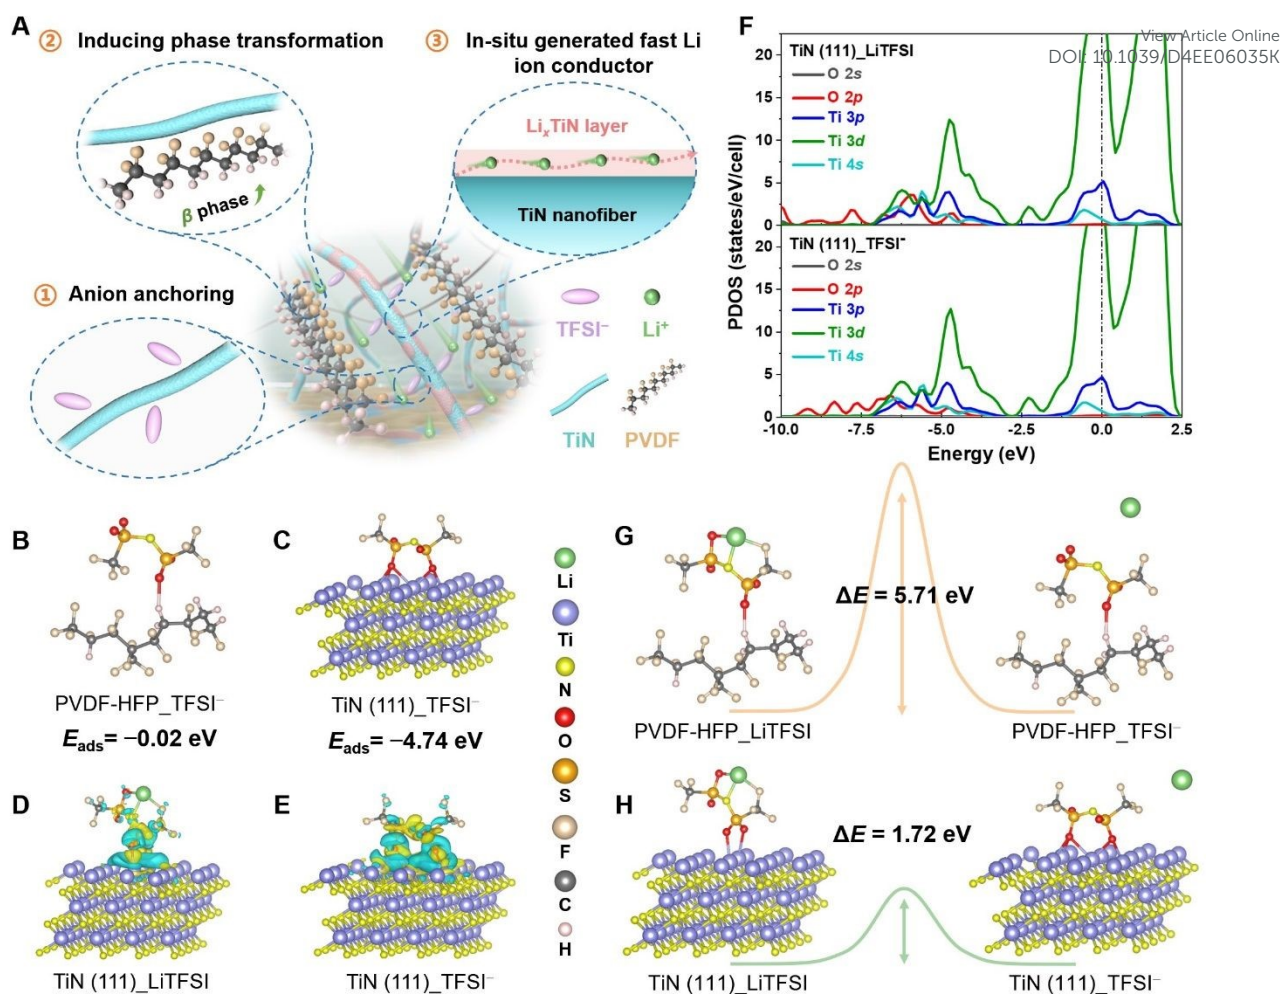


**Fig. 1** (A) Schematic diagram of the functions of TiN nanofibers in the electrolyte. The adsorption configurations of TFSI<sup>-</sup> anion on the (B) PVDF-HFP and (C) TiN (111). The calculated charge density difference for (D) LiTFSI and (E) TFSI<sup>-</sup> adsorption on TiN (111); Cyan and yellow iso-surfaces represent electron corresponding to charge density contours of  $-0.0025$  and  $+0.0025$  eÅ<sup>-3</sup>, respectively. (F) PDOS plots of LiTFSI and TFSI<sup>-</sup> on TiN (111). The dissociation energy barrier of LiTFSI on surfaces of (G) PVDF-HFP and (H) TiN (111), respectively.

For practical applications, the mechanical properties of electrolytes are crucial. Fig. S7 displays the optical photograph of PHLT possessing a smooth and dense morphology with excellent flexibility and foldability, which is beneficial for future flexible smart devices. The PHLT achieves a significantly higher mechanical toughness and strain of 5.78 MPa and 197.9% (Fig. S8), remarkably outperforming PHL (2.86 MPa and 17.1%). Even after wetting with liquid electrolyte, the PHLT still retains superior mechanical strength and improved ductility, ensuring effective dendrite suppression while maintaining excellent interfacial compatibility. Furthermore, the PHLT exhibits superior thermal conductivity, evidenced by uniform heat distribution and a minor temperature difference (Fig. S8), which is anticipated to balance the uneven electrochemical kinetics in space caused by thermal contrast. The decomposition temperature of PHLT is about 20 °C higher than that of the PHL, and the dimethyl formamide (DMF) contents in PHL and PHLT are less than 3 wt% (Fig. S9).<sup>21</sup> Fourier transform infrared spectrometer (FT-IR) results confirm that all DMF molecules are coordinated with Li<sup>+</sup> ions, ensuring their complete interaction with the electrolyte matrix (Fig. S10).

The lower crystallization of the polymer, the higher Li-ion transport kinetics. The XRD (Fig. S11, S12) and differential scanning calorimetry (DSC) analyses (Fig. S13) reveal that the crystallinity degree and crystallization temperature are simultaneously reduced in PHLT, suggesting that the TiN fillers facilitate the formation of amorphous regions to enhance the transport of Li<sup>+</sup>. Additionally, a shift from non-polar  $\alpha$ -phase (766 cm<sup>-1</sup>) to polar  $\beta/\gamma$ -phases (840 cm<sup>-1</sup>) is also witnessed by FT-IR, which is primarily attributed to the interactions between TiN and the dipole moment of the polymer (Fig. 2C). The proportion of  $\beta$ -phase and  $\gamma$ -phase can be determined by the absorbance peaks at 1276 and 1232 cm<sup>-1</sup>, respectively.<sup>22</sup> As estimated, the incorporation of TiN leads to decreased  $\alpha$ -phase and increased  $\beta$ -phase by 15.4% and 12.4%, respectively (Fig. 2D). Thus, the incorporation of TiN fillers in PHLT has profound effects on reducing the polymer crystallization and promoting favored composition of  $\beta$ -phase, enhancing Li-ion transport kinetics. Further, the polarity phase could enhance the dissociation of LiTFSI and shorten the Li<sup>+</sup> migration path, thereby reducing the diffusion barrier of Li<sup>+</sup> (Fig. 2E).<sup>23</sup> Raman analysis further reveals that the TFSI<sup>-</sup> anion presents a higher



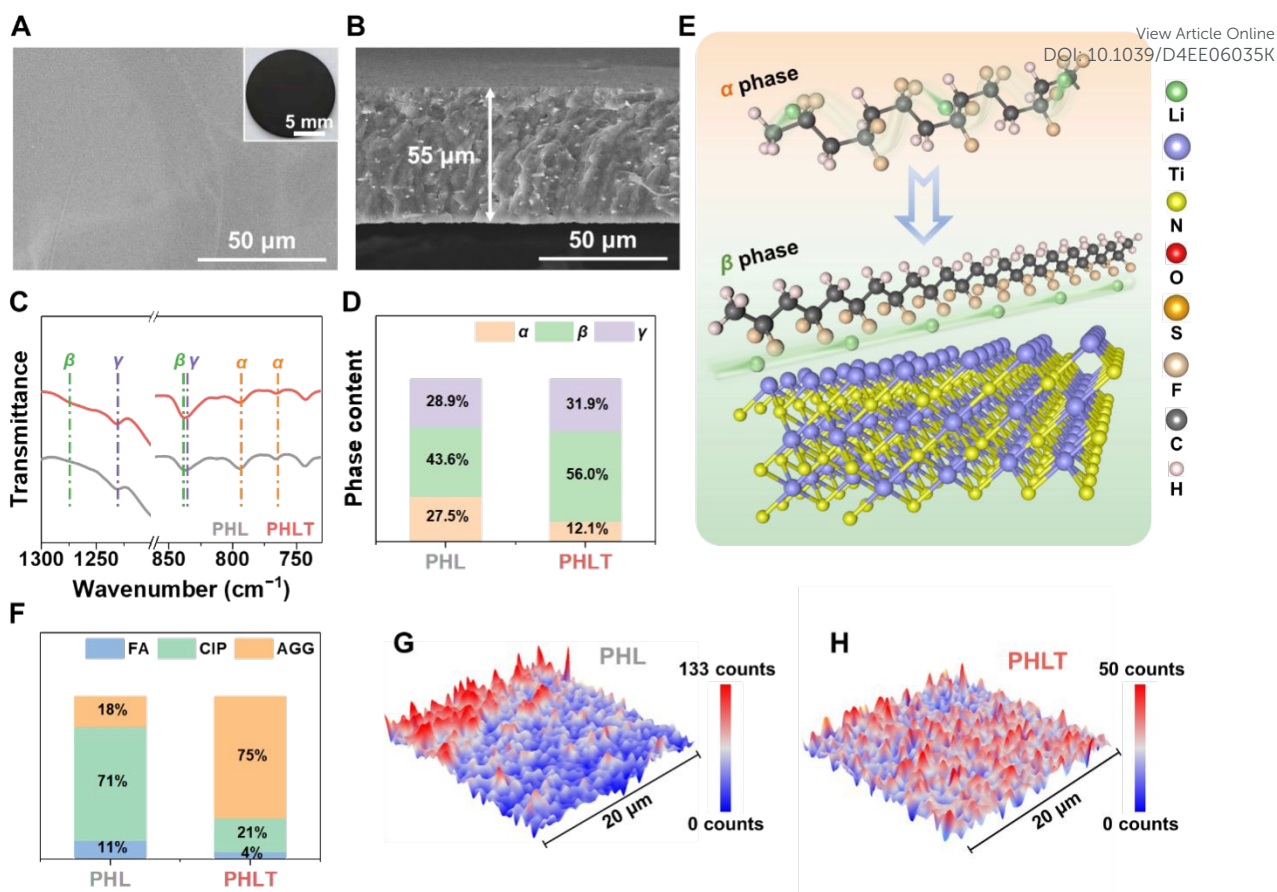

**Fig. 2** (A) The top-view and (B) cross-sectional scanning electron microscope (SEM) images of PHLT, respectively; the inset is an optical photograph. (C) FT-IR spectra and (D) the crystal phase content of PVDF in PHL and PHLT. (E) Schematic diagram of the conformational transformation of the polymer matrix and the facilitated  $\text{Li}^+$  transport pathway. (F) The corresponding Raman quantification results of the TFSI $^-$  state in the electrolytes. Raman mapping plots of the TFSI $^-$  signal at 730–760  $\text{cm}^{-1}$  of (G) PHL and (H) PHLT.

proportion of contact ion pairs (CIP, ~71%) and a lower proportion of free anion (FA) in PHL, indicating the weak dissociation of salt. The aggregate (AGG, ~75%) dominates in the PHLT, corresponding to the coupling between TFSI $^-$  and TiN (Fig. 2F, S14).

Furthermore, the Raman mapping of PHL reveals the presence of a lithium salt-enriched area, confirming that PHL has an uneven distribution of anions, leading to heterogeneous solid electrolyte interphase (SEI) structure and electrochemical performance (Fig. 2G). In contrast, PHLT shows a uniform distribution of anions (Fig. 2H), indicating consistent composition and electrochemical properties at the micrometer scale owing to the even dispersion of TiN fillers and their anchoring effect on TFSI $^-$  anions.

#### Evaluation of electrochemical properties and stability against Li metal anode

As expected, the PHLT not only demonstrates a higher ionic conductivity but also a reduced activation energy of 0.14 eV (Fig. 3A). The  $\text{Li}^+$  transference number ( $t_{\text{Li}^+}$ ) increases to 0.46 (Fig. 3B and S15) due to the “anchor” effect of TiN on anions. Notably, TiN fillers exhibit a negligible effect on the electronic conductivity of PHLT, ensuring it is sufficient to meet the requirement of batteries (Fig. S16 and Table S1). Furthermore,

the PHLT shows higher exchange current density of 0.142  $\text{mA cm}^{-2}$  and limiting current density up to 4.3  $\text{mA cm}^{-2}$ , surpassing those of PHL (Fig. 3C and S17). The electrochemical stability window of the PHLT is broadened to 0–4.89 V (Fig. 3D), and the flat cyclic voltammetry (CV) curves of Li|5%|stainless steel cells in the voltage range of 0–3 V and 3–5 V (Fig. S18) further confirm its superior electrochemical stability both towards oxidation and reduction reactions. The enhanced ionic conductivity facilitates efficient charge transfer at the electrode-electrolyte interface, reducing  $\text{Li}^+$  accumulation and minimizing localized overpotentials, thereby reducing the risk of localized oxidation. Additionally, TiN fillers promote anion anchoring, which inhibits their deposition and decomposition at the cathode side to some extent, further improving the oxidation stability of the electrolyte.<sup>24</sup> Subsequently, the critical current density (CCD) values are determined in Li||Li cells, as illustrated in Fig. 3E, F, and S19. In the time-constant mode, the CCD value increases from 0.6  $\text{mA cm}^{-2}$  to 0.85  $\text{mA cm}^{-2}$ . In the capacity-constant mode, PHLT exhibits CCD values of 3.1, 1.6, and 0.7  $\text{mA cm}^{-2}$  when the capacity set at 0.2, 0.5, and 1 mAh  $\text{cm}^{-2}$ , respectively, significantly higher than those of the PHL (2.1, 1.0, and 0.3  $\text{mA cm}^{-2}$ ). These enhanced CCD values highlight that TiN nanofibers reinforce the electrolyte's capability of inhibiting dendritic lithium growth. The PHLT-based Li symmetric cells operate stably over 1400 h at



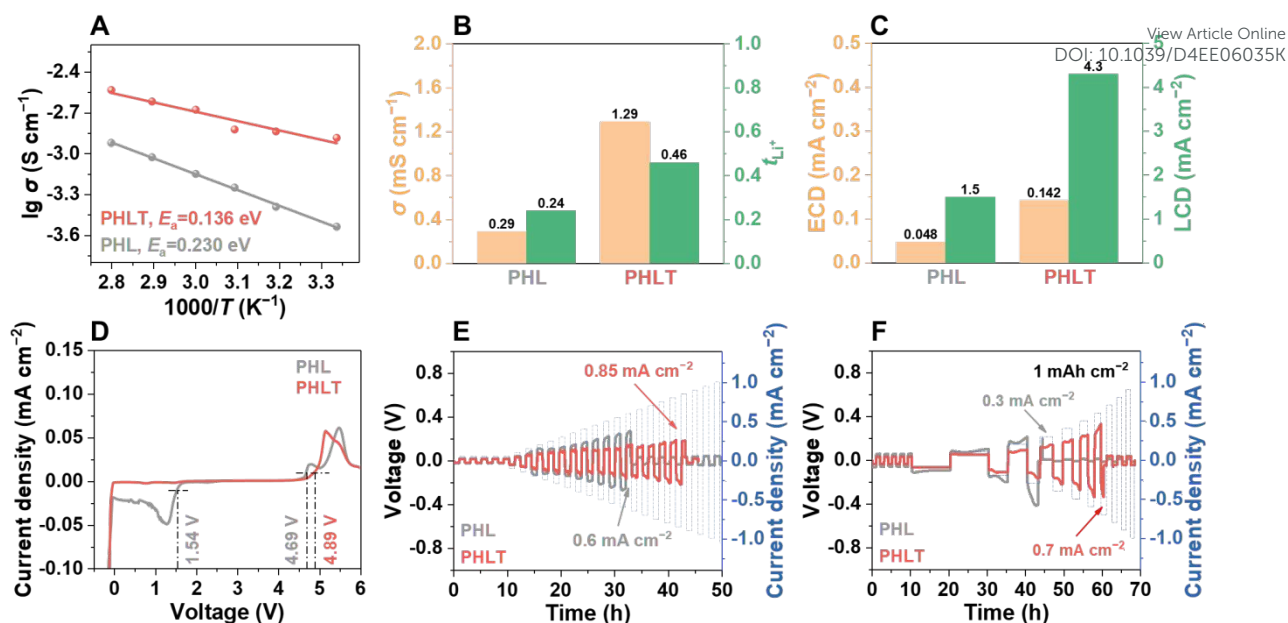


Fig. 3 (A) Arrhenius plots of the QPEs. (B) Ionic conductivity, Li<sup>+</sup> transference number, (C) exchange current density (ECD), limiting current density (LCD) results, (D) LSV curves, CCD tests using (E) time-constant mode (1 h for plating and 1 h for stripping), and (F) the capacity-constant mode (1 mAh cm<sup>-2</sup>) at 25 °C, respectively.

0.1 mA cm<sup>-2</sup> (Fig. 4A), significantly outlasting the Li|PHL|Li symmetric cell (376 h, Fig. S20). Increasing the current density to 0.2 mA cm<sup>-2</sup>, the Li|PHLT|Li symmetric cell still enables a longer life (Fig. S21) with smaller resistances (Fig. S22). To investigate the complex interfacial evolution and kinetics characteristic, electrochemical impedance spectroscopy (EIS) was further analyzed by the distribution of relaxation times (DRT), which is a model-free, time-domain analysis technique (Fig. 4B, C, and S23). Three typical electrochemical processes are identified at 10<sup>-6</sup> s, 10<sup>-4</sup>–10<sup>-3</sup> s, and 10<sup>-2</sup>–10<sup>-1</sup> s, corresponding to electrolyte resistance ( $R_b$ ), SEI resistance ( $R_{SEI}$ ), and charge-transfer resistance ( $R_{ct}$ ), respectively.<sup>25</sup> The Li|PHL|Li cell exhibits a high  $R_{SEI}$  value initially, which rapidly decreases due to lithium dendrite growth. Meanwhile, dead lithium and parasitic reactions lead to the deterioration of PHL, resulting in a rapid rise in  $R_b$ . In stark contrast, the Li|PHLT|Li cell displays much more stable cycling behavior with minimal fluctuations. Interestingly, a unique new peak emerges at 10<sup>-5</sup> s after initial cycling, indicative of the formation of a novel Li<sup>+</sup> conductive phase, which differs from the pristine PHLT (Fig. 4C). Correspondingly, Li–N bond has been detected on the cycled TiN surface by ex-situ X-ray photoelectron spectroscopy (XPS) analysis (Fig. 4D, E), supporting the formation of lithiated TiN phase, i.e. Li<sub>x</sub>TiN. Previous studies have demonstrated the feasibility of TiN lithiation, with the lithiation behavior occurring on its surface and grain boundary.<sup>26, 27</sup> In addition, even if there exists the possible dendrite formation on the Li metal surface, the TiN fillers help mitigate lithium dendrite growth by reacting with dendrites, thereby preventing short-circuiting and prolonging the lifespan of lithium metal batteries. These findings suggest that TiN filler not only enhances the ion transport kinetics of the electrolyte but also stabilizes the interface between the electrolyte and Li metal, thereby improving cycling stability. Furthermore, the presence of LiTFSI

signal on the cycled TiN surface confirms that LiTFSI molecules are strongly bound to the filler surface and cannot be completely removed even after repeated washing and centrifugation, providing additional evidence for the strong adsorption between LiTFSI and TiN.

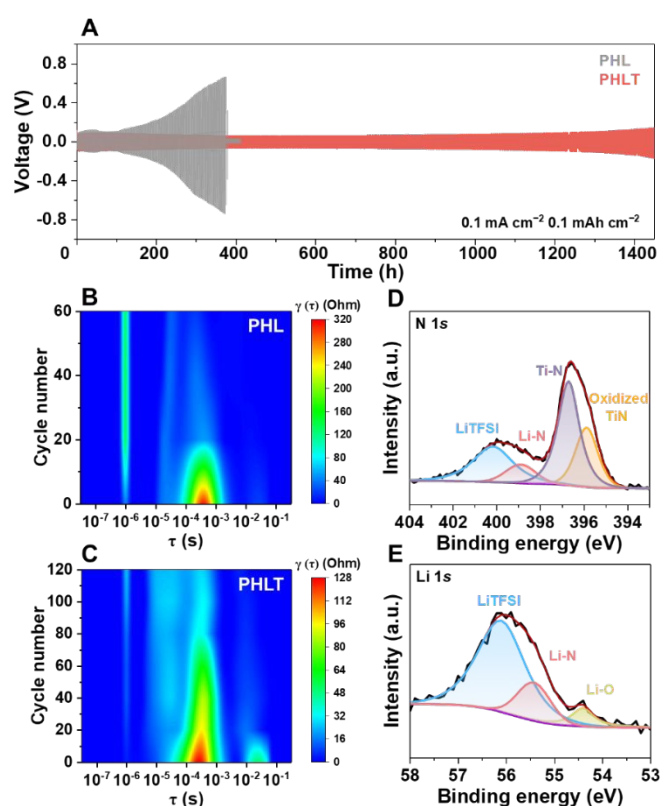


Fig. 4 (A) Lithium stripping-plating profiles at 0.1 mA cm<sup>-2</sup> and 0.1 mAh cm<sup>-2</sup>. DRT results of the (B) Li|PHL|Li and (C) Li|PHLT|Li cells cycled at 0.2 mA cm<sup>-2</sup> and 0.2 mAh cm<sup>-2</sup>. Ex-situ XPS analysis of (D) N 1s and (E) Li 1s spectra of recovered TiN nanofibers.




## Investigation of composition and structure of solid electrolyte interphase

The Li||Li cells (300 h, 0.1 mA cm<sup>-2</sup>, and 0.1 mAh cm<sup>-2</sup>) were disassembled to analyze the morphologies of the cycled lithium metal electrodes and the SEI components. Fig. S24 shows the SEM image of fresh Li, which displays a relatively smooth and flat surface. While in the case of using PHL as the electrolyte, the Li metal shows a mossy and porous surface with an 80–130 μm thick reaction layer (Fig. 5A, B and Fig. S25A, B). In sharp contrast, a significantly flat and denser morphology is observed by using PHLT electrolyte (Fig. 5C, D and Fig. S25C, D), indicating suitable contact and uniform Li<sup>+</sup> distribution. Ex-situ XPS reveals significant differences in the SEI composition of the two systems (Fig. S26 and Table S2). In the PHL system, the SEI contains massive organic components and Li<sub>2</sub>CO<sub>3</sub> is produced owing to the decomposition of solvents, while LiF and Li<sub>3</sub>N are found only in minor quantities (Fig. 5E, S27). However, in the case of PHLT, the organic components are minimal (~4%), instead, with an F-rich SEI layer as high as ~53% (Fig. 5F). The robust and stable LiF exceeds over 90% in the F 1s XP spectrum, and a higher proportion of Li<sub>3</sub>N is also observed (Fig. S28). Besides, the ex-situ time of flight secondary ion mass spectrometry (ToF-SIMS) analysis was also performed to provide the spatial distribution of SEI components.<sup>28, 29</sup> The depth profiling of secondary ion fragments (Fig. 5G and S29) demonstrates that in the PHLT system, the concentration of the

F species is relatively low, whereas the proportions of organic species (CH<sub>2</sub><sup>-</sup>), anionic fragments (SO<sub>2</sub>N<sup>-</sup>), and CO<sub>3</sub><sup>2-</sup> are higher. In sharp contrast, PHLT promotes an abundant and homogeneous distribution of F species within the SEI, with a reduction of CH<sub>2</sub><sup>-</sup> and SO<sub>2</sub>N<sup>-</sup> species (Fig. 5H, I, S30, and S31). Consequently, TiN fillers are instrumental in promoting the formation of a robust, LiF-dominated dense SEI, which substantially inhibits the lithium dendrite growth, and minimizes the interfacial parasitic reactions (Fig. 5K). In contrast, in the PHL system, persistent side reactions lead to the generation of dead lithium and lithium dendrites (Fig. 5J).

## Evaluation of full cell performance and safety property

The CV curves (Fig. S32) confirm the superior reversibility and enhanced reaction kinetics of the PHLT electrolyte. The Li|PHLT|LiFePO<sub>4</sub> (LFP) cell delivers specific discharge capacities of 158.7 (0.1 C), 153.3 (0.2 C), 143.3 (0.5 C), 131.6 (1 C), 117.2 (2 C), and 88.6 (5 C) mAh g<sup>-1</sup>, respectively (Fig. 6A), which are much higher than those of the Li|PHL|LFP cell, i.e., 141.2 (0.1 C), 122.3 (0.5 C) and 38.9 (5 C) mAh g<sup>-1</sup>. Further, the Li|PHLT|LFP cell exhibits a flatter charge/discharge voltage and smaller polarization (Fig. S33). The Li|PHLT|LFP cell achieves excellent long-term cycling stability, evidenced by a capacity retention of 62.2% after 3000 cycles at 2 C with an average Coulombic efficiency of 99.8% (Fig. 6B).

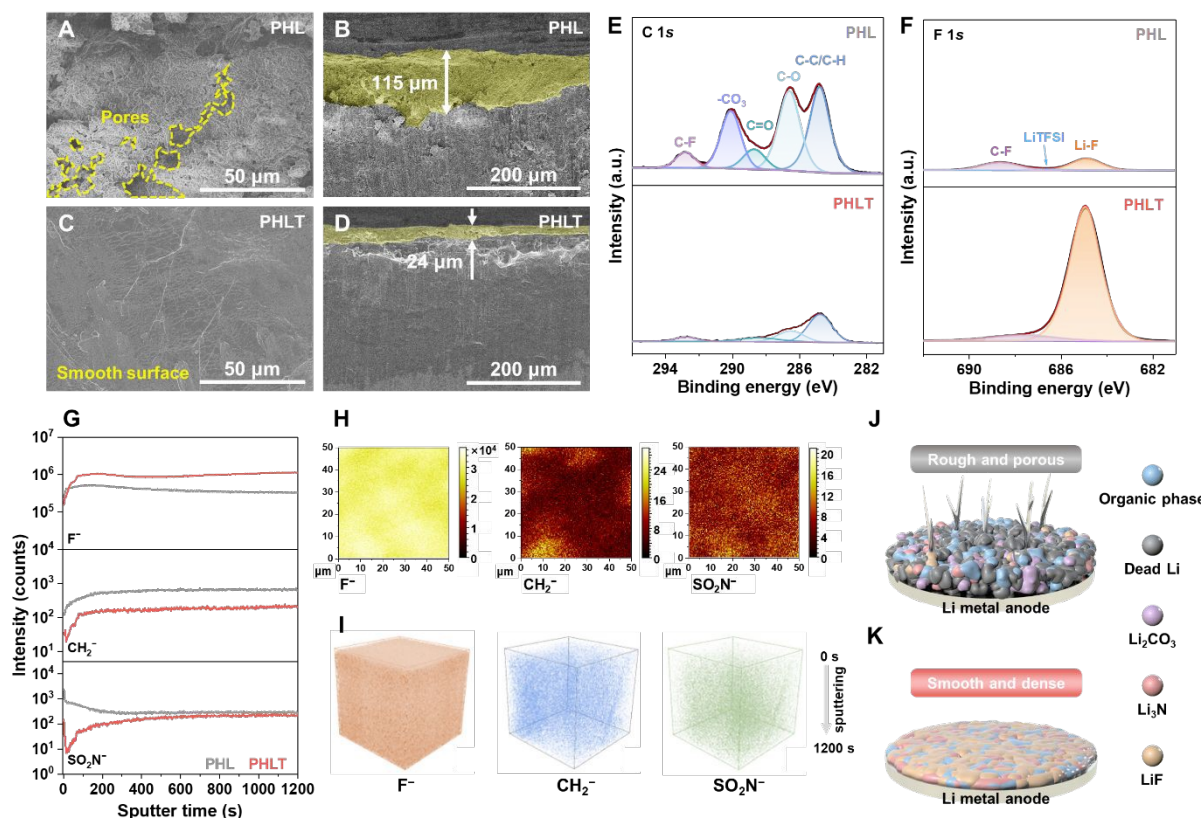


**Fig. 5** Ex-situ SEM images of the (A, C) surface and (B, D) cross-sectional view of the cycled Li electrodes recovered from Li||Li cells. Ex-situ XPS spectra of (E) C 1s and (F) F 1s of the cycled Li electrodes. (G) ToF-SIMS depth profiling, (H) surface mapping, and (I) 3D reconstruction images of the F<sup>-</sup>, CH<sub>2</sub><sup>-</sup>, and SO<sub>2</sub>N<sup>-</sup> fragments of the Li electrode operated with PHLT. Schematic representation of lithium deposition morphology on the Li anode using (J) PHL or (K) PHLT as the electrolyte.





This performance contrasts sharply with the Li|PHL|LFP cell, which only retains a capacity of 19.7 mAh g<sup>-1</sup> after 700 cycles, corresponding to a capacity retention ratio of 18.0%. Correspondingly, the impedance evolution of the Li|PHL|LFP cell demonstrates continuous growth over 400 cycles, while the Li|PHLT|LFP cell maintains remarkably stable impedance throughout cycling (Fig. S34). The Li|PHLT|LiNi<sub>0.8</sub>Co<sub>0.1</sub>Mn<sub>0.1</sub>O<sub>2</sub>

cells also display superior rate capability and cycling stability (Fig. S35, Table S3). Compared with the recently reported PVDF-based electrolytes modified by inorganic fillers, the TiN nanofiber enhanced polymer-based electrolyte stands out with its impressive cycling stability and overall electrochemical performance (Fig. 6C and Table S4).<sup>30-39</sup>

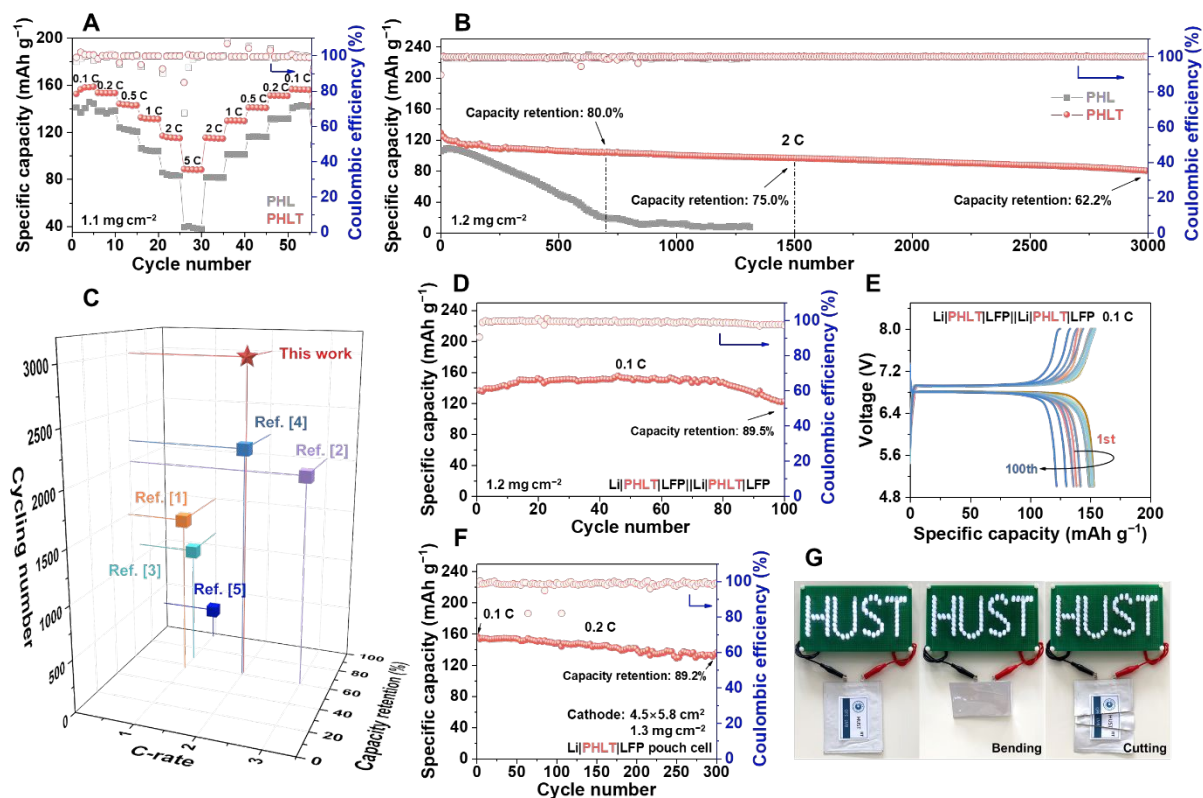

**Fig. 6** (A) Rate capabilities and (B) cycling stability of the Li|LFP cells. (C) A comparison of C-rate, cycling number, and capacity retention between this work and other reported PVDF-based electrolytes in recent literature. (D) Cycling stability and (E) charge/discharge voltage profiles of the bipolar stacking cell. (F) The cycling performance of a Li|PHLT|LFP pouch cell at 0.2 C. (G) Optical photographs illustrating the bending and cutting tests of the pouch cell.

Thanks to the immobilization properties of the QPE, we successfully constructed bilayer bipolar stacking cells comprising two Li|PHLT|LFP units in series using stainless steel sheets as the bipolar plates (Fig. S37). This design enables a high-voltage output in a single cell, reduces internal resistance, simplifies packaging, and improves the overall energy density of the cells, demonstrating its significant potential for practical applications. At 0.1 C, the cell enables outstanding capacity retention of 89.5% after 100 cycles and an average Coulombic efficiency of 99%, outputting a discharge voltage platform of 6.7 V (Fig. 6D, E). To the best of our knowledge, the bipolar stacking cells in this work exhibit superior cycling stability and capacity retention compared to other reported in the literature (Fig. S36).<sup>40-45</sup> Further, coupling with high-mass-loading cathode electrodes of 9.5 mg cm<sup>-2</sup> (~1.6 mAh cm<sup>-2</sup>), the Li|PHLT|LFP cell still delivers a high specific discharge capacity of over 150 mAh g<sup>-1</sup> (0.1 C) for more than 30 cycles (Fig. S37). Additionally, a single-layer pouch cell (4.5×5.8 cm<sup>2</sup>) was assembled with an LFP cathode and thin lithium foil (80 μm). The pouch cell delivers a discharge capacity of 153 mAh g<sup>-1</sup> at 0.2 C, and capacity retention of 89.2% after 300 cycles (Fig. 6F and S38). The pouch

cell shows stable operation even under severe abuse conditions such as bending or cutting (Fig. 6G and S39), underscoring its superior mechanical flexibility and excellent safety. These results, collectively, highlight the PHLT as a promising candidate for practical diverse applications.

## Conclusions

In summary, we propose a structurally compact, kinetically enhanced, and interface-stable QPE by incorporating multifunctional TiN nanofiber fillers into PVDF-HFP-based electrolyte. The interactions between the polymer matrix and TiN fillers promote conformational transformation and enhance the dissociation of lithium salt while constraining the movement of anions. Additionally, the introduction of TiN facilitates the formation of a LiF-rich and dense SEI, which ensures uniform lithium deposition, inhibits lithium dendrite growth, and effectively mitigates parasitic reactions. Consequently, the Li|LiFePO<sub>4</sub> cells can operate stably for over 3000 cycles at 2 C. The two-layer bipolar stacking cells (5–8 V), high mass-loading coin cells (9.5 mg cm<sup>-2</sup>), and pouch cells also exhibit excellent



cycling and safety performance. Our work provides an efficient and valuable strategy for leveraging the multifunctional properties of fillers to enhance the performance of polymer electrolytes, facilitating their practical applications in SSLMBs.

### Conflicts of interest

There are no conflicts to declare.

### Acknowledgments

This work is supported by the National Natural Science Foundation of China (52277215 and 52377206), the China Postdoctoral Science Foundation (2023M730884), the Heilongjiang Provincial Postdoctoral Science Foundation (LBH. Z23024), and opening funding from Key Laboratory of Engineering Dielectrics and Its Application (Harbin University of Science and Technology) (No. KFM202507, Ministry of Education). Dr. Jian Wang also thanks the fellowship support from Alexander von Humboldt Foundation.

### References

- D. Lin, Y. Liu and Y. Cui, *Nat. Nanotechnol.*, 2017, **12**, 194-206.
- X. Wang, Z. Chen, K. Jiang, M. Chen and S. Passerini, *Adv. Energy Mater.*, 2024, **14**, 2304229.
- J. Wang, J. Zhang, Y. Zhang, H. Li, P. Chen, C. You, M. Liu, H. Lin and S. Passerini, *Adv Mater*, 2024, **36**, e2402792.
- J. Wang, L. Li, H. Hu, H. Hu, Q. Guan, M. Huang, L. Jia, H. Adenusi, K. V. Tian, J. Zhang, S. Passerini and H. Lin, *ACS Nano*, 2022, **16**, 17729-17760.
- Q. Wang, L. Jiang, Y. Yu and J. Sun, *Nano Energy*, 2019, **55**, 93-114.
- F. Ye, Z. Wang, M. Li, J. Zhang, D. Wang, M. Liu, A. Liu, H. Lin, H. T. Kim and J. Wang, *Nano Lett.*, 2024, **24**, 6850-6857.
- E. Quartarone and P. Mustarelli, *Chem. Soc. Rev.*, 2011, **40**, 2525-2540.
- Y. Wang, Z. Chen, K. Jiang, Z. Shen, S. Passerini and M. Chen, *Small*, 2024, **20**, 2402035.
- Z. Chen, G.-T. Kim, Z. Wang, D. Bresser, B. Qin, D. Geiger, U. Kaiser, X. Wang, Z. X. Shen and S. Passerini, *Nano Energy*, 2019, **64**, 103986.
- M. Chen, W. Liu, Z. Yue, Y. Wang, Y. Wu, Y. Li and Z. Chen, *Batteries*, 2023, **9**, 270.
- Y. Wu, Z. Chen, Y. Wang, Y. Li, C. Zhang, Y. Zhu, Z. Yue, X. Liu and M. Chen, *J. Energy Chem.*, 2024, **89**, 437-448.
- Y. Wang, Z. Chen, Y. Wu, Y. Li, Z. Yue and M. Chen, *ACS Appl. Mater. Interfaces*, 2023, **15**, 21526-21536.
- Y. Wu, Y. Li, Y. Wang, Q. Liu, Q. Chen and M. Chen, *J. Energy Chem.*, 2022, **64**, 62-84.
- Y. Jiang, C. Xu, K. Xu, S. Li, J. Ni, Y. Wang, Y. Liu, J. Cai and C. Lai, *Chem. Eng. J.*, 2022, **442**, 136245.
- M. Li, H. An, Y. Song, Q. Liu, J. Wang, H. Huo, S. Lou and J. Wang, *J. Am. Chem. Soc.*, 2023, **145**, 25632-25642.
- X. Song, R. Zhao, J. Zhu, J. Zhang, N. Xu, J. Liu, Y. Liu, H. Zhang, Y. Ma, C. Li and Y. Chen, *National Science Review*, 2025, nwaf016.
- Y. Zhu, Z. Lao, M. Zhang, T. Hou, X. Xiao, Z. Piao, G. Lu, Z. Han, R. Gao, L. Nie, X. Wu, Y. Song, C. Ji, J. Wang and G. Zhou, *Nat. Commun.*, 2024, **15**, 3914.
- C. M. Thomas, W. J. Hyun, H. C. Huang, D. Zeng and M. C. Hersam, *ACS Energy Lett.*, 2022, **7**, 1558-1565. DOI: 10.1039/D4EE06035K
- Q. Zhou, X. Yang, X. Xiong, Q. Zhang, B. Peng, Y. Chen, Z. Wang, L. Fu and Y. Wu, *Adv. Energy Mater.*, 2022, **12**, 2201991.
- X. Guo, Z. Ju, X. Qian, Y. Liu, X. Xu and G. Yu, *Angew. Chem. Int. Ed.*, 2023, **62**, e202217538.
- Y. Yuan, L. Chen, Y. Li, X. An, J. Lv, S. Guo, X. Cheng, Y. Zhao, M. Liu, Y.-B. He and F. Kang, *Energy Mater. Devices*, 2023, **1**, 9370004.
- A. Ma, C. Fu, H. Chu, X. Ran and W. Nie, *Chin. J. Appl. Chem.*, 2020, **37**, 1411-1419.
- Y. Huang, J. Zeng, S. Li, C. Dai, J.-F. Liu, C. Liu and Y.-B. He, *Adv. Energy Mater.*, 2023, **13**, 2203888.
- J. Zhang, J. Zhu, R. Zhao, J. Liu, X. Song, N. Xu, Y. Liu, H. Zhang, X. Wan, Y. Ma, C. Li and Y. Chen, *Energy Environ. Sci.*, 2024, **17**, 7119-7128.
- Q. Gao, D. Wu, Z. Wang, P. Lu, X. Zhu, T. Ma, M. Yang, L. Chen, H. Li and F. Wu, *Energy Storage Mater.*, 2023, **63**, 103007.
- K. H. T. Raman, T. R. Penki, N. Munichandraiah and G. M. Rao, *Electrochim. Acta*, 2014, **125**, 282-287.
- H.-S. Tsai, C.-H. Hsu, C.-C. Chi, Y.-C. Wang, F.-W. Liu, S.-Y. Tang, C.-J. Tsai, H. Ouyang, Y.-L. Chueh and J.-H. Liang, *Inorg. Chem. Front.*, 2019, **6**, 172-175.
- J. Wang, J. Zhang, J. Wu, M. Huang, L. Jia, L. Li, Y. Zhang, H. Hu, F. Liu, Q. Guan, M. Liu, H. Adenusi, H. Lin and S. Passerini, *Adv Mater*, 2023, **35**, e2302828.
- Z. Zhang, J. Wang, H. Qin, B. Zhang, H. Lin, W. Zheng, D. Wang, X. Ji and X. Ou, *ACS Nano*, 2024, **18**, 2250-2260.
- P. Shi, J. Ma, M. Liu, S. Guo, Y. Huang, S. Wang, L. Zhang, L. Chen, K. Yang, X. Liu, Y. Li, X. An, D. Zhang, X. Cheng, Q. Li, W. Lv, G. Zhong, Y.-B. He and F. Kang, *Nat. Nanotechnol.*, 2023, **18**, 602-610.
- Q. Wu, M. Fang, S. Jiao, S. Li, S. Zhang, Z. Shen, S. Mao, J. Mao, J. Zhang, Y. Tan, K. Shen, J. Lv, W. Hu, Y. He and Y. Lu, *Nat. Commun.*, 2023, **14**, 6296.
- W. Yang, Y. Liu, X. Sun, Z. He, P. He and H. Zhou, *Angew. Chem. Int. Ed.*, 2024, **63**, e202401428.
- X. An, Y. Liu, K. Yang, J. Mi, J. Ma, D. Zhang, L. Chen, X. Liu, S. Guo, Y. Li, Y. Ma, M. Liu, Y.-B. He and F. Kang, *Adv. Mater.*, 2024, **36**, 2311195.
- W. Huang, S. Wang, X. Zhang, Y. Kang, H. Zhang, N. Deng, Y. Liang and H. Pang, *Adv. Mater.*, 2023, **35**, 2310147.
- J. Pan, Y. Zhang, J. Wang, Z. Bai, R. Cao, N. Wang, S. Dou and F. Huang, *Adv. Mater.*, 2022, **34**, 2107183.
- S. Lv, X. He, Z. Ji, S. Yang, L. Feng, X. Fu, W. Yang and Y. Wang, *Adv. Energy Mater.*, 2023, **13**, 2302711.
- L. Bi, L. He, Y. Song, Y. Wang, Q. Xie, P. Dong, Y. Zhang, Y. Yao, J. Liao and S. Wang, *Adv. Funct. Mater.*, 2024, **34**, 2311848.
- H. Cheng, D. Li, B. Xu, Y. Wei, H. Wang, B. Jiang, X. Liu, H. Xu and Y. Huang, *Energy Storage Mater.*, 2022, **53**, 305-314.
- Y. Jin, X. Zong, X. Zhang, Z. Jia, H. Xie and Y. Xiong, *Energy Storage Mater.*, 2022, **49**, 433-444.
- S.-H. Kim, K.-H. Choi, S.-J. Cho, J. Yoo, S.-S. Lee and S.-Y. Lee, *Energy Environ. Sci.*, 2018, **11**, 321-330.
- S.-H. Kim, J.-H. Kim, S.-J. Cho and S.-Y. Lee, *Adv. Energy Mater.*, 2019, **9**, 1901841.
- Z. Chen, G.-T. Kim, J.-K. Kim, M. Zarrabeitia, M. Kuenzel, H. Liang, D. Geiger, U. Kaiser and S. Passerini, *Adv. Energy Mater.*, 2021, **11**, 2101339.
- J. Lee, J. Song, H. Lee, H. Noh, Y.-J. Kim, S. H. Kwon, S. G. Lee and H.-T. Kim, *ACS Energy Lett.*, 2017, **2**, 1232-1239.



44. H. W. Kim, J. Kim, D. Kim, Y. Kim and W.-G. Lee, *J. Mater. Chem. A*, 2023, **11**, 14655-14662.
45. K.-S. Oh, J.-H. Kim, S.-H. Kim, D. Oh, S.-P. Han, K. Jung, Z. Wang, L. Shi, Y. Su, T. Yim, S. Yuan and S.-Y. Lee, *Adv. Energy Mater.*, 2021, **11**, 2101813.



## Data availability statements

View Article Online  
DOI: 10.1039/D4EE06035K

The data supporting this article have been included as part of the Supplementary Information.

