


Energy & Environmental Science

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: Q. Wu and Y. Qi, *Energy Environ. Sci.*, 2025, DOI: 10.1039/D5EE00206K.

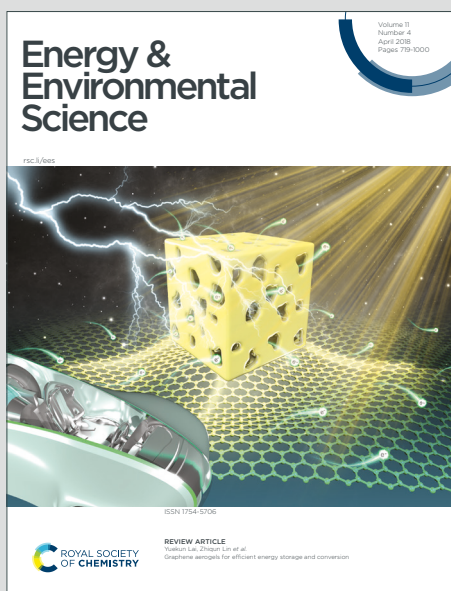

This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Broader context statement

The high-energy-density Li metal batteries show promising applications in electric vehicles, low-altitude economy and many others. However, the drastic reactivity of Li metal anode limits its battery performance. The localized high-concentration electrolytes (LHCE), demonstrate low viscosity, high ionic conductivity, and stable solid-electrolyte interphase (SEI) formation that can protect the Li metal anode, thus dramatically improving the performance and durability. Recently, we have proposed micelle-like structures to fully understand the underlying microstructural characteristics of the bulk LHCE to bridge the scales from the atomistic solvation structures to the macroscopically homogeneous liquid electrolyte (*Nat. Mater.* 2023, 22, 1531). It is important to recognize that the SEI formation occurs near the negatively charged negative electrode surface. This paper reveals the heterogeneous electric double layer (EDL) structures of the prototypical LHCE consisting of LiFSI salt, DME solvent, and TFEO diluent. We find that the classical Stern model missed the heterogeneity of this type of electrolyte. The micelle-like structures in LHCE are maintained in its EDL, which are divided into the Li⁺-rich salt-solvent cluster region and the Li⁺-poor diluent region. The diluent region contains Li⁺ ions in the EDL but has no ions in the bulk of LHCE. The appearance of Li⁺ ions in the diluent region is necessary for the EDL, as TFEO alone cannot screen the charge. Thus, the reduction voltage of TFEO diluent will be increased by the association of Li⁺ ions in the EDL, highlighting one of the impacts of the heterogeneous EDL structures on SEI formation. This work helps extend the development of the EDL theory and guides the design of more effective LHCE for high-performance rechargeable batteries.



Revealing Heterogeneous Electric Double Layer (EDL) Structures of Localized High-Concentration Electrolytes (LHCE) and Their Impact on Solid-Electrolyte Interphase (SEI) Formation in Lithium Batteries

Qisheng Wu and Yue Qi*

School of Engineering, Brown University, Providence, RI 02912, United States

KEYWORDS: lithium-metal batteries, electric double layer, localized high-concentration electrolytes, molecular dynamics

Abstract

Recently, we have proposed micelle-like structures to fully understand microstructures in localized high-concentration electrolytes (LHCE) that show many benefits to high-capacity electrodes. It is critical to understand the electric double layer (EDL) structures of LHCE, how they differ from the bulk electrolyte structure, and how they impact the solid electrolyte interphase (SEI) formation on Li-metal electrode with a combined DFT-MD-data approach. In this work, we reveal the heterogeneous EDL structures of the prototypical LHCE consisting of lithium bis(fluorosulfonyl)imide (LiFSI) salt, dimethoxyethane (DME) solvent, and tris(2,2,2-trifluoroethyl)orthoformate (TFEO) diluent at a concentration of LiFSI-1.2DME-2TFEO for lithium batteries. We find that the 1D EDL Stern model with an adsorbed cation layer and a more diffused layer with ions, solvents, and diluents missed the heterogeneity of this type of electrolyte. The micelle-like structures in LHCE are maintained in its EDL, which are divided into the Li⁺-



rich salt-solvent cluster region and the Li^+ -poor diluent region. The diluent region contains Li^+ ions in the EDL but has no ions in the bulk of LHCE. This is because TFEO cannot form a complete solvation shell in the bulk electrolyte due to the steric effect, however, only a partial solvation shell is needed near the surface. The appearance of Li^+ ions in the diluent region is also necessary for the EDL, as TFEO alone cannot screen the charge. Thus, the reduction voltage of TFEO will be increased by the association of Li^+ ions in the EDL, highlighting one of the impacts of the heterogeneous EDL structures on SEI formation. This work helps extend the development of the EDL theory and guides the design of more effective LHCE for high-performance rechargeable batteries.

*Email: yueqi@brown.edu



1. Introduction

The use of high-capacity anodes (e.g., Li metal, Si, and Na metal) has posed significant challenges to the conventional low-concentration electrolytes (LCEs) in developing high-energy rechargeable batteries that are needed to advance electric vehicle and electric aircraft capabilities.¹ The solvent-derived solid-electrolyte interphase (SEI) layers are not stable on the high-capacity anodes that experiences large volume changes, leading to continuous loss of active materials and rapid dendrite growth.²⁻⁴ These challenges can be largely tackled by increasing the salt concentration to form high-concentration electrolytes (HCEs) so that anion reduction to form stable, inorganic-rich SEI is preferred.^{5,6} However, sluggish ion transport and an increase in cost come with increasing salt concentration.⁵ To mitigate these pitfalls, a low-viscosity diluent is added to form localized high-concentration electrolytes (LHCEs), thus improving high-capacity anode performance.⁷ It has been realized in both experiments and computations that the cation solvation shells are fully occupied by the salt anion and solvent with little diluent participation if there is any.^{7,8} The information about the LHCE microstructures has remained unclear until the recently proposed micelle-like structures, where a network of salt-solvent clusters are mostly separated from the diluent matrix by a solvent-rich surfactant region.^{9,10} In LHCE, the salt is soluble in the solvent but not in the diluent and the diluent is completely miscible with the solvent. The relationship among salt, solvent, and diluent is analogical to that among water, oil, and the surfactant being widely recognized in micelles.^{11,12} While the micelle-like structure is consistent with the previously proposed solvation cluster model of LHCEs,^{7,13} it further explains why those clusters are stable and why salt concentration can be even higher in the salt-solvent clusters, which further improve the SEI formation comparing to their HCE counterparts with the same salt to



solvent ratio.⁹ However the details of SEI formation of the LHCE electrolyte have not been fully understood.

It is important to recognize that the SEI formation occurs near the negatively charged negative electrode surface. The electric double layer (EDL) structure of electrolytes near a charged surface is a fundamental question in electrochemistry important for energy storage, electrocatalysis, and many other technological applications.^{14,15} Salt ions, solvents, and additive molecules redistribute in the EDL, wherein the electrolyte structures differ from those in the bulk phase and vary as a function of the potential on the electrode.^{16,17} The SEI layers, mainly formed by electrolyte reduction reactions,^{18–20} must be sensitive to the electrolyte structures within the EDL that are subject to an external electric field.^{17,21} Therefore, it is critical to gain atomistic insights into the reduction reactions of the electrolyte species in the EDL to help predict and control the formation of the SEI layers as well as the Li plating morphology.²² In our recent work,²¹ we have developed an interactive DFT-MD-data model and applied it to investigate the EDL structures of commonly used LCEs (e.g. 1 M LiPF₆ in carbonate electrolytes for graphite anode and 1 M LiTFSI in ether electrolytes for Li-metal anode) and their effects on reduction reactions of multi-component electrolytes and SEI formations. In contrast to that of LCE, there are much fewer reports on the EDL structures of HCE in the literature. One special case of HCE is the so-called water-in-salt electrolyte (WiSE), a highly concentrated aqueous electrolyte,^{23,24} whose interface structures near the electrode were revealed through molecular dynamics (MD) simulations.^{25,26} Both LCE and HCE systems feature homogeneous spatial distributions of the salt-solvent cluster,⁹ however, like microemulsion,²⁷ LHCE systems are microscopically heterogeneous featuring micelle-like structures.⁹ Considering the significance of EDL, the questions naturally arise: what are the characteristics of the EDL structures of heterogeneous liquids like LHCE and how will the



EDL of LHCE impact its electrolyte reduction and SEI formation? The EDL structures of LHCE have been rarely discussed in the literature despite the rich understanding of LHCE structures in its bulk phase.^{13,28}

The idea of EDL has been extensively developed²⁹ since its initial definition by Helmholtz in 1853.³⁰ Despite its success, the classical Gouy-Chapman-Stern model^{31–33} neglects ion size effect (or steric effect), short-range correlations, and solvent polarization.¹⁴ The Gouy-Chapman theory provides an analytical solution for the Poisson-Boltzmann equation at steady state, however, it works well only for a dilute electrolyte, where the ion concentration is usually at least one order of magnitude less than 1.0 molar (M).¹⁴ Since salt concentrations in the battery electrolytes are typically around 1.0 M for LCE and much higher for HCE,³⁴ more advanced theories are urgently needed.^{35–39} As a step forward, a simple modified Poisson–Fermi theory was recently developed for EDL in WiSE that helped further understand and quantify the competing solvation and polarization forces acting on water molecules near electrified interfaces in WiSE.⁴⁰ Other hybrid methods that combine the electron density, electric potential, and solvent polarization are being developed.⁴¹ Despite a recent attempt to develop the theory of bulk structures in LHCE,⁴² the theory of EDL for LHCE is yet to be developed. To achieve that, it requires a precise microscopic picture of the EDL of LHCE that can be provided by cost-effective yet powerful MD simulations.^{29,43–45}

In this work, we have conducted comprehensive MD simulations (more details in the Supplementary Information, SI) of the EDL structures for LCE, HCE, and LHCE, as well as made systematic comparison between them with the prototypical systems consisting of lithium bis(fluorosulfonyl)imide (LiFSI) salt, dimethoxyethane (DME) solvent, and tris(2,2,2-trifluoroethyl)orthoformate (TFEO) diluents, whose molecular structures are given in **Figure 1**.



The different electrolyte compositions are highlighted in the ternary phase diagram in **Figure 1**.⁹ LiFSI salt and DME solvent can form homogenous electrolytes with different salt concentrations. Here we use LiFSI-9DME, namely LCE(1-9), to represent a LCE system.⁴⁶ In addition, we use LiFSI-1.4DME (4 M) and LiFSI-1.2DME to represent HCE systems, namely HCE(1-1.4) and HCE(1-1.2), both of which were shown to exhibit high Coulombic efficiency and excellent cycling stability.^{46,47} Connecting the point of HCE(1-1.2) and TFEO corner in the phase diagram, a series of LHCE(1-1.2-*x*) can be formed. Here we use LiFSI-1.2DME-2TFEO, namely LHCE(1-1.2-2), to represent the LHCE system, which was shown to be able to stabilize the high-voltage cathode, suppress the continuous SEI growth on Li metal anode, and enable high capacity retention (>80% over 200 cycles) of Li metal batteries.⁴⁷

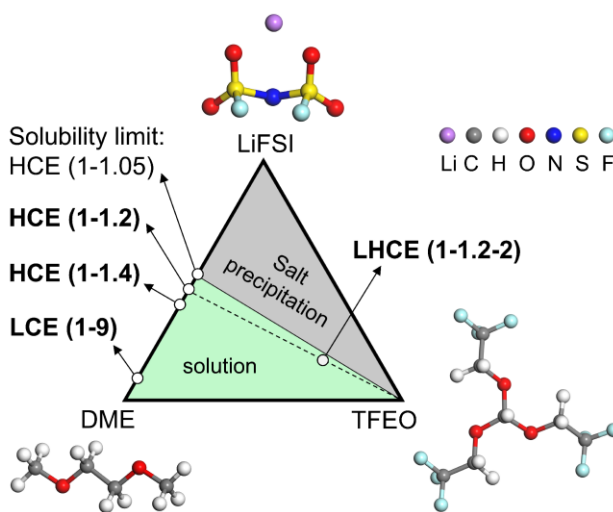


Figure 1. The ternary phase diagram with LiFSI, DME, and TFEO as the three variable phases, whose molecular structures are shown correspondingly. The LCE(1-9), HCE (1-1.4), HCE(1-1.2), and LHCE (1-1.2-2) electrolytes under investigation in this work are highlighted with bold texts. The ternary phase diagram is divided into two regions, the solution phase (green) and the salt precipitation phase (gray). Color schemes for atoms: purple for Li, gray for C, white for H, red for O, dark blue for N, yellow for S, and light blue for F.



Based on the MD simulations and structural analyses (**Section 2.1 and 2.2**), we have drawn the schematics for illustration of the EDL structures in LCE, HCE, and LHCE near the negatively charged electrode, as shown in **Figure 2**. For LCE (**Figure 2a**), the EDL near the negatively charged electrode (i.e., the Li-metal/graphene anode during the charging process) features adsorbed Li^+ ions that mainly coordinate with solvent molecules with a tiny fraction of anions (most of the anions are repelled from the negatively charged electrode).²¹ For HCE (**Figure 2b**), more Li^+ ions are found to be in the EDL region due to the increasing salt concentration. The Li^+ ions are not only coordinating with solvent molecules but also coordinating with a significant amount of salt anions due to strong ion pairing and the formation of aggregates in HCE.^{40,48,49} Both LCE and HCE show homogeneous spatial distributions of species in the EDL. In contrast, the heterogeneous micelle-like structures of bulk LHCE are extended to the EDL with different characteristics from its bulk structures. As shown in **Figure 2c**, the EDL of LHCE can be divided into two distinct regions, one being Li^+ -rich with aggregated clusters that maintain the micelle-like characteristics and the other being Li^+ -poor mainly with diluent. The diluent region contains Li^+ ions near the negatively charged surface but does not have any ions in the bulk of LHCE.⁹ The reasons for these differences will be investigated in **Section 2.2** and **Section 2.3**. In addition, the impacts of the heterogeneous EDL structures on the electrolyte reduction and SEI formation are discussed in **Section 2.4**.



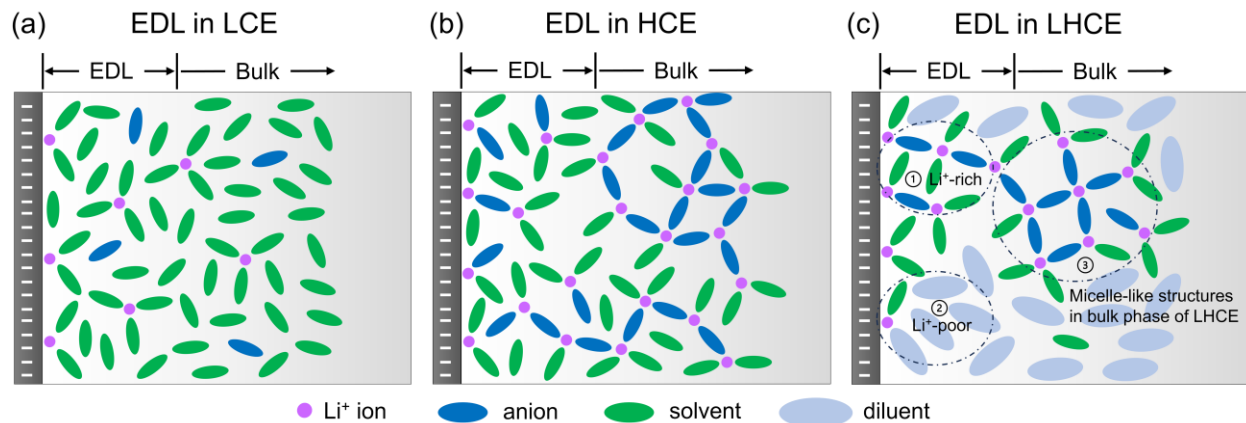


Figure 2. Schematics of EDL structures in LCE (a), HCE (b), and LHCE (c) near the negatively charged electrode. The purple circles represent Li^+ ions, while the dark blue, green, and light blue ovals represent anion, solvent, and diluent, respectively. In the EDL of LHCE, region (1) stands for the Li^+ -rich region (with aggregated clusters) in the EDL, region (2) for Li^+ -poor region (mainly with diluent), and region (3) for the salt-solvent clusters in the bulk phase.

2. Results and Discussions

2.1. EDL structures for LCE, HCE, and LHCE

Before introducing the EDL structures, we first summarize the structures in bulk electrolytes, LCE(1-9), HCE(1-1.4), HCE(1-1.2), and LHCE(1-1.2-2), obtained from our previous MD work.⁹ In LCE(1-9), the LiFSI is dissolved in the DME solvent to mainly form solvent-separated ionic pairs (SSIP, >70%) along with a small portion of contact ion pairs (CIP). In HCE(1-1.4) and HCE(1-1.2), the salt-solvent clusters are dominated by ion-pair aggregates (AGG) along with some CIP and more coordinated ion-pair aggregates (AGG+). In LHCE(1-1.2-2), the salt-solvent clusters are dominated by AGG and AGG+ with a small fraction of CIP. It is worth mentioning that the salt-solvent clusters LHCE(1-1.2-2) feature higher AGG+ contribution than its HCE counterpart, *i.e.* HCE(1-1.2), due to the existence of micelle-like structures. In the micelle-like structures, the DME solvent plays the role of surfactant and tends to show more in the



interfacial region between the salt-solvent cluster region and the TFEO diluent region since it is miscible with the TFEO diluent. A small fraction of the DME solvent is completely dissolved into the TFEO diluent region. As a result, more Li^+ -FSI $^-$ coordination appears in the salt-solvent clusters, giving higher local salt concentration.

To investigate the EDL structures of the abovementioned electrolytes, interfacial systems have been built in which the electrolyte is sandwiched by two graphene electrodes with constant charges. See more details in the **Methods** section in the Supporting Information (SI). The number of LiFSI salt, DME solvent, and TFEO diluent in the interfacial systems for LCE(1-9), HCE(1-1.4), HCE(1-1.2), and LHCE(1-1.2-2) are given in **Table S1**. The final frames of the MD trajectories for LCE(1-9), HCE(1-1.4), and HCE(1-1.2) under the graphene surface charge density of $\sigma = \pm 0.6 \text{ e/nm}^2$ are shown in **Figure 3a-c**, while those under $\sigma = \pm 0.8 \text{ e/nm}^2$ are also displayed in **Figure S1**. Special attentions are paid to $\sigma = \pm 0.6 \text{ e/nm}^2$ since it is about the surface charge at the electrochemical equilibrium condition for Li^+/Li^0 .⁵⁰ The structures of EDLs for LCE and HCEs under other surface charge densities are not shown, but their statistical analyses will be discussed later. As revealed in the previous study,⁹ the salt-solvent clusters of LHCE(1-1.2-2) in its bulk phase form a three-dimensional connected network surrounded by the TFEO matrix. Due to the limited sizes of the simulated interfacial systems in this work, the three-dimensional connected network of salt-solvent clusters may not be captured in a single simulation setup. To resolve this, we have considered two different initial configurations for LHCE(1-1.2-2), as demonstrated in **Figure S2**. In the first initial configuration, namely LHCE-1(1-1.2-2), the system is built so that the salt-solvent clusters are connected along the direction perpendicular to the graphene plane (**Figure S2a**). In the second initial configuration, namely LHCE-2(1-1.2-2), the system is built so that the salt-solvent clusters are connected along a direction that is parallel with the graphene plane



(Figure S2b). The time-averaged energies between these two systems are small (Figure S2c), suggesting both scenarios would occur in the real interfacial system that is large enough along the graphene electrode plane. The final frames of the interfacial systems for LHCE-1(1-1.2-2) and LHCE-2(1-1.2-2) under surface charge density of $\sigma = \pm 0.6 \text{ e/nm}^2$ are shown in Figure 3d-e, while those under all other surface charge densities are presented in Figure S3-S4. It is seen that some of the salt-solvent networks are broken after MD simulations due to their interactions with diluent and graphene electrodes (both uncharged and charged).

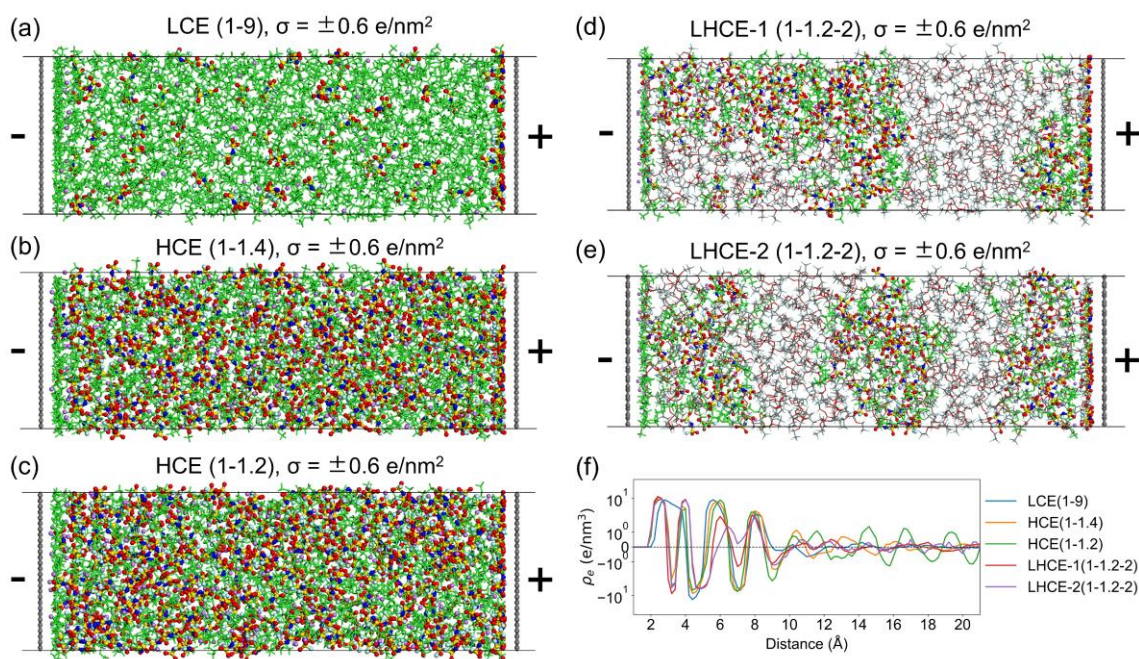


Figure 3. Final frames of the MD trajectories for (a) LCE(1-9), (b) HCE (1-1.4), (c) HCE(1-1.2), and (d,e) LHCE (1-1.2-2) under the graphene surface charge density of $\sigma = \pm 0.6 \text{ e/nm}^2$. (f) Charge density profiles (as functions of distance from the negatively charged graphene electrode; in symmetric logarithmic plot) of the LCE, HCE, and LHCE systems.

It is expected that some Li^+ ions are attracted to the negatively charged graphene electrode, and FSI^- ions are gathered near the positively charged graphene electrode in all LCE, HCE, and LHCE systems due to Coulombic interactions between ions and the charged graphene electrodes,



as seen in the number density profiles in **Figures S5-S9**. This becomes clearer with increasing negative charge densities on the surface and the increasing salt density in the electrolyte. In comparison, the interface adsorption interactions are more important for the first peak near the surface on zero-charged surfaces. This also suggests that the EDL structure is less sensitive to the electrode materials given the similar surface voltages. As a result, the EDL forms near the charged electrode, as clearly shown by the charge density profiles in **Figure S10**. In this work, the thickness of EDL is defined as the region within 10.0 Å from the surface of the negatively charged graphene electrode⁵¹ based on these charge density profiles (**Figures S5-S10**) converging at distances of around 10 Å from the graphene electrode. This is much larger than the classical Debye length, which is about 0.6 Å for 1 M salt and 0.3 Å for 4 M salt in DME solvent with dielectric constant of 2.97. To compare different electrolytes, the charge density profiles (in log scale to amplify the small fluctuations beyond the EDL region) under surface charge density of $\sigma = \pm 0.6 \text{ e/nm}^2$ are shown in **Figure 3f**. It is seen that the HCE(1-1.2) features the most prominent fluctuations in its charge density profile beyond the EDL region, which is probably due to its higher overall salt concentration among the electrolyte systems investigated in this work. This is also opposite to the classical Debye length, which decreases with increasing salt concentration.

2.2 Solvation shell of Li⁺ ions in the EDL of LCE, HCE, and LHCE

Understanding the Li⁺ solvation shell in the EDL is important for the two reasons: a) the desolvation of Li⁺ from its solvation shell impacts the Li⁺/Li⁰ charge transfer kinetics; and b) the Li⁺ coordination can increase the reduction voltage of a solvent species dramatically.⁵² The interfacial structures of the electrolyte species that directly contact the negatively charged graphene electrode for LCE(1-9), HCE(1-1.2), and LHCE-1(1-1.2-2) under surface charge



densities of $\sigma = \pm 0.6 \text{ e/nm}^2$ and $\sigma = \pm 0.8 \text{ e/nm}^2$ are shown in **Figure 4**, while those for HCE(1-1.4) and LHCE-2(1-1.2-2) are shown in **Figure S11**. Near the negatively charged graphene electrode of LCE(1-9) (**Figure 4a**), many Li^+ ions accumulate in the EDL along with much fewer FSI^- ions, phenomenologically consistent with typical EDL models. In the adsorbed layer near the negatively charged graphene electrode for HCE(1-1.4) and HCE(1-1.2), the amount of both Li^+ and FSI^- is significant due to the high salt concentration in this type of electrolyte. Both the Li^+ - FSI^- and Li^+ -DME coordinated pairs are present in the EDL for LCE and HCEs, as shown in **Figure 4b** and **Figure S11a**. For both LHCE-1(1-1.2-2) and LHCE-2(1-1.2-2), TFEO diluent molecules show up in the EDL as well in addition to the presence of Li^+ , FSI^- , and DME solvent (**Figure 4c** and **Figure S11b**).

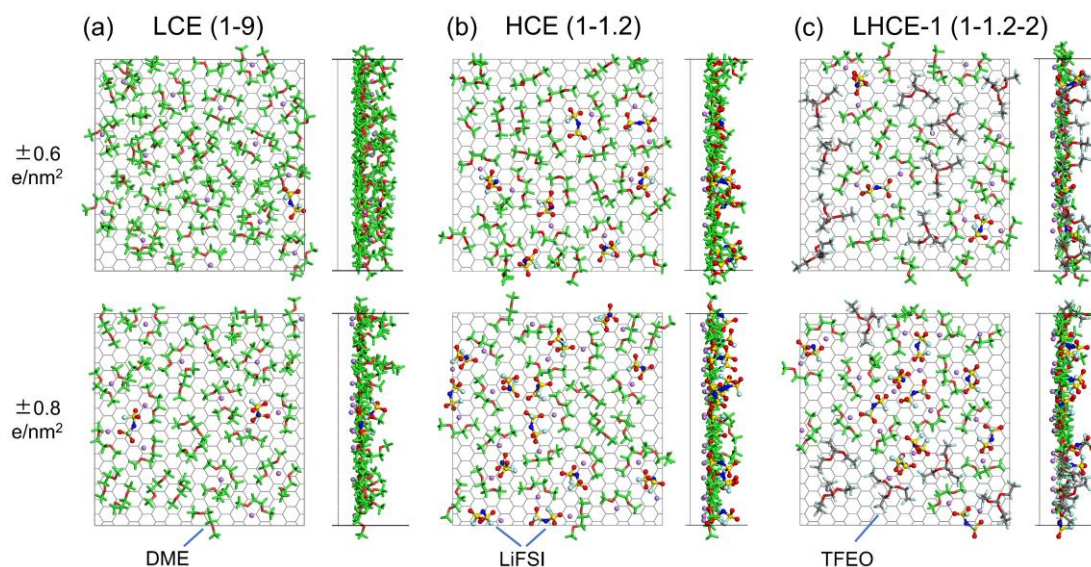


Figure 4. Snapshots of interfacial structures of the directly adsorbed electrolyte species for (a) LCE(1-9), (b) HCE(1-1.2), and (c) LHCE-1 (1-1.2-2) systems under graphene electrode surface charge densities of $\sigma = \pm 0.6 \text{ e/nm}^2$ and $\sigma = \pm 0.8 \text{ e/nm}^2$. The DME molecules are represented with green stick models but the oxygen atoms in DME are highlighted with red for clarity.



Surprisingly, in the EDL of LHCE(1-1.2-2), the Li^+ ions appear in the diluent region and coordinate with the TFEO diluent molecules, behaving differently from that in the bulk phase.⁹ On one hand, the existence of Li^+ ions in the TFEO diluent region is needed to screen the surface charge, as TFEO itself cannot completely screen the charges on the electrodes. As shown in **Figure S12**, in the pure TFEO system that is sandwiched by the negatively and positively charged graphene electrodes, the TFEO molecules could form layered structures when the surface charge density of the graphene electrode is high enough ($|\sigma| \geq 0.6 \text{ e/nm}^2$). This is clearly shown by the visualization of the simulated layered molecular structures under the surface charge density of $\sigma = \pm 0.6 \text{ e/nm}^2$ (**Figure S12a-b**) and verified by the repeated sparks in the charge density profiles (**Figure S12c**). This suggests that TFEO itself does not form EDL and cannot screen the surface charges. Thus, the cations must exist in the TFEO region to screen the surface charge, which is the reason why EDL forms. On the other hand, partial desolvation allows coordination between Li^+ and TFEO diluent, which will be explained in **Section 2.3**.

2.3 The adsorption layer in the EDL

In the bulk phase of LCE(1-9), each Li^+ is solvated by a total number of around 3.02 anion and solvent molecules (0.32 FSI^- and 2.71 DME) on average (**Figure S13a**). The total Li^+ ion coordination numbers are 3.81 (2.44 FSI^- and 1.37 DME) in the bulk phase of HCE(1-1.4) and 3.93 (2.73 FSI^- and 1.20 DME) in the bulk phase of HCE(1-1.2). In the bulk phase of LHCE(1-1.2-2) with a total Li^+ coordination number of 3.90, the coordination number of Li^+ to FSI^- is slightly increased to 2.74 and the coordination number to DME is slightly decreased to 1.14 compared to those in HCE(1-1.2). More than that, the ratio of AGG⁺ is significantly increased from 17% to 25% while the ratios of both CIP and AGG are reduced, indicating higher localized



concentration.⁹ The coordination number of Li⁺-TFEO is 0.02 in LHCE(1-1.2-2), suggesting minimal participation of TFEO in the solvation shell of Li⁺ ions.⁹

The Li⁺ solvation shell in LHCE(1-1.2-2) has changed when it comes to the EDL and it will return to its bulk properties outside of EDL. To capture this transition, we further divide the EDL (10 Å from the charged electrode) into two regions, *i.e.* 0-5 Å region as the first layer and 5-10 Å region as the second layer. Within 5 Å from the electrode, the number density profiles of Li⁺ ions (in **Figures S5-S9**) all show the first prominent peak value at around 2.5 Å from the negatively charged electrode (**Figures S5-S9**). Thus, these are considered as adsorbed cations.

Figure 5 shows all the possible solvation shells of the adsorbed Li⁺ ions for the investigated electrolyte systems. In most cases, Li⁺ ions coordinate with only two of the anion, solvent, and diluent molecules due to partial desolvation (**Figures 5a,c-f**). A particularly interesting finding is that the TFEO molecule can enter the solvation shell of Li⁺ ions (**Figures 5d-e**), which cannot be found in the bulk LHCE(1-1.2-2). It has been shown in our previous study that each Li⁺ ion can be solvated by three DME molecules or two TFEO molecules in the gas phase.⁹ The binding energies for Li⁺-FSI⁻ pair (6.07 eV) and Li⁺-3DME pair (5.39 eV) are both significantly higher than that for the Li⁺-2TFEO pair (2.89 eV).⁹ As a result, the TFEO diluent molecule is not able to enter the Li⁺ ion solvation shell in the bulk LHCE(1-1.2-2). However, in the EDL of LHCE(1-1.2-2), the partial solvation shell of the adsorbed Li⁺ ions can be filled by the participation of the TFEO molecule. The partial solvation shell of Li⁺ ion can be even solely occupied by three ether oxygen atoms from one single TFEO molecule without any participation of FSI⁻ ion or DME (**Figure 5g**).



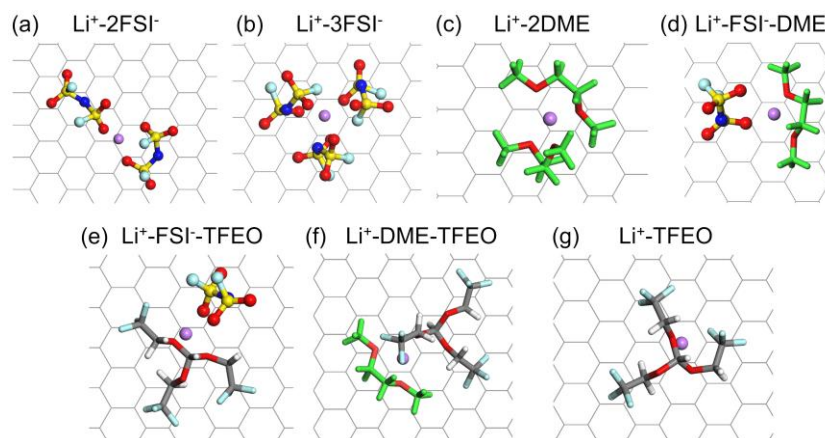


Figure 5. Representative solvation shells of the adsorbed Li^+ ions in the LCE, HCE, and LHCE systems consisting of LiFSI salt, DME solvent, and TFEO diluent: Li^+ coordinating with (a) two FSI $^-$; (b) three FSI $^-$; (c) two DME; (d) one FSI $^-$ and two DME; (e) one FSI $^-$ and one TFEO; (f) one DME and one TFEO; (g) one TFEO.

Figure 6 shows the total coordination numbers of the first-layer Li^+ ions to the other electrolyte species decrease by around 1.5 when the surface charge density of the graphene electrode increases from $\sigma=0.0 \text{ e/nm}^2$ to $\sigma=\pm 1.2 \text{ e/nm}^2$, suggesting the desolvation of Li^+ ions under more negative overpotential. As shown in **Figure 5**, when Li^+ ion adsorbs on the electrode, only half of its solvation shell can be occupied by the electrolyte species. It is seen from **Figures 6d-e** that, in the EDL of LHCE(1-1.2-2) systems, starting at the surface charge density of $\sigma=\pm 0.6 \text{ e/nm}^2$, an average of 0.1-0.8 TFEO molecules show up in the solvation shell of each first-layer Li^+ ion. For the second-layer Li^+ ions, their solvation shells can be completely occupied by other electrolyte species, and thus the total coordination numbers are mostly independent of the surface charge densities of the graphene electrode (**Figure S14**). Beyond the EDL region, the coordination of Li^+ is close to the bulk electrolytes.



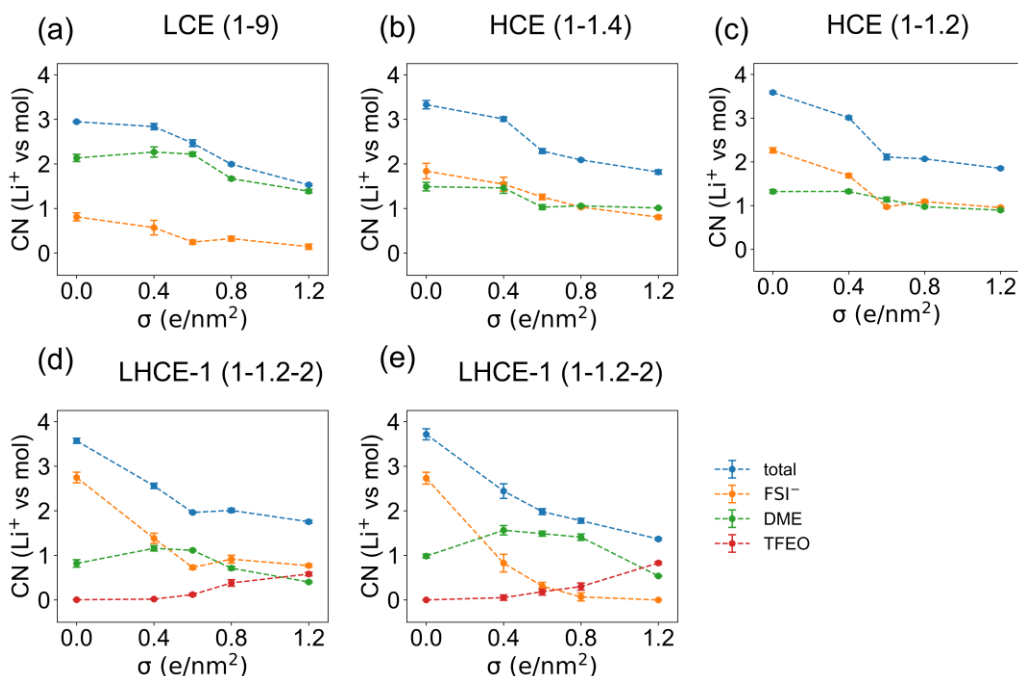


Figure 6. Coordination numbers between the first-layer Li⁺ ions in the EDL (within 5.0 Å from the negatively charged graphene electrode) and other species (FSI⁻, DME, and TFEO) under different surface charge densities of the graphene electrode.

The Stern model with an adsorbed cation layer and a more diffused layer with cation, anion, solvent, and diluents, can be used to describe the EDL of this type of electrolyte but would miss the heterogeneity.³³ Because only a partial solvation shell is needed in the Stern layer in the EDL, the heterogeneous structures of LHCE in the EDL can be very different from that in the bulk. The diluent region contains Li⁺ ions in the EDL but does not have any ions in the bulk of LHCE.⁹ This is because TFEO cannot form a complete solvation shell in the bulk electrolyte due to the steric effect. The appearance of Li⁺ ions in the diluent is also necessary for the EDL, as TFEO alone cannot screen the charge. This implies the TFEO will also contribute to SEI formation, especially when it is coordinated with Li⁺, in which case its reduction voltage will be increased (**Figure 7** and **Table S2**).



2.4 Impact of the EDL of LHCE on its electrolyte reduction and SEI formation

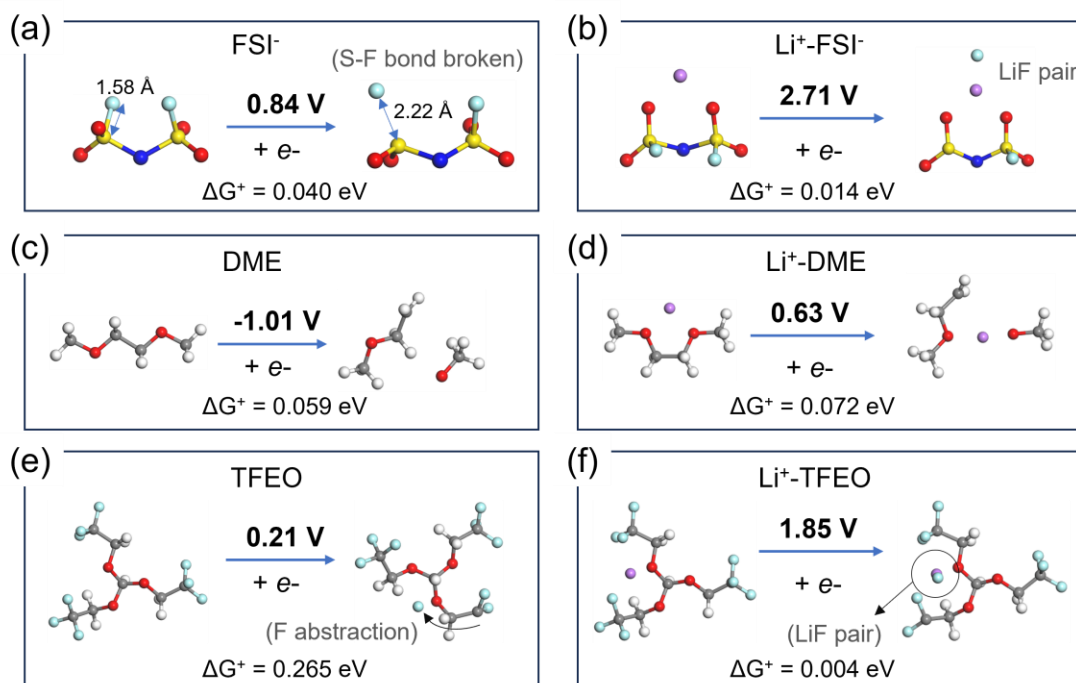


Figure 7. DFT-optimized geometries of the redox species and calculated reduction potentials for (a) FSI, (b) LiFSI, (c) DME, (d) Li⁺-DME, (e) TFEO, and (f) Li⁺-TFEO. The gray, red, white, purple, light blue, yellow, and dark blue spheres stand for C, O, H, Li, F, S, and N atoms, respectively. Reduction reaction barriers are calculated following Nelsen's four-point method.⁵³

Figure 7 shows the DFT computed reduction voltage of the anion, solvent, and diluent that constitute the LHCE electrolyte. The reduction reaction barriers (ΔG^\ddagger) are also calculated following Marcus theory⁵⁴⁻⁵⁶ and Nelsen's four-point method⁵³ to account for the outer-shell and inner-shell reorganization energies (**Figure S15** and Methods in SI). Since the Marcus theory estimation for the outer-shell reorganization energy is based on homogenous solutions, its accuracy on LHCE needs to be validated in future studies with more advanced methods using molecular dynamics simulations.^{57,58} Nevertheless, the results show that free DME will not be reduced and contribute to SEI formation. As many experiments have correlated better SEI performance with F



species in the SEI. Both FSI⁻ anion (other reduction pathways are shown in **Figure S16**) and the TFEO can contribute to LiF in SEI. Free TFEO can be reduced above Li deposition voltage, but the barrier is higher compared to other reduction reactions. The reduction of TFEO occurs at a much higher voltage with a much lower barrier when it is associated with Li⁺ ion. Thus, without clarifying the EDL structure of LHCE, the contribution of TFEO diluent on SEI formation may be overlooked.

As we discussed above, the EDL presents complicated local structures that can dramatically change the reduction voltage and the composition of the SEI layer. Following the MD-DFT-data protocol devised by Wu et al.,²¹ we assume all the species in the EDL may be reduced via out-sphere electron transfer reactions. Thus, the statistics of the electrolyte in the EDL are analyzed in terms of a) solvents/anions/diluent coordinated with Li⁺ in the first solvation shell and b) free solvent/anions/diluent species (not coordinated to any Li⁺).²¹ The numbers of these electrolyte species in the EDL for the LCE, HCE, and LHCE electrolyte systems are summarized in **Figure S17**. Then the onset of the one-electron reduction reaction voltage was calculated for all the major Li⁺ solvation shell structures (**Figure S18**) and the free species (**Figure 7**). Their occurrence probabilities are ranked to show the sequence of reduction reactions while the potential on the electrode is lowered to the Li⁺/Li⁰ reduction voltage, to directly correlate with the SEI components observed in experiments (**Figure S19**).



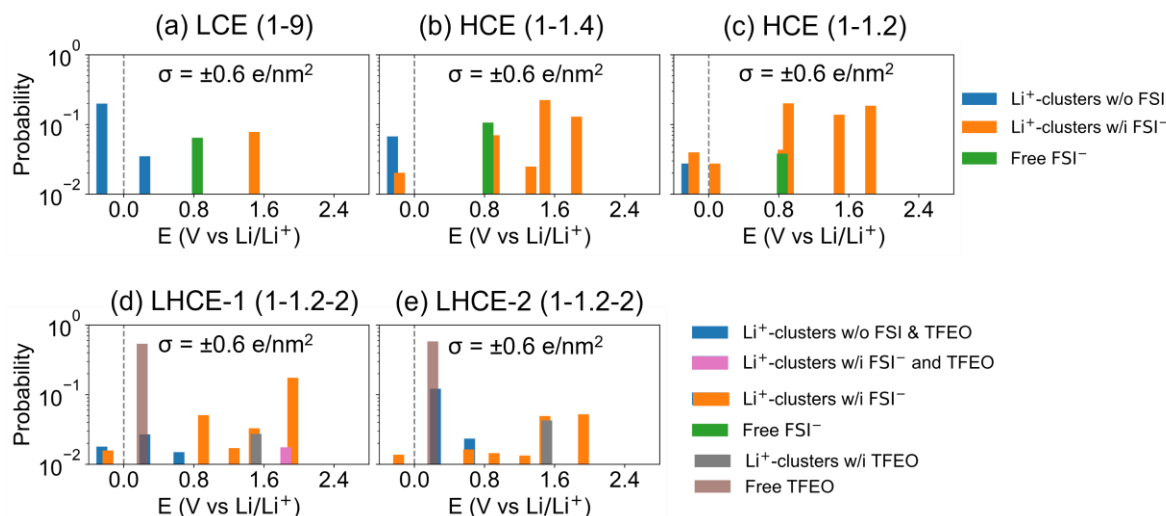


Figure 8. Probabilities in logscale of DFT-calculated reduction potentials in the EDL for (a) LCE(1-9), (b) HCE(1-1.4), (c) HCE(1-1.2), (d) LHCE-1(1-1.2-2) and (e) LHCE-2(1-1.2-2) electrolytes under surface charge density of $\sigma = \pm 0.6 \text{ e/nm}^2$. Contributions from different clusters and species are color-encoded, including Li⁺-coordinated clusters with or without FSI⁻ and/or TFEO, as well as free FSI⁻ and free TFEO. Free DME has a negative reduction potential of -1.01 V vs Li/Li⁺, and is not shown in this figure.

Figure 8 shows the probability of different types of EDL species being reduced at different voltages. See more details about the definition of the probability of different types in the Methods section of SI. As the electric potential is lowered in SEI formation cycles (i.e., from higher to lower values), the first to be reduced are Li⁺ associated FSI⁻ anions (orange color), followed by Li⁺ associated TFEO (gray color); free FSI⁻ (green color); and lastly Li⁺ associated DME (blue color) species. Although FSI⁻ anions reduce first, the LCE has a higher percentage of DME reduction induced SEI, thus less LiF content (**Figure 8a**). With increasing salt concentrations to HCE, the probability of Li⁺ associated DME (blue color) reduction is minimized and the contributions from various FSI⁻ containing species are dramatically increased. **Figures 8b** and **8c** indeed predict that HCE(1-1.4) and HCE(1-1.2) only have anion derived SEI and there are no contributions from DME reduction above the Li/Li⁺ reduction voltage. Adding TFEO will introduce another F source,



as both Li^+ -associated and free TFEOs can be reduced and generate LiF in the SEI. It is predicted that Li^+ -associated DME also contributes to SEI formation (blue colors in **Figure 8d and 8e**), however its contribution is much smaller than the TFEO. The multiple LiF sources and the different reduction kinetics of free TFEO versus other species may generate more heterogeneous nano-grained LiF phases in the SEI, as reported recently on the local SEI structures probed by NMR.⁵⁹ This suggests the design of LHCE must consider the SEI formability of the diluents, as they have a large contribution to the EDL layer. Fluorinated diluents that generate LiF are needed.^{60–62}

4. Conclusions

To conclude, we have revealed the EDL structures of LHCE through MD simulations of the prototypical system of LiFSI-1.2DME-2TFEO for Li batteries. Systematic comparisons have been made with the EDL structures for LCE (LiFSI-9DME), HCE (LiFSI-1.4DME) and HCE (LiFSI-1.2DME). Both LCE and HCE show homogeneous spatial distributions of species in the EDL. For LCE, the adsorbed Li^+ ions mainly coordinate with solvent molecules while the anion species are mostly repelled away from the negatively charged electrode surface. For HCE, the Li^+ ions are not only coordinating with solvent molecules but also coordinating with a significant amount of salt anions due to strong ion pairing and the formation of aggregates.

For LHCE, the heterogeneous micelle-like structures of the bulk are extended to the EDL, which are divided into the Li^+ -rich salt-solvent cluster region and the Li^+ -poor diluent region. The heterogeneity of this type of electrolyte is beyond what can be described by the Stern model with an adsorbed cation layer and a more diffused layer with ions, solvents, and diluents. Despite non-



coordination between Li^+ ion and TFEO diluent in the bulk of LHCE, the diluent region contains Li^+ ions in the EDL to effectively screen the negative charge from the electrode. Only a partial solvation shell is needed near the surface, which allows coordination between Li^+ and TFEO diluent. Thus, the reduction voltage of TFEO will be increased by the association of Li^+ ions in the EDL, highlighting one of the impacts of the heterogeneous EDL structures on SEI formation. This work helps extend the development of the EDL theory and guides the design of more effective LHCE for high-performance rechargeable batteries.

Conflict of interest

The authors have no conflicts to disclose.

Acknowledgments

Q. Wu and Y. Qi thank NASA for financial support (grant no. 80NSSC21M0107) and the Center for Computation and Visualization at Brown for providing computational resources.

Data Availability

The data that support the findings of this study are available from the corresponding author upon reasonable request.



REFERENCES

- [1] Wang, H.; Yu, Z.; Kong, X.; Kim, S. C.; Boyle, D. T.; Qin, J.; Bao, Z.; Cui, Y. Liquid Electrolyte: The Nexus of Practical Lithium Metal Batteries. *Joule* **2022**, *6* (3), 588–616.
- [2] Li, S.; Jiang, M.; Xie, Y.; Xu, H.; Jia, J.; Li, J. Developing High-Performance Lithium Metal Anode in Liquid Electrolytes: Challenges and Progress. *Advanced Materials* **2018**, *30* (17), 1–29.
- [3] Kim, J.; Chae, O. B.; Lucht, B. L. Perspective—Structure and Stability of the Solid Electrolyte Interphase on Silicon Anodes of Lithium-Ion Batteries. *J Electrochem Soc* **2021**, *168* (3), 030521.
- [4] Lee, B.; Paek, E.; Mitlin, D.; Lee, S. W. Sodium Metal Anodes: Emerging Solutions to Dendrite Growth. *Chem Rev* **2019**, *119* (8), 5416–5460.
- [5] Wang, J.; Yamada, Y.; Sodeyama, K.; Chiang, C. H.; Tateyama, Y.; Yamada, A. Superconcentrated Electrolytes for a High-Voltage Lithium-Ion Battery. *Nat Commun* **2016**, *7* (May), 1–9.
- [6] Yamada, Y.; Yamada, A. Review—Superconcentrated Electrolytes for Lithium Batteries. *J Electrochem Soc* **2015**, *162* (14), A2406–A2423.
- [7] Cao, X.; Jia, H.; Xu, W.; Zhang, J.-G. Review—Localized High-Concentration Electrolytes for Lithium Batteries. *J Electrochem Soc* **2021**, *168* (1), 010522.
- [8] Piao, N.; Ji, X.; Xu, H.; Fan, X.; Chen, L.; Liu, S.; Garaga, M. N.; Greenbaum, S. G.; Wang, L.; Wang, C.; et al. Countersolvent Electrolytes for Lithium-Metal Batteries. *Adv Energy Mater* **2020**, *10* (10), 1–9.
- [9] Efaw, C. M.; Wu, Q.; Gao, N.; Zhang, Y.; Zhu, H.; Gering, K.; Hurley, M. F.; Xiong, H.; Hu, E.; Cao, X.; et al. Localized High-Concentration Electrolytes Get More Localized through Micelle-like Structures. *Nat Mater* **2023**, *22* (12), 1531–1539.
- [10] Hossain, M. J.; Wu, Q.; Marin Bernardez, E. J.; Quilty, C. D.; Marschilok, A. C.; Takeuchi, E. S.; Bock, D. C.; Takeuchi, K. J.; Qi, Y. The Relationship between Ionic Conductivity and Solvation Structures of Localized High-Concentration Fluorinated Electrolytes for Lithium-Ion Batteries. *J Phys Chem Lett* **2023**, *14* (34), 7718–7731.
- [11] Schryver, S. B.; Ramsden, W.; Cross, C. F.; Schidrowitz, P.; Dreaper, W. P.; McBain, J. W.; Turner, T.; Worley, F. P.; Martin, C. J.; Bousfield, W. R.; et al. Discussion: Colloids and Their Viscosity. *Transactions of the Faraday Society* **1913**, *9*, 93.
- [12] McClements, D. J. Nanoemulsions versus Microemulsions: Terminology, Differences, and Similarities. *Soft Matter* **2012**, *8* (6), 1719–1729.
- [13] Verma, A.; Schulze, M. C.; Colclasure, A. Micelle-like Bulk Structure of Localized High-Concentration Electrolytes. *Joule* **2024**, *8* (1), 10–12.



- [14] Wu, J. Understanding the Electric Double-Layer Structure, Capacitance, and Charging Dynamics. *Chem Rev* **2022**, *122* (12), 10821–10859.
- [15] Swift, M. W.; Swift, J. W.; Qi, Y. Modeling the Electrical Double Layer at Solid-State Electrochemical Interfaces. *Nat Comput Sci* **2021**, *1* (3), 212–220.
- [16] Jorn, R.; Kumar, R.; Abraham, D. P.; Voth, G. A. Atomistic Modeling of the Electrode-Electrolyte Interface in Li-Ion Energy Storage Systems: Electrolyte Structuring. *Journal of Physical Chemistry C* **2013**, *117* (8), 3747–3761.
- [17] Borodin, O.; Ren, X.; Vatamanu, J.; Von Wald Cresce, A.; Knap, J.; Xu, K. Modeling Insight into Battery Electrolyte Electrochemical Stability and Interfacial Structure. *Acc Chem Res* **2017**, *50* (12), 2886–2894.
- [18] Wang, A.; Kadam, S.; Li, H.; Shi, S.; Qi, Y. Review on Modeling of the Anode Solid Electrolyte Interphase (SEI) for Lithium-Ion Batteries. *NPJ Comput Mater* **2018**, *4* (1), 15.
- [19] Attia, P. M.; Das, S.; Harris, S. J.; Bazant, M. Z.; Chueh, W. C. Electrochemical Kinetics of SEI Growth on Carbon Black: Part I. Experiments. *J Electrochem Soc* **2019**, *166* (4), E97–E106.
- [20] Das, S.; Attia, P. M.; Chueh, W. C.; Bazant, M. Z. Electrochemical Kinetics of SEI Growth on Carbon Black: Part II. Modeling. *J Electrochem Soc* **2019**, *166* (4), E107–E118.
- [21] Wu, Q.; McDowell, M. T.; Qi, Y. Effect of the Electric Double Layer (EDL) in Multicomponent Electrolyte Reduction and Solid Electrolyte Interphase (SEI) Formation in Lithium Batteries. *J Am Chem Soc* **2023**, *145* (4), 2473–2484.
- [22] Chen, F. Atomistic Modelling Approaches to Understanding the Interfaces of Ionic Liquid Electrolytes for Batteries and Electrochemical Devices. *Curr Opin Electrochem* **2022**, *35*, 101086.
- [23] Suo, L.; Borodin, O.; Gao, T.; Olguin, M.; Ho, J.; Fan, X.; Luo, C.; Wang, C.; Xu, K. “Water-in-Salt” Electrolyte Enables High-Voltage Aqueous Lithium-Ion Chemistries. *Science (1979)* **2015**, *350* (6263), 938–943.
- [24] Yang, C.; Chen, J.; Qing, T.; Fan, X.; Sun, W.; von Cresce, A.; Ding, M. S.; Borodin, O.; Vatamanu, J.; Schroeder, M. A.; et al. 4.0 V Aqueous Li-Ion Batteries. *Joule* **2017**, *1* (1), 122–132.
- [25] Vatamanu, J.; Borodin, O. Ramifications of Water-in-Salt Interfacial Structure at Charged Electrodes for Electrolyte Electrochemical Stability. *Journal of Physical Chemistry Letters* **2017**, *8* (18), 4362–4367.
- [26] Li, C.-Y.; Chen, M.; Liu, S.; Lu, X.; Meng, J.; Yan, J.; Abruña, H. D.; Feng, G.; Lian, T. Unconventional Interfacial Water Structure of Highly Concentrated Aqueous Electrolytes at Negative Electrode Polarizations. *Nat Commun* **2022**, *13* (1), 5330.
- [27] Kahlweit, M. Microemulsions. *Science (1979)* **1988**, *240* (4852), 617–621.



- [28] Holoubek, J.; Yu, K.; Wu, J.; Wang, S.; Li, M.; Gao, H.; Hui, Z.; Hyun, G.; Yin, Y.; Mu, A. U.; et al. Toward a Quantitative Interfacial Description of Solvation for Li Metal Battery Operation under Extreme Conditions. *Proceedings of the National Academy of Sciences* **2023**, *120* (41), 2017.
- [29] Zeng, L.; Peng, J.; Zhang, J.; Tan, X.; Ji, X.; Li, S.; Feng, G. Molecular Dynamics Simulations of Electrochemical Interfaces. *J Chem Phys* **2023**, *159* (9).
- [30] Helmholtz, H. Ueber Einige Gesetze Der Vertheilung Elektrischer Ströme in Körperlichen Leitern, Mit Anwendung Auf Die Thierisch-elektrischen Versuche (Schluss.). *Ann Phys* **1853**, *165* (7), 353–377.
- [31] Gouy, M. Sur La Constitution de La Charge Électrique à La Surface d'un Électrolyte. *Journal de Physique Théorique et Appliquée* **1910**, *9* (1), 457–468.
- [32] Chapman, D. L. LI. A Contribution to the Theory of Electrocapillarity. *The London, Edinburgh, and Dublin Philosophical Magazine and Journal of Science* **1913**, *25* (148), 475–481.
- [33] Stern, O. ZUR THEORIE DER ELEKTROLYTISCHEN DOPPELSCHICHT. *Zeitschrift für Elektrochemie und angewandte physikalische Chemie* **1924**, *30* (21–22), 508–516.
- [34] Giffin, G. A. The Role of Concentration in Electrolyte Solutions for Non-Aqueous Lithium-Based Batteries. *Nat Commun* **2022**, *13* (1), 5250.
- [35] Borukhov, I.; Andelman, D.; Orland, H. Steric Effects in Electrolytes: A Modified Poisson-Boltzmann Equation. *Phys Rev Lett* **1997**, *79* (3), 435–438.
- [36] Kornyshev, A. A. Double-Layer in Ionic Liquids: Paradigm Change? *Journal of Physical Chemistry B* **2007**, *111* (20), 5545–5557.
- [37] Bazant, M. Z.; Storey, B. D.; Kornyshev, A. A. Double Layer in Ionic Liquids: Overscreening versus Crowding. *Phys Rev Lett* **2011**, *106* (4), 046102.
- [38] Goodwin, Z. A. H.; Kornyshev, A. A. Underscreening, Overscreening and Double-Layer Capacitance. *Electrochem commun* **2017**, *82* (June), 129–133.
- [39] Zhang, Z.; Gao, Y.; Chen, S.; Huang, J. Understanding Dynamics of Electrochemical Double Layers via a Modified Concentrated Solution Theory. *J Electrochem Soc* **2020**, *167* (1), 013519.
- [40] McEldrew, M.; Goodwin, Z. A. H.; Kornyshev, A. A.; Bazant, M. Z. Theory of the Double Layer in Water-in-Salt Electrolytes. *Journal of Physical Chemistry Letters* **2018**, *9* (19), 5840–5846.
- [41] Zhang, M.; Chen, Y.; Eikerling, M.; Huang, J. Grand-Canonical Variational Theory of Oscillatory Fields at Electrified Metal-Solution Interfaces. **2024**, doi: 10.26434/chemrxiv-2024-c5dvr.



- [42] Goodwin, Z. A. H.; McEldrew, M.; Kozinsky, B.; Bazant, M. Z. Theory of Cation Solvation and Ionic Association in Nonaqueous Solvent Mixtures. *PRX Energy* **2023**, *2* (1), 013007.
- [43] Yao, N.; Chen, X.; Fu, Z.; Zhang, Q. Applying Classical, Ab Initio, and Machine-Learning Molecular Dynamics Simulations to the Liquid Electrolyte for Rechargeable Batteries. *Chem Rev* **2022**, *122* (12), 10970–11021.
- [44] Scalfi, L.; Salanne, M.; Rotenberg, B. Molecular Simulation of Electrode-Solution Interfaces. *Annu Rev Phys Chem* **2021**, *72* (1), 189–212.
- [45] Sundararaman, R.; Vigil-Fowler, D.; Schwarz, K. Improving the Accuracy of Atomistic Simulations of the Electrochemical Interface. *Chem Rev* **2022**, *122* (12), 10651–10674.
- [46] Qian, J.; Henderson, W. A.; Xu, W.; Bhattacharya, P.; Engelhard, M.; Borodin, O.; Zhang, J.-G. High Rate and Stable Cycling of Lithium Metal Anode. *Nat Commun* **2015**, *6* (1), 6362.
- [47] Cao, X.; Zou, L.; Matthews, B. E.; Zhang, L.; He, X.; Ren, X.; Engelhard, M. H.; Burton, S. D.; El-Khoury, P. Z.; Lim, H. S.; et al. Optimization of Fluorinated Orthoformate Based Electrolytes for Practical High-Voltage Lithium Metal Batteries. *Energy Storage Mater* **2021**, *34*, 76–84.
- [48] McEldrew, M.; Goodwin, Z. A. H.; Bi, S.; Bazant, M. Z.; Kornyshev, A. A. Theory of Ion Aggregation and Gelation in Super-Concentrated Electrolytes. *Journal of Chemical Physics* **2020**, *152* (23).
- [49] Goodwin, Z. A. H.; McEldrew, M.; De Souza, J. P.; Bazant, M. Z.; Kornyshev, A. A. Gelation, Clustering, and Crowding in the Electrical Double Layer of Ionic Liquids. *Journal of Chemical Physics* **2022**, *157* (9).
- [50] Li, Y.; Qi, Y. Energy Landscape of the Charge Transfer Reaction at the Complex Li/SEI/Electrolyte Interface. *Energy Environ Sci* **2019**, *12* (4), 1286–1295.
- [51] Abbott, J. W.; Hanke, F. Kinetically Corrected Monte Carlo–Molecular Dynamics Simulations of Solid Electrolyte Interphase Growth. *J Chem Theory Comput* **2022**, *18* (2), 925–934.
- [52] Borodin, O.; Olguin, M.; Spear, C. E.; Leiter, K. W.; Knap, J. Towards High Throughput Screening of Electrochemical Stability of Battery Electrolytes. *Nanotechnology* **2015**, *26* (35), 354003.
- [53] Nelsen, S. F.; Blackstock, S. C.; Kim, Y. Estimation of Inner Shell Marcus Terms for Amino Nitrogen Compounds by Molecular Orbital Calculations. *J Am Chem Soc* **1987**, *109* (3), 677–682.
- [54] Marcus, R. A. On the Theory of Electron-Transfer Reactions. VI. Unified Treatment for Homogeneous and Electrode Reactions. *J Chem Phys* **1965**, *43* (2), 679–701.
- [55] Marcus, R. A. Electron Transfer Reactions in Chemistry. Theory and Experiment. *Rev Mod Phys* **1993**, *65* (3), 599–610.



- [56] Silverstein, T. P. Marcus Theory: Thermodynamics CAN Control the Kinetics of Electron Transfer Reactions. *J Chem Educ* **2012**, *89* (9), 1159–1167.
- [57] Kuharski, R. A.; Bader, J. S.; Chandler, D.; Sprik, M.; Klein, M. L.; Impey, R. W. Molecular Model for Aqueous Ferrous–Ferric Electron Transfer. *J Chem Phys* **1988**, *89* (5), 3248–3257.
- [58] Yang, C.-H.; Wang, C.-I.; Wang, Y.-S.; Hsu, C.-P. Non-Negligible Outer-Shell Reorganization Energy for Charge Transfer in Nonpolar Systems. *J Chem Theory Comput* **2024**, *20* (16), 6981–6991.
- [59] Svirinovsky-Arbeli, A.; Juelsholt, M.; May, R.; Kwon, Y.; Marbella, L. E. Using NMR Spectroscopy to Link Structure to Function at the Li Solid Electrolyte Interphase. *Joule*. Cell Press July 17, 2024, pp 1919–1935.
- [60] Chen, J.; Zhang, H.; Fang, M.; Ke, C.; Liu, S.; Wang, J. Design of Localized High-Concentration Electrolytes via Donor Number. *ACS Energy Lett* **2023**, *8* (4), 1723–1734.
- [61] Wang, Y.; Li, Z.; Hou, Y.; Hao, Z.; Zhang, Q.; Ni, Y.; Lu, Y.; Yan, Z.; Zhang, K.; Zhao, Q.; et al. Emerging Electrolytes with Fluorinated Solvents for Rechargeable Lithium-Based Batteries. *Chemical Society Reviews*. Royal Society of Chemistry April 3, 2023, pp 2713–2763.
- [62] Moon, J.; Kim, D. O.; Bekaert, L.; Song, M.; Chung, J.; Lee, D.; Hubin, A.; Lim, J. Non-Fluorinated Non-Solvating Cosolvent Enabling Superior Performance of Lithium Metal Negative Electrode Battery. *Nat Commun* **2022**, *13* (1), 4538.



Data Availability Statement

View Article Online
DOI: 10.1039/D5EE00206K

The data that support the findings of this study are available from the corresponding author upon reasonable request.

