

Faraday Discussions

Accepted Manuscript



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

This article can be cited before page numbers have been issued, to do this please use: Z. Liu, A. Saiani and A. F. Miller, *Faraday Discuss.*, 2025, DOI: 10.1039/D5FD00036J.

Investigating the co-assembly of amphipathic peptides

*Zixuan Liu^a; Alberto Saiani^b and Aline F. Miller^{a, *}*

View Article Online
DOI: 10.1039/D5FD00036J

^a Department of Chemical Engineering & Manchester Institute of Biotechnology, School of Engineering, Faculty of Science and Engineering, The University of Manchester.

^b Division of Pharmacy and Optometry & Manchester Institute of Biotechnology, School of Health Sciences, Faculty of Biology, Medicine and Health, The University of Manchester.

* Corresponding author: Email: aline.miller@manchester.ac.uk; Phone: 07714094668



Abstract

Self-assembling peptide hydrogels (SAPHs) are increasingly recognised for their potential in biomedical and bioelectronic applications, with recent work focussing on exploiting the understanding of molecular self-assembly across the length scales. The resulting soft hydrogel materials are typically formulated by exploiting the self-assembly of short peptides into fibrillar aggregates that entangle and associate into networks. As more complex systems are thought to be needed to accommodate the needs of various applications, the mixing of peptides to form mixed SAPHs has come to the fore as a potential approach to design new systems with tailored and functional properties. This strategy has raised the question of whether when mixing peptides with different chemical structures results in co-assembly or the formation of distinct fibrillar aggregates. In this work we have used the FITC / Dabcyl FRET pair to investigate the co-assembly of a set of amphipathic short peptides. Our results show that the occurrence of co-assembly is affected the peptides physicochemical properties, in particular solubility and hydrophobic residue side group nature.

Article Online
DOI: 10.1039/D5FD00036J



Introduction

Self-assembling peptide hydrogels (SAPHs) have attracted significant interest over the last decade due to their potential for use in a broad range of biomedical applications, ranging from fully defined scaffolds for in-vitro cell and organoid culture to in-vivo delivery vehicles for molecular drugs, biologics and cells.¹⁻² These soft materials are formulated by exploiting the self-assembly properties of short peptides. A variety of peptide designs that self-assemble into fibres and form hydrogels have been developed over time.³⁻⁶ One particular design that has attracted significant interest is based on the alternation of hydrophobic and hydrophilic residues. Originally developed by Zhang and coworkers⁷⁻⁸ these short peptides, typically 4 to 16 amino acid long, have the ability to self-assemble into β -sheet rich fibres that above a critical gelation concentration associate and/or entangle to form hydrogels.⁹⁻¹¹ This particular family of SAPHs has been shown to be biocompatible¹²⁻¹⁴, non-immunogenic^{12, 15-16} and allow the 3D culture of a broad variety of cells and organoids.¹⁷⁻²³ Recently we have also shown how the physicochemical properties of these peptides, and therefore of the fibres forming the hydrogels, can have a strong impact on cell behaviour and fate.²⁴⁻²⁶

As more complex systems are thought to accommodate the needs of various applications, the integration of different peptides to form mixed SAPHs has come to the fore as a potential approach to design new systems with tailored properties.²⁷⁻²⁹ This strategy has raised the question of when mixing peptides with different chemical structures together, whether co-assembly occurs or distinct fibrillar aggregates form. The issue of short peptide co-assembly has been the subject of a number of recent works showing that peptide properties such as pH and temperature of self-assembly, molecular structure and formulation pathway can dictate whether co-assembly occurs.³⁰⁻³⁴



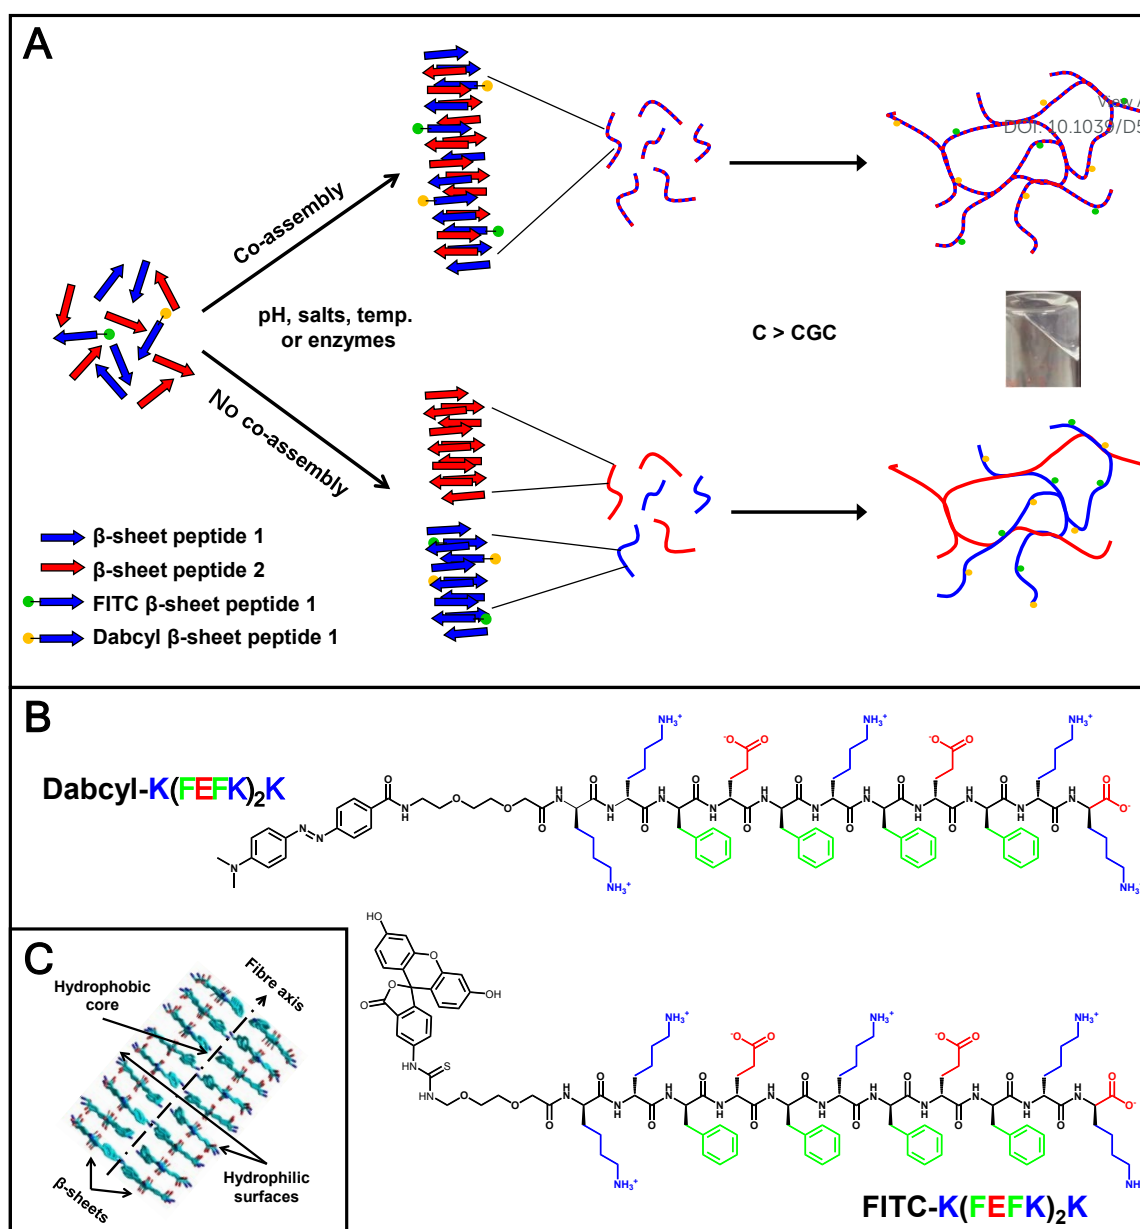


Figure 1 **A)** Schematic representation of the self-assembly pathway of our peptides and labelling approach used to investigate co-assembly; If co-assembly occurs the average spacing between FITC and Dabcyl chromophores increases resulting in an increase in fluorescence. **B)** Chemical structure of labelled peptides used. **C)** Schematic representation of the β -sheet fibres molecular packing.

In the present work we explore whether the Förster resonance energy transfer (FRET) pair fluorescein isothiocyanate (FITC) / 4-(dimethylaminoazo) benzene-4-carboxylic acid (Dabcyl) could be used to investigate the co-assembly of our family of amphipathic oligopeptides. Dabcyl is known



to quench the fluorescence of FITC when the distance between the two chromophores is in the 1 to 10 nm range.³⁵ In Figure 1A a schematic representation of the strategy used is shown. We chose K(FEFK)₂K (F: phenylalanine; E: glutamic acid; K: lysine) as our base peptide (peptide 1 in Figure 1A). This peptide is known to self-assemble into β -sheet rich fibres that entangle and associate to form transparent and stable hydrogels at pH 7.³⁶ This sequence has also been used in previous work to design hydrogels for a range of biomedical applications including drug delivery³⁷ and cell culture³⁸. We conjugated both FITC and Dabcyl to the end N-terminus of K(FEFK)₂K via a short linker to create FITC-K-K(FEFK)₂K and Dabcyl-K-K(FEFK)₂K (Figure 1B). The hypothesis was that when adding a second peptide (peptide 2 in Figure 1A) during hydrogel formulation, if co-assembly occurs the average spacing between FITC and Dabcyl chromophores along the peptide fibres increases resulting in an increase in the overall sample fluorescence. On the other hand, if no co-assembly occurs and distinct fibrillar aggregates are formed, the overall average spacing between FITC and Dabcyl chromophores will remain unchanged resulting in an unchanged overall sample fluorescence.

Mixed SAPHs were created by mixing K(FEFK)₂K with six other peptides whose sequences were built using the same design but had difference physicochemical properties. (AEAK)₂ (A: alanine) was shown in a previous study to be soluble due to its reduced hydrophobicity (replacement of F by A) and therefore did not self-assemble nor form hydrogels at pH 7.³⁹ ^DK(^DF^DE^DF^DK)₂^DK has the opposite chirality to the base peptide which was synthesised using L-amino acids and therefore is not expected to co-assemble with K(FEFK)₂K but to form separate fibrillar aggregates.³³ These two peptides were used as negative controls as in both cases co-assembly was not expected to occur. As the positive control, the base peptide K(FEFK)₂K was used as the secondary peptide as in this case co-assembly will of course occur.

We then used the following four self-assembling peptides: (FEFK)₂, (FEFK)₂K, (VEVK)₂ and (VEVK)₂K (V: valine) to explore the effect that the physicochemical properties of the peptide sequence had on the propensity of co-assembly. These four peptides have been used by our group in previous studies and have all been shown to form on their own similar β -sheet rich fibres and



hydrogels.^{36, 40-42} (FEFK)₂ and (VEVK)₂ will carry an overall neutral charge at pH 7 while (VEVK)₂K and (FEFK)₂K will carry an overall +1 charge. The replacement of F by V in the main sequence will result in a decrease in the overall hydrophobicity of the peptide and is also thought to affect the molecular packing in the core of the β -sheet fibre. A schematic representation of self-assembled fibre structure formed by this family of peptides is shown in Figure 1C. Due to the design used all the hydrophobic side chain residues are thought to be located within the core of the β -sheet fibre, which is formed by two cross- β -sheets coming together to bury their hydrophobic faces.^{36, 39, 43}



Materials and Methods

Materials: All peptides used in this study were purchased from LifeTein Inc. (USA) as HCl salts with a nominal sequence purity of 95%. Peptide sequence purities were confirmed by reverse-phase high performance liquid chromatography and mass spectroscopy by the supplier. All other chemicals were purchased from Sigma-Aldrich and Merk and used as received.

Self-assembling peptide hydrogels (SAPHs) formulation: SAPHs at pH 7 were prepared in 5 mL batches by dissolving the required amount of peptide and conjugated peptide powders in 3.5 mL of HPLC grade water using vigorous vortex mixing for 60 s. The samples initial pH ranged from 2.1 to 2.3. The pH was then adjusted to 7 by the stepwise addition of a 0.5 M NaOH solution. The samples were mixed vigorously and gently centrifuged, if necessary, to remove any bubbles after each NaOH addition. Once pH 7 was achieved, the required additional HPLC-grade water was added to achieve the target batch volume and concentration. The samples were then mixed a final time and stored (at least 12 h) in a fridge before use. Diluted SAPH samples were prepared by adding the required volume, to achieve the targeted dilution, of HPLC-grade water on top of the pre-prepared SAPH and mixing using a vortex. The samples were then once again stored in a fridge for at least 12 hours before use.

Fluorescence: Sample fluorescence emission was measured using an Agilent Cary Eclipse Fluorescence Spectrometer at 520 nm (excitation wavelength 490 nm). 2 ml of each sample was placed in a cuvette with a 2 cm path length. The sample quenching percentage was defined as the ratio of the sample fluorescence with added Dabcyl-K-K(FFFK)₂K to the samples fluorescence without added Dabcyl-K(FFFK)₂K.

Characterization of ¹⁵NK(¹⁵F¹⁵E¹⁵F¹⁵K)₂¹⁵NK SAPH: Attenuated Total Reflectance Fourier-Transform Infrared (ATR-FTIR) spectroscopy and transmission electron microscopy (TEM) were used to characterise the SAPH formed by ¹⁵NK(¹⁵F¹⁵E¹⁵F¹⁵K)₂¹⁵NK at 7.5 mg ml⁻¹. ATR-FTIR measurements were performed on a Bruker VERTEX 80 FTIR spectrometer equipped with a single-bounce diamond ATR accessory. A small drop of hydrogel was placed on the surface of the diamond and pressed in position



using a spatula to ensure good contact between the hydrogel and the diamond surface. The beam path was purged with dry CO₂-scrubbed air. The spectra were an average of 256 scans collected using a 4 cm⁻¹ resolution. An HPLC grade water spectrum was used as a background and subtracted from each sample spectrum. For TEM preparation, samples were diluted 20-fold and vigorously mixed with a vortex to maximise the separation of the fibres. A carbon-coated copper grid (400 mesh grid Electron Microscopy Sciences, Hatfield, Pennsylvania, USA) was glow discharged and charged negatively. The carbon copper grid was then placed sequentially on a 10 µL sample droplet for 60 s, a 10 µL droplet of HPLC grade water for 10 s, a 10 µL droplet of 5% uranyl acetate solution for 30 s, and finally, on a 10 µL droplet of HPLC grade water for 10 s. After each step, excess liquid was drained off using lint-free tissue (90 mm Whatman 1). The grid was then left to air-dry for 2 to 5 min. TEM images were taken using an FEI Tecnai12 BioTwin transmission electron microscope running at 100 kV and equipped with a Gatan Orius SC1000A CCD camera. Rheological measurements were performed using a Discovery Hybrid 2 (DHR-2) rheometer from TA Instruments (New Castle, Delaware, USA) using a 20 mm parallel plate geometry and a 500 µm gap. Hydrogel (200 µL) was pipetted onto the rheometer's static bottom plate and the rheometer top plate lowered to the desired gap size. Sample was covered with a solvent trap to avoid evaporation. Strain sweep experiments were performed at 1 Hz in the 0.01–100% strain range.

Review Article
DOI: 10.1039/D5FD00036J



Result and discussion

First, we investigated the effect that adding FITC-K-K(FEFK)₂K to a range of mixed SAPHs had on the overall samples' fluorescence. All mixed SAPHs were prepared with a base peptide concentration of 3.75 mg ml⁻¹ and a total peptide (base + secondary peptide) concentration of 7.5 mg ml⁻¹. This gave a base to secondary peptide mass ratio of 1:1.

First, we added FITC-K-K(FEFK)₂K only to the mixed SAPHs. As can be seen from **Error! Reference source not found.A**, the samples' fluorescence increased linearly with increasing FITC-K-K(FEFK)₂K content, and this was independent of which second peptide was used to create the mixed SAPHs. This result clearly shows that the secondary peptide does not affect the sample fluorescence in anyway and therefore fluorescence of the mixed SAPHs can be directly compared.

We then chose the highest concentration of FITC-K-K(FEFK)₂K probe containing sample (0.01 mg ml⁻¹) and investigated the effect that adding Dabcyl-K-K(FEFK)₂K to the base SAPHs had on the samples' fluorescence via the quenching percentage which was defined as:

$$\frac{\text{sample fluorescence with Dabcyl-K-K(FEFK)}_2\text{K}}{\text{sample fluorescence without Dabcyl-K-K(FEFK)}_2\text{K}} \times 100 \quad (1)$$

Two K(FEFK)₂K concentrations were used to make these SAPHs: 3.75 mg ml⁻¹ for the initial concentration of the 'base' formulation, and 7.5 mg ml⁻¹, which is the total peptide concentration of the 'mixed' formulations. As can be seen from **Error! Reference source not found.B** the quenching percentage was directly proportional to the Dabcyl-K-K(FEFK)₂K concentration in the range investigated. As expected, the quenching percentages for the 3.75 mg ml⁻¹ base SAPHs were found to be significant higher compared to the 7.5 mg ml⁻¹ base SAPHs, which reflects the increase in distance between the fluorophore, FITC, and quencher, Dabcyl moieties at higher peptide concentration. In addition, the overall quenching percentage for both SAPHs were found to be directly proportional to the Dabcyl-K-K(FEFK)₂K concentration (**Error! Reference source not found.B** open symbols: concentration normalised values). These results confirm that both labelled peptides



co-assembled with the base peptide and that the approach used allows the investigation of co-assembly in these systems. The quenching percentages of these two base SAPH formulations represent the minimum and the maximum quenching expected when co-assembly does, and does not, occur respectively.

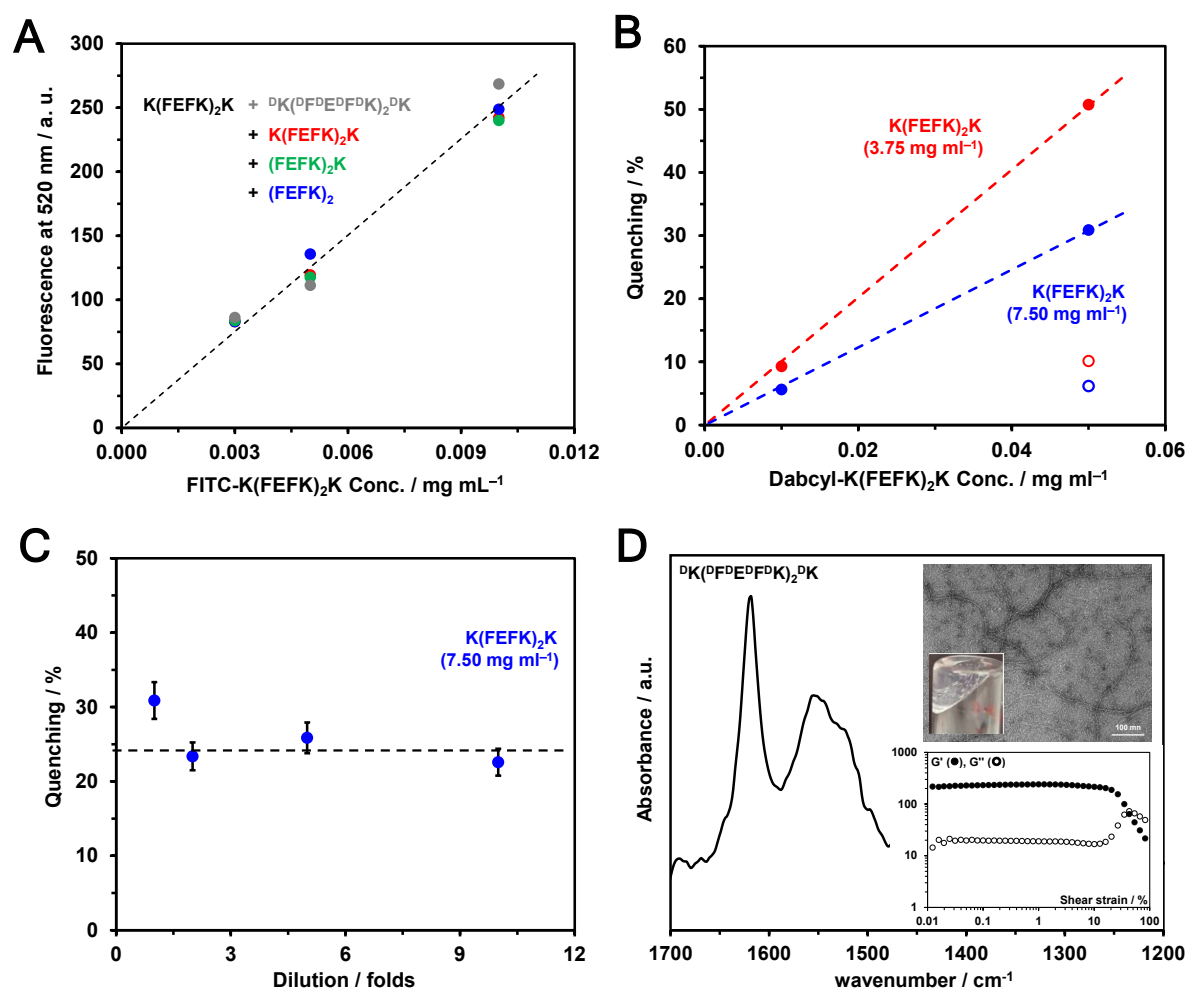


Figure 2: **A)** FITC-K-K(FFFK)₂K concentration vs mixed SAPHs fluorescence; total sample peptide concentration: 7.5 mg mL⁻¹; base peptide to secondary peptide mass ratio: 1:1. **B)** Base SAPHs fluorescence quenching percentage [(sample fluorescence with Dabcyl-K-K(FFFK)₂K / sample fluorescence without Dabcyl-K-K(FFFK)₂K) × 100] vs Dabcyl-K-K(FFFK)₂K concentration; K(FFFK)₂K base SAPHs peptide concentration: 3.75 mg mL⁻¹ (red) and 7.5 mg mL⁻¹ (blue); FITC-K-K(FFFK)₂K concentration: 0.01 mg mL⁻¹; Open symbols: quenching percentages normalised to 0.01 mg mL⁻¹ Dabcyl-



K-K(FEFK)₂K concentration. C) Base SAPH quenching percentage vs dilution fold; base SAPH peptide concentration: 7.5 mg ml⁻¹. D) FTIR spectra of ^DK(^DF^DE^DF^DK)₂^DK SAPH prepared at 7.5 mg ml⁻¹; Insert top: TEM image of fibres formed and photograph of hydrogel; Insert bottom: storage (G') and loss (G'') moduli vs shear strain.

Article Online
DOI: 10.1039/D5FD00036J

It should be noted that FITC quenching can have an intra-fibre, Dabcyl situated along the same peptide fibre, or an inter-fibre, Dabcyl located on a different fibre, origin. In order for this methodology to be reliable the quenching observed should mainly be due to intra-fibre quenching events. We have shown in previous works the mesh size in these networks is in the 10-30 nm range depending on peptide concentration^{39, 43} and therefore inter-fibre quenching events are a possibility. To investigate this point further, we diluted the 7.5 mg ml⁻¹ base SAPH formulation 2-, 5- and 10-folds and measured the resulting samples' fluorescence. By diluting the full sample, the network mesh size / distance between peptide fibres is increased^{39, 43} resulting in an increase in distance between FITC and Dabcyl chromophores located on different fibres. As a result, inter-fibre quenching events are expected to decrease with increasing dilution. On the other hand, along the peptide fibres the ratios between FITC and Dabcyl conjugated peptides and base peptide remain the same and therefore the distance between FITC and Dabcyl along the fibre remains unchanged. As a result, intra-fibre quenching events are expected not to be affected by dilution. Consequently, in the absence of inter-fibre quenching events the diluted samples quenching percentages are expected to remain unchanged. As can be seen from **Error! Reference source not found.C** when diluting 2-fold the quenching percentage was found to decrease slightly ~ 8% and then remained unchanged when further dilutions were performed. This result shows that indeed at 7.5 mg ml⁻¹ concentration some inter-fibre quenching events occur but overall, the quenching observed is mainly due to intra-fibre quenching events.

Next, we investigated how the sample's fluorescence changed when adding the two negative control peptides – (AEAK)₂ and ^DK(^DF^DE^DF^DK)₂^DK – to the base peptide. As mentioned above,



neither of these two peptides are expected to co-assemble with the base peptide. For the latter peptide, $^D\text{K}(\text{DF}^D\text{E}^D\text{F}^D\text{K})_2^D\text{K}$, we first confirmed that it indeed self-assembled into β -sheet rich fibres and formed hydrogels on its own. In Figure 2D where the FTIR spectra obtained for the hydrogel prepared using this peptide at 7.5 mg ml^{-1} is shown. A strong peak at $\sim 1630 \text{ cm}^{-1}$ and a weaker peak at $\sim 1696 \text{ cm}^{-1}$ typical of the adoption by this family of peptides of cross- β -sheet conformations are observed.⁴⁴⁻⁴⁵ The TEM image (Figure 2D insert top) clearly showed the formation of thin semi-flexible fibres with similar dimension, ~ 3 to 4 nm in diameter, to those observed for the base peptide.³⁶ Formation of a hydrogel was confirmed visually (photograph Figure 2D insert top) and mechanically through shear rheometry (Figure 2D insert bottom). As typical for solid-like materials the SAPH storage modulus (G') was found to be one order of magnitude larger than then the loss modulus (G'') and both were found to be constant up to 15% shear strain.

As can be seen from Figure 3A, when adding $(\text{AEAK})_2$ to the base peptide no change in quenching percentage compared to the base SAPH formulation at 3.75 mg ml^{-1} was observed confirming that as expected no co-assembly occurred. As mentioned above $(\text{AEAK})_2$ is soluble and does not self-assemble³⁹ and is therefore simply molecularly dissolved in the water phase of the hydrogel. For the $^D\text{K}(\text{DF}^D\text{E}^D\text{F}^D\text{K})_2^D\text{K}$ peptide a slight decrease in quenching percentage ($\sim 4 \%$, Figure 3A) was observed compared to the base SAPH formulation at 7.5 mg ml^{-1} . In this case too no co-assembly was expected but this peptide, as shown above, does self-assemble into β -sheet rich fibres. As a result, two independent interpenetrating fibrillar networks are thought to form. The slight decrease observed in quenching percentage is thought to be due to the presence of $^D\text{K}(\text{DF}^D\text{E}^D\text{F}^D\text{K})_2^D\text{K}$ fibrillar network limiting inter-fibre quenching events.

We then went on to investigate the change in samples' fluorescence when the peptides: $(\text{FEFK})_2$ and $(\text{FEFK})_2\text{K}$ were used to create mixed SAPHs. It should be noted that when formulating the SAPHs, peptide powders were mixed first, before water was added resulting in the formation of acidic peptide solutions ($\text{pH} \sim 2.2$). Self-assembly and hydrogelation were then triggered by adjusting the pH of the solutions through stepwise addition of NaOH and vortexing after each step to ensure



homogeneity (see materials and methods section for more details). These three peptides (base peptide + the two secondary peptides) were designed with the same sequence core – (FEFK)₂ – but with different numbers of K tagged at the peptide ends – none, one and two – leading to varying peptide charge vs pH profiles (Figure 3B). As we have shown in our previous work, transparent hydrogel formation in these systems tends to occur when the overall charge carried by the peptide is in the $\sim +2.5$ to $+1.5$ range.^{36, 46} As can be seen from Figure 3B this leads to different phase behaviour vs pH profiles for each peptide. The base peptide, K(FEFK)₂K, formed transparent SAPHs for pH $> \sim 5.5$. For (FEFK)₂K transparent SAPHs were found to form in the pH range: ~ 4 to 5.5 . Above ~ 5.5 the charge carried by the peptide is approaching $+1$ resulting in the formation of cloudy SAPHs. As discussed in our previous work this is due to the formation of large fibre aggregates that scatter light. Indeed, as electrostatic repulsion between fibre decreases with increasing pH, hydrophobic attractive inter-fibre interactions become dominant leading to fibre aggregation. This effect is even more marked for (FEFK)₂. In this case transparent SAPHs formed in the pH range: ~ 3 to 4 , while cloudy SAPHs form in the pH range: ~ 4 to 5.5 . Above 5.5 the overall charge carried by the peptide becomes neutral and hydrophobic interactions dominate leading to fibre aggregation and precipitation.^{36, 46}



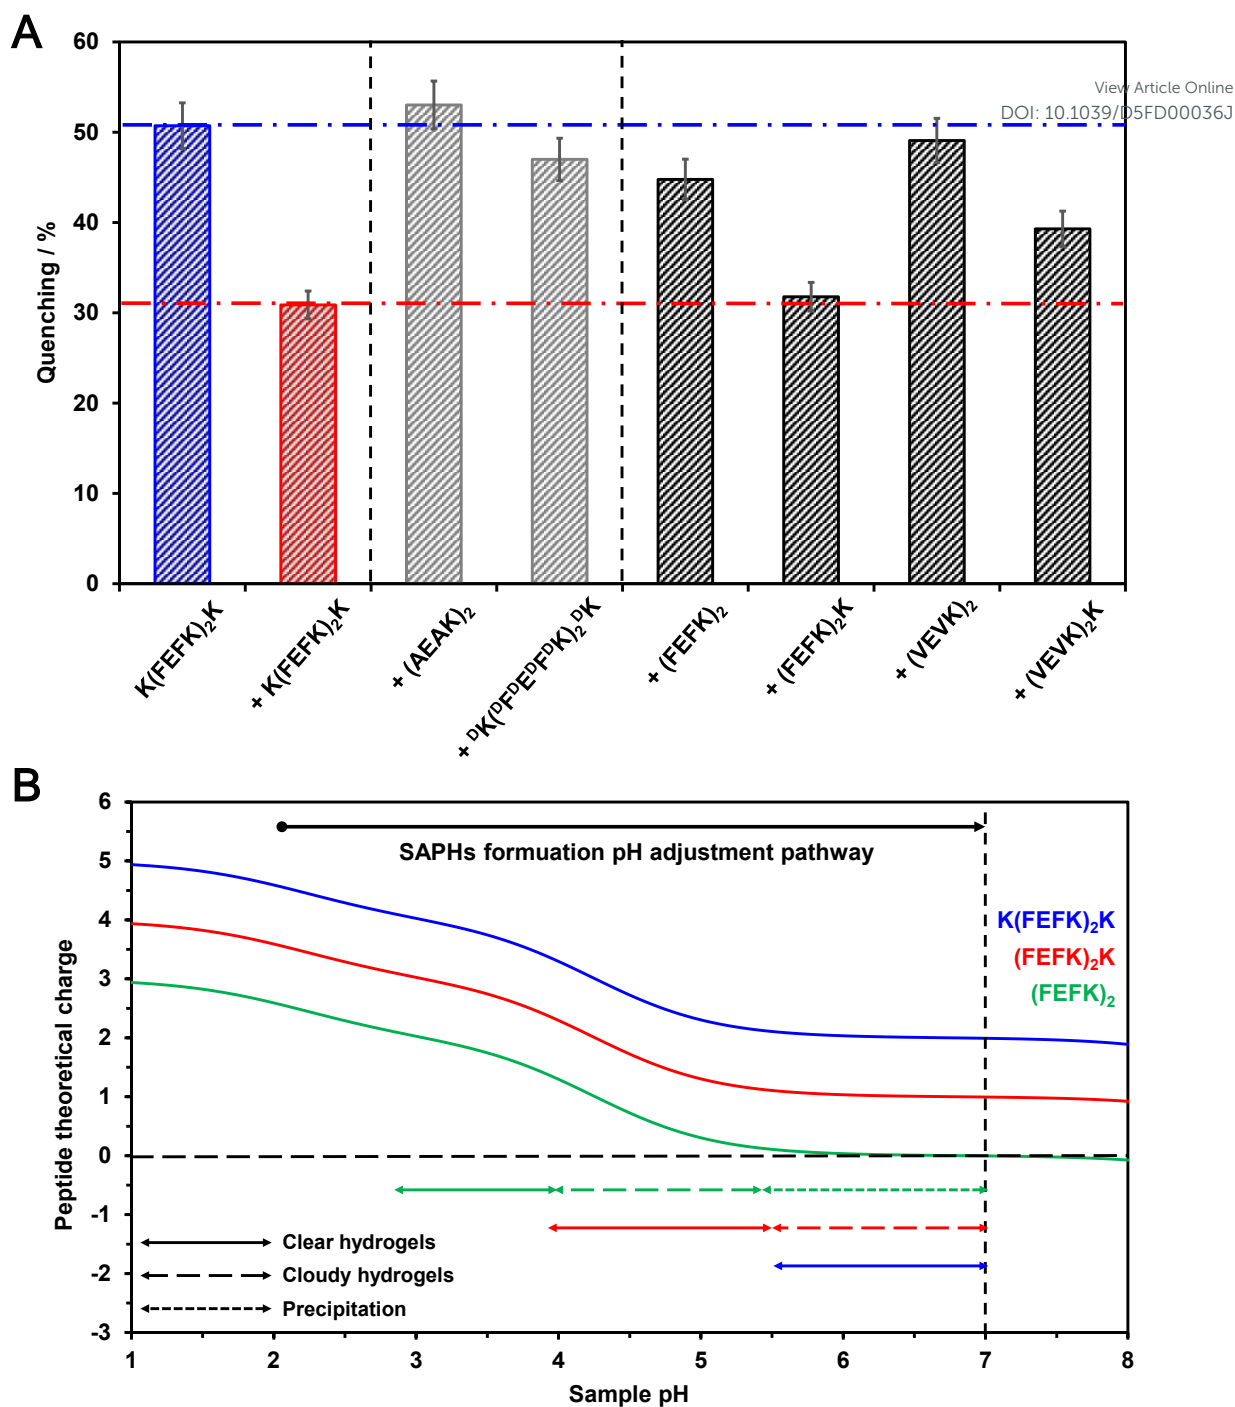


Figure 3: **A)** Fluorescence quenching percentage vs peptide used to prepare mixed SAPHs. **B)** Theoretical overall peptide charge and sample phase behaviour vs formulation pH pathway. The overall charge carried by a peptide was calculated using the following equation:

$$Z = \sum_i N_i \frac{10^{pK_{a_i}}}{10^{pH} + 10^{pK_{a_i}}} - \sum_j N_j \frac{10^{pH}}{10^{pH} + 10^{pK_{a_j}}} \quad (2)$$



where N_{ij} are the numbers and $pK_{a\ ij}$ the pK_a values of the basic ($i - pK_a > 7$) and acidic ($j - pK_a < 7$) groups present respectively. The ionic groups present on the peptides are carboxylic acid ($\text{COOH} / \text{COO}^-$) at the C-terminus (theoretical pK_a 2.18) and on the glutamic acid side chains (theoretical pK_a 4.25), and amine ($\text{NH}_3^+ / \text{NH}_2$) at the N-terminus (theoretical pK_a 8.95 and 9.13 on K and F side, respectively) and on the lysine side chains (theoretical pK_a 10.53).

Article Online
DOI: 10.1039/D5FD00036J

As can be seen from Figure 3A the overall phase behaviour of the peptide affects the occurrence of co-assembly. For $(\text{FEFK})_2\text{K}$ there is no change in sample's fluorescence quenching percentage compared to the base SAPHs at 7.5 mg ml^{-1} . This indicates that co-assembly did occur in this case. It is thought that the decrease in peptide hydrophobicity at pH 7 resulting from the presence of the additional K allows the gelation ranges of this and the base peptide to overlap, enabling co-assembly to occur in the mixed SAPH formulation. For $(\text{FEFK})_2$ the quenching percentage was similar to the value observed for the $^{\text{D}}\text{K}(\text{D}^{\text{F}}\text{D}^{\text{E}}\text{D}^{\text{F}}\text{D}^{\text{K}})_2^{\text{D}}\text{K}$ mixed SAPH, suggesting that in this case no, or very limited, co-assembly occurred. It is thought that for this latter peptide co-assembly is prevented as aggregation and precipitation occurs in the pH range, where the base peptide on its own is known to self-assemble and form a hydrogel.

Finally, we investigated whether co-assembly occurred when $(\text{VEVK})_2$ and $(\text{VEVK})_2\text{K}$ were used to formulate the mixed SAPHs. A similar phase behaviour vs pH was observed for these two systems as for their F-equivalent peptides discussed above. No change in quenching percentage was observed for the $(\text{VEVK})_2$ mixed SAPH compared to $^{\text{D}}\text{K}(\text{D}^{\text{F}}\text{D}^{\text{E}}\text{D}^{\text{F}}\text{D}^{\text{K}})_2^{\text{D}}\text{K}$ mixed SAPH, once again suggesting that no co-assembly occurred. Here too, the poor solubility of this peptide and the fibres formed at pH 7 are thought to prevent any co-assembly with the base peptide. Interestingly though $(\text{VEVK})_2\text{K}$ was found to have an intermediate behaviour, with the quenching percentage of this mixed SAPH ($\sim 40\%$) being in between the quenching percentages expected when co-assembly did ($\sim 30\%$) and did not ($\sim 50\%$) occur. This result suggests that partial co-assembly may occur. As for



(FEFK)₂K, no solubility issues were expected to prevent co-assembly therefore, it is thought that the replacement of F by V is affecting co-assembly. The side groups of F and V have different volumes and sizes and therefore are expected to lead to different packing constraints in the core of the beta-sheet fibres. This is thought to lead to partial co-assembly and formation of 'blocky' assemblies, where blocks of base peptide and (VEVK)₂K alternate along the same fibre. This result is in agreement with our previous work where we showed that changing one F residue side group to 2,3-dibromomaleimide in (FEFK)₂K can lead to a change in fibre morphology. This was thought to be due to a change in packing constraints in the fibre core resulting from introduction of the modification.⁴⁰

View Article Online
DOI: 10.1039/D5FD00036J



Conclusions:

Here, we have investigated the possibility of using the FRET pair FITC/ Dabcyl to investigate the co-assembly of short amphipathic oligopeptides into mixed SAPHs formulations. Our results clearly show that this methodology can be used to explore the co-assembly phenomenon, and that the occurrence of co-assembly is affected by the peptides physicochemical properties, in particular the overall charge carried by the peptide and the resulting phase behaviour. Interestingly, our work also shows that the nature of the hydrophobic residues side group and therefore the packing on the fibre core also affects co-assembly. Indeed, when using (VEVK)₂K peptides to prepare mixed SAPH with our K(FEFK)₂K base peptide, the results suggest formation of 'blocky' assemblies, alternation of different peptide self-assembled blocks along the same fibre.

This work clearly shows how peptide design plays a key role in defining co-assembly occurrence in these systems and how mixed SAPHs can be a promising route to build novel hydrogel systems. Developing our molecular understanding of co-assembly in these systems is key to design hydrogels with novel properties and functionalities.



Acknowledgement

The authors acknowledge the financial support from the MRC Acellular/Smart Materials 3D Architecture: UK RMP Hub (Grant no: MR/R015651/1). The authors also acknowledge the support from the Biological Electron Microscopy Core Facility (RRID: SCR_021147), Faculty of Biology, Medicine and Health, University of Manchester for their assistance with the TEM experiments. All research data supporting this publication are directly available within this publication

bioRxiv preprint doi: <https://doi.org/10.1039/D5FD00036J>; this version posted November 10, 2025. The copyright holder for this preprint (which was not certified by peer review) is the author/funder, who has granted bioRxiv a license to display the preprint in perpetuity. It is made available under aCC-BY 4.0 International license.



References

1. Chen, J.; Zou, X., Self-assemble peptide biomaterials and their biomedical applications. *Bioactive Materials* **2019**, *4*, 120-131. DOI: 10.1039/D5FD00036J
2. Pugliese, R.; Gelain, F., Peptidic Biomaterials: From Self-Assembling to Regenerative Medicine. *Trends in Biotechnology* **2017**, *35* (2), 145-158.
3. Wang, Y.; Rencus-Lazar, S.; Zhou, H.; Yin, Y.; Jiang, X.; Cai, K.; Gazit, E.; Ji, W., Bioinspired Amino Acid Based Materials in Bionanotechnology: From Minimalistic Building Blocks and Assembly Mechanism to Applications. *ACS nano* **2024**, *18* (2), 1257-1288.
4. Soliman, M. A. N.; Khedr, A.; Sahota, T.; Armitage, R.; Allan, R.; Laird, K.; Allcock, N.; Ghuloum, F. I.; Amer, M. H.; Alazragi, R.; Edwards-Gayle, C. J. C.; Wychowanec, J. K.; Vargiu, A. V.; Elsayy, M. A., Unraveling the Atomistic Mechanism of Electrostatic Lateral Association of Peptide β -Sheet Structures and Its Role in Nanofiber Growth and Hydrogelation. *Small* **2025**, *21* (6), 2408213.
5. Sinha, N. J.; Langenstein, M. G.; Pochan, D. J.; Kloxin, C. J.; Saven, J. G., Peptide Design and Self-assembly into Targeted Nanostructure and Functional Materials. *Chemical Reviews* **2021**, *121* (22), 13915-13935.
6. Cui, H.; Webber, M. J.; Stupp, S. I., Self-assembly of peptide amphiphiles: from molecules to nanostructures to biomaterials. *Biopolymers* **2010**, *94* (1), 1-18.
7. Zhang, S., Discovery and design of self-assembling peptides. *Interface Focus* **2017**, *7* (6), 20170028.
8. Zhang, S. G., Emerging biological materials through molecular self-assembly. *Biotechnology Advances* **2002**, *20* (5-6), 321-339.
9. Sun, Y.; Li, W.; Wu, X.; Zhang, N.; Zhang, Y.; Ouyang, S.; Song, X.; Fang, X.; Seeram, R.; Xue, W.; He, L.; Wu, W., Functional Self-Assembling Peptide Nanofiber Hydrogels Designed for Nerve Degeneration. *Acs Applied Materials & Interfaces* **2016**, *8* (3), 2348-2359.
10. Caplan, M. R.; Schwartzfarb, E. M.; Zhang, S. G.; Kamm, R. D.; Lauffenburger, D. A., Control of self-assembling oligopeptide matrix formation through systematic variation of amino acid sequence. *Biomaterials* **2002**, *23* (1), 219-227.
11. Caplan, M. R.; Moore, P. N.; Zhang, S. G.; Kamm, R. D.; Lauffenburger, D. A., Self-assembly of a beta-sheet protein governed by relief of electrostatic repulsion relative to van der Waals attraction. *Biomacromolecules* **2000**, *1* (4), 627-631.



12. Bolan, F.; Dickie, B. R.; Cook, J. R.; Thomas, J. M.; Pinteaux, E.; Allan, S. M.; Saiani, A.; Lawrence, C. B., Intracerebral Administration of a Novel Self-Assembling Peptide Hydrogel Is Safe and Supports Cell Proliferation in Experimental Intracerebral Haemorrhage. *Translational Stroke Research* **2023**. DOI: 10.1039/D5FD00036J
13. Morris, O.; Elsayy, M. A.; Fairclough, M.; Williams, K. J.; McMahon, A.; Grigg, J.; Forster, D.; Miller, A. F.; Saiani, A.; Prenant, C., In vivo characterisation of a therapeutically relevant self-assembling F-18-labelled -sheet forming peptide and its hydrogel using positron emission tomography. *Journal of Labelled Compounds & Radiopharmaceuticals* **2017**, 60 (10), 481-488.
14. Raspa, A.; Marchini, A.; Pugliese, R.; Mauri, M.; Maleki, M.; Vasita, R.; Gelain, F., A biocompatibility study of new nanofibrous scaffolds for nervous system regeneration. *Nanoscale* **2016**, 8 (1), 253-265.
15. Burgess, K. A.; Frati, C.; Meade, K.; Gao, J.; Castillo Diaz, L.; Madeddu, D.; Graiani, G.; Cavalli, S.; Miller, A. F.; Oceandy, D.; Quaini, F.; Saiani, A., Functionalised peptide hydrogel for the delivery of cardiac progenitor cells. *Materials Science and Engineering: C* **2021**, 119, 111539.
16. Markey, A.; Workman, V. L.; Bruce, I. A.; Woolford, T. J.; Derby, B.; Miller, A. F.; Cartmell, S. H.; Saiani, A., Peptide hydrogel in vitro non-inflammatory potential. *Journal of Peptide Science* **2017**, 23 (2), 148-154.
17. Worthington, P.; Pochan, D. J.; Langhans, S. A., Peptide hydrogels - versatile matrices for 3D cell culture in cancer medicine. *Frontiers in Oncology* **2015**, 5.
18. Lingard, E.; Dong, S.; Hoyle, A.; Appleton, E.; Hales, A.; Skaria, E.; Lawless, C.; Taylor-Hearn, I.; Saadati, S.; Chu, Q.; Miller, A. F.; Domingos, M.; Saiani, A.; Swift, J.; Gilmore, A. P., Optimising a self-assembling peptide hydrogel as a Matrigel alternative for 3-dimensional mammary epithelial cell culture. *Biomaterials Advances* **2024**, 160, 213847.
19. Treacy, N. J.; Clerkin, S.; Davis, J. L.; Kennedy, C.; Miller, A. F.; Saiani, A.; Wychowanec, J. K.; Brougham, D. F.; Crean, J., Growth and differentiation of human induced pluripotent stem cell (hiPSC)-derived kidney organoids using fully synthetic peptide hydrogels. *Bioactive Materials* **2023**, 21, 142-156.
20. Lachowski, D.; Matellan, C.; Cortes, E.; Saiani, A.; Miller, A. F.; del Río Hernández, A. E., Self-Assembling Polypeptide Hydrogels as a Platform to Recapitulate the Tumor Microenvironment. *Cancers* **2021**, 13 (13).



21. Faroni, A.; Workman, V. L.; Saiani, A.; Reid, A. J., Self-Assembling Peptide Hydrogel Matrices Improve the Neurotrophic Potential of Human Adipose-Derived Stem Cells. *Advanced Healthcare Materials* **2019**, *8* (17), 1900410. DOI: 10.1039/D5FD00036J
22. Kumar, D.; Workman, V. L.; O'Brien, M.; McLaren, J.; White, L.; Ragunath, K.; Rose, F.; Saiani, A.; Gough, J. E., Peptide Hydrogels-A Tissue Engineering Strategy for the Prevention of Oesophageal Strictures. *Advanced Functional Materials* **2017**, *27* (38).
23. Pugliese, R.; Gelain, F., Peptidic Biomaterials: From Self-Assembling to Regenerative Medicine. *Trends in Biotechnology* **2016**.
24. Xin, Y.; Ligorio, C.; O'Brien, M.; Collins, R.; Dong, S.; Miller, A. F.; Saiani, A.; Gough, J. E., Effect of supramolecular peptide hydrogel scaffold charge on HepG2 viability and spheroid formation. *Journal of Materials Chemistry B* **2024**, *12* (48), 12553-12566.
25. Dong, S.; Chapman, S. L.; Pluen, A.; Richardson, S. M.; Miller, A. F.; Saiani, A., Effect of Peptide-Polymer Host-Guest Electrostatic Interactions on Self-Assembling Peptide Hydrogels Structural and Mechanical Properties and Polymer Diffusivity. *Biomacromolecules* **2024**, *25* (6), 3628-3641.
26. Castillo-Díaz, L. A.; Gough, J. E.; Miller, A. F.; Saiani, A., RGD-functionalised self-assembling peptide hydrogel induces a proliferative profile in human osteoblasts in vitro. *Journal of Peptide Science* **2025**, *31* (2), e3653.
27. Wen, Y.; Roudebush, S. L.; Buckholtz, G. A.; Goehring, T. R.; Giannoukakis, N.; Gawalt, E. S.; Meng, W. S., Coassembly of amphiphilic peptide EAK16-II with histidinylated analogues and implications for functionalization of β -sheet fibrils in vivo. *Biomaterials* **2014**, *35* (19), 5196-5205.
28. Wong, K. M.; Robang, A. S.; Lint, A. H.; Wang, Y.; Dong, X.; Xiao, X.; Seroski, D. T.; Liu, R.; Shao, Q.; Hudalla, G. A.; Hall, C. K.; Paravastu, A. K., Engineering β -Sheet Peptide Coassemblies for Biomaterial Applications. *The journal of physical chemistry. B* **2021**, *125* (50), 13599-13609.
29. Chan, K. H.; Lim, J.; Jee, J. E.; Aw, J. H.; Lee, S. S. Peptide-Peptide Co-Assembly: A Design Strategy for Functional Detection of C-peptide, A Biomarker of Diabetic Neuropathy *International Journal of Molecular Sciences* [Online], 2020.
30. Morris, K. L.; Chen, L.; Raeburn, J.; Sellick, O. R.; Cotanda, P.; Paul, A.; Griffiths, P. C.; King, S. M.; O'Reilly, R. K.; Serpell, L. C.; Adams, D. J., Chemically programmed self-sorting of gelator networks. *Nature Communications* **2013**, *4* (1), 1480.



31. Seroski, D. T.; Dong, X.; Wong, K. M.; Liu, R.; Shao, Q.; Paravastu, A. K.; Hall, C. K.; Hudalla, G. A., Charge guides pathway selection in β -sheet fibrillizing peptide co-assembly. *Communications Chemistry* **2020**, *3* (1), 172. DOI: 10.1039/D5FD00036J
32. Panja, S.; Dietrich, B.; Smith, A. J.; Seddon, A.; Adams, D. J., Controlling Self-Sorting versus Co-assembly in Supramolecular Gels. *ChemSystemsChem* **2022**, *4* (4), e202200008.
33. Sangji, M. H.; Lee, S. R.; Sai, H.; Weigand, S.; Palmer, L. C.; Stupp, S. I., Self-Sorting vs Coassembly in Peptide Amphiphile Supramolecular Nanostructures. *ACS nano* **2024**, *18* (24), 15878-15887.
34. Shao, Q.; Wong, K. M.; Seroski, D. T.; Wang, Y.; Liu, R.; Paravastu, A. K.; Hudalla, G. A.; Hall, C. K., Anatomy of a selectively coassembled β -sheet peptide nanofiber. *Proceedings of the National Academy of Sciences* **2020**, *117* (9), 4710-4717.
35. Rowland, C. E.; Brown, C. W.; Medintz, I. L.; Delehanty, J. B., Intracellular FRET-based probes: a review. *Methods and Applications in Fluorescence* **2015**, *3* (4), 042006.
36. Wychowanec, J. K.; Smith, A. M.; Ligorio, C.; Mykhaylyk, O. O.; Miller, A. F.; Saiani, A., Role of Sheet-Edge Interactions in β -sheet Self-Assembling Peptide Hydrogels. *Biomacromolecules* **2020**, *21* (6), 2285-2297.
37. Elsayy, M. A.; Wychowanec, J. K.; Castillo Díaz, L. A.; Smith, A. M.; Miller, A. F.; Saiani, A., Controlling Doxorubicin Release from a Peptide Hydrogel through Fine-Tuning of Drug–Peptide Fiber Interactions. *Biomacromolecules* **2022**, *23* (6), 2624-2634.
38. Raphael, B.; Khalil, T.; Workman, V. L.; Smith, A.; Brown, C. P.; Streuli, C.; Saiani, A.; Domingos, M., 3D cell bioprinting of self-assembling peptide-based hydrogels. *Materials Letters* **2017**, *190*, 103-106.
39. Saiani, A.; Mohammed, A.; Frielinghaus, H.; Collins, R.; Hodson, N.; Kielty, C. M.; Sherratt, M. J.; Miller, A. F., Self-assembly and gelation properties of alpha-helix versus beta-sheet forming peptides. *Soft Matter* **2009**, *5* (1), 193-202.
40. Elsayy, M. A.; Smith, A. M.; Hodson, N.; Squires, A.; Miller, A. F.; Saiani, A., Modification of beta-Sheet Forming Peptide Hydrophobic Face: Effect on Self-Assembly and Gelation. *Langmuir* **2016**, *32* (19), 4917-4923.
41. Mujeeb, A.; Miller, A. F.; Saiani, A.; Gough, J. E., Self-assembled octapeptide scaffolds for in vitro chondrocyte culture. *Acta Biomaterialia* **2013**, *9* (1), 4609-4617.



42. Roberts, D.; Rochas, C.; Saiani, A.; Miller, A. F., Effect of Peptide and Guest Charge on the Structural, Mechanical and Release Properties of beta-Sheet Forming Peptides. *Langmuir* **2012**, *28* (46), 16196-16206. View Article Online
DOI: 10.1039/D5FD00036J
43. Gao, J.; Tang, C.; Elsayy, M. A.; Smith, A. M.; Miller, A. F.; Saiani, A., Controlling Self-Assembling Peptide Hydrogel Properties through Network Topology. *Biomacromolecules* **2017**, *18* (3), 826-834.
44. Barth, A., Infrared spectroscopy of proteins. *Biochimica Et Biophysica Acta-Bioenergetics* **2007**, *1767* (9), 1073-1101.
45. Barth, A.; Zscherp, C., What vibrations tell us about proteins. *Quarterly Reviews of Biophysics* **2002**, *35* (4), 369-430.
46. Boothroyd, S.; Miller, A. F.; Saiani, A., From fibres to networks using self-assembling peptides. *Faraday Discussions* **2013**, *166*, 195-207.



Investigating the co-assembly of amphipathic peptides

[View Article Online](#)

DOI: 10.1039/D5FD00036J

Zixuan Liu^a; Alberto Saiani^b and Aline F. Miller^{a,}*

All research data supporting this publication are directly available within this publication.

