

Industrial Chemistry & Materials

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: X. Gao, P. Lu, I. Kuzmenko, J. Ilavsky and G. Gadikota, *Ind. Chem. Mater.*, 2025, DOI: 10.1039/D4IM00157E.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

ARTICLE

Reactive CO₂ Capture and Mineralization of Magnesium Hydroxide to Produce Hydromagnesite with Inherent Solvent Regeneration

Xun Gao,^a Peilong Lu,^a Ivan Kuzmenko,^b Jan Ilavsky^b and Greeshma Gadikota^{*ac}Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Valorization of multiple low value streams including CO₂ emissions and magnesium-hydroxide bearing mine tailings to produce magnesium carbonate through reactive CO₂ capture and mineralization provides a less explored opportunity to manage several gigatons of CO₂ emissions. To resolve the feasibility of converting magnesium hydroxide to magnesium carbonate through reactive CO₂ capture and mineralization, CO₂ capture solvents such as sodium glycinate are harnessed to capture CO₂ and react directly with Mg(OH)₂ to produce hydromagnesite (Mg₅[(CO₃)₄(OH)₂]-4H₂O). This approach eliminates the energy-intensive step of producing high purity CO₂ associated with regenerating the solvent, and redissolving CO₂ to produce magnesium carbonate. Interestingly, while temperatures below 50 °C facilitate CO₂ capture, the mineralization kinetics are slow. However, at higher temperatures, accelerated carbon mineralization is favored by the faster kinetics of Mg(OH)₂ dissolution and precipitation of magnesium carbonate. Reacting Mg(OH)₂ at 90 °C with 15 wt% solids in the presence of 2.5 M sodium glycinate after 3 hours under well-stirred conditions results in an extent of carbon mineralization of 75.5%. The theoretical maximum extent of carbon mineralization when hydromagnesite is formed is 80%. Pre-loading CO₂ on the solvent is also an effective approach to ensure that sufficient CO₂ is available for reactive CO₂ capture and mineralization, particularly when dilute CO₂ and N₂ mixtures are used. Higher extents of carbon mineralization are associated with an increase in the particle size and a reduction in the cumulative pore volume. These insights unlock the feasibility of harnessing reactive CO₂ capture and mineralization as a pathway to convert magnesium-hydroxide bearing resources into industrially relevant magnesium carbonate products.

Keywords: Reactive CO₂ capture and mineralization, Magnesium hydroxide, Magnesium carbonate, Regenerable CO₂ capture solvents, Hydromagnesite

1. Introduction

Harnessing multiple emissions such as CO₂-bearing flue gas streams and magnesium hydroxide (or brucite) bearing tailings is emerging as a viable approach to capture and store CO₂ emissions as stable magnesium carbonates, given the thermodynamically downhill nature of carbon mineralization pathways.^{1,2} The direct carbon mineralization of Mg(OH)₂-bearing mine tailings with CO₂ in ultra-dilute streams including air and flue gas is feasible but kinetically slow.^{1,3} Alternatively, bubbling highly concentrated or nearly pure CO₂ through Mg(OH)₂ is known to facilitate rapid carbon mineralization within two hours or less.⁴ However, CO₂ capture technologies are needed to concentrate CO₂ that can be used for subsequent carbon mineralization using this approach.^{5,6} To achieve fast kinetics of carbon mineralization while directly harnessing ultra-dilute sources of CO₂ including flue gas streams or even air without

additional steps to regenerate the solvents and solubilize CO₂, reactive CO₂ capture and mineralization pathways are being developed.⁷

Reactive CO₂ capture and mineralization pathways involve concentrating CO₂ emissions to produce CO₂-loaded solvents. These CO₂-loaded solvents react directly with the alkaline source to produce the respective carbonates with concurrent regeneration.⁸ This approach is designed to overcome: (i) the low solubility of CO₂ by harnessing CO₂ capture solvents with basic functionalities that enhance CO₂ solubility at very low gas phase concentrations, (ii) energy needs associated with producing high purity CO₂ for subsequent mineralization, and (iii) the additional unit operations associated with producing high purity CO₂ which occurs conventionally via pressure-swing or thermal-swing sorption processes.

The efficacy of these pathways for mineralizing calcium-bearing resources, such as oxides and silicates, and heterogeneous resources, such as fly ash, has been verified by harnessing polyamines and water-lean solvents such as 1,8-diazabicyclo[5.4.0]undec-7-ene (DBU), branched amines such as 2-Amino-2-Methyl-1-Propanol (AMP), monoamines such as monoethanolamine (MEA), and amino acid salts with varying alkyl functional groups such as sodium

^a School of Civil and Environmental Engineering, Cornell University, Ithaca, NY 14853.

^b Advanced Photon Source, Argonne National Laboratory, Lemont, IL 60439.

^c Smith School of Chemical and Biological Engineering, Cornell University, Ithaca, NY 14853. Phone: +1 607-255-4796; E-mail: gg464@cornell.edu

† Footnotes relating to the title and/or authors should appear here.

Supplementary Information available: [details of any supplementary information available should be included here]. See DOI: 10.1039/x0xx00000x



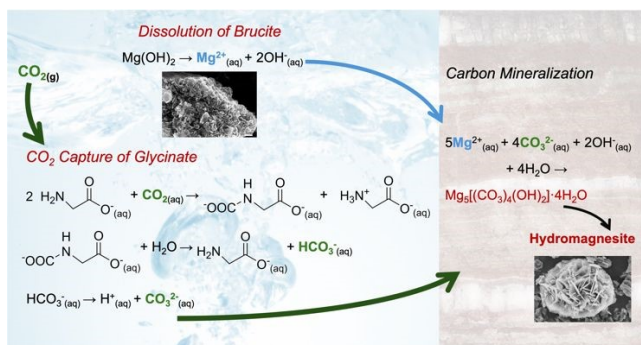


Fig. 1 Schematic representation of reactive CO₂ capture and carbon mineralization by harnessing Mg(OH)₂ as the alkaline source and N-glycinate as the CO₂ capture solvent.

glycinate and sodium sarcosinate.^{9–14} These studies established that temperatures in range of 50–75 °C facilitate reactive CO₂ capture and mineralization, with lower temperatures favouring CO₂ capture but challenged by slow mineralization kinetics, whereas higher temperatures enable faster carbon mineralization but limit CO₂ capture.

While the efficacy of reactive CO₂ capture and mineralization of magnesium oxide was established using amine bearing solvents, the use of more environmentally benign solvents such as sodium glycinate has not been explored.¹⁵ Sodium glycinate is the simplest unit of amino acid salts. Establishing the efficacy of reactive CO₂ capture and mineralization using this amino acid salt translates into the use of other amino acids with multiple amine groups, straight and branched alkyl groups, and varying positions of amine groups (e.g., alpha and beta positions) for this approach. Regardless of the placement of the amine functional groups, the key reactions associated with reactive CO₂ capture and mineralization include: (i) CO₂ hydration, (ii) dissolution of Mg(OH)₂, and (iii) the formation of Mg-carbonate, which is shown in **Fig. 1**.¹⁶

Despite considerable advances made in reactive CO₂ capture and mineralization,¹⁵ several outstanding research questions remain including: (i) Is reactive CO₂ capture and mineralization of Mg(OH)₂ favoured at temperatures above or below 50 °C and why? (ii) How does the reactivity of Mg(OH)₂ compare with that of Ca-bearing oxides and silicates for reactive CO₂ capture and mineralization at comparable experimental conditions? (iii) Given that Mg²⁺ ions have a stronger hydration shell compared to Ca²⁺ ions,¹⁷ what is the influence of reactive CO₂ capture and mineralization on the structural evolution of magnesium carbonate phases? For example, are metastable hydrated magnesium carbonate phases formed as opposed to stable magnesite forms? (iv) What is the influence of CO₂ compositions in the range of 4–20 vol.% on reactive CO₂ capture and mineralization of Mg(OH)₂? (v) What is the influence of the extent of carbon mineralization on the pore and particle morphological evolution of the Mg-bearing materials?

To address these questions, reactive CO₂ capture and mineralization studies are conducted with 1 M and 2.5 M Na-glycinate contrasted with water at temperatures in the range of 25–90 °C with CO₂ concentrations ranging from 4–100 vol.%. The morphological features of the materials are characterized before and after carbon mineralization to determine the influence of

carbon mineralization on the particle and pore morphologies of the products.
 DOI: 10.1039/D4IM00157E

2. Results and Discussion

2.1. Reactive CO₂ capture and mineralization of magnesium hydroxide

Reactive CO₂ capture and mineralization involves harnessing CO₂ capture solvents to capture and concentrate CO₂ in the aqueous phase and reacting these CO₂-loaded solvents with an alkaline source to produce Mg-carbonate and regenerate the solvent. In this multiphase chemical reaction pathway, the solubility of CO₂, reactivity of the alkaline source, and subsequent carbon mineralization behaviour are influenced by temperature, solvent concentration, and pH of the system. CO₂ capture is aided at temperatures below 40 °C while mineralization kinetics are aided at higher temperatures. Furthermore, the solubility of magnesium carbonates decreases with temperature, thus favouring precipitation. To resolve the influence of temperature, reactive CO₂ capture and mineralization behaviour with Mg(OH)₂ is investigated at 25, 50, 75, and 90 °C. The reactivity of Mg(OH)₂ is established with water, 1.0 M and 2.5 M sodium glycinate. Furthermore, the reactivity of Mg(OH)₂ is compared with that of calcium oxide and calcium silicate at comparable experimental conditions to contrast their reactivity. These results are discussed in this section.

To investigate the influence of temperature, experiments are conducted in a pure CO₂ environment with 1.0 M and 2.5 M Na-glycinate and deionized water for comparison at 25, 50, 75, and 90 °C, respectively. As shown in **Fig. 2**, the extent of carbon mineralization increases from 17.1% at 25 °C to 75.5% at 90 °C when Mg(OH)₂ is reacted in the presence of 2.5 M Na-glycinate. This enhancement in carbon mineralization which is more than three-fold indicates that the fast kinetics of carbon mineralization and lower

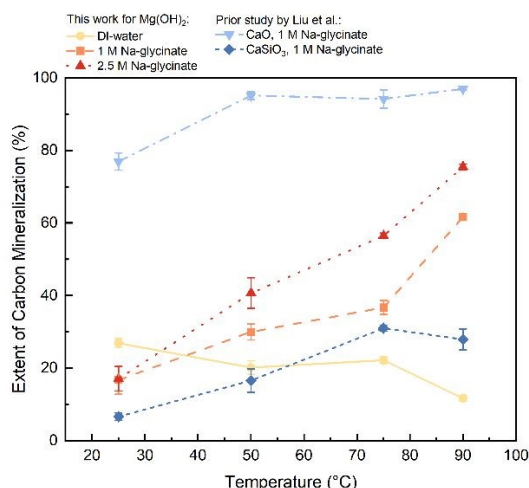


Fig. 2 The extents of carbon mineralization of Mg(OH)₂ with various Na-glycinate concentrations at different temperatures. All experiments are conducted at 1 atm of CO₂. The solid products were analyzed by Thermogravimetric Analysis (TGA). Extents of carbon mineralization reported for CaO and CaSiO₃ from Liu and coworkers are included for comparison.¹⁸



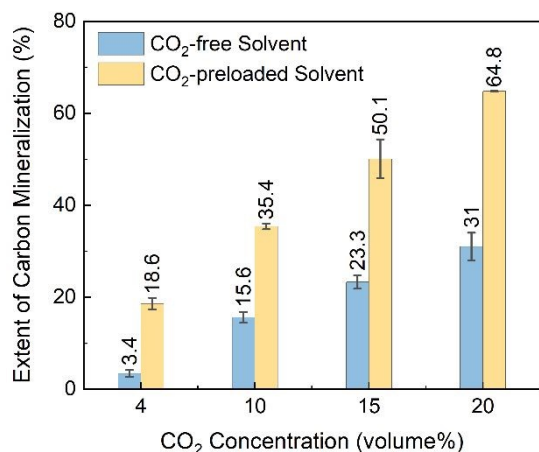


Fig. 3 The extents of carbon mineralization of Mg(OH)₂ using binary flue gas with various CO₂/N₂ ratios. The carbonate content in the solid products is analyzed by Thermogravimetric Analysis (TGA).

solubility of Mg-carbonate at higher temperature of 90 °C dominate higher solubility of CO₂ at lower temperatures.^{19–21} In the absence of the solvent, extents of carbon mineralization decreased from 26.9% at 25 °C to 22.2% at 75 °C and to 11.7% at 90 °C, respectively, due to the reduced solubility of CO₂ with rising temperature which limits the availability of carbonate species needed for carbon mineralization.²² In contrast, calcium oxide is highly reactive, and carbon mineralization extents of 80% or higher are achieved at 25 °C or above. Interestingly, the reactivity of CaSiO₃ increases to 31% at 75 °C and decreases at 90 °C. These results show that Ca-bearing solids are more reactive at temperatures below 90 °C. The significantly lower extents of carbon mineralization noted using Ca-silicate are attributed to the slow dissolution rate of silicate materials and the formation of silica passivation layer that may limit the diffusivity of the ions for carbon mineralization.^{23–25}

Investigations of the influence of 1 M and 2.5 M Na-glycinate on reactive CO₂ capture and mineralization showed that higher extents of carbon mineralization are achieved with 2.5 M Na-glycinate compared to 1 M counterparts due to the greater availability of amine functional groups for reactive CO₂ capture and mineralization. Specifically, extents of carbon mineralization achieved with Mg(OH)₂ are 61.7% and 75.5% with 1 M and 2.5 M Na-glycinate, respectively, at 90 °C. It is important to note that the theoretical maximum extent of carbon mineralization for hydromagnesite is 80%, because the stoichiometric ratio of Mg(OH)₂ to CO₂ is determined to be 5:4 based on **Reaction 2**. Assuming all Mg(OH)₂ reacts with CO₂, the EoC is calculated to be 80% based on **Equation 2**. As a result, the normalized extent of carbon mineralization is up to 94.3% for the 2.5 M Na-glycinate case at 90 °C (**Fig. S1**). It is also worth noting that the extents of carbon mineralization of Mg(OH)₂ at 25 °C in the presence of water, 1 M and 2.5 M Na-glycinate are 26.9%, 16.7%, and 17.1%, respectively. At 25 °C, the glycinate ligands can bind with the Mg²⁺ ions in the slurry to form Mg-glycinate complexes, which may be too stable to react with (bi)carbonate species to produce Mg-carbonates.²⁶

While the efficacy of harnessing highly concentrated CO₂ streams for the reactive CO₂ capture and mineralization of Mg(OH)₂ to

produce the respective Mg-carbonate has been established, the influence of the dilute CO₂ streams or flue gas which are representative of industrial operations remains less studied. Flue gas is the tail gas bearing nitrogen, carbon dioxide, and steam with trace amount of sulfur oxide or nitrogen oxide emerging from fuel combustion, industrial calcination or reduction processes.^{27,28} To simulate the conditions of industrial flue gases, a binary gas mixture of nitrogen and carbon dioxide is prepared and used to investigate reactive CO₂ capture and mineralization with magnesium hydroxide.

As shown in the experimental section reactive CO₂ capture and mineralization studies are conducted with binary mixture of N₂ and CO₂ inside a gas circulation system with CO₂-preloaded solutions at 25 °C. A constant binary gas flow is injected into the Mg(OH)₂ slurry as the CO₂ source. Following the same calculation approach, the carbon mineralization extents from flue gas having varying CO₂ levels with different pre-loading protocols are shown in **Fig. 3**. Generally, as the CO₂ concentration in the binary gas flow increases from 4% to 20%, the extent of carbon mineralization increases from 3.4% to 31% in cases without CO₂ pre-loading. The monotonically increasing correlation is aligned with Henry's law, by which CO₂ solubility and dissolution rate are determined by the CO₂ partial pressure, equivalent to the CO₂ concentration in the flue gas.²⁹ This observation indicates that increasing CO₂ concentrations can linearly improve the extent of carbon mineralization by enhancing the amount of dissolved CO₂. In contrast, CO₂ pre-loading remarkably increases the extent of carbon mineralization compared to the cases without CO₂ pre-loading, with increases of 15.2%, 19.9%, 26.8%, and 33.8% for 4, 10, 15, and 20 vol.% CO₂ at 25 °C, with associated extents of 18.6%, 35.4%, 50.1%, and 64.8%, respectively.

The significant increase in the extents of carbon mineralization with pre-loaded solvents are attributed to the ready availability of dissolved carbon for reacting with Mg(OH)₂ to produce Mg-carbonate bearing species. This approach overcomes the challenge of the mass transfer of CO₂ from the gas to the liquid phase. Pre-loading the solvent with CO₂ also ensures that glycinate is effectively bound to CO₂ as opposed to Mg²⁺ ions to produce Mg-glycinate complexes. When Na-glycinate is mixed with Mg(OH)₂ before CO₂ is introduced, the formation of Mg-glycinate complex over CO₂-loaded Na-glycinate may limit CO₂ loading and subsequent reactivity with Mg²⁺ ions to produce hydromagnesite.

It is interesting to note that the extents of carbon mineralization are 61.7% and 75.5% with 100 vol% CO₂ without pre-loading 1.0 M and 2.5 M Na-glycinate solvent at 90 °C for a reaction time of 3 hours, respectively. In contrast, the extent of carbon mineralization is 64.4% with the pre-loaded 2.5 M Na-glycinate CO₂ capture solvent when reacted at 25 °C for 3 hours. These results demonstrate that pre-loading the CO₂ capture solvent is effective in enabling carbon mineralization at room temperature. Thus, these results show the feasibility of reactive CO₂ capture and mineralization with Mg(OH)₂ at 25 °C by harnessing pre-loaded CO₂ capture solvents.

2.2. Chemical and structural evolution during reactive CO₂ capture and mineralization

Evidence of carbonate formation in Mg-carbonate bearing products is established using Attenuated Total Reflection Fourier Transform-Infrared (ATR FT-IR) spectroscopy and Wide-Angle X-Ray



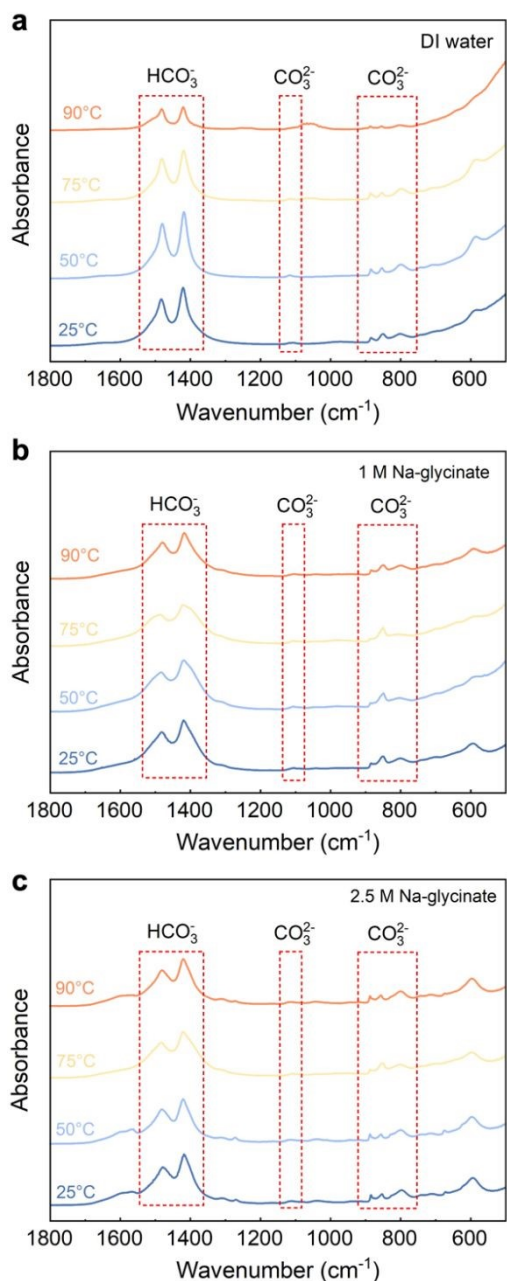


Fig. 4 Evidence of (bi) carbonate species as determined using Attenuated Total Reflection-Fourier Transform Infrared (ATR-FTIR) spectra for carbonate-bearing solid products obtained on reacting in (a) DI water, (b) 1 M Na-glycinate, and (c) 2.5 M Na-glycinate solutions. The characteristic peaks in the dotted square areas indicate the formation of HCO_3^- and CO_3^{2-} species.

Scattering (WAXS). First, the formation of CO_3^{2-} symmetric stretching vibration at 1119 cm^{-1} in the products as determined using ATR FT-IR measurements confirms solid carbonate formation (Fig. 4).³⁰ The corresponding bending vibration of CO_3^{2-} is also detected at 885 cm^{-1} , 854 cm^{-1} , and 798 cm^{-1} , respectively.³¹ Besides, the CO_3^{2-} asymmetric stretching vibration splits into two peaks at 1485 cm^{-1} and 1421 cm^{-1} , respectively, which emerges in all the carbonate-bearing products, indicating the existence of bicarbonate in the

CO_3^{2-}	1119	Symmetric stretching
	885	
	CO_3^{2-}	854
	798	
HCO_3^-	1485	Asymmetric stretching
	1421	

Table 1. The infrared bands of various carbonate-bearing species and the corresponding assignments.

carbonate-bearing solids.³² The identified infrared bands of different carbonate-bearing species and the corresponding assignments are listed in Table 1. The formation of hydromagnesite in the products is further confirmed through the Wide-Angle X-Ray Scattering (WAXS) measurements.

As shown in Fig. 5 (a), the emerging peaks noted with black circles are observed after $\text{Mg}(\text{OH})_2$ mineralization in DI water. These well-defined characteristic peaks correspond to hydromagnesite (PDF 98-001-1519, noted with open circle). Products obtained after reacting in water do not have prominent hydromagnesite peaks compared to brucite (PDF 98-000-0130, noted with closed circle), indicating low extents of carbon mineralization. Additionally, the peak intensity of hydromagnesite showed negligible changes with temperature, demonstrating that carbon mineralization in DI water is not significantly influenced by temperature, which is consistent with the extents of carbon mineralization in Table 2.^{33,34}


In sharp contrast, the presence of Na-glycinate solution, particularly at elevated temperature, resulted in products with more prominent characteristic peaks of hydromagnesite with higher intensity. As shown in Fig. 5 (b) & 5 (c), magnesium hydroxide is the dominant phase at $25\text{ }^\circ\text{C}$, while hydromagnesite formation increases with temperature. At $90\text{ }^\circ\text{C}$, the dominance of hydromagnesite phase over $\text{Mg}(\text{OH})_2$ is noted.³⁴ Prominent peaks corresponding to hydromagnesite emerge at $75\text{ }^\circ\text{C}$ with 2.5 M Na-glycinate and at $90\text{ }^\circ\text{C}$ with 1.0 M Na-glycinate. Furthermore, WAXS results in Fig. 5 confirm the formation of hydromagnesite, as the only Mg-carbonate bearing phase formed. Hydromagnesite formation is known to be dominant at $25\text{ - }90\text{ }^\circ\text{C}$ and in alkaline environments.^{35,36}

Table 2. Summary of experimental conditions, corresponding extents of carbon mineralization (EoC), mean particle sizes, and pore volumes of the unreacted and reacted $\text{Mg}(\text{OH})_2$ materials.

	Temperature ($^\circ\text{C}$)	EoC (%)	Mean Particle Size (μm)	Pore Volume (cc g^{-1})
$\text{Mg}(\text{OH})_2$	/	/	7.85	0.047
H_2O	25	26.90 ± 1.28	15.41	0.133
	50	20.14 ± 1.88	16.97	0.218
	75	22.18 ± 0.93	19.85	0.118
	90	11.68 ± 0.85	15.63	0.101
1 M Na-glycinate	25	16.71 ± 3.88	7.77	0.066
	50	29.97 ± 2.17	9.64	0.071
	75	36.71 ± 1.93	16.75	0.036
	90	61.69 ± 0.35	18.43	0.026
2.5 M Na-glycinate	25	17.08 ± 3.38	8.17	0.016
	50	40.67 ± 4.25	9.63	0.02
	75	56.45 ± 0.72	20.56	0.011
	90	75.46 ± 0.77	19.30	0.008

Species	Band Position (cm^{-1})	Assignment
---------	------------------------------------	------------



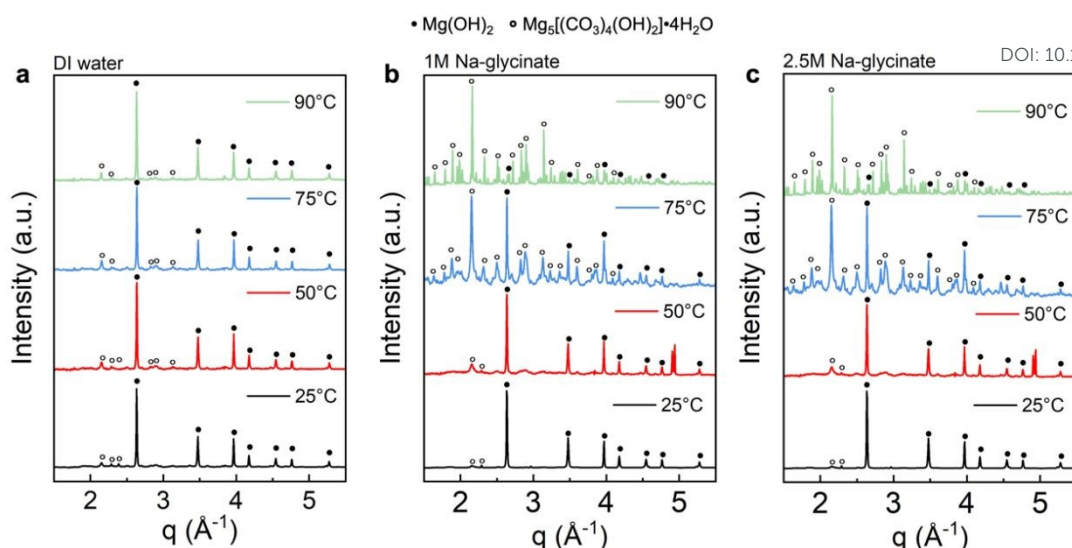

View Article Online
DOI: 10.1039/D4IM00157E

Fig. 5 Evidence of hydromagnesite formation as determined using Wide Angle X-ray Scattering (WAXS) patterns for the carbonate-bearing solid products obtained using (a) DI water, (b) 1 M Na-glycinate, and (c) 2.5 M Na-glycinate at different temperatures. Two types of crystal structures are observed: $\text{Mg}(\text{OH})_2$, originating from unreacted brucite, and $\text{Mg}_5[(\text{CO}_3)_4(\text{OH})_2]\cdot 4\text{H}_2\text{O}$, originating from the carbonate products.

2.3. Morphological changes during reactive CO_2 capture and mineralization

Insights into the influence of carbon mineralization on the morphological evolution of Mg-carbonate are unlocked through particle and pore size analyses and microscopy, as discussed in the following sections.

2.3.1. Evolution in particle morphology on reactive CO_2 capture and mineralization

The morphological changes in the product during the mineralization are revealed by scanning electron microscopy (SEM) images. The unreacted particles are present as hexagonal flakes with diameters of several microns, which is typical for brucite given its hexagonal crystal structure (**Fig. 6 (a)**).³⁷ On carbon mineralization, the hexagonal flakes transformed into nest-like hydromagnesite particles (**Fig. 6(b)**), which is a typical particle shape of hydromagnesite at pH range of 8 - 9 with an average particle size in the range of 10 - 15 μm .^{36,38} As the temperature is increased to 90 $^\circ\text{C}$, the hydromagnesite particles became larger and more compact (**Fig. 6(c)**). Additionally, some of the nest-like particles transformed into flat lamellar particles due to a pH variation from 9.04 at 75 $^\circ\text{C}$ to 9.19 at 90 $^\circ\text{C}$, which is consistent with previous studies.^{36,39} As shown in **Fig. 6(d) & 6(e)**, carbon mineralization with 2.5 M Na-glycinate solution generated more lamellar-shaped particles and possessed a more compact structure compared to counterparts with 1 M Na-glycinate solution, which can be attributed to higher pH values resulting from higher Na-glycinate concentrations (9.57 at 75 $^\circ\text{C}$ and 9.60 at 90 $^\circ\text{C}$).³⁶

2.3.2. Evolution of particle size distributions on reactive CO_2 capture and mineralization

The mechanisms of brucite dissolution and hydromagnesite precipitation are evident from the particle size distributions of the unreacted and reacted particles, as shown in **Fig. 7**. Unreacted brucite particles with sizes smaller than 10 μm dissolve preferentially particularly at 75 $^\circ\text{C}$ and 90 $^\circ\text{C}$ in the presence of water, 1 M and 2.5

M Na-glycinate and precipitate hydromagnesite. Increasing temperatures from 25 $^\circ\text{C}$ to 90 $^\circ\text{C}$ corresponds to higher extents of carbon mineralization (**Fig. 2**) and larger particle sizes (**Fig. 7**). Carbon mineralization in the presence of Na-glycinate versus water results in the growth of larger particles, particularly at elevated temperatures of 75 $^\circ\text{C}$ and 90 $^\circ\text{C}$ (**Fig. 7**). The mean particle diameters increased nearly 2.4 times from 7.85 μm to 19.3 μm on carbon mineralization. The dissolution of unreacted $\text{Mg}(\text{OH})_2$ particles smaller than 10 μm and the subsequent growth of carbonate-bearing particles ($\sim 20 \mu\text{m}$) with more distinct particle size distributions is evident in the presence of 1 M and 2.5 M Na-glycinate solutions at 90 $^\circ\text{C}$, indicating the emergence of more distinct morphologies on carbon mineralization.

2.3.3. Evolution of pore size distributions on reactive CO_2 capture and mineralization

During carbon mineralization, dissolution is known to increase the pore volume while extensive carbonate growth reduces the pore volume. To delineate the competing effects of dissolution and carbonate growth, the pore volume distributions are determined using BET N_2 adsorption-desorption isotherms conducted at 77 K. The cumulative pore volume distributions demonstrate that the cumulative pore volume of the products increase when $\text{Mg}(\text{OH})_2$ is reacted in water (**Fig. 8 (a)**). Compared to the unreacted magnesium hydroxide, the significantly higher cumulative pore volume in the products obtained on reaction in water (as seen in **Table 2**) corresponds to low extents of carbon mineralization ranging from 11.7 % to 26.9 % within the temperature range of 25 - 90 $^\circ\text{C}$ and the dominance of dissolution over carbon mineralization. Interestingly, products obtained on reacting $\text{Mg}(\text{OH})_2$ in 1.0 M Na-glycinate showed a higher cumulative pore volume at 25 $^\circ\text{C}$ and 50 $^\circ\text{C}$ with corresponding extents of reaction of 16.7% and 30%, respectively. In contrast, the cumulative pore volume decreased compared to the base case at 75 $^\circ\text{C}$ and 90 $^\circ\text{C}$ with the corresponding respective extents of carbon mineralization of 36.7% and 61.7%. The crossover in the cumulative pore volumes occurs between 50 $^\circ\text{C}$ and



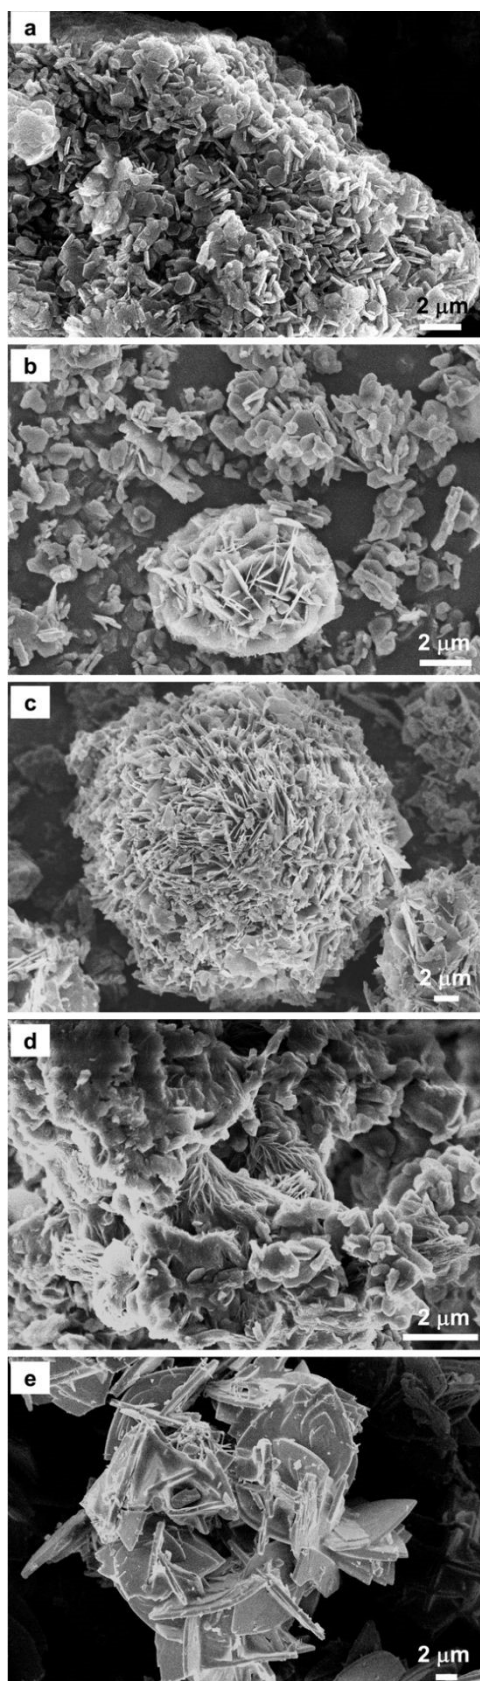


Fig. 6 Morphologies of (a) unreacted brucite, and carbonated solid with 1M Na-glycinate solution at (b) 50°C and (c) at 90°C, and carbonated solid with 2.5M Na-glycinate solution at (d) 50°C and (e) 90°C, determined by scanning electron micrographs (SEM).

75 °C with increasing extents of carbon mineralization. In addition to extensive carbonate growth decreasing the cumulative pore volume, nest-like hydromagnesite particles transform into denser lamellar morphologies with increasing alkalinity and at higher temperatures also decreases the cumulative pore volume compared to the unreacted material.^{36,40}

It is interesting to note that with increasing temperature in the presence of higher concentration of 2.5 M Na-glycinate results in a lower cumulative pore volume at all temperatures of interest (**Fig. 8 (c)**). The extensive formation of lamellar hydromagnesite (**Fig. 6(d) & 6(e)**) at higher temperatures in the presence of 2.5 M Na-glycinate corresponds to a 77% and 83% reduction in the pore volume at 75 °C and 90 °C, respectively (**Table 2**). Additionally, it is also worth noting that the highest pore volume and specific surface area are observed at 50 °C for all cases, indicating that hydromagnesite formation is not as extensive at these conditions to close the pore spaces (**Fig. S3**). The increase in the pore volume at 50 °C facilitates greater diffusion of ions or mass transfer enabling carbon mineralization.

These studies show that hydromagnesite with varying morphologies can be produced by tuning the temperatures associated with reactive CO₂ capture and mineralization with regenerable solvents such as Na-glycinate. Nest-like hydromagnesite at lower temperature is effective for flame retardant materials, while hydromagnesite with elongated lamellar particles can provide extra mechanical reinforcement as additives.^{41,42}

Therefore, achieving tunable controls on the morphologies of the magnesium-carbonate bearing products unlocks new opportunities for introducing these products produced by harnessing CO₂ emissions into markets for sustainable materials.



2.3.4. Mechanisms informed by chemo-morphological transformations

Mechanistic insights into reactive CO₂ capture and mineralization are established by probing and linking the coupled chemo-morphological transformations to the reactivity for producing solid magnesium carbonates (**Table 2**). When carbon mineralization of Mg(OH)₂ occurs in the presence of water without any carbon capture solvent, the relatively low extents of carbon mineralization below 27% and the significant increase in pore volume correspond to the dominance of Mg(OH)₂ dissolution over carbonate formation (**Fig. 2 and Table 2**).^{36,43} In the presence of water alone, lower CO₂ solubility with rising temperature results in an inverse trend in decreasing extents of carbon mineralization with temperature. Limited CO₂ availability and associated proton availability limit the dissolution of Mg(OH)₂ and subsequent carbon mineralization.

In contrast, Na-glycinate enhances the solubility of CO₂ and provides sufficient concentration of (bi)carbonate species needed for carbon mineralization. While CO₂ capture is aided at lower temperatures of 25 °C and 50 °C, the kinetics of Mg(OH)₂ dissolution and the formation and precipitation of Mg-carbonate are aided at higher temperatures of 75 °C and 90 °C.^{19,44} Therefore, higher extents of carbon mineralization of Mg(OH)₂ are noted at 75 °C and 90 °C relative to 25 °C and 50 °C. Interestingly, pre-loading the solvent with CO₂ prior to reactive CO₂ capture and mineralization overcomes the limitation of CO₂ mass transfer from the gas to the liquid phase and provides a ready supply of carbonate species which enables rapid carbon mineralization as noted in **Fig. 3**. Higher concentrations of Na-glycinate of 2.5 M provide additional functional groups and enhanced alkalinity to enhance CO₂ capture and mineralization compared to the 1 M Na-glycinate case (**Fig. 2 and Table 2**). The formation of hydromagnesite as the preferential magnesium carbonate phase is consistent with alkalinity, temperature, and ionic environments.⁴⁵

Elevated temperature of 75 °C and 90 °C and enhanced alkalinity in the case of 2.5 M Na-glycinate facilitates the preferential formation of lamellar-shaped over nest-like hydromagnesite (**Fig. 6**). Carbon mineralization proceeds via the dissolution of particles smaller than 20 μm and the precipitation of Mg-carbonate particles with larger particle sizes (**Fig. 7**). The evolution of well-defined particle size distributions on extensive carbon mineralization is consistent with prior studies indicating that extensive carbonate formation in olivine ((Mg, Fe)₂SiO₄) results in distinct particle size distributions.^{46,47} The extensive formation of hydromagnesite phases and extents of carbon mineralization exceeding 60% are associated with > 77% decrease in the cumulative pore volume (**Fig. 8**). These analyses establish the chemo-morphological mechanisms underlying reactive CO₂ capture and mineralization using Mg(OH)₂. These studies complement prior studies that discuss the feasibility of reactive CO₂ capture and mineralization pathways by harnessing Ca – bearing alkaline sources.^{8–10,18,48–50}

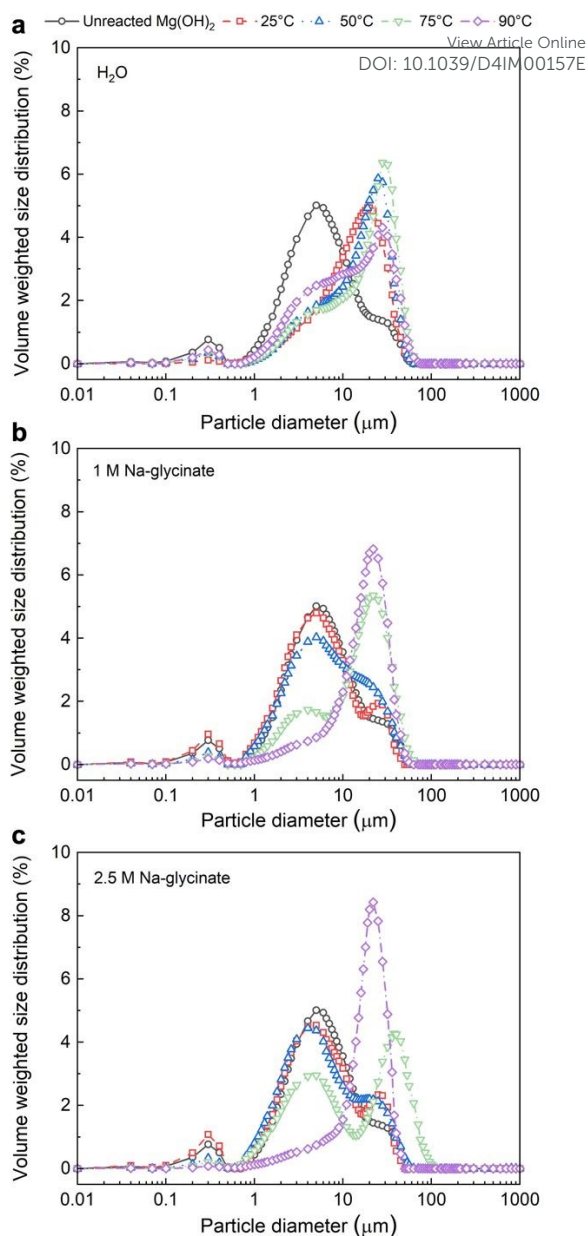


Fig. 7 Particle size distributions of the carbonate - bearing solids obtained with (a) DI water, (b) 1 M Na-glycinate solution, and (c) 2.5 M Na-glycinate solution. The size distributions are measured by light scattering instrument (PSA) with volume - based normalization of the particle size distributions.



3. Conclusions


Reactive CO₂ capture and mineralization of Mg(OH)₂ to produce hydromagnesite ((Mg₅[(CO₃)₄(OH)₂]-4H₂O) by harnessing CO₂ capture solvents such as Na-glycinate is established at concentrations of 1.0 M and 2.5 M and temperatures ranging from 25 to 90 °C. Reacting Mg(OH)₂ at 90 °C with 15 wt% solids in the presence of 2.5 M sodium glycinate after 3 hours under well-stirred conditions results in an extent of carbon mineralization of 75.5%. In contrast, the extents of carbon mineralization in the presence of water without any solvent do not exceed 27% at all conditions of temperature. As a reference, the maximum possible extent of carbon mineralization is 80% when 100% hydromagnesite is produced. The coupled effects of enhanced kinetics of magnesium hydroxide dissolution and Mg-carbonate precipitation at

CO₂ uptake by solvents at lower temperature of 25 °C. Well-defined particle size distributions and a significant decrease in the cumulative pore volume are noted with extensive hydromagnesite growth. Higher temperature and pH conditions favour the formation of lamellar-shaped versus nest-like hydromagnesite. Factors such as SO_x and NO_x in industrial flue gas, as well as operation optimization, need further investigation for practical applications. These findings unlock the potential for harnessing these reactive CO₂ capture and mineralization for harnessing earth abundant magnesium hydroxide-rich tailings and anthropogenic CO₂ emissions to produce Mg-carbonate bearing end products for a sustainable energy and environmental future.

4. Experimental Section

4.1. Chemicals

The reagents used in the study, magnesium hydroxide (Mg(OH)₂, 99%), sodium hydroxide (NaOH, 98%), and glycine (NH₂CH₂COOH, 99%) are procured from Sigma Aldrich. Na-glycinate solutions with concentrations of 1 M and 2.5 M are prepared by adding calculated amounts of sodium hydroxide and glycine to deionized water (18.2 MΩ·cm, Millipore) while stirring at 300 rpm for 1 hour at room temperature. The formation of Na - glycinate can be expressed by the following chemical equation (Reaction 1):



4.2. Experimental approach

4.2.1. Reactive CO₂ capture and mineralization with high purity CO₂

To investigate the influence of temperature and solvent concentration, experiments are conducted in a batch mode in which a slurry bearing Mg(OH)₂ and solvent such as water or sodium glycinate is reacted with CO₂ (Fig. 9 (a)). The slurry comprises 3 g of Mg(OH)₂ and 17 mL of water or the solvent, resulting in a weight ratio of 3:17 or 15 wt%. CO₂ gas (99.9% purity, Airgas Co., USA) is continuously injected into the reactor for five minutes to purge the residual air from the headspace. After the reactor is filled with CO₂, the outlet valve is slowly closed until the internal CO₂ pressure of 1

atm is reached. Next, the reactions are initiated by turning on stirrer with a set point of 300 rpm and applying a set of temperatures: 25 °C, 50 °C, 75 °C, and 90 °C, respectively. The reaction duration is set to 3 hours for each temperature. At the end of the reaction, the reactor is cooled and the solid carbonate-bearing products are collected by vacuum filtration, washed with deionized water, and dried at 80 °C for 24 hours. All experiments were replicated three times to calculate error bars.

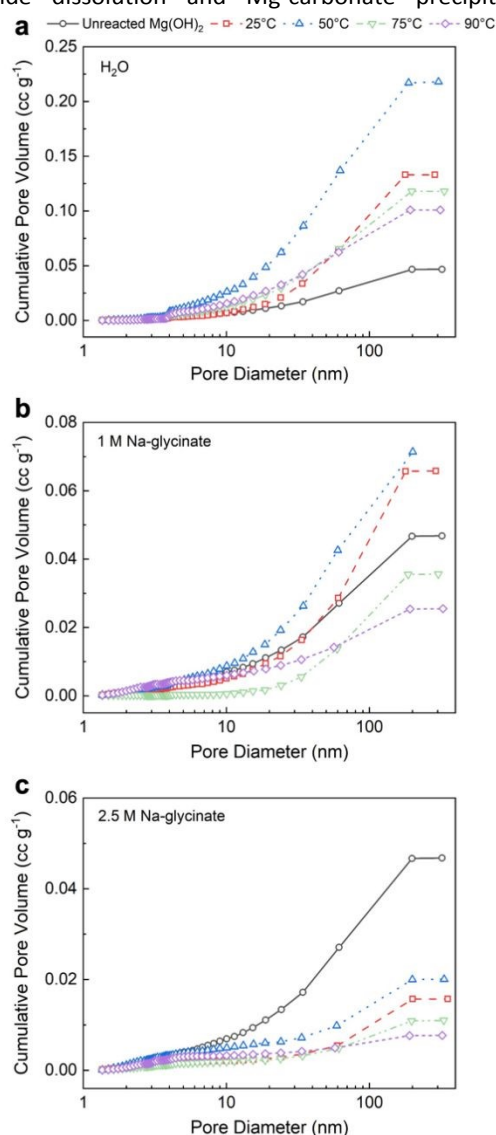


Fig. 8 The cumulative pore volumes of various carbonate - bearing solids obtained using (a) DI water, (b) 1 M Na-glycinate solution, and (c) 2.5 M Na-glycinate solution. The pore volume distributions are determined using the Barrett, Joyner, Halenda (BJH) method with N₂ adsorption data.

elevated temperatures of 75 °C and 90 °C dominate favourable




4.2.2. Reactive CO₂ capture and mineralization using binary mixtures of CO₂ and N₂

Mixtures of CO₂ and N₂ gases with varying compositions of 4, 10, 15, and 20 vol% are prepared to investigate the influence of CO₂ compositions representative of industrial flue gas streams on reactive CO₂ capture and mineralization of Mg(OH)₂. As shown in Fig. 9 (b), a pipe system with gas mixer and flow meter is developed to vary CO₂ concentrations for simulating exhaust flue gas. This gas mixture is injected into the beaker via a gas diffuser at a constant flow rate of 100 SCCM for 6 hours.

To investigate the influence of pre-loaded CO₂ capture solvents on reactive CO₂ capture and mineralization behaviour with Mg(OH)₂, experiments are conducted for 3 hours in the presence of various CO₂ and N₂ mixtures. The hypothesis that the initial loading of CO₂ overcomes the challenge of limited CO₂ availability initially and enables faster kinetics of carbon mineralization, is investigated. The ratio of Mg(OH)₂ to the solvent is 3:17 resulting in 15 wt% of solids in the system. The slurry is well-stirred at 300 rpm. The solid products are recovered through vacuum filtration, washed in deionized water, and dried at 80 °C for 48 hours before further characterization. All experiments were replicated three times to calculate error bars.

4.3. Determination of the extent of carbon mineralization

The extent of carbon mineralization defines CO₂ mineralization conversion of Mg(OH)₂ with respect to the theoretical maximum. In other words, this extent refers to the mole fraction of Mg(OH)₂ that converts into solid carbonate after mineralization. In this study, hydromagnesite (Mg₅[(CO₃)₄(OH)₂]·4H₂O), a hydrated form of magnesium carbonate is formed and is the only product of carbon mineralization, as determined by X-Ray Diffraction (XRD) and Thermo-Gravimetric Analyses (TGA).⁵¹ The formation of hydromagnesite via carbon mineralization is shown in Reaction 2.²¹ Accordingly, the extent of carbon mineralization can be defined as the ratio between the captured mole of CO₂ and the theoretical CO₂ mole capacity of the sorbent.⁵²



$$EoC = \frac{Wt\%_M/M_M}{Wt\%_M/M_M + (1-Wt\%_M)/M_B} \times 100\% \quad (\text{Equation 1})$$

In the expression above, *EoC* refers to the extent of carbon mineralization, *Wt%_M* refers to the weight percent of magnesium carbonate in the fully dried samples, while the *M_M* and *M_B* refer to the molecular weight of magnesium carbonate and brucite or magnesium hydroxide, respectively. Here, thermogravimetric analysis (TGA) is used to determine *Wt%_M*. As shown in Equation 2, *TGA* is the actual weight loss of the fully dried samples in the temperature range 300 - 600 °C, while *TGA_M* and *TGA_B* refer to the theoretical weight loss of pure magnesium carbonate and magnesium hydroxide, respectively. Magnesium carbonate (MgCO₃ → MgO + CO₂) and magnesium hydroxide (Mg(OH)₂ → MgO + H₂O) decompose at 300 - 600 °C, the *TGA_M* and *TGA_B* values are calculated to be 52.20% and 30.89%, respectively.


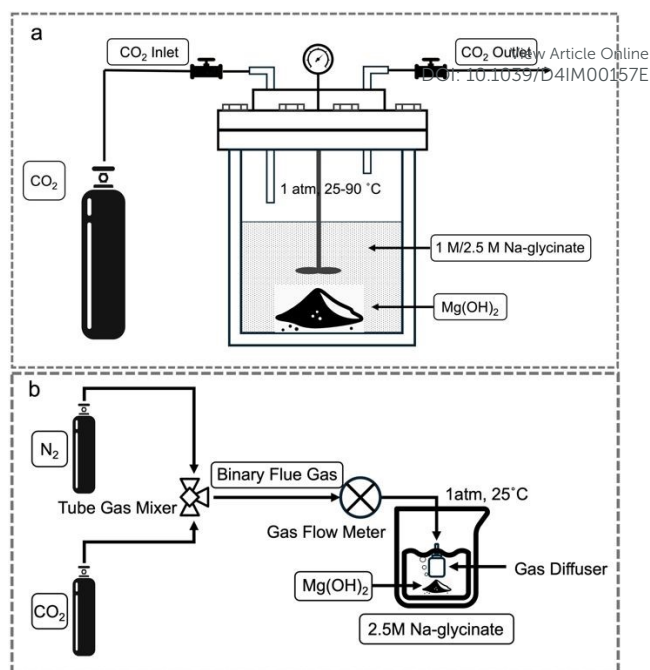


Fig. 9 Schematic representation of the integrated CO₂ capture and mineralization with (a) pure CO₂ and (b) mixed gases composed of CO₂ and N₂.

$$Wt\%_M = \frac{TGA - TGA_B}{TGA_M - TGA_B} \times 100\% \quad (\text{Equation 2})$$

4.4. Characterization of the carbonate-bearing products

The chemical compositions and the morphological features of the carbonate-bearing products are analysed to provide insights into the mechanisms of reactive CO₂ capture and mineralization. The CO₂ content in the carbonate-bearing products is determined using Thermogravimetric Analysis (TGA, TA Instruments, SDT 650), in which the temperature is ramped from 25 °C to 1000 °C with a 2 °C min⁻¹ ramping rate. Temperatures in the range of 300 - 500 °C are of particular interest since CO₂ and water releases occur in this range. The magnesium carbonate phases present are determined using Wide-Angle X-Ray Scattering (WAXS) measurements. These measurements are conducted at Sector 9-ID-C at the Advanced Photon Source (APS) in Argonne National Laboratory (ANL). For these experiments, the X-ray energy is set to 21.0 keV, which corresponds to the wavelength of 0.59 Å. The total X-ray flux during the measurements is 10¹³ photons mm⁻² s⁻¹.^{54,55} Detailed information about the instrument is reported in prior publications.^{54,55} To further confirm the chemical bonds and functional groups in the carbonate-bearing products, Attenuated Total Reflectance Fourier Transform-Infrared Spectroscopy (ATR-FTIR, Nicolet FT-IR IS50, Thermo Scientific) analyses are performed. The morphological features and the particle size distributions are analysed using Field Emission Scanning Electron Microscope (FESEM, LEO 1550 FESEM, Bruker) and the Laser Diffraction Particle Size Analyzer (PSA, Anton Paar), respectively. The surface area and pore size distributions (PSD) before and after carbon mineralization are determined from N₂ adsorption-desorption isotherms using the Brunauer-Emmett-Teller (BET) method and Barrett-Joyner-Halenda (BJH) method, respectively. (Quantachrome Autosorb iQ Analyzer, Boynton Beach,



FL). Prior to measuring the adsorption-desorption isotherms, the samples were outgassed at 120°C for 18 hours.

Author contributions

Greeshma Gadikota - supervision, conceptualization, data curation, formal analysis, funding acquisition, investigation, methodology, project administration, resources, software, validation, visualization, writing-original draft, writing-review & editing.

Xun Gao - investigation, data curation, formal analysis, methodology, resources, software, validation, visualization, writing-original draft, writing-review & editing.

Peilong Lu - validation, visualization, writing-review & editing.

Ivan Kuzmenko – investigation

Jan Ilavsky – investigation

Conflicts of interest

Greeshma Gadikota is the co-founder of Carbon To Stone which is commercializing technologies for industrial decarbonization and carbon management. The other authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Data availability

The data supporting this article have been included in the main manuscript and as part of the Supplementary Information.

Acknowledgements

G.G., X.G., and P. L.'s contributions are supported by the U. S. Department of Energy (DOE): DE-AC36-08GO28308. The authors acknowledge the use of shared facilities at the Cornell Center for Materials Research (CCMR). G.G. and P. L. gratefully acknowledge the support of the NSF Partnerships for Innovation (PFI) program (NSF Award #: 2141091). The authors also gratefully acknowledge the support of Ivan Kuzmenko and Jan Ilavsky at APS for assisting in this effort. This research used resources of the Advanced Photon Source, a U.S. Department of Energy (DOE) Office of Science user facility at Argonne National Laboratory and is based on research supported by the U.S. DOE Office of Science-Basic Energy Sciences, under Contract No. DE-AC02-06CH11357.

References

- 1 A. L. Harrison, I. M. Power, G. M. Dipple, Accelerated carbonation of brucite in mine tailings for carbon sequestration, *Environ. Sci. Technol.*, 2013, **47**, 126–134.
- 2 A. L. Harrison, G. M. Dipple, I. M. Power, K. U. Mayer, Influence of surface passivation and water content on mineral reactions in unsaturated porous media: Implications for brucite carbonation and CO₂ sequestration, *Geochim. Cosmochim. Acta*, 2015, **148**, 477–495.

- 3 I. M. Power, A. L. Harrison, G. M. Dipple, Accelerating mineral carbonation using carbonic anhydrase, *Environ. Sci. Technol.*, 2016, **50**, 2610–2618.
- 4 K. Rausis, A. Ćwik, I. Casanova, Phase evolution during accelerated CO₂ mineralization of brucite under concentrated CO₂ and simulated flue gas conditions, *J. CO₂ Util.*, 2020, **37**, 122–133.
- 5 E. S. Sanz-Pérez, C. R. Murdock, S. A. Didas, C. W. Jones, Direct capture of CO₂ from ambient air, *Chem. Rev.*, 2016, **116**, 11840–11876.
- 6 X. Wang, C. Song, Carbon capture from flue gas and the atmosphere: A perspective, *Front. Energy Res.*, 2020, **8**, 560849.
- 7 A. Sanna, M. Uibu, G. Caramanna, R. Kuusik, M. M. Maroto-Valer, A review of mineral carbonation technologies to sequester CO₂, *Chem. Soc. Rev.*, 2014, **43**, 8049–8080.
- 8 P. Ochonma, X. Gao, G. Gadikota, Tuning reactive crystallization pathways for integrated CO₂ capture, conversion, and storage via mineralization, *Acc. Chem. Res.*, 2024, **57**, 267–274.
- 9 T. Yin, S. Yin, A. Srivastava, G. Gadikota, Regenerable solvents mediate accelerated low-temperature CO₂ capture and carbon mineralization of ash and nano-scale calcium carbonate formation, *Resour. Conserv. Recycl.*, 2022, **180**, 106209.
- 10 M. Liu, A. Hohenshil, G. Gadikota, Integrated CO₂ capture and removal via carbon mineralization with inherent regeneration of aqueous solvents, *Energy Fuels*, 2021, **35**, 8051–8068.
- 11 X. Liu, S. Zhang, Q.-W. Song, X.-F. Liu, R. Ma, L.-N. He, Cooperative calcium-based catalysis with 1,8-diazabicyclo[5.4.0]-undec-7-ene for the cycloaddition of epoxides with CO₂ at atmospheric pressure, *Green Chem.*, 2016, **18**, 2871–2876.
- 12 J. M. Kang, et al., Energy-efficient chemical regeneration of AMP using calcium hydroxide for operating carbon dioxide capture process, *Chem. Eng. J.*, 2018, **335**, 338–344.
- 13 P. C. Chen, S.-Z. Lin, Optimization in the absorption and desorption of CO₂ using sodium glycinate solution, *Appl. Sci.*, 2018, **8**, 2041.
- 14 F. M. Brethomé, N. J. Williams, C. A. Seipp, M. K. Kidder, R. Custelcean, Direct air capture of CO₂ via aqueous-phase absorption and crystalline-phase release using concentrated solar power, *Nat. Energy*, 2018, **3**, 553–559.
- 15 M. Liu, H. Asgar, S. Seifert, G. Gadikota, Novel aqueous amine looping approach for the direct capture, conversion, and storage of CO₂ to produce magnesium carbonate, *Sustain. Energy Fuels*, 2020, **4**, 1265–1275.
- 16 L. Zhao, L. Sang, C. Jun, J. Ji, H. H. Teng, Aqueous carbonation of natural brucite: Relevance to CO₂ sequestration, *Environ. Sci. Technol.*, 2010, **44**, 406–411.
- 17 T. Dudev, C. Lim, Importance of metal hydration on the selectivity of Mg²⁺ versus Ca²⁺ in magnesium ion channels, *J. Am. Chem. Soc.*, 2013, **135**, 17200–17208.
- 18 M. Liu, G. Gadikota, Single-step, low-temperature and integrated CO₂ capture and conversion using sodium glycinate to produce calcium carbonate, *Fuel*, 2020, **275**, 117887.
- 19 P. Bénéth, G. D. Saldi, J.-L. Dandurand, J. Schott, Experimental determination of the solubility product of magnesite at 50 to 200°C, *Chem. Geol.*, 2011, **286**, 21–31.



- 20 D. Guo, et al., Amino acids as carbon capture solvents: Chemical kinetics and mechanism of the glycine + CO₂ reaction, *Energy Fuels*, 2013, **27**, 3898–3904.
- 21 Q. Gautier, P. Bénézech, V. Mavromatis, J. Schott, Hydromagnesite solubility product and growth kinetics in aqueous solution from 25 to 75°C, *Geochim. Cosmochim. Acta*, 2014, **138**, 1–20.
- 22 S. M. Klara, CO₂ solubility in water and brine under reservoir conditions, *Chem. Eng. Commun.*, 1990, **90**, 23–33.
- 23 P. Birkle, I. S. Torres-Alvarado, Water-Rock Interaction, CRC Press, 2010.
- 24 D. Daval, R. Hellmann, G. D. Saldi, R. Wirth, K. G. Knauss, Linking nm-scale measurements of the anisotropy of silicate surface reactivity to macroscopic dissolution rate laws: New insights based on diopside, *Geochim. Cosmochim. Acta*, 2013, **107**, 121–134.
- 25 X. Gao, D. Prasad, M. A. Mahadik, G. Gadikota, Enhanced H₂ recovery by coupling the water-gas shift reaction with in-situ CO₂ capture and mineralization using earth-abundant Ca- and Mg-silicates and hydroxides, *React. Chem. Eng.*, 2025.
- 26 C. Blaquiere, G. Berthon, Speciation studies in relation to magnesium bioavailability: Formation of Mg(II) complexes with glutamate, aspartate, glycinate, lactate, pyroglutamate, pyridoxine, and citrate, and appraisal of their potential significance towards magnesium gastrointestinal absorption, *Inorg. Chim. Acta*, 1987, **135**, 179–189.
- 27 R. Weber, S. Orsino, N. Lallemand, A. Verlaan, Combustion of natural gas with high-temperature air and large quantities of flue gas, *Proc. Combust. Inst.*, 2000, **28**, 1315–1321.
- 28 F. Gholami, M. Tomas, Z. Gholami, M. Vakili, Technologies for the nitrogen oxides reduction from flue gas: A review, *Sci. Total Environ.*, 2020, **714**, 136712.
- 29 V. Majer, J. Sedlbauer, G. Bergin, Henry's law constant and related coefficients for aqueous hydrocarbons, CO₂ and H₂S over a wide range of temperature and pressure, *Fluid Phase Equilib.*, 2008, **272**, 65–74.
- 30 A. Botha, C. A. Strydom, DTA and FT-IR analysis of the rehydration of basic magnesium carbonate, *J. Therm. Anal. Calorim.*, 2003, **71**, 987–996.
- 31 C. M. Janet, B. Viswanathan, R. P. Viswanath, T. K. Varadarajan, Characterization and photoluminescence properties of MgO microtubes synthesized from hydromagnesite flowers, *J. Phys. Chem. C*, 2007, **111**, 10267–10272.
- 32 T. Selvamani, A. Sinhamahapatra, D. Bhattacharjya, I. Mukhopadhyay, Rectangular MgO microsheets with strong catalytic activity, *Mater. Chem. Phys.*, 2011, **129**, 853–861.
- 33 R. Černý, V. Valvoda, M. Chládek, Empirical texture corrections for asymmetric diffraction and inclined textures, *J. Appl. Crystallogr.*, 1995, **28**, 247–253.
- 34 M. Akao, S. Iwai, The hydrogen bonding of hydromagnesite, *Acta Crystallogr. B*, 1977, **33**, 1273–1275.
- 35 A. Abu Fara, M. R. Rayson, G. F. Brent, T. K. Oliver, M. Stockenhuber, E. M. Kennedy, Formation of magnesite and hydromagnesite from direct aqueous carbonation of thermally activated lizardite, *Environ. Prog. Sustain. Energy*, 2019, **38**(3).
- 36 Y. Wang, et al., Preparation, properties and phase transition of mesoporous hydromagnesite with various morphologies from natural magnesite, *Powder Technol.*, 2020, **364**, 822–830. DOI: 10.1039/D4IM00157E
- 37 H. Pang, G. Ning, W. Gong, J. Ye, Y. Lin, Direct synthesis of hexagonal Mg(OH)₂ nanoplates from natural brucite without dissolution procedure, *Chem. Commun.*, 2011, **47**, 6317–6319.
- 38 D. Bhattacharjya, T. Selvamani, I. Mukhopadhyay, Thermal decomposition of hydromagnesite: Effect of morphology on the kinetic parameters, *J. Therm. Anal. Calorim.*, 2012, **107**, 439–445.
- 39 T. Selvamani, T. Yagyu, S. Kawasaki, I. Mukhopadhyay, Easy and effective synthesis of micrometer-sized rectangular MgO sheets with very high catalytic activity, *Catal. Commun.*, 2010, **11**, 537–541.
- 40 S. Guermeh, J. Mocellin, L.-H. Tran, G. Mercier, L.-C. Pasquier, A study of hydromagnesite and nesquehonite precipitation in indirect aqueous carbonation of thermally activated serpentine in a batch mode, *J. Cryst. Growth*, 2022, **584**, 126540.
- 41 H. Y. Atay, E. Çelik, Use of Turkish huntite/hydromagnesite mineral in plastic materials as a flame retardant, *Polym. Compos.*, 2010, **31**, 1692–1700.
- 42 A. A. Basfar, H. J. Bae, Influence of magnesium hydroxide and huntite hydromagnesite on mechanical properties of ethylene vinyl acetate compounds crosslinked by dicumyl peroxide and ionizing radiation, *J. Fire Sci.*, 2010, **28**, 161–180.
- 43 Q. Li, Y. Ding, G. Yu, C. Li, F. Li, Y. Qian, Fabrication of light-emitting porous hydromagnesite with rosette-like architecture, *Solid State Commun.*, 2003, **125**, 117–120.
- 44 D. A. Vermilyea, The dissolution of MgO and Mg(OH)₂ in aqueous solutions, *J. Electrochem. Soc.*, 1969, **116**, 1179.
- 45 R. Hay, N. T. Dung, A. Lesimple, C. Unluer, K. Celik, Mechanical and microstructural changes in reactive magnesium oxide cement-based concrete mixes subjected to high temperatures, *Cem. Concr. Compos.*, 2021, **118**, 103955.
- 46 S. Katre, P. Ochonma, H. Asgar, A. M. Nair, K. Ravi, G. Gadikota, Mechanistic insights into the co-recovery of nickel and iron via integrated carbon mineralization of serpentinized peridotite by harnessing organic ligands, *Phys. Chem. Chem. Phys.*, 2024, **26**, 9264–9283.
- 47 G. Gadikota, J. Matter, P. Kelemen, A. H. A. Park, Chemical and morphological changes during olivine carbonation for CO₂ storage in the presence of NaCl and NaHCO₃, *Phys. Chem. Chem. Phys.*, 2014, **16**, 4679–4693.
- 48 G. Gadikota, Carbon mineralization pathways for carbon capture, storage, and utilization, *Commun. Chem.*, 2021, **4**, 23.
- 49 G. Gadikota, Multiphase carbon mineralization for the reactive separation of CO₂ and directed synthesis of H₂, *Nat. Rev. Chem.*, 2020, **4**, 78–89.
- 50 M. Liu, G. Gadikota, Integrated CO₂ capture, conversion, and storage to produce calcium carbonate using an amine looping strategy, *Energy Fuels*, 2019, **33**, 1722–1733.
- 51 L. A. Hollingbery, T. R. Hull, The thermal decomposition of huntite and hydromagnesite—A review, *Thermochim. Acta*, 2010, **509**, 1–11.
- 52 A. A. Olajire, A review of mineral carbonation technology in sequestration of CO₂, *J. Pet. Sci. Eng.*, 2013, **109**, 364–392.
- 53 X. Gao, H. Asgar, I. Kuzmenko, G. Gadikota, Architected mesoporous crystalline magnesium silicates with ordered



ARTICLE

Journal Name

- pore structures, *Microporous Mesoporous Mater.*, 2021, **327**, 111381.
- 54 J. Ilavsky, F. Zhang, A. J. Allen, L. E. Levine, P. R. Jemian, G. G. Long, Ultra-small-angle X-ray scattering instrument at the Advanced Photon Source: History, recent development, and current status, *Metall. Mater. Trans. A*, 2013, **44**, 68–76.
- 55 U. Bonse, M. Hart, Tailless X-ray single-crystal reflection curves obtained by multiple reflection, *Appl. Phys. Lett.*, 1965, **7**, 238–240.

View Article Online
DOI: 10.1039/D4IM00157E

Open Access Article. Published on 20 February 2025. Downloaded on 2/22/2025 6:04:27 AM.
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.



Industrial Chemistry & Materials Accepted Manuscript

Data Availability Statement

The data supporting this article have been included in the main manuscript and as part of the Supplementary Information.

