

Materials Advances

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: J. A. Lirio Piñar, M. Lázaro, G. R. Iglesias, T. Romacho, A. Delgado, G. García-García and S. Ahualli, *Mater. Adv.*, 2025, DOI: 10.1039/D4MA01037J.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Title of the article:

View Article Online
DOI: 10.1039/D4MA01037J

Magnetic activated carbon particles as stimuli-responsive vehicles for methotrexate

J.A. Lirio Piñar^{1,2 †}, M. Lázaro^{1,2,3 †}, G.R. Iglesias^{1,2,3,4}, Tania Romacho⁵, A.V.Delgado^{1,2,3,4}, Gracia García-García^{2,5 *}, S. Ahualli^{1,4 *}

¹Department of Applied Physics, School of Sciences, University of Granada, 18071 Granada, Spain.

²NanoMag Lab. Department of Applied Physics, Faculty of Science University of Granada, Planta -1. Edificio I+D Josefina Castro, Av. de Madrid, 28, 18012, Granada, Spain.

³Biosanitary Research Institute of Granada (ibs.GRANADA), Andalusian Health Service (SAS), University of Granada, 18001, Granada, Spain.

⁴MNat Unit of Excellence. University of Granada. Spain.

⁵Chronic Complications Diabetes Lab (ChroCoDiL). Department of Nursing, Physiotherapy and Medicine. University of Almería. Ctra. Sacramento s/n, 04120 Almería, Spain.

† These authors contributed equally to this work

*Corresponding authors:

S. Ahualli

Departamento de Física Aplicada, Facultad de Ciencias. Universidad de Granada, 18071 Granada, Spain

Gracia García-García

Chronic Complications Diabetes Lab (ChroCoDiL). Department of Nursing, Physiotherapy and Medicine. University of Almería



Keywords: Magnetic Activated Carbon, Rotating Magnetic Field, Photothermia, MTX Adsorption and Release, Cytotoxicity

Abstract

This study investigates porous activated carbon (AC) particles as drug delivery vehicles for methotrexate (MTX). To enhance functionality, magnetic nanoparticles are embedded in AC imparting superparamagnetic properties (MAC composites), making them suitable for controlled transport and localization, as well as for facilitating their response to external fields. The composites are further functionalized with branched low molecular weight polyethyleneimine (PEI) to confer them a positive charge. After characterizing size, composition, and magnetic hysteresis, their potential as MTX carriers is assessed. Electrophoretic mobility and infrared data confirm the presence of magnetite, polymer, and drug. Photothermal therapy (PTT) tests reveal that MAC-PEI particles produce up to



180 W/g of specific absorption rate (SAR) under infrared laser radiation. Due to its anisotropy, rotating magnetic fields (RMF) induce particle rotation, offering another external stimulus. Biocompatibility studies with human skin M1 fibroblasts confirm no significant cytotoxicity at concentrations below 700 $\mu\text{g/mL}$. The particles adsorb over 80% of MTX from 0.6 mM solutions, with release evaluated at pH 5.8 under PTT and RMF stimuli. Both methods significantly enhance MTX release, achieving twice the drug release compared to passive conditions, demonstrating the particles' high potential as active vehicles for targeted MTX delivery.

View Article Online
DOI: 10.1039/D4MA01037J



1. Introduction

Cancer is one of the world's leading causes of death and its incidence is expected to triple by 2050, largely due to ageing population.^{1, 2} It is therefore evident that novel approaches are required to overcome the forthcoming challenges in cancer treatment. A promising strategy to address this issue involves the use of advanced carriers with the objective of optimizing conventional treatments (e.g. chemotherapy) and/or the implementation of novel therapeutic approaches such as antitumor hyperthermia.³⁻⁹

Methotrexate (MTX) is a standard anticancer drug employed in the treatment of a range of cancers, including acute lymphoblastic leukemia¹⁰, osteosarcoma¹¹, and lymphoma malignancies¹², among others. However, MTX is subject to rapid plasma clearance and poor solubility¹³, necessitating the administration of high doses over an extended infusion period to achieve effective treatment. Consequently, this dosage regimen is frequently associated with toxic effects and the development of resistance¹⁴⁻¹⁶. Therefore, the controlled delivery of MTX is being investigated as a means of enhancing the safety and efficacy of therapy¹⁷.

Among the potential advanced materials for MTX delivery, carbon-based microporous (pore size in the order of a few nm) particles have shown promise¹⁸⁻²⁰. The nanometer pore diameter of AC materials is responsible for a high surface area to volume ratio, which renders them potential candidates for high drug payloads, as has been previously reported^{21, 22}. In addition, AC particles possess a larger diameter pore structure, known as mesopores (2-50 nm) and macropores (above 50 nm), sufficiently large to accommodate large molecules, such as various drugs, including MTX.

Moreover, AC particles are cost-effective and safe, as they are already being employed in clinical settings²³. In addition to their potential for drug delivery, they are capable of



absorbing light within the NIR-I window, where tissues are nearly transparent, and converting it into heat. For example, Shahcheragh et al.²⁴ demonstrated a strong absorbance in the 300-1100 nm wavelength range. Furthermore, Li et al.²⁵ developed an innovative approach whereby the incorporation of carbon nanoparticles (NPs) facilitated the enhanced absorption of laser irradiation on a suspension of (low-absorbance) alumina, resulting in the production of particles with precisely controlled geometry.

In this work, interest is focused on achieving a local temperature elevation by application of external stimuli capable of releasing heat. This is a controlled way of reaching hyperthermia (temperature above 37.5 °C), and it is denominated photothermal therapy (PTT) when it is achieved by subjecting the target system to the action of a laser radiation, typically in the near-infrared (NIR) range. While other potential applications exist, most research efforts in the field of PTT are concentrated on the biomedical domain. The objective is to achieve localized heating, which can effectively eliminate malignant cells without affecting surrounding healthy tissue. This can be achieved through direct application of an infrared laser to skin tumors or indirectly to deeper tumors using techniques such as optical fibers, which can guide the light directly into the malignant area. While PTT has been the subject of extensive preclinical investigation (see, for example, references^{26, 27}), ongoing research is aimed at facilitating its translation into clinical applications²⁸.

Iron oxide NPs (magnetite and maghemite) have been the subject of extensive investigation due to their superparamagnetic and biocompatible character, with applications in drug delivery, magnetic resonance imaging (MRI), and magnetic hyperthermia²⁹. It is noteworthy that magnetite NPs also demonstrate a photothermal therapy response, as evidenced in previous studies³⁰⁻³³. Furthermore, it has recently been reported that a low-frequency magnetic field applied to drug-loaded magnetic particles




has the potential to induce a prompt release of the drug. In such circumstances, the magnetic particles align themselves with the direction of the rotating field, thereby generating a strong mechanical force that is capable of producing a rapid release of the drug^{34, 35}. In addition, *in vitro*³⁶ and *in vivo*³⁷ antitumor effect of magnetic particles under a low-frequency magnetic field have been recently demonstrated.

Polyethyleneimine (PEI) has been shown to be an effective coating agent for inorganic nanoparticles in a number of studies^{33, 38-41}. It is a versatile, highly positive charge-density polycation that creates a cationic surface, which has particular interest in the field of anticancer drug delivery. A positive surface can facilitate enhanced biological interactions with cellular surfaces, thereby improving cellular uptake. Additionally, it can facilitate interactions with tumor vasculature proteoglycans, which could improve specific targeting⁴². Furthermore, the characteristics of this polymer are highly advantageous for drug delivery, particularly due to its hydrophilic nature and its capacity to load negatively charged drugs such as MTX, as previously reported⁴³. Furthermore, and of greater relevance to the intended application, it endows the system with biocompatibility, given that low-molecular-weight branched PEI exhibits low cytotoxicity⁴⁴⁻⁴⁵.

This article proposes a method for the production of activated carbon (AC) microporous particles that are magnetizable (Magnetic Activated Carbons, or MAC) through the incorporation of magnetic iron oxide NPs. It has been previously demonstrated that carbon materials in the form of carbon nanodots, with different doping elements and surface modifications, are efficient carriers for drugs like camptothecin⁴⁶⁻⁴⁸, with significant *in vitro* anticancer activity.

The physicochemical and magnetic characterization of the particles confirm their structure, demonstrating an appropriate size, composition, and PTT and magnetic




character. The PEI surface coating of MAC was employed to enhance the particles interaction with MTX, given that this exhibits a negative charge. Moreover, the MAC-PEI structures demonstrated preliminary biocompatibility, as evidenced by the absence of cytotoxic effects in the human skin fibroblast cell line M1 in a broad concentration range (0-700 $\mu\text{g/ml}$). Finally, *in vitro* drug release studies demonstrated the potential of MTX-loaded MAC-PEI for stimuli-responsive drug delivery when an external NIR-I light or a low-frequency rotating magnetic field was applied. To the best of our knowledge, this is the first instance of a hybrid nanomaterial based on AC, magnetic nanoparticles and PEI having been engineered. To date, no studies have focused on the MTX adsorption and release of this material and the effect of PTT and low-strength rotating magnetic field stimuli. It is the objective of this research to facilitate the clinical translation of MAC particles as anticancer agents under external stimuli.

2. Materials and Methods

2.1. Materials

YP50F AC particles were purchased from Kuraray Europe GmbH (Finland). The iron salts $\text{FeSO}_4 \cdot 7\text{H}_2\text{O}$ and $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$ from Merck Sigma Aldrich (Germany), and a 32 % ammonia solution from Scharlau, Spain were used for the preparation of the magnetic NPs, together with water from a Milli-Q Academic device (Millipore, Spain). For the polymer coating, branched polyethyleneimine (PEI, MW \approx 2000 g/mol) was used, and for the drug adsorption and release experiments methotrexate (MTX) was chosen, both compounds from Sigma Aldrich (Germany). Phosphate buffer saline (PBS), glutaraldehyde, acetic acid, crystal violet solution (1%, aqueous solution) and antibiotic-antimycotic solution (10,000 units penicillin, 10 mg streptomycin and 25 μg amphotericin



B per mL) for cell culture and biocompatibility tests were also from Merck Sigma-Aldrich (Ger, and Dulbecco's modified Eagle's medium (DMEM), Fetal Bovine Serum (FBS), 0.05% trypsin-EDTA were supplied by Gibco™ (ThermoFisher Scientific, USA).

2.2. Methods

2.2.1. Preparation of polyethyleneimine-coated magnetic activated carbon particles preparation

The synthesis of Fe_3O_4 colloids was conducted in accordance with the chemical coprecipitation methodology previously reported in reference [46]. Magnetic activated carbon (MAC) particles were produced by the addition of YP50F AC to the aqueous media in which the Fe_3O_4 colloids were formed. The methodology commenced with the mechanical stirring of two aqueous solutions, comprising 0.9 g of $\text{FeSO}_4 \cdot 7\text{H}_2\text{O}$ in 8.6 mL and 1.7 g of $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$ in 10 mL, respectively, at room temperature. Subsequently, 5.2 g of YP50F AC was dispersed in 100 ml of water and added to the aforementioned solutions. The resulting suspension was then stirred for a period of 30 minutes. To induce the precipitation of Fe_3O_4 onto the surface of the AC particles, 4.4 mL of the ammonia solution was added. Following a period of one hour under mechanical stirring, the resulting MAC particles were subjected to three cycles of centrifugation (10 minutes at 15,000 rpm, using a Sigma 3-30KS centrifuge, Germany), followed by magnetic decanting and redispersion in water. Subsequently, the product was subjected to drying in an oven at a temperature of 50 degrees Celsius.

In order to obtain the MAC particles coated with the PEI polymer, 0.5 g of MAC particles were diluted in 30 mL of PEI, and MilliQ water was added to complete a solution of 250 mL. The mixture was then subjected to rigorous mechanical stirring for the duration of the night. Subsequently, the particles were purified by centrifugation at 21,000



rpm for 20 minutes, with this process repeated until the supernatant reached a pH range of 7-7.5.

View Article Online
DOI: 10.1039/D4MA01037J

2.2.2. Adsorption of methotrexate onto the surface of polyethyleneimine-coated magnetic activated carbon particles

MTX-loaded MAC-PEI nanoporous particles were produced by the incubation of MAC particles (6 mg/ml) in an aqueous solution containing MTX (0.6 mM) under mild stirring using a Stuart rotator SB3 (United States) at 30 rpm (Figure 1). Samples were centrifuged for 45 minutes at 14000 rpm (Mikro 220R, Hettich Zentrifugen, Germany) to remove the non-attached drug molecules. Two adsorption kinetics experiments were performed, the first one at a fixed concentration (the one chosen for the rest of the experiments, 0.6 mM MTX) versus time, in the range of 1, 2, 24, 72, 144 hours. The second one, at a fixed time (24 hours of adsorption) varying the drug concentration (between 0.2 mM-10 mM). Figure 1a provides a schematic representation of the process of MAC particle synthesis, coating with PEI, and drug incorporation.


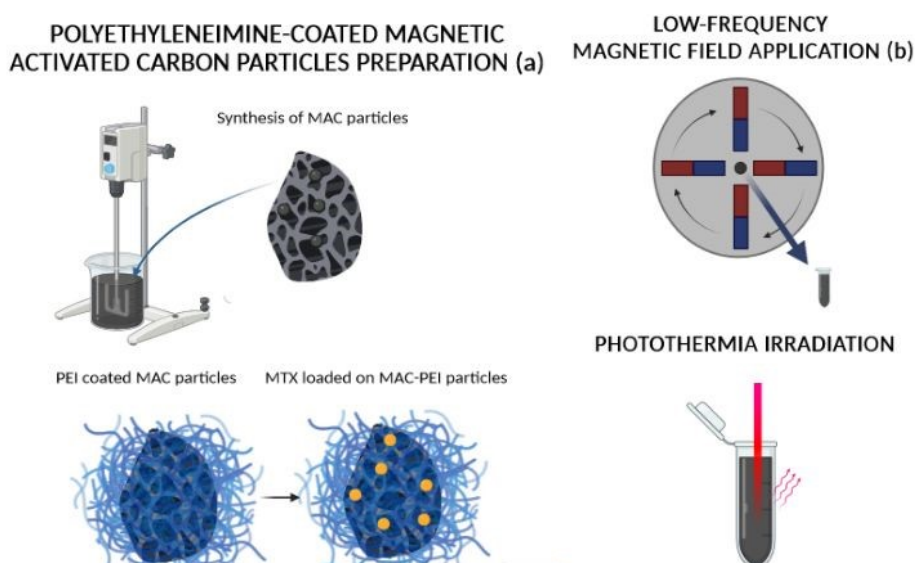



Fig. 1. (a) Scheme of the synthesis procedures of MAC particles, their coating with PEI and the incorporation of pharmacophore. (b) Diagram of the operation of the low-frequency rotating magnetic field device (top) and of the photothermia experiment (below). Images created with Biorender.com.

2.2.3. Size and shape of the particles

Evaluation of the size of the MAC nanoplateforms was carried out by electron microscopy analysis. Fe_3O_4 and MAC particles were studied by high-resolution transmission electron microscopy (HRTEM) and high-angle annular dark field scanning transmission electron microscopy (HAADF-STEM) (HAADF TALOS F200X, Thermofisher Scientific Inc., United States; accelerating voltage of 200 kV). Elemental analysis was performed during these electron microscopy observations [energy dispersive X-ray (EDX) spectrometer, Bruker Nano GmbH, Germany]. Particle size was also evaluated by Dynamic Light Scattering (DLS) using a Zetasizer Nano-ZS (Malvern Pananalytical, UK). The specific surface area of AC YP50F is $1692 \text{ m}^2/\text{g}$, and the micropore size distribution peaks at 1 nm (according to Kuraray Europe GmbH). These characteristics make it an ideal drug vehicle ⁴⁹.

2.2.4. Electrophoretic mobility

The determination of the surface electrical properties of AC, bare Fe_3O_4 , MAC-PEI and MTX-loaded MAC-PEI was carried out by measuring their electrophoretic mobility using the Zetasizer Nano-ZS device. A qualitative follow-up of the PEI coating of the MAC surface and the subsequent MTX adsorption was carried out by determining the influence of pH on their electrophoretic mobility in the presence of 1 mM KCl.



2.2.5. FTIR analysis

The structure of MAC-PEI was confirmed by Fourier transform infrared (FTIR) spectroscopy (FT/IR-6200 spectrometer, JASCO, United States; resolution of 0.25 cm^{-1}). For that purpose, the MAC-PEI spectrum was compared to those obtained for MAC, Fe_3O_4 and PEI.

2.2.6. Magnetic properties

The magnetization cycles were obtained at $(20.0 \pm 0.5)^\circ\text{C}$, in both a Vibrating Sample Magnetometer (PPMS DynaCool, Quantum Design, USA, maximum applied field strength 4700 kA/m) and an AC Hyster Series magnetometer (Nanotech Solutions S.L., Spain), operating at a frequency of 1.5 kHz and a maximum field strength of 120 kA/m .

2.2.7. Low-frequency rotating magnetic field application

The technique entails exposing the sample to a low-frequency RMF, thereby circumventing the heating phenomenon that occurs in magnetic hyperthermia. This approach facilitates drug release by rotating the particles, which enhances the diffusion process. This is accomplished through the utilisation of four permanent magnets positioned in a face-to-face configuration. The magnets are made to rotate in synchrony around the sample, with opposite polarities (Figure 1b). The synchronised rotation of the magnetic field induces a corresponding rotation of the magnetic particles within the sample. The field strength was 65 mT and the rotation speed $300 \pm 10\text{ rpm}$.

2.2.8. Thermal measurements

The photothermal (PTT) capacity of the various samples was evaluated using an 850 nm laser at powers of 0.5 , 1 and 1.5 W/cm^2 . The particle concentrations were 5 mg/mL .



Eppendorf tubes containing 100 μl of the nanoparticles (Fe_3O_4 , AC, MAC and MAC-PEI particles) in water were used. Irradiation was conducted from the top, and the temperature was recorded with a thermographic camera (FLIR E60, 320 x 240 pixel IR resolution, FLIR Systems, Inc., United States) throughout the experiment (Fig.1).

The amount of heat transferred from the particles to their surrounding environment is determined by the Specific Absorption Rate (*SAR*), which is calculated through experimental means as follows:

$$SAR = \frac{C_{liq} \rho_{liq}}{\phi} \frac{dT}{dt} \quad (1)$$

being C_{liq} , ρ_{liq} the mass specific heat and the density of the suspension and ϕ the NPs concentration (w/v). The essential quantity is the rate of temperature increase dT/dt , which is determined by the linear model⁵⁰. The densities of magnetite ($\rho_{MAG} = 5.2 \times 10^3$ g/L), and of AC ($\rho_{AC} = 0.3 \cdot 10^3$ g/L, provided by Kuraray Europe GmbH), as well as the magnetite-to-carbon ratio for the MAC sample were used for the SAR determination.

2.2.8. Magnetic activated carbon platforms as methotrexate delivery systems

In order to determine the concentration of MTX after adsorption, a calibration set of absorbance versus concentration data was obtained by measuring the optical absorbance at 305 nm (maximum absorbance wavelength for MTX) using a BioSpectrometer kinetic UV/VIS spectrophotometer (Eppendorf AG, Germany) for the concentrations used in the range of 0.001-0.2 mM of MTX.

Drug release experiments were conducted using MTX-loaded MAC-PEI particles (1.5 mL suspensions containing 6 mg/mL of particles) under two different conditions: physiological (pH 7.4 phosphate buffer) and tumour-like (pH 5.8 phosphate buffer). To




this end, 1.3 mL of the medium was withdrawn at predetermined intervals for UV spectrophotometric analysis. An equal volume of the release medium, maintained under the same conditions, was added after sampling to maintain the final volume (sink conditions⁴¹), and the release process was continued. When necessary, the laser for photothermia and/or the RMF were applied while the release process was taking place.

2.2.9. Cell culture and cytotoxicity assay

Cells from the human fibroblast-derived, non-tumor epithelial cells and not commercial M1 cell line were cultured in DMEM pH 7.4, supplemented with 10% (v/v) FBS and antibiotic-antimycotic solution (0.2%) as previously described⁵¹. Cells were incubated at 37° C with 5% CO₂. Medium was changed every 48h, unless stated.

MAC-PEI particles potential cytotoxicity was determined by crystal violet, following a previously described protocol³³. M1 cells were grown in a 96-well plate (25.000 cells per well) at 37° C with 5% CO₂ during 24 h. Then, cells were exposed to a broad concentration range (0-1000 µg/ml) of previously UV-and ethanol sterilized MAC-PEI particles. After 24 h incubation, the medium was removed from each well by aspiration cells washed with sterile PBS and were fixed with glutaraldehyde (1%) for 15 min. Glutaraldehyde was then washed with PBS 4X. Excess of PBS was removed by plate decantation and crystal violet (0.1% v/v) was added, incubated for 20 min and repeatedly washed with deionized water until no colour was leaking from the plate. The plate was dried overnight, the remaining dye was solubilized with 10% acetic acid and loaded per triplicates in a new 96 well plate. Absorbance was measured in each well at 590 nm with a microplate reader spectrophotometer (INNO, LTeK, Korea).



Statistical analysis was carried out using one-way ANOVA followed by Bonferroni test to determine statistical significance ($p \leq 0.05$). All statistical analysis were performed using GraphPad Prism (version 10.1.2, La Jolla, CA, USA).

View Article Online
DOI: 10.1039/D4MA01037J

3. Results and discussion

3.1. Characterization

3.1.1. Particle geometry

Fe_3O_4 and MAC particle sizes determined by HRTEM were found to be (6.59 ± 0.22) nm (Figure 1a) and (230 ± 170) nm, respectively (Figure 2b,c). These average sizes were determined by measuring at least 20 particles in different pictures using JImage software. EDX mapping of Fe and C employing HAADF-STEM imaging demonstrated that the magnetite (represented by Fe element) is distributed over specific areas of the carbon surface (represented by C element) in the MAC particles (Figure 2d,e,f). The sizes obtained by DLS were also measured (Figure S1, Supplementary Information), obtaining (74 ± 28) nm for magnetite, (355 ± 74) nm for carbon, (390 ± 170) nm for MAC and (590 ± 120) nm for MAC-PEI⁵².




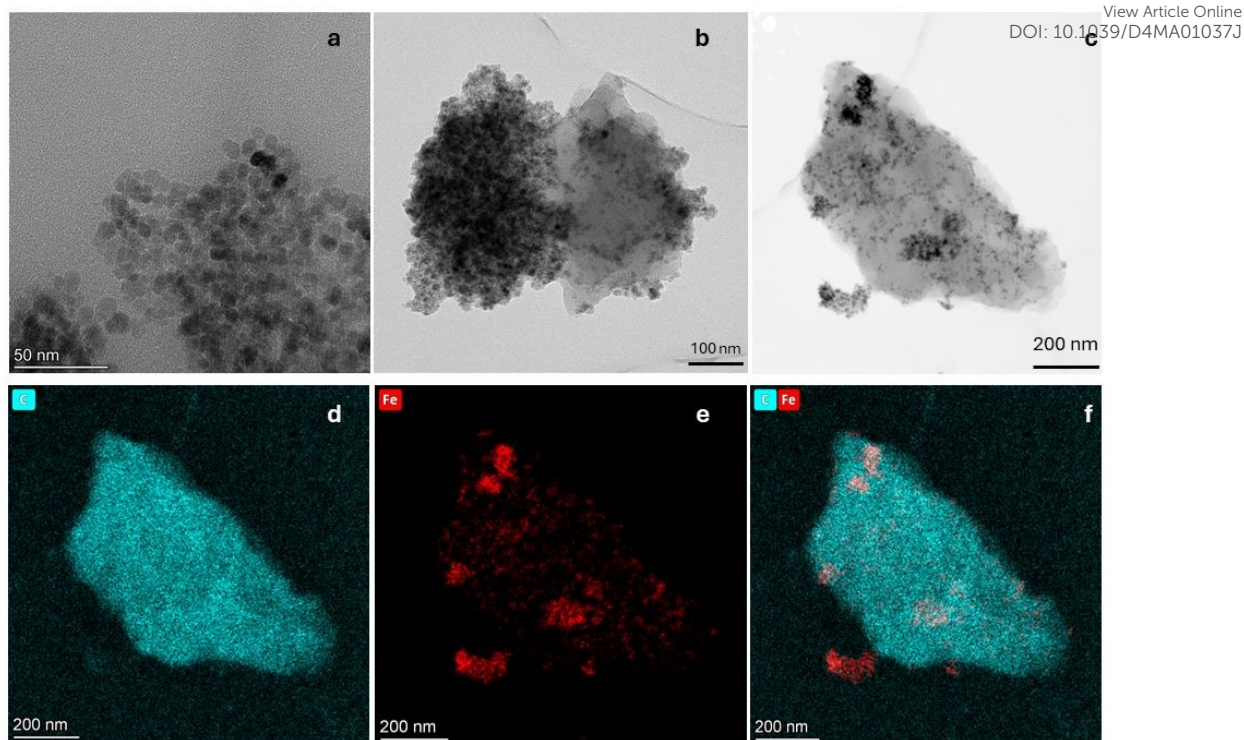


Fig. 2. HRTEM pictures of bare Fe_3O_4 and MAC platforms. (a) bare Fe_3O_4 ; (b and c) MAC; (d) EDX mapping analysis of C element of MAC particles; (e) EDX mapping analysis of Fe element of MAC particles; (f) EDX mapping analysis of overlapped C and Fe elements of magnetic carbon activated nanoplateforms.

3.1.2. Electrical surface characteristics

Electrophoretic mobility measurements of bare magnetite Fe_3O_4 , AC, MAC and MTX-loaded MAC in 1 mM KCl served as qualitative assessment of the surface changes during the preparation procedure steps (Figure 3). In accordance with previous studies, negative and neutral electrophoretic mobility was found for AC and bare Fe_3O_4 , respectively⁵³. When AC particles were decorated with Fe_3O_4 colloids following the coprecipitation method, the zeta potential values of the particles shifted from highly negative to moderate values, closer to those obtained for bare Fe_3O_4 . This could be explained by the coverage



of Fe_3O_4 onto AC surface, as demonstrated by EDX mapping analysis (Figure 2f). As expected, the PEI coating causes the mobility to move towards slightly more positive values, this being in fact a qualitative proof of the achieved coating⁴¹. Finally, MTX-loaded MAC particles depicted more moderately negative values than non-loaded ones⁵⁴. Potential conjugation between MAC and MTX through interaction of the MAC -COOH groups and MTX - NH_2 groups could explain that behavior, as it has been previously reported²⁰.


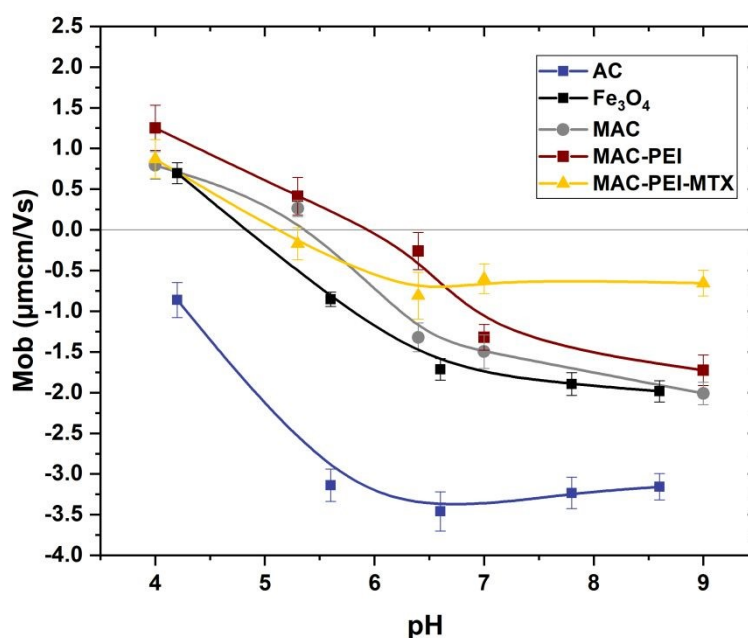


Fig. 3. Electrophoretic mobility measurements of bare Fe_3O_4 , AC, MAC and MTX-loaded MAC (1 mM KCl).

3.1.3. Infrared analysis

The MAC-PEI nanoporous particles were characterized by FTIR (Figure 4). The IR transmittance spectra matched well with the data already reported in the literature⁵⁵⁻⁵⁸. The following analysis focuses on the most significant peaks that enable the identification



of each material used. Symmetric and asymmetric C-H stretching vibrations of the fatty CH_2 on the PEI backbone signal were identified in the IR spectrum of MAC-PEI and PEI, at 2970 and 2894 cm^{-1} . Then, at 1635 cm^{-1} , the stretching vibration of C=O in the carboxyl group appeared for MAC and MAC-PEI. AC presence in MAC and MAC-PEI was also confirmed by the absorption peak located at 1020 cm^{-1} , as it is characteristic of some oxygen-containing functional groups. Because of that, this peak can also be observed in the Fe_3O_4 spectrum. PEI coating was again identified at 881 cm^{-1} , as an absorption peak appeared corresponding to the stretching vibration of the N-H bond in the PEI amine group. Finally, the absorption bands of the region around $\approx 550 \text{ cm}^{-1}$ are attributed to the stretching vibrations of metal oxide (Fe-O) bonds.

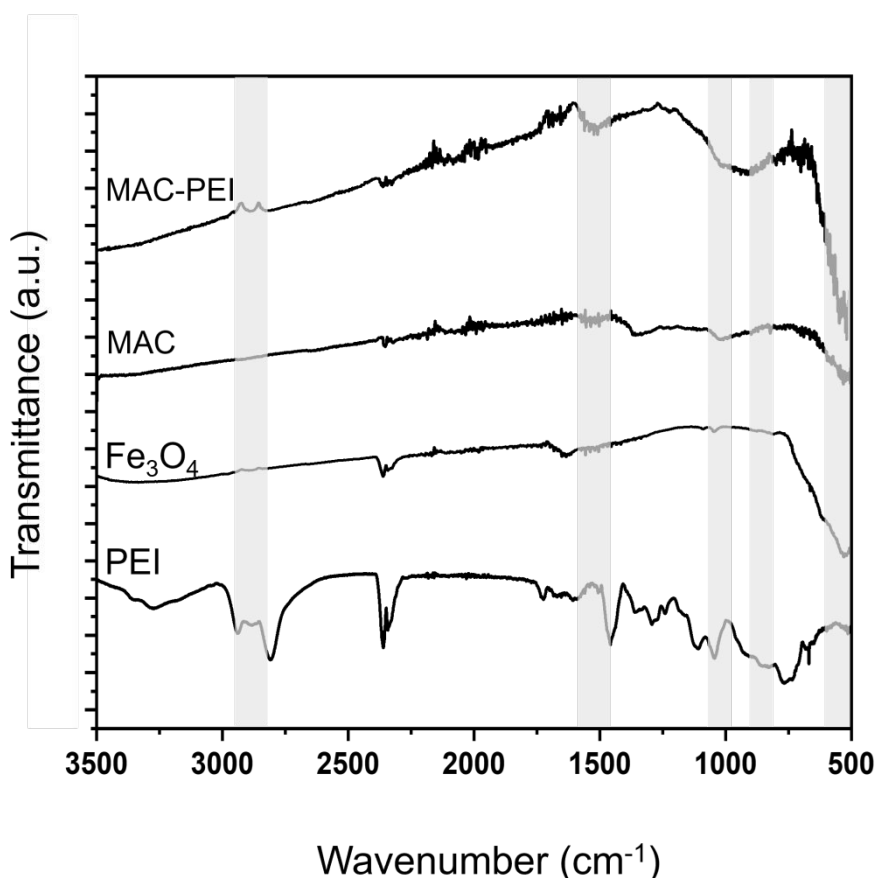


Fig. 4. FTIR analysis of the particles investigated.



3.2. Magnetic characterization

Magnetic characterization results of bare Fe₃O₄, MAC and PEI coated particles are depicted in Figure 5a. It can be observed that the magnetization of magnetite nanoparticles is 65 emu/g, somewhat lower than that of bulk magnetite and the value reported by other authors⁵⁹, probably due to a slight oxidation to maghemite, since the synthesis process is carried out in the presence of oxygen. The results obtained by the two methods are coherent, except for the range of magnetic field applied. In all cases, the increasing and decreasing field ramps are almost coincident, suggesting a superparamagnetic character of the magnetite NPs, a feature that is transferred to the magnetic carbon hybrid particles, as depicted in the low field detail of Figure 5b. The low magnetic hysteresis of the composites suggests a potential application of the MAC particles for biomedical purposes, given their moderate magnetization and their expectedly negligible risk of aggregation in blood vessels due to magnetic forces²⁹. This is also an indication of an efficient coating of the AC particles by magnetite, although the saturation magnetization of the former (6.0 ± 0.2 emu/g) is considerably lower due to the comparatively small mass of magnetic material.

In addition, the AC maximum magnetization of PEI-coated MAC particles was also determined, obtaining a very similar value (7.9 ± 0.3 emu/g), although slightly higher, probably due to the increased stability of the suspension (MAC particles tended to sediment quickly) (Figures 5a and 5b). This is because PEI is a sterically branched polymer with numerous amino groups, which are hydrophilic and capable of forming hydrogen bonds with water⁶⁰⁻⁶². This characteristic provides stability to the NPs in the dispersion medium, due to the strong electrostatic repulsion forces between them, thus preventing their aggregation. Note in Figure S1 the narrower size distribution of MAC-



PEI composites, as compared to bare activated carbon particles. The slightly increased average size of MAC-PEI suggests that the PEI layer is thin enough to provide stability and biocompatibility without significantly increasing the particle dimensions.

View Article Online
DOI: 10.1039/D4MA01037J

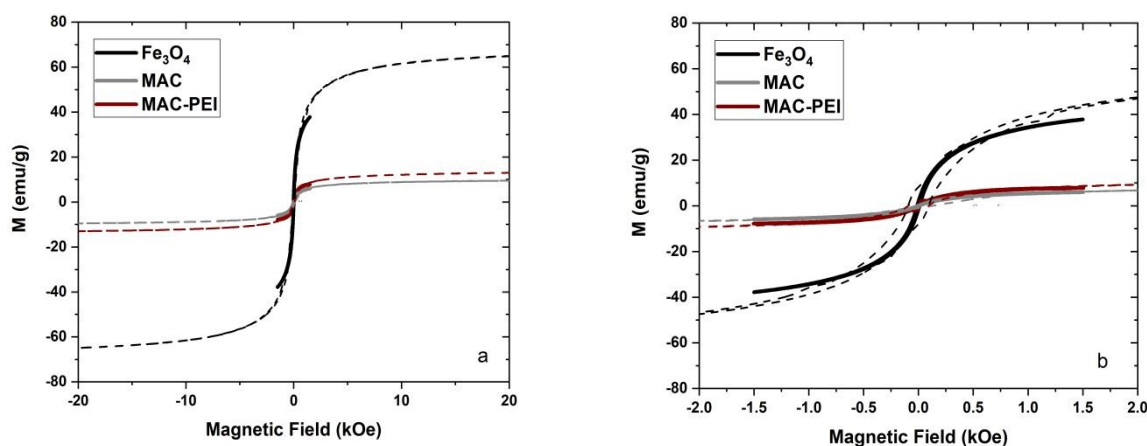


Fig. 5. Magnetic characterization of the obtained MAC nanoporous particles. (a) Magnetization curves of the bare Fe₃O₄, MAC and PEI coated particles using VSM (dotted lines) and AC magnetometry (solid lines); (b) Low-field detail of the plots in (a). Hysteresis cycles carried out at 300 K.

3.3. Photothermal response

Experimental conditions were carefully selected regarding clinical safety limits for photothermia. A wavelength in the first biological transparency window (NIR-I) was chosen, in addition to laser power densities within the range of acceptable values previously reported^{26, 63-65}. Therefore, our research was focused on evaluating the impact of heating induced by NPs at mild conditions where the impact of tissue damage caused solely by the laser power irradiation would be negligible.



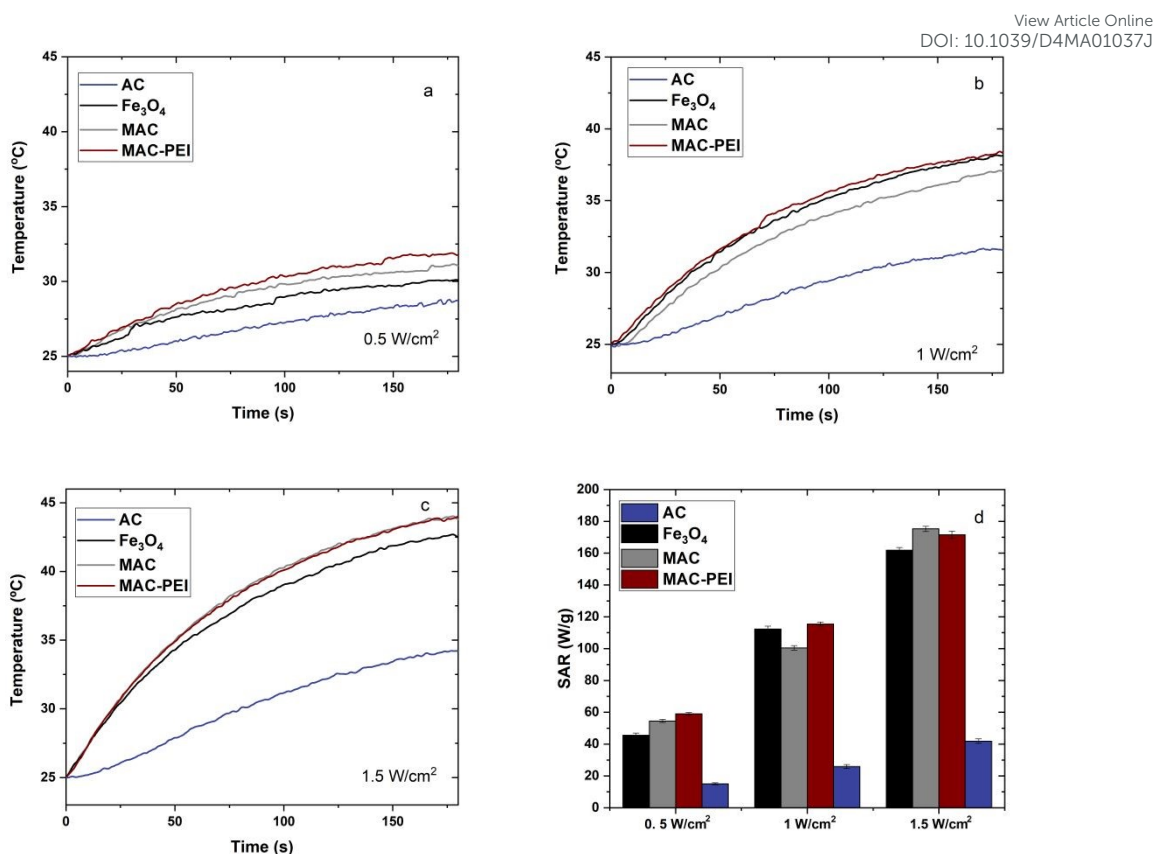


Fig. 6. Temperature increases for PTT therapy, at a power irradiation of 0.5 W/cm² (a), 1 W/cm² (b), and 1.5 W/cm² (c), using 100 μ L of sample at 5 mg/mL. Determination of the SAR obtained (d).

As can be seen in Figure 6a,b,c, magnetic NPs are an excellent heating agent in photothermal therapy, as has been demonstrated previously by several authors^{26, 66, 67}. Moreover, their magnetic properties allow them to be directed with an external field. In the case of activated carbon alone, the temperature rise and hence the SAR achieved is certainly lower, although considering its advantageous high surface area, AC particles cannot be neglected as tools in photothermia⁶⁸. What is particularly interesting is the PTT behavior of MAC particles. These retain the photothermal response of magnetite and, thanks to their content of AC, also have a high specific surface area. It is worth



mentioning that for bare Fe₃O₄, MAC and MAC-PEI samples, the results obtained are always very similar, MAC-PEI always presenting a slightly better performance. This demonstrates the advantage of the polymer coating, since the layer is thin enough not to affect the amount of magnetite or carbon present in the sample, but provides greater stability, resulting in better PTT results, as was also observed in the electrophoretic mobility (subsection 3.1.2), and in the magnetic characterization (section 3.2).

On the other hand, the SAR determination (Figure 6d), becomes another evidence of how the incorporation of magnetite is necessary to improve the photothermal response of activated carbon, as in most cases a higher SAR is obtained for magnetite/carbon composite particles than for magnetite alone. It should be mentioned that for the determination of the SAR of MAC and MAC-PEI samples it has been considered that approximately 86% of the sample is activated carbon, while 14% is magnetic material (as estimated from the saturation magnetizations in Figure 5a).

In addition to the characterization performed, it is important to consider that drug release experiments are carried out with a much larger sample volume, which can affect the heating produced. Therefore, a comparative test was performed using 1.5 mL of sample (Figure S2), in which it was observed that the temperature increase obtained is again sufficient to reach the hyperthermia region (between 42 and 46 °C) (Figure S2).

3.4. Cell viability of the magnetic activated carbon nanoporous particles

Cell viability experiments were performed to determine whether the MAC-PEI nanoporous particles obtained provided the necessary biocompatibility. For this purpose, human skin M1 fibroblasts were plated. After 24 h, cells were exposed to different concentrations (from 25 to 1000 µg/mL) of MAC-PEI particles. This evaluation of the potential cytotoxic effects of MAC-PEI was based on the quantification of viable cells by



crystal violet. Viable cells are stained with the dye, in contrast to non-viable ones. Increasing concentrations of MAC-PEI nanoporous particles did not significantly alter the viability of the fibroblasts in a broad range of concentrations (from 25 to 500 $\mu\text{g}/\text{mL}$; Figure 7). Only concentrations higher than 700 $\mu\text{g}/\text{mL}$ significantly reduced cell viability (29,76% compared to untreated control levels). Thus, we can conclude that MAC-PEI microporous particles at concentrations intended for biomedical applications exert negligible cytotoxic effects.

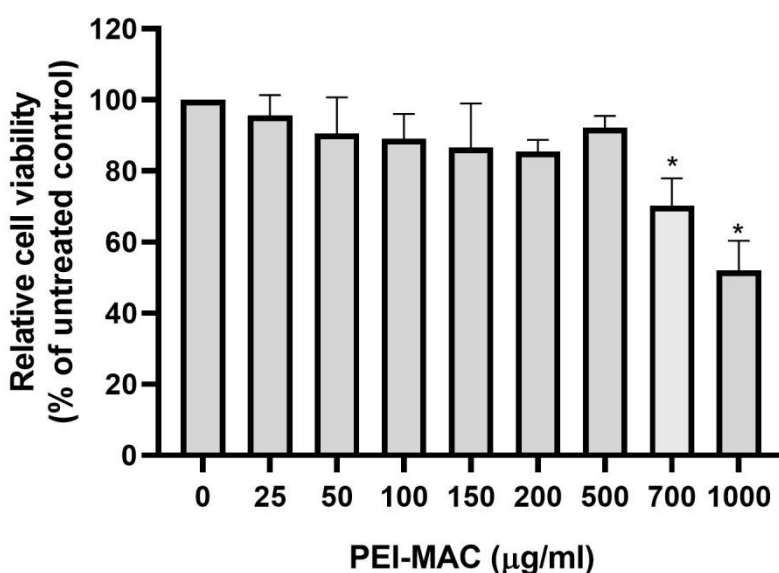


Fig. 7. Effects of MAC-PEI on M1 human skin fibroblasts viability. Cell was tested after 24 h exposure to MAC-PEI (0-1000 $\mu\text{g}/\text{ml}$). Data are shown as the mean \pm SEM of 3 independent experiments and expressed as a percentage of untreated control levels. Cytotoxicity assays were performed in triplicates per experimental condition. Statistical significance was established at p values below or equal to 0.05 (*).



3.5. Methotrexate vehiculation and controlled drug release. Effect of external stimuli

View Article Online

DOI: 10.1039/D4MA01037J

As mentioned above, a calibration was first performed to determine the concentration of adsorbed and released MTX (data in Figure S3). In addition, adsorption kinetics tests (solutions 0.6 mM MTX, particle concentration 6 mg/mL) were performed in the range of 1, 2, 24, 72, 144 h, showing that adsorption in the first two hours exceeded 80% (Figure S4). For the sake of comparison, experiments were also performed on MAC particles without PEI coating, and it was found that 76 % MTX was adsorbed in the same conditions. This suggests that the high porosity of the MAC particles is largely responsible for the total adsorption found. Further evidence of this high MTX loading is provided by drug adsorption tests (up to 10 mM) in which the MAC-PEI sample adsorbed almost all the drug brought into contact with the particles (Figure S5).

As can be seen in Figure 8, drug release at pH 5.8, which mimics the tumor environment, is significantly enhanced by the application of external stimuli such as photothermia and rotating fields. Drug release induced by laser irradiation on magnetic particles has been described by other authors with different drugs such as AS-48⁶⁹ or doxorubicin⁷⁰. In the latter study, mesoporous silica particles with a magnetic core loaded between 20% and 40% of the drug, which allows us to conclude that: (1) MAC particles are a more effective alternative for drug loading than conventional magnetic particles and even mesoporous silica with a magnetic core, since they load almost all the drug available in the solution due to their high specific surface area, and (2) although the release may seem low (around 4%), the large amount of drug adsorbed in absolute terms is sufficient to optimise future anti-tumour treatments compared to other studies such as the one mentioned above or to our previous work with doxorubicin and PEI-coated magnetite particles (5 $\mu\text{mol/g}$ drug release in the best conditions³³).



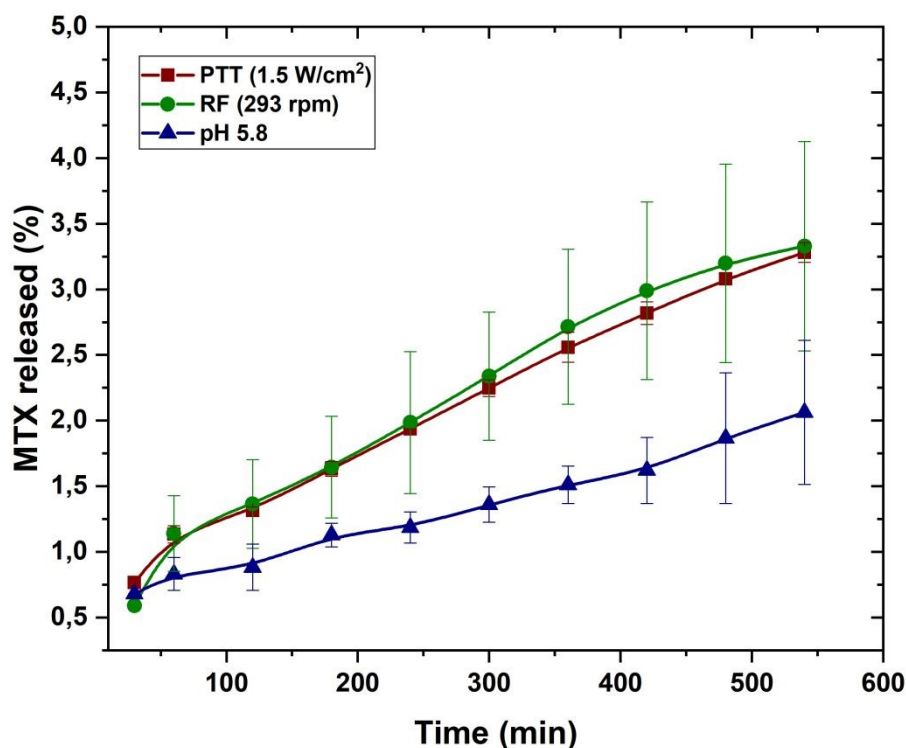


Fig. 8. Release of MTX with respect to the amount previously adsorbed on PEI-coated MAC particles using different stimuli: photothermal therapy (PTT), rotating fields (RF), and with no stimuli applied, all of them in phosphate buffer at pH 5.8.

Figure 8 also shows that drug release using rotating fields slightly improves release performance, probably due to mechanically enhanced diffusion. In general, the release achieved under either PTT or MRF is significantly higher compared to our results under non stimulated conditions. The latter were also investigated at pH 7.4, as depicted in Figure S6: although at this pH the drug tends to be released more rapidly initially, this is not of great significance, as the time that the particles typically would employ to reach the target organ would be much shorter (blood completes a full circulation through the




vascular system within minutes), and so no significant release would have occurred during the transit. In fact, the drug administration times are much longer, and hence the period of interest for observation would be in the range of hours. In this case, the drug release under stimuli (with particles already at the acidic tumor pH) is larger than without rotating magnetic field or photothermia (Figure 8). Similar results have been reported by Nappini et al.⁷¹, who observed that magnetoliposomes loaded with carboxyfluorescein experienced a significantly enhanced release of the fluorescent agent under the influence of a low-frequency alternating magnetic field (5.8 kHz). This is a very interesting result, as this technique has been less studied and could be more effective than photothermia for biomedical applications requiring high tissue penetration.

View Article Online
DOI: 10.1039/D4MA01037J

4. Conclusions

This work describes the utilisation of porous activated carbon particles as vehicles for the anti-tumour drug MTX. The particles are coated with magnetite nanoparticles, which confer them superparamagnetic behaviour, thus extending the field of application to situations where it is possible to use external magnetic fields to transport the particles to their action site or eventually produce heating if the field is alternating, or torque if the magnetic field is rotating. To enhance the stability of the particles and their interaction with the anti-tumour agent, a cationic polymer, low molecular weight PEI, is employed for their coating. The MAC-PEI particles demonstrate high biocompatibility at concentrations suitable for biomedical applications, and exhibit a photothermal response to infrared laser irradiation, whereby local heating is generated. This phenomenon is exploited in this research as a stimulus to enhance MTX release. The photothermal response is markedly elevated for the activated carbon-magnetite (MAC) composites, and




it is little affected by the application of the polymer coating. The synthesised MAC-PEI composite particles demonstrated the capacity to adsorb up to 80% of the drug from a 0.6 mM MTX solution after 20 hours of contact. The drug release was conducted at pH 5.8 with and without the application of external photothermal and rotating magnetic field stimuli. The process is gradual and can be controlled using stimuli of different intensity, resulting in a considerable increase in the amount of drug released. The designed porous particles thus appear to be excellent smart platforms for the transport and release of MTX, as they can load significant quantities of drug and releasing it gradually at a rate that can be controlled by both PTT and RMF external stimuli, while preserving biocompatibility.

Acknowledgements

Financial support of this investigation by the grant TED2021-131855BI00/AEI/10.13039/501100011033/Unión Europea Next Generation EU/PRTR and PID2023-151881OB-I00 MICIU/ AEI/10.13039/501100011033/ and FEDER, EU is gratefully acknowledged. We also thank Juan M. Falcón-Perez (Metabolomics Unit, Centro de Investigación Cooperativa en Biociencias, Derio, Vizcaya, Spain) for providing M1 human fibroblasts, and Pedro Urquiza (Torrecárdenas University Hospital, Biomedical Research Unit-Biotechnology Laboratory, Almería, Spain) for his technical assistance with them. TR is the recipient of a Ramón y Cajal RYC2022-035807.

Conflicts of interest

The authors declare that they have no competing interests. The funders had no role in the design of the study; in the collection, analysis, or interpretation of data; in the writing of the manuscript, or in the decision to publish the results.



References

1. E. Laconi, F. Marongiu and J. DeGregori, *Brit. J. Cancer*, 2020, **122**, 943-952.
2. S. Pilleron, E. Soto-Perez-de-Celis, J. Vignat, J. Ferlay, I. Soerjomataram, F. Bray and D. Sarfati, *Int. J. Cancer*, 2021, **148**, 601-608.
3. F. Fernández-Alvarez, C. Caro, G. García-García, M. L. García-Martín and J. L. Arias, *J. Mater. Chem. B*, 2021, **9**, 4963-4980.
4. F. Fernandez-Alvarez, G. García-García and J. L. Arias, *Pharmaceutics*, 2021, **13**, 1232.
5. P. T. Ribeiro, J. A. Moreira, J. F. Monterio and S. M. Laranjeira, *J. Control. Rel.*, 2022, **347**, 89-103.
6. K. Loomis, K. McNeeley and R. V. Bellamkonda, *Soft Matter*, 2011, **7**, 839-856.
7. K. Y. Choi, G. Liu, S. Lee and X. Chen, *Nanoscale*, 2012, **4**, 330-342.
8. M. E. Davis, *MRS Bull.*, 2012, **37**, 828-835.
9. R. Wang, P. S. Billone and W. M. Mullett, *J. Nanomater.*, 2013, **2013**, 629681.
10. L. N. Toksvang, S. H. R. Lee, J. J. Yang and K. Schmiegelow, *Leukemia*, 2022, **36**, 1749-1758.
11. B. Zhang, Y. Zhang, R. Z. Li, J. Z. Li and X. C. Lu, *J. Orthop. Surg. Res.*, 2020, **15**, 5101-5128.
12. J. May, K. R. Carson, S. Butler, W. J. Liu, N. L. Bartlett and N. D. Wagner-Johnston, *Leukemia & Lymphoma*, 2014, **55**, 1345-1349.
13. H. Shariatifar, F. Ranjbarian, F. Hajiahmadi and A. Farasat, *Mol. Biol. Rep.*, 2022, **49**, 11049-11060.
14. L. B. Ramsey, F. M. Balis, M. M. O'Brien, K. Schmiegelow, J. L. Pauley, A. Bleyer, B. C. Widemann, D. Askenazi, S. Bergeron, A. Shirali, S. Schwartz, A. A. Vinks and J. Heldrup, *Oncologist*, 2018, **23**, 52-61.
15. Y. Y. Yang, C. Y. Wang, Y. T. Chen, X. B. Wang, Z. Jiao and Z. Wang, *Eur. J. Pharm. Sci.*, 2023, **186**.
16. D. Banerjee, P. Mayer-Kuckuk, G. Capiiaux, T. Budak-Alpdogan, R. Gorlick and J. R. Bertino, *Biochim. Biophys. Acta, Mol. Basis Dis.*, 2002, **1587**, 164-173.
17. Z. A. Khan, R. Tripathi and B. Mishra, *Expert Opin. Drug Delivery*, 2012, **9**, 151-169.
18. G. Choi, T. H. Kim, J. M. Oh and J. H. Choy, *Coordin. Chem. Rev.*, 2018, **359**, 32-51.
19. M. Thangavelu, A. Adithan, S. T. Parvathaleswara and C. Munusamy, *Pharm. Res.*, 2018, **35**, 184.
20. T. H. Hsin, N. Dhenadhayalan and K. C. Lin, *ACS Appl. Biomater.*, 2020, **3**, 8786-8794.
21. F. Guo, X. Mao, J. Wang, F. Luo and Z. Wang, *J. Int. Med. Res.*, 2011, **39**, 2217-2227.
22. N. Miriyala, D. F. Ouyang, Y. Perrie, D. Lowry and D. J. Kirby, *Eur. J. Pharm. Biopharm.*, 2017, **115**, 197-205.




23. K. R. Olson, *J. Med. Toxicol.*, 2010, **6**, 190-198.
24. S. K. Shahcheragh, M. M. B. Mohagheghi and A. Shirpay, *Sn Appl. Sci.*, 2023, **5**.
25. X. Y. Li, Y. Shimizu, A. Pyatenko, H. Q. Wang and N. Koshizaki, *J. Mater. Chem.*, 2011, **21**, 14406-14409.
26. A. Espinosa, J. Kolosnjaj-Tabi, A. Abou-Hassan, A. P. Sangnier, A. Curcio, A. K. A. Silva, R. Di Corato, S. Neveu, T. Pellegrino, L. M. Liz-Marzan and C. Wilhelm, *Adv. Funct. Mater.*, 2018, **28**.
27. H. Belkahla, R. Boudjemaa, V. Caorsi, D. Pineau, A. Curcio, J. S. Lomas, P. Decors, A. Chevillot-Biraud, T. Azais, C. Wilhelm, H. Randriamahazaka and M. Hemadi, *Nanoscale Adv.*, 2019, **1**, 2571-2579.
28. X. S. Li, J. F. Lovell, J. Yoon and X. Y. Chen, *Nature Rev. Clin. Oncol.*, 2020, **17**, 657-674.
29. L. H. Reddy, J. L. Arias, J. Nicolas and P. Couvreur, *Chem. Rev.*, 2012, **112**, 5818-5878.
30. T. J. Yu, P. H. Li, T. W. Tseng and Y. C. Chen, *Nanomedicine*, 2011, **6**, 1353-1363.
31. M. Y. Liao, P. S. Lai, H. P. Yu, H. P. Lin and C. C. Huang, *Chem. Comm.*, 2012, **48**, 5319-5321.
32. M. Q. Chu, Y. X. Shao, J. L. Peng, X. Y. Dai, H. K. Li, Q. S. Wu and D. L. Shi, *Biomaterials*, 2013, **34**, 4078-4088.
33. M. Lazaro, P. Lupianez, J. L. Arias, M. P. Carrasco-Jimenez, A. V. Delgado and G. R. Iglesias, *Polymers*, 2022, **14**, 4913.
34. X. Hua, Q. Yang, Z. Dong, J. Zhang, W. Zhang, Q. Wang, S. Tan and H. Smyth, *Drug Delivery*, 2017, **24**, 511-518.
35. T. Marín, P. Montoya, O. Arnache, R. Pinal and J. Calderón, *Materials and Design*, 2018, **152**, 78-87.
36. S. Cho, N. Min, W. Park, S. Kim and D. Kim, *Adv. Funct. Mater.*, 2019, **29**, 1901384.
37. Y. Cheng, M. Muroski, D. Petit, R. Mansell, T. Vemulkar, R. Morshed, Y. Han, I. Balyasnikova, C. Horbinski, X. Huang, L. Zhang, R. Cowburn and M. Lesniak, *J. Control. Rel.*, 2016, **223**, 75-84.
38. J. Zhao, C. Lu, X. He, X. Zhang, W. Zhang and X. Zhang, *ACS Appl. Mater. & Interf.*, 2015, **7**, 2607-2615.
39. X. Sun, C. Cai, Q. Wang, D. Cai, J. Qian, Y. Chi, K. Zheng, X. Zhang, G. Zhang, K. Zhong and Z. Wu, *Phys. Chem. Chem. Phys.*, 2016, **18**, 7820-7828.
40. M. Lázaro, A. Sola-Leyva, M. Jimenez-Carretero, M. Jiménez, A. Delgado and G. Iglesias, *J. Drug Deliv. Sci. Technol.*, 2024, **95**, 105622.
41. M. D. Ramos-Tejada, J. L. Viota, K. Rudzka and A. V. Delgado, *Coll. Surf. B Biointerf.*, 2015, **128**, 1-7.
42. B. Chertok, A. David and V. Yang, *Biomaterials*, 2010, **31**, 6317-6324.
43. E. dos-Santos-Silva, M. Alves-Silva, J. de Medeiros, R. dos Santos-Cavalcante, A. Cornélio, M. Fernandes-Pedrosa, E. do Egito, R. de Araujo and A. da Silva, *J. Mol. Liq.*, 2020, **315**, 113721.

View Article Online
DOI: 10.1039/D4MA01037J



44. R. Goyal, S. K. Tripathi, E. Vazquez, P. Kumar and K. C. Gupta, *Biomacromolecules*, 2012, **13**, 73-83. New Article Online
DOI: 10.1039/D4MA01037J
45. M. Ramos-Tejada, J. Viota, K. Rudzka and A. Delgado, *Coll. Surf. B Biointerf.*, 2015, **128**, 1-7.
46. A. Alexander, A. Pillai, V. Manikantan, G. Varalakshmi, B. Akash and I. Enoch, *Materials Letters*, 2022, **313**.
47. A. Balan, M. M. R. Kennedy, V. Manikantan, A. Alexander, G. S. Varalakshmi, S. Ramasamy, A. S. Pillai and I. V. M. V. Enoch, *Bulletin of Materials Science*, 2024, **47**, 28.
48. M. Williams, S. Grace, V. Manikantan, A. Alexander, G. Varalakshmi, S. Ramasamy, A. Pillai, I. Enoch and D. Núñez, *Materials Letters*, 2024, **355**.
49. Z. Nazarkina, T. Savostyanova, B. Chelobanov, I. Romanova, P. Simonov, R. Kvon, A. Karpenko and P. Laktionov, *Pharmaceutics*, 2022, **14**, 6713.
50. B. Sanz, M. P. Calatayud, N. Cassinelli, M. R. Ibarra and G. F. Goya, *Eur. J. Inorg. Chem.*, 2015, **2015**, 4524-4531.
51. P. Urquiza, A. Laín, A. Sanz-Parra, J. Moreno, G. Bernardo-Seisdedos, P. Dubus, E. González, V. Gutiérrez-de-Juan, S. García, H. Eraña, I. Juan, I. Macías, F. Ben Bdira, P. Pluta, G. Ortega, J. Oyarzábal, R. González-Muñiz, J. Rodríguez-Cuesta, J. Anguita, E. Díez, J. Blouin, H. de Verneuil, J. Mato, E. Richard, J. Falcón-Pérez, J. Castilla and O. Millet, *Sci. Translat. Med.*, 2018, **10**, eaat7467.
52. S. Bhattacharjee, *J. Control. Rel.*, 2016, **235**, 337-351.
53. G. García-García, M. Lázaro-Callejón, F. Fernández-Alvarez, G. R. Iglesias and J. L. Arias, *J. Magn. Magn. Mater.*, 2023, **588**, 171500.
54. F. Ahmadijokani, S. Tajahmadi, M. Rezakazemi, A. Sehat, H. Molavi, T. Aminabhavi and M. Arjmand, *J. Environ. Manag.*, 2021, **277**, 111448.
55. H. Javadian, F. Ghorbani, H. Tayebi and S. Asl, *Arab. J. Chem.*, 2015, **8**, 837-849.
56. G. García-García, F. Fernández-Alvarez, L. Cabeza, A. Delgado, C. Melguizo, J. Prados and J. Arias, *Polymers*, 2020, **12**, 2790.
57. T. Maneerung, J. Liew, Y. Dai, S. Kawi, C. Chong and C. Wang, *Biores. Technol.*, 2016, **200**, 350-359.
58. S. Sambaza, M. Masheane, S. Malinga, E. Nxumalo and S. Mhlanga, *Phys. Chem. of Earth*, 2017, **100**, 236-246.
59. S. Kemp, R. Ferguson, A. Khandhar and K. Krishnan, *RSC Adv.*, 2016, **6**, 77452-77464.
60. N. Bayliss and B. Schmidt, *Progr. Polym. Sci.*, 2023, **147**, 101753.
61. J. Akoto, F. Chai, E. Repo, Z. Yang, D. Wang, F. Zhao, Q. Liao and L. Chai, *J. Environ. Chem. Eng.*, 2022, **10**, 108589.
62. R. Megias, M. Arco, J. Ciriza, L. del Burgo, G. Puras, M. López-Viota, A. Delgado, J. Dobson, J. Arias and J. Pedraz, *Int. J. Pharm.*, 2017, **518**, 270-280.
63. A. Bucharskaya, G. Maslyakova, G. Terentyuk, A. Yakunin, Y. Avetisyan, O. Bibikova, E. Tuchina, B. Khlebtsov, N. Khlebtsov and V. Tuchin, *Int. J. Mol. Sci.*, 2016, **17**, 1295.



64. S. Jacques, *Surgical Clinics of North America*, 1992, **72**, 531-558. View Article Online
DOI: 10.1039/D4MA01037J
65. A. Gobin, M. Lee, N. Halas, W. James, R. Drezek and J. West, *Nanolett.*, 2007, **7**, 1929-1934.
66. S. Cabana, A. Curcio, A. Michel, C. Wilhelm and A. Abou-Hassan, *Nanomaterials*, 2020, **10**, 1548.
67. A. Wlodarczyk, S. Gorgon, A. Radon and K. Bajdak-Rusinek, *Nanomaterials*, 2022, **12**, 1807.
68. M. Chu, J. Peng, J. Zhao, S. Liang, Y. Shao and Q. Wu, *Biomaterials*, 2013, **34**, 1820-1832.
69. S. C. Gaglio, Y. Jabalera, M. Montalban-Lopez, A. C. Millan-Placer, M. Lazaro-Callejon, M. Maqueda, M. P. Carrasco-Jimenez, A. Laso, J. A. Ainsa, G. R. Iglesias, M. Perduca and C. J. Lopez, *Pharmaceutics*, 2022, **14**, 2744.
70. A. Adam, S. Harlepp, F. Ghilini, G. Cotin, B. Freis, J. Goetz, S. Bégin, M. Tasso and D. Mertz, *Coll. Surf. A Physicochem. Eng. Asp.*, 2022, **640**, 128407.
71. S. Nappini, F. Bombelli, M. Bonini, B. Nordèn and P. Baglioni, *Soft Matter*, 2010, **6**, 154-162.



Data availability

View Article Online
DOI: 10.1039/D4MA01037J

The data used to support the finding of this study are included within the article and SI.

