

Soft Matter

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: S. Lin, C. Ye, C. Wei, J. Liu, T. H. Wong, X. Liu, Z. Song, C. Wu and Z. Li, *Soft Matter*, 2025, DOI: 10.1039/D4SM01522C.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

ARTICLE

Mechano-diffusion of Particles in Stretchable HydrogelsChuwei Ye^{a†}, Congjie Wei^{b†}, Jiabin Liu^{a†}, Tsz Hung Wong^{a†}, Xinyue Liu^c, Ziyou Song^d, Chenglin Wu^{b*}, Zhaojian Li^{a*}, Shaoting Lin^{a*}Received 00th January 20xx,
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

Precise control over particle diffusion is promising for diverse modern technologies. Traditionally, particle diffusion is governed by the inherent properties of liquid medium, limiting versatility and controllability. Here, we report a mechano-diffusion mechanism that harnesses mechanical deformation to control particle diffusion in stretchable hydrogels with a significantly enlarged tuning ratio and highly expanded tuning freedom. The working principle is to leverage the mechanical deformation of stretchable hydrogels for modulating the polymer network's geometric transformation and the polymer chain's energy, which synergistically tunes the energy barrier for particle diffusion. Using a model particle-hydrogel material system and a customized mechano-diffusion characterization platform, we demonstrate that tension loads can enhance the diffusivity of gold nanoparticles up to 22 times, far exceeding that in traditional liquid medium and by external fields. Additionally, we show particle diffusion in hydrogels can be manipulated spatiotemporally by controlling the hydrogels' stress state and loading rate. To further push the limit of the mechano-diffusion, we use experiment, theory, and simulation to explore particle diffusion in biaxially stretched hydrogels, simultaneously expanding the mesh size and reducing the energy barrier. The enlarged tuning ratio and expanded tuning freedom enable a model-guided drug delivery system for pressure-controlled release of drug molecules. Understanding this spatiotemporal mechano-diffusion mechanism will provide insights pertinent to a broad range of biological and synthetic soft materials.

1. Introduction

The movement of particles such as biomacromolecules, gold nanoparticles, and quantum dots from one location to another, broadly impacts many fundamental processes in life science and physical systems. On one hand, particle diffusion plays a critical role in maintaining the function and survival of living organisms with examples such as intracellular transport^{1, 2}, mucus clearance³, and cytoplasmic streaming^{4, 5}. On the other hand, technologies that facilitate nanoparticle diffusion with high efficiency, specificity, and tunability have shown promising applications in drug delivery^{6, 7}, water treatment^{8, 9}, and in-situ biosensing^{10, 11}.

The diffusion of particles is typically characterized by their diffusivity (D), which describes the rate of particles moving from

high-concentration regions to low-concentration regions within a liquid medium. Traditionally, the particle diffusivity is governed by the liquid medium's viscosity and temperature, following the Stokes-Einstein equation^{12, 13}. However, controlling particle diffusion in liquid media presents two main challenges. First, the temperature variation for a specific liquid medium is often narrow¹⁴, limiting the range of achievable particle diffusivities. For example, in aqueous solutions of biomedical or environmental applications, the temperature range of 273 to 373 K results in only a 2.4-fold difference in diffusivity¹⁵. Second, the spatially uniform viscosity and temperature across the liquid medium do not allow for precise manipulation of specific diffusion directions or complex diffusion patterns.

In contrast, solid materials such as polymers, elastomers, and hydrogels can sustain mechanical stress without flowing, allowing them to be deformed under mechanical load. Hydrogels, as polymer networks infiltrated with a large quantity of water molecules, are particularly effective for transporting particles in aqueous environments^{16–17, 18–20}. Different from the diffusion of particles in liquid medium, the diffusion of particles in hydrogels is dominated by the confinement from polymer networks^{19–21}. Applying mechanical deformation to hydrogels offers unique capabilities for modulating particle diffusion, surpassing the limitation of liquid medium. These capabilities include a broader spectrum of diffusivities, directional movement of particles, and triggered release of particles in response to mechanical cues. In particular, recent

^a Department of Mechanical Engineering, Michigan State University, East Lansing, MI, USA

^b Department of Civil and Environmental Engineering, Texas A&M University, College Station, TX, USA

^c Department of Chemical Engineering and Material Science, Michigan State University, East Lansing, MI, USA

^d Department of Mechanical Engineering, National University of Singapore, Singapore

† These authors contribute equally to this work: Chuwei Ye, Congjie Wei, Jiabin Liu, Tsz Hung Wong.

* Corresponding authors. Email: chenglinwu@tamu.edu, lizhaoj1@msu.edu, linshaot@msu.edu

Supplementary Information available: [details of any supplementary information available should be included here]. See DOI: 10.1039/x0xx00000x



developments of tough^{22, 23} and fatigue-resistant²⁴⁻²⁶ hydrogels enable the potential to further push the limit of particle diffusion tuning by leveraging their superior mechanical properties. The ability to apply mechanical deformation to these hydrogels with varying magnitude, direction, and timing provides vast possibilities for engineering particle diffusion. Despite this promise, the effects of mechanical deformation on particle diffusion in hydrogels remain largely unexplored. The existing understanding of strain-dependent diffusivity in hydrogels is mainly attributed to strain-induced geometrical transformation^{27, 28} such as the size of polymer meshes^{19, 20}, the connectivity of pores, and the tortuosity of diffusion pathways. In this work, we report a mechano-diffusion mechanism that harnesses mechanical deformation to control particle diffusion in stretchable hydrogels via the synergy of geometrical transformation and energy modulation, achieving a significantly enlarged tuning ratio and highly expanded tuning freedom. Using a model particle-hydrogel material system and a customized mechano-diffusion characterization platform, we systematically investigate the diffusion of gold nanoparticles (AuNPs) of various sizes in hydrogels under controlled stress states and loading rates. Our experiments demonstrate that tension loads can enhance AuNP diffusivity by up to 22 times, far surpassing that in traditional liquid medium (e.g., 2.43 times in water, 1.34 times in diluted polymer solution, 1.21 times in concentrated polymer solution) and by external fields (e.g., 3.86 times for light, 0.99 times for magnetic field, 1.15 times for electrical field). Intriguingly, torsion loads slightly suppress AuNP diffusivity by 33%. We also observe that increasing the loading rate from 0 to 4.8 s⁻¹ reduces AuNP diffusivity by approximately 50%. To further push the limit of mechano-diffusion, we combine our mechano-transport theory with coarse-grained simulations to study particle diffusion in biaxially stretched polymer networks, which simultaneously expand the mesh size and reduce the energy barrier. This dual effect amplifies particle diffusivity by approximately 50 times due to the synergy of the polymer network's geometric transformation and the polymer chain's energy modulation. This work not only provides fundamental insights into the mechano-diffusion mechanism pertinent to a broad range of biological and synthetic soft materials, but also lays a theoretical foundation for developing previously inaccessible transport-based technologies.

2. Materials and Methods

2.1. Synthesis of hydrogels

A 50 mL hydrogel precursor solution was prepared by mixing a 4 M lithium chloride (LiCl) aqueous solution, 3.5 g of Acrylamide (AAM), 30 mg of *N,N'*-Methylenebis(acrylamide) (MBAA), 500 μL of a 10 wt.% Ammonium persulfate (APS) aqueous solution, and 50 μL of *N,N,N',N'*-Tetramethylethylenediamine (TEMED) using a centrifugal mixer (Kr-100, THINKY). The introduction of the LiCl salt served the purpose of preventing significant dehydration during prolonged diffusion experiments. The hydrogel was cast in a mold measuring 20 mm × 20 mm × 20 mm (length × width × height). To create a reservoir of the AuNPs

solution at the top center of the hydrogel, an acrylic cuboid measuring 3 mm × 3 mm × 8 mm (length × width × height) was affixed to the acrylic lid. The acrylic molds were cut using a laser cutter (Epilog Laser) and assembled using superglue (Krazy). The hydrogel precursor solution was then poured into the mold with the cuboid securely positioning at the top. The assembly was subsequently placed in an oven (CL-1000 Ultraviolet Crosslinker) and cured at 60 °C for 2 hours. Afterward, the hydrogel sample was gently released from the mold, and the concentrated AuNPs were injected into the central reservoir for further measurement and analysis.

2.2. Synthesis of functionalized AuNPs

To synthesize AuNPs with precise control over their core and hydrodynamic diameters, we followed a modified protocol^{27, 29}. Specifically, a mixture of 20 mL deionized (DI) water, 0.25 mM HAuCl₄, and 0.25 mM tri-sodium citrate were stirred magnetically at 650 rpm for 15 minutes. Concurrently, we added 600 μL of ice-cold 0.1 M NaBH₄ solution into the mixture, which instantly transformed the initially colorless solution into a vivid red hue. The mixture was left undisturbed for 1 hour to allow the solution to reach reaction³⁰. To enhance the compatibility between the hydrophobic AuNPs and the hydrophilic hydrogel, the AuNPs' surfaces were functionalized with thiol-terminated PEG chains. Specifically, 50 mg of MPEG1000-SH was dissolved in 500 μL of DI water and then added dropwise to the 20 mL AuNPs solution while stirring at 650 rpm, resulting in a solution with deeper color. Subsequently, the mixture was stirred for 1 hour to ensure a thorough ligand exchange. The solution was then allowed to stand for 1 hour to stabilize. Afterward, 4 mL of the solution was transferred to a centrifugal filter and centrifuged at 4000 rpm for 10 minutes to eliminate any residual reagents. This centrifugation process was repeated three times, each time with the addition of 4 mL of DI water. After the final centrifugation, the concentrated AuNPs solution exhibited a dark purple color³¹.

2.3. Structural characterization of AuNPs

The core diameter and hydrodynamic diameter of the AuNPs were characterized by transmission electron microscopy (TEM) imaging and dynamic light scattering (DLS), respectively. Specifically, the TEM imaging was carried out using the JEOL 1400 Flash TEM equipment with a maximum accelerating voltage of 120 kV and a lattice resolution of 0.2 nm; and the DLS was performed using the Malvern Zetasizer Nano-ZS equipment. Given the measured distributions of AuNPs' core diameter and hydrodynamic diameter, we can identify the mean values of core diameter and hydrodynamic diameter of the two kinds of AuNPs as $d_c = 6$ nm and 18 nm and $d_h = 12$ nm and 28 nm, respectively.

2.4. Mechano-transport characterization platform.

The platform can be divided into the mechanical loading module, the force/torque measurement module, and the imaging module. In the mechanical loading module, a two-phase stepper motor drives a 1604-type ball screw with a linear guide to achieve static or dynamic uniaxial stretching of the hydrogel samples. Additionally, another two-phase stepper motor is used to apply torsion loads to the hydrogel samples. An Arduino UNO microcontroller controls the movement of this



module. The force/torque measurement module integrates a force sensor with a 9.8 N measurement range and a 1.9 mV/V sensitivity, as well as a torque sensor with a 0.3 Nm measurement range and a 0.6 mV/V sensitivity. Since the sensor outputs are at millivolt levels, an amplification circuit based on an INA128P instrumental amplifier amplifies the signals to volt levels. These measured forces and torques are then calculated and recorded on a computer via an NI USB 6008 data acquisition board and LabVIEW software. In the imaging module, a high-resolution camera with a maximum resolution of 3264×2448 pixels and a video capture capability of 15 frames per second captures images. This setup depicts the diffusion profiles of the AuNPs in the hydrogel. During experiments, the camera's spatial resolution is approximately 0.015 mm/pixel, which is sufficient for determining diffusivity, as the diffusion profiles are at the millimeter scale.

2.5. Coarse-grained molecular dynamics simulation.

The coarse-grained (CG) molecular dynamics (MD) modeling is based on the molecular dynamic simulation software package LAMMPS. A 3D crosslinked network is constructed with 3546 sphere monomers that are modeled with CG beads. To model the influence of the solutions on the diffusion mechanism, solution CG beads are also constructed with an initial uniform interval of 1σ along all directions. Using the Lennard-Jones (LJ) unit system, the diameter of the CG bead σ for the polymer chains was set as the length unit, while the diameter for the solution CG beads was set as 0.1σ . Along all three directions, the length of polymer chains is set as 36σ while the periodic boundary conditions (PBC) are applied. Cubic cells with a uniform side length of 6σ are considered, creating 8 polymer chains along each direction and a total of 125 cells in the whole system via the crosslinkers. More details on the simulation settings are provided in ESI.

3. Results

3.1. Working principle

The working principle of the mechano-diffusion mechanism is to leverage the mechanical deformation of stretchable hydrogels for modulating the polymer network's geometric transformation and the polymer chain's energy modulation, which synergistically tunes the energy barrier for particle diffusion. As illustrated in Fig. 1A, particles with controlled diameter d diffuse across a layer of undeformed hydrogel with controlled mesh size ξ , the particle diffusivity of which is governed by the elastic energy barrier U for deforming polymer chains, known as hopping diffusion^{32,33}. As a tensile stretch λ is applied to the hydrogel (Fig. 1B), the hydrogel reduces in thickness and expands in area, enlarging the polymer mesh size $\xi(\lambda)$ and reducing the energy barrier $U(\lambda, d/\xi)$, enabling the strain-controlled and size-dependent particle diffusivity $D(\lambda, d/\xi)$.

3.2. Mechano-diffusion characterization

We develop a customized mechano-diffusion characterization platform and synthesize a model particle-hydrogel system to rigorously investigate the mechano-diffusion mechanism. As

illustrated in Fig. 1C and Supplementary Fig. S1, the mechano-diffusion characterization platform integrates a mechanical system to apply controlled tension and torsion loads to hydrogels, and an imaging system to measure the spatiotemporal diffusion profiles of AuNP particles³⁴. For the mechanical system, we adopt two-phase stepper motors controlled by a microcontroller to independently drive linear and rotary motions. The mechanical system allows for the application and recording of controlled tension and torsion loads on hydrogel samples with adjustable of linear and angular velocities, further enabling various loading stretching and torsion rates applied to hydrogel samples. For the imaging system, we employ a high-resolution camera with a maximum resolution of 3264×2448 pixels and a video capture rate of 15 frames per second to capture images, measuring the diffusion profiles of AuNPs in deformed hydrogels. In a typical mechano-diffusion experiment, the camera resolution is approximately 0.015 mm/pixel, which is sufficient for determining the diffusivity of AuNPs, since their diffusion profiles are on the millimeter scale.

As illustrated in Fig. 1D, the particle-hydrogel system consists of a single-network hydrogel³⁵ made of polyacrylamide (PAAm) and functionalized AuNPs²⁹ modified with polyethylene (PEG) chains. The functionalized AuNPs are synthesized by surface-modifying pristine AuNPs with 1 kDa PEG shells, resulting in two critical dimensions: the core diameter d_c of the pristine AuNPs and the hydrodynamic diameter d_h of the overall AuNPs with PEG shells. We synthesized two types of functionalized AuNPs with average core diameters of 6 nm and 18 nm, detailed in Supplementary Fig. S2 and Supplementary Fig. S3, respectively. The core diameter d_c and the hydrodynamic diameter d_h of the functionalized AuNPs were characterized using transmission electron microscopy (TEM, Fig. 1E, F) and dynamic light scattering (DLS, Fig. 1G), respectively. The zeta potentials of both functionalized AuNPs are nearly 0 mV, indicating their neutral surface electrokinetic potential and inert surface charge characteristics (Supplementary Fig. S4). The PAAm hydrogel was chosen for its superior resilience and high stretchability³⁵, therefore allowing us to exclude the effect of polymer-network evolution in this study. As shown in Fig. 1H, the PAAm hydrogel achieves a high stretchability of more than five times its original length while maintaining negligible mechanical hysteresis (Fig. 1I) and minimal stress shakedown under cyclic loading (Fig. 1J). Additionally, we incorporated hygroscopic salts (i.e., 4 M lithium chloride) into the hydrogel to prevent dehydration during long-term mechano-diffusion experiments (Supplementary Fig. S5).

3.3. Effects of uniaxial tension and pure torsion

We first examine the impact of tension and torsion on the diffusion of AuNPs in hydrogels under static loading. As illustrated in Fig. 2A, an aqueous AuNP solution is initially placed in the central reservoir of a cylindrical hydrogel sample with a radius R of 9 mm and a height H of 6 mm, which is then subjected to controlled tension and torsion. As illustrated in Supplementary Fig. S6, the hydrogel sample is covalently bonded between two glass substrates via saline chemistry³⁶ allowing the application of tension and torsion on the hydrogel



sample by manipulating the glass substrates while preventing delamination between the hydrogel sample and the glass substrates. A typical measured diffusion profile sequence of AuNPs in the hydrogel sample is presented in Fig. 2B. The AuNPs gradually diffuse along the radial direction, forming an increasingly larger circle. To extract the diffusivity D of AuNPs, we use the numerical finite difference method implemented in MATLAB to solve the diffusion governing equation in the cylindrical coordinate system, reading as $\partial c/\partial t = D(\partial^2 c/\partial r^2 + \partial c/(r\partial r) + \partial^2 c/\partial z^2)$. In the simulation, the cylindrical sample occupies the domain where $-9 \text{ mm} < r < 9 \text{ mm}$ and $0 < z < 6 \text{ mm}$, and the AuNP reservoir occupies the domain where $-1.5 \text{ mm} < r < 1.5 \text{ mm}$ and $0 < z < 3 \text{ mm}$. The initial concentration of AuNPs in the reservoir is set as a constant $c = c_0$, while the initial concentration of AuNPs in the rest of the cylindrical sample is set as $c = 0$. A typical simulated diffusion profile sequence of AuNPs in the hydrogel sample is presented in Fig. 2C. By fitting the simulated concentration profile to the measured concentration profile, we can extract the measured diffusivity D of AuNPs in hydrogels subjected to controlled stress states (Supplementary Fig. S7).

We first compare the diffusion concentration profile of both types of AuNPs in undeformed ($\lambda = 1$, $\alpha = 0^\circ$), stretched ($\lambda = 2$), and twisted ($\alpha = 90^\circ$) hydrogels after the same diffusion duration. As shown in Fig. 2D, the 18 nm AuNPs in the stretched hydrogel ($\lambda = 2$) exhibit an extended diffusion front compared to the undeformed hydrogel ($\lambda = 1$), indicating enhanced diffusion due to tension. In contrast, the 18 nm AuNPs in the twisted hydrogel ($\alpha = 90^\circ$) exhibit a significantly suppressed diffusion front compared to the undeformed hydrogel ($\alpha = 0^\circ$), indicating a slight reduction in diffusion due to torsion. To further quantify the strain effect, we compare the diffusivity of AuNPs in undeformed and stretched hydrogels at various diffusion times. Traditionally, particle diffusivity in hydrogels is constant throughout the diffusion process²⁷, consistent with our measurements of the diffusivity of AuNPs in the undeformed hydrogel (Fig. 2E). Intriguingly, the diffusivity of 18 nm AuNPs in the stretched hydrogel shows pronounced spatial dependence, suggesting that tensile strain plays a role in tuning particle diffusivity due to the nonuniform stress state along the radial direction in the cylindrical hydrogel sample³⁷. As shown in Fig. 2E, the diffusivity decreases from $44.1 \pm 3.98 \mu\text{m}^2/\text{s}$ to $22.3 \pm 3.47 \mu\text{m}^2/\text{s}$ as the 18 nm AuNPs diffuse from the center to the edge of the sample. In contrast, the diffusivity of 18 nm AuNPs in the twisted hydrogel ($\alpha = 90^\circ$) shows a slight spatial dependence from $1.53 \pm 0.16 \mu\text{m}^2/\text{s}$ to $1.19 \pm 0.25 \mu\text{m}^2/\text{s}$, suggesting that shear strain slightly reduces particle diffusivity as the AuNPs diffuse from the center to the edge of the sample (Fig. 2F). Compared to the 18 nm AuNPs, the 6 nm AuNPs exhibit enhanced diffusivity but less pronounced spatial-dependent particle diffusivity (Supplementary Fig. S8). This discrepancy is primarily due to the variation in AuNP core diameters, as larger AuNPs require higher energy barriers for particle diffusion compared to smaller AuNPs.

To further quantify the spatial-dependent diffusivity of AuNPs in the deformed cylindrical hydrogel sample, we take the measured AuNPs diffusivity at the center of the sample as center diffusivity D_c , while defining the measured AuNPs diffusivity at the edge of the sample as edge diffusivity D_e . As shown in Fig. 3A and 3B, when the hydrogel is

under tension, the center diffusivity and the edge diffusivity of the 18 nm AuNPs increases by 22 times and 14 times, respectively, as the tensile stretch reaches 2. In contrast, when the hydrogel is under torsion, the center diffusivity and the edge diffusivity of the 18 nm AuNPs decreases by 33% and 31%, respectively, as the torsion angle reaches 120 degrees (Fig. 3C, D). Notably, the center diffusivity and the edge diffusivity of the 6 nm AuNPs increases by 7.5 times and 4.6 times at the same tensile stretch of 2 (Supplementary Fig. S9) and decreases by 14% and 29% at the same torsion angle of 120 degree (Supplementary Fig. S10). We compare our strain-controlled particle diffusion with existing particle diffusion tuning approaches. As summarized in Fig. 3F and Table S1, the particle diffusivity tuning by temperature variation from 273 K to 333K in water, diluted polymer solution, and concentrated polymer solution achieves tuning ratios around 2.43¹⁴, 1.34³⁸, and 1.21³⁹⁻⁴¹, respectively, which are governed by the temperature-dependent viscosity of the liquid medium (Supplementary Fig. S11a). The particle diffusivity tuning by external fields such as light, magnetic field, and electrical field achieves tuning ratios of around 3.86⁴², 0.99⁴³, and 1.15⁴⁴, respectively. Furthermore, the particle diffusivity tuning by mechanical deformation to biological porous tissue (e.g., meniscus) and synthetic porous material attain tuning ratios of approximately 0.45⁴⁵ and 5⁴⁶ respectively, which are mainly attributed to the deformation-induced changes in porosity (Supplementary Fig. S11b). In contrast, our strain-controlled particle diffusion achieves a diffusivity tuning ratio up to 22, thanks to the substantial reduction in the energy barrier encountered by particles (Supplementary Fig. S11c). We further exam the effect of loading rate on center diffusivity D_c and edge diffusivity D_e . As shown in Fig. 3E, both D_c and D_e decrease as the stretch rate increases. Generally, the loading rate modulates the mode of diffusion, depending on the interplay among three critical time scales: the time scale associated with loading rate τ_1 on the order of a few seconds, the time scale associated with relaxation of polymer chains τ_2 measured to be around 19.4 seconds³⁴, and the time scale associated with particle diffusion τ_3 that varies significantly depending on its travel distance. At a low loading rate ($\tau_1 \gg \tau_2, \tau_3$), the diffusion system has sufficient time to reach its equilibrium state, and the diffusion process is primarily governed by the inherent particle diffusivity without interference from loading rate. At a high loading rate ($\tau_1 \ll \tau_2, \tau_3$), the polymer chains do not have enough time to relax during the loading, leading to a non-equilibrium state where polymer chain relaxation and particle hopping diffusion are coupled. The reduced diffusivity of AuNPs in a dynamically stretched hydrogel indicates a non-equilibrium hopping diffusion process. To summarize, the reduction in diffusivity under dynamic load is mainly attributed to the interplay among the time for particle hopping, the time for mechanical loading, and the time for polymer relaxation, which will be thoroughly investigated in future studies.

3.4. Effects of biaxial tension

Despite the high diffusivity tuning ratio under uniaxial tensile loading, the potential of strain-controlled particle diffusivity tuning has not been achieved. According to our mechano-diffusion theory³⁷, particle diffusivity in uniaxially stretched hydrogels is controlled by the combined effects of geometric transformation of the deformed polymer networks and energy modulation of the stretched polymer



chains. While the stretched polymer chains reduce the energy barrier to enhance particle diffusivity, the deformed polymer networks contract significantly perpendicular to the stretch direction, leading to either enhanced or suppressed particle diffusivity depending on the stretch ratio. In contrast to uniaxial tension, biaxial tension causes elongation in both in-plane directions, which can collectively enhance particle diffusivity. In this section, we use experiment, theory, and simulation to uncover the potential of harnessing mechanical deformation to control particle diffusion in biaxially stretched hydrogels.

We first develop a customized experimental setup to measure the AuNP diffusivity in hydrogels subjected to controlled biaxial tensile stretch λ . As illustrated in Supplementary Fig. S13, the experimental setup consists of a mechanical system for applying x - y plane biaxial tensile deformation and an imaging system for recording the diffusion process of AuNPs along the z direction. The four arms of the hydrogel are stretched in x and y directions by manipulating the glass slides covalently bonded to the arms. We measure the out-of-plane diffusivity of AuNPs subject to in-plane equal biaxial tensile stretch $\lambda_x = \lambda_y = \lambda$ (Fig. 4A). The penetration depth of the 6 nm AuNPs in the undeformed hydrogel ($\lambda = 1$) is less than 2 mm after a 300-minute duration; in contrast, the penetration depth of the AuNPs in the deformed hydrogel ($\lambda = 1.3$) increases significantly to 5 mm (Fig. 4B and Movie. S3). Compared to uniaxial tension, the 6 nm AuNPs exhibit higher diffusivity in hydrogels under biaxial tensile load at the same stretch level (Fig. 4C).

To maximize the potential of biaxial tension in facilitating mechano-diffusion of particles, we next formulate a cross-scale mechano-diffusion theory to establish the relationship between biaxial tensile stretch λ and particle diffusivity D with various diameters d . The key idea of the mechano-diffusion theory is to establish the relationship between the macroscopic deformation of soft materials and the microscopic diffusion of particles. As illustrated in Supplementary Fig. S15, the mechano-transport theory combines three models: 1) the eight-chain model⁴⁷, which connects the bulk deformation of soft materials to the stretch state of individual polymer chains, 2) the ideal chain model⁴⁸, which correlates the free energy of an individual polymer chain with its specified stretch state, and 3) the particle diffusion models, which quantify the diffusivity of particles with various diameters. Specifically, for particles larger than the mesh size of polymer networks, we adopt the hopping diffusion model³² to determine particle diffusivity, which depends on the energy barrier encountered during particle movements; while for particles smaller than the mesh size of polymer networks, we adopt the obstruction model⁴⁹ to determine particle diffusivity, which depends on the probability of the particle encountering neighboring polymer chains. The mechano-diffusion theory was adopted to capture the mechano-diffusion of particles in uniaxially stretched polymer networks³⁷.

Here, we use the theory to study the mechano-diffusion of particles in polymer networks subjected to equal biaxial tension. As schematically illustrated in Fig. 4D, as a hydrogel is subjected to an equal biaxial tension stretch λ , the unit-cell polymer network of the hydrogel expands its area to $\lambda a_0 \times \lambda a_0$ and reduces its thickness to $\lambda^{-2} a_0$, where a_0 is the length of the unit cell at an undeformed state. The biaxial tension induces two effects that collectively enhance the particle diffusivity: 1) geometric transformation that enhances

particle diffusivity via enlarged mesh size regardless of particle diameters, and 2) energy modulation that enhances particle diffusivity via reduced energy barrier dependent on particle diameters. We plot the calculated particle diffusivity normalized by its corresponding value at an undeformed state. As shown in Fig. 4E, for particles with small diameters ($d/\xi < 1$), the normalized particle diffusivity increases drastically at small deformation and gradually reaches a plateau at large deformation. The particle diffusivity tuning ratio for small particles is low (e.g., 1.21 for $d/\xi = 0.5$), because the diffusion of small particles in polymer networks is governed by the obstruction model⁴⁹ that is predominately influenced by geometric transformation instead of energy modulation. In contrast, for particles with large diameters ($d/\xi > 1$), the particle diffusivity tuning ratio significantly increases (e.g., 48 for $d/\xi = 1.8$), because the diffusion of large particles in polymer networks is governed by the hopping diffusion model³² that is impacted by both geometric transformations and energy modulations (Fig. 4F). As summarized in Fig. 4G, the maximum particle diffusivity tuning ratio reaches up to ~ 50 as particle diameter increases. Notably, as the stretch reaches a critical value, the diffusivity tuning ratio reaches a plateau, indicating a transition in the diffusion mode from hopping diffusion to Brownian diffusion within the polymer network. This shift occurs due to the reduction of mesh size in the biaxially stretched polymer network. The significantly enhanced particle diffusivity tuning ratio suggests the potential for achieving on and off tuning of particle diffusion⁵⁰, a key mechanism essential for on-demand and real-time control of particle diffusion in practical applications such as drug delivery and biomarker detection.

We then conducted coarse-grained molecular dynamics (CGMD) to investigate the effect of particle size on mechano-diffusion in polymer networks under biaxial tension. CGMD simplifies complex molecular systems, enabling the study of particle diffusion within cross-linked polymer networks. For example, recent studies have employed CGMD to investigate the transport behavior of penetrant by revealing the interplay between penetrant size, polymer relaxation, and mesh confinement^{51, 52}. By modeling large-scale dynamics, CGMD highlights the critical role of cross-link density, temperature, and penetrant characteristics⁵³. Additionally, CGMD has been applied to nanoparticle diffusion in biological systems, focusing how the structure of extracellular matrix modulates the nanoparticle transport efficiency⁵⁴.

We start with the simulation of a single particle diffusion in an aqueous medium with and without polymer networks (Fig. 5A and Movie. S4), where the polymer chain in the polymer network is simulated based on a coarse-grained bead-spring-chain model^{55, 56} (Fig. 5B). We employ a uniform mesh size that simplifies the real structural complexity of hydrogels, which offers the advantage of reducing computational resource demands while providing a foundational understanding of the mechano-diffusion of particles in a model polymer network. As shown in Fig. 5C, the mean square displacement (MSD) of particles diffusing in an aqueous medium with polymer networks is slightly lower than that of particles diffusing in an aqueous medium without polymer networks, suggesting the role of polymer network in suppressing particle diffusion. We further simulate the diffusion of particles with various diameters in undeformed polymer networks, calculating the



diffusivity of particles with polymer networks D_0 normalized by that without polymer networks D_{Sol} as a function of normalized particle size d/ξ . As shown in Fig. 5D, the simulated particle diffusivity decreases significantly with increasing particle diameter, aligning qualitatively with our mechano-diffusion theory. However, quantitatively, the simulated diffusivity of particles with diameters slightly smaller than mesh size is lower than the theoretical prediction. This discrepancy may arise from the polymer network in MD simulation imposing constraints on the particle diffusion, which are not fully captured by the obstruction model. For example, a previous study showed that diffusivity of water molecules (much smaller than mesh size) decreases with an increase in the polymer volume fraction⁵⁷, indicating that the polymer hinders the diffusivity of particles (i.e., ~ 0.3 nm for water molecules) even smaller than monomer radius (~ 0.5 nm for polyethylene hydrogels).

We next simulate the single-particle diffusion in polymer networks subject to equal biaxial tensile stretch λ (Fig. 5E and Movie. S4). As shown in Fig. 5F, for particles with diameters smaller than mesh size (e.g., $d = 0.5\xi$), the biaxial tension has a minimal impact on particle diffusivity tuning, because the diffusion of smaller particles is primarily governed by strain-induced geometrical transformation, with little influence from strain-induced energy modulation. In contrast, for particles with diameters slightly larger than mesh size (e.g., $d = 4\xi$), there exists a critical stretch λ_c , below which the equal biaxial tensile load effectively promotes hopping diffusion of particles due to a significant reduction in the energy barrier experienced by particles, and beyond which the equal biaxial tensile load has little effect on particle diffusivity since the energy barrier is completely diminished. As shown in Fig. 5G, biaxial tension dramatically increases particle diffusivity at large deformation, by approximately 40 times in simulation, due to the combined effects of strain-induced geometrical transformation and energy modulation. For particles much larger than mesh size (e.g., $d = 6\xi$), particle diffusion does not occur due to the ultra-high energy barrier encountered by the particles, even when individual chains in the polymer network are stretched to their breaking point, resulting in no strain effect. The comparisons between simulation and theory are presented in Supplementary Fig. S18, qualitatively matching well with each. We also simulate the energy barrier when a particle is passing the mesh cage. As shown in Fig. 5J, the polymer networks without tension build up a higher energy barrier, the total energy consisting of both potential energy and kinetic energy, for particle passing through than the polymer networks with tension-induced deformation. The simulation and theoretical results underscore the critical role of particle size in determining the particle diffusivity tuning ratio.

3.5. Model-guided drug delivery System

The mechano-diffusion of particles holds promise as a model-guided drug delivery system for pressure-controlled release of drug molecules. To demonstrate the potential, we develop a pressure-triggered drug delivery system, which consists of a closed-loop pneumatic actuator and a drug-load hydrogel membrane (Fig. 6A, Fig. S19-20). As the inflation pressure p increases, the hydrogel membrane is subjected to an approximately biaxial tensile deformation (Fig. 6D), controlling the release rate of drug molecules from the hydrogel into the surrounding environment (i.e. deionized

water bath). To harness the potential of model-guided drug release, we first carry out finite element simulation to correlate the inflated pressure p with the average effective stretch λ_{eff} applied on the hydrogel membrane (Fig. 6B, Fig. S21, Movie S5). We further perform a comparison experiment to quantify the impact of biaxial tensile deformation on the enhanced drug release rate. The comparison of drug release profiles from deformed and undeformed hydrogel membranes indicates that a compressive stress of 10 kPa (equivalently biaxial tensile load) effectively increases the concentration of released drug molecules by around 1.5 times (Fig. 6C). Given the simulated stress distribution and the particle mechano-diffusion in the hydrogel membrane, we quantitatively predict the concentration of drug molecules released into the water bath, matching the experimental results (Fig. 6D). The model-guided drug delivery system has the potential to revolutionize drug delivery in biomedical applications such as closed-loop glucose control, scar-free wound healing, ophthalmic drug delivery, which require drug delivery that responds to mechanical forces in the surrounding environment.

4. Conclusions

Building a mechano-diffusion characterization platform and a model particle-hydrogel system, we experimentally studied the diffusion of AuNPs in hydrogels subjected to the controlled stress state and loading rate. Our experiments demonstrate that tension loads can enhance AuNP diffusivity by up to 22 times, far surpassing that traditional particle diffusivity tuning approaches. Further empowered by mechano-diffusion theory and coarse-grained simulation, we push the limit of mechano-diffusion of particles in biaxially stretched polymer networks, which simultaneously expand the mesh size and reduce the energy barrier. This dual effect amplifies particle diffusivity by approximately 30 times due to the synergy of the polymer network's geometric transformation and the polymer chain's energy modulation. The geometric transformation of polymer networks affects the dynamics of particles, primarily following the obstruction model, a continuous process where particles diffuse through the aqueous medium; while the energy modulation of polymer chains impacts the dynamics of particles following the hopping diffusion model, a discrete process where particles escape from one polymer cage to another. This work will not only advance new knowledge of mechano-diffusion mechanisms pertinent to a broad range of biological and synthetic soft materials, but also lay a foundation for developing transport-based technologies that were previously inaccessible including but not limited to high-specific electrochemical biosensors with selective transport of biomarker⁵⁸, force-sensitive cargo for on-demand drug delivery⁵⁹, nanoparticle-induced biopolymer hydrogel toughening⁶⁰, and strain-programmable tissue adhesive for prolonged tissue repair⁶¹.

Author contributions



S. L. conceived the idea. C. Y., C. W., J. L., and T. W. performed the experiments and analysed the data. C. Y., C. W., J. L., T. W., and S. L. wrote the manuscript with inputs from all the authors. C. Y., C. W., J. L., T. W., X. L., Z. S., C. W., Z. L., and S. L. analysed and interpreted the results. S. L., Z. L., and C. W. supervised the research.

Conflicts of interest

The authors declare no conflict of interest.

Data availability

The data supporting this article have been included as part of the ESI.

Acknowledgements

The authors thank A. Withrow for help with TEM imaging and W. Zhang and R. Benedict for help with DLS characterization. The authors thank Dr. J. Laaser for helpful discussion on AuNP diffusion characterization in hydrogels. S. L. thank the support of National Science Foundation grant NSF-CMMI-2338747 and National Science Foundation grant NSF-CBET-2320716. C. W. thank the support of National Science Foundation grant NSF-CBET-2320717.

Notes and references

- Patel, S.; Ashwanikumar, N.; Robinson, E.; Xia, Y.; Mihai, C.; Griffith, J. P., 3rd; Hou, S.; Esposito, A. A.; Ketova, T.; Welsher, K.; Joyal, J. L.; Almarsson, O.; Sahay, G., Naturally-occurring cholesterol analogues in lipid nanoparticles induce polymorphic shape and enhance intracellular delivery of mRNA. *Nat Commun* **2020**, *11* (1), 983.
- Liu, M.; Li, Q.; Liang, L.; Li, J.; Wang, K.; Li, J.; Lv, M.; Chen, N.; Song, H.; Lee, J.; Shi, J.; Wang, L.; Lal, R.; Fan, C., Real-time visualization of clustering and intracellular transport of gold nanoparticles by correlative imaging. *Nat Commun* **2017**, *8*, 15646.
- Pino-Argumedo, M. I.; Fischer, A. J.; Hilkin, B. M.; Gansemer, N. D.; Allen, P. D.; Hoffman, E. A.; Stoltz, D. A.; Welsh, M. J.; Abou Alaiwa, M. H., Elastic mucus strands impair mucociliary clearance in cystic fibrosis pigs. *Proc Natl Acad Sci U S A* **2022**, *119* (13), e2121731119.
- Gu, H.; Hanedan, E.; Boehler, Q.; Huang, T.-Y.; Mathijssen, A. J. T. M.; Nelson, B. J., Artificial microtubules for rapid and collective transport of magnetic microcargoes. *Nature Machine Intelligence* **2022**, *4* (8), 678-684.
- Mateu-Regue, A.; Christiansen, J.; Bagger, F. O.; Winther, O.; Hellriegel, C.; Nielsen, F. C., Single mRNP Analysis Reveals that Small Cytoplasmic mRNP Granules Represent mRNA Singletons. *Cell Rep* **2019**, *29* (3), 736-748 e4.
- Hu, S.; Pei, X.; Duan, L.; Zhu, Z.; Liu, Y.; Chen, J.; Chen, T.; Ji, P.; Wan, Q.; Wang, J., A mussel-inspired film for adhesion to wet buccal tissue and efficient buccal drug delivery. *Nat Commun* **2021**, *12* (1), 1689.
- Basu, S.; Holbrook, L. T.; Kudlaty, K.; Fasanmade, O.; Wu, J.; Burke, A.; Langworthy, B. W.; Farzal, Z.; Mandani, M.; Bennett, W. D.; Fine, J. P.; Senior, B. A.; Zanation, A. M.; Ebert, C. S., Jr.; Kimple, A. J.; Thorp, B. D.; Frank-Ito, D. O.; Garcia, G. J. M.; Kimbell, J. S., Numerical evaluation of spray position for improved nasal drug delivery. *Sci Rep* **2020**, *10* (1), 10568.
- Raju, S.; Carbery, M.; Kuttykattil, A.; Senthirajah, K.; Lundmark, A.; Rogers, Z.; Scb, S.; Evans, G.; Palanisami, T., Improved methodology to determine the fate and transport of microplastics in a secondary wastewater treatment plant. *Water Res* **2020**, *173*, 115549.
- Freeman, S.; Booth, A. M.; Sabbah, I.; Tiller, R.; Dierking, J.; Klun, K.; Rotter, A.; Ben-David, E.; Javidpour, J.; Angel, D. L., Between source and sea: The role of wastewater treatment in reducing marine microplastics. *J Environ Manage* **2020**, *266*, 110642.
- Zhang, H.; Wang, Z.; Wang, F.; Zhang, Y.; Wang, H.; Liu, Y., In Situ Formation of Gold Nanoparticles Decorated Ti(3)C(2) MXenes Nanoprobe for Highly Sensitive Electrogenerated Chemiluminescence Detection of Exosomes and Their Surface Proteins. *Anal Chem* **2020**, *92* (7), 5546-5553.
- Lin, S.; Wang, B.; Zhao, Y.; Shih, R.; Cheng, X.; Yu, W.; Hojajji, H.; Lin, H.; Hoffman, C.; Ly, D.; Tan, J.; Chen, Y.; Di Carlo, D.; Milla, C.; Emaminejad, S., Natural Perspiration Sampling and in Situ Electrochemical Analysis with Hydrogel Micropatches for User-Identifiable and Wireless Chemo/Biosensing. *ACS Sens* **2020**, *5* (1), 93-102.
- Miller, C. C., The Stokes-Einstein law for diffusion in solution. *Proceedings of the Royal Society of London. Series A, Containing Papers of a Mathematical and Physical Character* **1924**, *106* (740), 724-749.
- Liu, Q.; Huang, S.; Suo, Z., Brownian Motion of Molecular Probes in Supercooled Liquids. *Phys Rev Lett* **2015**, *114* (22), 224301.
- Poling, B. E.; Prausnitz, J. M.; O'connell, J. P., *Properties of gases and liquids*. McGraw-Hill Education: 2001.
- Carruthers, A.; Melchior, D., Study of the relationship between bilayer water permeability and bilayer physical state. *Biochemistry* **1983**, *22* (25), 5797-5807.
- Hu, Y.; Zhao, X.; Vlassak, J. J.; Suo, Z., Using indentation to characterize the poroelasticity of gels. *Applied Physics Letters* **2010**, *96* (12).
- Baumberger, T.; Caroli, C.; Martina, D., Solvent control of crack dynamics in a reversible hydrogel. *Nature materials* **2006**, *5* (7), 552-555.
- Zhao, X.; Chen, X.; Yuk, H.; Lin, S.; Liu, X.; Parada, G., Soft materials by design: unconventional polymer networks give extreme properties. *Chemical Reviews* **2021**, *121* (8), 4309-4372.
- Lee, C. H.; Crosby, A. J.; Emrick, T.; Hayward, R. C., Characterization of heterogeneous polyacrylamide hydrogels by tracking of single quantum dots. *Macromolecules* **2014**, *47* (2), 741-749.
- Parrish, E.; Caporizzo, M. A.; Composto, R. J., Network confinement and heterogeneity slows nanoparticle diffusion in polymer gels. *The Journal of Chemical Physics* **2017**, *146* (20).
- Hartquist, C. M.; Li, B.; Zhang, J. H.; Yu, Z.; Lv, G.; Shin, J.; Boriskina, S. V.; Chen, G.; Zhao, X.; Lin, S., Reversible two-way tuning of thermal conductivity in an end-linked star-shaped thermoset. *Nature communications* **2024**, *15* (1), 5590.
- Gong, J. P.; Katsuyama, Y.; Kurokawa, T.; Osada, Y., Double - network hydrogels with extremely high mechanical strength. *Advanced materials* **2003**, *15* (14), 1155-1158.



23. Sun, J.-Y.; Zhao, X.; Illeperuma, W. R.; Chaudhuri, O.; Oh, K. H.; Mooney, D. J.; Vlassak, J. J.; Suo, Z., Highly stretchable and tough hydrogels. *Nature* **2012**, *489* (7414), 133-136.
24. Lin, S.; Liu, X.; Liu, J.; Yuk, H.; Loh, H.-C.; Parada, G. A.; Settens, C.; Song, J.; Masic, A.; McKinley, G. H., Anti-fatigue-fracture hydrogels. *Science advances* **2019**, *5* (1), eaau8528.
25. Hua, M.; Wu, S.; Ma, Y.; Zhao, Y.; Chen, Z.; Frenkel, I.; Strzalka, J.; Zhou, H.; Zhu, X.; He, X., Strong tough hydrogels via the synergy of freeze-casting and salting out. *Nature* **2021**, *590* (7847), 594-599.
26. Steck, J.; Kim, J.; Kutsovsky, Y.; Suo, Z., Multiscale stress deconcentration amplifies fatigue resistance of rubber. *Nature* **2023**, *624* (7991), 303-308.
27. Moncure, P. J.; Simon, Z. C.; Millstone, J. E.; Laaser, J. E., Relationship between gel mesh and particle size in determining nanoparticle diffusion in hydrogel nanocomposites. *The Journal of Physical Chemistry B* **2022**, *126* (22), 4132-4142.
28. Axpe, E.; Chan, D.; Offeddu, G. S.; Chang, Y.; Merida, D.; Hernandez, H. L.; Appel, E. A., A multiscale model for solute diffusion in hydrogels. *Macromolecules* **2019**, *52* (18), 6889-6897.
29. Gole, A.; Murphy, C. J., Seed-mediated synthesis of gold nanorods: role of the size and nature of the seed. *Chemistry of Materials* **2004**, *16* (19), 3633-3640.
30. Murphy, A. G. a. C. J., Seed-Mediated Synthesis of Gold Nanorods: Role of the Size and Nature of the Seed. *Chemistry of Materials* **2004**, *16* (19), 3633-3640.
31. Moncure, P. J.; Simon, Z. C.; Millstone, J. E.; Laaser, J. E., Relationship between Gel Mesh and Particle Size in Determining Nanoparticle Diffusion in Hydrogel Nanocomposites. *J Phys Chem B* **2022**, *126* (22), 4132-4142.
32. Cai, L.-H.; Panyukov, S.; Rubinstein, M., Hopping diffusion of nanoparticles in polymer matrices. *Macromolecules* **2015**, *48* (3), 847-862.
33. Xu, Z.; Dai, X.; Bu, X.; Yang, Y.; Zhang, X.; Man, X.; Zhang, X.; Doi, M.; Yan, L.-T., Enhanced heterogeneous diffusion of nanoparticles in semiflexible networks. *ACS nano* **2021**, *15* (3), 4608-4616.
34. Ye, C.; Lin, S., A mechano-diffusion characterization platform for probing strain-programmable nanoparticle diffusion in hydrogels. *MRS Communications* **2024**, 1-8.
35. Kim, J.; Zhang, G.; Shi, M.; Suo, Z., Fracture, fatigue, and friction of polymers in which entanglements greatly outnumber cross-links. *Science* **2021**, *374* (6564), 212-216.
36. Yuk, H.; Zhang, T.; Lin, S.; Parada, G. A.; Zhao, X., Tough bonding of hydrogels to diverse non-porous surfaces. *Nature materials* **2016**, *15* (2), 190-196.
37. Liu, J.; Lin, S., Strain-Engineered Particle Diffusion in Uniaxially Deformed Polymer Networks. *Journal of the Mechanics and Physics of Solids* **2024**, 105732.
38. Graessley, W. W., *Polymeric liquids & networks: structure and properties*. Garland Science: 2003.
39. De Gennes, P.-G., *Scaling concepts in polymer physics*. Cornell university press: 1979.
40. Flory, P. J., *Principles of polymer chemistry*. Cornell university press: 1953.
41. Dunstan, D. E., The viscosity-radius relationship for concentrated polymer solutions. *Scientific reports* **2019**, *9* (1), 543.
42. Moniruzzaman, M.; Bellerby, J. M.; Mai, N., The effect of light on the viscosity and molecular mass of nitrocellulose. *Polymer degradation and stability* **2011**, *96* (5), 929-935.
43. Ghauri, S.; Ansari, M., Increase of water viscosity under the influence of magnetic field. *Journal of Applied Physics* **2006**, *100* (6).
44. Zong, D.; Hu, H.; Duan, Y.; Sun, Y., Viscosity of water under electric field: Anisotropy induced by redistribution of hydrogen bonds. *The Journal of Physical Chemistry B* **2016**, *120* (21), 4818-4827.
45. Schwartz, G.; Morejon, A.; Best, T. M.; Jackson, A. R.; Travascio, F., Strain-dependent diffusivity of small and large molecules in meniscus. *Journal of biomechanical engineering* **2022**, *144* (11), 111010.
46. Wu, H.; Fang, W.-Z.; Kang, Q.; Tao, W.-Q.; Qiao, R., Predicting effective diffusivity of porous media from images by deep learning. *Scientific reports* **2019**, *9* (1), 20387.
47. Arruda, E. M.; Boyce, M. C., A three-dimensional constitutive model for the large stretch behavior of rubber elastic materials. *Journal of the Mechanics and Physics of Solids* **1993**, *41* (2), 389-412.
48. Kuhn, W.; Grün, F., Beziehungen zwischen elastischen Konstanten und Dehnungsdoppelbrechung hochelastischer Stoffe. *Kolloid-Zeitschrift* **1942**, *101*, 248-271.
49. Amsden, B., An obstruction-scaling model for diffusion in homogeneous hydrogels. *Macromolecules* **1999**, *32* (3), 874-879.
50. Alvarez-Lorenzo, C.; Concheiro, A., Intelligent drug delivery systems: polymeric micelles and hydrogels. *Mini reviews in medicinal chemistry* **2008**, *8* (11), 1065-1074.
51. Mei, B.; Lin, T.-W.; Sheridan, G. S.; Evans, C. M.; Sing, C. E.; Schweizer, K. S., How segmental dynamics and mesh confinement determine the selective diffusivity of molecules in cross-linked dense polymer networks. *ACS Central Science* **2023**, *9* (3), 508-518.
52. Lin, T.-W.; Mei, B.; Schweizer, K. S.; Sing, C. E., Simulation study of the effects of polymer network dynamics and mesh confinement on the diffusion and structural relaxation of penetrants. *The Journal of Chemical Physics* **2023**, *159* (1).
53. Mei, B.; Lin, T.-W.; Sing, C. E.; Schweizer, K. S., Self-consistent hopping theory of activated relaxation and diffusion of dilute penetrants in dense crosslinked polymer networks. *The Journal of Chemical Physics* **2023**, *158* (18).
54. He, X.; Yang, Y.; Han, Y.; Cao, C.; Zhang, Z.; Li, L.; Xiao, C.; Guo, H.; Wang, L.; Han, L., Extracellular matrix physical properties govern the diffusion of nanoparticles in tumor microenvironment. *Proceedings of the National Academy of Sciences* **2023**, *120* (1), e2209260120.
55. Zhao, B.-R.; Li, B., Molecular simulation of hopping mechanisms of nanoparticles in regular cross-linked polymer networks. *The Journal of Chemical Physics* **2022**, *157* (10).
56. Goodrich, C. P.; Brenner, M. P.; Ribbeck, K., Enhanced diffusion by binding to the crosslinks of a polymer gel. *Nature communications* **2018**, *9* (1), 4348.
57. Fujiyabu, T.; Li, X.; Chung, U.-i.; Sakai, T., Diffusion behavior of water molecules in hydrogels with controlled network structure. *Macromolecules* **2019**, *52* (5), 1923-1929.
58. Jia, X.; Dong, S.; Wang, E., Engineering the bioelectrochemical interface using functional nanomaterials and microchip technique toward sensitive and portable electrochemical biosensors. *Biosensors and Bioelectronics* **2016**, *76*, 80-90.
59. Zhao, X.; Kim, J.; Cezar, C. A.; Huebsch, N.; Lee, K.; Bouhadir, K.; Mooney, D. J., Active scaffolds for on-demand drug and cell delivery. *Proceedings of the National Academy of Sciences* **2011**, *108* (1), 67-72.
60. Ronsin, O.; Naassaoui, I.; Marcellan, A.; Baumberger, T., Environmental Nanoparticle-Induced Toughening and Pinning of a Growing Crack in a Biopolymer Hydrogel. *Physical review letters* **2019**, *123* (15), 158002.



Journal Name

ARTICLE

61. Ma, Z.; Bao, G.; Li, J., Multifaceted design and emerging applications of tissue adhesives. *Advanced Materials* **2021**, *33* (24), 2007663.

View Article Online
DOI: 10.1039/D4SM01522C

Open Access Article. Published on 18 February 2025. Downloaded on 2/21/2025 10:46:16 AM.
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.



Soft Matter Accepted Manuscript

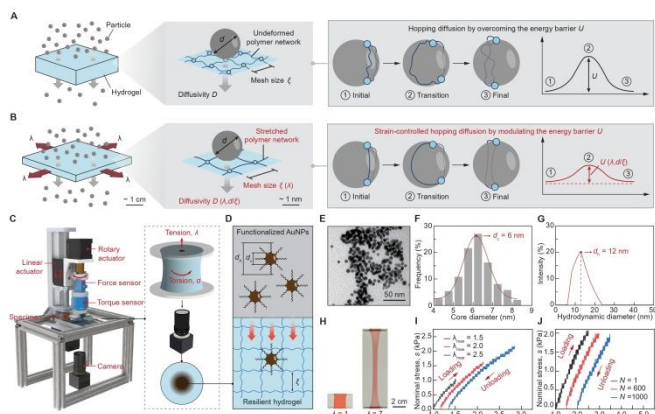


Fig. 1 | Working principle of mechano-diffusion of particles in stretchable hydrogels. **A**, Illustration of particles transport in undeformed hydrogel medium. The particles need to overcome a high energy barrier U when diffusing through the polymer networks. **B**, Illustration of particles transport in deformed hydrogel medium. The particles need to overcome a lower energy barrier $U(\lambda, d/\xi)$ due to the synergy of geometrical transformation and energy modulation. **C**, Schematics of the mechano-transport characterization platform, which can apply tension and torsion to hydrogel samples. **D**, Schematics of polyethylene glycol (PEG) functionalized gold nanoparticles (AuNPs) with core diameter d_c and hydrodynamic diameter d_h diffusing through hydrogels with controlled mesh size ξ . **E**, Transmission electron microscopy (TEM) image of 6 nm AuNPs. **F**, Statistical size distribution of 6 nm AuNPs based on TEM image. **G**, Hydrodynamic diameter distribution of 6 nm AuNPs characterized by dynamic light scattering (DLS). **H**, Optical image showing the stretchability of the hydrogel. **I**, Single-cycle stress-stretch curves of the hydrogel at different stretch ratios, showing negligible mechanical hysteresis. **J**, Multiple-cycle stress-stretch curves of the hydrogel under different cycle numbers, showing little stress shakedown. The scale bars in **E** and **H** are 50 nm and 2 cm, respectively.

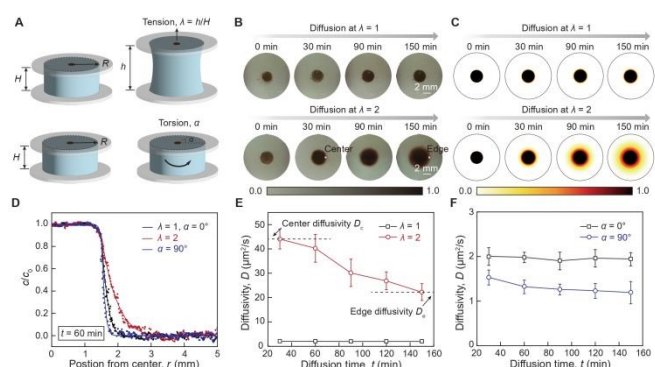


Fig. 2 | Mechano-diffusion characterization of AuNPs in deformed hydrogels. **A**, Illustration of the experiment setups of AuNPs diffusion in a cylindrical hydrogel with radius R and height H subjected to uniaxial tensile stretch λ or pure torsion angle α . **B**, Optical images of 18 nm AuNPs diffusion in undeformed ($\lambda = 1$) and stretched ($\lambda = 2$) hydrogels at various diffusion times. The AuNPs diffusivity at the center of the sample is denoted as center diffusivity D_c , while the AuNPs diffusivity at the edge of the sample is denoted as edge diffusivity D_e . **C**, Numerical simulations of 18 nm AuNPs diffusion in undeformed ($\lambda = 1$) and stretched ($\lambda = 2$) hydrogels at various diffusion times. **D**, Concentration of 18 nm AuNPs along radius direction in undeformed ($\lambda = 1$), stretched ($\lambda = 2$), and twisted ($\alpha = 90^\circ$) hydrogels. The solid dots denote the measured experimental results, and the solid lines denote the

fitted simulation results using the numerical finite difference method. **E**, Comparison of the extracted diffusivity D as a function of diffusion time t in undeformed ($\lambda = 1$) and stretched ($\lambda = 2$) hydrogels. The short-term diffusivity corresponds to center diffusivity D_c , while the long-term diffusivity corresponds to center diffusivity D_e . **F**, Comparison of the extracted diffusivity D as a function of diffusion time t in undeformed ($\alpha = 0^\circ$) and twisted ($\alpha = 90^\circ$) hydrogels. The error bars in **E** and **F** represent the standard deviation from at least three independent tests. The scale bar in **B** is 2 mm.

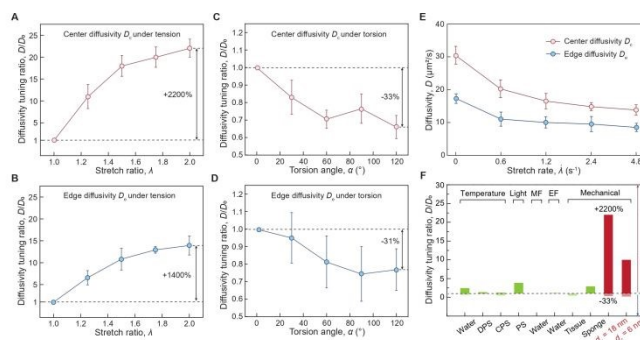


Fig. 3 | Effects of stress states and loading rates on mechano-diffusion of AuNPs in hydrogels. **A**, Center diffusivity tuning ratio D_c/D_0 versus stretch ratio λ of 18 nm AuNPs in hydrogels under uniaxial tension. **B**, Edge diffusivity tuning ratio D_e/D_0 versus stretch ratio λ of 18 nm AuNPs in hydrogels under uniaxial tension. **C**, Center diffusivity tuning ratio D_c/D_0 versus torsion angle α of 18 nm AuNPs in hydrogels under pure torsion. **D**, Edge diffusivity tuning ratio D_e/D_0 versus torsion angle α of 18 nm AuNPs in hydrogels under pure torsion. **E**, Center diffusivity D_c and edge diffusivity D_e versus stretch rates λ and torsion angle α of 18 nm AuNPs in hydrogels under uniaxial tension. **F**, Summarized diffusivity tuning ratio D/D_0 of existing particle diffusion tuning approaches (green columns) and mechano-diffusion approach in this work (red columns). The existing particle diffusion tuning approaches include the particle diffusivity tuning by temperature variation from 273 K to 333K in water, diluted polymer solution (DPS), and concentrated polymer solution (CPS), by external fields such as light, magnetic field (MF), and electrical field (EF), and by mechanical deformations. The error bars in **A** to **E** represent the standard deviation from at least three independent tests.

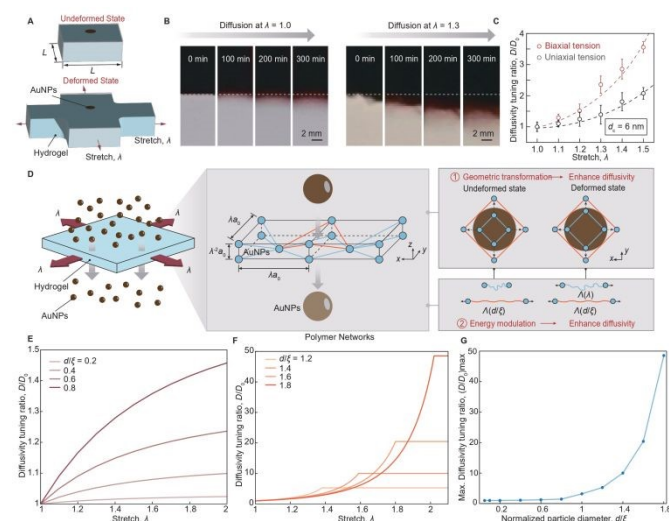


Fig. 4 | Effect of biaxial tension on mechano-diffusion of particles in hydrogels. **A**, Schematic illustration of the



experimental setup for mechano-diffusion of AuNPs in hydrogels under biaxial tension. **B**, Optical images of 6 nm AuNPs diffusion in undeformed ($\lambda = 1$) and biaxially stretched ($\lambda = 2$) hydrogels at various diffusion times. **C**, Comparison of diffusivity tuning ratio D/D_0 as a function of stretch ratio λ for 6 nm AuNPs diffusion in uniaxially and biaxially stretched hydrogels. **D**, Schematic illustration of particle diffusion in a polymer network under biaxial tension. The unit-cell polymer network expands its area to $\lambda a_0 \times \lambda a_0$ and reduces its thickness to $\lambda^{-2} a_0$, where a_0 is the length of the unit cell at its undeformed state. Biaxial tension induces geometric transformation and energy modulation that collectively enhance the particle diffusivity. **E**, Calculated diffusivity tuning ratio D/D_0 versus stretch ratio λ for particles with small diameters ($d/\xi < 1$) governed by the obstruction model. **F**, Calculated diffusivity tuning ratio D/D_0 versus stretch ratio λ for particles with small diameters ($d/\xi > 1$) governed by the hopping diffusion model. **G**, Maximum diffusivity tuning ratio $(D/D_0)_{\max}$ versus normalized particle diameters d/ξ . The error bars in **C** represent the standard deviation from at least three independent tests.

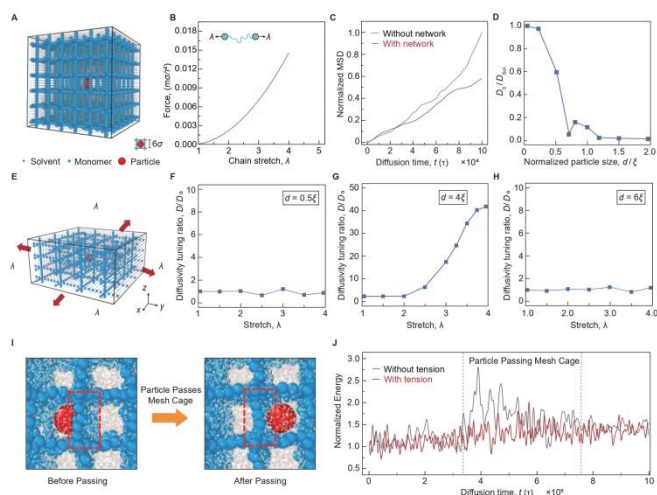


Fig. 5 | MD simulation of mechano-diffusion of particles in polymer networks under biaxial tension. **A**, Coarse-grained molecular dynamics simulation model of single-particle diffusion in polymer networks at undeformed state. **B**, Force in the unit of $m\sigma/\tau^2$ versus stretch λ curve of a single polymer chain in the simulation model, where m is the mass of the coarse-grained beads. **C**, Normalized mean-square displacement (MSD) versus diffusion time t for particle diffusion in an aqueous medium with and without polymer networks. The MSD is normalized by the MSD of particle diffusion in an aqueous medium without polymer networks at the diffusion time $t = 10^5 \tau$. **D**, Diffusivity of particles with polymer networks D_0 normalized by that without polymer networks D_{Sol} as a function of normalized particle size d/ξ . **E**, Coarse-grained molecular dynamics simulation model of single-particle diffusion in polymer networks under biaxial tension. **F**, Diffusivity tuning ratio D/D_0 versus stretch ratio λ for particles with diameters smaller than mesh size (e.g., $d = 0.5\xi$). **G**, Diffusivity tuning ratio D/D_0 versus stretch ratio λ for particles with diameters slightly larger than mesh size (e.g., $d = 4\xi$). **H**, Diffusivity tuning ratio D/D_0 versus stretch ratio λ for particles with diameters much larger than mesh size (e.g., $d = 6\xi$). **I**, Zoom-in visualization of the process of a single particle passing through the polymer network in the MD simulation. **J**, Energy barrier overcome by a particle when passing through polymer networks with and without biaxial tension.

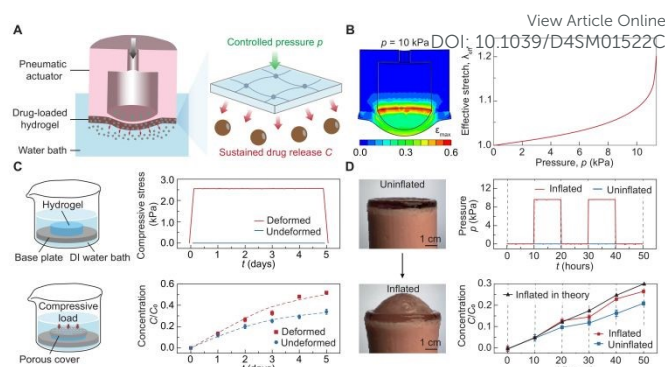


Fig. 6 | Model-guided drug delivery system. **A**, Design of pressure-triggered drug delivery system, which consists of a pneumatic actuator and a drug-loaded hydrogel membrane. As the inflation pressure p increases, the hydrogel membrane is subjected to an approximately biaxial tensile deformation, controlling the release rate of drug molecules from the hydrogel into the surrounding environment (i.e. deionized water bath). **B**, Finite element simulation (left panel) to correlate the inflated pressure p with the average effective stretch λ_{eff} applied on the hydrogel membrane (right panel). **C**, A comparison experiment (left panel) to quantify the impact of biaxial tensile deformation on the enhanced drug release rate (right panel). **D**, A comparison of drug release profile C/C_0 (bottom right panel) of inflated and uninflated drug delivery systems (left panel) subject to controlled inflation pressure p (top right panel), where C is the drug concentration released into the environment and C_0 is the initial drug concentration in the hydrogel membrane. The triangle dots in the bottom right panel are the theoretical prediction based on the simulated stress distribution and the mechano-diffusion of particles in the hydrogel membrane.

The data supporting this article have been included as part of the Supplementary Information.

