

# Journal of Materials Chemistry A

Materials for energy and sustainability

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: K. Niwa, H. Ogasawara, T. Sasaki, S. Nomura, G. Azuma, S. Pitie, G. Frapper and M. Hasegawa, *J. Mater. Chem. A*, 2025, DOI: 10.1039/D5TA01488C.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

## ARTICLE

High-Pressure Synthesis of  $\text{PbN}_2$ , the Missing Group 14  $\text{AN}_2$ -type CompoundKen Niwa,<sup>a,b,\*</sup> Hirokazu Ogasawara,<sup>c</sup> Takuya Sasaki,<sup>b</sup> Shunsuke Nomura,<sup>b</sup> Gendai Azuma,<sup>b</sup> Sylvain Pitié,<sup>d</sup> Gilles Frapper<sup>d</sup> and Masashi Hasegawa<sup>a,b</sup>Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

The direct reaction of Pb with molecular nitrogen was investigated using a laser-heated diamond anvil cell combined with high-pressure in-situ synchrotron X-ray powder diffraction measurements and Raman spectroscopy. From the results of the experiments and DFT calculations, it was revealed that a novel  $\text{PbN}_2$  was successfully synthesized above 50 GPa, and it was observed to crystallize in a tetragonal system (indexation in the  $\text{CuAl}_2$ -type structure,  $I4/mcm$ ), comprising  $\text{PbN}_8$  units connected via N-N dimers. Room-temperature compression and decompression experiments revealed that  $\text{PbN}_2$  retained its structural integrity up to a pressure of approximately 90 GPa, while it decomposed into lead and nitrogen at around 15 GPa. The experimental evidence indicates that the encapsulated nitrogen dumbbells act as anionic units,  $(\text{N}_2)^{2-}$  interaction with the lead lattice. The newly synthesized  $\text{PbN}_2$  exhibits a distinct crystal structure in comparison to the pyrite form of the other group-14 pernitrides ( $\text{SiN}_2$ ,  $\text{GeN}_2$ , and  $\text{SnN}_2$ ) that have been previously reported. This finding provides novel insights into the high-pressure crystal chemistry of nitrogen-based compounds.

## Introduction

The development of ultrahigh-pressure generation techniques has facilitated new insights into material science, including the study of superconductivity and superhard materials.<sup>1</sup> In particular, the laser-heated diamond-anvil cell (LHDAC), when combined with advanced characterization methods (such as synchrotron radiation, infrared spectroscopy, electron diffraction spectroscopy, and so forth) represents a promising tool for the synthesis of novel and attractive materials.<sup>2,3</sup> Furthermore, the LHDAC enables the convenient loading of gaseous samples, transportation to the synchrotron facility, and setup at the latter location.<sup>4,5</sup> A quarter of a century ago, these noteworthy features led to synthesizing novel nitrogen-based compounds, including  $\gamma\text{-Si}_3\text{N}_4$ <sup>6</sup> and  $\text{PtN}_2$ <sup>7,8</sup> among others.<sup>9–11</sup> Subsequently, numerous novel nitrides [ $\text{N}^{3-}$ ], dumbbells [ $\text{N}_2^q$ ], and polynitrogen-based units [ $\text{N}_x^q$ ] have been discovered in almost all binary nitrogen-based systems to date [e.g. some examples in the transition metal-nitrogen system].<sup>12–19</sup> The recent synthesis of new nitrogen-based compounds identified

in the pnictogen (Pn)–nitrogen systems provides an illustrative example of this high-pressure chemistry.<sup>20–23</sup> The synthesis of  $\text{AsN}$  and  $\text{BiN}$  was successfully achieved at 30–40 GPa and 50 GPa, respectively.<sup>20,22</sup> Furthermore, nitrogen-rich phases ( $\text{Sb}_2\text{N}_3$ ,  $\text{SbCN}_3$ ) were synthesized through the nitridation experiments of Sb at approximately 32 GPa<sup>21,24</sup>. What about the nitrides of group 14 elements? They are of significant importance in the field of functional ceramics.<sup>25</sup> Two structural polymorphs of  $\text{Si}_3\text{N}_4$  have been identified at ambient pressure,<sup>26–29</sup> and a third polymorph,  $\gamma\text{-Si}_3\text{N}_4$ ,<sup>6</sup> was discovered through direct nitridation of silicon at 15 GPa. Subsequently, the  $\gamma$ -phase was also found in  $\text{Ge}_3\text{N}_4$  under high pressure.<sup>30</sup> The synthesis of  $\gamma\text{-Sn}_3\text{N}_4$  has also been achieved without the use of high-pressure conditions,<sup>31</sup> while the high-pressure technique was employed to prevent the decomposition of nitride under high temperatures.<sup>32</sup> Subsequent high-pressure nitridation experiments on Si, Ge, and Sn were successful in synthesizing the pyrite-type  $\text{AN}_2$  ( $\text{A}=\text{Si}$ ,  $\text{Ge}$ , and  $\text{Sn}$ ) above approximately 60 GPa.<sup>33,34</sup>

The pyrite type is one of the high-density structures observed in  $\text{MX}_2$ -type compounds. Therefore, the exploration of higher-density phases than pyrite-type represents a promising avenue of research, offering insights not only into high-pressure crystal chemistry but also in the development of novel functional nitrogen-based ceramics. In accordance with the phase transition sequence upon pressure in  $\text{AO}_2$  ( $\text{A}=\text{Si}$ ,  $\text{Ge}$ ,  $\text{Sn}$ , and  $\text{Pb}$ ), the crystal structure of the high-pressure phase that manifests in low-Z oxides is analogous to that of high-Z oxides at low pressure.<sup>35–40</sup> It is therefore important to investigate the Pb-N system under conditions of elevated pressure and at atmospheric conditions, where the only

<sup>a</sup> Research Center for Crystalline Materials Engineering, Nagoya University, Furo-cho, Chikusa-ku, Nagoya, Aichi 464-8603, Japan

<sup>b</sup> Department of Materials Physics, Nagoya University, Furo-cho, Chikusa-ku, Nagoya, Aichi 464-8603, Japan

<sup>c</sup> Department of Crystalline Materials Science, Nagoya University, Furo-cho, Chikusa-ku, Nagoya, Aichi 464-8603, Japan

<sup>d</sup> Applied Quantum Chemistry group, E4 team, IC2MP UMR 7285, Université de Poitiers – CNRS, 4, rue Michel Brunet TSA 51106 – 86073, Poitiers, France.

Supplementary Information available: [Additional Experimental details; Measured Raman spectra; XRD pattern and analysis results; Scanning Electron Microscope image, Additional calculations details with computational methods; Calculated Raman spectra; ]. See DOI: 10.1039/x0xx00000x



observed binary phase is  $\text{Pb}(\text{N}_3)_2$  azide.<sup>41–43</sup> Lead typically assumes the +2 and +4 oxidation states. The  $\text{Pb}^{2+}$ -containing compounds exhibit remarkable dielectricity due to the distortion of the unit cell induced by the lone-pair electrons,<sup>44–46</sup> although the use of lead in material development is discouraged. The effect of lone-pair electrons on structural stability was also highlighted in the high-pressure synthesis of the novel  $\text{PnN}$  compounds.<sup>22</sup> As evidenced by the synthesis of  $\text{Pn}_x\text{N}_y$  compounds,<sup>20–22</sup> the high-pressure technique represents a more effective and advantageous approach for accessing the synthesis of the remaining group-14 pernitride,  $\text{PbN}_2$  ( $\text{Pb}^{2+}\text{N}_2^{2-}$  or  $\text{Pb}^{4+}\text{N}_2^{4-}$ ). However, to the best of our knowledge, only the explosive material, lead azide  $\text{Pb}(\text{N}_3)_2$ , has been identified as a thermodynamically metastable compound within the Pb-N binary system.<sup>41–43</sup> In contrast to these experimental findings, a recent theoretical study has been conducted to investigate the Pb-N phase diagram under pressure using evolutionary algorithms combined with density functional theory (DFT) calculations.<sup>47</sup> This study revealed the phase stability and crystal chemistry of novel  $\text{PbN}_z$  phases ( $z=2-4,6,8$ ) when pressure is increased up to 100 GPa, including the hitherto unidentified pernitride  $\text{PbN}_2$  of group 14 elements.<sup>47</sup> The Pb- $\text{N}_2$  system offers a diverse range of opportunities for the exploration of pernitrides and polynitrides, which could result in the development of high-energy materials. The objective of the present study is to conduct high-pressure synthesis experiments (LHDAC) on the Pb- $\text{N}_2$  system up to approximately 90 GPa, with a particular focus on the  $\text{PbN}_2$ .

## Experimental

We performed five independent experiments (sample number: OH#45, OH#52, NS#1, AG#1, AG#2) and the details of the experimental setup are given below. Further additional information for each experiment is given in Supporting Information (please refer to Experimental details of the SI). The high-pressure synthesis experiments were conducted using a laser-heated diamond anvil cell (LHDAC) equipped with a 350  $\mu\text{m}$  culet size anvil. Stainless steel (OH#45, OH#52, AG#1, AG#2) or rhenium (NS#1) plate with an initial thickness of approximately 280  $\mu\text{m}$  was used as a gasket material. The gasket material was indented, and the intended area was drilled with a pulsed infrared laser to make a sample chamber with a diameter of 1/2 or 1/3 of the culet size. Lead foil (99.99 %, The Nilaco Corporation) was stretched, thinned, and then shaped with less than approximately  $80 \times 80 \mu\text{m}^2$ . After that, the lead thin film was placed in the sample hole with ruby chips as a pressure marker and then the sample chamber was filled with liquid nitrogen. The pressure was increased up to the desired pressure under room temperature, and then, the sample was heated by irradiating the infrared laser (SPI, Ltd  $\lambda=1090 \text{ nm}$ ) from both sides. The sample was monitored during laser heating. The temperature was not measured in this study however, intense thermal radiation was observed during laser irradiation, which might correspond to over 2000 K. The unheated regions were probably due to the insufficient thickness of the thermal insulating layer. The heated sample

was evaluated by optical microscope observation, Raman scattering, and X-ray diffraction measurements under high pressures. Argon ion (488 nm, <100 mW) or diode-pumped (473 nm, <100 mW) laser was used as an excitation source for Raman scattering measurements. The incident laser was focused with a size of less than approximately 10  $\mu\text{m}$  through the diamond. The Raman signal was detected with the liquid nitrogen-cooled CCD detector. High-pressure *in-situ* X-ray diffraction experiments were conducted at BL2S1, the Nagoya University beamline of Aichi Synchrotron Radiation Center, Aichi Science & Technology Foundation,<sup>48</sup> and BL10XU, SPring-8.<sup>49</sup> The distance between the sample and detector, the wavelength of the X-ray, the tilting of the detector, etc. were calibrated based on the diffraction profile of standard material  $\text{CeO}_2$  before the sample measurements. At BL2S1, the monochromatic X-ray with the size of 75 – 100  $\mu\text{m}$  was introduced to the sample chamber at 15 degrees tilting from the compression axis, which allows measuring the wide 2-theta range, while for the experiments at BL10XU, the X-rays with the size of approximately 10  $\mu\text{m}$  were introduced parallel to the compression axis. The diffracted X-rays were recorded with a typical exposure time of 3-5 minutes and 2 seconds for the experiments at BL2S1 and BL10XU, respectively. Details of high-pressure *in-situ* XRD measurements are described elsewhere.<sup>48,49</sup> The 2-dimensional (2-D) diffraction pattern was converted to the conventional 1-D profile by using IPAnalyzer.<sup>50</sup> The phase identification and indexing analysis were conducted using dedicated software of PDIndexer<sup>50</sup> and DICVOL06, respectively.<sup>51</sup> Le Bail refinement was carried out using RIETAN-FP.<sup>52</sup> The pressure was evaluated based on the pressure dependence of the ruby fluorescence peak<sup>53</sup> and the equation of the state of rhenium (gasket material),<sup>54</sup> solid nitrogen,<sup>55</sup> and residual lead.<sup>56,57</sup> The recovered sample was characterized by a scanning electron microscope equipped with energy-dispersive spectroscopy (FlexSEM 1000 II, Hitachi High-Tech Corporation, accelerating voltage: 15 kV).

The energy and crystal structure calculations of  $\text{PbN}_2$  phases with different nitrogen dimer arrangement in  $2 \times 2 \times 2$  supercell was carried out by density functional theory (DFT) calculations performed using the CASTEP *ab initio* program<sup>58</sup> on the Materials Studio package. The generalized gradient approximation (GGA-PBE)<sup>59,60</sup> was applied, and wave functions were characterized by a plane wave basis set, whereas ultrasoft pseudopotentials were employed with a cutoff energy of 570 eV. k-Point grids of  $4 \times 4 \times 4$  were used for geometry optimizations. The energy, atomic force, and displacement convergence criteria were set to  $5 \times 10^{-6} \text{ eV/atom}$ ,  $1 \times 10^{-2} \text{ eV/\AA}$ , and  $5 \times 10^{-4} \text{ \AA}$ , respectively. To obtain the Raman spectra, we employed the VASP code<sup>61,62</sup> or the computation of phonons. These calculations were performed at the PBE level of theory using the finite displacement method implemented in the PHONOPY code (for additional details regarding the phonon calculation, please refer to Section S1.1 – 1.3 of the SI).<sup>63,64</sup> Based on these phonon calculations, we extracted and computed the intensity of the active Raman bands using the Phonopy-Spectroscopy package.<sup>65,66</sup>



Frequency calculations were performed at  $\Gamma$ , thanks to the Phonopy package with a finite difference approach (0.01 Å displacements), employing VASP 5.4.4 as the force calculator. IR intensities and Raman activities were evaluated, thanks to the Phonopy-spectroscopy framework. A  $2 \times 2 \times 1$  and  $2 \times 1 \times 1$  supercells were needed for the  $I4/mcm$   $\text{PbN}_2$  and  $R-3c$   $\text{Pb}(\text{N}_2)_3$  crystals to ensure convergence.

## Results and discussion

Fig.1(a) and (b) show the high-pressure *in-situ* Raman spectra (AG#1) obtained prior to and following laser heating of lead in nitrogen, respectively. The application of laser heating at approximately 50 GPa resulted in a notable alteration of the sample's colour, transitioning from a metallic to a black colour. The Raman scattering measurements conducted following the heating process revealed the emergence of several additional sharp peaks and a notable reduction in the intensity of the nitrogen pressure medium. These findings provide compelling evidence that the synthesis of new  $\text{Pb}_x\text{N}_y$  compounds can be achieved by reacting between lead and nitrogen under high-pressure conditions. Then, the pressure was decreased from approximately 55 GPa to 40 GPa, while Raman spectra were recorded. The newly emerged Raman peaks underwent a shift, yet no additional peaks or those that had disappeared were observed (see Fig.S1). These findings suggest that the novel  $\text{Pb}_x\text{N}_y$  compound was stable at pressures down to approximately 40 GPa. Notably, the Raman peak situated at approximately  $2100\text{ cm}^{-1}$  shifted to a higher wavenumber with

decreasing pressure, which represents an inverse pressure response to that observed in conventional solid state materials and will be discussed subsequently.

The newly synthesized compounds were characterized by high-pressure *in-situ* powder X-ray diffraction measurements at synchrotron facilities. Recently, a technique using high-intensity synchrotron radiation has been widely used to characterize the crystal structure by extracting single-domain-derived diffraction spots from a multi-grain sample.<sup>67</sup> Unfortunately, we have used conventional powder diffraction technique in this study, while have attempted to access the details of newly synthesized compound by combining the results of Raman scattering measurements and first-principles calculations in addition to an information of the powder diffraction pattern. A finely focused X-ray beam at BL10XU, SPring-8, allows the diffracted X-rays from heated and unheated areas to be measured separately, as illustrated in Fig.1(c). The diffraction peaks from the unheated area were assigned using lead<sup>56,57</sup> and solid molecular nitrogen.<sup>55</sup> Conversely, several sharp diffraction peaks distinct from those observed in solid nitrogen and lead were identified in the heated region. The crystal symmetry was investigated through the assignment of over fifteen intense diffraction peaks using dedicated indexing software, leading to the identification of a tetragonal cell with lattice parameters  $a = 3.297(1)\text{ Å}$  and  $c = 3.089(2)\text{ Å}$  as the most plausible candidate (see Table S1). Additionally, the orthorhombic cell was identified as a potential candidate, but some XRD peak positions could not be accurately fitted. The Miller indices of the tetragonal unit cell follow the extinction rule of the  $P$  lattice. Further analysis by the charge-flipping method<sup>68</sup> utilizing the extracted intensity data revealed the Pb position at the vertex of the tetragonal cell. Two Pb-Pb distances were identified within the tetragonal Pb-lattice. One ( $d \approx 3.1\text{ Å}$ ) exhibited a comparable value to that observed in the high-pressure hexagonal phase of lead ( $d \approx 3.1\text{ Å}$ ),<sup>56,57</sup> while the other ( $d \approx 3.3\text{ Å}$ ) demonstrated a slightly longer distance. The longer Pb-Pb distance may be attributed to the incorporation of nitrogen atoms or dimers into the Pb lattice.

As illustrated in Fig. 2(a), modifying the charge density map contrast results in a diminished charge density at the intermediate sites among Pb, which signifies the incorporation and alignment of the nitrogen dimer within the Pb lattice. The state of nitrogen was additionally evaluated through a volumetric comparison with  $\text{Pb}+\text{N}_2$ . It can be postulated that the nitrogen dimer existed in the tetragonal Pb lattice, forming the  $\text{Pb}(\text{N}_2)_x$ . The unit cell is assumed to be  $Z = 1$  and the volume is compared with that of  $\text{Pb}+\text{N}_2$  using the equation of state for lead and solid molecular nitrogen. It was determined that the formation of  $\text{PbN}_2$  via the reaction between lead and nitrogen molecules resulted in a reasonable volume reduction of approximately 18%. To gain insight into the details of the newly synthesized  $\text{PbN}_2$ , several model structures were proposed. In consideration of the alignments of the nitrogen dimer, the  $2 \times 2 \times 2$  size of the initial Pb-lattice was postulated, and the total electronic energies of these structural models were calculated, with the experimentally determined lattice parameters held constant (constant volume). It should be noted that  $\text{N}_2$  units can align in different directions within each  $\text{Pb}_8$  tetragonal cage, a

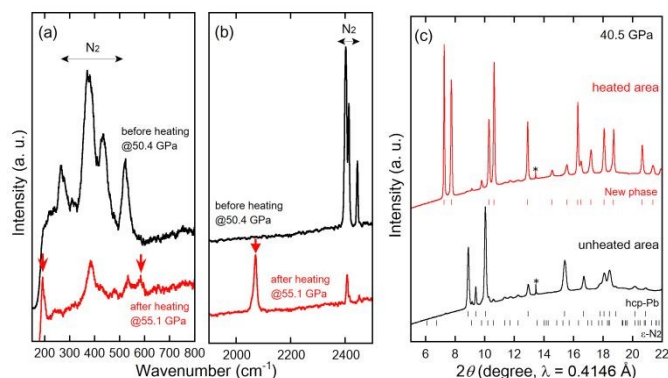


Fig.1 Raman spectra and XRD profiles under high pressures. (a) and (b) shows the Raman spectra corresponding to the  $\text{Pb}-\text{N}_2$  sample (AG#1) before and after laser heating at approximately 50 GPa. Two wavenumber regions were separately displayed. Intense peaks after laser-heating are marked with arrows. The horizontal arrows show the wavenumber region derived from solid molecular nitrogen. (c) High-pressure *in-situ* X-ray diffraction profiles acquired from the heated and unheated areas. The diffraction peak positions of Pb, and  $\text{N}_2$  are represented with tics at the bottom of the profiles. The intense peak positions derived from the new phase that appeared after laser heating are also indicated with tics. The peak marked with an asterisk might be derived from the device.





## ARTICLE

## Journal Name

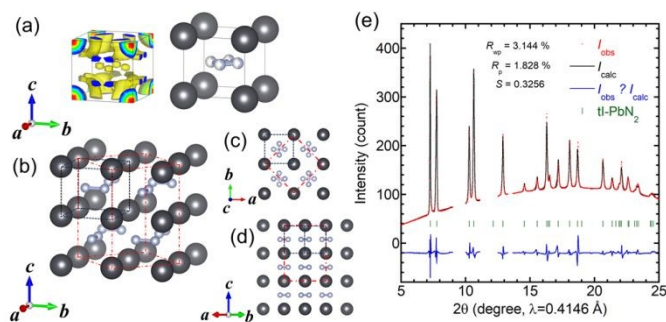


Fig.2 Charge density map, atomic arrangement, and refined XRD profile of newly synthesized  $\text{PbN}_2$ . (a) Charge density map and corresponding atomic assignment of the tetragonal cell. Large and small half-filled balls correspond to Pb and N, respectively. (b) Atomic arrangements in the  $2 \times 2 \times 2$  extended cell of the initially obtained one. The nitrogen dimers alternatively align in the neighbor cell which was obtained by the energy calculation results. The initial obtained  $P$  lattice cell and extended cell ( $I$  lattice) are represented with the dashed and dot-dashed lines, respectively. (c-d) Projected atomic arrangement along the  $c$ -axis and  $[110]$  direction, respectively. (e) LeBail refinement based on the tetragonal symmetry having the  $I$  lattice. The  $2\theta$  regions where nitrogen diffraction peaks appeared are excluded from the refinements. The crystal structures are drawn with 3D visualization program

condition that is considered in our models. As illustrated in Fig. 2(b-d) and Fig. S2, the DFT computational analysis indicated that the most energetically favorable structure involved the alternate alignment of the nitrogen dimers within the Pb lattice. Considering the data yielded by the experiments, the  $\text{CuAl}_2$ -type structure ( $I4/mcm$ , No. 140) was put forth as a potential hypothesis. The unit cell of the  $I$  lattice is equivalent to the  $\sqrt{2}a \times \sqrt{2}a \times 2c$  of the initially obtained  $P$  lattice unit cell (Fig.2(b-d)). This equivalence can be confirmed by the existence of 213 diffraction in the  $I$  lattice setting, as no peak corresponding to this index exists in the  $P$  lattice. Upon examination of the unrolled Debye-ring recorded on a two-dimensional detector, weak diffraction spots corresponding to 213 of the  $I$  lattice were identified (Fig.S3). Fig.2(e) represents the Le Bail refinement of the XRD profile based on the space group of  $I4/mcm$  with the lattice parameters of  $a=4.6266(1)$  Å and  $c=6.1278(2)$  Å. In this  $\text{CuAl}_2$ -type phase, each Pb atom coordinates to eight nitrogen atoms, in which a coordination number is higher than that observed in the pyrite form of other group-14 pnitrides. Furthermore, structural diversity is permitted for  $\text{CuAl}_2$ -type compounds, exemplifying the considerable variation in axial length ratio contingent on the constituent elements.<sup>69</sup> Lead exhibits compressive behavior,<sup>56,57</sup> a known property of Pb, whereby the nitrogen dimer may align flexibly within the structure and the structure diversity may be yielded. The present result, which is based on modeling that has been guided by experimental insights and DFT calculations, is in perfect agreement with the *ab initio* evolutionary (EA-DFT) study that has been conducted to investigate the potential emergence of  $\text{Pb}_x\text{N}_y$  compounds in the Pb-N system up to a pressure of 100 GPa.<sup>47</sup> Firstly, the crystal structure prediction (CSP EA-DFT) searches identified the

1:2 composition as lying on the convex hull, i.e.  $\text{PbN}_2$  is a dynamically and thermodynamically stable compound above 32 GPa and at least up to 100 GPa. Secondly,  $\text{PbN}_2$  crystallizes in the  $\text{CuAl}_2$ -type structure within the aforementioned pressure range. At 50 GPa, the  $a$ - and  $c$ -lattices were calculated to be 4.588 Å and 6.007 Å, respectively (meta-GGA  $r^2\text{SCAN}$  level of theory), and these calculated values are in perfect agreement with the experimental data.

The phase stability of  $\text{PbN}_2$  was investigated based on the additional high-pressure *in-situ* XRD measurements and Raman spectroscopy along with the compression and decompression process. As illustrated in Fig.3, the XRD peaks derived from the  $\text{PbN}_2$  remained intact up to 86.9 GPa under room temperature compression. In that experiment, it is possible that the pressure was overestimated because the pressure was determined by the equation of state of the rhenium gasket which was uniaxially compressed. Upon decompression process at room temperature,  $\text{PbN}_2$  underwent decomposition at approximately 15 GPa. Our experiments did not yield substantial evidence for the other metastable low-pressure phase prior to decomposition. Furthermore, the room temperature re-compression of the decomposed sample (AG#1) was conducted, yet no  $\text{PbN}_2$  was observed to reappear (for details, please refer to Fig. S4). The pressure dependence of the cell volume per formula unit and Pb-Pb distances are displayed in Fig. 4. Additionally, the pressure-volume relation for  $\text{Pb}+\text{N}_2$  is

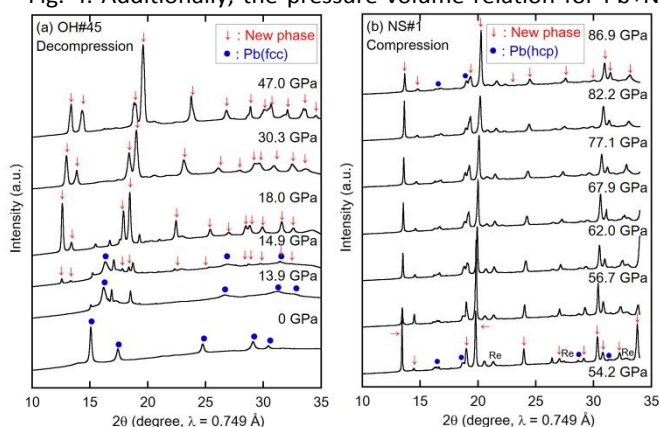


Fig.3 Pressure evolution of X-ray diffraction profiles (OH#45 and NS#1) (a) The XRD profile of the sample (OH#45) acquired during the decompression from 47 GPa. The top profile corresponds to the sample after heating at 47 GPa. Newly appeared peaks are marked with arrows. XRD patterns were acquired along the decompression to ambient pressure at room temperature. (b) The XRD profile of the sample (NS#1) was acquired during the compression from 54.2 GPa. The bottom profile corresponds to the laser-heated sample. The arrows correspond to the peaks of the newly synthesized compound as well as (a). XRD patterns were acquired along the compression to approximately 90 GPa under room temperature. Non-marked peaks might be derived from nitrogen and weak peaks from the rhenium gasket are detected with the labeling of "Re" in (b). There are still a few unidentified peaks that might represent other new compounds, which should be investigated further.



also shown there. The zero-pressure bulk modulus ( $K_0$ ) of 65(3) GPa and unit cell volume ( $V_0$ ) of 44.7(3) Å<sup>3</sup> were preliminarily obtained by fitting the pressure-volume data (OH#45) to the 2nd-order Birch-Murnaghan equation of state. The zero-pressure bulk modulus is markedly lower than that of other group-14 pernitrides<sup>33</sup> SiN<sub>2</sub>, GeN<sub>2</sub>, and SnN<sub>2</sub>, reflecting the weaker Pb-N interactions. It is approximately 1.5 times that of lead.<sup>56,57</sup> This phenomenon is likely attributable to the incorporation of the nitrogen dimer into the Pb lattice, resulting in a charge transfer from Pb to N<sub>2</sub>. The experimentally observed volume reduction is reasonably consistent with the result of the first principles calculation (41 % from 0 GPa to 100 GPa) if the uncertainty of the pressure determination was considered. In addition to bulk compressibility, axial compressibility and ratio were evaluated (see Fig.S5). It was established that PbN<sub>2</sub> displays enhanced compressibility along the *c*-axis relative to the *a*-axis, which leads to the decreasing of *c/a* with increasing the pressure. This finding aligns with the incorporation of nitrogen dimers that are alternatively aligned in the *a-b* plane.

Raman scattering measurements provide useful information to assess the newly synthesized material's phase stability and bonding nature. Fig.5(a)(b) shows the Raman spectra of the samples (AG#2) acquired during the decompression process. As mentioned earlier, the peaks around 200 and 2100 cm<sup>-1</sup> became less intense, shifting to lower and higher wavenumbers

respectively with decreasing pressure. A lower wavenumber peak could not be detected below 23 GPa due to the cutting-edge wavenumber of the long pass filter for this sample. The high-resolution Raman spectra were also obtained using an argon ion laser (488 nm), which allows the detection of low wavenumber peaks down to ambient pressure by using a suitable long-pass filter (see Fig.S6). The nature of remaining weak peaks is unclear but may be related to the slow decompression rate, high crystallinity, high detector sensitivity, etc. On the other hand, the higher wavenumber peak eventually disappeared or merged with the N<sub>2</sub> pressure medium (see Fig.5(b)), although it could be detected down to around 10 GPa when the Raman spectra were measured from different positions (see Fig.S7).

The nitrogen dimer [NN]<sup>q-</sup> gives a vibrational wavenumber depending on the *q* negative charge, which is reflected in the bond order in N<sub>2</sub> dumbbells. As the bond order increases, i.e. one in [N-N]<sup>4-</sup>, two in [N=N]<sup>2-</sup> and three in neutral [N≡N], the vibrational frequency increases, i.e. approximately 900, 1300, and 2400 cm<sup>-1</sup>, respectively.<sup>7,71-75</sup> The vibrational mode wavenumbers associated with the [N-N]<sup>4-</sup> stretching mode in group-14 element pernitrides of SiN<sub>2</sub>, GeN<sub>2</sub>, and SnN<sub>2</sub> are observed around 1000-1100 cm<sup>-1</sup>.<sup>33</sup> However, the Raman wavenumber of PbN<sub>2</sub> is largely different from the other group-14 element pernitrides. What are the Raman active modes and spectra of the CuAl<sub>2</sub>-type PbN<sub>2</sub>? To give a response, we have conducted a study of the Raman spectra of the ground state *I4/mcm* PbN<sub>2</sub> phase at 50 GPa using DFT calculations. The simulated Raman spectra are shown in Fig.5(c)(d), and the corresponding wavenumbers are provided in Table S2. The pressure dependences of measured and calculated wavenumbers are plotted in Fig.6. A factor group analysis predicts the presence of five Raman-active modes: E<sub>g</sub>, E<sub>g</sub>, B<sub>1g</sub>, B<sub>2g</sub>, and A<sub>1g</sub>. In the wavenumber range below 800 cm<sup>-1</sup>, the Raman spectrum of *I4/mcm* PbN<sub>2</sub> at 50 GPa is distinguished by

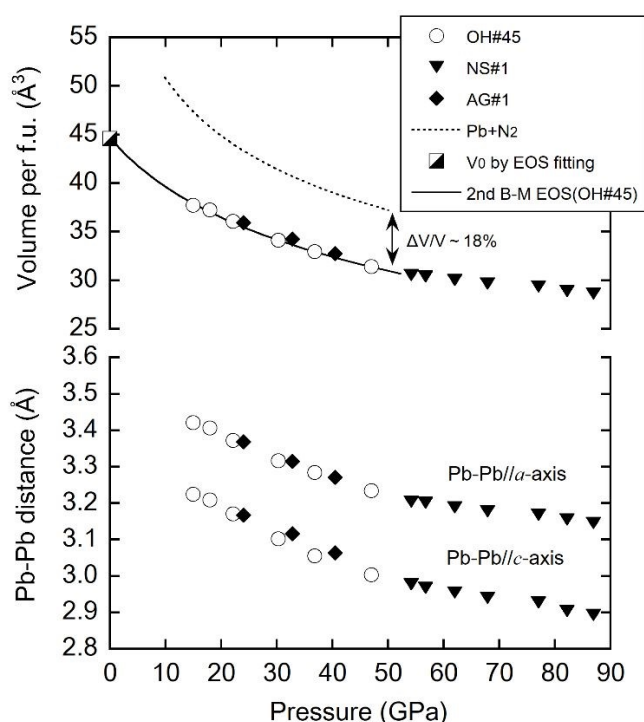


Fig.4 Pressure dependence of volume per formula unit and Pb-Pb distances. The bulk modulus volume at ambient pressure (half-filled square) was determined by fitting pressure-volume data for OH#45 to B-M EOS. The equimolar volume of Pb+N<sub>2</sub> is represented as a dashed line calculated from the reported P-V data for Pb and N<sub>2</sub>. The Pb-Pb distances parallel to the *a*- and *c*-axes correspond to the lattice parameters of the tetragonal Pb-lattice, respectively.

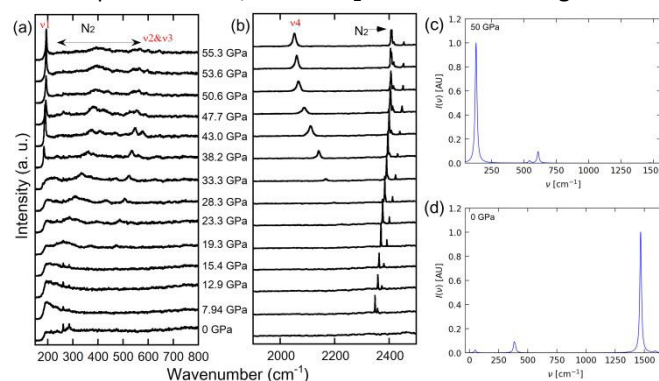


Fig.5 Pressure dependence of the measured (AG#2) and calculated Raman spectra. Two wavenumber regions are separately shown in (a) and (b). Newly appeared peaks are represented with  $\nu_i$  ( $i=1-4$ ). Wavenumber regions corresponding to the N<sub>2</sub> pressure medium are represented with horizontal arrows. Spiky peaks at low wavenumber regions at low pressures might be derived from the instruments or atmospheric species. Calculated Raman spectra of *I4/mcm* PbN<sub>2</sub> at 0 K (c) 50 GPa and (d) 0 GPa.



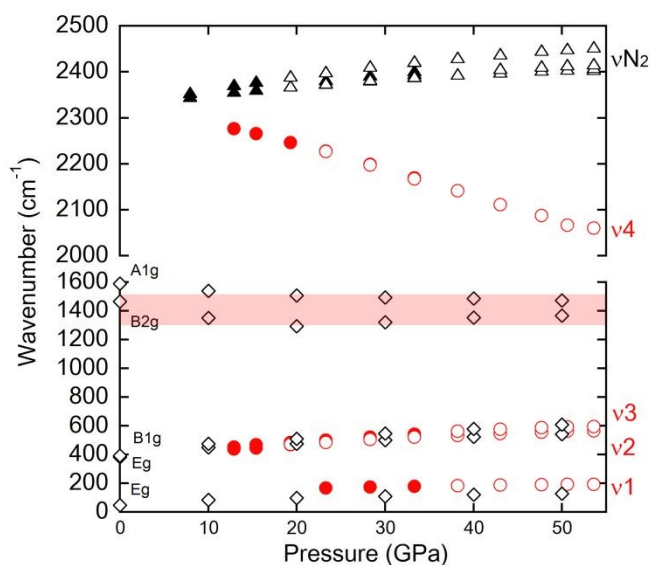


Fig.6 Pressure dependence of experimentally detected wavenumber (AG#2) together with wavenumbers of  $\text{PbN}_2$  obtained by DFT calculation. Open and solid circles correspond to the different positions (position 1 and position 2) on the same sample, respectively. The spectra of position 2 are shown in Fig.S7. Open and solid triangles correspond to the wavenumbers of nitrogen from the same positions. The open diamond represents the wavenumbers of  $\text{PbN}_2$  obtained by DFT calculation. The data are listed in Table S2. The Diamond-Raman band with the range of 1300-1500  $\text{cm}^{-1}$  is hatched.

an intense and sharp mode at 130  $\text{cm}^{-1}$  ( $E_g$ ), accompanied by lower intensity satellite modes at 543  $\text{cm}^{-1}$  ( $E_g$ ) and 609  $\text{cm}^{-1}$  ( $B_{1g}$ ).

As the pressure is reduced from 50 GPa to atmospheric pressure, the intensity of the  $E_g$  mode diminishes, and its wavenumber decreases from 130  $\text{cm}^{-1}$  to 49  $\text{cm}^{-1}$ . This behavior is in complete accordance with the experimental Raman spectra, as illustrated in Fig. 5, 6, S6, and S7. Conversely, the relative intensity of the  $B_{2g}$  mode is observed to increase with a decrease in pressure, becoming the most intense and sharp mode at atmospheric pressure. Moreover, a slight shift of this  $B_{2g}$  mode is observed when the pressure increases, from 1468  $\text{cm}^{-1}$  to 1369  $\text{cm}^{-1}$  at 0 and 50 GPa, respectively. It would be reasonable to posit that an increase in pressure would increase wavenumbers (and a concomitant decrease in lattice volume and bond lengths). However, the data indicate that this is not the case for both  $B_{2g}$  and  $A_{1g}$  modes, where the opposite effect is observed. In  $I4/mcm$   $\text{PbN}_2$ , the N-N bond length exhibits a slight but sensitive increase from 1.21 Å to 1.27 Å as the pressure rises from 0 to 100 GPa. This apparent anomaly in high-pressure chemistry can be attributed to the relative positioning of the 6s (Pb) level in relation to the antibonding NN  $\pi^*$  orbitals.<sup>47</sup> A 6s(Pb) band contribution is observed below the  $\pi^*$  ( $\text{N}_2$ ) levels at atmospheric pressure. In contrast, at 50 GPa, the 6s(Pb) band is above the vacant  $\pi^*$  ( $\text{N}_2$ ) levels. This alteration in electronic density is an unambiguous indication of

the oxidation of Pb in the  $I4/mcm$   $\text{PbN}_2$  as pressure increases (reduction when the applied external pressure tends to zero). Furthermore, this behavior can also account for the instability of  $\text{PbN}_2$  at atmospheric pressure, given that the  $\text{Pb}^{(2-6)+}$  oxidation state is not thermodynamically favorable. However, the calculated  $B_{2g}$  and  $A_{1g}$  Raman-active bands located in the 1300-1600  $\text{cm}^{-1}$  region are not visible in the experimental Raman spectra. This could be due to the essential technical problems of the DAC and the Raman band of approximately 1300-1500  $\text{cm}^{-1}$  region is masked by the Diamond-Raman band (see Fig. S8).

Moreover, the experimental band observed at around 2050  $\text{cm}^{-1}$  is absent in the theoretical Raman spectra of  $I4/mcm$   $\text{PbN}_2$  at 50 GPa. This band value is typically observed in activated  $\text{N}_2$  species with a bond order of 3 or slightly less.<sup>75</sup> This DFT study demonstrates unequivocally that the measured high wavenumber of 2000-2300  $\text{cm}^{-1}$  is not associated with the  $\text{CuAl}_2$ -type  $I4/mcm$   $\text{PbN}_2$ . To modelize the high wavenumbers (2000-2300  $\text{cm}^{-1}$ ) obtained from the samples, the need for a second model (or more) of the Pb-N system should be considered in which the  $\text{N}_2$  dimers undergo a minor activation process when mixing with electropositive metals. We propose two hypotheses in the following section.

The first one is that an increase in the  $\text{N}_2/\text{Pb}$  ratio will result in a reduction in the negative charge of each anionic  $\text{N}_2^{q-}$  dimer, thus the +2 |e| charge given by Pb would be shared by several  $\text{N}_2$  dimers, decreasing the negative charge of  $\text{N}_2^{q-}$  dimer. Fortunately, some of us recently showed that stable  $\text{Pb}(\text{N}_2)_z$  phases comprising several  $\text{N}_2$  dumbbells per unit cell emerge on the convex hull of the Pb-N system when the pressure increases.<sup>47</sup> We selected the nitrogen-rich  $R\text{-}3c$   $\text{Pb}(\text{N}_2)_3$  phase as a model of  $\text{N}_2$ -rich compounds for the investigation of its Raman spectra. Hexagonal  $R\text{-}3c$  has nine Raman-active modes with  $A_{1g}$  calculated at 2175  $\text{cm}^{-1}$  and  $E_g$  at 2041  $\text{cm}^{-1}$  at 50 GPa (2154 and 2023  $\text{cm}^{-1}$  at 10 GPa, respectively), as illustrated in Fig. S9. Nevertheless, the wavenumbers slightly increased up to 50 GPa. It can thus be concluded that the  $\text{N}_2$ -rich model in question,  $R\text{-}3c$   $\text{Pb}(\text{N}_2)_3$ , does not provide an adequate explanation of the experimental Raman spectra in the 2000-2300  $\text{cm}^{-1}$  region. To account for the observed increase in Raman bands at lower pressures, it is necessary, at least, to consider a decrease in the bond order of  $\text{N}_2$ , i.e. an increase in electron occupation of the antibonding  $\text{N}_2 \pi^*$  levels.<sup>47</sup> This phenomenon is not observed in  $R\text{-}3c$   $\text{Pb}(\text{N}_2)_3$  from 100 to 0 GPa, as in other high-pressure stable  $\text{Pb}(\text{N}_2)_z$  in Fig. S10, which depicts the evolution of N-N interatomic distances upon pressure.

The other hypothesis, among others, is in which  $\text{N}_2$  dimers are adsorbed on the crystallite surfaces of the samples. However, the DFT modeling of such  $\text{PbN}_2$  surfaces and  $\text{N}_2$  adsorption is beyond the scope of the present study. Further advanced study would find reasonable solutions for this issue, including ones other than mentioned above.

The present XRD, Raman measurements, and bonding analysis indicate a weak interaction between the Pb lattice and the nitrogen dimers at low pressure as evidenced by the decomposition of  $\text{PbN}_2$  into Pb and nitrogen molecules upon decompression. The recovered sample was characterized by





scanning electron microscopy equipped with energy-dispersive spectroscopy (see Fig.S11). The surface texture of the heated area was different from that of the unheated one and no nitrogen was detected anywhere. It is noteworthy that the CSP EA-DFT study indicated the ambient pressure recoverability of  $\text{PbN}_2$ ,  $\text{Pb}(\text{N}_2)_4$ , and  $\text{Pb}(\text{cyclo-N}_5)_2$  based on the phonon mode analysis and *ab initio* molecular dynamic simulations at atmospheric conditions compounds.<sup>47</sup> It is important to note that experimental metastability is dependent on several factors, including decompression speed, crystallinity, and other variables. Therefore, further rigorous experimentation with comprehensive analysis is essential to gain a deeper understanding of the Pb-N binary phase diagram under pressure.

To date, the  $\text{CuAl}_2$ -type structure was found for  $\text{TiN}_2$  and  $\text{VN}_2$  compounds, which can be synthesized at pressure exceeding 70 GPa.<sup>13,19</sup> The coordination number of cations in the  $\text{CuAl}_2$ -type structure is eight, which is greater than that of the six in the pyrite-type structure, as shown in Fig.S12. Considering the high-pressure phase transition analogy,<sup>35–40</sup> this result suggests that a phase transition from pyrite-type to  $\text{CuAl}_2$ -one may occur with increasing pressure. However,  $\text{FeS}_2$ , a prototype of the pyrite structure, was revealed to be stable up to 80 GPa and 2400 K.<sup>76</sup> For the high-pressure experiments on the intermetallic compound  $\text{CrSb}_2$ , the  $\text{CuAl}_2$ -type  $\text{CrSb}_2$  was synthesized above 5.5 GPa and 600°C, and the boundary between the low pressure phase of marcasite-type, which have a similar crystallographic aspect to pyrite-type, and high pressure phase with  $\text{CuAl}_2$ -type, was established.<sup>77</sup> These experimental results indicate that pyrite-type structure is stable under wide pressure and temperature, and it seems difficult to find the compounds that transform directly from pyrite- to  $\text{CuAl}_2$ -type structure, probably due to large rearrangement of atomic coordination including the increment of coordination number of cations through the transition. Even in the case of pernitrides, the recent advanced high-pressure study revealed that pyrite-type  $\text{SiN}_2$  does not undergo a phase transition to a denser phase up to 140 GPa.<sup>34</sup> As previously outlined, lead is a compressive element,<sup>56,57</sup> and the influence of pressure on the chemical bonding may be amplified, resulting in the synthesis of  $\text{PbN}_2$ , distinct from the pyrite-type group-14 pernitrides. Theoretical calculations have also indicated the potential for forming several new  $\text{Pb}(\text{N}_2)_x$  phases, contingent on the pressure.<sup>47</sup> The recent findings from both experiments and calculations have significantly advanced our understanding of the high-pressure crystal chemistry of group-14 pernitrides. However, there are still some unclear issues, indicating a need for further advanced experimental and theoretical approaches to gain a deeper understanding of pernitrides material science.

## Conclusions

The chemistry of the lead-nitrogen binary system was investigated under high pressure using a laser-heated diamond-anvil cell combined with synchrotron XRD measurements, Raman spectroscopy, and DFT modeling. A novel compound,  $\text{PbN}_2$ , was successfully synthesized above 50 GPa, and

crystallized in a tetragonal system having Pb atom bonded to 8N atoms and encapsulated anionic  $\text{N}_2$  dimers in  $\text{Pb}_8$  cages. Both experimental and DFT calculations analysis led to the  $\text{CuAl}_2$ -type crystal of  $\text{PbN}_2$  at 50 GPa. This differs from the pyrite-form other group-14 pernitrides ( $\text{SiN}_2$ ,  $\text{GeN}_2$ , and  $\text{SnN}_2$ ) that have been synthesized to date. This compound was found to remain stable up to 90 GPa at room temperature, however, it was unable to be recovered into ambient conditions. The presence of a Raman band at around 2000-2200  $\text{cm}^{-1}$  remains unexplained and requires further experimental and theoretical investigation. The newly synthesized  $\text{PbN}_2$  offers new insight into the high-pressure crystal chemistry of nitrogen rich compounds in terms of the interaction between nitrogen dimer and host-lattice.

## Author contributions

The manuscript was written through the contributions of all authors. All authors have approved the final version of the manuscript.

## Conflicts of interest

There are no conflicts to declare.

## Data availability

The data that support the findings of this study are available from the corresponding author upon reasonable request.

## Acknowledgements

This research was partially supported by JSPS KAKENHI (Grant Number 15H05542, 20K21080, 23K23039), and JST FOREST Program (JPMJFR213T). Synchrotron X-ray diffraction measurements were conducted at the BL2S1 of Aichi Synchrotron Radiation Center, Aichi Science & Technology Foundation, Aichi, Japan (Proposal Number 2016N1001, 2016N3001, 2019N4001, 2019N5011, 2023N3002, 2023N5002) with the financial and technical support of the Synchrotron Radiation Research Center, Nagoya University, and at the BL10XU SPring-8 (Proposal Number 2023B1301). This research was made possible by two grants from the French National Research Agency (ANR) for postdoctoral fellowships S.P. (PRC TcPredictor, PRC Hydroptere). This work was partially supported by the European Union (ERDF), and Région Nouvelle Aquitaine (France). We thank the PHC Sakura 2019 (MEAE/MESR France and Japon) for supporting this France-Japon collaborative research. The authors acknowledge the High-Performance Computing Centers (HPC) of Irène/TGCC, and Jean Zay/IDRIS of GENCI (France) under projects no. A0140807539 and A0160815101 and "Grand Challenge 2023 TGCC" Session A14 spe00040 for generous allocations of computing time.

## References





## ARTICLE

## Journal Name

- 1 L. Zhang, Y. Wang, J. Lv and Y. Ma, *Nat Rev Mater*, 2017, **2**, 17005.
- 2 H. B. Elisabeta, R. Riedel, A. Zerr, P. F. Mc Millan, G. Auffermann, Y. Prots, W. Bronger, R. Kniep and P. Kroll, *Chem Soc Rev*, 2006, **35**, 987–1014.
- 3 A. Zerr, R. Riedel, T. Sekine, J. E. Lowther, W. Y. Ching and I. Tanaka, *Advanced Materials*, 2006, **18**, 2933–2948.
- 4 M. Rivers, V. Prakapenka, A. Kubo, C. Pullins, C. Holl and S. Jacobsen, *High Press Res*, 2008, **28**, 273–292.
- 5 G. Shen and H. K. Mao, *Reports on Progress in Physics*, 2017, **80**, 016101.
- 6 A. Zerr, G. Miehe, G. Serghiou, M. Schwarz, E. Kroke, R. Riedel, H. Fueß, P. Kroll and R. Boehler, *Nature*, 1999, **400**, 340–342.
- 7 J. C. Crowhurst, A. F. Goncharov, B. Sadigh, C. L. Evans, P. G. Morrall, J. L. Ferreira and A. J. Nelson, *Science (1979)*, 2006, **311**, 1275–1278.
- 8 E. Gregoryanz, C. Sanloup, M. Somayazulu, J. Badro, G. Fiquet, H. K. Mao and R. J. Hemley, *Nat Mater*, 2004, **3**, 294–297.
- 9 A. F. Young, C. Sanloup, E. Gregoryanz, S. Scandolo, R. J. Hemley and H. Mao, *Phys Rev Lett*, 2006, **96**, 155501.
- 10 J. A. Montoya, A. D. Hernandez, C. Sanloup, E. Gregoryanz and S. Scandolo, *Appl Phys Lett*, 2007, **90**, 011909.
- 11 J. C. Crowhurst, A. F. Goncharov, B. Sadigh, J. M. Zaug, D. Aberg, Y. Meng and V. B. Prakapenka, *J Mater Res*, 2008, **23**, 1–5.
- 12 W. P. Clark, S. Steinberg, R. Dronskowski, C. McCammon, I. Kuppenko, M. Bykov, L. Dubrovinsky, L. G. Akselrud, U. Schwarz and R. Niewa, *Angewandte Chemie - International Edition*, 2017, **56**, 7302–7306.
- 13 S. Asano, K. Niwa, T. Sasaki, N. A. Gaida and M. Hasegawa, *Dalton Transactions*, 2022, **51**, 2656–2659.
- 14 M. Bykov, E. Bykova, E. Koemets, T. Fedotenko, G. Aprilis, K. Glazyrin, H. Liermann, A. V. Ponomareva, J. Tidholm, F. Tasn, I. A. Abrikosov, N. Dubrovinskaia and L. Dubrovinsky, *Angew.Chem. Int. Ed.*, 2018, **57**, 9048–9053.
- 15 K. Niwa, T. Terabe, D. Kato, S. Takayama, M. Kato, K. Soda and M. Hasegawa, *Inorg Chem*, 2017, **56**, 6410–6418.
- 16 D. Laniel, A. Dewaele, S. Anzellini and N. Guignot, *J Alloys Compd*, 2018, **733**, 53–58.
- 17 M. Bykov, E. Bykova, G. Aprilis, K. Glazyrin, E. Koemets, I. Chuvashova, I. Kuppenko, C. McCammon, M. Mezouar, V. Prakapenka, H.-P. Liermann, F. Tasnádi, A. V. Ponomareva, I. A. Abrikosov, N. Dubrovinskaia and L. Dubrovinsky, *Nat Commun*, 2018, **9**, 2756.
- 18 M. Bykov, S. Chariton, E. Bykova, S. Khandarkhaeva, T. Fedotenko, A. V. Ponomareva, J. Tidholm, F. Tasnádi, I. A. Abrikosov, P. Sedmak, V. Prakapenka, M. Hanfland, H. P. Liermann, M. Mahmood, A. F. Goncharov, N. Dubrovinskaia and L. Dubrovinsky, *Angewandte Chemie - International Edition*, 2020, **59**, 10321–10326.
- 19 V. S. Bhadram, D. Y. Kim and T. A. Strobel, *Chemistry of Materials*, 2016, **28**, 1616–1620.
- 20 K. Glazyrin, A. Aslandukov, A. Aslandukova, T. Fedotenko, S. Khandarkhaeva, D. Laniel, M. Bykov and L. Dubrovinsky, *Front Chem*, 2023, **11**, 10.3389/fchem.2023.1257942.
- 21 M. Ceppatelli, M. Serrano-Ruiz, M. Morana, K. Dziubek, D. Scelta, G. Garbarino, T. Poręba, M. Mezouar, R. Bini and M. Peruzzini, *Angewandte Chemie International Edition*, 2024, **63**, e202319278.



- 22 M. Ceppatelli, D. Scelta, M. Serrano-Ruiz, K. Dziubek, M. Morana, V. Svitlyk, G. Garbarino, T. Poręba, M. Mezouar, M. Peruzzini and R. Bini, *Angewandte Chemie International Edition*, 2022, **61**, e202114191.
- 23 K. Landskron, H. Huppertz, J. Senker and W. Schnick, *Angewandte Chemie - International Edition*, 2001, **40**, 2643–2645.
- 24 L. Brüning, N. Jena, E. Bykova, P. L. Jurzick, N. T. Flosbach, M. Mezouar, M. Hanfland, N. Giordano, T. Fedotenko, B. Winkler, I. A. Abrikosov and M. Bykov, *Angewandte Chemie - International Edition*, 2023, **62**, e202311519.
- 25 F. L. Riley, *Journal of the American Ceramic Society*, 2000, **83**, 245–265.
- 26 P. Yang, H. K. Fun, I. A. Rahman and M. I. Saleh, *Ceram Int*, 1995, **21**, 137–142.
- 27 H. L. Kornberg and H. A. Krebs, *Nature*, 1957, **180**, 756–757.
- 28 P. Popper and S. N. Ruddlesden, *Nature*, 1957, **179**, 1129.
- 29 S. N. Ruddlesden and P. Popper, *Acta Crystallogr*, 1958, **11**, 465–468.
- 30 G. Serghiou, G. Miehe, R. Boehler, O. Tschauner and A. Zerr, *J Chem Phys*, 2002, **111**, 4659–4662.
- 31 N. Scotti, W. Kockelmann and J. Senker, Z. *Anorg. Allg. Chem.*, 1999, **624**, 1435–1439.
- 32 M. P. Shemkunas, G. H. Wolf, K. Leinenweber and W. T. Petuskey, *Journal of the American Ceramic Society*, 2002, **85**, 101–104.
- 33 K. Niwa, H. Ogasawara and M. Hasegawa, *Dalton Transactions*, 2017, **46**, 9750–9754.
- 34 P. L. Jurzick, G. Krach, L. Brüning, W. Schnick and M. Bykov, *Acta Crystallogr E Crystallogr Commun*, 2023, **79**, 923–925.
- 35 E. C. T. Chao, J. J. Fahey and J. Littler, *J Geophys Res*, 1962, **67**, 419–421. DOI: 10.1039/D5TA01488C
- 36 L. C. Ming and M. H. Manghnani, *Physics of the Earth and Planetary Interiors*, 1983, **33**, 26–30.
- 37 J. Haines and J. M. Léger, *Phys Rev B*, 1997, **55**, 11144–11154.
- 38 J. Haines, J. M. Leger and O. Schulte, *Journal of Physics Condensed Matter*, 1996, **8**, 1631–1646.
- 39 J. Haines, J. M. Léger and O. Schulte, *Science (1979)*, 1996, **271**, 629–631.
- 40 Y. Kuwayama, K. Hirose, N. Sata and Y. Ohishi, *Science (1979)*, 2005, **309**, 923–925.
- 41 Th. Curtius, *Berichte der deutschen chemischen Gesellschaft*, 1891, **24**, 3341–3349.
- 42 M. Frank Douglas, *J Chem Soc*, 1931, 2532–2542.
- 43 L. V. AzÁroff, *Zeitschrift für Kristallographie*, 1956, **107**, 362–369.
- 44 Y. Kuroiwa, S. Aoyagi, A. Sawada, J. Harada, E. Nishibori, M. Takata and M. Sakata, *Phys Rev Lett*, 2001, **87**, 217601.
- 45 R. V. Shpanchenko, V. V. Chernaya, A. A. Tsirlin, P. S. Chizhov, D. E. Sklovsky, E. V. Antipov, E. P. Khlybov, V. Pomjakushin, A. M. Balagurov, J. E. Medvedeva, E. E. Kaul and C. Geibel, *Chemistry of Materials*, 2004, **16**, 3267–3273.
- 46 A. A. Belik, M. Azuma, T. Saito, Y. Shimakawa and M. Takano, *Chemistry of Materials*, 2005, **17**, 269–273.
- 47 S. Pitié, K. Niwa and G. Frapper, *The Journal of Physical Chemistry C*, 2024, **128**, 19410–19422.
- 48 N. Watanabe, T. Nagae, Y. Yamada, A. Tomita, N. Matsugaki and M. Tabuchi, *J Synchrotron Radiat*, 2017, **24**, 338–343.



## ARTICLE

## Journal Name

- 49 S. Kawaguchi-Imada, R. Sinmyo, K. Ohta, S. Kawaguchi and T. Kobayashi, *J Synchrotron Radiat*, 2024, **31**, 343–354.
- 50 Y. SETO, D. NISHIO-HAMANE, T. NAGAI and N. SATA, *The Review of High Pressure Science and Technology*, 2010, **20**, 269–276.
- 51 A. Boultif and D. Loue, *J Appl Crystallogr*, 2004, **37**, 724–731.
- 52 F. Izumi and K. Momma, *Solid State Phenomena*, 2007, **130**, 15–20.
- 53 H. K. Mao, J. Xu and P. M. Bell, *J Geophys Res*, 1986, **91**, 4673.
- 54 C. S. Zha, W. A. Bassett and S. H. Shim, *Review of Scientific Instruments*, 2004, **75**, 2409–2418.
- 55 H. Olijnyk, *J Chem Phys*, 1990, **93**, 8968–8972.
- 56 T. Takahashi, H. K. Mao and W. A. Bassett, *Science (1979)*, 1969, **165**, 1352–1353.
- 57 H. K. Mao, Y. Wu, J. F. Shu, J. Z. Hu, R. J. Hemley and D. E. Cox, *Solid State Commun*, 1990, **74**, 1027–1029.
- 58 S. J. Clark, M. D. Segall, C. J. Pickard, P. J. Hasnip, M. I. J. Probert, K. Refson and M. C. Payne, *Z Kristallogr Cryst Mater*, 2005, **220**, 567–570.
- 59 J. P. Perdew, K. Burke and M. Ernzerhof, *Phys Rev Lett*, 1996, **77**, 3865–3868.
- 60 J. P. Perdew, K. Burke and M. Ernzerhof, *Phys Rev Lett*, 1997, **78**, 1396–1396.
- 61 G. Kresse and J. Furthmüller, *Phys Rev B*, 1996, **54**, 11169–11186.
- 62 G. Kresse and J. Furthmüller, *Comput Mater Sci*, 1996, **6**, 15–50.
- 63 A. Togo, *J Physical Soc Japan*, 2023, **92**, 012001.
- 64 A. Togo, L. Chaput, T. Tadano and I. Tanaka, *Journal of Physics: Condensed Matter*, 2023, **35**, 353001. DOI: 10.1039/D5TA01488C
- 65 J. M. Skelton, L. A. Burton, A. J. Jackson, F. Oba, S. C. Parker and A. Walsh, *Physical Chemistry Chemical Physics*, 2017, **19**, 12452–12465.
- 66 <https://github.com/skelton-group/Phonopy-Spectroscopy>.
- 67 E. Bykova, *Doctoral thesis, University of Bayreuth*, 2015, 1.
- 68 L. Palatinus and G. Chapuis, *J Appl Crystallogr*, 2007, **40**, 786–790.
- 69 Ralph W. G. Wyckoff, *Crystal Structures*, Second., 1963, vol. 1.
- 70 K. Momma and F. Izumi, *J Appl Crystallogr*, 2011, **44**, 1272–1276.
- 71 M. I. Eremets, A. G. Gavriluk, I. A. Trojan, D. A. Dzivenko and R. Boehler, *Nat Mater*, 2004, **3**, 558–563.
- 72 G. V Vajenine, G. Auffermann, Y. Prots, W. Schnelle, R. K. Kremer, A. Simon and R. Ildiger Kniep, *Inorg Chem*, 2001, **40**, 4866–4870.
- 73 S. B. Schneider, R. Frankovsky and W. Schnick, *Inorg Chem*, 2012, **51**, 2366–2373.
- 74 M. E. Fieser, D. H. Woen, J. F. Corbey, T. J. Mueller, J. W. Ziller and W. J. Evans, *Dalton Transactions*, 2016, **45**, 14634–14644.
- 75 H. Schneider, W. Hiifner, A. Wokaun and H. Olijnyk, *Journal of Chemical Physics*, 1992, **96**, 8046–8053.
- 76 E. C. Thompson, B. A. Chidester, R. A. Fischer, G. I. Myers, D. L. Heinz, V. B. Prakapenka and A. J. Campbell, *American Mineralogist*, 2016, **101**, 1046–1051.
- 77 H. Takizawa, K. Uheda and T. Endo, *J Alloys Compd*, 1999, **287**, 145–149.



Open Access Article. Published on 23 May 2025. Downloaded on 6/1/2025 4:26:51 AM.  
This article is licensed under a Creative Commons Attribution-NonCommercial 3.0 Unported Licence.





## Data Availability Statement

The data that support the findings of this study are available from the corresponding author upon reasonable request and the data supporting this article have been included as part of the Supplementary Information.

Ken NIWA

Research Center for Crystalline Materials Engineering

Department of Materials Physics

Nagoya University

Furo-cho, Chikusa-ku, Nagoya

Aichi 464-8603, Japan

TEL:+81-52-789-5515

FAX:+81-52-789-3252

E-mail:niwa@mp.pse.nagoya-u.ac.jp

