

Nanoscale

Accepted Manuscript




This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

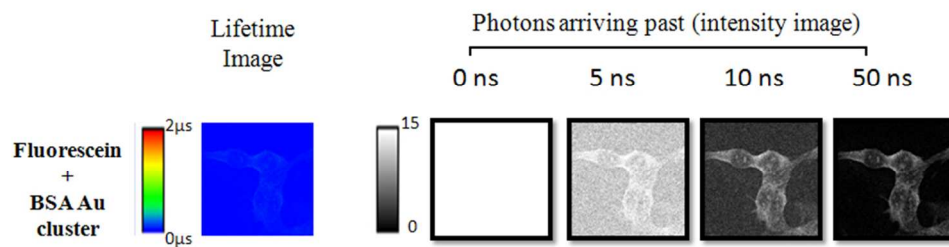

Fluorescence lifetime and time gated intensity images of BSA Au clusters treated cells and fluorescein was added as high intensity artificial background.
143x36mm (150 x 150 DPI)

COMMUNICATION

Long Lived BSA Au Clusters as a Time Gated Intensity Imaging Probe

Cite this: DOI: 10.1039/x0xx00000x

S. L. Raut,^a R. Fudala,^a R. Rich,^a R.A. Kokate,^a R. Chib,^a Z. Gryczynski,^{a,b} and I. Gryczynski^a

Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

The work presented here reports the use of long lifetime (>1 μs) BSA Au clusters as a cellular/tissue, time gated, intensity imaging probe. By collecting the emission signal 50 ns post excitation, one can off-gate the intense auto-fluorescence background, thereby greatly enhancing the clarity/specificity in fluorescence imaging.

Introduction

Near infrared (NIR) imaging is one of the most widespread optical imaging techniques in biomedical sciences. Fluorescence imaging modalities, particularly NIR fluorescence imaging, has several advantages over other imaging techniques, such as sensitivity and multiplex detection capabilities. Current NIR imaging heavily relies upon NIR organic dyes. Utilizing organic dyes remains problematic due to several reasons such as rapid photo-bleaching, small Stokes shift between excitation and emission, and partial spectral overlap with auto-fluorescence. Moreover, organic fluorophores have their fluorescence lifetimes in the range of 1-5 ns, close to auto-fluorescence lifetime, making it difficult to separate the emission signal of the fluorophore from the auto-fluorescence of the cell. Auto-fluorescence from biological samples is one of the biggest hurdles in fluorescence experiments. It is not only difficult to separate the auto-fluorescence from the organic dye spectrally, but temporally as well, since the lifetime of auto-fluorescence is similar to the lifetime of routinely used organic fluorophores (fluorescein and rhodamine). Rich et al., in their recent report, explained different methods to overcome issues with auto-fluorescence and the disadvantages associated with them, by showing how a long fluorescence lifetime organic dye can be used to remove auto-fluorescence background¹. Hence, there is a fundamental need to develop new imaging probes for emission intensity and lifetime imaging applications.

With rapid growth and development in biomedical nanotechnology, synthesis and development of luminescent nanomaterials is gaining increasing attention among the scientific community²⁻⁴. Despite the superior optical properties of quantum dots, they are of limited use due to several disadvantages. First, quantum dots emitting in visible region tend to overlap with the auto-fluorescence spectra. Second, quantum dots with NIR emission are large in size and can introduce perturbations in the targeted cell. Third, toxicity due to toxic core materials used in synthesis further limits its usage^{5,6}. Lastly, despite good photo stability, quantum dots show photo-blinking which affects the emission signal during imaging. Recently, a newer class of nanobio probe protein protected metal nanoclusters has gained increasing attention due to reasonably strong and tunable fluorescence in visible and NIR region. Proteins with differing molecular weight and amino acid sequences have been used to synthesize these metal nanoclusters. Namely, bovine serum albumin (BSA), human serum albumin (HSA), lysozyme, trypsin and the ferritin family of proteins have been used to synthesize metal nanoclusters⁷⁻¹¹. Among these BSA Au clusters appear to be most researched preparation due to its optical properties¹²⁻¹⁷ and biosensing applications^{7,18-21}.

We are interested in cellular imaging applications of these BSA Au nanoclusters. There are several reports mentioning the use of BSA Au clusters as emission intensity based imaging probes. Koyakutty et al. showed that folic acid conjugated BSA Au clusters can internalize into oral and breast cancer cells through interaction with folate receptor²². Koyakutty et al., in another report, showed that BSA Au clusters conjugated with antibodies against CD33 myeloid antigen, were specifically taken up by leukemia cells over expressing CD33 myeloid antigens thus enabling their use in targeted flow cytometry and imaging of cancer cells²³. Chen et al. simultaneously conjugated folic acid and doxorubicin to BSA Au nanoclusters and used them for in vivo tracking and cancer therapy²⁴. Methionine

conjugated BSA Au clusters were also used similarly as doxorubicin conjugated BSA Au clusters to treat and image cancer cells in vivo²⁵. Irudayaraj et al. conjugated BSA Au clusters with Herceptin to show that it can be used simultaneously as an imaging and treatment modality²⁶.

Thermo Scientific) against de-ionized water for at least 12 hr with periodic change of water to remove any small impurities. The dialyzed cluster solution was filtered using a 0.02 μm syringe filter and then used for subsequent measurements.

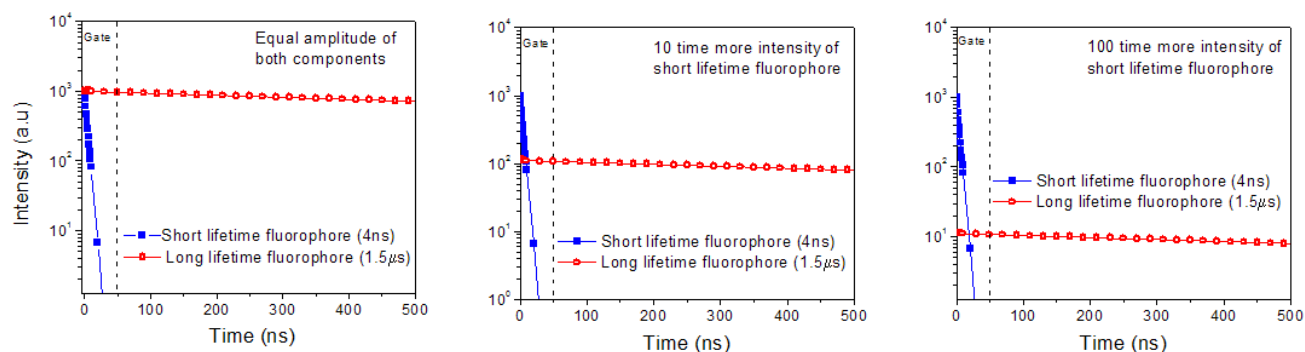


Figure 1: Simulated fluorescence intensity decays (assuming single exponential decay) of representative short lifetime fluorophore and long lifetime fluorophore at different situations. Equal intensity (left panel), 10 times (middle panel) and 100 times (right panel) more intensity of short lifetime fluorophore than long lifetime probe.

Furthermore, Qing et al. reported the use of BSA Au clusters for in vivo imaging of mice tumor xenograft models and showed that BSA Au clusters accumulate in the tumor through enhanced permeability and retention (EPR) effect²⁷.

Despite the numerous reports on the use of BSA Au clusters as an imaging probe due to its emission intensity, there are no reports on its use as a fluorescence lifetime and time gated intensity imaging probe to the best of our knowledge. There are several publications reporting the microsecond lifetime of BSA Au clusters^{14, 16, 28}. This long lifetime is several hundred fold longer than the auto-fluorescence lifetime (~ 7 ns)^{29, 30} and can be effectively used to off-gate cellular auto-fluorescence by time gated imaging. The approach, referred to as “time gating”, entails discarding all detected photons after each excitation pulse until the point where the background (auto-fluorescence) has decayed completely and the probe continues to fluoresce. Herein we report a strategy utilizing the long fluorescence lifetime of BSA Au cluster as a fluorescence lifetime and time gated intensity imaging probe.

Experimental Section

Materials

Chloroauric acid (HAuCl_4), bovine serum albumin, fraction V (BSA) and acetone (reagent grade) were purchased from Sigma Aldrich Co. LLC. RPMI 1640 medium supplemented with 10% fetal bovine serum (FBS) and 1% penicillin-streptomycin (Pen-strep), and EDTA were purchased from Gibco, Life Technologies.

Synthesis of BSA Au clusters

The Au nanoclusters used in this study were synthesized using an approach developed by Xie et al.¹¹. Typically, 5 mL of 10 mM HAuCl_4 was mixed with 5 mL of 50 mg/mL BSA and incubated overnight at 37°C. The light brown cluster solution was further dialyzed (2000 MWCO membrane, Slide-A-lyzer, dialysis cassette,

Cellular staining

4T1 murine mammary carcinoma cell line obtained from American Type Culture Collection (ATCC), Manassas, VA, USA was grown to seventy percent confluence in RPMI supplemented with 10% FBS and 1% Pen-Strep. Cells were trypsinized using 0.25 % Trypsin-EDTA and seeded on 20 mm round glass cover slips. After 24 hrs, cells were fixed using cold acetone (reagent grade-Sigma Aldrich)

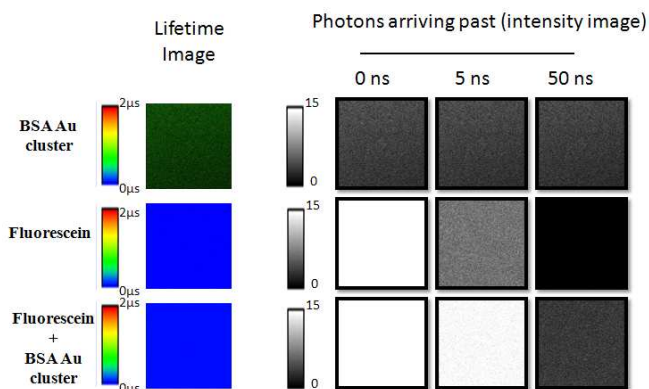


Figure 2: Fluorescence lifetime and time gated intensity images of BSA Au cluster, Fluorescein and mixture of BSA Au cluster with fluorescein prepared on glass cover slips.

for 10 min at 4 °C followed by blocking with 1% BSA solution for 15-20 min at room temperature. Cells were washed with PBS and incubated with BSA Au clusters (5 μM) and fluorescein (0.2 μM) for 60 min and rinsed with PBS. The cluster loaded cells on the cover-slips were air dried and mounted on 24X24 mm cover glass using ProLong® Gold Antifade Reagent and stored at 4°C for fluorescence lifetime imaging experiments.

Lifetime and time gated imaging

Laser excitation was provided by a pulsed laser diode (PDL-470) emitting 470 nm light and driven by a PDL 828 “Sepia II” driver. This driver was operated at 315 KHz. Measurements were performed on a MicroTime 200 time-resolved, confocal microscope by PicoQuant. The excitation and emission light was focused by a 60X 1.2 NA Olympus objective in an Olympus IX71 microscope, and the emission light was filtered by a 488 long wave pass filter before passing through a 50 μm pinhole. Detection was made by a hybrid photomultiplier assembly. The resolution of the time correlated single photon counting (TCSPC) module was set to 512 ps/bin in order to facilitate the detection of the long-lived dye, producing a measurement window around 1.2 μs in length. All data analysis was performed using the SymPhoTime software, version 5.3.2. All experimental equipment and the SymPhoTime software were provided by PicoQuant, GmbH as part of the MicroTime 200 system.

Results and discussion

In cellular imaging using fluorescence intensity, the contribution from light scattering and sample auto-fluorescence imparts large background signal to all images. Fluorescence lifetime imaging microscopy (FLIM) offers two big advantages, namely the separation of fluorescence emission not only in the energy/color scale but also in time. FLIM can not only be used to image/measure lifetimes of the individual fluorophores due to environmental effects, but can also be used to differentiate between distinct fluorophores of the same color that stain different parts of the cell. The obstacle for FLIM has been the available dyes. Today, all common, bright dyes have lifetimes in the range of 0.2-5 ns making it difficult to distinguish two dyes from each other³¹⁻³³. One of the strengths of

photons past 50 ns of the excitation pulse owing to the complete decay of short lifetime background. It is evident that the addition of long lived BSA Au clusters opens up the entire lifetime spectrum in FLIM and time gated imaging, allowing multiple probes to be detected in the same color channel. We tested our hypothesis by placing a drop of each of the three samples on a glass cover slip: BSA Au clusters, fluorescein and a mixture of fluorescein and BSA Au clusters. Lifetime images and intensity images at 5 and 50 ns post excitation pulse were acquired for all the three samples. Figure 2 shows the results of this measurement. The top panel depicting BSA Au clusters shows that even after 50 ns post excitation, we did not lose much of the emission signal. The fluorescein only sample (middle panel), on the other hand, shows reduced intensity after 5 ns gating and complete signal depletion after 50 ns gate. Furthermore, a mixture of fluorescein and BSA Au cluster in the lower panel shows strong signal from fluorescein even after gating for 5 ns. However, the 50 ns gate completely removed the fluorescein signal and BSA Au clusters' emission dominated the signal intensity. This suggests that BSA Au clusters can be used to probe the systems with enormously high background samples.

To demonstrate the applicability in a biological setting, a comparative study was initiated using fluorescein to mimic background fluorescence of enormous intensity, a situation far worse than is likely to be experienced with real life biological samples (worst case scenario). The long lived nanoclusters, in this case BSA Au clusters, could give a signal significant enough to be distinguished from the fluorescein background. It can be concluded that with gated imaging, suppressing all background is possible using this novel dye. The results of this experiment are shown in figure 3. First the fluorescence lifetime image is shown, followed by

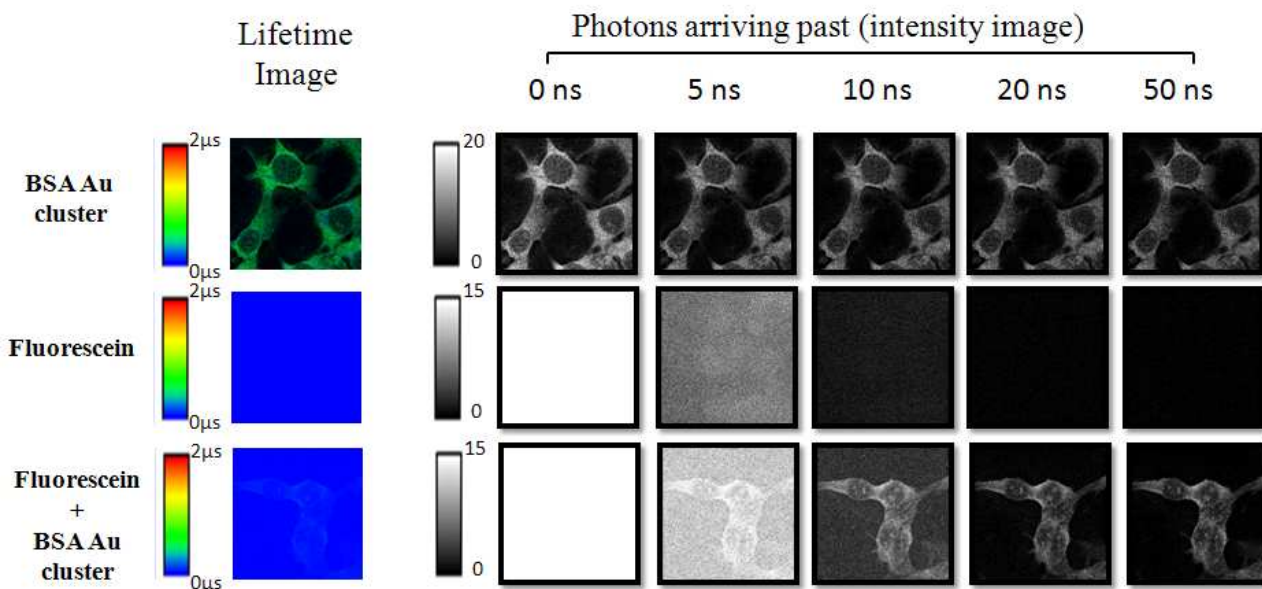


Figure 3 : Fluorescence lifetime and time gated intensity images of BSA Au cluster, Fluorescein and mixture of BSA Au cluster and fluorescein treated breast cancer cell line (4T1) mounted on glass slide.

the BSA Au clusters is its very long fluorescence lifetime that enables us to suppress the background signal using gated detection. Figure 1 shows the simulated fluorescence intensity decays (at 1:1, 10:1 and 100:1 intensity ratio of a short to a long lifetime fluorophore) of typical fluorophores with lifetime 4 ns and BSA Au cluster (long lifetime fluorophore, 1.5 μs). It is visible that even with 10 times and 100 times brighter background one can collect the photons/signal coming from BSA Au clusters, if we collect the

a series of images showing the intensity of emission collected after 5 different delay times. The important information gained from the images of individual dyes is that no fluorescein emission is observed after 20 ns; however the BSA Au clusters are still bright enough. More importantly/significantly, the difference between the dyes is very clear in the cells stained with both dyes. Here the intensity of BSA Au clusters dominates after 10 ns and it is the only type present after 20 ns. The important finding is that with just the addition of a

short gating time, the background suppression is clearly visible using these long lifetime BSA Au clusters, making their use very attractive in the biological sample fluorescence imaging.

Conclusions

We have shown that BSA Au clusters can be potentially used as novel fluorescent probe to stain cells. BSA Au clusters can be used as a cellular stain, advancing the bioimaging technology via their long fluorescence lifetime. BSA Au clusters allows for application in FLIM and time gated detection to visualize the stained parts of cells with close to zero background.

Acknowledgements

This work was supported by the NIH grant R01EB12003 (Z.G) and NSF grant CBET-1264608(I.G). S.L.R and R.F have contributed equally to this work. We would like to thank Smrithi Rajendiran for proofreading the manuscript.

Notes and references

^a Center for Commercialization of Fluorescence Technologies, Department of Cell Biology and Immunology, University of North Texas Health Science Center, 3500 Camp Bowie Blvd. Fort Worth, Texas, USA, 76107.

^b Department of Physics, Texas Christian University, 2800 S. University Dr., Fort Worth, Texas, USA, 76129.

*Corresponding Authors

SR (sraut@live.unthsc.edu) and IG (Ignacy.gryczynski@unthsc.edu)

† Footnotes should appear here. These might include comments relevant to but not central to the matter under discussion, limited experimental and spectral data, and crystallographic data.

Electronic Supplementary Information (ESI) available: [details of any supplementary information available should be included here]. See DOI: 10.1039/c000000x/

1. R. M. Rich, M. Mummert, Z. Gryczynski, J. Borejdo, T. J. Sorensen, B. W. Laursen, Z. Foldes-Papp, I. Gryczynski and R. Fudala, *Anal. Bioanal. Chem.*, 2013, **405**, 4887-4894.
2. D. K. Chatterjee, M. K. Gnanasammandhan and Y. Zhang, *Small*, 2010, **6**, 2781-2795.
3. S. N. Baker and G. A. Baker, *Angewandte Chemie International Edition*, 2010, **49**, 6726-6744.
4. M. Baker, *Nature Methods*, 2010, **7**, 957-962.
5. T. S. Hauck, R. E. Anderson, H. C. Fischer, S. Newbigging and W. C. Chan, *Small*, 2010, **6**, 138-144.
6. A. M. Derfus, W. C. Chan and S. N. Bhatia, *Nano Letters*, 2004, **4**, 11-18.
7. L. Hu, S. Han, S. Parveen, Y. Yuan, L. Zhang and G. Xu, *Biosens. Bioelectron.*, 2012, **32**, 297-299.
8. X. Le Guevel, N. Daum and M. Schneider, *Nanotechnology*, 2011, **22**, 275103.
9. T. Zhou, Y. Huang, W. Li, Z. Cai, F. Luo, C. J. Yang and X. Chen, *Nanoscale*, 2012, **4**, 5312-5315.
10. T. H. Chen and W. L. Tseng, *Small*, 2012, **8**, 1912-1919.
11. J. Xie, Y. Zheng and J. Y. Ying, *J. Am. Chem. Soc.*, 2009, **131**, 888-889.
12. I. Sakanaga, M. Inada, T. Saitoh, H. Kawasaki, Y. Iwasaki, T. Yamada, I. Umezumi and A. Sugimura, *Applied Physics Express*, 2011, **4**, 5001.
13. Z. Wu and R. Jin, *Nano Lett.*, 2010, **10**, 2568-2573.
14. X. Wen, P. Yu, Y. Toh and J. Tang, *The Journal of Physical Chemistry C*, 2012, **116**, 11830-11836.
15. X. Wen, P. Yu, Y. Toh, A. Hsu, Y. Lee and J. Tang, *The Journal of Physical Chemistry C*, 2012, **116**, 19032-19038.

16. S. Raut, R. Chib, R. M. Rich, D. Shumilov, Z. Gryczynski and I. Gryczynski, *Nanoscale*, 2013, .
17. M. Zhu, C. M. Aikens, F. J. Hollander, G. C. Schatz and R. Jin, *J. Am. Chem. Soc.*, 2008, **130**, 5883-5885.
18. X. X. Wang, Q. Wu, Z. Shan and Q. M. Huang, *Biosens. Bioelectron.*, 2011, **26**, 3614-3619.
19. Z. Chen, S. Qian, J. Chen, J. Cai, S. Wu and Z. Cai, *Talanta*, 2012, **94**, 240-245.
20. Z. Chen, S. Qian, X. Chen, W. Gao and Y. Lin, *Analyst*, 2012, **137**, 4356-4361.
21. C. V. Durgadas, C. P. Sharma and K. Sreenivasan, *Analyst*, 2011, **136**, 933-940.
22. A. Retnakumari, S. Setua, D. Menon, P. Ravindran, H. Muhammed, T. Pradeep, S. Nair and M. Koyakutty, *Nanotechnology*, 2010, **21**, 055103.
23. A. Retnakumari, J. Jayasimhan, P. Chandran, D. Menon, S. Nair, U. Mony and M. Koyakutty, *Nanotechnology*, 2011, **22**, 285102.
24. H. Chen, S. Li, B. Li, X. Ren, S. Li, D. M. Mahounga, S. Cui, Y. Gu and S. Achilefu, *Nanoscale*, 2012, **4**, 6050-6064.
25. H. Chen, B. Li, X. Ren, S. Li, Y. Ma, S. Cui and Y. Gu, *Biomaterials*, 2012, .
26. Y. Wang, J. Chen and J. Irudayaraj, *ACS Nano*, 2011, **5**, 9718-9725.
27. X. Wu, X. He, K. Wang, C. Xie, B. Zhou and Z. Qing, *Nanoscale*, 2010, **2**, 2244-2249.
28. C. Li, J. U. Sutter, D. Birch and Y. Chen, 2012, 1-4.
29. W. Becker, *J. Microsc.*, 2012, **247**, 119-136.
30. H. Schneckenburger, M. Wagner, P. Weber, W. S. Strauss and R. Sailer, *J. Fluoresc.*, 2004, **14**, 649-654.
31. M. Sauer, K. Han, R. Müller, S. Nord, A. Schulz, S. Seeger, J. Wolfrum, J. Arden-Jacob, G. Deltau and N. Marx, *J. Fluoresc.*, 1995, **5**, 247-261.
32. J. E. Berlier, A. Rothe, G. Buller, J. Bradford, D. R. Gray, B. J. Filanoski, W. G. Telford, S. Yue, J. Liu and C. Cheung, *Journal of Histochemistry & Cytochemistry*, 2003, **51**, 1699-1712.
33. N. Panchuk-Voloshina, R. P. Haugland, J. Bishop-Stewart, M. K. Bhalgat, P. J. Millard, F. Mao, W. Leung and R. P. Haugland, *Journal of Histochemistry & Cytochemistry*, 1999, **47**, 1179-1188.