

ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

COMMUNICATION

Cite this: DOI: 10.1039/x0xx00000x

Biocatalytic amide condensation and gelation controlled by light

Received 00th January 2013,
Accepted 00th January 2013

DOI: 10.1039/x0xx00000x

Jugal Kishore Sahoo^a, Siva Krishna Mohan Nalluri^a, Nadeem Javid^a, Hannah Webb^a,
Rein V. Ulijn^{a*}

www.rsc.org/Chemcomm


We report on a supramolecular self-assembly system that displays coupled light switching, biocatalytic condensation/hydrolysis and gelation. The equilibrium state of this system can be regulated by light, favouring *in situ* formation, by protease catalysed peptide synthesis, of self-assembling *trans*-Azo-YF-NH₂ in ambient light, while irradiation with UV light gives rise to the *cis*-isomer which readily hydrolyses to amino acid derivatives (*cis*-Azo-Y + F-NH₂) with consequent gel dissolution.

Molecular self-assembly¹ provides methodology for the fabrication of functional nanostructures for next generation healthcare and energy related technologies.² Peptide based systems are attractive in this regard, as they combine chemical versatility with ease of synthesis and biological relevance.³ Aromatic peptide amphiphiles, comprising di- or tripeptides incorporating (non-biological) aromatic residues are increasingly studied due to their simplicity and versatility.⁴ The interplay of kinetics (self-assembly route)⁵ in addition to thermodynamics (optimised supramolecular interactions) contribute to the properties of the assembled material. Methods to control the self-assembly process are therefore extensively researched.

Light has been used to control molecular assembly, typically by *cis*-to-*trans* isomerisation and consequent differences in stacking of the required light sensitive aromatic residues (typically derivatives of azobenzene). Using light in this context is attractive due to its non-invasiveness, wavelength selectivity and the possibility of patterning using photo-masks. A number of light responsive peptide self-assembly systems have been reported including an Azo-dipeptide.⁶

Alternatively, biocatalytic control of molecular self-assembly,^{7,8} *i.e.* enzymatic conversion of non-assembling precursors into self-assembling molecules, provides an attractive approach, combining biological selectivity, a level of space-time control of nucleation and

structure growth and amplification associated with catalysis with both equilibrium⁸ and non-equilibrium⁹ approaches demonstrated. Bing Xu's group recently demonstrated a system that combined enzymatic and light responsiveness, where an enzymatic reaction was performed to generate a hydrogel that showed light responsive assembly and disassembly.¹⁰

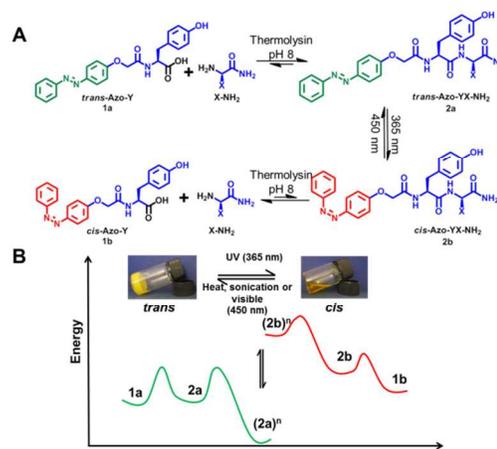

Scheme 1. A. *Trans*-azobenzene substituted tyrosine derivatives (*trans*-azo-Y) upon enzymatic condensation with amide derivatives of amino amides (F-, L-, V-NH₂) generate the corresponding dipeptide hydrogelators (Azo-YX-NH₂, X = F, CH₂-C₆H₅; L, CH₂-CH-(CH₃)₂; V, CH-(CH₃)₂) in presence of thermolysin at pH 8 in phosphate buffer under ambient conditions. Exposure to UV-light induces Azo switching, resulting in disassembly and hydrolysis of the gelator. B. Proposed energy diagrams for condensation and self-assembly of azo-peptide hydrogel for the *trans*- and *cis*-isomer. *Left*: energy difference for self-assembly exceeds that of hydrolysis, resulting in overall favourable condensation and self-assembly. *Right*: Self-assembly is not favoured resulting in hydrolysis, rather than condensation of the Azo-peptide.

Responsiveness in biological systems is commonly achieved by molecular systems that are able to respond to applied stimuli by a redistribution of components in coupled (networked) reactions. A similar adaptive behaviour may be achieved in synthetic systems, by coupling reactions. Conceptually, this idea fits with the objectives of *Systems Chemistry*¹¹ to make synthetic networked molecular systems that are adaptive.

In here, we demonstrate the coupling of light switching with biocatalytic amide condensation/hydrolysis. The equilibrium position of the amide reaction is controlled by the self-assembly propensity of the azo-peptide vs its amino acid precursors,⁸ which in turn is regulated by the input of energy (light), thus indirectly affecting the equilibrium situation of the system (**Scheme 1**). The free energy changed associated with molecular self-assembly and gelation is sufficiently thermodynamically favourable to overcome the bias for peptide hydrolysis normally observed in aqueous systems to facilitate condensation. This has been shown before for Fmoc,^{8a} Naphthoxy^{8b} peptides as well as purely peptidic¹² systems but has not yet been demonstrated for peptides linked to light responsive aromatic moieties. This reversible biocatalytic condensation is combined with the well-known *cis*-to-*trans* isomerisation for azobenzene, which has been used successfully in a range of light switchable systems.¹³ Xu's system focuses on enzymatic activation of the system which in itself, is irreversible. Our system is different in that the enzyme action and self-assembly is coupled and reversibly influenced by light.

Azobenzene functionalised tyrosine was prepared *via* a four step synthetic procedure (supporting information **Scheme S1**) to form **Azo-Y** (compound **5** in **Scheme S1**). First, we investigated, the enzymatic formation (using thermolysin from *Bacillus thermoproteolyticus rokko*) of different **Azo-YX-NH₂** derivatives (X= F-, L-, V-, represented as **YX**) in order to select a system most suited to demonstrate the concept. The molecular self-assembly of building blocks upon the addition of thermolysin, was macroscopically observed by transformation from a translucent solution to a self-supporting (yellow coloured) hydrogel. Of the systems tested, **YF** gelled rapidly (within 2-5 min. after the addition of enzyme) while **YL** and **YV** gelled within periods of 15 and 30 min, respectively. The percentage conversion to the dipeptide derivatives was determined by reverse-phase high performance liquid chromatography (HPLC). As shown in **Figure 1A**, the dipeptide derivatives formed in good yields of **YF** (84%), **YL** (59%) and **YV** (63%) at 24h after enzyme addition. While **YL** and **YF** appeared to have reached an equilibrium conversion after 4 hours, the **YV** conversion is slower and still increased substantially between 4 and 24 hrs. These results indicate that the gelation-driven self-assembly is sufficiently thermodynamically favourable to reverse peptide hydrolysis substantially to condensation. The contributing interactions are π - π stacking between *trans*-azobenzene moieties, as well as the aromatic amino acids, combined with and hydrogen bonding interactions between dipeptide units. The higher percentage conversion obtained for **YF** is likely a result of its more favourable self-assembly, due to additional aromatic stacking contributions in **F** compared to **V** and **L**. Competitive sequence selection for self-assembly under thermodynamic control for naphthalene- peptides also showed **YF** as a preferred sequence.^{8b}

Next, fluorescence spectroscopy was used to monitor any changes in the fluorophore environment upon assembly. The fluorescence emission peak of the starting mixture (**Azo-Y** + **X-NH₂**) exhibits a weak emission peak at 552 nm. The addition of thermolysin to this mixture induces a red-shift (558 nm) accompanied by a substantial increase in the relative emission intensity peak (**Figure 1B**). This

aggregation-induced emission (AIE)¹⁴ behaviour indicates that self-assembly of the dipeptide derivatives induces dramatic changes in the electronic properties, most likely due to changes in π -stacking interactions. In addition to spectroscopy, investigations into their nanoscale architecture were carried out by a transmission electron microscopy (TEM). The starting materials, before enzyme addition, showed micellar structure while after enzyme addition, the presence of entangled nanofibres was observed for the three dipeptide sequences investigated (**Figure 1c**). The diameter of the nanofibres was 20-30 nm and the length of the fibres were up to several micrometers, in line with nanostructures observed for other aromatic peptide amphiphiles.⁴ Fibres formed by **YF** appeared to be significantly shorter compared to those found for **YL** and **YV**.

The gel-like behaviour of the self-supporting hydrogels was confirmed by oscillatory rheology (**Figure S2**). For the three dipeptide derivatives, the elastic modulus (G') is over 10 times greater than viscosity modulus (G'') confirming the existence of a strong hydrogel network for each system with similar moduli observed for each system. The data suggests **YV** has more stiffness (higher G') than **YL** and **YF** derivatives.

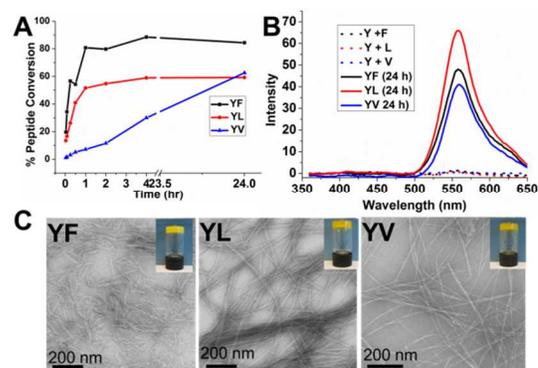


Figure 1: (a) HPLC data, showing the percentage peptide conversion of different dipeptide derivatives over time ($\lambda=340$ nm) (b) Fluorescence spectroscopy of azobenzene based dipeptide hydrogels (**Azo-YX-NH₂**, X= F, L, V) before and 24 h after thermolysin addition. ($\lambda_{\text{excitation}}= 343$ nm). (c) TEM images of the dipeptide derivatives.

Among the three dipeptide derivatives tested, **YF** showed a high conversion and rapid response time, so was used to investigate its light-responsive properties. When the hydrogel (**10 mM**, 24h after enzyme addition) was irradiated using a UV lamp (365 nm), the hydrogel disintegrated and dissolved after 48-72 h exposure.¹⁵ This gel-sol transition of **YF** is expected due to the conformation change of azobenzene from planar *trans*- (E) to non-planar (bent) *cis*- (Z) form, with the *cis*-isomer prohibiting effective hydrophobic association and π - π stacking between azobenzene chromophores.¹⁰ This unfavourable self-assembly further results in switch from favourable condensation in the self-assembling system (**Scheme 1**) to a situation where the enzymatic peptide hydrolysis takes over (**Figure S5**), resulting in degradation of the fibrous network. (HPLC yields confirm the peptide hydrolysis, as discussed below). Upon heating and sonication during 60 s, the *cis*-isomer (sol), reverts back to the *trans*-isomer after 48-72 h and gelation is observed. This gel-sol-gel transition of the system upon UV irradiation was further characterised by TEM. As shown in **Figure S4**, in the gel-phase **YF** arranges itself into a three dimensional network of nanofibres, which upon UV irradiation, converts to micellar aggregates. Under ambient light, nanofibres reform over time (48-72 h).

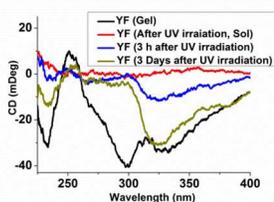


Figure 2: Circular dichroism (CD) spectra of Azo-YF-NH₂ (10 mM) before (gel) and after (sol) UV irradiation. Corresponding HT (high tension) voltage (Figure S3).

CD analysis reveals insights into changes in the chiral supramolecular arrangement during the photoisomerisation process as previously shown for Azo-dipeptide.^{6b} As shown in Figure 2, for *trans*-Azo-YF-NH₂ a broad CD signal at 300–360 nm originates is observed, due to π - π^* transition of the azobenzene chromophore^{13,16}. After UV induced gel dissolution, the system becomes CD silent which is in line with expectation for the formation of a micellar aggregate system. 3h after UV treatment, we observe supramolecular chirality which confirms the isomerisation of the *cis*-into *trans*-form favours the reformation of chiral nanofibres. After 3 days, the CD signal reverts back to similar intensity, albeit, with a change in spectral shape, suggesting a slight difference in supramolecular arrangement compared to the initial gel formed. HPLC analysis (Figure S5) was performed to assess the influence of light on the condensation/hydrolysis equilibrium, demonstrating that the peptide (2a) upon UV irradiation hydrolysed back to 1a and 1b (Figure S5).

To further confirm that UV irradiation not only switches the self-assembly properties but also enables hydrolysis, the system was started under UV illumination (Scheme 1B, right). To this end, the starting solution (Azo-Y + F-NH₂; 10 mM), was isomerised under UV-light in solution state before addition of enzyme. The conversion of *trans*- to *cis*- isomer could be monitored by UV-vis spectroscopy (Figure S6). The enzyme was subsequently added and the biocatalytic self-assembly of the dipeptide derivative monitored by HPLC, giving rise to a 7.6 % conversion after 24h (Figure S7) (instead of 84 % for the *trans* isomer) which indicates that *cis*-isomer disfavours condensation and gelation.

In summary, we demonstrated the ability to control and direct enzymatic amide condensation using light. This is achieved by using a coupled system, involving biocatalytic condensation, gelation and light switching. Influencing of biological pathways by using light may provide important tools for the development of adaptive nanotechnology, with possible therapeutic implications, e.g. in photo modulation of cellular environments.¹⁷

Notes and references

We thank BBSRC for funding through Award 120315. The research leading to these results has received funding from the European Research Council under the European Union's Seventh Framework Programme (FP7/2007-2013) / ERC grant agreement n° [258775].

*Corresponding Author

rein.ulijn@strath.ac.uk

Notes

The authors declare no competing financial interest.

† ¹ WestCHEM, Department of Pure and Applied Chemistry, Thomas Graham Building, 295 Cathedral Street, Glasgow G1 1XL, UK

Electronic Supplementary Information (ESI) available:

See DOI: 10.1039/c000000x/

- (a) G. M. Whitesides and B. Grybowski, *Science*, 2002, **295**, 2418. (b) J. –M. Lehn, *Science*, 2002, **295**, 2400.
- N. L. Rosi, C. A. Mirkin, *Chem. Rev.*, 2005, **105**, 1547.
- (a) J. M. Fletcher, R. L. Harniman, F. R. H. Barnes, A. L. Boyle, A. Collins, J. Mantell, T. H. Sharp, M. Antognozzi, P. J. Booth, N. Linden, M. J. Miles, R. B. Sessions, P. Verkade, D. N. Woolfson, *Science*, 2013, **340**, 595. (b) L. C. Palmer, S. I. Stupp, *Acc. Chem. Res.*, 2008, **41**, 1674. (c) R.V. Ulijn and A.M. Smith. *Chem. Soc. Rev.*, 2008, **37**, 664. (d) L. E. R. O'Leary, J. A. Fallas, E. L. Bakota, M. K. Kang and J. D. Hartgerink *Nature Chem.*, 2011, **3**, 821.
- (a) M. Reches, E. Gazit, *Science*, 2003, **300**, 625. (b) Y. Zhang, H. Gu, Z. Yang, B. Xu, *J. Am. Chem. Soc.*, 2003, **125**, 13680. (c) D. J. Adams, P. D. Topham, *Soft Matter*, 2010, **6**, 3707.
- (a) A. R. Hirst, S. Roy, M. Arora, A. K. Das, N. Hodson, P. Murray, S. Marshall, N. Javid, J. Sefcik, J. Boekhoven, J. H. van Esch, S. Santabarbara, N. T. Hunt, R. V. Ulijn, *Nature Chem.*, 2010, **2**, 1089. (b) J. M. A. Carnall, C. A. Waudby, A. M. Belenguer, M. C. A. Stuart, J. J.-P. Peyralans, S. Otto, *Science*, 2010, **327**, 1502. (c) J. Raeburn, A. Z. Cardoso, D. J. Adams, *Chem. Soc. Rev.*, 2013, **42**, 5143.
- (a) J. Raeburn, T. O. McDonald, D. J. Adams, *Chem. Commun.*, 2012, **48**, 9355. (b) Y. Huang, Z. Qiu, Y. Xu, J. Shi, H. Lin, Y. Zhang, *Org. Biomol. Chem.*, 2011, **9**, 2149. (c) J. H. Collier, B. –H. Hu, J. W. Ruberti, J. Zhang, P. Shum, D. H. Thompson, P. B. Messersmith, *J. Am. Chem. Soc.*, 2001, **123**, 9463.
- Z. Yang, H. Gu, D. Fu, P. Gao, J. K. Lam, B. Xu, *Adv. Mater.*, 2004, **16**, 1440.
- (a) R. J. Williams, A. M. Smith, R. Collins, N. Hodson, A. K. Das, R. V. Ulijn, *Nat. Nanotechnol.*, 2009, **4**, 19. (b) S. K. M. Nalluri, R. V. Ulijn, *Chem. Sci.*, 2013, **4**, 3699. (c) J. W. Sadownik, R. V. Ulijn, *Chem. Commun.*, 2010, **46**, 3481.
- S. Debnath, S. Roy, R. V. Ulijn, *J. Am. Chem. Soc.* 2013, **135**, 16789.
- X. Li, Y. Gao, Y. Kuang, B. Xu, *Chem. Commun.*, 2010, **46**, 5364.
- (a) R. F. Ludlow, S. Otto, *Chem. Soc. Rev.*, 2008, **37**, 101. (b) J. R. Nitschke, *Nature*, 2009, **462**, 736. (c) J. F. Stoddart, *Angew. Chem. Int. Ed.*, 2012, **51**, 12902.
- J. –B. Guilbaud, E. Vey, S. Boothtoyd, A. M. Smith, R. V. Ulijn, A. Saiani, A. F. Miller, *Langmuir*, 2010, **26**, 11297.
- Y. Lin, Y. Qiao, P. Tang, Z. Li, J. Huang, *Soft Matter*, 2011, **7**, 2762.
- Y. Hong, J. W. Y. Lam, B. Z. Tang, *Chem. Soc. Rev.*, 2011, **40**, 5361.
- The reason for the long irradiation time, can be attributed to the strong fibrous network of the hydrogel and weak intensity (100 W) of the UV-lamp.
- Q. Hu, Y. Wang, J. Jia, C. Wang, L. Feng, R. Dong, X. Sun, J. Hao, *Soft Matter*, 2012, **8**, 11492.
- M. He, J. Li, S. Tan, R. Wang, Y. Zhang, *J. Am. Chem. Soc.*, 2013, **135**, 18718.

