

# ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

## COMMUNICATION

# Pd Nanoparticle Concentration Dependent Self-assembly of Pd@SiO<sub>2</sub> Nanoparticles into Leaching Resistant Microcubes

Cite this: DOI: 10.1039/x0xx00000x

Received 00th January 2012,  
Accepted 00th January 2012Abheek Datta,<sup>a</sup> Anustup Sadhu,<sup>a</sup> Subhankar Santra,<sup>a</sup> S. M. Shivaprasad,<sup>b</sup> Swadhin K. Mandal,<sup>a</sup> and Sayan Bhattacharyya<sup>\*a</sup>

DOI: 10.1039/x0xx00000x

www.rsc.org/

**Pd NP concentration guided the self-assembly of core-shell Pd@SiO<sub>2</sub> nanoparticles (NPs) into microcubes. The Pd NPs were stacked by molten dodecyltrimethylammonium bromide (DTAB) to create the SiO<sub>2</sub> envelope. The microcubes demonstrated improved leaching resistance in heterogeneous catalysis over a conventional porous support.**

Although discrete NPs could be easily synthesized by surfactant assisted wet-chemical routes, easy handling of these NPs requires well-defined superstructures for practical applications.<sup>1,2</sup> In the past, the self-assembled superstructures or microstructures were obtained by solvent evaporation,<sup>3</sup> surfactant templates,<sup>4,5</sup> or molecular cross-linking.<sup>6</sup> Molecular simulations have shown that NPs coated with surfactants can self-assemble into larger structures based on solvent selectivity of the NPs and the surfactants.<sup>7</sup> NPs tend to remain aggregated in order to minimize their free energy and the self-assembled shapes are dependent on a particular solvent medium. The self-assembly processes are so far shown to be dependent on specific and non-specific interactions of the surfactants with the NPs. Also, the shape and size of nanocomposites are known to be engineered by the NPs and surfactants.<sup>8-11</sup> However, keeping the synthesis parameters constant, the self-assembly process was never observed to be guided by the NP concentration.


In most of the metal NP and SiO<sub>2</sub> composites, the shape of the SiO<sub>2</sub> support was governed by the organic linkers and the metal NPs were added post-fabrication of the support.<sup>12,13</sup> Quite a few studies are available on *in-situ* synthesis where the metal NPs occupy site selective locations.<sup>14-16</sup> The Pd NP - SiO<sub>2</sub> composites are excellent heterogeneous catalysts in formation of C-C and C-X (X = Cl, Br, I) bonds.<sup>12,17,18</sup> Self-assembly of an ensemble of Pd NPs into 3-dimensional (3D) micron-sized architectures can improve robustness of the system, still maintaining the novel properties of the NPs. The A precise knowledge of the metal NP distribution is necessary such

as if the NPs are immobilized on the outer surface or embedded inside the support to understand the transport of reactant molecules to the active sites.<sup>18,19</sup> The designed 3D composites should offer improved control over the surface chemistry and NP size, which are key factors in the construction of next generation catalysts.

Herein we demonstrate the morphology evolution of porous silica to non-porous Pd-SiO<sub>2</sub> microcubes aided by <0.5 wt% Pd NPs and DTAB. Acid hydrolysis of TEOS in presence of DTAB generated porous SiO<sub>2</sub> and with the optimal presence of Pd NPs in the solution, micron sized cubes of SiO<sub>2</sub> was formed. Acid hydrolysis was carried out with different concentrations of Pd NPs separately in air and N<sub>2</sub> to synthesize the as-synthesized (AS) products which were hydrogenated at 550°C. ICP-MS analyses of the hydrogenated (H-550) Pd-SiO<sub>2</sub> composites provided the final weight% of Pd NPs. Two Pd-SiO<sub>2</sub> composites were synthesized in N<sub>2</sub> with Pd wt% of 0.09 and 0.34, whereas those synthesized in air had Pd wt% of 0.14 and 0.41. Also a separate sample was synthesized where 0.37 wt% Pd NPs were exclusively immobilized on the surface of mesoporous SiO<sub>2</sub> by PVP binder. Fig. 1a shows the transmission electron micrograph (TEM) of the pristine citrate ligand stabilized spherical Pd NPs of diameter 4.3 ± 0.4 nm. The inter-planar spacing of 0.23 nm corresponds to the (111) reflection. The X-ray diffraction (XRD) patterns of the H-550 composites correspond to metallic Pd<sup>0</sup> (JCPDS No. 87-0639) over a background of amorphous SiO<sub>2</sub> (Fig. S2).

The morphological trends are similar in the AS (Fig. S3) and H-550 composites (Fig. 1 and S4). In the absence of Pd NPs, porous SiO<sub>2</sub> was obtained. With <0.2 wt% Pd NPs, 10-20 nm well-defined spherical clusters were formed, and these particles aggregated into ~600 nm diameter spheres (Fig. 1b). The clusters consisted of SiO<sub>2</sub> shell encapsulated Pd NPs. When 0.34-0.41 wt% Pd NPs were present, grooved SiO<sub>2</sub> microcubes were observed (Fig. 1d, g). In fact, a threshold ~0.2 wt% Pd NPs was required to form the microcubes. Enlarged view of the field emission scanning electron microscope

(FESEM) images in Fig. 1e, h shows that there are 100-200 nm clusters and Pd NPs dispersed both inside and outside the microcubes. The inhomogeneous distribution of Pd NPs was examined by energy dispersive analysis of X-ray (EDAX) spectra (Fig. S5) and the concentration of Pd was higher inside the grooves of the microcubes than on the surface. With ~1 wt% Pd NPs, almost all the Pd NPs remain confined inside the microcubes with fewer grooves (Fig. S6).

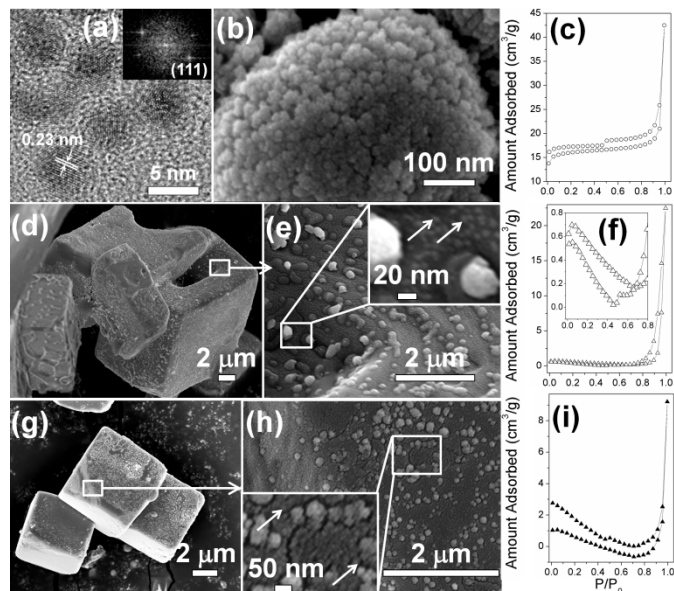


**Fig. 1** (a) High-resolution TEM image of pristine Pd NPs and (inset) FFT pattern. FESEM images of H-550 Pd-SiO<sub>2</sub> composites with Pd wt% of (b) 0.14 (air), (d) 0.41 (air), (e) enlarged view of the marked area in (d), (g) 0.34 (N<sub>2</sub>) and (h) enlarged view of the marked area in (g). Arrows inside the insets show Pd NPs. N<sub>2</sub> adsorption/desorption isotherms with Pd wt% of (c) 0.14, (f) 0.41 and (i) 0.34. Inset (f) shows the low pressure hysteresis.

Pd NPs converted the porous SiO<sub>2</sub> into non-porous Pd-SiO<sub>2</sub> microcubes as evident from the N<sub>2</sub> adsorption/desorption isotherms in Fig. 1, S7 and S8. In the absence of Pd NPs, SiO<sub>2</sub> had decent surface area 574-581 m<sup>2</sup>/g with type IV physisorption isotherm and H2 hysteresis loop, indicative of mesopores (Fig. S9).<sup>20</sup> When the AS samples were hydrogenated, two competing factors of shrinkage of pores and decomposition of surfactants determine the change in surface area. With the addition of < 0.2 wt% Pd, the surface area of the AS samples dropped to 8-11 m<sup>2</sup>/g, primarily due to partial collapse of the mesoporous matrix and formation of Pd@SiO<sub>2</sub> core-shell particles. The physisorption isotherms of the AS and H-550 0.09-0.14 wt% Pd@SiO<sub>2</sub> samples did not possess limiting adsorption at high relative pressure (H3 type hysteresis loop). The physisorption isotherms of the ≥ 0.2 wt% Pd samples possessed H3 type hysteresis with minimum surface area and negligible micropores (Fig. 1f, i). After hydrogenation, decomposition of the surfactants did not lead to new pores. Significant low pressure hysteresis was observed, which is associated with the irreversible uptake of adsorbate (N<sub>2</sub>) molecules within Å-wide diameter pores. Bond formation and breaking of the citrate and DTAB molecules could result in pore dimensions comparable to the diameter of the N<sub>2</sub> molecules. Once adsorbed into the Å-wide pores, the adsorbate molecules could not be desorbed.

The SiO<sub>2</sub> microcubes were formed with Pd NPs situated both inside and outside the cubes (Fig. 2). The Pd NPs were stabilized by electrostatic repulsion due to the presence of citrate ions adsorbed on their surface. When DTAB [CH<sub>3</sub>(CH<sub>2</sub>)<sub>11</sub>N<sup>+</sup>(CH<sub>3</sub>)<sub>3</sub>Br<sup>-</sup>] was added to the Pd NPs in the presence of TEOS at acidic pH, DTAB could bind

to the negatively charged citrate groups and the hydrolysis of TEOS took place around the ~4.3 nm Pd NPs to form core-shell Pd-SiO<sub>2</sub> particles of diameter 10-20 nm. The self-assembly of these core-shell particles was strongly intertwined with the concentration of Pd NPs and DTAB. The AS products were dried at 150°C and DTAB with a melting point of 246°C could not decompose completely even in air. Secondly the formation of cubes required layer-by-layer stacking of a threshold ~0.2 wt% Pd NP support and below this critical loading, the cubes were not obtained. In the AS samples with ≥ 0.2 wt% Pd NPs, complete stacking could take place at 150°C due to partial decomposition of DTAB. The SiO<sub>2</sub> envelope remained discontinuous and the microcubes were deformed and grooved. During hydrogenation, DTAB remains in the molten state at 550°C but still could not decompose completely due to the absence of atmospheric oxygen. The molten DTAB breaks the SiO<sub>2</sub> shell over the Pd@SiO<sub>2</sub> NPs and the core-shell morphology disintegrates, which helps silica to form a continuous envelope around the Pd NPs upon cooling. DTAB acts as the carrier of silica over an ensemble of stacked Pd NPs. Thermogravimetric analysis have shown that ~14 wt% DTAB contributed in the morphological transformation and 6-10 wt% DTAB helped in stabilizing the microcubes (Fig. S10). However, the assembly of the Pd NPs inside the cubes is guided by the stacking process in the AS precursor. Thus several deformations and grooves were observed in the H-550 cubes. Due to this non-uniformity in stacking, Pd@SiO<sub>2</sub> NPs were observed even on the surface of the microcubes. Generally, in cubic NPs a large fraction of atoms reside on the edges and vertices which leads to high free energy.<sup>21</sup> The microcubes could be stabilized since with increase in size, the contribution from the edges and vertices to the overall free energy decreases.

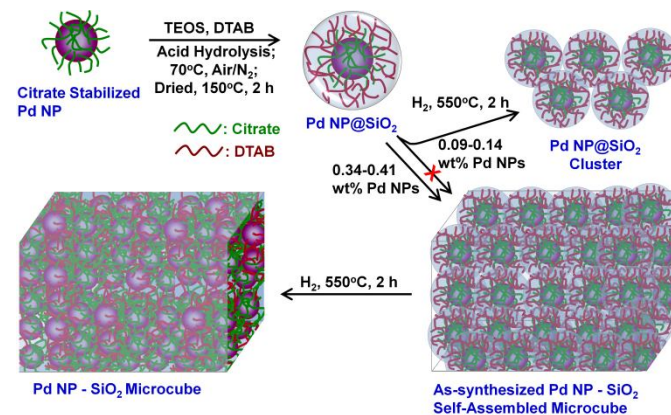


**Fig. 2** Schematic illustration of the formation process of Pd-SiO<sub>2</sub> microcubes.

FTIR spectra showed that a lesser concentration of DTAB was still retained in the H-550 samples (Fig. S11). An optimum 0.05 g DTAB is crucial in stabilizing the microcubes, without which well-defined cube shapes were not obtained (Fig. S12). In fact, anionic and neutral surfactants also gave irregular cube-like shapes. This emphasizes that irrespective of an electrostatic interaction to bind Pd NPs to SiO<sub>2</sub>, the stacking of Pd NPs will take place depending on the Pd NP concentration in the presence of a surfactant.

Although, TEM and XRD did not provide any evidence of Pd<sup>2+</sup> species, X-ray photoelectron spectroscopy (XPS) analyses showed the presence of 36-37% and 43-49% amorphous PdO in H-550 0.41 wt% Pd-SiO<sub>2</sub> (air) and 0.37 wt% Pd deposited outside mesoporous SiO<sub>2</sub>, respectively (Fig. 3). The extent of oxidation is less when part of the Pd NPs is confined inside the SiO<sub>2</sub> microcubes. In the microcubes, Si-OH species was also observed along with SiO<sub>2</sub>,

where the peaks at 103.6 and 103.9 eV are due to Si-OH bonds in SiO<sub>2</sub> and hydroxylated SiO<sub>2</sub>, respectively (Fig. S13).<sup>22</sup>

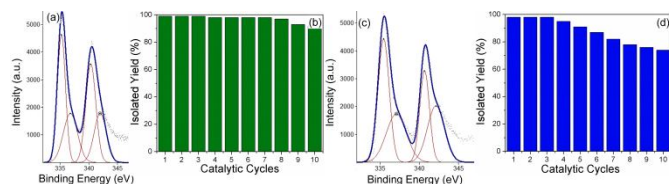

**Fig. 3** (a, c) Pd 3d XPS spectra and (b, d) isolated yield of the product after recycling the catalysts up to 10 cycles for 0.41 wt% P-SiO<sub>2</sub> microcubes (a, b) and 0.37 wt% Pd NP – porous SiO<sub>2</sub> (c, d), respectively.

To study the dependence of the yield and recyclability in Suzuki-Miyaura C-C cross coupling on the catalyst morphology, the performance of H-550 0.41 wt% Pd-SiO<sub>2</sub> microcubes was compared to the 0.37 wt% Pd NPs immobilized on mesoporous SiO<sub>2</sub>. In the coupling of phenylboronic acid and 4-bromotoluene an optimum activity was obtained when K<sub>2</sub>CO<sub>3</sub> was the base and DMF:H<sub>2</sub>O (1:3) the solvent (Table S15). The initial turnover numbers were 5183 and 5799 for the microcubes and mesoporous catalysts with Pd wt% of 0.41 and 0.37, respectively (Fig. S16). Fig. 3 shows recyclability performance of the catalysts in 10 runs. Although the initial yields were similar, the mesoporous catalyst was deactivated from 4<sup>th</sup> catalytic cycle. The microcubes retain decent catalytic activity throughout. The microcubes showed excellent leaching resistance since majority of the Pd NPs was embedded inside the cube. The slight drop in yield% from the 8<sup>th</sup> cycle was due to leaching of the unprotected Pd NPs from the microcube surface. In contrast, when all the Pd NPs remain attached to the surface of mesoporous SiO<sub>2</sub>, the chance of leaching of the NPs is higher. However, the microcubes were non-porous (Fig. 1c, f, i) and the reactant molecules could enter through the Å-sized pores but the Pd NPs could not leach out. It was also observed by FESEM studies that after the 5<sup>th</sup> and 10<sup>th</sup> cycle, the microcubes retain their bulk morphology but the mesoporous structure was ruptured (Fig. S17). The strong network of Pd@SiO<sub>2</sub> NP stacks and surfactant scaffold holds the cubic microstructure and generates NP leaching resistance.

## Conclusions

In summary, morphology evolution of SiO<sub>2</sub> aided by ~4.3 nm Pd NPs was demonstrated whereby ~0.1 wt% Pd NPs could transform porous SiO<sub>2</sub> into 10-20 nm Pd@SiO<sub>2</sub> NPs. Self-assembly of ≥ 0.2 wt% Pd@SiO<sub>2</sub> NPs resulted in Pd-SiO<sub>2</sub> non-porous microcubes. Incomplete decomposition of the surfactant DTAB under H<sub>2</sub> at 550°C helps SiO<sub>2</sub> to form a continuous envelope around the stacked ensemble of Pd NPs which self-assemble to form grooved microcubes upon cooling. The Pd-SiO<sub>2</sub> microcubes demonstrated superior leaching resistance. The Pd NP governed self-assembly process can be extended to other NPs for creating self-assembled microstructures for a wide range of practical applications in catalysis, bio-reactors, molecular separations media, optical and magnetic devices.

## Notes and references

<sup>a</sup> Department of Chemical Sciences, Indian Institute of Science Education and Research (IISER) Kolkata, Mohanpur - 741246, India.

Email: sayanb@iiserkol.ac.in

<sup>b</sup> International Centre for Materials Science & Chemistry and Physics of Materials Unit, Jawaharlal Nehru Centre for Advanced Scientific Research, Jakkur, Bangalore – 560064, India.

† This work is supported by Department of Science and Technology (DST), Government of India under grant no. SR/S1/PC-28/2011. AD thanks University Grants Commission (UGC), New Delhi for his fellowship.

Electronic Supplementary Information (ESI) available: [Experimental section, XRD patterns, FESEM images, Details of surface area, <sup>1</sup>H NMR, FTIR and XPS measurements, control experiments and catalysis standardization]. See DOI: 10.1039/c000000x/

- M. Li, H. Schnablegger and S. Mann, *Nature*, 1999, **402**, 393-395.
- Y. Deng, Y. Cai, Z. Sun, J. Liu, C. Liu, J. Wei, W. Li, C. Liu, Y. Wang and D. Zhao, *J. Am. Chem. Soc.*, 2010, **132**, 8466–8473.
- G. V. R. Rao, G. P. López, J. Bravo, H. Pham, A. K. Datye, H. Xu and T. L. Ward, *Adv. Mater.*, 2002, **14**, 1301-1304.
- Th. Zemb, M. Dubois, B. Demé and Th. Gulik-Krzywicki, *Science*, 1999, **283**, 816-819.
- X. Ji, Q. Hu, J. E. Hampsey, X. Qiu, L. Gao, J. He and Y. Lu, *Chem. Mater.*, 2006, **18**, 2265-2274.
- K. L. Hamner, C. M. Alexander, K. Coopersmith, D. Reishofer, C. Provenza and M. M. Maye, *ACS Nano*, 2013, **7**, 7011-7020.
- Z. Zhang, M. A. Horsch, M. H. Lamm and S. C. Glotzer, *Nano Lett.*, 2002, **14**, 1301-1304.
- D. A. Walker, E. K. Leitsch, R. J. Nap, I. Szeifer and I. Grzybowski, *Nature Nanotech.*, 2013, **8**, 676-681.
- G. Liu, K. L. Young, X. Liao, M. L. Personick and C. A. Mirkin, *J. Am. Chem. Soc.*, 2013, **135**, 12196-12199.
- S. Bhattacharyya and A. Gedanken, *J. Phys. Chem. C*, 2008, **112**, 659-665.
- S. Bhattacharyya and A. Gedanken, *J. Phys. Chem. C*, 2008, **112**, 13156-13162.
- G. Park, S. Lee, S. Son and S. Shin, *Green Chem.*, 2013, **15**, 3468-3473.
- P. Li, H. Liu, Y. Yu, C. -Y. Cao and W. -G. Song, *Chem. Asian J.*, 2013, **8**, 2459-2465.
- L. Li, D.L. King, J. Liu, Q. Huo, K. Zhu, C. Wang, M. Gerber, D. Stevens and Y. Wang, *Chem. Mater.*, 2009, **21**, 5358-5364.
- H. Song, R. M. Rioux, J. D. Hoefelmeyer, R. Komor, K. Niesz, M. Grass, P. Yang and G. A. Somorjai, *J. Am. Chem. Soc.*, 2006, **128**, 3027-3037.
- L. Chen, J. Hu, Z. Qi, Y. Fang and R. Richards, *Ind. Eng. Chem. Res.*, 2011, **50**, 13642–13649.
- Z. Chen, Z. M. Cui, F. Niu, L. Jiang and W. G. Song, *Chem. Commun.*, 2010, **46**, 6524–6526.
- J. C. Park, E. Heo, A. Kim, M. Kim, K. H. Park and H. Song, *J. Phys. Chem. C.*, 2011, **115**, 15772–15777.
- S. M. Kim, M. Jeon, K. W. Kim, J. Park and I. S. Lee, *J. Am. Chem. Soc.*, 2013, **135**, 15714–15717.
- K. S. W. Sing, D. H. Everett, R. A. W. Haul, L. Moscou, R. A. Pierrotti, J. Rouquerol and T. Siemieniowska, *Pure Appl. Chem.*, 1985, **57**, 603-619.
- A. S. Barnard and P. A. Zapol, *J. Chem. Phys.*, 2004, **121**, 4276-4283.
- M. L. Miller and R. W. Linton, *Anal. Chem.*, 1985, **57**, 2314-2319.