

# ChemComm

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

## COMMUNICATION

## Solvent induced single-crystal to single-crystal structural transformation and concomitant transmetalation in a 3D cationic Zn(II)-framework

Cite this: DOI: 10.1039/x0xx00000x

Susan Sen<sup>a</sup>, Subhadip Neogi<sup>a</sup>, Kari Rissanen<sup>b</sup> and Parimal K. Bharadwaj<sup>a\*</sup>Received 00th January 2014,  
Accepted 00th January 2014

DOI: 10.1039/x0xx00000x

www.rsc.org/

**A 3D cationic Zn(II) framework, based on  $Zn_2(CO_2)_4$  paddle-wheel secondary building units (SBUs) and  $Zn_{16}(CO_2)_{32}$  polyhedral supramolecular building blocks (SBBs) has been synthesized. At room temperature, the framework undergoes guest solvent triggered reversible structural transformation and concomitant Zn(II) to Cu(II) transmetalation in a single-crystal to single-crystal fashion.**

Most of the studies on metal–organic frameworks (MOFs) are concentrated towards creation of robust frameworks, where particular emphasis has been focused on their ability to retain the architecture even after removal of guest solvent molecules for practical applications.<sup>1</sup> In addition to their large well-defined pore shapes and sizes, an important feature of these frameworks is the presence of metal clusters, serving as secondary building units (SBUs).<sup>2</sup> Adopting the SBU approach, a large number of novel MOFs,<sup>3–5</sup> have been constructed. MOFs that undergo single-crystal to single-crystal (SC-SC) structural transformations<sup>6</sup> triggered by external stimuli have received considerable current attention. Selective molecular motions<sup>7</sup> as well as metal/ligand substitution<sup>8</sup> in MOF crystals without losing single crystallinity, are largely being pursued in several laboratories to design and construct functional materials.<sup>9</sup> Although, substitution of a linker in a MOF by another one has often been realized in SC-SC transformation,<sup>10</sup> exchange of metal,<sup>11</sup> however, is experienced in only a handful of examples.

<sup>a</sup>Department of Chemistry, Indian Institute of Technology, Kanpur 208016, India. E-mail: [pkb@iitk.ac.in](mailto:pkb@iitk.ac.in)

<sup>b</sup>Department of Chemistry, NanoScience Center, University of Jyväskylä, P.O. Box 35, 40014 Jyväskylä, Finland. E-mail: [kari.t.rissanen@jyu.fi](mailto:kari.t.rissanen@jyu.fi)

†Electronic Supplementary Information (ESI) available: Experimental details, NMR, PXRD patterns, FT-IR spectra, TGA, SEM images, EDS spectrum, tables, additional figures and CIF files. CCDC 1037351 (**1**), CCDC 1037352 (**2**-MeCN), CCDC 1037353 (**2**-DCM), CCDC 1037354 (**1**<sub>Cu</sub>-DMF), CCDC 1037355 (**2**<sub>Cu</sub>-MeCN). For ESI and crystallographic data in CIF or other electronic format See DOI: 10.1039/c000000x/

Transmetalations are primarily attractive to overcome the limitation of achieving multifunctional MOFs by direct solvothermal synthesis<sup>12</sup> and to fabricate the interior as well as exterior of MOF materials with improved properties.<sup>13</sup> To better elucidate the exchange mechanism, investigations of the metal replacement behaviour are indispensable. Using a rigid and angular tetracarboxylic acid ligand ( $H_4L^+$ )<sup>14</sup>, incorporating imidazolium group in the middle and aromatic carboxylate at the terminals, a cationic Zn(II) framework (**1**) based on  $Zn_2(CO_2)_4$  paddle-wheel SBUs and  $Zn_{16}(CO_2)_{32}$  polyhedral supramolecular building blocks (SBBs), has been synthesized. We demonstrate that the imidazolium moiety reorients in solvents like acetonitrile, chloroform, dichloromethane, benzene, toluene to make the dihedral angle between the plane of the imidazolium moiety and the phenyl ring to be 122.56° in transformed Zn(II) framework (**2**) while in solvents like dimethyl sulfoxide (DMSO), dimethylformamide (DMF), methanol (MeOH), tetrahydrofuran (THF), Dimethylcarbonate ( $Me_2CO_3$ ) the dihedral angle changes to 63.94° in framework **1**. Interestingly, the Zn(II)-MOF (**1**) readily undergoes transmetalation from Zn(II) to Cu(II), whereupon **1** is converted to **2**<sub>Cu</sub>, only when the dihedral angle changes from 63.94° to 122.56°. To the best of our knowledge, this is the first report where transmetalation has been achieved as a consequence of the change in the ligand conformation. In addition, the Cu-exchanged MOF **2**<sub>Cu</sub> transforms to **1**<sub>Cu</sub> in a reversible SC-SC fashion when simply dipped in solvents having at least one oxygen atom as a part of their molecule such as DMSO, DMF, MeOH, THF, Dioxane. All the changes are realized in SC-SC fashion at room temperature and characterized by single crystal X-ray diffraction studies.

Colorless octagonal crystals of  $\{[Zn_2(L)(H_2O)_2] \cdot NO_3 \cdot xDMF \cdot yH_2O\}_n$ , (**1**) were synthesized solvothermally by reacting 1,3-bis-(3,5-dicarboxyphenyl) imidazoliumchloride ( $LCI^+ = H_4L^+Cl^-$ ) with  $Zn(NO_3)_2 \cdot 6H_2O$  in DMF at 90 °C for 3 days. The single-crystal X-ray diffraction study demonstrates (Table S1, ESI<sup>†</sup>) that **1** crystallizes in

tetragonal  $P4_1/nm$  space group. Structural investigation revealed that the asymmetric unit contains one half of ligand **L**, two crystallographically independent Zn(II) ions (Zn1 and Zn2) each with half occupancy and one water molecule. Both Zn1 and Zn2 lie on the  $C_4$  axis and adopts the square pyramidal geometry to coordinate with four  $\mu_2\text{-}\eta^1, \eta^1$  carboxylates of **L** to form the paddlewheel  $[\text{M}_2(\text{CO}_2)_4]$ , with average Zn–Zn distance of 3.009 Å (Zn1–Zn1, 2.999(1) Å; Zn2–Zn2, 3.0186(6) Å) (Fig. S4, ESI<sup>†</sup>). The fifth coordination site is occupied by a solvent water molecule. Notably, the paddle-wheel  $\text{Zn}_2(\text{CO}_2)_4$  carry no charge that enables the entire framework to be cationic, owing to the positive charge on the central imidazolium ring.<sup>14</sup> The nitrate anion rests in the cavity. Although we could not locate this nitrate anion, due to the inherent disorder nature, its presence is confirmed by IR spectra (Fig. S8a, ESI<sup>†</sup>). As illustrated in Figure 1, eight **L** ligands are linked with eight Zn(II)-paddle-wheels, to produce a  $\text{Zn}_{16}(\text{CO}_2)_{32}$  gyrobifastigium polyhedra (combination of two triangular prism), having eight vertices, eight faces and fourteen edges, in which the core cavity is accessible through four triangular and four square faces.

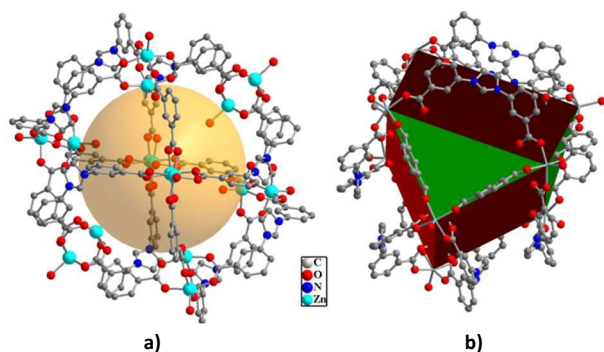


Fig. 1 Representation of the (a) MOP and (b) gyrobifastigium.

The internal spherical cavity of this polyhedron in **1** has a diameter of  $\sim 14.7$  Å (distance refers to atom-to-atom distance throughout this communication) ignoring coordinated solvents, while the size of the triangular aperture is  $\sim 12.2$  Å. All edges of the polyhedron are decorated with cationic imidazolium moieties that point outwards. These polyhedral  $\text{Zn}_{16}(\text{CO}_2)_{32}$  units can be regarded as SBBs that are interconnected through the paddlewheel  $\text{Zn}_2(\text{CO}_2)_4$  SBUs and **L** ligands to form a non-interpenetrated 3D structure. When viewed along the crystallographic  $c$  axis, the structure presents 1D hexagonal channels, with a cross-section of 8.786 Å between the opposite vertices (Fig. S22, ESI<sup>†</sup>). Views along  $a$  and  $b$  axes reveal additional square-shaped channels with a cross section of 8.839 Å and 8.359 Å (Fig S23, ESI<sup>†</sup>) respectively. These voids are occupied by solvent molecules and nitrate anions. The high disorder nature of the guest solvent molecules did not allow us to establish the guest molecules unambiguously. The total solvent-accessible volume is estimated using PLATON<sup>15</sup> which reveals the calculated guest accessible area per unit cell volume for **1** to be 5678 Å<sup>3</sup> ( $\sim 64\%$ ). Thermogravimetric analysis of **1** exhibits (Fig. S8b, ESI<sup>†</sup>) a continuous loss of solvent molecules, starting from room temperature without a plateau, corroborating the limited thermal stability of the framework. The bulk-phase purity of **1** was

confirmed by comparing the experimentally observed powder X-ray diffraction (PXRD) pattern with the simulated pattern (Fig. S24, ESI<sup>†</sup>).

A close look into the packing diagram of **1** reveals that the water molecules coordinated to the Zn(II) ions of SBUs are projected towards the hexagonal channels and are also directed along the  $a$ - and  $b$ - axes (Fig. S23, ESI<sup>†</sup>). This observation led us to probe for possible substitution of the axial sites by other solvent molecules. Interestingly, when a single crystal of **1** is dipped into a solution of  $\text{CH}_3\text{CN}$  for 24 h at room temperature, the colour and morphology of the crystal remains the same (Fig. S28, ESI<sup>†</sup>), the structure reveals the formation of  $\{[\text{Zn}_2(\text{L})(\text{H}_2\text{O})_2]\cdot\text{NO}_3\cdot y\text{H}_2\text{O}\cdot z\text{MeCN}\}_n$  (**2-MeCN**) where space group changes to  $I4_1/amd$ , with considerable changes in the lattice parameters (Table S1, ESI<sup>†</sup>). Single-crystal X-ray analyses indicate the presence of three crystallographically independent Zn(II) ions and one entire ligand in the asymmetric unit. A comparison between the structure of **1** and **2-MeCN** shows that the coordination modes of **L** ligands as well as the metal bound water molecules remain intact with the difference that the paddle-wheel SBUs are twisted with respect to the isophthalate moiety, as a consequence of the free rotation of imidazolium ring around the C–N bond (Fig. 2a). This twist also affects many of the key dihedral

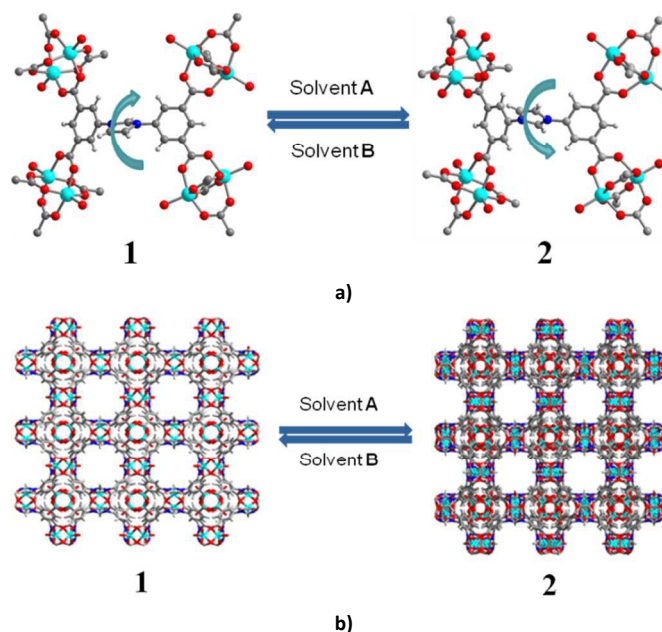


Fig. 2 (a) Solvent induced reversible orientation of the imidazolium moiety and (b) parallel movement in the  $\text{Zn}_2(\text{CO}_2)_4$  paddle-wheel unit, leading to positional change in the packing diagram of **1** and **2** along the  $c$ -axis. (Solvent A: solvent molecules that do not have oxygen atom as a part of their molecule, solvent B: solvent molecules having at least one oxygen atom as a part of their molecule)

angles. Particularly, the dihedral angle between plane of the imidazolium moiety and the plane of the phenyl ring that changes from  $63.94^\circ$  to  $122.56^\circ$ . Furthermore, the average Zn–Zn distance in the  $\text{Zn}_2(\text{CO}_2)_4$  paddle wheel units changes from  $\sim 3.009$  Å in **1** to  $\sim 3.0190$  Å in **2-MeCN** (Zn1–Zn1, 3.0266(18) Å; Zn2–Zn3, 3.0114(16) Å) (Fig. S5 and Table S3, ESI<sup>†</sup>). Although, the movement of the

paddlewheel SBUs does not drastically affect the overall 3D packing of the framework, the rotational rearrangement leads to positional changes of the individual atoms in **2**-MeCN (Fig. 2b). The total solvent-accessible volume, as estimated using PLATON,<sup>15</sup> shows the calculated guest accessible area per unit cell volume for **2**-MeCN (64.2%) is similar to that of **1**. In relation to the mother framework **1** here also, highly disordered guest solvent molecules cannot be mapped by single crystal XRD. Bulk purity of **2**-MeCN is corroborated by PXRD measurement, which reveals perfect agreement between the simulated pattern and also with the pattern obtained for **1** (Fig S25, ESI<sup>†</sup>). After careful screening of different solvents (Table S4, ESI<sup>†</sup>), we conclude that the above SC-SC structural deformation phenomena transpire in the presence of solvents (DCM, chloroform, carbon tetrachloride, acetonitrile, toluene, benzene) that do not have any oxygen atom as a part of their molecule.

Besides, **2**-MeCN undergoes reversible SC-SC transformation to **1** (Table S2, ESI<sup>†</sup>) at room temperature, on exposing the former to solvents that have at least one oxygen atom as a part of their molecule, like DMSO, DMF, DEF, DMA, THF, Me<sub>2</sub>CO<sub>3</sub> and alcohol (methanol, ethanol, propanol). It should be pointed here that independent solvothermal synthesis of **2** by mixing H<sub>4</sub>L<sup>+</sup> and Zn(II) in the solvents that do not have oxygen atom as a part of their molecule proved unsuccessful, signifying that SC-SC transformation is the only route towards its formation. The aforementioned results strongly indicate that the rotational movement of the molecular components in the crystal actually depends on the nature of solvent molecules. We assume that H-bonding interaction between the ligand moiety and guest solvent molecule is crucial for such solvent induced reversible single-crystal to single-crystal transformation. Unfortunately, we could not model the guest solvent molecule to assess those particular interactions. In order to further check the influence of the oxygen atom containing solvent on the transformation of **1** to **2**, additional experiments with different solvent ratio were carried out. As summarized in Table S4 (ESI<sup>†</sup>), we confirm that even a small amount of oxygen atom containing solvent is sufficient to inhibit the aforesaid transformation.

Direct synthesis of the copper analogue of **1** by replacing Zn(NO<sub>3</sub>)<sub>2</sub>·6H<sub>2</sub>O with Cu(NO<sub>3</sub>)<sub>2</sub>·3H<sub>2</sub>O, as described above, was not successful. Presence of paddlewheel SBUs and accessibility of polyhedral SBBs from the large channels prompted us to explore the possibility of metal ion exchange within the framework via the post-synthesis approach. In principle, metal centers, having similar preferred coordination geometries will undergo metal-exchange reactions more readily, since low energy is needed to overcome changes in coordination geometry. To test our above hypothesis, crystals of **1** were immersed in a DMF solution of Cu(NO<sub>3</sub>)<sub>2</sub>·3H<sub>2</sub>O (0.04 M) at room temperature, whereupon no apparent colour change occurred even throughout a period of long one month. Quite in contrast, crystals of **1** when dipped in acetonitrile solution of Cu(NO<sub>3</sub>)<sub>2</sub>·3H<sub>2</sub>O (0.04 M), the original colourless crystals gradually turned into green-blue in 12h while maintaining their original shapes and sizes (Fig S28 ESI<sup>†</sup>). The metal replacement was

confirmed by the EPR spectrum (Fig. S29, ESI<sup>†</sup>) of green-blue crystals. We attempted to confirm the Cu-exchanged framework by single-crystal XRD analysis, which indicates (Table S1, ESI<sup>†</sup>) that the completely exchanged product has similar framework as **2** with the formula  $\{[\text{Cu}_2(\text{L})(\text{H}_2\text{O})_2] \cdot \text{NO}_3 \cdot y\text{H}_2\text{O} \cdot z\text{MeCN}\}_n$  (**2**<sub>Cu</sub>-MeCN). Furthermore, X-ray fluorescence spectroscopy (XFS) studies demonstrates that no significant amount of Zn(II) ions is left in the framework **2**<sub>Cu</sub>-MeCN. Since a transmetalation reaction principally demands cleavage and formation of coordinate bonds, the aforesaid observations led us to hypothesize that solvent induced ligand flipping and consequent SBU twisting in **1** perturb the coordination geometry at the Zn(II) center, which ultimately facilitates replacement by Cu(II) through SC-SC fashion. The kinetics of the Zn<sup>2+</sup> to Cu<sup>2+</sup> ion exchange process was monitored by energy-dispersive X-ray spectroscopy, which showed that nearly 50% of the framework Zn<sup>2+</sup> ions were replaced by Cu<sup>2+</sup> within 1 h, and 95% of the Zn<sup>2+</sup> ions were exchanged by Cu<sup>2+</sup> within 12h (Fig. 3). Complete exchange (99%) is achieved in two days.

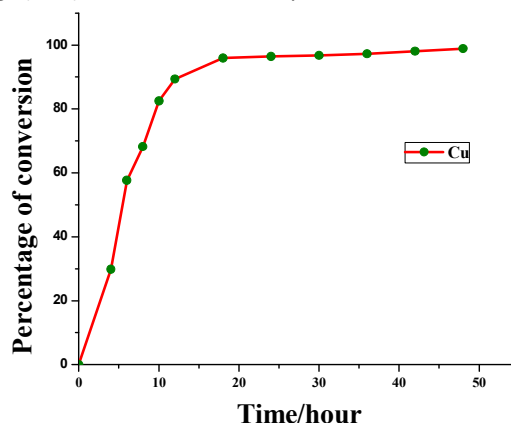


Fig. 3 Kinetic profile of the Zn(II) to Cu(II) transmetalation process.

Having successfully converted framework **1** to **2**<sub>Cu</sub>, we finally examined whether we can generate the structure **1**<sub>Cu</sub> through the solvent induced reversible SC-SC structural transformation. As monitored from single crystal X-ray diffraction studies (Table S1, ESI<sup>†</sup>), the blue crystals of **2**<sub>Cu</sub>-MeCN indeed change to **1**<sub>Cu</sub>-DMF, when kept in DMF for 2days, as a consequence of the reorientation of the imidazolium moiety. During the transmetalation reaction, the average M–M distance in the M<sub>2</sub>(CO<sub>2</sub>)<sub>4</sub><sup>-</sup> paddle wheel units (Table S3, ESI<sup>†</sup>) changes from 3.008 Å (Zn–Zn) in **1** to 2.658 Å (Cu–Cu) in **2**<sub>Cu</sub>-MeCN (Fig. S6, ESI<sup>†</sup>) that further changes to 2.679 Å in **1**<sub>Cu</sub>-DMF (Fig S7, ESI<sup>†</sup>). The experimental PXRD patterns of **1**<sub>Cu</sub>-DMF and **2**<sub>Cu</sub>-MeCN (Fig. S26 and S27, ESI<sup>†</sup>) respectively, are identical to their simulated patterns, signifying the bulk purity. Moreover, the PXRD patterns of the transmetalated frameworks are similar to that of their corresponding mother Zn(II)-frameworks, demonstrating that the frameworks were preserved throughout the metal-ion exchange. In a similar way, **2** also undergoes structural transformation with concomitant transmetalation to **1**<sub>Cu</sub> (Table S1, ESI<sup>†</sup>) in Cu(NO<sub>3</sub>)<sub>2</sub> solution of a solvent that does not have any oxygen atom as a part of their molecule. It should be noted that the straightforward metal replacement, i.e. **2** to **2**<sub>Cu</sub>, does not occur,

demonstrating once more (*vide supra*) that flipping of the imidazolium moiety with parallel twist in  $Zn_2(CO_2)_4$  SBUs is an essential prerequisite for the metal exchange to take place in these frameworks. However, the reverse transmetalation processes do not occur, i.e., for both **1**<sub>Cu</sub>-DMF and **2**<sub>Cu</sub>-MeCN, Cu(II) ions cannot be replaced by Zn(II) ions even in a concentrated DMF/ MeCN solution of  $Zn(NO_3)_2 \cdot 6H_2O$  (1 M) under long exchange time (1 month), suggesting that the Cu(II)-frameworks are more stable than the corresponding Zn(II)-frameworks.<sup>13c</sup>

In conclusion, using an angular tetracarboxylic acid ligand  $H_4L^+$ , incorporating imidazolium group, we have synthesized a 3D cationic Zn(II) framework, based on  $Zn_2(CO_2)_4$  paddle-wheel SBUs and  $Zn_{16}(CO_2)_{32}$  polyhedral SBBs. At room temperature, the framework undergoes reversible SC-SC structural transformation as a consequence of the reorientation in the imidazolium moiety, in presence of solvents that do not have any oxygen atom as a part of their molecule. Although, the straightforward metal replacement, i.e. **1** to **1**<sub>Cu</sub>, does not occur, framework **1** undergoes transformation with concomitant transmetalation to **2**<sub>Cu</sub> in the presence of solvents that have no oxygen atom as a part of their molecule. Similarly, **2**-MeCN undergoes metal exchange to **1**<sub>Cu</sub> only when dipped in solvents that have least one oxygen atom as a part of their molecule. The results demonstrate that flipping of the imidazolium moiety with parallel twist in  $Zn_2(CO_2)_4$  SBUs is an essential prerequisite for the metal exchange to take place in these frameworks. To the best of our knowledge, this is the first report exemplifying SC-SC transmetalation as a consequence of change in ligand conformation and should provide insight in fabricating switch emergent molecular devices. Possibility of transmetalation reactions and their kinetics with different transition metal ions, are currently underway.

## Notes and references

We gratefully acknowledge the financial support from the Department of Science and Technology, New Delhi, India (J.C. Bose National Fellowship to P.K.B.). S.N. thanks IIT Kanpur for a postdoctoral fellowship. Dr. Fangfang Pan (Chem Dept, Jyväskylä) is thanked for some preliminary structural work on **1** and **2**-MeCN. The Academy of Finland (KR. grant no. 265328 and 263256) is kindly acknowledged for financial support.

1 (a) T. A. Makal, J.-R. Li, W. Lu and H.-C. Zhou, *Chem. Soc. Rev.*, 2012, **41**, 7761–7779; (b) B. Li, H.-M. Wen, W. Zhou, and B. Chen, *J. Phys. Chem. Lett.*, 2014, **5**, 3468–3479.

2 D. J. Tranchemontagne, J. L. Mendoza-Cortés, M. O'Keefe and O. M. Yaghi, *Chem. Soc. Rev.*, 2009, **38**, 1257–1283.

3 (a) T. H. Park, A. J. Hickman, K. Koh, S. Martin, A. G. Wong-Foy, M. S. San-ford and A. J. Matzger, *J. Am. Chem. Soc.*, 2011, **133**, 20138–20141; (b) S. Horike, M. Dinca, K. Tamaki and J. R. Long, *J. Am. Chem. Soc.*, 2008, **130**, 5854–5855; (c) K. S. Jeong, Y. B. Go, S. M. Shin, S. J. Lee, J. Kim, O. M. Yaghi and N. Jeong, *Chem. Sci.*, 2011, **2**, 877–882; (d) F. Vermoortele, M. Van-dichel, B. V. Voorde, R. Ameloot, M. Waroquier, V. V. Speybroeck and D. E. D. Vos, *Angew. Chem. Int. Ed.*, 2012, **51**, 4887–4890.

4 G. J. T. Cooper, G. N. Newton, P. Kçgerler, D. L. Long, L. Engelhardt, M. Luban and L. Gronin, *Angew. Chem.*, 2007, **119**, 1362–1366; *Angew. Chem. Int. Ed.*, 2007, **46**, 1340–1344.

5 S. R. Caskey and A. J. Matzger, *Inorg. Chem.*, 2008, **47**, 7942–7944.

6 (a) S. Neogi, S. Sen and P. K. Bharadwaj, *Cryst Eng Comm.*, 2013, **15**, 9239–9248; (b) Y. Han, J.-R. Li, Y. Xie and G. Guo, *Chem. Soc. Rev.*, 2014, **43**, 5952–5981; (c) H. Aggarwal, P. Lama and L. J. Barbour, *Chem. Commun.*, 2014, **50**, 14543–14546; (d) M. C. Das and P. K. Bharadwaj, *J. Am. Chem. Soc.*, 2009, **131**, 10942–10949; (e) M. C. Das and P. K. Bharadwaj, *Chem. Eur. J.*, 2010, **16**, 5070–5077; (f) R. K. Das, A. Aijaz, M. K. Sharma, P. Lama and P. K. Bharadwaj, *Chem. Eur. J.*, 2012, **18**, 6866–6872.

7 (a) E. Y. Lee, S. Y. Jang, M. P. Suh, *J. Am. Chem. Soc.*, 2005, **127**, 6374–6381; (b) M. K. Sharma and P. K. Bharadwaj, *Inorg. Chem.*, 2011, **50**, 1889–1897; (c) H. Aggarwal, P. M. Bhatt, C. X. Bezuidenhout, and L. J. Barbour, *J. Am. Chem. Soc.*, 2014, **136**, 3776–3779.

8 (a) C. K. Brozek and M. Dinca, *Chem. Sci.*, 2012, **3**, 2110–2113; (b) Z. Zhang, L. Wojtas, M. Eddaoudi and M. J. Zaworotko, *J. Am. Chem. Soc.*, 2013, **135**, 5982–5985; (c) J.-R. Li and H.-C. Zhou, *Nat. Chem.*, 2010, **2**, 893–898; (d) T. Li, M. T. Kozlowski, E. A. Doud, M. N. Blakely and N. L. Rosi, *J. Am. Chem. Soc.*, 2013, **135**, 11688–11691.

9 G. J. Halder and C. J. Keppert, *J. Am. Chem. Soc.*, 2005, **127**, 7891–7900.

10 (a) C. G. Bezzu, M. Helliwell, J. E. Warren, D. R. Allan and N. B. McKeown, *Science*, 2010, **327**, 1627–1630; (b) H. J. Park, Y. E. Cheon and M. P. Suh, *Chem. Eur. J.*, 2010, **16**, 11662–11669; (c) B. J. Burnett, P. M. Barron, C. Hu and W. Choe, *J. Am. Chem. Soc.*, 2011, **133**, 9984–9987; (d) T. Li, M. T. Kozlowski, E. A. Doud, M. N. Blakely and N. L. Rosi, *J. Am. Chem. Soc.*, 2013, **135**, 11688–11691.

11 (a) S. Das, H. Kim and K. Kim, *J. Am. Chem. Soc.*, 2009, **131**, 3814–3815; (b) J. Tian, L. V. Saraf, B. Schwenzer, S. M. Taylor, E. K. Brechin, J. Liu, S. J. Dalgarno and P. K. Thallapally, *J. Am. Chem. Soc.*, 2012, **134**, 9581–9584; (c) T.-F. Liu, L. Zou, D. Feng, Y.-P. Chen, S. Fordham, X. Wang, Y. Liu and H.-C. Zhou, *J. Am. Chem. Soc.*, 2014, **136**, 7813–7816.

12 (a) S. Huang, X. Li, X. Shi, H. Hou and Y. Fan, *J. Mater. Chem.*, 2010, **20**, 5695–5699; (b) Y. Han, N. F. Chilton, M. Li, C. Huang, H. Xu, H. Hou, B. Moubaraki, S. K. Langley, S. R. Batten, Y. Fan and K. S. Murray, *Chem. Eur. J.*, 2013, **19**, 6321–6328.

13 (a) D. Denysenko, T. Werner, M. Grzywa, A. Puls, V. Hagen, G. Eicklerling, J. Jelic, K. Reuter and D. Volkmer, *Chem. Commun.*, 2012, **48**, 1236–1238; (b) X. J. Wang, P. Z. Li, L. Liu, Q. Zhang, P. Borah, J. D. Wong, X. X. Chan, G. Rakesh, Y. Li and Y. Zhao, *Chem. Commun.*, 2012, **48**, 10286–10288; (c) X. Song, T. K. Kim, H. Kim, D. Kim, S. Jeong, H. R. Moon and M. S. Lah, *Chem. Mater.*, 2012, **24**, 3065–3073.

14 S. Sen, S. Neogi, A. Aijaz, Q. Xu, and P. K. Bharadwaj, *Inorg. Chem.*, 2014, **53**, 7591–7598.

15 A. L. Spek *J. Appl. Crystallogr.*, 2003, **36**, 7–13.