

# Catalysis Science & Technology

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.



[www.rsc.org/catalysis](http://www.rsc.org/catalysis)

Yamamoto et al.  
Porphyrin Derivative-Modified TiO<sub>2</sub> Photocatalysts for Visible-Light-Assisted Selective Catalytic Reduction of NO  
with NH<sub>3</sub>

**Title:** Visible-Light-Assisted Selective Catalytic Reduction of NO with NH<sub>3</sub> on Porphyrin Derivative-Modified TiO<sub>2</sub> Photocatalysts

**Corresponding authors**

Dr. Kentaro Teramura and Professor Tsunehiro Tanaka

Department of Molecular Engineering, Graduate School of Engineering, Kyoto University, Kyotodaigaku Katsura, Nishikyo-ku, Kyoto 615-8510, Japan

Tel: +81-75-383-2559 Fax: +81-75-383-2561

E-mail address: teramura@moleng.kyoto-u.ac.jp

**List of the authors**

Akira Yamamoto<sup>a</sup>, Yuto Mizuno<sup>a</sup>, Kentaro Teramura<sup>a,b,c\*</sup>, Saburo Hosokawa<sup>a,b</sup>, Tetsuya Shishido<sup>b,d</sup>, Tsunehiro Tanaka<sup>a,b\*</sup>

**Affiliation and full postal address**

- a. Department of Molecular Engineering, Graduate School of Engineering, Kyoto University, Kyotodaigaku Katsura, Nishikyo-ku, Kyoto 615-8510, Japan
- b. Elements Strategy Initiative for Catalysts & Batteries (ESICB), Kyoto University, 1-30 Goryo-Ohara, Nishikyo-ku, Kyoto 615-8245, Japan
- c. Precursory Research for Embryonic Science and Technology (PRESTO), Japan Science and Technology Agency (JST), 4-1-8 Honcho, Kawaguchi, Saitama 332-0012, Japan
- d. Department of Applied Chemistry, Graduate School of Urban Environmental Sciences, Tokyo Metropolitan University, 1-1 Minami-Osawa, Hachioji, Tokyo

Yamamoto et al.  
Porphyrin Derivative-Modified TiO<sub>2</sub> Photocatalysts for Visible-Light-Assisted Selective Catalytic Reduction of NO  
with NH<sub>3</sub>

192-0397, Japan

Yamamoto et al.  
Porphyrin Derivative-Modified TiO<sub>2</sub> Photocatalysts for Visible-Light-Assisted Selective Catalytic Reduction of NO  
with NH<sub>3</sub>

### Abstract

Porphyrin-derivative modified TiO<sub>2</sub> photocatalysts showed high photocatalytic activity for the selective catalytic reduction of NO with NH<sub>3</sub> in the presence of O<sub>2</sub> under visible-light irradiation. Tetra(p-carboxyphenyl)porphyrin (TCPP) was the most effective photosensitizer among the five porohyrin derivatives investigated. NO conversion and N<sub>2</sub> selectivity of 79.0% and 100% respectively, were achieved at a gas hourly space velocity of 50,000 h<sup>-1</sup>. UV-Vis and photoluminescence spectroscopies revealed the presence of two species of TCPP on the TiO<sub>2</sub> surface; one was a TCPP monomer and the other was a H-aggregate of the TCPP molecules. It was concluded that the TCPP monomer is an active species for the photo-assisted selective catalytic reduction (photo-SCR). Moreover, an increase in the fraction of H-aggregates with the increasing TCPP loading amount resulted in a decrease in the decrease of the photocatalytic activity of the photo-SCR.

Yamamoto et al.

Porphyrin Derivative-Modified TiO<sub>2</sub> Photocatalysts for Visible-Light-Assisted Selective Catalytic Reduction of NO with NH<sub>3</sub>

## 1. Introduction

NO<sub>x</sub>, which is present in the exhaust gas of stationary emission sources, is removed by the selective catalytic reduction with NH<sub>3</sub> (NH<sub>3</sub>-SCR) over vanadium oxide-based catalysts according to the following equation:  $(4\text{NO} + 4\text{NH}_3 + \text{O}_2 \rightarrow 4\text{N}_2 + 6\text{H}_2\text{O})$ <sup>1-3</sup>. The NH<sub>3</sub>-SCR process is performed at temperatures above 573 K. To save the energy used for heating the catalyst bed, novel catalysts are required for performing the NH<sub>3</sub>-SCR at low temperatures<sup>4-6</sup>. Photocatalysis is one of the promising candidates for the NH<sub>3</sub>-SCR because photocatalytic reactions proceed at room temperature. We have reported the photo-assisted selective catalytic reduction (photo-SCR) of NO with NH<sub>3</sub> in the presence of O<sub>2</sub> over TiO<sub>2</sub> photocatalysts under UV-light irradiation<sup>7-10</sup>. In this system, the NO conversion and N<sub>2</sub> selectivity of 90% and 99%, respectively, were achieved at a gas hourly space velocity (GHSV) of 8,000 h<sup>-1</sup>, which is sufficient for the deNO<sub>x</sub> process in typical stationary sources such as power plants, blast furnaces, and incinerators. However, a very high GHSV was required in diesel engines owing to the limited installation space of the deNO<sub>x</sub> process and a high flow rate of the exhaust gas. The volume of the catalyst was required to be of the order of the volume of the diesel engine cylinder (typical GHSV in a three-way catalyst is approximately 100,000 h<sup>-1</sup>)<sup>11</sup>. Unfortunately, the NO conversion decreased with the increasing GHSV in the photo-SCR system and it decreased to 40% at a GHSV of 100,000 h<sup>-1</sup><sup>10</sup>. Therefore, the photocatalytic activity of the photo-SCR has to be improved at a high GHSV region in order to remove the NO<sub>x</sub> from the exhaust gas of diesel engines.

Expansion of the adsorption wavelength to the visible-light region is an effective way of improving the photocatalytic activity. TiO<sub>2</sub> photocatalysts do not absorb visible light because of their wide band gap (> 3.2 eV). Surprisingly, the photo-SCR proceeds to

Yamamoto et al.  
Porphyrin Derivative-Modified TiO<sub>2</sub> Photocatalysts for Visible-Light-Assisted Selective Catalytic Reduction of NO  
with NH<sub>3</sub>

some extent under visible-light irradiation over the TiO<sub>2</sub> photocatalysts. This is due to the direct electron transfer from the electron donor level of the N 2p orbital of the adsorbed NH<sub>3</sub> to the conduction band of the Ti 3d orbital of TiO<sub>2</sub> (in-situ doping)<sup>12, 13</sup>. However, the photocatalytic activity under visible-light irradiation is not sufficient for the application of the photo-SCR technology to the system at a high GHSV region. Thus, the proposed study aims to increase the photocatalytic efficiency under visible-light irradiation.

Porphyrin derivatives have absorption bands in the visible region owing to the  $\pi$ - $\pi^*$  transitions. Porphyrin derivatives are widely used as sensitizers in dye-sensitized solar cells (DSSCs)<sup>14-17</sup> and dye-sensitized photocatalysts<sup>18-20</sup> under visible-light irradiation owing to the following properties: 1) they exhibit intense absorption bands in the visible-light region, and 2) their photochemical and electrochemical properties can be tuned by the modification of the substituents and selection of the central metal. In previous studies, the porphyrin-sensitized photocatalysts were used for performing liquid phase reactions such as the hydrogen production from water<sup>20</sup>, and degradation of organic compounds<sup>18, 19, 21</sup>. However, there are only a few reports on the reactions involving porphyrin-sensitized photocatalysts in the gas phase. Recently, Ismail et al. reported that the porphyrin-sensitized mesoporous TiO<sub>2</sub> films exhibited an improved photocatalytic activity for the photodegradation of acetaldehyde in the gas phase under visible-light irradiation<sup>22</sup>. The porphyrin derivative-modified photocatalyst works efficiently as a visible-light response photocatalyst in the gas phase. In this study, we used five types of porphyrins for the modification of the TiO<sub>2</sub> photocatalyst, and investigated their performances in the photo-SCR using a gas flow reactor at a high GHSV of 50,000 h<sup>-1</sup>.

## 2. Results and Discussion

### 2.1 Effects of functional group in the porphyrins

Figure 1 shows the conversion of NO during the photo-SCR over the various porphyrin derivative-modified TiO<sub>2</sub> photocatalysts at a GHSV of 50,000 h<sup>-1</sup> after 6 h of visible-light irradiation, because the steady state reaction rate was obtained after 6 h. The conversion of NO over the unmodified TiO<sub>2</sub> photocatalyst was 13.4% under visible-light irradiation. Modification of the TiO<sub>2</sub> photocatalyst with the porphyrin derivatives greatly enhanced the photocatalytic conversion of NO under the visible-light irradiation as shown on the top of the Figure 1. Among the five porphyrin derivative-modified TiO<sub>2</sub> photocatalysts, the TCPP-TiO<sub>2</sub> photocatalyst showed the highest conversion of NO (71.4%). The conversion of NO decreased in the following order: TCPP-TiO<sub>2</sub> > TPP-TiO<sub>2</sub> > TSPP-TiO<sub>2</sub> > TMPP-TiO<sub>2</sub> > TAPP-TiO<sub>2</sub> > TiO<sub>2</sub>. Hence, it can be seen that the porphyrin functional group used for the modification of TiO<sub>2</sub> had a significant effect on the photo-SCR activity.

Figure 2 shows the UV-Vis DR spectra of the various porphyrin modified TiO<sub>2</sub> photocatalysts. The unmodified TiO<sub>2</sub> photocatalyst did not absorb the visible-light above 400 nm. The modification of the porphyrin derivatives increased the absorption in the visible-light region. The absorption at 420 nm (Soret band) decreased in the following order: TCPP-TiO<sub>2</sub> > TPP-TiO<sub>2</sub> ≅ TSPP-TiO<sub>2</sub> > TMPP-TiO<sub>2</sub> > TAPP-TiO<sub>2</sub> > TiO<sub>2</sub>. The order of the absorption is consistent with that of the NO conversion. The photocatalytic activities of NO were strongly dependent on the absorbance in the visible-light region, which suggested that the porphyrin derivatives functioned as photosensitizers under visible-light irradiation.

## 2.2 Effect of TCPP loading on the activity of photo-SCR

Figure 3 shows the UV/Vis DR spectra of the different loading amounts of the TCPP-TiO<sub>2</sub> photocatalysts. One major peak and four minor peaks were observed in the visible region in each sample. The major peak is the Soret band ( $S_2 \leftarrow S_0$  transition) and the four minor peaks are the Q bands ( $S_1 \leftarrow S_0$  transition). The Q bands are attributed to the 0-0 and 0-1 components of the non-degenerated Q<sub>x</sub> and Q<sub>y</sub> bands (etio type)<sup>23</sup>, as expected for the D<sub>2h</sub> symmetry. The increase in the TCPP loading amount enhanced the capability of visible-light absorption.

The peak positions of the Soret band and Q bands as a function of TCPP loading are shown in Table 1. The peak position of the Soret band of 1.3 μmol g<sup>-1</sup> TCPP-TiO<sub>2</sub>-IMP (417 nm) corresponded to those of the TCPP molecules dissolved in CH<sub>3</sub>OH (418 nm). The TCPP molecules existed as a monomer in the CH<sub>3</sub>OH solution and the peak position of the TCPP monomer coincided with that reported previously<sup>24</sup>. Thus, the TCPP molecules existed as monomers on the TiO<sub>2</sub> surface at the low loading amount of 1.3 μmol g<sup>-1</sup>. The peak position of the Soret band was shifted from 417 nm to 407 nm (blue-shift) when the loading amount of TCPP was increased from 1.3 μmol g<sup>-1</sup> to 62.5 μmol g<sup>-1</sup>. The origin of the blue-shift can be explained on the basis of a “face to face” stacking pattern of TCPP (H-aggregate) according to Kasha’s exciton theory<sup>25</sup>. Thus, the blue-shifted peak observed at 407 nm can be attributed to the Soret exciton band in the H-aggregates of the TCPP. The gradual spectral shift can be explained as the result of the relative contribution of the monomers and H-aggregates. The H-aggregates were generated with the increase in the TCPP loading. The contribution of the H-aggregates became dominant for the Soret band of adsorption spectra of various loading amount of TCPP-TiO<sub>2</sub>, which results in the gradual blue shift of the Soret band.



Yamamoto et al.

Porphyrin Derivative-Modified TiO<sub>2</sub> Photocatalysts for Visible-Light-Assisted Selective Catalytic Reduction of NO with NH<sub>3</sub>

On the other hand, the peak positions of the Q bands of 1.3  $\mu\text{mol g}^{-1}$  TCPP-TiO<sub>2</sub>-IMP (519, 555, 592, 649 nm) were slightly shifted to longer wavelengths compared to those of the TCPP monomer in CH<sub>3</sub>OH (515, 549, 590, 646 nm). The slight red-shift can be ascribed to the aggregation of TCPP<sup>24</sup> and/or the interactions between the TCPP and a solid surface<sup>26</sup>. The peak positions of the four Q bands of the TCPP-TiO<sub>2</sub>-IMP were shifted to longer wavelengths with an increase in the TCPP loading amount. The peak position of the Q bands of the H-aggregates of the TCPP is larger than that of the TCPP monomers<sup>24</sup>. Thus, the red-shift of the Q bands is due to the generation of the H-aggregates. Consequently, both the monomers and H-aggregates of TCPP are generated on TiO<sub>2</sub> and the fraction of the H-aggregates increased with the increasing TCPP loading amount.

Figure 4 shows the effect of various loading amounts of TCPP-TiO<sub>2</sub>-IMP on the photo-SCR. The conversion of NO increased with the increasing TCPP loading amount up to 12.5  $\mu\text{mol g}^{-1}$ . The surface density of TCPP molecules on 12.5  $\mu\text{mol g}^{-1}$  TCPP-TiO<sub>2</sub>-IMP is estimated to be  $2.8 \times 10^{-2}$  molecule nm<sup>-2</sup>. As shown in Figure 3, increasing the loading amount of TCPP enhanced the capability of the visible-light absorption, which leads to the higher conversion of NO. On the other hand, the conversion of NO decreased when the TCPP loading was higher than 12.5  $\mu\text{mol g}^{-1}$ . The UV-Vis spectroscopy revealed that the H-aggregates of TCPP were generated with the increase of the TCPP loading amount. The excited state lifetime of the H-aggregates was slightly shorter than those of the monomers<sup>24,27</sup>. The generation of H-aggregates with a short excited state lifetime decreased the electron transfer efficiency from the excited state of TCPP to the conduction band of TiO<sub>2</sub> due to non-radiative deactivation, which possibly resulted in the decrease of the photo-SCR activity.

### 2.3 Photo-SCR under various reaction conditions

Table 2 summarizes the concentrations of N<sub>2</sub> in the outlet gas for the photo-SCR under various reaction conditions. The conversion of NO in the photo-SCR over TCPP-TiO<sub>2</sub>-IMP was 79.0% (Entry 1) and the activity was stable for at least 6 h of visible-light irradiation (the time course is shown in Figure S1 in the supporting information). N<sub>2</sub> was the only product observed and N<sub>2</sub>O was not detected in any of the reactions. The utilization of visible-light was advantageous for the high selectivity to N<sub>2</sub>, since N<sub>2</sub>O was generated as a by-product of the photo-SCR over TiO<sub>2</sub> photocatalyst under UV-light irradiation. Turnover number (TON) of TCPP was calculated to be 810 after 6 h of visible-light irradiation. Thus, the total N<sub>2</sub> in the outlet gas was originated from the nitrogen atoms of NO and NH<sub>3</sub> molecules in the gas phase and not from the TCPP molecules. The reaction hardly proceeded over the TCPP-TiO<sub>2</sub> photocatalyst without a substrate such as NO, NH<sub>3</sub>, and O<sub>2</sub> (Entry 2, 3, and 4). The O<sub>2</sub> concentrations did not affect the generation rate of N<sub>2</sub> over 2% (Entry 1, 5, and 6). The TCPP-SiO<sub>2</sub>-IMP showed much lower activity under the same reaction conditions than that of the TCPP-TiO<sub>2</sub>-IMP (Entry 7), although the TCPP on SiO<sub>2</sub> absorbed visible-light as well as that on TiO<sub>2</sub> as shown in Figure 5. In addition, the activity of the photo-SCR over the TCPP-TiO<sub>2</sub> photocatalyst prepared by a physical mixture method (TCPP-TiO<sub>2</sub>-MIX) was similar to that of the unmodified TiO<sub>2</sub>, although the TCPP-TiO<sub>2</sub>-MIX absorbed in the visible region as shown in Figure 5.

Figure 6 shows the photoluminescence spectra of TCPP-TiO<sub>2</sub>-IMP, TCPP-SiO<sub>2</sub>-IMP, TCPP-TiO<sub>2</sub>-MIX, and TCPP monomer in CH<sub>3</sub>OH. Two emission bands were observed in the TCPP monomer in CH<sub>3</sub>OH solution (650 and 714 nm), which coincided with the previously reported values<sup>24</sup>. The emission bands at 650 nm and 714 nm can be attributed to the transition from the vibrational ground state of S<sub>1</sub> to the vibrational

Yamamoto et al.

Porphyrin Derivative-Modified TiO<sub>2</sub> Photocatalysts for Visible-Light-Assisted Selective Catalytic Reduction of NO  
with NH<sub>3</sub>

ground state of S<sub>0</sub> (Q<sub>x(0,0)</sub> transition) and to the vibrational excited state of S<sub>0</sub> (Q<sub>x(0,1)</sub> transition) of the TCPP monomer, respectively<sup>24,28</sup>. The peak positions of the emission bands in the TCPP-TiO<sub>2</sub>-IMP (654 and 715 nm) were almost similar to those of the TCPP monomer in CH<sub>3</sub>OH. It is reported that the emission bands of the H-aggregates of TCPP have lower intensity and are shifted to longer wavelengths than those of the monomers<sup>29</sup>, which is totally different from the emission spectrum of the TCPP-TiO<sub>2</sub>-IMP. Accordingly, the emission bands of TCPP-TiO<sub>2</sub>-IMP were mainly composed of the TCPP monomer emissions.

Two emission bands were observed at 658 and 713 nm, and the peak positions were similar to those of the TCPP in CH<sub>3</sub>OH (650 and 714 nm) and TCPP-TiO<sub>2</sub>-IMP (654 and 715 nm) (Figure 6). Thus, the TCPP species on SiO<sub>2</sub> possesses a monomeric state, which is similar to that on TiO<sub>2</sub>. The low activity of TCPP-SiO<sub>2</sub>-IMP can be explained by an electron transfer mechanism, which is the key step in the DSSCs and dye-sensitized photocatalysts. In the first step of the photo-SCR over the TCPP-TiO<sub>2</sub>-IMP, the TCPP is excited by the visible-light irradiation. In the next step, the electron transfer occurs from the photo-excited TCPP to the conduction band of TiO<sub>2</sub>. However, the electron transfer cannot occur from the photo-excited TCPP to the conduction band of SiO<sub>2</sub> because the energy level of the SiO<sub>2</sub> conduction band is much higher than that of the lowest unoccupied molecular orbital (LUMO) of TCPP, which results in the low activity of the TCPP-SiO<sub>2</sub>-IMP. Hence, the photo-SCR over TCPP-TiO<sub>2</sub>-IMP under visible-light irradiation proceeds via the electron transfer from the photo-excited TCPP to the conduction band of TiO<sub>2</sub>.

No emission peak was observed for the TCPP-TiO<sub>2</sub>-MIX and TCPP powder (Figure 6). The interaction between the TCPP molecules might lead to the non-radiative deactivation of the photo-excited states of TCPP, resulting in the luminescence

quenching for the TCPP-TiO<sub>2</sub>-MIX and TCPP powder. These results explain the low activity of the TCPP-TiO<sub>2</sub>-MIX, *i.e.* though the TCPP molecules on the TCPP-TiO<sub>2</sub>-MIX absorb visible-light, they do not function as a photosensitizer under visible-light irradiation because of the fast non-radiative quenching.

#### 2.4 On-off response tests of visible light irradiation

Figure 7 shows the on-off response for the photo-SCR under visible-light irradiation over the TCPP-TiO<sub>2</sub> photocatalyst at a GHSV of 50,000 h<sup>-1</sup>. The conversion of NO was about 6% without visible-light irradiation. The conversion of NO significantly increased to 86.5% under visible-light irradiation, indicating the function of the TCPP-TiO<sub>2</sub> photocatalyst as a visible-light-driven photocatalyst for the photo-SCR. The conversion of NO gradually decreased to 81.2% with the increasing irradiation time, although the conversion was restored to the original level (85.5%) after the on-off action. The decrease in the conversion of NO with the irradiation time was not due to the decomposition of TCPP. If the TCPP on the TiO<sub>2</sub> surface was decomposed under visible-light irradiation, the initial conversion of NO was expected to decrease gradually in the second, third, and fourth times. However, we did not observe a decrease in the initial conversion of NO. The recovery of the initial conversion of NO took place reversibly.

Yamamoto et al.

Porphyrin Derivative-Modified TiO<sub>2</sub> Photocatalysts for Visible-Light-Assisted Selective Catalytic Reduction of NO  
with NH<sub>3</sub>

### 3. Experimental Section

#### 3.1 Catalyst Preparation

A TiO<sub>2</sub> powder (ST-01, anatase, 273 m<sup>2</sup> g<sup>-1</sup>) was purchased from Ishihara Sangyo Kaisha, Ltd. A SiO<sub>2</sub> powder (630 m<sup>2</sup> g<sup>-1</sup>) was prepared by hydrolysis of tetraethyl orthosilicate (TEOS) in a water-ethanol mixture at boiling point, followed by calcination in dry air at 773 K for 5 h. Tetraphenylporphyrin (TPP), Tetra(*p*-carboxyphenyl)porphyrin (TCPP), Tetra(*p*-sulfonatephenyl)porphyrin (TSPP), Tetra(*p*-methoxyphenyl)porphyrin (TMPP), and Tetra(*p*-aminophenyl)porphyrin (TAPP) were purchased from Tokyo Chemical Industry Co., Ltd. and used without further purification (see Figure 1). The porphyrin derivatives were impregnated over the TiO<sub>2</sub> powder and the porphyrin-modified TiO<sub>2</sub> photocatalysts were abbreviated to porphyrin-TiO<sub>2</sub> (e.g. TCPP-TiO<sub>2</sub>). Various loading amount of TCPP-TiO<sub>2</sub> catalysts were prepared by an impregnation method using 1 M NH<sub>3</sub> aqueous solution as a solvent (TCPP-TiO<sub>2</sub>-IMP). A TCPP-modified SiO<sub>2</sub> catalyst was prepared by the impregnation method as shown above (TCPP-SiO<sub>2</sub>-IMP). A physical mixture catalyst of TCPP and the TiO<sub>2</sub> powder was prepared as a reference (TCPP-TiO<sub>2</sub>-MIX).

#### 3.2 Photocatalytic reaction

The photo-SCR was carried out in a conventional fixed-bed flow system at an atmospheric pressure. The catalyst was fixed with quartz wool and filled up in a quartz reactor with flat facets (H12 mm × W10 mm × D1.0 mm). The reaction gas composition was as follows: NO 1000 ppm, NH<sub>3</sub> 1000 ppm, O<sub>2</sub> 2–10%, He balance. 300 W Xe lamp (PERKIN-ELMER PE300BF) equipped with a L-42 cut-off filter was used as a light source ( $\lambda > 400$  nm) and the sample was irradiated from the one side of the flat facets of

Yamamoto et al.  
Porphyrin Derivative-Modified TiO<sub>2</sub> Photocatalysts for Visible-Light-Assisted Selective Catalytic Reduction of NO  
with NH<sub>3</sub>

the reactor. N<sub>2</sub> and N<sub>2</sub>O were analyzed by SHIMADZU GC-8A TCD gas chromatographs equipped with MS-5A and Porapak Q.

### 3.3 Characterization

UV-Vis transmission adsorption and diffuse reflectance spectra were obtained with a UV-Vis spectrometer (JASCO V-650). Transmission adsorption spectra were measured using a 1 cm quartz cell at room temperature in the scan range of 300–800 nm. Photoluminescence spectra were recorded on a Hitachi F-7000 fluorospectrometer in the scan range of 550–760 nm at an excitation wavelength of 410 nm. The concentrations of TCPP in methanol solution used in the adsorption and emission spectroscopy were  $3.4 \times 10^{-6}$  mol L<sup>-1</sup> and  $1.0 \times 10^{-6}$  mol L<sup>-1</sup>, respectively.

Yamamoto et al.

Porphyrin Derivative-Modified TiO<sub>2</sub> Photocatalysts for Visible-Light-Assisted Selective Catalytic Reduction of NO  
with NH<sub>3</sub>

## Conclusion

We found that porphyrin derivative-modified TiO<sub>2</sub> functions as a visible-light-driven photocatalyst for the photo-SCR. The TCPP-modified TiO<sub>2</sub> photocatalyst showed the highest activity of the photo-SCR among the TiO<sub>2</sub> photocatalysts modified with the five porphyrin derivatives investigated. We elucidated the state of TCPP on TiO<sub>2</sub> affect the photocatalytic conversion of NO and the active species is a TCPP monomer adsorbed on TiO<sub>2</sub> due to efficient electron transfer from the photo-excited TCPP monomer to the conduction band of TiO<sub>2</sub>.

## Acknowledgement

This study was partially supported by the Program for Element Strategy Initiative for Catalysts & Batteries (ESICB), commissioned by the Ministry of Education, Culture, Sports, Science and Technology (MEXT) of Japan, and the Precursory Research for Embryonic Science and Technology (PRESTO), supported by the Japan Science and Technology Agency (JST). Akira Yamamoto thanks the JSPS Research Fellowships for Young Scientists.

## References

1. H. Bosch and F. Janssen, *Catal. Today*, 1988, **2**, 369-379.
2. G. Busca, L. Lietti, G. Ramis and F. Berti, *Appl. Catal., B*, 1998, **18**, 1-36.
3. P. Forzatti and L. Lietti, *Heterog. Chem. Rev.*, 1996, **3**, 33-51.
4. R. Q. Long, R. T. Yang and R. Chang, *Chem. Commun.*, 2002, 452-453.
5. J. Li, H. Chang, L. Ma, J. Hao and R. T. Yang, *Catal. Today*, 2011, **175**, 147-156.
6. P. G. Smirniotis, D. A. Peña and B. S. Uphade, *Angew. Chem. Int. Ed.*, 2001, **40**, 2479-2482.
7. T. Tanaka, K. Teramura, K. Arakaki and T. Funabiki, *Chem. Commun.*, 2002, 2742-2743.
8. K. Teramura, T. Tanaka, S. Yamazoe, K. Arakaki and T. Funabiki, *Appl. Catal., B*, 2004, **53**, 29-36.
9. S. Yamazoe, T. Okumura, K. Teramura and T. Tanaka, *Catal. Today*, 2006, **111**, 266-270.
10. A. Yamamoto, Y. Mizuno, K. Teramura, T. Shishido and T. Tanaka, *Catal. Sci. Technol.*, 2013, **3**, 1771-1775.
11. M. Koebel, M. Elsener and M. Kleemann, *Catal. Today*, 2000, **59**, 335-345.
12. S. Yamazoe, K. Teramura, Y. Hitomi, T. Shishido and T. Tanaka, *J. Phys. Chem. C*, 2007, **111**, 14189-14197.
13. T. Shishido, K. Teramura and T. Tanaka, *Catal. Sci. Technol.*, 2011, **1**, 541-551.
14. A. Kay and M. Graetzel, *J. Phys. Chem.*, 1993, **97**, 6272-6277.
15. W. M. Campbell, A. K. Burrell, D. L. Officer and K. W. Jolley, *Coord. Chem. Rev.*, 2004, **248**, 1363-1379.
16. H. Imahori, H. Norieda, H. Yamada, Y. Nishimura, I. Yamazaki, Y. Sakata and S. Fukuzumi, *J. Am. Chem. Soc.*, 2000, **123**, 100-110.
17. A. Yella, H.-W. Lee, H. N. Tsao, C. Yi, A. K. Chandiran, M. K. Nazeeruddin, E. W.-G. Diao, C.-Y. Yeh, S. M. Zakeeruddin and M. Grätzel, *Science*, 2011, **334**, 629-634.
18. G. Mele, R. Del Sole, G. Vasapollo, E. García-López, L. Palmisano and M. Schiavello, *J. Catal.*, 2003, **217**, 334-342.
19. S. Murphy, C. Saurel, A. Morrissey, J. Tobin, M. Oelgemöller and K. Nolan, *Appl. Catal., B*, 2012, **119-120**, 156-165.
20. H. Hagiwara, N. Ono, T. Inoue, H. Matsumoto and T. Ishihara, *Angew. Chem. Int. Ed.*, 2006, **45**, 1420-1422.



Yamamoto et al.  
Porphyrin Derivative-Modified TiO<sub>2</sub> Photocatalysts for Visible-Light-Assisted Selective Catalytic Reduction of NO  
with NH<sub>3</sub>

21. D. Li, W. Dong, S. Sun, Z. Shi and S. Feng, *J. Phys. Chem. C*, 2008, **112**, 14878-14882.
22. A. A. Ismail and D. W. Bahnemann, *ChemSusChem*, 2010, **3**, 1057-1062.
23. M. Gouterman, *J. Mol. Spectrosc.*, 1961, **6**, 138-163.
24. N. C. Maiti, S. Mazumdar and N. Periasamy, *J. Phys. Chem. B*, 1998, **102**, 1528-1538.
25. M. Kasha, H. R. Rawls and M. A. El-Bayoumi, *Pure Appl. Chem.*, 1965, **11**, 371-392.
26. S. Cherian and C. C. Wamser, *J. Phys. Chem. B*, 2000, **104**, 3624-3629.
27. N. C. Maiti, M. Ravikanth, S. Mazumdar and N. Periasamy, *J. Phys. Chem.*, 1995, **99**, 17192-17197.
28. M. Gouterman and G.-E. Khalil, *J. Mol. Spectrosc.*, 1974, **53**, 88-100.
29. S. Verma, A. Ghosh, A. Das and H. N. Ghosh, *J. Phys. Chem. B*, 2010, **114**, 8327-8334.

Yamamoto et al.  
Porphyrin Derivative-Modified TiO<sub>2</sub> Photocatalysts for Visible-Light-Assisted Selective Catalytic Reduction of NO  
with NH<sub>3</sub>

Table 1. Peak positions of the soret band and Q bands

Sample	Loading of TCPP / $\mu\text{mol g}^{-1}$	Soret / nm	Q <sub>y(0, 1)</sub> / nm	Q <sub>y(0, 0)</sub> / nm	Q <sub>x(0, 1)</sub> / nm	Q <sub>x(0, 0)</sub> / nm
TCPP-TiO <sub>2</sub> -IMP	1.3	417	519	555	592	649
TCPP-TiO <sub>2</sub> -IMP	6.3	416	520	557	592	651
TCPP-TiO <sub>2</sub> -IMP	12.5	411	521	559	593	652
TCPP-TiO <sub>2</sub> -IMP	37.5	411	522	562	595	654
TCPP-TiO <sub>2</sub> -IMP	62.5	407	522	560	594	653
TCPP-TiO <sub>2</sub> -MIX	12.5	419	529	565	600	658
TCPP-SiO <sub>2</sub> -IMP	12.5	422	521	556	593	649
TCPP in MeOH	–	418	515	549	590	646

Yamamoto et al.  
Porphyrin Derivative-Modified TiO<sub>2</sub> Photocatalysts for Visible-Light-Assisted Selective Catalytic Reduction of NO  
with NH<sub>3</sub>

Table 2. Result of photo-SCR under various reaction conditions

Entry	Catalyst	Inlet gas conc. (ppm)			N <sub>2</sub> conc. <sup>a</sup> (ppm)
		NO (ppm)	NH <sub>3</sub> (ppm)	O <sub>2</sub> (%)	
1	TCPP-TiO <sub>2</sub> -IMP <sup>b</sup>	1000	1000	2	790
2	TCPP-TiO <sub>2</sub> -IMP <sup>b</sup>	0	1000	2	57
3	TCPP-TiO <sub>2</sub> -IMP <sup>b</sup>	1000	0	2	24
4	TCPP-TiO <sub>2</sub> -IMP <sup>b</sup>	1000	1000	0	42
5	TCPP-TiO <sub>2</sub> -IMP <sup>b</sup>	1000	1000	5	780
6	TCPP-TiO <sub>2</sub> -IMP <sup>b</sup>	1000	1000	10	771
7	TCPP-SiO <sub>2</sub> -IMP <sub>2</sub> <sup>b</sup>	1000	1000	2	63
8	TCPP-TiO <sub>2</sub> -MIX <sup>b</sup>	1000	1000	2	140

<sup>a</sup>Concentration of N<sub>2</sub> in the outlet gas. Catalyst amount: 110 mg (TiO<sub>2</sub>, TCPP-TiO<sub>2</sub>), 50 mg (TCPP-SiO<sub>2</sub>), <sup>b</sup>TCPP loading: 12.5 μmol g<sup>-1</sup>.

Yamamoto et al.  
Porphyrin Derivative–Modified TiO<sub>2</sub> Photocatalysts for Visible–Light–Assisted Selective Catalytic Reduction of NO  
with NH<sub>3</sub>

### Figure legends

Figure 1.

Title: Structures of porphyrin derivatives and conversion of NO in the photo–SCR over the various porphyrin derivative–modified TiO<sub>2</sub> photocatalysts after 6 h of visible–light irradiation (loading of porphyrin derivative: 18 μmol g<sup>-1</sup>, catalyst amount: 110 mg, NO: 1000 ppm, NH<sub>3</sub>: 1000 ppm, O<sub>2</sub>: 2 %, GHSV: 50,000 h<sup>-1</sup>).

Figure 2.

Title: UV–Vis diffuse reflectance spectra of (A) TiO<sub>2</sub>, (B) TCPP–TiO<sub>2</sub>, (C) TSPP–TiO<sub>2</sub>, (D) TPP–TiO<sub>2</sub>, (E)TMPP –TiO<sub>2</sub>, and (F)TAPP –TiO<sub>2</sub>.

Figure 3.

Title: UV–Vis diffuse reflectance spectra of various loading of TCPP–TiO<sub>2</sub>. (A) 0 μmol g<sup>-1</sup>, (B) 1.3 μmol g<sup>-1</sup>, (C) 6.3 μmol g<sup>-1</sup>, (D) 12.5 μmol g<sup>-1</sup>, (E) 37.5 μmol g<sup>-1</sup>, and (F) 62.5 μmol g<sup>-1</sup>.

Figure 4.

Title: Dependence of conversion of NO on TCPP loading on TiO<sub>2</sub> (catalyst amount: 110 mg, NO: 1000 ppm, NH<sub>3</sub>: 1000 ppm, O<sub>2</sub>: 2 %, GHSV: 50,000 h<sup>-1</sup>).

Figure 5.

Title: UV–Vis diffuse reflectance spectra of (A) TCPP–TiO<sub>2</sub>(IMP), (B) TCPP–SiO<sub>2</sub>, and (C) TCPP–TiO<sub>2</sub>(MIX), and adsorption spectra of 3.4×10<sup>-6</sup> mol L<sup>-1</sup> TCPP in methanol (D).


Yamamoto et al.  
Porphyrin Derivative-Modified TiO<sub>2</sub> Photocatalysts for Visible-Light-Assisted Selective Catalytic Reduction of NO  
with NH<sub>3</sub>

Figure 6.

Title: Photoluminescence spectra of (A) TCPP-TiO<sub>2</sub>-IMP, (B) TCPP in methanol, (C) TCPP-SiO<sub>2</sub>-IMP, (D) TCPP-TiO<sub>2</sub>-MIX, and (E) TCPP powder. The excitation wavelength was 410 nm. The spectra of (A), (C), (D), and (E) were measured at the voltage of photomultiplier tube of 700 V and spectrum (B) was of 450 V. Loading of TCPP was 12.5 μmol g<sup>-1</sup>, and the concentration of TCPP in methanol was 1.0×10<sup>-6</sup> mol L<sup>-1</sup>.

Figure 7.

Title: Conversion of NO during several on/off cycles of visible-light irradiation over the TCPP/TiO<sub>2</sub> photocatalyst: each cycle consisted of two-hours light on and off (TCPP loading: 12.5 μmol g<sup>-1</sup>, catalyst amount: 110 mg, NO: 1000 ppm, NH<sub>3</sub>: 1000 ppm, O<sub>2</sub>: 2 %, GHSV: 50,000 h<sup>-1</sup>).

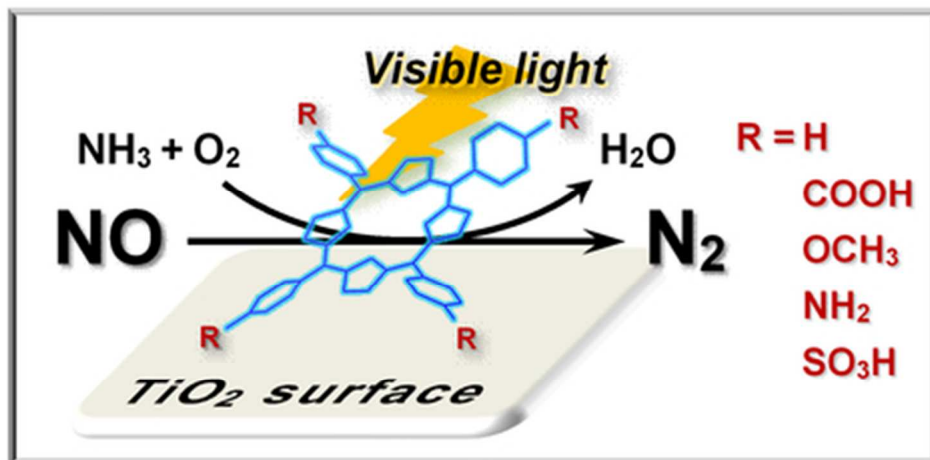

Porphyrin derivatives-modified  $TiO_2$  photocatalysts exhibited high activity for photo-assisted selective catalytic reduction of  $NO$  with  $NH_3$  ( $NH_3$ -SCR) under visible-light irradiation.  
39x19mm (300 x 300 DPI)

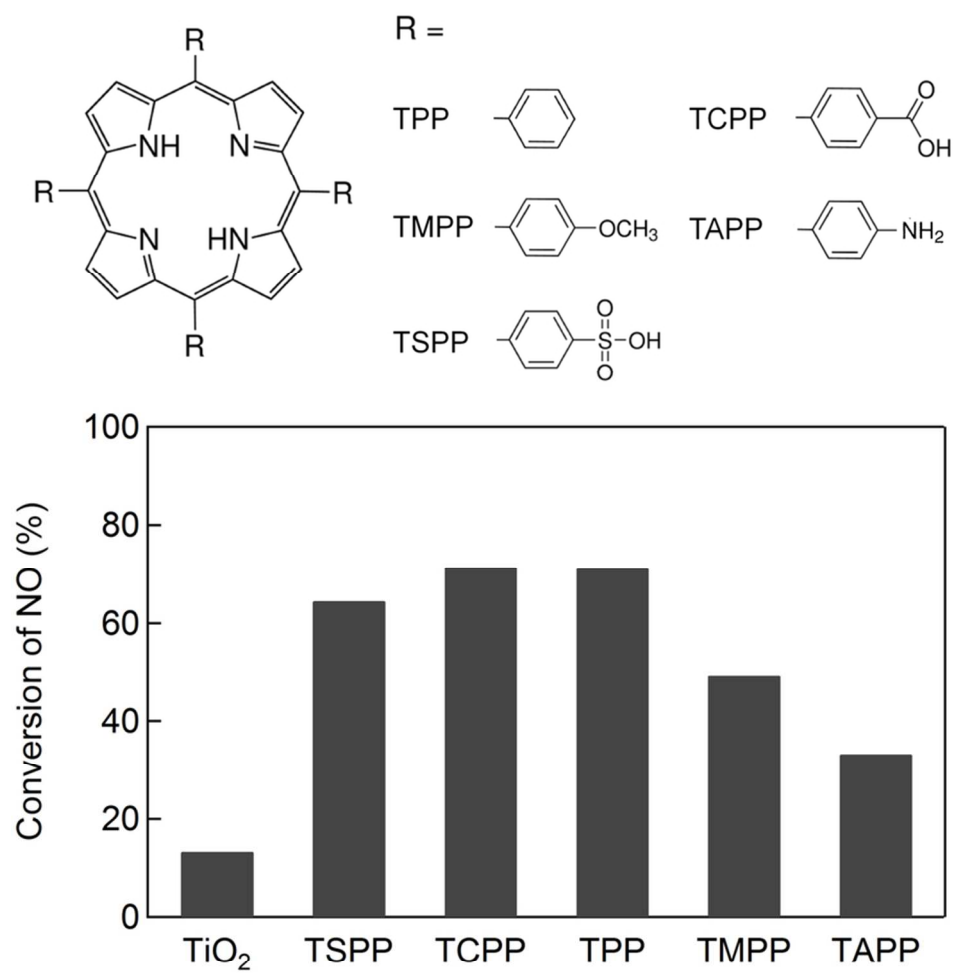


Figure 1.  
80x87mm (300 x 300 DPI)

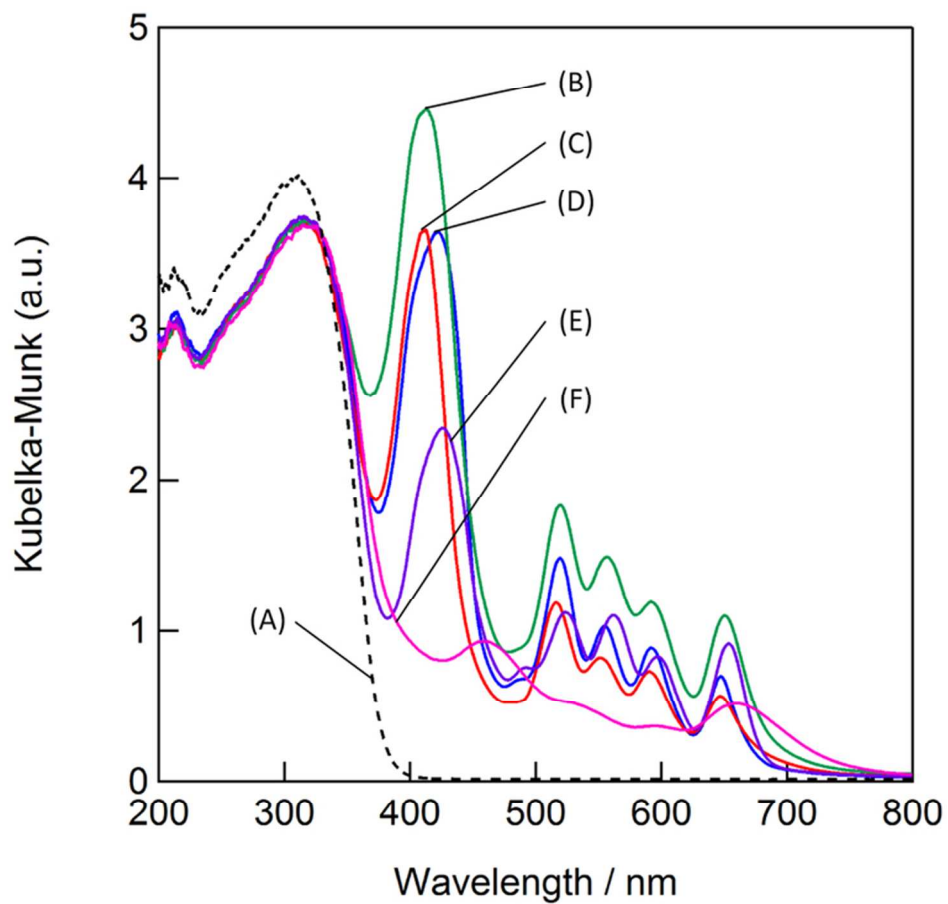


Figure 2.  
68x63mm (300 x 300 DPI)



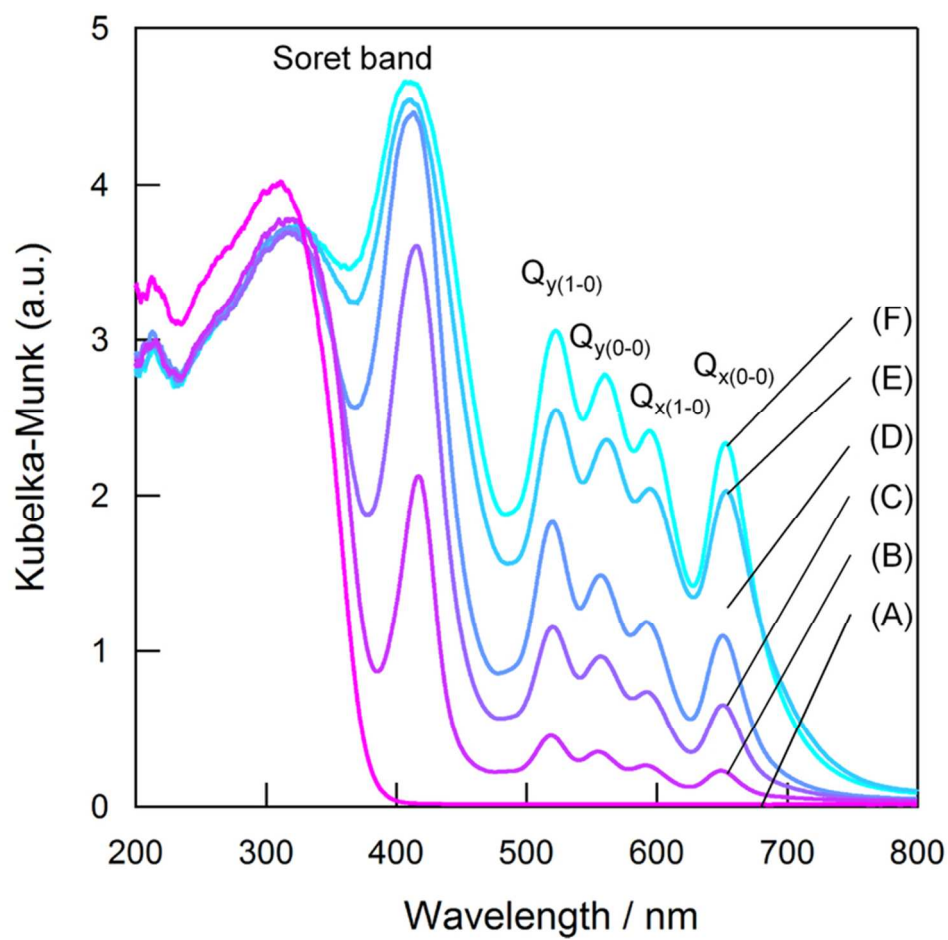


Figure 3.  
71x67mm (300 x 300 DPI)

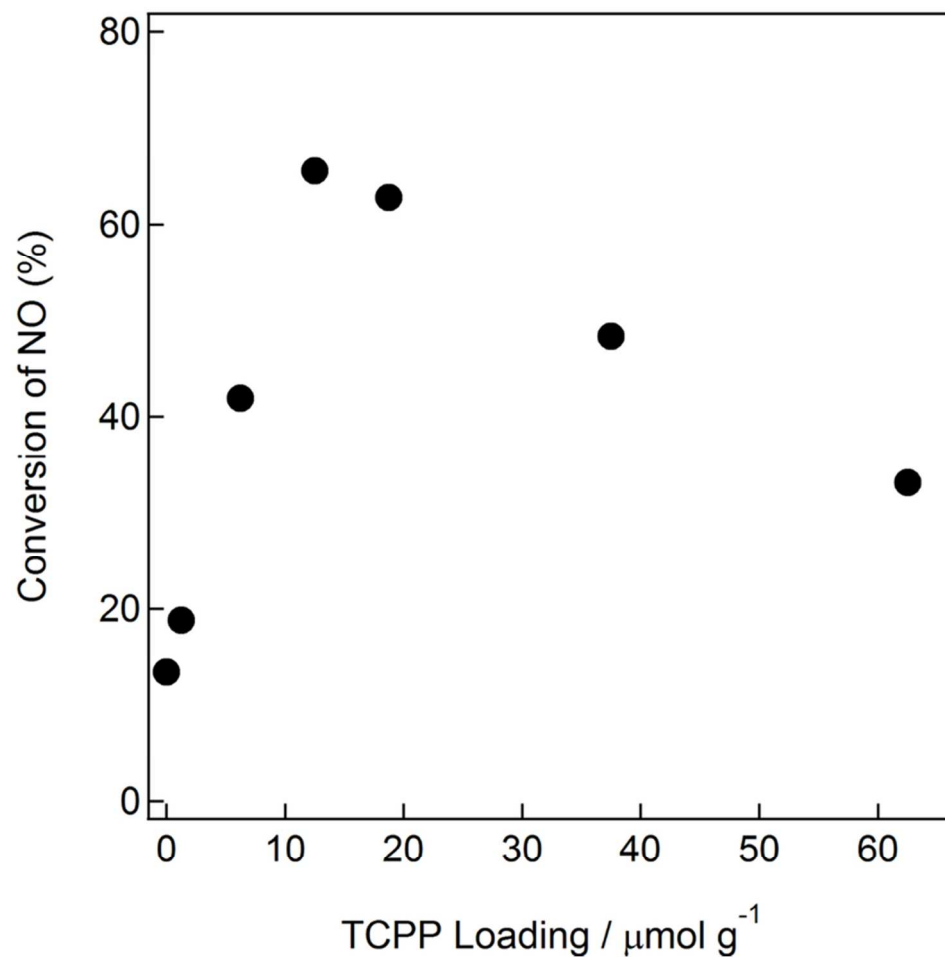


Figure 4.  
75x75mm (300 x 300 DPI)

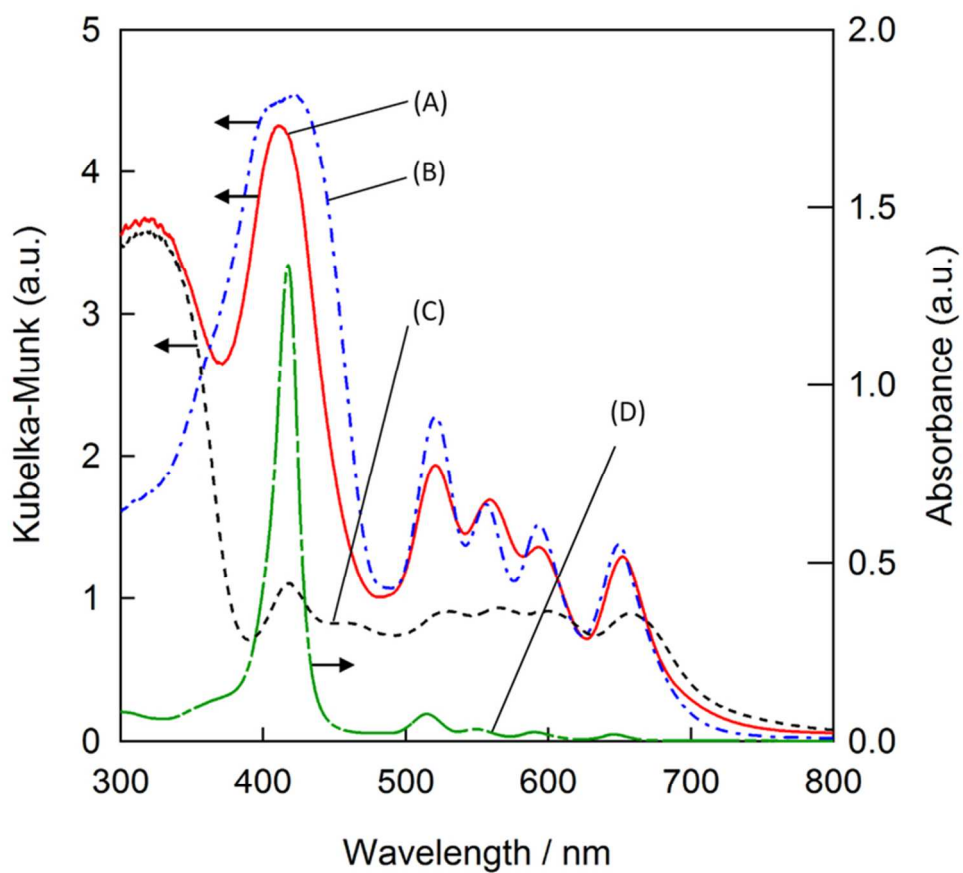


Figure 5.  
69x64mm (300 x 300 DPI)

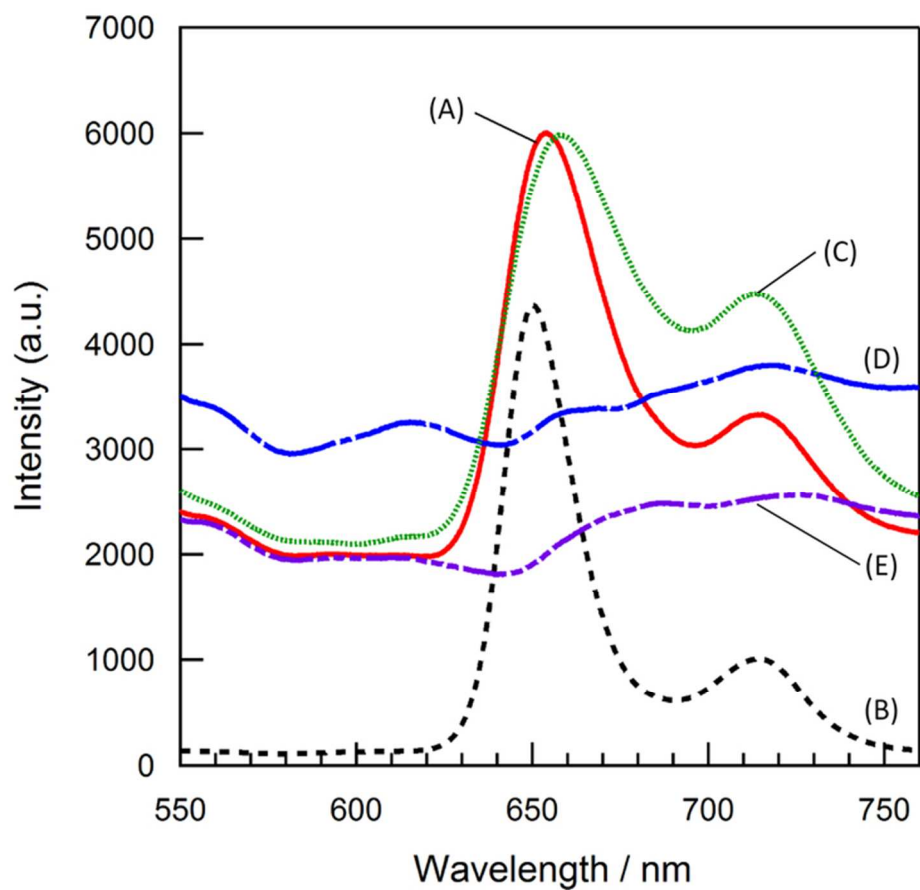


Figure 6.  
67x60mm (300 x 300 DPI)

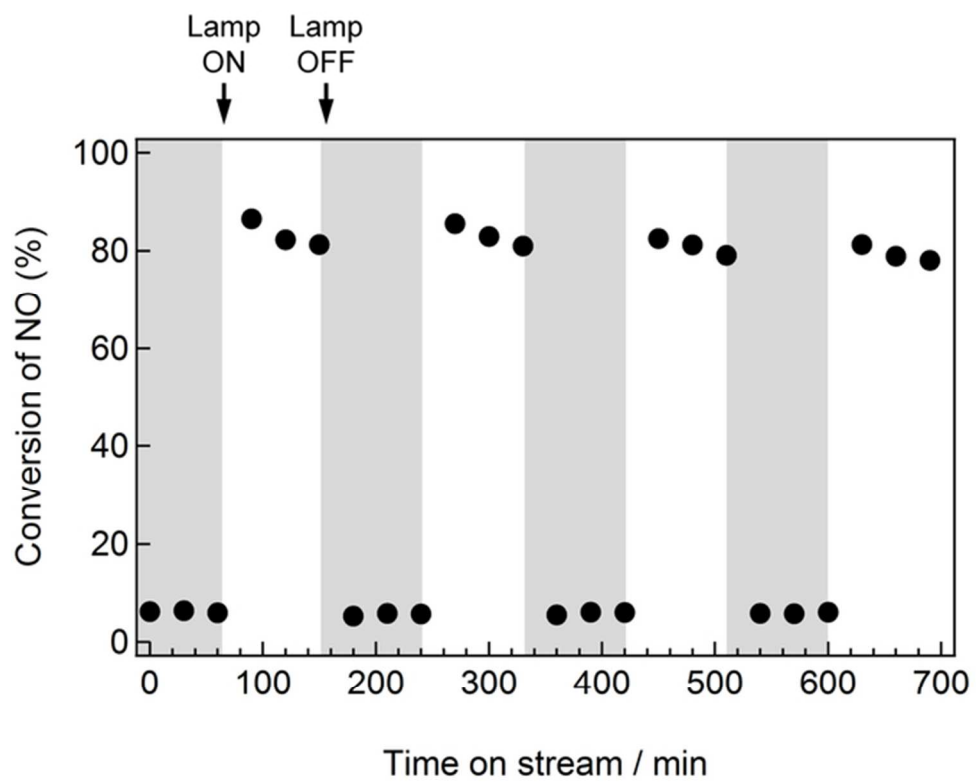


Figure 7.  
58x46mm (300 x 300 DPI)