

Catalysis Science & Technology

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

The relationship between the surface oxygen species and the acidic properties of mesoporous metal oxides and their effects on propane oxidation

Cite this: DOI: 10.1039/x0xx00000x

Shu Chen^a, Yanhua Li^a, Fei Ma^a, Fang Chen^a, Weimin Lu^{*a}

Received 00th January 2012,
Accepted 00th January 2012

Abstract

The V, Cu and Mo catalysts change the surface oxygen species of meso-Mn₂O₃ and have been used in the oxidation of propane. The oxygen species on the different catalysts were studied in detail including in situ IR of propane under aerobic and anaerobic conditions, X-ray Photoelectron Spectroscopy (XPS) and in situ IR of CO₂ adsorption. The in situ IR experiments of NH₃ showed changes of the Lewis and Brønsted acid on the catalysts. We discuss the relationship between acidic properties and oxygen species. The results showed that the performance of the catalysts was significantly affected by the different oxygen species.

DOI: 10.1039/x0xx00000x

www.rsc.org/

1 Introduction

Effective catalysts for deep oxidation (combustion) and selective oxidation are urgently needed because of environmental and industrial concerns. The deep oxidation catalysts mainly include manganese oxides such as Mn₂O₃ used for the total oxidation of organic compounds¹⁻⁶ owing to its high activity and high mobility of lattice oxygen.⁷⁻⁹ Recently, the modified Mn₂O₃ catalysts have gradually been applied to the selective oxidation of light alkanes due to its surface oxygen properties.¹⁰

The surface chemistry of Mn₂O₃ materials, especially surface oxygen species, is a very important factor that affects their utility as absorbents, catalysts and/or catalyst supports. Catalyst selectivity is largely governed by the nature of the surface oxygen species.¹¹⁻¹³ These same authors explained that the catalytic reaction occurs mainly due to the effect of lattice oxygen and adsorbed oxygen. Others¹ considered that active surface oxygen species could equally be nucleophilic (O²⁻) or electrophilic (O⁻²), and suggested Lewis acid sites (Mn⁺) to initiate the activation of C-H bonds and the involvement of nucleophilic O²⁻ surface species in total oxidation reactions. Thus far, the study of the role of the surface oxygen species in catalytic oxidation reactions is still controversial.

The acid properties are also taken seriously in the catalytic reaction like the oxygen species, but there is also debate about the role of the acidity. For propane oxidation, many authors believe that the acid property is a key factor for the catalytic activity. In the selective oxidation of propane to propylene, some authors reported that the amount of acid influenced the propane conversion, and the Brønsted acid affected the selectivity of propylene.¹⁴ Many reports considered the acid properties to be significant and used high surface area supporters like SBA-15 and meso-Al₂O₃ to load several

different elements including Mo and V to adjust the acidity of the catalysts, but ignored the reasons of the acid changes.^{15, 16} Therefore, it is favorable to enhance catalytic properties by adjusting catalyst acidity.

The synthesis and properties of bulk Mn₂O₃ materials have been intensively studied. Our group synthesized meso-Mn₂O₃ to improve the dispersion of some elements and to adjust the acidity of the catalysts and thus the distribution of the surface oxygen species. We loaded V, Cu and Mo on meso-Mn₂O₃ because V activates the α -H of propane and is acidic, Cu is the total oxidation element and Mo also activates the α -H of propane but is not as acidic as V. Here we study the influence of different acidic properties of the catalysts in the oxidation of propane and explore the relationship between the acid properties and the different oxygen species. Our goal is to understand propane oxidation by the different catalysts.

2. Experimental

2.1 Catalyst preparation

Ordered mesoporous silica with cubic Ia3d symmetry (KIT-6) was prepared from TEOS, P₁₂₃ (EO₂₀PO₇₀EO₂₀, MW = 5800), butanol, and HCl at 308 K.¹⁷

In a typical synthesis of ordered mesoporous Mn₂O₃ (meso-Mn₂O₃), 1 g of KIT-6 was added in 50 mL of acetone. After stirring at room temperature for 2 h, 2 mL of Mn(NO₃)₂ solution (C = 5.2446 mol/L) was added slowly under stirring. After stirring overnight, filtering and drying at room temperature, a dry powder was obtained, followed by calcination at 873 K for 3 h and removal of silica with 2 M NaOH solution in water. After washing with water and drying at 333 K, the meso-Mn₂O₃ is finally obtained.¹⁸

For comparison, bulk Mn_2O_3 was synthesized by thermal decomposition of MnCO_3 . As a typical run, an equal volume and concentration of Na_2CO_3 and MnCl_2 were mixed and stirred for 30 min. After washing and filtrating, the precipitate was dried at 373 K, and the resulting white powder (MnCO_3) was then calcined at 873 K in air for 4 h with a ramping rate of 2 K/min.

The introduction of various elements such as V, Mo, and Cu in the meso- Mn_2O_3 samples ($\text{MO}_x\text{-Mn}_2\text{O}_3$) were prepared from by an impregnation of meso- Mn_2O_3 with ammonium metavanadate, ammonium molybdate, or copper nitrate as the precursor. After stirring overnight, the catalyst was dried at 338 K for 12 h and calcined at 623 K in air for 3 h with a ramping rate of 2 K/min.

2.2. Catalyst characterization

The N_2 sorption isotherms were recorded on a TriStarII 3020 instrument at 77 K. Before measurement, the samples were evacuated at 473 K for 2 h. The specific surface area was determined by the Braunauer-Emmett-Teller (BET) method. High resolution transmission electron microscopy (HRTEM) used a JEOL-135 2010F TEM at an accelerating voltage of 200 kV. To prepare the TEM samples, a dilute particle-ethanol colloidal mixture was ultrasonicated for 30 min and a drop of solution was placed on a carbon coated Cu TEM grid. Powder XRD patterns of the samples were obtained on an X-ray diffractometer (XRD, Rigaku-D/Max-B automated powder X-ray diffractometer) operating at 45 kV and 40 mA using Cu $\text{K}\alpha$ radiation ($\lambda = 0.15418$ nm). The crystal phase was obtained by wide-angle scanning in range of 10 - 80° and low-angle scanning in range of 0.5 - 10°.

IR spectra were recorded with a BioRad, FTS-40A FT-IR spectrophotometer with an IR cell equipped with CaF_2 windows connected to a vacuum dosing system. The catalyst powder was pressed into self-supporting disc and activated at 200 °C in vacuum for 1 h before the adsorption experiments. *In situ* IR spectra of propane, propylene, and propane/ O_2 gaseous species were recorded under vacuum or 5% O_2/He at elevated temperature after the gas phase components in the IR cell were removed by evacuation. The spectrum of the adsorbed species was referenced to the background spectrum of the pretreated catalyst recorded under vacuum at the same temperature before the introduction of adsorbents. Because propane is inert, a slightly different protocol was used. A gas mixture of propane/oxygen was added to the catalyst at 323, 373, 423, 473 and 523 K. We then recorded the spectrum at each temperature.

For the IR spectra of NH_3 or CO_2 , all catalysts were pretreated under vacuum at 300 °C for 1 h and chemisorbed under NH_3 or CO_2 when the sample cooled to room temperature. Adsorption of NH_3 was performed at room temperature (rt), followed by evacuation to remove the adsorbed NH_3 . Adsorption of CO_2 was performed at room temperature for 1 h, followed by increasing the temperature to 323, 373, 423, 473, 523 and 573 K. Evacuation and stabilization times at each temperature were 20 min. The signal of the NH_3 or CO_2 desorption was analyzed by IR spectroscopy.

X-ray photoelectron spectroscopy (XPS) experiments used a Thermo ESCALAB 250 system with Al K radiation (1486.6 eV).

The X-ray anode operated at 150 W, and the binding energies were calibrated using the C1s line as a standard (284.8 eV).

2.3. Catalytic performance

The oxidation of propane was carried out in a tubular, fixed bed flow quartz reactor (i.d. 7.4 mm, 270 mm long) under atmospheric pressure. Catalyst (0.2 g) was used to test the catalytic performance. The feed stock of $\text{C}_3\text{H}_8/\text{O}_2$ had a molar ratio of 1.0 at GHSV = 4500 $\text{ml (g}\cdot\text{h)}^{-1}$ and reaction temperature at 480 °C. Products and reactants were analyzed by a dual channel on-line gas chromatograph equipped with both TCD and FID detectors and Porapak QS (4.0 $\text{m} \times 1/8$ in) and TDX-01 (2.0 $\text{m} \times 1/8$ in) columns.

3 Results and Discussion

3.1. Meso- Mn_2O_3 Characterizations

Fig. 1A shows TEM image of KIT-6, giving very ordered mesostructure. Fig. 1B shows TEM image of Meso- Mn_2O_3 , also giving ordered mesostructure. These results suggest that the mesostructure of the meso- Mn_2O_3 is well templated from the KIT-6 mesostructure. The sample HRTEM image (Fig. 1C) clearly exhibits hexagonally cubic close packed mesopores with crystalline walls. The sample Low-angle powder X-ray diffraction pattern (Fig. 1D) shows one sharp peak at $\sim 0.9^\circ$ and a broad peak at 1.7-1.8°, in good agreement with those of the Ia-3d space group. These results confirm that the meso- Mn_2O_3 crystals have ordered mesostructure.

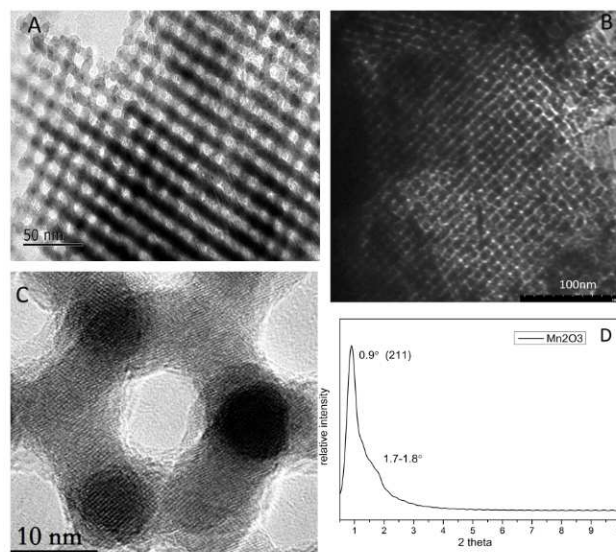


Fig.1 TEM images of (A) KIT-6 and (B) meso- Mn_2O_3 . HRTEM image of (C) meso- Mn_2O_3 and Low angle XRD patterns of (D) meso- Mn_2O_3 .

Figure 2 shows wide angle XRD patterns of meso- Mn_2O_3 , giving characteristic peaks associated with the $\alpha\text{-Mn}_2\text{O}_3$ (JCPDS No. 73-1826), where Mn(III) cations are surrounded by six oxygen atoms forming a distorted octahedron.¹⁹ Similarly, the bulk- Mn_2O_3 is also crystalline $\alpha\text{-Mn}_2\text{O}_3$. In addition, it does not observe the any metal oxide phase except for the $\alpha\text{-Mn}_2\text{O}_3$ in the Cu- Mn_2O_3 , V- Mn_2O_3 and Mo- Mn_2O_3 even if the metal

loading at 10%. This phenomenon suggests that the supported oxides had good dispersion in meso-Mn₂O₃. Furthermore, the sample Raman spectra (Fig.S1 and) show that there is a little oligomer of V and Mo species, while Cu species are highly dispersed. HAADF-STEM and elemental mapping images (Fig.S2A and Fig.S2B) prove the well dispersion of V and Mo on meso-Mn₂O₃.

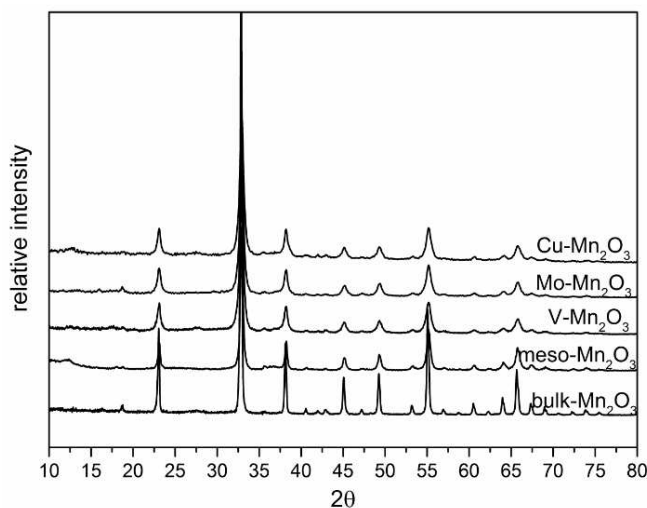


Fig.2 Wide-angle XRD patterns for bulk, meso-Mn₂O₃ and supported catalysts.

Table 1. Surface areas and average pore width (nm) of catalysts and KIT-6.

catalyst	KIT-6	meso-Mn ₂ O ₃	V-Mn ₂ O ₃	Cu-Mn ₂ O ₃	Mo-Mn ₂ O ₃
Area (m ² •g ⁻¹)	614	81	46	65	59
Average pore width (nm)	6.6	8.2	6.8	7.6	7.5

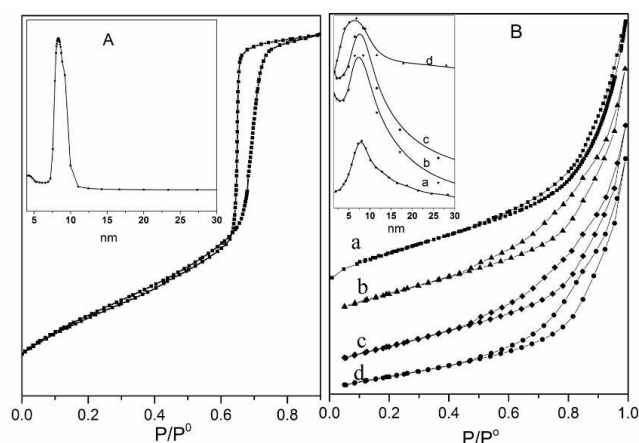


Fig.3. N₂ nitrogen sorption isotherms and average pore size distribution of (A) KIT-6, (B) catalysts: (a) meso-Mn₂O₃, (b) Cu-Mn₂O₃, (c) Mo-Mn₂O₃, (d) V-Mn₂O₃.

Figure 3 shows nitrogen sorption isotherms of the samples, giving typical type-IV adsorption. The Brunauer-Emmett-Teller

(BET) surface area for KIT-6 is 614 m²•g⁻¹, but the surface area of the meso-Mn₂O₃ is much smaller (81, m²•g⁻¹). After introduction of various elements as V, Mo, and Cu, the sample surface areas are further reduced, as summarized in Table 1. The pore size distributions, calculated from desorption isotherms, exhibit a narrow distribution centered at 6.6 nm for mesoporous KIT-6 and a bigger pore size (8.2 nm) for meso-Mn₂O₃. The pore size of the supported catalysts is centered nearby at 7 nm, which is smaller than meso-Mn₂O₃.

3.2 Catalytic tests in propane oxidation

Table 2 (Table.1S) presents catalytic data of the propane oxidation reaction performance over the different catalysts. Notably, they have similar conversion, but their product selectivities are quite distinguishable. Propane on meso-Mn₂O₃ underwent a deep oxidation reaction to yield CO₂ (sel. 58.2%) as the main product as well as ethylene (sel. 20.6%). All the loaded catalysts were compared with meso-Mn₂O₃ in the followed. After loading 10% CuO, the ethylene selectivity reduced (12.2%), while propylene as the selective oxidation product of propane increased (29.5%) and CO₂ selectivity remains 50%. After loading 10% MoO₃, the propylene selectivity (37.2%) increased, and the cleavage product of ethylene reduced while CO₂ is predominant and little CO was noted. The 10% V₂O₅ offered selective oxidation of propane and gave propylene as the primary product (sel. 51%). Because of these different products, we suggest that the catalysts have different reaction pathways.

The catalytic performance was measured at V loading levels of 1% to 15% to study the influence of different loading levels on the catalytic activity. The propane conversion is invariant from 24.4 to 28.8%. Increasing V has no impact except V loading levels of 15%. The selectivity of propylene increases from 17.4 to 51.0% with 10% V. Concurrently, the CO₂ selectivity drops greatly and CO rises.

Table 2. The performance of the catalysts. Reaction condition: Temperature 480°C, GHSV = 4500 mL (g h)⁻¹, and C₃H₈ : O₂ = 1 : 1 (molar ratio)

catalyst	Conversion (%)		Selectivity (%)		
	Propane	Ethylene	Propene	CO	CO ₂
meso-Mn ₂ O ₃	24.3	20.6	18.6	0.0	58.2
bulk-Mn ₂ O ₃	21.1	30.6	22.8	0.0	41.1
10%Mo-Mn ₂ O ₃	22.2	12.0	37.2	11.6	33.0
10%Cu-Mn ₂ O ₃	19.7	12.2	29.5	0.0	56.6
1%V-Mn ₂ O ₃	25.7	27.5	17.4	0.0	50.2
1%V-Mn ₂ O ₃	24.4	35.8	28.7	0.0	23.5
5%V-Mn ₂ O ₃	25.6	27.8	31.0	0.0	26.9
10%V-Mn ₂ O ₃	28.8	9.0	51.0	21.1	11.6
15%V-Mn ₂ O ₃	11.9	4.9	41.6	36.4	16.8

3.3 In-Situ IR analysis

The catalysts exhibited different catalytic activities after the different elements were loaded. To understand possible reaction pathways for the oxidation of propane, the surface species

formed by adsorption of the reactant (propane) and the reaction products (propylene), as well as the transformation of these species on the catalysts were studied with IR spectroscopy using both vacuum and different reaction atmospheres as well as temperature change.

3.3.1 *In-situ* IR collected in the reaction atmosphere

FT-IR spectra of the catalysts under the reaction atmosphere (propane : O₂ = 1:1) were recorded from 373 to 573 K (Fig.S3). For the meso-Mn₂O₃, the 1699 cm⁻¹ band at 373 K red-shifted to 1710 cm⁻¹ when the temperature increased but vanished at 573 K. This band can be assigned to the $\nu_{C=O}$ of acetone coordinated with different Lewis-acid site of the catalyst surface.²⁰ A new vibration at 1290 cm⁻¹ appears with increasing temperature but disappeared at 573 K. This peak is assigned to the carbonate adsorption on the surface of the catalyst and is considered to be a precursor salt of CO₂. Unlike meso-Mn₂O₃, the Cu-Mn₂O₃ catalyst showed low reactivity at low temperature (373 ~ 473 K). A strong band at 1259 cm⁻¹ is detected above 473 K, which means that a large number of carbonate exists. The band of 1650 cm⁻¹ is physical adsorption of alkenes, indicating that the reaction of the propane on the Cu-Mn₂O₃ produced propylene or ethylene. The 10% V-Mn₂O₃ and 10% Mo-Mn₂O₃ catalysts exhibit similar absorption spectra and have two weak bands near 1600 cm⁻¹ belonging to the Π -bonded propylene species interacting with Lewis acid sites on the surface of catalysts. The peak at 1255 cm⁻¹ is from the precursor of the carbon oxides. The difference between the V-Mn₂O₃ and Mo-Mn₂O₃ catalysts is that a vibration peak at 1715 cm⁻¹ appears with increasing temperature for the 10% V-Mn₂O₃. This implies that the catalytic reaction goes through the acetone step.^{21, 22}

Fig. 4 compares the FT-IR spectra of the catalysts at 573 K. The CO₂ vibration peak at 2350 cm⁻¹ is very strong for the meso-Mn₂O₃ and has intensity of: meso-Mn₂O₃ > Cu-Mn₂O₃ > Mo-Mn₂O₃ > V-Mn₂O₃. These results combined with the carbonate peak at 1250 cm⁻¹ verified that propane on the Cu-Mn₂O₃ and meso-Mn₂O₃ makes more CO₂ than the other catalysts. In addition, isopropanol intermediate (1065 cm⁻¹) and Π -bonded propene (1600 cm⁻¹) appeared both on V-Mn₂O₃ and Mo-Mn₂O₃, but the acetone peak (1715 cm⁻¹) is only seen on V-Mn₂O₃. These differences illustrate that the oxidation of propane on each catalyst under the reaction atmosphere occurs through two routes. One is mostly complete oxidation to give CO_x such as on the meso-Mn₂O₃ and Cu-Mn₂O₃. The other is primarily a selective oxidation to achieve olefins. The isopropanol salt intermediate is further oxidized to acetone and propylene on V-Mn₂O₃ during the reaction, but is further oxidized to propylene and CO₂ on Mo-Mn₂O₃. The Π -bonded propylene was not detected on the meso-Mn₂O₃ and Cu-Mn₂O₃ catalysts, but gaseous olefins at 1630 cm⁻¹ were detected on the Cu-Mn₂O₃. This is inconsistent with the fact that the propylene selectivity is as high as 51% in 10% V-Mn₂O₃. We next studied the adsorption and desorption reaction of propylene on the

catalysts to illustrate the huge differences in selectivity between the catalysts.

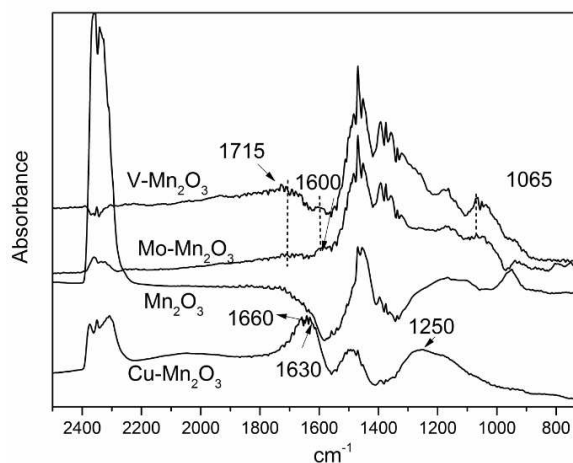


Fig.4 FT-IR spectra of reaction atmosphere (propane:O₂=1:1) adsorbed on 10% V-Mn₂O₃, 10% Cu-Mn₂O₃, 10% Mo-Mn₂O₃, and meso-Mn₂O₃ sample at 573 K.

3.3.2 *In-situ* IR of propylene adsorption

Fig.5 shows the IR spectra of the catalysts after adsorption of propylene at 323 K and their evolution at 373 K. Propylene adsorption on the meso-Mn₂O₃ was detected at 323 K. A broad vibration peak at 1600 cm⁻¹ belongs to the Π -bond propylene combined with a Lewis acid site, and a shoulder peak at 1630 cm⁻¹ is due to the physically adsorbed propylene.²² A new peak at 1670 cm⁻¹ appeared at 373 K, and the intensity of the Π -bonded propene at 1600 cm⁻¹ decreased. The peak of 1670 cm⁻¹ is regarded as the C=O in aldehyde. This is attributed to the reaction of the Π -bonded propene with the oxide species on the meso-Mn₂O₃ surface. This is evidence that propylene is prone chemisorption on the meso-Mn₂O₃ with resulting deep oxidation. The propylene adsorption on Cu-Mn₂O₃ is similar to meso-Mn₂O₃ at 323 K. The wide peak around 1630 cm⁻¹ could include both the vibration of the physical adsorption and Π -bonded propylene. After increasing the temperature to 373 K, a sharp peak at 1600 cm⁻¹ for the Π -bonded propylene appeared because the propylene easily desorbed. In the spectra of the V-Mn₂O₃ and Mo-Mn₂O₃, only the peak of physically adsorbed propylene (1630 cm⁻¹) remained at 323 K. It is markedly weakened as the temperature increases. When comparing different catalysts at 323 K (Fig. 5), we see that the intensity of propylene adsorption is: meso-Mn₂O₃ > Cu-Mn₂O₃ > V-Mn₂O₃ > Mo-Mn₂O₃. The Π -bonded propylene is seen only on meso-Mn₂O₃ and Cu-Mn₂O₃, and the intensity is stronger on meso-Mn₂O₃ than Cu-Mn₂O₃.

The results of the infrared spectra of propylene adsorption on the catalysts show that there are more Lewis acid sites that could easily produce a stable combination with propylene on the surface of Cu-Mn₂O₃ and meso-Mn₂O₃. After loading V and Mo, propylene adsorption is decreased. Considering the IR results of (propane + O₂) adsorption, the acid properties of the

catalysts affected propylene adsorption-desorption that in turn determined the selectivity of propylene and CO_x production.

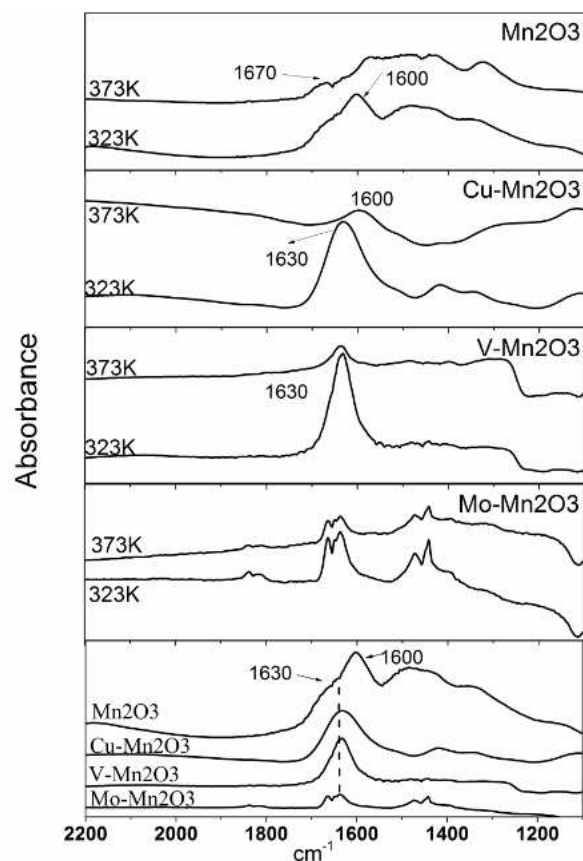


Fig.5. FT-IR spectra of propylene adsorbed on meso-Mn₂O₃, 10% V-Mn₂O₃, 10% Mo-Mn₂O₃, 10% Cu-Mn₂O₃ from 323 to 373 K, and the comparison of catalysts at 323 K.

3.3.3 *In-situ* IR of NH₃ adsorption

The nature of acid sites (Lewis and Brønsted) on the surface of the catalysts has been studied by IR spectroscopy of NH₃ as a probe molecule. The spectra arising from NH₃ adsorption at room temperature followed by evacuation at the same temperature are shown in Fig. 6.

Adsorption of NH₃ on the meso-Mn₂O₃ leads to the appearance of two strong IR bands at 1425 and 1610 cm⁻¹ corresponding to Brønsted (NH₄⁺ deformation vibrations) and Lewis acid sites, respectively.²³⁻²⁵ Adsorption of NH₃ on the Cu-Mn₂O₃ shows a strong band centered at 1600 cm⁻¹ and two bands from 1350 to 1470 cm⁻¹ that could be related to inhomogeneity of the Brønsted acid sites or a splitting of the δ_{as} vibration due to the adsorption symmetry of the NH₄⁺ molecule with the catalyst surface. The V-Mn₂O₃ and Mo-Mn₂O₃ show a weak IR band at 1640 cm⁻¹ and a medium-strong band at 1420 cm⁻¹. This suggests very little Lewis acid content and dominant Brønsted acid on the surface of these two catalysts. The amount of both Brønsted and Lewis acid sites in the meso-Mn₂O₃ and Cu-Mn₂O₃ samples is larger than those in the V-Mn₂O₃ and Mo-Mn₂O₃ samples: meso-Mn₂O₃ > Cu-Mn₂O₃ > V-Mn₂O₃ >

Mo-Mn₂O₃. The amount of Lewis acid changed more obviously as the dopant changed.

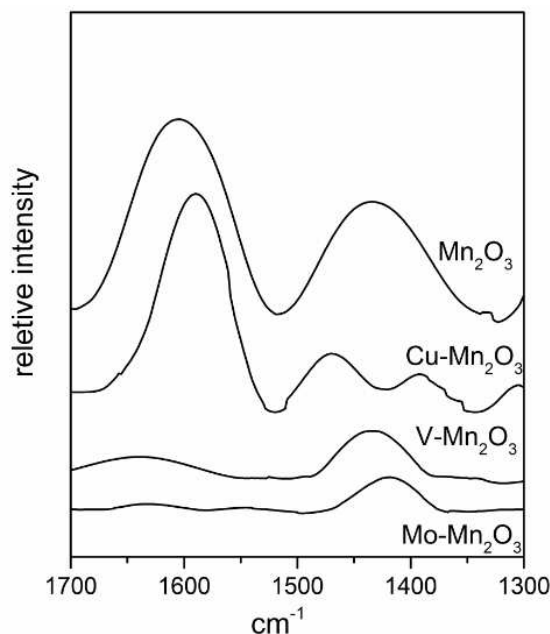


Fig.6 FT-IR spectra of NH₃ adsorbed and desorbed at room temperature on meso-Mn₂O₃, Cu-Mn₂O₃, V-Mn₂O₃, and Mo-Mn₂O₃.

The large number of Lewis acid on the meso-Mn₂O₃ and Cu-Mn₂O₃ is liable to adsorb propylene and then continues to be oxidized to CO₂ in the presence of a Brønsted acid. This caused greater than 50% selectivity for CO₂ on both catalysts. The low amounts of Lewis acid on the V-Mn₂O₃ and Mo-Mn₂O₃ allowed propylene to physically adsorb and then desorb. Thus, both catalysts have higher selectivity for propylene. With increasing V loading, the amount of Lewis acid is significantly reduced, and thereby the selectivity of propylene increased from 17.4 to 51%. Simultaneously, the selectivity of CO is influenced. Too much Lewis acid on the meso-Mn₂O₃ and Cu-Mn₂O₃ and low loadings (1%, 1%, and 5%) V-Mn₂O₃ resulted in no CO. Increasing V loadings reduced the Lewis acid and increased the CO selectivity as high as 36.4%. Thus, if a large number of Lewis acid sites exists on the surface of the catalysts, it is favorable to deep oxidation of propane and increases the selectivity of CO₂. That is, lower amounts of Lewis acids increase the selectivity for propylene and CO.

3.4 surface oxygen species

3.4.1 XPS and IR

The composition and oxidation state of the catalysts were confirmed by XPS. The XPS results (Table 3) account for the presence of charged oxygen atoms and hydroxyl oxygen (-OH). On the surface of meso-Mn₂O₃, the atomic percentage is 71.99% for O and 28.01% for Mn, respectively. These results indicate that the O : Mn atomic ratio (2.57:1) is much higher

than expected (1.5:1) and the test sample exposes oxygen-rich surfaces.

The sample of bulk-Mn₂O₃ has a lower O:Mn atomic ratio (2.35:1) than meso-Mn₂O₃, which indicates the oxygen-rich capacity of the meso-Mn₂O₃. The peaks of Mn 2p_{3/2} and Mn 2p_{1/2} are shown at 642.0 and 653.78 eV, respectively, and the spin-orbit splitting is 11.8 eV. These match well with the Mn₂O₃ data.²⁶ Two peaks appeared near 531.5 and 529 eV in the XPS profiles for the O 1s region (Fig. S4) and are attributed to oxygen O²⁻ in the lattice of Mn-O-Mn or low coordination O²⁻ anions in the bulk (O²⁻) and -OH in the interlayers or on the surfaces, respectively.²⁷⁻³⁰ The ratio of the two kinds of oxygen (-OH : O²⁻) on meso-Mn₂O₃ surface is the highest (0.774), while the bulk-Mn₂O₃ is only 0.432. After loading different elements, the ratio decreases in the order of Cu-Mn₂O₃ > V-Mn₂O₃ > Mo-Mn₂O₃, which is consistent with the changing amounts of Brønsted acid. The ratio of the two kinds of oxygen decreased upon increasing the amount of vanadium loading.

Table 3 Surface chemical composition of pure Mn₂O₃ and loaded catalysts by XPS.

Catalyst	Mn ³⁺ (%)	O ²⁻ (%)	M ^{x+} (%)	O ²⁻ /Mn ³⁺	-OH/O ²⁻ (area)
Meso-Mn ₂ O ₃	28.0	72.0	0	2.57	0.774
Bulk-Mn ₂ O ₃	29.8	70.2	0	2.35	0.432
10%Mo-Mn ₂ O ₃	22.5	71.7	5.76	3.18	0.428
10%Cu-Mn ₂ O ₃	21.5	69.6	8.85	3.22	0.773
10%V-Mn ₂ O ₃	21.0	71.9	1.63	2.66	0.454
1%V-Mn ₂ O ₃	26.1	73.5	0.43	2.81	0.500
5%V-Mn ₂ O ₃	24.6	74.2	1.15	3.01	0.473
15%V-Mn ₂ O ₃	27.0	70.7	2.34	2.61	0.261

^a M^{x+}: loaded metal elements.

We used *in situ* IR to verify the change in surface -OH. Fig. 7 shows a -OH vibration peak at 3700 cm⁻¹ in all the samples. The meso-Mn₂O₃ has maximum surface -OH, followed by Cu-Mn₂O₃, V-Mn₂O₃ and Mo-Mn₂O₃. The meso-Mn₂O₃ has a sharp and strong peak of -OH, while the intensity is very weak in bulk-Mn₂O₃. The -OH difference in meso- and bulk-Mn₂O₃ was further confirmed by XPS. It is clear that the changes of acidity in the supported catalyst are due to oxygen species on the catalyst surface.

Thus, the Brønsted acids depend on the amount of -OH that in turn affects propylene selectivity. With differing amounts of V, the Lewis and Brønsted acid reduced with increasing loading, while the propylene selectivity increased from 17.4% to more than 40% and CO₂ decreases significantly. At 10%V, the products are mainly propylene and CO. In short, the surface oxygen species changed the acid properties and thereby affected the reactive products of propane.

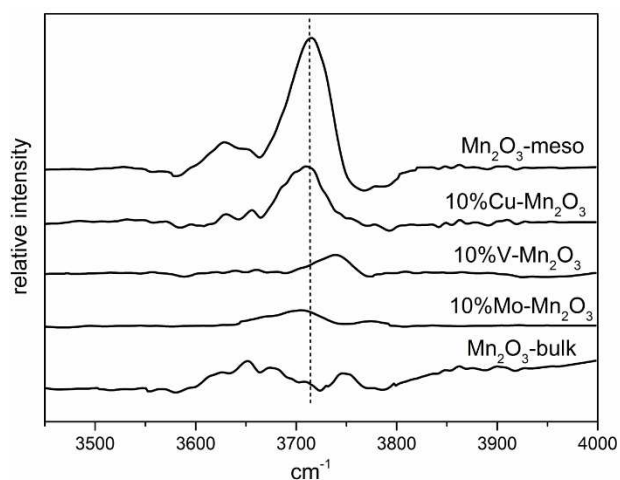


Fig. 7 FT-IR spectra of -OH on the surface of the samples.

3.4.2 The action of oxygen species

To illustrate the role of oxygen species in the reaction, the adsorption of propane on the catalysts under an oxygen-free atmosphere was measured by *in-situ* IR (Fig. 8). Meso-Mn₂O₃ and Cu-Mn₂O₃ show a C=C vibration peak near 1580 cm⁻¹ at 423K. The C=O peak at 2400 cm⁻¹ is attributed to CO₂ and increases as the temperature increases. For the Cu-Mn₂O₃ catalyst, a peak at 1722 cm⁻¹ belongs to the acetone vibration and emerges at 373 K, and also increases with increasing temperature. A weak peak of π -bonded propylene at 1591 cm⁻¹ is seen only on V-Mn₂O₃ at elevated temperatures. There is very little CO₂ on the V-Mn₂O₃ and Mo-Mn₂O₃ versus meso-Mn₂O₃ and Cu-Mn₂O₃. The Mo-Mn₂O₃ did not show any reaction intermediates of propane with increasing temperature. Thus, Mo-Mn₂O₃ does not have catalytic activity for propane under anaerobic conditions.

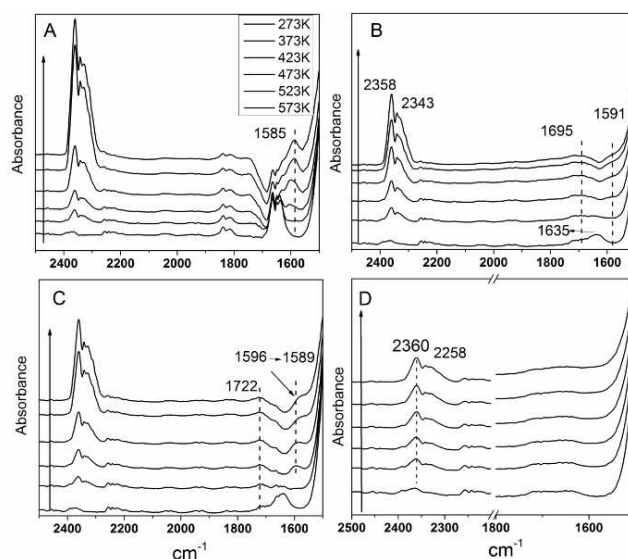


Fig. 8 FT-IR spectra of propane (in the absence of O₂) adsorbed on (A) meso-Mn₂O₃, (B) 10% V-Mn₂O₃, (C) 10% Cu-Mn₂O₃ and (D) 10% Mo-Mn₂O₃, from 323 to 573 K.

The reaction intermediate could be compared with the adsorption of propane under aerobic and anaerobic atmospheres on the different catalysts. This relates closely to the different products of propane. The reaction intermediate on meso-Mn₂O₃ is not detected except with significant CO₂ under aerobic atmosphere. However, the surface oxygen species on meso-Mn₂O₃ is involved in the reaction of propane. Here, olefins are generated under anaerobic conditions. Olefins and acetone appeared in the IR spectra of Cu-Mn₂O₃ in the anaerobic atmosphere. On the V-Mn₂O₃, the reaction intermediates of propylene and acetone and a trace of CO₂ were detected under both aerobic and anaerobic conditions. No olefins were detected under anaerobic conditions on the Mo-Mn₂O₃ as seen with aerobic conditions. The difference in performance under aerobic and anaerobic conditions suggested different exchanges between surface-bound and free oxygen.

The peak near 3800 cm⁻¹ is the -OH vibration on the surface of the catalysts (Fig. S5). The intensity of the peak decreases gradually as the temperature rises, and the trend is the same for all catalysts except Mo-Mn₂O₃. Therefore, the number of -OH on the surface of the catalysts has a great influence on the catalytic reaction of propane. The formation of acetone during propane adsorption suggests that propane is activated by removing a hydrogen atom from the methylene group. This is followed by bonding of the oxygen species nearby over the catalyst with the secondary carbon of the isopropyl species. This leads to the formation of an isopropoxy species as shown by Iglesia and co-workers.³¹ Thus, when the propane is adsorbed, different oxygen species on the surface of the catalysts are prone to oxidize, which is necessary for identification.

3.4.3 CO₂-IR

Infrared spectra recorded following CO₂ adsorption on catalysts at RT and subsequent temperature-programmed desorption are shown in Fig.9. A number of IR bands from 2000 to 1000 cm⁻¹ are observed when CO₂ was adsorbed on the catalysts. This was mainly due to the various types of carbonate-like (-CO₃) and bicarbonate (-HCO₃) species.³²⁻³⁶ There are three adsorption situations: unidentate carbonate, bidentate carbonate and bicarbonate. The formation of unidentate carbonate requires isolated surface O²⁻ ions, i.e. low-coordination anions such as those present in corners or edges. Bidentate carbonate forms on the Lewis acid-Brønsted base pairs (M²⁺-O²⁻ pair site), and the formation of bicarbonate species involves surface hydroxyl groups. The different CO₂ adsorption modes reveal that the surface of the catalysts may contain different oxygen species.

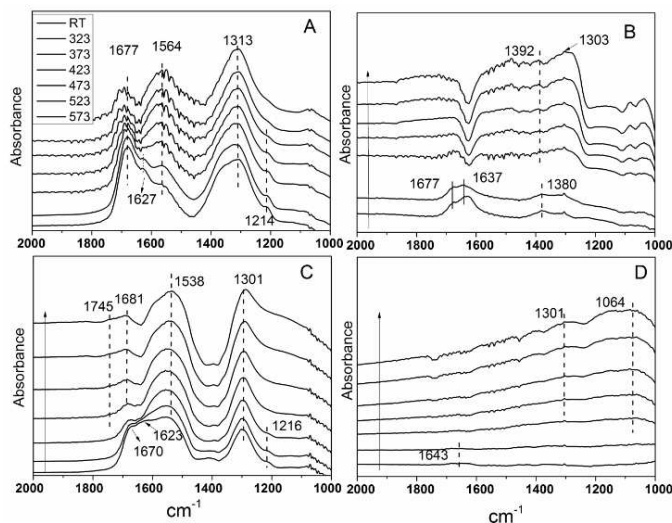


Fig.9 Infrared spectra of CO₂ adsorbed at 298 K on (A) meso-Mn₂O₃, (B) 10% V-Mn₂O₃, (C) 10% Cu-Mn₂O₃ and (D) 10% Mo-Mn₂O₃ taken as a function of temperature during progressive heating under vacuum.

On meso-Mn₂O₃, bicarbonates show a C-OH bending mode at 1214 cm⁻¹ as well as an asymmetric O-C-O stretching at 1677 cm⁻¹. The intensity of the two peaks reduced with increasing temperature. The C-OH bending mode at 1214 cm⁻¹ disappeared at 523 K, indicating that bicarbonate is prone to decomposition. Bidentate carbonate shows symmetric and asymmetric O-C-O vibrations at 1313 and 1627 cm⁻¹, respectively. The intensity of 1313 cm⁻¹ peak decreases slightly with temperatures up to 573 K indicating that bidentate carbonate is more stable than bicarbonates. Unidentate carbonate shows a vibration peak at 1564 cm⁻¹ that increased with increasing temperature. Of the three adsorption situations for meso-Mn₂O₃, bicarbonate is the most labile. Both the unidentate and bidentate carbonates remain on the surface after evacuation at 573 K. However, only the unidentate band is enhanced with rising temperature. The stability of adsorption suggests the strength order for the surface sites is as follows: O²⁻ ions > oxygen in M-O pairs > -OH groups.

The adsorption on Cu-Mn₂O₃ also has three carbonate vibrations in the IR (Fig. 9). Bicarbonates show a C-OH bending mode at 1216 cm⁻¹, as well as an asymmetric O-C-O stretching at 1670 cm⁻¹. This shifts to 1681 cm⁻¹ at 423 K. Bidentate carbonate vibration appears at 1301 and 1623 cm⁻¹. The peak of 1301 cm⁻¹ is stable at 573 K, but the peak at 1623 cm⁻¹ vanishes when the temperature rises. Unidentate carbonate shows a vibration peak at 1538 cm⁻¹ (asymmetric O-C-O stretching). Versus the meso-Mn₂O₃, the mode of the oxide species does not change on the surface of Cu-Mn₂O₃, but the amount on each mode does change. Bicarbonate species on Cu-Mn₂O₃ is less than that on the meso-Mn₂O₃, while the unidentate carbonate is much greater on Cu-Mn₂O₃ than on

meso-Mn₂O₃. Thus, Cu loading increased the isolated surface O²⁻ ions and decreased the -OH group.

The CO₂ adsorption intensity on the V-Mn₂O₃ is much weaker than that on the Cu-Mn₂O₃. Two peaks appear at 1677 and 1637 cm⁻¹ at room temperature and nearly disappear at 373 K. These are asymmetric O-C-O stretching vibrations of bicarbonates and bidentate carbonates, respectively. The unidentate carbonate shows a weak peak at 1380 cm⁻¹ (symmetric O-C-O stretching) and highlights the stability at 573 K. The adsorption of CO₂ on Mo-Mn₂O₃ is the weakest in all the catalysts. Weak bidentate carbonate appeared at 1643 cm⁻¹ and vanished with warming. No bicarbonates and unidentate carbonates were detected. These results also suggest the following content order for OH groups: meso-Mn₂O₃ > Cu-Mn₂O₃ > V-Mn₂O₃ > Mo-Mn₂O₃. For O²⁻ ion groups this trend is: Cu-Mn₂O₃ > meso-Mn₂O₃ > V-Mn₂O₃ > Mo-Mn₂O₃, and for oxygen in M-O pairs: meso-Mn₂O₃ > Cu-Mn₂O₃ > V-Mn₂O₃ > Mo-Mn₂O₃. The order for -OH groups is consistent with the results of XPS and IR.

In summary, the amount of -OH oxide species (-HCO₃) is the same as that of the Brønsted acid. This shows that the amount of Brønsted acid on the catalysts is completely determined and controlled by these oxygen species. From the association with the catalytic properties, it can be seen that this kind of oxygen species (i.e., Brønsted acid) mainly undergoes a deep oxidation process during propane oxidation and generates CO₂. It has been shown from the results of NH₃-IR and CO₂-IR that the change in Mn³⁺-O²⁻ pairs is the same as the Lewis acid. Thus, the Lewis acid-base pairs of Mn³⁺-O²⁻ on the surface of the catalysts are deemed to form Lewis acid sites. The decrease in Lewis acid-base pairs decreases the number of Lewis acid sites when the V content increases from 0.01 to 0.15. Meanwhile, the selectivity of CO₂ drops from 50.2 to 16.8%, and the selectivity of propylene rises from 17.4 to 50%. Although it could not be proven that propane on the Lewis acid-base pairs (Lewis acid sites) also generates CO₂, it is clear that a small amount of the Lewis acid-base pairs are unfavorable for CO₂ generation, but advantageous for propylene production.

When comparing V-Mn₂O₃ and Mo-Mn₂O₃ catalysts, they have nearly the same amount of -OH (Brønsted acid) from the results of IR and NH₃-IR, but have a big difference in propylene selectivity because the oxide species of Mn³⁺-O²⁻ pairs (Lewis acid sites) on V-Mn₂O₃ is more than that on Mo-Mn₂O₃. That is to say a certain amount of Mn³⁺-O²⁻ pairs favor propylene during propane oxidation.

Conclusions

The meso-Mn₂O₃ was loaded different elements (V, Mo and Cu) to change the acid properties of the catalysts and further influence the catalytic reaction pathways of probe molecules (propane). A large number of Brønsted acids (controlled by -OH) exist on the surface of the catalysts (meso-Mn₂O₃, Cu-Mn₂O₃). Brønsted acids mainly go through the deep oxidation process during propane oxidation and are conducive to the generation of CO₂. Lower amounts of Lewis acids are

advantageous to the selectivity of propylene and CO. The surface oxygen species were detected by XPS and CO₂-IR. A small amount of the Lewis acid-base pairs decreases CO₂ generation, but is advantageous for propylene. This implies that Mn³⁺-O²⁻ could be considered to form the Lewis acid sites. Different oxygen species play a different role on propane oxidation as propane molecules could carry out selective oxidation or complete oxidation reactions. Thus, these results provide a basis for managing complete or selective oxidation of light alkanes by adjusting the surface oxygen species.

Acknowledgements

The authors are grateful for the financial support of the National Science Foundation of China (Grant No. 21173186).

Notes and references

^a Institute of Catalysis, Zhejiang University (Xixi Campus), Hangzhou 310028, PR China.

1. M. A. Hasan, M. I. Zaki and L. Pasupulety, *J. Phys. Chem. B*, 2002, **106**, 12747.
2. V. P. Santos, M. F. R. Pereira, J. J. M. Orfao and J. L. Figueiredo, *Appl. Catal. B-Environ.*, 2009, **88**, 550.
3. Y. Liu, X.-S. Li, C. Shi, J.-L. Liu, A.-M. Zhu and B. W. L. Jang, *Catalysis Science & Technology*, 2014.
4. H. Li, G. Qi, Tana, X. Zhang, W. Li and W. Shen, *Catalysis Science & Technology*, 2011, **1**, 1677.
5. J. Verhelst, D. Decroupet and D. De Vos, *Catalysis Science & Technology*, 2013, **3**, 1579.
6. M. Baldi, V. S. Escribano, J. M. G. Amores, F. Milella and G. Busca, *Appl. Catal. B-Environ.*, 1998, **17**, L175.
7. S. J. A. Figueroa, F. G. Requejo, E. J. Ledo, L. Lamaita, M. A. Peluso and J. E. Sambeth, *Catal. Today*, 2005, **107-08**, 849.
8. S. L. Suib, *J. Mater. Chem.*, 2008, **18**, 1623.
9. M. A. Peluso, E. Pronsato, J. E. Sambeth, H. J. Thomas and G. Busca, *Appl. Catal. B-Environ.*, 2008, **78**, 73.
10. M. Baldi, E. Finocchio, C. Pistarino and G. Busca, *Appl. Catal. a-Gen.*, 1998, **173**, 61.
11. M. Che and A. J. Tench, *Adv. Catal.*, 1982, **31**, 77.
12. M. Che and A. J. Tench, *Adv. Catal.*, 1983, **32**, 1.
13. P. J. Gellings and H. J. M. Bouwmeester, *Catal. Today*, 1992, **12**, 1.

14. S. Chen, F. Ma, A. X. Xu, L. N. Wang, F. Chen and W. M. Lu, *Appl. Surf. Sci.*, 2014, **289**, 316.
15. X. T. Gao, J. L. G. Fierro and I. E. Wachs, *Langmuir*, 1999, **15**, 3169.
16. S. Rajagopal, J. A. Marzari and R. Miranda, *J. Catal.*, 1995, **151**, 192.
17. F. Kleitz, S. H. Choi and R. Ryoo, *Chem. Commun.*, 2003, 2136.
18. F. Jiao, A. Harrison, A. H. Hill and P. G. Bruce, *Adv. Mater.*, 2007, **19**, 4063.
19. V. Escax, M. Imperor-Clerc, D. Bazin and A. Davidson, *Cr Chim.*, 2005, **8**, 663.
20. X. D. Yi, X. B. Zhang, W. Z. Weng and H. L. Wan, *J. Mol. Catal. a-Chem.*, 2007, **277**, 202.
21. A. A. Davydov, V. G. Mikhaltchenko, V. D. Sokolovskii and G. K. Boreskov, *J. Catal.*, 1978, **55**, 299.
22. P. Concepcion, P. Botella and J. M. L. Nieto, *Appl. Catal. a-Gen.*, 2004, **278**, 45.
23. W. M. Zhang, P. G. Smirniotis, M. Gangoda and R. N. Bose, *J. Phys. Chem. B*, 2000, **104**, 4122.
24. P. G. Smirniotis, P. M. Sreekanth, D. A. Pena and R. G. Jenkins, *Ind. Eng. Chem. Res.*, 2006, **45**, 6436-6443.
25. A. M. Venezia, L. Palmisano, M. Schiavello, C. Martin, I. Martin and V. Rives, *J. Catal.*, 1994, **147**, 115.
26. H. Q. Dong, Y. Y. Chen, M. Han, S. L. Li, J. Zhang, J. S. Li, Y. Q. Lan, Z. H. Dai and J. C. Bao, *J. Mater Chem. A*, 2014, **2**, 1272.
27. M. I. Zaki, M. A. Hasan, L. Pasupulety and K. Kumari, *New J. Chem.*, 1998, **22**, 875.
28. W. S. Choi, *Electron Mater. Lett.*, 2012, **8**, 87.
29. N. Ohno, Y. Akeboshi, M. Saito, J. Kuwano, H. Shiroishi, T. Okumura and Y. Uchimoto, *Top Catal.*, 2009, **52**, 903.
30. X. J. Yang, Y. Makita, Z. H. Liu, K. Sakane and K. Ooi, *Chem. Mater.*, 2004, **16**, 5581.
31. K. D. Chen, A. T. Bell and E. Iglesia, *J. Catal.*, 2002, **209**, 35.
32. V. K. Diez, C. R. Apesteguia and J. I. Di Cosimo, *Catal. Today*, 2000, **63**, 53.
33. N. Hiyoshi, K. Yogo and T. Yashima, *Micropor. Mesopor. Mat.*, 2005, **84**, 357.
34. A. C. C. Chang, S. S. C. Chuang, M. Gray and Y. Soong, *Energ Fuel*, 2003, **17**, 468.
35. K. Pokrovski, K. T. Jung and A. T. Bell, *Langmuir*, 2001, **17**, 4297.
36. W. G. Su, J. Zhang, Z. C. Feng, T. Chen, P. L. Ying and C. Li, *J. Phys. Chem. C*, 2008, **112**, 7710.