

Catalysis Science & Technology

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Bi-functional NH₂-MIL-101(Fe) for One-Pot Tandem Photo-oxidation/Knoevenagel Condensation between Aromatic Alcohols and Active Methylene Compounds

*Dengke Wang and Zhaohui Li**

Research Institute of Photocatalysis, State Key Laboratory of Photocatalysis on Energy and Environment, College of Chemistry, Fuzhou University, Fuzhou 350002, People's Republic of China

* Author to whom all correspondences should be addressed.
E-mail: zhaohuili1969@yahoo.com

Abstract

Tandem reaction, which enables multistep reactions in one pot, offers enormous economical advantages. For the first time, this manuscript reported that NH₂-MIL-101(Fe), an earth abundant Fe-containing MOF material, can efficiently catalyze the one-pot reaction between aromatic alcohols and active methylene compounds via a tandem photo-oxidation/Knoevenagel condensation under visible light and at room temperature. NH₂-MIL-101(Fe) acts as a photocatalyst for the oxidation of aromatic alcohols to aldehydes as well as a base catalyst for Knoevenagel condensation between the as-formed aldehydes and the active methylene compounds. The comparison of the reactions over NH₂-MIL-101(Fe) and another two MOFs (NH₂-UiO-66(Zr) and NH₂-MIL-125(Ti)) reveals that the strength of the basic sites in the MOFs significantly influences the efficiency of the tandem reaction. This study highlights the great potential of MOFs as multifunctional photocatalysts for one-pot tandem reactions.

Keywords: tandem reaction; NH₂-MIL-101(Fe); photocatalytic oxidation; Knoevenagel condensation; base catalysis

Introduction

Tandem reaction, which enables multistep reactions in one pot, has attracted a great deal of attention since it avoids the isolation of intermediates and reduces the production of wastes, thus offering enormous economical advantages.¹ Multifunctional catalyst which contains different catalytically active sites in a site-isolation manner to maintain their independent function is usually required for an efficient one-pot tandem reaction. Currently most of the already reported one-pot tandem reactions involve homogeneous catalysts, which usually suffer from product contamination and limited recyclability. It is the current research focus to obtain multifunctional solid catalysts with controlled spatial arrangement of a high-density yet continuous range of different active sites for one-pot heterogeneous tandem reaction, yet it is still challenging.²

Metal-organic frameworks (MOFs) are a class of crystalline micro-mesoporous hybrid materials which have already shown a variety of applications.³ The inherent high specific surface areas, uniform but tunable cavities make MOFs to be promising heterogeneous catalysts.⁴ Since the constituent, topology and surface functionality of MOFs can be readily tuned by varying the metal ions or the bridging organic linkers, MOFs can be an interesting platform to engineer molecular solids for multifunctional catalysis.⁵ By adopting this strategy, bi/multi-functionalizations on MOFs have been achieved for catalyzing the one-pot tandem reactions.⁶ However almost all the investigated tandem catalytic reactions can only take effect at elevated temperature. Photocatalysis is a unique heterogeneous catalysis, which can make use of the solar light as the energy source to achieve the organic transformations under mild condition.⁷ Previous studies have revealed that MOFs can be promising photocatalyst for a variety of redox reactions, like CO₂ reduction, water reduction and photo-oxidation.⁸ The coupling of the current MOF-based catalysis with photocatalysis over multi-functional MOFs to achieve some tandem reactions under mild condition would be appealing, yet this field is almost unexplored. Until recently, Matsuoka et al. reported the one pot reaction between benzyl alcohol and malononitrile to synthesize benzylidene malononitrile over NH₂-UiO-66(Zr) via a coupled photooxidation and Knoevenagel condensation. Unfortunately, the reaction can only be achieved upon UV irradiations and when heated.^{6f} Unlike UV light responsive Zr-containing MOFs, all the Fe-based MOF materials already reported

show intensive light absorption in the visible light region due to the existence of extensive iron oxo-clusters, which enable them to take effective utilization of the solar energy. Moreover, iron is an earth-abundant metal, which makes it extremely appealing for applications of Fe-containing MOFs in the visible-light-induced photocatalysis coupled one-pot tandem reaction.

In this manuscript, we reported a one-pot tandem photo-oxidation/Knoevenagel condensation between benzyl alcohols and active methylene compounds over visible light irradiated NH₂-MIL-101(Fe) at room temperature. In addition to acting as a photocatalyst for the oxidation of aromatic alcohols to aldehydes, NH₂-MIL-101(Fe) acts as a base catalyst for Knoevenagel condensation between the as-formed aldehydes and the active methylene compounds. The mechanism for the tandem reaction over NH₂-MIL-101(Fe) was proposed. This study highlights the great potential of MOFs as multifunctional photocatalysts for one-pot tandem reactions.

Experimental Section

Preparation

All the reagents and solvents employed were commercially available and used as supplied without further purifications. NH₂-MIL-101(Fe) was prepared following the previously reported procedures.⁹ Typically, 0.675 g (2.497 mmol) of FeCl₃·6H₂O was dissolved in 7.5 mL of DMF, and a solution of 0.225 g (1.242 mmol) of 2-aminoterephthalic acid in 7.5 mL of DMF was added. After thermal treatment in a stainless steel autoclave for 24 h at 110°C, the reaction product was recovered by filtration, washed with DMF and methanol for several times. Then the obtained solid was finally dried overnight at 60°C in oven.

Characterizations

The as-prepared sample was characterized by X-ray diffraction (XRD) patterns on a D8 Advance X-ray diffractometer (Bruker, Germany) using Cu K_α (λ= 1.5406 Å) radiation at a voltage of 40 kV and 40 mA. XRD patterns were scanned over the angular range of 5-25° (2θ) with a step size of 0.02°. The IR experiments were carried out on a Nicolet 670 FT-IR spectrometer. N₂ adsorption/desorption experiments were carried out on a Micrometrics ASAP 2020 M volumetric gas sorption instrument. After the sample was degassed in a vacuum at 150°C for 10 h, the nitrogen adsorption and desorption isotherms were measured at -196°C. UV-vis diffuse reflectance

spectrum (UV-vis DRS) was obtained by a UV-vis spectrophotometer (Varian Cary 500). Barium sulfate (BaSO_4) was used as a reference. In the temperature-programmed desorption of CO_2 (CO_2 -TPD; Micromeritics Auto Chem 2920 instrument), the catalyst was pretreated at 150°C for 2 h. CO_2 was adsorbed at 40°C for 1 h. The sample was, then, flushed for 1 h to remove physical adsorbed CO_2 . The TPD was conducted from 40°C to 250°C at a heating rate of $10^\circ\text{C}/\text{min}$. The sample was then kept at 250°C for 2 min.

Catalytic Reactions

The photocatalytic oxidation of benzyl alcohol to benzyl aldehyde was performed as follows. In a typical process, a mixture of benzyl alcohol (0.1 mmol) and trifluorotoluene/acetonitrile (B/A, 10:1) (3.0 mL) saturated with O_2 was transferred into a 10mL schlenk tube containing 20 mg of catalyst. The suspension was irradiated with a 300 W Xe arc lamp (Beijing Perfectlight, PLS-SXE300c) with a UV cutoff filter ($\lambda \geq 420\text{nm}$). For the one-pot tandem reactions, a mixture of aromatic alcohol (0.1 mmol) and active methylene compounds (0.3 mmol) were reacted in B/A (10:1) (3.0 mL) saturated with O_2 . After the reaction, the reaction mixture was filtered through a porous membrane (20 μm in diameter) and the products were determined by GC (Shimadzu GC-2014) equipped with a flame ionization detector using a HP-5 capillary column.

Results and discussion

NH_2 -MIL-101(Fe) was synthesized using 2-aminoterephthalic acid (H_2ATA) as organic linker according to the procedures reported previously.⁹ The XRD patterns and FT-IR spectra of the as-obtained product indicate that pure phase of NH_2 -MIL-101(Fe) have been obtained (Fig. S1 and S2). The N_2 adsorption/desorption analysis on the as-obtained NH_2 -MIL-101(Fe) reveals a BET specific surface area to be $2476\text{ m}^2/\text{g}$, comparable to that reported previously ($2436\text{ m}^2/\text{g}$) (Fig. S3).^{9b} The UV-vis spectrum of the as-prepared NH_2 -MIL-101(Fe) shows the absorption edge extending to around 750 nm, in agreement with its brown color (Fig. S4).

Inspired by the previous report that photocatalytic oxidation of benzyl alcohol to aldehyde can be achieved over visible light irradiated NH_2 -UiO-66(Zr),¹⁰ we first investigated the visible-light-induced photocatalytic oxidation of benzyl alcohol over NH_2 -MIL-101(Fe). Like that over NH_2 -UiO-66(Zr), benzyl alcohol can also be

oxidized to benzyl aldehyde over irradiated NH₂-MIL-101(Fe) and the reaction medium played an important role in this reaction (Table S1). Among all the solvents investigated, a mixed solvent containing benzotrifluoride and acetonitrile (B/A) in a 10:1 ratio gave the best performance by showing the highest conversion of benzyl alcohol at 39% and a selectivity to benzyl aldehyde at 95% after irradiated for 40 h (Table S1, entry 4). Control experiments in absence of NH₂-MIL-101(Fe) or without light irradiations did not give any detectable product, indicating that the transformation of benzyl alcohol to benzyl aldehyde was truly induced by the photocatalysis over NH₂-MIL-101(Fe) (Table S1, entry 5 and 6).

Knoevenagel condensation between an active methylene compound and a carbonyl group (C=O) is a useful C-C bond coupling reaction for the preparations of several important chemical intermediates.¹¹ Previous result has showed that NH₂-MIL-101(Fe) can act as a Bronsted base to catalyze the Knoevenagel reaction between benzyl aldehyde and malononitrile due to the existence of the amine functionality.¹² We wondered whether it is possible to couple the photocatalytic oxidation of benzyl alcohol to benzyl aldehyde with the Knoevenagel condensation between benzyl aldehyde and malononitrile over NH₂-MIL-101(Fe) in a one-pot reaction. Therefore the reaction between benzyl alcohol and malononitrile in B/A (10:1), the best reaction medium observed on the photo-oxidation of benzyl alcohol, was investigated over visible light irradiated NH₂-MIL-101(Fe). To our anticipation, the reaction between benzyl alcohol with malononitrile over NH₂-MIL-101(Fe) gave benzylidene malononitrile as the main product, indicating the successful coupling of photo-oxidation with the Knoevenagel condensation in a one pot tandem reaction. As shown in Fig. 1, the formation of benzylidene malononitrile increased with the irradiation time and after irradiated for 40 h, the conversion of benzyl alcohol reached 88% with the yield of benzylidene malononitrile at 72% (Fig. 1a and Table 1, entry 1). In addition to benzyl aldehyde (5%) and benzylidene malononitrile, β -hydroxyl benzalmalononitrile with a yield of 9% was also detected. It is interesting to observe that the conversion of benzyl alcohol in the multi-component reaction is higher than that observed over photo-oxidation alone (39%, Table S1, entry 4), indicating that the removal of the intermediate (benzyl aldehyde) is beneficial to the photo-oxidation reaction. Controlled experiments in absence of either NH₂-MIL-101(Fe) or visible light irradiations under otherwise similar conditions gave almost negligible products,

indicating that the formation of benzylidene malononitrile was truly induced by the irradiated NH₂-MIL-101(Fe) (Table 1, entry 2 and 3). The heterogeneous nature of this reaction was confirmed by the filtrate reaction. No further reaction occurred in the filtrate after the solid catalyst was removed from the reaction system after 12 h irradiation (Fig. 1b). The recycling use of the photocatalyst for three runs showed no obvious decrease of the photocatalytic activity (Fig. 2). Besides this, the XRD, IR and N₂ adsorption/desorption isotherms of the photocatalyst after the reaction did not show much change (Fig. S5-7). All these suggest that NH₂-MIL-101(Fe) is stable and reusable during the reaction.

Having established that NH₂-MIL-101(Fe) can catalyze the one-pot reaction between benzyl alcohol and malononitrile, we extend the study to various substrates, including different alcohols and other active methylene compounds. First, a series of substituted aromatic alcohols were selected as the substrates and reacted with malononitrile. Although the transformations of all the aromatic alcohol derivatives to the corresponding benzylidene malononitriles proceeded under the reaction conditions, the different substituents on the phenyl ring influenced the conversion ratio and suggested the existence of an electronic effect. As compared with bare benzyl alcohol, aromatic alcohols with electron withdrawing substituent like -NO₂ showed significantly decreased conversion ratio (24%, Table 1, entry 4), while aromatic alcohols with *para*-substituted electron donating groups like -CH₃ and -OCH₃ exhibited slightly increased conversion ratio (90%-93%, Table 1, entry 5 and 6). The existence of the steric hindrance on this reaction was also observed since aromatic alcohols with methyl group (-CH₃) substituted at different positions of phenyl ring showed reaction rate in the order of *meta*- < *ortho*- < *para*- substituted (Table 1, entry 6-8). The reaction between the benzyl alcohol with other organics containing active methylene groups, like ethyl cyanoacetate or diethyl malonate, also occurred over NH₂-MIL-101(Fe) under visible light irradiations. But the performance for different substrates varied. For the reaction between ethyl cyanoacetate and benzyl alcohol, the reaction proceeded efficiently with 83% of benzyl alcohol converted in 40 h and a relative high yield of 66% to ethyl (benzylidene)cyanoacetate was achieved (Table 1, entry 9). On the contrary, the reaction between benzyl alcohol and diethyl malonate did not proceed smoothly. A low conversion of benzyl alcohol (18%) with an even lower yield to diethyl benzylidene malonate (2.7%) was observed (Table 1, entry 10).

The different reactivity of the methylene compounds can be well explained in terms of their different acidity, which decreases in the order of malononitrile ($pK_a = 11.1$) > ethyl cyanoacetate ($pK_a = 13.1$) > diethyl malonate ($pK_a = 16.4$).¹³ Since the first step of Knoevenagel condensation involves the deprotonation of the active methylene group, the higher pK_a value of the methylene group in diethyl malonate (16.4) indicates that the deprotonation of diethyl malonate is difficult, which leads to the low efficiency of the formation of diethyl benzylidene malonate via Knoevenagel condensation between benzyl aldehyde and diethyl malonate.¹⁴

The one-pot reaction between aromatic alcohols and active methylene compounds over NH_2 -MIL-101(Fe) via tandem photo-oxidation/Knoevenagel condensation can be well illustrated in the following Scheme 1. First, the aromatic alcohol was photocatalytically oxidized to aldehyde over irradiated NH_2 -MIL-101(Fe). It is believed that the organic linker ATA in NH_2 -MIL-101(Fe) acts as an antenna to absorb visible light. Upon irradiation, the excited ligand ATA can transfer electrons to the Fe-oxo clusters, and Fe^{3+} in the Fe-O clusters is reduced to Fe^{2+} , which can reduce O_2 to form $O_2^{\cdot-}$ radical (step a). In the meantime, the organic substrates adsorbed on the surface of the MOF material can donate an electron to form the carbonium ions (step b), which can further react with the as-formed $O_2^{\cdot-}$ radicals to form the aromatic aldehydes (step c). The confinement effect of the nanometer-sized cavities in MOF material helps to stabilize the as-formed $O_2^{\cdot-}$ radical and the reactive intermediates. Such a photo-oxidation mechanism has already been demonstrated previously over irradiated NH_2 -UiO-66(Zr).¹⁰ Due to the existence of the basic $-NH_2$ site in NH_2 -MIL-101(Fe), the as-formed aromatic aldehydes can further react with active methylene compounds via a Knoevenagel condensation. The first step in this process involves the deprotonation of the active methylene group under the assistance of the basic $-NH_2$ site in NH_2 -MIL-101(Fe) to form a carbonanion (step i). The as-formed carbon anion can make nucleophilic attack on the carbonyl carbon atoms of the aromatic aldehydes (step ii). The as-formed intermediate can take up one proton from the catalyst to form the β -hydroxyl compound and the catalyst is regenerated (step iii). Finally, the β -hydroxyl compound can eliminate one molecule of water to form the α,β -unsaturated compound (step iv).

The reaction between benzyl alcohol and malononitrile over other amine-functionalized photocatalytic active MOFs like NH_2 -MIL-125(Ti) and

NH₂-UiO-66(Zr) under visible light irradiations was also investigated and the results were shown in Table 2. Although the reaction between benzyl alcohol and malononitrile also led to the formation of benzylidene malononitrile over all three MOFs, both the conversion ratio of the benzyl alcohol and the yield to benzylidene malononitrile varied significantly among these MOFs. The yield to benzylidene malononitrile was much lower over irradiated NH₂-UiO-66(Zr) (4.6%) and NH₂-MIL-125(Ti) (3.3%) under otherwise similar reaction condition as compared to that over NH₂-MIL-101(Fe) (72%). However, the photocatalytic oxidation of benzyl alcohol to form benzyl aldehyde over NH₂-UiO-66(Zr) (28%) and NH₂-MIL-125(Ti) (37%) are comparable to that over irradiated NH₂-MIL-101(Fe) (39%) (Table S2). This indicates that the lower efficiency of the one-pot photo-oxidation/Knoevenagel condensation over NH₂-UiO-66(Zr) and NH₂-MIL-125(Ti) was induced by their lower efficiency in the Knoevenagel condensation, instead of the lower activity for the photo-oxidation. This assumption is confirmed by the control Knoevenagel reaction between benzaldehyde and malononitrile under otherwise similar conditions, which shows a similar activity order of NH₂-MIL-101(Fe) > NH₂-Uio-66(Zr) > NH₂-MIL-125(Ti) (Fig. S8).

Based on the proposed mechanism, the efficiency of Knoevenagel condensation is mainly depended on the deprotonation of the active methylene group. Therefore the strength of the basic site in different MOF materials should play an important role in the Knoevenagel reaction. To explore the basic characteristic of the above three MOF materials, their CO₂-TPD profiles were investigated and the results were shown in Fig. 3. TPD is a very useful technique for characterizing chemically bonded surface or adsorbed species and CO₂-TPD profile has been extensively used in determining the basic strength of the catalyst.¹⁵ As shown in Fig. 3(a), the CO₂-TPD profile of NH₂-MIL-101(Fe) shows three peaks at T_{max} of 118°C, 217°C and 240°C. The desorption peak occurs at 217°C can be ascribed to desorption of CO₂ adsorbed on the basic -NH₂ site. As compared with the CO₂-TPD file of NH₂-MIL-101(Fe), those of NH₂-UiO-66(Zr) and NH₂-MIL-125(Ti) also show big desorption peaks, corresponding to desorption of CO₂ adsorbed on basic site (-NH₂). However, the desorption peak of NH₂-UiO-66(Zr) occurs at 214°C (Fig. 3(b)), while that of NH₂-MIL-125(Ti) occur at 192°C (Fig. 3(c)). Since the basic strength of the catalyst is correlated with the desorption temperature in CO₂-TPD profile, the lower

desorption temperature observed over NH₂-UiO-66(Zr) and NH₂-MIL-125(Ti) indicate that the strength of the basic sites in these two MOFs are not as strong as that in NH₂-MIL-101(Fe). Therefore, the Knoevenagel condensation over NH₂-UiO-66(Zr) and NH₂-MIL-125(Ti) is not as efficient as that over NH₂-MIL-101(Fe).

Conclusion

In summary, NH₂-MIL-101(Fe) can catalyze the one-pot reaction between aromatic alcohols and active methylene compounds under visible light and at room temperature. NH₂-MIL-101(Fe) acts as a photocatalyst for oxidation of aromatic alcohols to aldehydes as well as a base catalyst for Knoevenagel condensation between the as-formed aromatic aldehydes and the active methylene compounds. The efficiency of the tandem reaction is significantly influenced by the strength of the basic sites in the MOF materials. We believe that the present study will stimulate intensive research in developing MOF-based multifunctional photocatalysts for one-pot tandem reactions. Considering the versatile structures of MOF materials and their facile modulations, it is believed that more and more multifunctional MOF-based photocatalysts for one-pot tandem reaction can be obtained.

Acknowledgments

This work was supported by NSFC (21273035), 973 Programs (2014CB239303) and Specialized Research Fund for the Doctoral Program of Higher Education (20123514110002). Z. Li thanks the Award Program for Minjiang Scholar Professorship for financial support.

Supplementary material

Electronic Supplementary Information (ESI) available: Experimental details; characterizations; figures of XRD, IR, BET and UV-vis; other catalytic reaction data. See DOI: 10.1039/b000000x/

References

- 1 (a) J. M. Lee, Y. Na, H. Han, and S. Chang, *Chem. Soc. Rev.*, 2004, **33**, 302; (b) J. -C. Wasilke, S. J. Obrey, R. T. Baker and G. C. Bazan, *Chem. Rev.*, 2005, **105**, 1001.
- 2 (a) J. M. Notestein and A. Katz, *Chem. Eur. J.*, 2006, **12**, 3954; (b) Y. Yang, X. Liu, X. Li, J. Zhao, S. Bai, J. Liu and Q. Yang, *Angew. Chem. Int. Ed.*, 2012, **51**, 9164; (c) C. Yu and J. He, *Chem. Commun.*, 2012, **48**, 4933.

- 3 (a) P. Horcajada, R. Gref, T. Baati, P. K. Allan, G. Maurin, P. Couvreur, G. Férey, R. E. Morris and C. Serre, *Chem. Rev.*, 2012, **112**, 1232; (b) T. R. Cook, Y. R. Zheng and P. J. Stang, *Chem. Rev.*, 2013, **113**, 734; (c) J. R. Li, J. Sculley and H. C. Zhou, *Chem. Rev.*, 2012, **112**, 869; (d) B. Chen, S. Xiang and G. Qian, *Acc. Chem. Res.*, 2010, **43**, 1115; (e) K. Sumida, D. L. Rogow, J. A. Mason, T. M. McDonald, E. D. Bloch, Z. R. Herm, T.-H. Bae and J. R. Long, *Chem. Rev.*, 2012, **112**, 724; (f) J. Lee, O. K. Farha, J. Roberts, K. A. Scheidt, S. T. Nguyen and J. T. Hupp, *Chem. Soc. Rev.*, 2009, **38**, 1450.
- 4 (a) A. Corma, H. García and F. X. L. i. Xamena, *Chem. Rev.*, 2010, **110**, 4606; (b) W. M. Xuan, C. F. Zhu, Y. Liu and Y. Cui, *Chem. Soc. Rev.*, 2012, **41**, 1677; (c) A. Dhakshinamoorthy, M. Opanasenko, J. Čejka and H. Garcia, *Catal. Sci. Technol.*, 2013, **3**, 2509; (d) W. -Y. Gao, M. Chrzanowski and S. Q. Ma, *Chem. Soc. Rev.*, 2014, **43**, 5841; (e) K. G. M. Laurier, F. Vermoortele, R. Ameloot, D. E. D. Vos, J. Hofkens, M. B. J. Roeffae, *J. Am. Chem. Soc.*, 2013, **135**, 14488; (f) A. Dhakshinamoorthy, M. Alvaro and H. Garcia, *Catal. Sci. Technol.*, 2011, **1**, 856; (g) D. K. Wang, R. K. Huang, W. J. Liu, D. R. Sun, Z. H. Li, *ACS Catal.*, 2014, **4**, 4254.
- 5 (a) C. Wang, D. Liu and W. B. Lin, *J. Am. Chem. Soc.*, 2013, **135**, 13222 (b) J. Gascon, A. Corma, F. Kapteijn and F. X. L. i Xamena, *ACS Catal.*, 2011, **1**, 1734; (c) T. Truong, C. K. Nguyen, T. V. Tran, T. T. Nguyen and N. T. S. Phan, *Catal. Sci. Technol.*, 2014, **4**, 1276.
- 6 (a) M. Yoon, R. Srirambalaji and K. Kim, *Chem. Rev.*, 2012, **112**, 1196; (b) R.-Q. Zou, H. Sakurai and Q. Xu, *Angew. Chem., Int. Ed.*, 2006, **45**, 2542; (c) R. Srirambalaji, S. Hong, R. Natarajan, M. Yoon, R. Hota, Y. Kim, Y. H. Ko and K. Kim, *Chem. Commun.*, 2012, **48**, 11650; (d) M. Pintado-Sierra, A. M. Rasero-Almansa, A. Corma, M. Iglesias and F. Sánchez, *J. Catal.*, 2013, **299**, 137; (e) F. Vermoortele, R. Ameloot, A. Vimont, C. Serre and D. D. Vos, *Chem. Commun.*, 2011, **47**, 1521; (f) T. Toyao, M. Saito, Y. Horiuchi and M. Matsuoka, *Catal. Sci. Technol.*, 2014, **4**, 625; (g) B. Li, Y. Zhang, D. Ma, L. Li, G. Li, G. Li, Z. Shi and S. Feng, *Chem. Commun.*, 2012, **48**, 6151; (h) P. Y. Wu, C. He, J. Wang, X. J. Peng, X. Z. Li, Y. L. An and C. Y. Duan, *J. Am. Chem. Soc.*, 2012, **134**, 14991.
- 7 X. J. Lang, X. D. Chen and J. C. Zhao, *Chem. Soc. Rev.*, 2014, **43**, 473.
- 8 (a) Y. H. Fu, D. R. Sun, Y. J. Chen, R. K. Huang, Z. X. Ding, X. Z. Fu and Z. H. Li, *Angew. Chem. Int. Ed.*, 2012, **51**, 3364; (b) D. R. Sun, Y. H. Fu, W. J. Liu, L. Ye, D. K. Wang, L. Yang, X. Z. Fu and Z. H. Li, *Chem. Eur. J.*, 2013, **19**, 14279; (c) Y. Horiuchi, T. Toyao, M. Saito, K. Mochizuki, M. Iwata, H. Higashimura, M. Anpo and M. Matsuoka, *J. Phys. Chem. C*, 2012, **116**, 20848; (d) C. Wang, Z. G. Xie, K. E. deKrafft and W. B. Lin, *J. Am. Chem. Soc.*, 2011, **133**, 13445; (e) M.

- H. Xie, X. –L. Yang, C. Zou and C. –D. Wu, *Inorg. Chem.*, 2011, **50**, 5318.
- 9 (a) S. Bauer, C. Serre, T. Devic, P. Horcajada, J. Marrot, G. Férey and N. Stock, *Inorg. Chem.*, 2008, **47**, 7568; (b) M. Savonnet, E. Kockrick, A. Camarata, D. Bazer-Bachi, N. Bats, V. Lecocq, C. Pinel and D. Farrusseng, *New J. Chem.*, 2011, **35**, 1892.
- 10 J. L. Long, S. B. Wang, Z. X. Ding, S. C. Wang, Y. G. Zhou, L. Huang and X. X. Wang, *Chem. Commun.*, 2012, **48**, 11656.
- 11 (a) M. J. Climent, A. Corma and S. Iborra, *Chem. Rev.*, 2011, **111**, 1072; (b) S. Shylesh, A. Wagner, A. Seifert, S. Ernst and W. R. Thiel, *Chem. Eur. J.*, 2009, **15**, 7052.
- 12 M. Hartmann and M. Fischer, *Microporous Mesoporous Mater.*, 2012, **164**, 38.
- 13 (a) W.N. Olmstead and F.G. Bordwell, *J. Org. Chem.*, 1980, **45**, 3299; (b) F.G. Bordwell and H.E. Fried, *J. Org. Chem.*, 1981, **46**, 4328; (c) B. R. Gelin and M. Karplus, *J. Am. Chem. Soc.*, 1975, **26**, 6996.
- 14 Y. Yang, H. –F. Yao, F. –G. Xi and E. –Q. Gao, *J. Mol. Catal. A: Chem.*, 2014, **390**, 198.
- 15 L. K. Ono and B. R. Cuenya, *J. Phys. Chem. C*, 2008, **112**, 18543.

Captions for Figures

Fig. 1 Conversion ratio of benzyl alcohol as a function of irradiation time in one-pot tandem reaction over (a) NH₂-MIL-101(Fe); (b) reaction system after NH₂-MIL-101(Fe) was removed after irradiated for 12 h.

Fig. 2 Conversion of benzyl alcohol (▨) and yields to benzaldehyde (▩), benzylidene malononitrile (▧) in the one-pot tandem reaction over NH₂-MIL-101(Fe) for recycling use.

Fig. 3 CO₂-TPD profiles of CO₂ adsorbed MOF materials: (a) NH₂-MIL-101(Fe); (b) NH₂-UiO-66(Zr); (c) NH₂-MIL-125(Ti).

Caption for Tables

Table 1 Reaction between substituted aromatic alcohols and active methylene compounds over NH₂-MIL-101(Fe).

Table 2 One-pot tandem reaction over different MOFs.

Caption for Scheme

Scheme 1 Proposed mechanism for one-pot tandem photocatalytic oxidation/Knoevenagel condensation over bi-functional NH₂-MIL-101(Fe).

Fig. 1

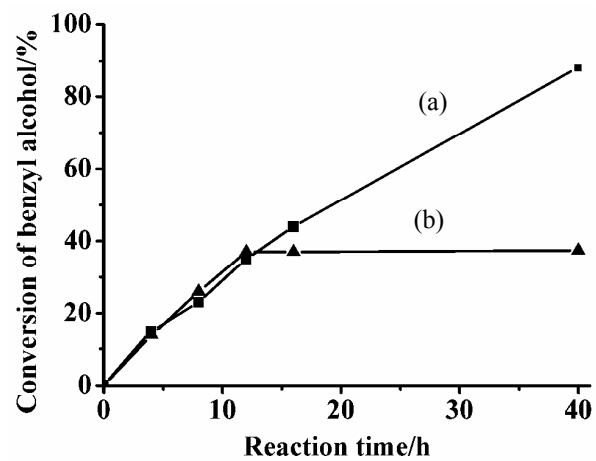


Fig. 2

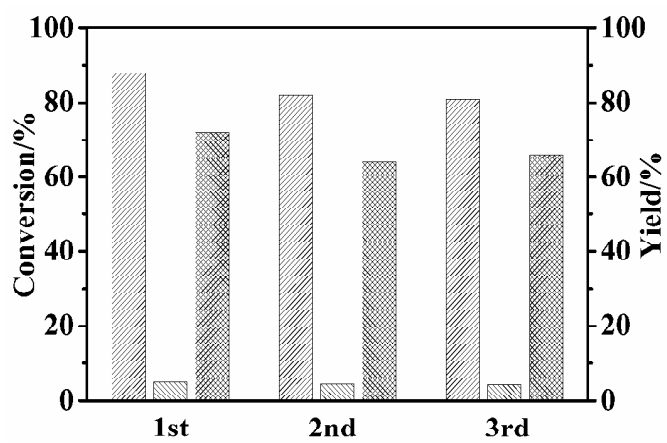


Fig. 3

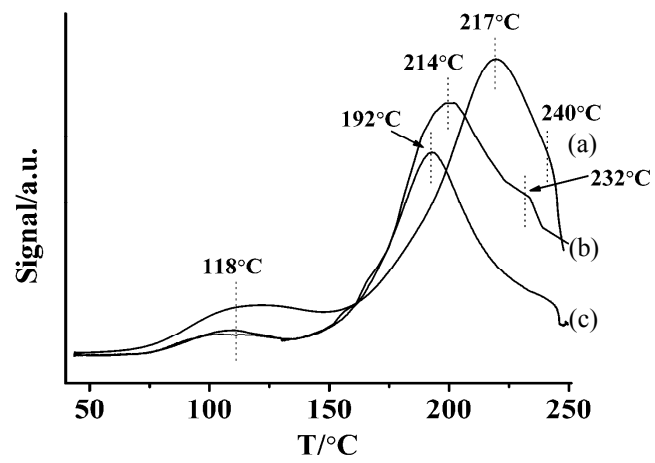


Table 1

entry	substrates		conv. of alcohol (%)	yield (%)	
	R ₁ =				
1	-H	R ₂ ,R ₃ = -CN	88	5	72
2 ^[a]	-H	R ₂ ,R ₃ = -CN	0.9	- ^[c]	-
3 ^[b]	-H	R ₂ ,R ₃ = -CN	0.8	-	-
4	-NO ₂	R ₂ ,R ₃ = -CN	24	3.7	20
5	<i>p</i> -OCH ₃	R ₂ ,R ₃ = -CN	93	8	76
6	<i>p</i> -CH ₃	R ₂ ,R ₃ = -CN	90	5.5	76
7	<i>m</i> -CH ₃	R ₂ ,R ₃ = -CN	80	7	63
8	<i>o</i> -CH ₃	R ₂ ,R ₃ = -CN	82	6.1	66
9	-H	R ₂ = -CN R ₃ = -COOEt	83	5.4	66
10	-H	R ₂ ,R ₃ = -COOEt	18	12	2.7

Reaction conditions: aromatic alcohols (0.1 mmol), methylene compounds (0.3 mmol), B/A (10:1) (3 mL), NH₂-MIL-101(Fe) (20 mg), O₂ (1 atm), light irradiation ($\lambda \geq 420$ nm), 40 h. [a] Without visible light irradiation. [b] No catalyst. [c] “-” refers to no products or negligible products have been detected.

Table 2

entry	catalyst	conv. of alcohol (%)	yield (%)	
			benzyl aldehyde	benzylidene malononitrile
1	NH ₂ -MIL-101(Fe)	88	5	72
2	NH ₂ -UiO-66(Zr)	38	29	4.6
3	NH ₂ -MIL-125(Ti)	47	39	3.3

Reaction conditions: benzyl alcohol (0.1mmol), malononitrile (0.3mmol), B/A (10:1) (3mL), MOFs (20mg), O₂ (1atm), light irradiation ($\lambda \geq 420\text{nm}$), 40h.

Scheme 1

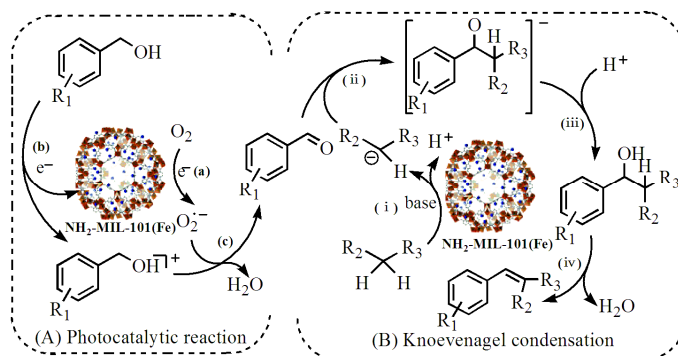


Table of Content

Bi-functional NH₂-MIL-101(Fe) can efficiently catalyze the one-pot reaction between aromatic alcohols and active methylene compounds via a tandem photo-oxidation/Knoevenagel condensation under visible light and at room temperature.

