

Dalton Transactions

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

Structure, stability and photocatalytic H₂ production by Cr-, Mn-, Fe-, Co-, and Ni-substituted decaniobate clusters

Jung-Ho Son,^{*a} Jiarui Wang^a and William H. Casey^{*a,b}

Received (in XXX, XXX) Xth XXXXXXXXX 20XX, Accepted Xth XXXXXXXXX 20XX

DOI: 10.1039/b000000x

Here we report synthesis and characterization of early transition-metal(TM)-substituted decaniobates as a continuation of our previous report of tetramethylammonium (TMA) salt of FeNb₉ and NiNb₉:

TMA₆[H₂Cr^{III}Nb₉O₂₈]·14H₂O (**1**, CrNb₉), TMA₈[Mn^{III}Nb₉O₂₈]·29H₂O (**2**, MnNb₉) and

TMA₇[H₂Co^{II}Nb₉O₂₈]·25H₂O (**3**, CoNb₉). Among the TM-substituted decaniobates, CoNb₉ or NiNb₉

exhibit a higher photocatalytic H₂ evolution activity in methanol-water mixtures than others.

Early transition-metal (TM) substituted Keggin-type polyoxotungstates have been studied for decades because of their rich electrochemical, optical, magnetic and catalytic properties.¹ In group 5 polyoxometalate chemistry, decametallate ions with D_{2d} symmetry, such as decavanadate and decaniobate (Nb₁₀) ions, are well known,² but TM-substituted decametallates are rare, although Ti^{IV}-, Fe^{III}-, Ni^{II}-substituted decaniobates (henceforth denoted: FeNb₉ and NiNb₉, respectively) and Pt-substituted decavanadate have been synthesized.³ Herein we describe the synthesis of the Cr-, Mn-, and Co-substituted decaniobates, and examine the trend in their structural, magnetic, optical, and photocatalytic H₂-evolution properties. These substituted decaniobates exhibit different stabilities and ease of synthesis that seem to be relatable to their structures. Moreover, the clusters show photocatalytic H₂-evolution, with Ni- and Co-substituted decaniobate ions being more active than other substituted decaniobates, although the molecules partly dissociate during irradiation into the corresponding MO_x and niobate. The results can aid the understanding of the factors governing the photocatalytic H₂-evolution properties of TM-doped metal oxides, including titanates,⁴ other niobates,⁵ and related polyoxoniobate systems.⁶

Isolation of tetramethylammonium (TMA) salts of Cr-, Mn- and Co-substituted decaniobates in this paper, TMA₆[H₂Cr^{III}Nb₉O₂₈]·14H₂O (**1**, CrNb₉), TMA₈[Mn^{III}Nb₉O₂₈]·29H₂O (**2**, MnNb₉) and TMA₇[H₂Co^{II}Nb₉O₂₈]·25H₂O (**3**, CoNb₉) was more challenging than our previously work on the Fe- and Ni-substituted decaniobates. We noticed that in the chromium-substitution reaction, CrNb₉ coexisted with previously reported [Cr₂(OH)₄Nb₁₀O₃₀]⁸⁻ (Cr₂Nb₁₀) in most of the syntheses.⁷ These structurally distinct clusters were separable by taking advantage of their slightly different solubility. Firstly, TMA salt of Cr₂Nb₁₀ was extracted with ethanol, and remaining TMA salt of CrNb₉/Nb₁₀ mixture was extracted with ethanol/methanol to yield an extract of **1**. Crystallization of **2** and **3** were challenging because of the slow decomposition of MNb₉ (M = Mn or Co) to

Nb₁₀ in the viscous liquid product. The color of the oily product changed from purple to brown (MnNb₉) and pink to blue (CoNb₉) during the crystallization attempt, concomitant with Nb₁₀ crystal formation. This observation suggests decomposition of MNb₉ cluster and oxidation of the corresponding released transition metal oxide (M=Mn or Co) by O₂ in air. However, we were able to isolate decent amount of MnNb₉ and CoNb₉ crystals (28 and 45% yields, respectively) by cooling the concentrated ethanolic solution after extraction. Decomposition of Mn- and Co-substituted decaniobate structures during storage was avoided by prompt filtration by washing with ethanol, followed by drying and storage *in vacuo*. On the other hand, Cr-, Fe- or Ni-substituted decaniobate ions did not decompose noticeably either during the long crystallization step in a viscous liquid product or upon storage in air.

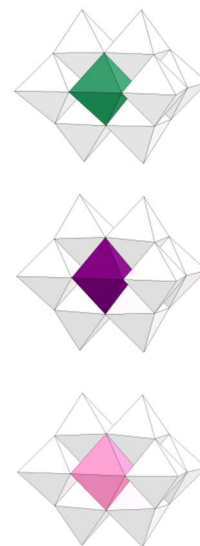


Fig. 1 Polyhedral model of MNB₉ clusters (M=Cr^{III}, Mn^{III} and Co^{II}, from top to bottom) in **1-3** (white: Nb, green: Cr, purple: Mn, pink: Co).

Electrospray-ionization mass spectrometry (ESI-MS) was used to

determine the identities of substituted decaniobates [Fig. 2]. The purified samples were dissolved in water for ESI-MS analyses. ESI-MS of **1-3** shows peaks in the lower m/z region compared to Nb_{10} due to the substitution of one Nb^{V} site with an early TM of lower atomic mass than niobium. ESI-MS also indicates a single-site substitution, as was confirmed by X-ray crystallography (*vide infra*). We find no evidence of multiple site substitution, in spite of exploration of other reagent stoichiometries and/or different reaction temperatures.

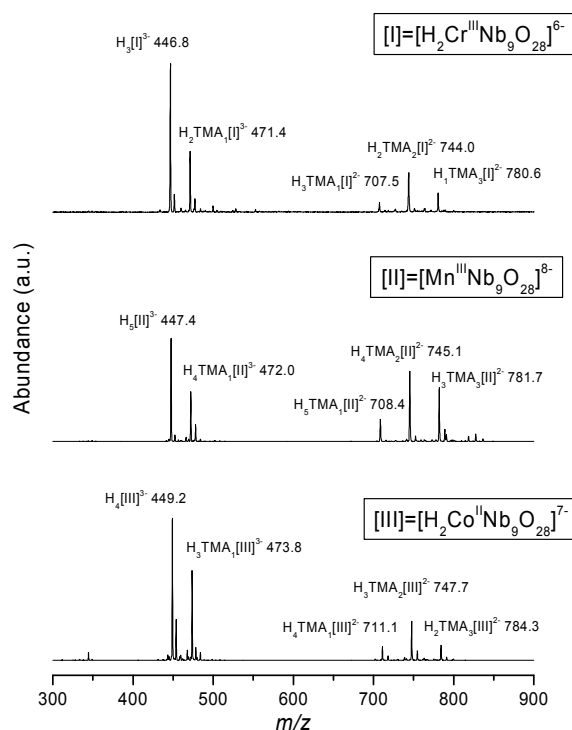


Fig. 2 ESI-MS of compounds **1-3** dissolved in water (from top to bottom).

Structures of the substituted decaniobate clusters with Cr, Mn and Co substituents were determined by X-ray single crystallography. The results show that the substitution occurred exclusively at the central site of the decaniobate moiety, similar to other substituted decaniobate structures ($\text{M}=\text{Ti}$, Fe, Ni) [Fig. 1].³ Bond-valence sum (BVS) calculations of metal centres suggest the oxidation state of the metals as Cr^{III} (2.86 and 2.90), Mn^{III} (3.07) and Co^{II} (1.92) [Table S1]. We note that some Mn^{IV} -included heteropolyniobate clusters have been reported previously.⁸ Numbers of TMA counteranions found in the crystal structures of **1-3** are 6, 8 and 7, respectively, and these numbers agree well with the elemental analysis results. Thus the formulae of the clusters in **1-3** can be expressed as $[\text{H}_2\text{Cr}^{\text{III}}\text{Nb}_9\text{O}_{28}]^{6-}$, $[\text{Mn}^{\text{III}}\text{Nb}_9\text{O}_{28}]^{8-}$ and $[\text{H}_2\text{Co}^{\text{II}}\text{Nb}_9\text{O}_{28}]^{7-}$, respectively. In the CrNb_9 structure, two protons are found on the two $\mu_2\text{-O}$ atoms between Cr and Nb. Protons were not found in the electron-density map of the CoNb_9 structure, but BVS calculation of the two $\mu_2\text{-O}$ bound to Co (0.983 and 1.013) suggests that two $\mu_2\text{-O}$ between Co and Nb are protonated, as in the CrNb_9 molecule. In MnNb_9 structure, BVS values of all Mn-bound oxygen atoms are higher than 1.5, supporting a conclusion that MnNb_9 is not protonated. While Cr^{III}

and Co^{II} retained their oxidation state from the source reagent, Mn^{II} from the reagent was oxidized to Mn^{III} in the cluster, which might have happened in the hydrothermal synthesis condition.

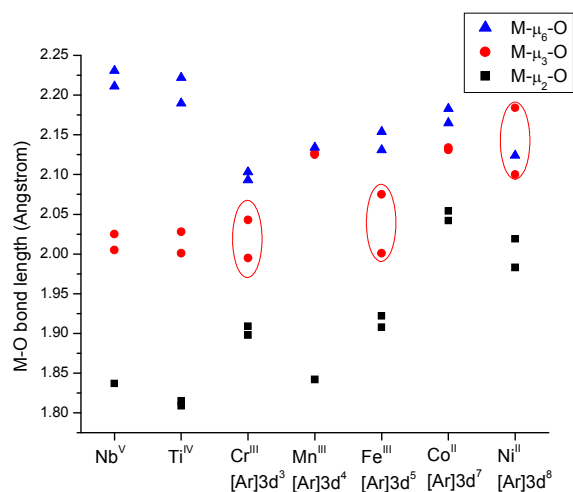


Fig. 3 The central M-O bond lengths in decaniobate and TM-substituted decaniobates. X-axis shows corresponding central atoms and their electron configurations.

Enough of these MNb_9 structures are now available to compare the M-O bond lengths [Fig. 3]. We find that the $\text{M-}\mu_6\text{-O}$ and $\text{M-}\mu_2\text{-O}$ lengths increase from Cr to Co then decrease slightly for the Ni-substituted molecule. This trend is similar to the Shannon's ionic radii of the TM ion series.⁹ We speculate that a discrepancy in this trend for MnNb_9 is due to the disordered central site with half occupancy of Nb in the structure of MnNb_9 . We point out that two axial *trans* $\text{M-}\mu_3\text{-O}$ bonds are asymmetric in Cr, Fe and Ni derivatives of the MNb_9 , while those in Mn- and Co-substituted MNb_9 are more symmetric [Fig. 3]. Larger differences in the axial *trans* $\text{M-}\mu_3\text{-O}$ bond lengths are observed as the group number of the substituted metal increases (The red stretched circles are shown the same size to better indicate how asymmetry increases as one moves to the right in the Fig. 3). We note that clusters with large asymmetry in the axial $\text{M-}\mu_3\text{-O}$ bonds have greater stability than clusters with symmetric $\text{M-}\mu_3\text{-O}$ bond lengths: MnNb_9 and CoNb_9 slowly decomposed to Nb_{10} in the viscous crude product, as described above. The correlation is interesting but inconclusive and but immediately suggests a useful computational study.

An ESI-MS titration of 2 mM solutions of each cluster was performed to compare the stabilities of the substituted decaniobates as a function of pH [Fig. S1-S3]. The varying intensity of the strongest peak of each ESI-MS data (445-450 m/z) was plotted to evaluate the stability of the each substituted decaniobate clusters according to pH [Fig. 4]. While **1-3** show similarly decreasing peak abundance above pH 11 in the base titration, which suggests decomposition, a different trend is evident in the acid titration. CoNb_9 forms a precipitate immediately upon adding a small amount of acid, as we have found previously in the titration of FeNb_9 and NiNb_9 .^{3d} However, MnNb_9 and CrNb_9 did not readily precipitate by adding acid; titration of MnNb_9 and CrNb_9 with acid exhibited some buffering

and significant precipitation only occurred below pH 5.3 and pH 4.7, respectively. Although the stabilities are broadly similar across the series [Fig. 4], the stability window in acidic region is $\text{CrNb}_9 > \text{MnNb}_9 > \text{Fe} \approx \text{Co} \approx \text{NiNb}_9$.

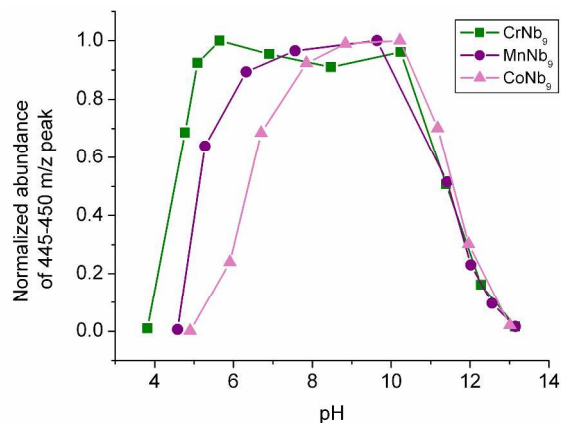


Fig. 4 Normalized peak intensity (strongest peak) in ESI-MS of 1-3 as a function of pH, based on Figures S1-S3

A purified sample of **1** has a lighter green color relative to the dark turquoise (bluish green) of $[\text{Cr}_2\text{Nb}_{10}\text{O}_{34}]^{8-}$, both in solution and solid. Crystals of **2** are deep purple and those of **3** are violet. The UV-Vis spectra of **1-3** during titration with TMAOH solution are shown in Figures S4-S6. The solution of **1** shows absorption at 450 and 650 nm from ${}^4\text{A}_{2g}(\text{F}) \rightarrow {}^4\text{T}_{1g}(\text{F})$ and ${}^4\text{A}_{2g}(\text{F}) \rightarrow {}^4\text{T}_{2g}(\text{F})$ transitions, respectively [Fig. S4].¹⁰ Different electronic transitions from light absorption are responsible for the slightly different colors of CrNb_9 and $\text{Cr}_2\text{Nb}_{10}$, as CrNb_9 is absorbing at 650 nm, while $\text{Cr}_2\text{Nb}_{10}$ shows absorption at 600 nm.⁷ During the titration of **1** with base, the two absorption maxima at 450 and 650 nm start to shift to 470 and 670 nm above pH 9 and a new absorption at 320 nm becomes evident. Titration coupled to ESI-MS indicated that significant decomposition only occurred above pH~11 [Fig. 4 and Fig. S1]. We thus suggest that the change of spectral profile of CrNb_9 above pH 9 is more likely due to deprotonation than decomposition, although this conclusion is speculative. A solution of **2** exhibits a broad absorption at 550 nm, which can be assigned to ${}^5\text{E}_g \rightarrow {}^5\text{T}_{2g}$ transition of Mn^{III} [Fig. S5].¹⁰ The natural pH attained by a 2mM solution of **2** is relatively high (~10), compared to **1** (pH 6.7) and **3** (pH 8.6), indicating a higher proton affinity. During the base titration of **2**, an isosbestic point was observed around pH 11. A solution of **3** shows absorption at 500 and 545 nm (${}^4\text{T}_{1g}(\text{F}) \rightarrow {}^4\text{T}_{1g}(\text{P})$ transition), which is a similar feature in the $[\text{Co}(\text{H}_2\text{O})_6]^{2+}$ ion [Fig. S6].¹⁰ The spectra of CoNb_9 did not change significantly until pH~12, which is similar to the behavior found in UV-Vis titrations of FeNb_9 and NiNb_9 .^{3d}

The magnetic measurements satisfy the Curie law, as can be seen from the almost linear $1/\chi_m$ vs temperature plot of each compound [Fig. S7]. Thus the compounds are paramagnetic, as is expected given that the clusters each contain a single isolated TM in otherwise diamagnetic niobate framework. The Curie constants derived by curve fitting χ_m vs temperature plot are presented in Table S2. Figure 5 shows the effective magnetic moments (μ_{eff}) of the series as a function of temperature. The μ_{eff} values of each compound at their maxima are close to typical experimental μ_{eff}

values for compounds with single corresponding TM ion in high-spin configuration (i.e. 3.8, 4.9, 5.9, 4.8, 3.2 for Cr^{III} , Mn^{III} , Fe^{III} , Co^{II} , Ni^{II} , respectively)¹¹, confirming the single-site substitution, the assigned oxidation states and high-spin states of the heterometals. However, the μ_{eff} values of all compounds slightly decrease with increasing temperature, which might be due to the spin disorder at higher temperatures. We note that FeNb_9 and CrNb_9 have maximum μ_{eff} around 7 K. On the other hand, NiNb_9 , MnNb_9 and CoNb_9 show maxima at 20 K, 35 K and 120 K, respectively. The sharp decrease of μ_{eff} of Ni^{II} and Mn^{III} compounds in the low-temperature region is known to be due to zero-field splitting.¹² The gradual decrease of μ_{eff} for the Co^{II} -substituted decaniobate at lower temperatures has been observed for other Co^{II} compounds, and is generally attributed to spin-orbit coupling.¹²

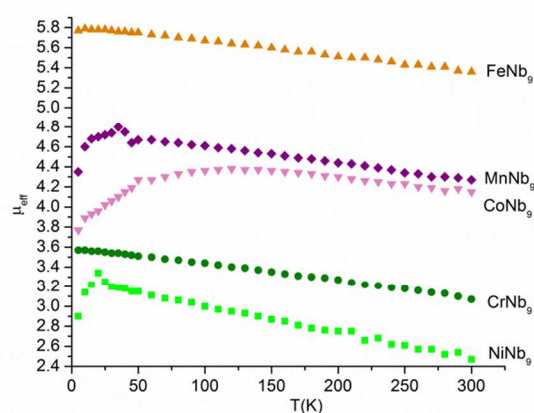


Fig. 5 μ_{eff} vs Temperature for TMA salts of TM-substituted decaniobates.

TM-doped polyoxometalate clusters have recently been shown to possess electrocatalytic properties for water oxidation.¹³ To test the ability of the niobate clusters to act as photocatalysts for H_2 evolution, irradiation tests were conducted. For the experiment, 50 mg of each compound was dissolved in mixed solution of methanol and water (50 mL, 20% v/v, methanol as sacrificial oxidant). Visible-light irradiation by using UV filter (cut-off wavelength < 400 nm) on the sample solutions showed no appreciable H_2 evolution, indicating that the electron-hole pairs created by excitation of the TMs by visible light are not accessible for redox reactions on the cluster surface. However, irradiation with the full spectrum of the Xe lamp produced significant amounts of H_2 . NiNb_9 and CoNb_9 showed ~4 times higher H_2 evolution than Nb_{10} [Fig S8]. FeNb_9 , MnNb_9 and CrNb_9 showed similar or lower activity than Nb_{10} . ESI-MS of the solutions after irradiation indicated that a significant amount each cluster had decomposed to hexaniobate and Nb_{10} during irradiation. To explain the nature of active photocatalyst, we carried out H_2 -evolution experiments using higher cluster concentrations.

When the H_2 -evolution experiment was performed with four-times higher cluster concentration (i.e. with 0.2 g of sample in 50 mL MeOH/water, 20% v/v; 1.6 to 2.0 mM), similar trends were found, with NiNb_9 (217 $\mu\text{mol/g/h}$) and CoNb_9 (214 $\mu\text{mol/g/h}$) showing higher H_2 -evolution activity than the other clusters,

which was generally similar or lower than Nb_{10} (59 $\mu\text{mol/g/h}$) [Fig. 6]. The non-linearly increasing H_2 -evolution rate of both NiNb_9 and CoNb_9 suggests formation of photocatalytically active forms from consumption or dissociation of original cluster. The color of the solutions changed after irradiation [Fig S9] and the solution exhibited scattering of laser light by colloids. Overall absorbance in UV-Vis spectra of the solutions increased after irradiation, which is also consistent with the formation of metal-oxide colloids upon irradiation [Fig S10]. ESI-MS indicated that a large portion of the MnNb_9 clusters in solutions decomposed after irradiation to hexaniobate and Nb_{10} , but some MnNb_9 still remained [Fig. S11]. Similarly, we observed photodecomposition of the Te-substituted Lindqvist-type niobate clusters into hexaniobate and metallic tellurium nanowires, which showed high H_2 -evolution activity.¹⁴ High H_2 -evolution activity from NiNb_9 is not surprising, since Ni-doped $\text{K}_4\text{Nb}_6\text{O}_{17}$ showed much higher H_2 -evolution activity compared to other early TM- (from Cr to Cu) doped $\text{K}_4\text{Nb}_6\text{O}_{17}$.⁵ The high H_2 -evolution activity of Ni-loaded $\text{K}_4\text{Nb}_6\text{O}_{17}$ was attributed to segregated NiO nanoparticles on $\text{K}_4\text{Nb}_6\text{O}_{17}$ sheets.¹⁵ Thus the high activity of NiNb_9 could similarly be attributed to formation of Ni^0 or NiO_x particles and their interaction with niobates. Niobate will generate electron-hole pairs upon UV light irradiation¹⁶ and Ni^0/NiO_x particle will reduce protons, producing H_2 . We note that whether Ni^0 , or NiO_x , or both, are the active cocatalyst is controversial; we cannot contribute to this discussion here.¹⁷

Upon irradiation, CoNb_9 solutions exhibited H_2 -evolution curves that were similar to NiNb_9 solutions. ESI-MS spectrum after irradiation indicated that a solution of CoNb_9 is still dominated by the CoNb_9 ion, but the UV-Vis spectra had changed, indicating some decomposition. The appreciable activity of CoNb_9 in photocatalytic H_2 -evolution is interesting because Co-doped $\text{K}_4\text{Nb}_6\text{O}_{17}$ showed much lower H_2 -evolution activity compared to Ni-doped $\text{K}_4\text{Nb}_6\text{O}_{17}$.⁵ Hill et al remarked that the distinction between homogeneous and heterogeneous catalysis is elusive for their Co-doped polyoxotungstate catalytic systems, and that is certainly also true here for the substituted niobates.¹⁸

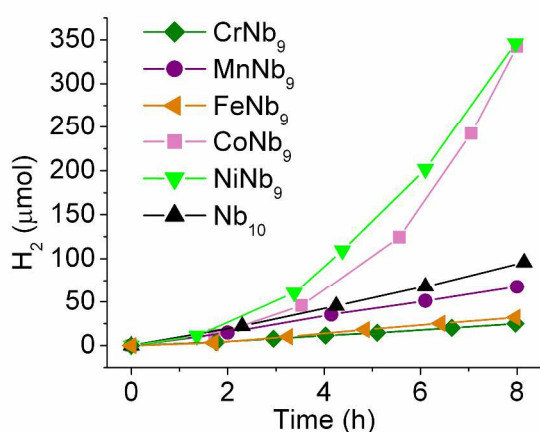


Fig.6 H_2 -evolution upon Xe-lamp irradiation of 0.2 g of TM-substituted decaniobate TMA salts in 50mL MeOH/ H_2O solution (20% v/v).

The H_2 -evolution activity of the cluster solution depends on pH. A large amount of light grey precipitate formed after irradiating the NiNb_9 solution when the pH was lowered before irradiation, and this solution showed enhanced H_2 -evolution activity upon irradiation, with a distinct nonlinear curve (986 $\mu\text{mol/g/h}$) [Fig. S12]. No clusters remained in the solution after irradiation, as indicated by ESI-MS. The pH after irradiation was 5.8, much lower than natural pH of a solution formed from freshly dissolved solid, and is instead consistent with extensive hydrolysis reactions upon irradiation, leading to proton release and precipitation. Transmission-electron microscopy (TEM) images of the precipitate showed agglomerated nanoparticles (<10nm), and the composition is about $\text{Ni:Nb}=1:8.7$, as determined by energy-dispersive X-ray spectroscopy (EDS) [Fig. S13], which is close to the cluster composition. This result suggests that the nanoparticles are composed of NiO_x and NbO_x , but phase distinction was not possible due to resolution limit. Powder X-ray diffraction of this precipitate indicated no crystallinity. One hypothesis is that, by forcing precipitation at low pH, the NiNb_9 system exhibited a higher H_2 -evolution because the colloids were catalytic. Interestingly, CoNb_9 exhibited an opposite trend [Fig. S12]. The H_2 -evolution activity of CoNb_9 was nearly lost after precipitate formed by lowering the pH, which suggests that H_2 evolution in CoNb_9 solution may be from cluster ions and not the precipitate.

Conclusions

Early TM-substituted (from group 6 to 10) decaniobate ions have differences in their solid-state structure that can be related to their stability and properties. The range of widely varying stabilities of the clusters was a key challenge in the synthesis and purification of this series of polyoxoniobates. We suggest that the higher H_2 -evolution activity from the Ni- and Co-substituted decaniobate ions arises via separate heterogeneous (Ni) and homogeneous (Co) routes, but in any case is only evident during UV irradiation. Their increased activity is attributed to cocatalysis from the photodecomposition products, most likely as Ni^0 and Ni oxide, and Co hydroxide, with amorphous Nb_2O_5 or with the niobate cluster in solution. CoNb_9 is interesting because a relatively larger amount of the cluster ions survive irradiation.

Acknowledgement

This work was supported by an NSF CCI grant through the Center for Sustainable Materials Chemistry, number CHE-1102637. We thank Prof. Frank E. Osterloh for useful discussions. We thank Aimee Brian and Peter Klavins for magnetic property measurements, and Prof. Kirill Kovnir for discussion about magnetism data.

Notes and references

⁹⁰ ^a Department of Chemistry, University of California, Davis, One Shields Ave. Davis, CA 95616, USA. Fax: +1 530 752 8995; Tel: +1 530 752 3211; E-mail: junghoson@gmail.com, whcasey@ucdavis.edu

^b Department of Geology, University of California, Davis, One Shields Ave., Davis, CA 95616, USA

⁹⁵ † Electronic Supplementary Information (ESI) available: ESI-MS and UV-Vis titration data, magnetism data, detailed H_2 evolution data with

change of solution speciation by ESI-MS, UV-Vis, and TEM/EDS data of the colloids after irradiation. See DOI: 10.1039/b000000x/

‡ Experimental Details.

Synthesis of **1** (CCDC 990475) : Hydrous niobium oxide (5 g) was mixed with 0.89 g of $\text{CrCl}_3 \cdot 6\text{H}_2\text{O}$ in a 23 mL capacity PTFE-lined autoclave and 5.5 g of TMAOH $\cdot 6\text{H}_2\text{O}$ was added. The mixture was reacted at 110 °C for 4 days. Reaction mixture solution was washed with isopropanol in a plastic centrifuge tube (50 mL) several times until the sticky product remained. The product was extracted with ethanol until extract was nearly colorless. Ethanol extract was discarded and remaining green precipitate was extracted with methanol/ethanol (ca 1:1) solution. Crystalline product was obtained after evaporation. Yield = 1.9 g (28%). Elemental analysis Found: C 14.34, H 5.19, N 4.06, Cr 2.34, Nb 38.40. Calcd for $\text{C}_{24}\text{H}_{102}\text{N}_6\text{CrNb}_9\text{O}_{42}$: C 14.15, H 5.05, N 4.13, Cr 2.56, Nb 41.09.

Synthesis of **2** (CCDC 990476) : Hydrous niobium oxide (5 g) was mixed with 0.66 g of $\text{MnCl}_2 \cdot 4\text{H}_2\text{O}$ in a 23 mL capacity PTFE-lined autoclave and 5.5 g of TMAOH $\cdot 6\text{H}_2\text{O}$ was added. The mixture was reacted at 110 °C for 4 days. Reaction mixture solution was washed with isopropanol in a plastic centrifuge tube (50 mL) several times until the sticky product remained. The product was extracted with ethanol (ca. 200 mL). The ethanolic solution was concentrated to less than 50 mL by using rotary evaporator and kept in a freezer. Dark purple rod-like crystals formed. The product crystals were quickly filtered on a frit and washed with minimum amount of ethanol, and dried in vacuo. Yield = 2.3 g (28%). Elemental analysis Found: C 15.39, H 5.99, N 4.41, Mn 2.19, Nb 34.10. Calcd for $\text{C}_{32}\text{H}_{154}\text{N}_8\text{MnNb}_9\text{O}_{57}$: C 15.65, H 6.32, N 4.56, Mn 2.24, Nb 34.07.

Synthesis of **3** (CCDC 990477) : Hydrous niobium oxide (5 g) was mixed with 0.8 g of $\text{CoCl}_2 \cdot 6\text{H}_2\text{O}$ in a 23 mL capacity PTFE-lined autoclave and 5.5 g of TMAOH $\cdot 6\text{H}_2\text{O}$ was added. The mixture was reacted at 110 °C for 4 days. Reaction mixture solution was washed with isopropanol in a plastic centrifuge tube (50 mL) several times until the sticky product remained. The product was extracted with ethanol (ca. 200 mL). The ethanolic solution was concentrated to less than 50 mL by using rotary evaporator and kept in a freezer. Pale violet needle-like crystals formed were quickly filtered on a frit and washed with minimum amount of ethanol and dried in vacuo. Yield = 3.5 g (45%). Elemental analysis Found: C 14.53, H 6.01, N 4.44, Co 2.50, Nb 34.30. Calcd for $\text{C}_{28}\text{H}_{136}\text{N}_7\text{CoNb}_9\text{O}_{53}$: C 14.52, H 5.92, N 4.24, Co 2.55, Nb 36.14.

Crystal Data. (**1**) CCDC 990475. $\text{C}_{24}\text{H}_{93}\text{N}_6\text{Cr}_{1.03}\text{Nb}_{8.98}\text{O}_{42.44}$, $M = 2032.17$, Monoclinic, $a = 16.6016(8)$, $b = 17.2436(8)$, $c = 24.0263(11)$ Å, $\beta = 106.121(1)^\circ$, $U = 6607.6(5)$ Å³, $T = 93$ K, space group $P2_1/n$ (no.14), $Z = 4$, 66308 reflections measured, 13488 unique ($R_{\text{int}} = 0.0218$) which were used in all calculations. The final $wR(F^2)$ was 0.0656 (all data). (**2**) CCDC 990476. $\text{C}_{33.60}\text{H}_{60}\text{N}_8\text{Mn}_{1.04}\text{Nb}_{8.96}\text{O}_{56.90}$, $M = 2376.48$, Monoclinic, $a = 22.846(6)$, $b = 13.767(4)$, $c = 17.970(5)$ Å, $\beta = 129.353(4)^\circ$, $U = 4370(2)$ Å³, $T = 93$ K, space group $C2/m$ (no.12), $Z = 2$, 23936 reflections measured, 5199 unique ($R_{\text{int}} = 0.0138$) which were used in all calculations. The final $wR(F^2)$ was 0.1285 (all data). (**3**) CCDC 990477. $\text{C}_{28}\text{H}_{72}\text{N}_7\text{CoNb}_9\text{O}_{53}$, $M = 2250.05$, Monoclinic, $a = 25.543(2)$, $b = 13.8124(12)$, $c = 23.383(2)$ Å, $\beta = 104.026(1)^\circ$, $U = 8003.9(12)$ Å³, $T = 88$ K, space group $P2_1/c$ (no.14), $Z = 4$, 126087 reflections measured, 24416 unique ($R_{\text{int}} = 0.0315$) which were used in all calculations. The final $wR(F^2)$ was 0.1700 (all data).

References

¹ a) L. C. W. Baker, V. S. Baker, K. Eriks, M. T. Pope, M. Shibata, O. W. Rollins, J. H. Fang, L. L. Koh, *J. Am. Chem. Soc.* **1966**, *88*, 2329; b) L. C. W. Baker, J. S. Figgis, *J. Am. Chem. Soc.* **1970**, *92*, 3794-3797; c) T. J. R. Weakley, *J. Chem. Soc., Dalton Trans.* **1973**, 341-346; d)

C. L. Hill, R. B. Brown Jr., *J. Am. Chem. Soc.* **1986**, *108*, 536-538; e) M. Faraj, C. L. Hill, *J. Chem. Soc. Chem. Commun.* **1987**, 1487-1489; f) J. Hu, R. C. Burns, *J. Mol. Catal. A: Chemical* **2002**, *184*, 451-464; g) J.-H. Choi, J. K. Kim, D. R. Park, T. H. Kang, J. H. Song, I. K. Song, *J. Mol. Catal. A: Chemical* **2013**, *371*, 111-117.

² M. T. Pope, *Heteropoly and Isopolyoxometalates*, Springer Verlag: Berlin, **1983**.

³ a) M. Nyman, L. J. Criscenti, F. Bonhomme, M. A. Rodriguez, R. T. Cygan, *J. Solid State Chem.* **2003**, *176*, 111-119; b) U. Lee, H.-C. Joo, K.-M. Park, S.S. Mal, U. Kortz, B. Keita, L. Nadjo, *Angew. Chem., Int. Ed.* **2008**, *47*, 793-796; c) C. A. Ohlin, E. M. Villa, J. C. Fettinger, W. H. Casey, *Dalton Trans.* **2009**, 2677-2678; d) J.-H. Son, C. A. Ohlin, W. H. Casey, *Dalton Trans.* **2013**, *42*, 7529-7533.

⁴ a) A. Fujishima, K. Honda, *Nature* **1972**, *238*, 37-38; b) D. W. Hwang, H. G. Kim, J. S. Jang, S. W. Bae, S. M. Ji, J. S. Lee, *Catal. Today* **2004**, *93*, 845-850; c) R. Niishiro, H. Kato, A. Kudo, *Phys. Chem. Chem. Phys.* **2005**, *7*, 2241-2245; d) P. D. Tran, L. Xi, S. K. Batabyal, L. H. Wong, J. Barber, J. S. C. Loo, *Phys. Chem. Chem. Phys.* **2012**, *14*, 11596-11599; e) H. Yu, S. Ouyang, S. Yan, Z. Li, T. Yua, Z. Zou, *J. Mater. Chem.* **2011**, *21*, 11347-11351; f) R. Dholam, N. Patel, M. Adami, A. Miotello, *Int. J. Hydrogen Ener.* **2009**, *34(13)*, 5337-5346.

⁵ a) K. Domen, A. Kudo, A. Shinozaki, A. Tanaka, K. Maruya, T. Onishi, *J. Chem. Soc., Chem. Commun.* **1986**, 356-357; b) A. Kudo, A. Tanaka, K. Domen, K. Maruya, K. Aika, T. Onishi, *J. Catal.* **1988**, *111*, 67-76; c) Y. Miseki, A. Kudo, *ChemSusChem* **2011**, *4*, 245-251.

⁶ a) Z. Zhang, Q. Lin, D. Kurunthu, T. Wu, F. Zuo, S.-T. Zheng, C. J. Bardeen, X. Bu, P. Feng, *J. Am. Chem. Soc.* **2011**, *133*, 6934-6937; b) P. Huang, C. Qin, Z.-M. Su, Y. Xing, X.-L. Wang, K.-Z. Shao, Y.-Q. Lan, E.-B. Wang, *J. Am. Chem. Soc.* **2012**, *134*, 14004-14010; c) Z.-L. Wang, H.-Q. Tan, W.-L. Chen, Y.-G. Li, E.-B. Wang, *Dalton Trans.* **2012**, *41*, 9882-9884.

⁷ J.-H. Son, C. A. Ohlin, W. H. Casey, *Dalton Trans.* **2012**, *41*, 12674-12677.

⁸ a) B. W. Dale, M. T. Pope, *Chem. Commun.* **1967**, 792; b) B. W. Dale, J. M. Buckley, M. T. Pope, *J. Chem. Soc. A* **1969**, 301-304; c) C. M. Flynn Jr., G. D. Stucky, *Inorg. Chem.* **1969**, *8*, 332-334; d) C. M. Flynn Jr., G. D. Stucky, *Inorg. Chem.* **1969**, *8*, 335-344; e) J.-H. Son, W. H. Casey, *Dalton Trans.* **2013**, *42*, 13339-13342.

⁹ a) R. D. Shannon, C. T. Prewitt, *Acta Cryst.* **1969**, *B25*, 925-945; b) R. D. Shannon, *Acta Cryst.* **1976**, *A32*, 751-767.

¹⁰ F. A. Cotton, G. Wilkinson, C. A. Murillo, M. Bochmann *Advanced Inorganic Chemistry*, 6th Ed. Wiley-Interscience: New York, **1999**.

¹¹ J. M. D. Coey, *Magnetism and Magnetic Materials*, Cambridge University Press, **2010**.

¹² H. Liu, C. J. Gómez-García, J. Peng, J. Sha, Y. Li, Y. Yan, *Dalton Trans.* **2008**, 6211-6218.

¹³ Yin, Q. S.; Tan, J. M.; Besson, C.; Geletii, Y. V.; Musaev, D. G.; Kuznetsov, A. E.; Luo, Z.; Hardcastle, K. I.; Hill, C. L., *Science* **2010**, *328*, 342-345.

¹⁴ J.-H. Son, J. Wang, F. E. Osterloh, P. Yu, W. H. Casey, *Chem. Commun.* **2014**, *50*, 836-838.

¹⁵ A. Kudo, K. Sayama, A. Tanaka, K. Asakura, K. Domen, K. Maruya, T. Onishi, *J. Catal.* **1989**, *120*, 337-352.

¹⁶ a) A. Furube, T. Shiozawa, A. Ishikawa, A. Wada, K. Domen, C. Hirose *J. Phys. Chem. B* **2002**, *106*, 3065-3072; b) A. G. S. Prado, L. B. Bolzon, C. P. Pedroso, A. O. Moura, L. L. Costa, *Appl. Catal., B* **2008**, *82*, 219-224.

¹⁷ T. K. Townsend, N. D. Browning, F. E. Osterloh, *Energy Environ. Sci.* **2012**, *5*, 9543-9550.


¹⁸ J. W. Vickers, H. Lv, J. M. Sumliner, G. Zhu, Z. Luo, D. G. Musaev, Y. V. Geletii, C. L. Hill, *J. Am. Chem. Soc.* **2013**, *135*, 14110-14118.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

TOC figure

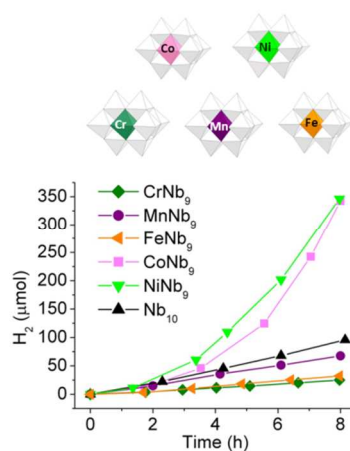

Among the series of early transition-metal-substituted decaniobate ions synthesized and characterized in this paper, Co- or Ni-substituted decaniobates showed enhanced photocatalytic H₂-evolution activity compared to others.