

Dalton Transactions

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

ARTICLE

Structural complexity in indium selenides prepared using bicyclic amines as structure-directing agents

Cite this: DOI: 10.1039/x0xx00000x

S. J. Ewing^a and P. Vaquero^{a,b*}Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

The synthesis and characterization of five new indium selenides, $[\text{C}_9\text{H}_{17}\text{N}_2]_3[\text{In}_5\text{Se}_{8+x}(\text{Se}_2)_{1-x}]$ (1-2), $[\text{C}_6\text{H}_{12}\text{N}_2]_4[\text{C}_6\text{H}_{14}\text{N}_2]_3[\text{In}_{10}\text{Se}_{15}(\text{Se}_2)_3]$ (3), $[\text{C}_6\text{H}_{14}\text{N}_2][(\text{C}_6\text{H}_{12}\text{N}_2)_2\text{NaIn}_5\text{Se}_9]$ (4) and $[\text{enH}_2][\text{NH}_4][\text{In}_7\text{Se}_{12}]$ (5), are described. These materials were prepared under solvothermal conditions, using 1,8-diazabicyclo[5.4.0]undec-7-ene (DBU) and 1,4-diazabicyclo[2.2.2]octane (DABCO) as structure-directing agents. Compounds 1-4 represent the first examples of ribbons in indium selenides, and 4 is the first example of incorporation of an alkali metal complex. Compounds 1, 2 and 4 contain closely related $[\text{In}_5\text{Se}_{8+x}(\text{Se}_2)_{1-x}]^{3-}$ ribbons which differ only in their content of $(\text{Se}_2)^{2-}$ anions. These ribbons are interspaced by organic counteranions in 1 and 2, while in 4 they are linked by highly unusual $[\text{Na}(\text{DABCO})_2]^+$ units into a three-dimensional framework. Compound 3 contains complex ribbons, with a long repeating sequence of *ca.* 36 Å, and 4 is a non-centrosymmetric three-dimensional framework, formed as a consequence of the decomposition of DABCO into ethylenediamine (*en*) and ammonia.

Introduction

Open-framework chalcogenides are of considerable interest due to their potential as multifunctional materials in which semiconductivity and porosity coexist, and have already shown promising behavior as photocatalysts,¹ fast-ion conductors² and for the selective ion exchange of heavy metals.³ Moreover, the primary building units in many of these chalcogenides lack an inversion centre, and hence are ideal building blocks for non-centrosymmetric solids, which may find applications in second-order nonlinear optics.⁴ Significant progress has already been made in the synthesis of open-framework indium sulfides, which are frequently built from supertetrahedral clusters.⁵ In comparison with indium sulfides, few examples are known of the corresponding selenides.

With the exception of $[\text{C}_7\text{H}_{10}\text{N}][\text{In}_3\text{Se}_5]$,⁶ which contains octahedrally coordinated indium, the primary building unit found to date in the limited number of solvothermally-prepared indium selenides is the InSe_4^{5-} tetrahedron. Vertex linkage of these tetrahedra can result in the formation of supertetrahedral clusters, but very few indium selenides contain supertetrahedral clusters as secondary building units. This includes three-dimensional frameworks with the double- and single-diamond

topologies,^{2,7} and $[\text{NH}_4][\text{InSe}_2]$, which is a non-centrosymmetric material with nonlinear optical behaviour.⁸ Vertex-linking of InSe_4^{5-} tetrahedra can lead to other secondary building units, such as the nona-nuclear indium clusters found in the microporous structure of $[\text{NH}_4]_4[\text{In}_{12}\text{Se}_{20}]$,³ or to the helical chains found in the $[\text{In}_{33}\text{Se}_{56}]^{13-}$ open framework.⁹ Edge-sharing of InSe_4^{5-} tetrahedra is also possible, as exemplified by $[\text{C}_7\text{H}_{10}\text{N}][\text{In}_9\text{Se}_{14}]$, in which edge- and vertex-sharing tetrahedra coexist.¹⁰ When InSe_4^{5-} tetrahedra are linked exclusively by their edges, $[\text{InSe}_2]^-$ chains are obtained. These have been found in a polymorphic form of $[\text{NH}_4][\text{InSe}_2]$ ⁸ and in $[\text{bdah}][\text{InSe}_2]$ (where bda = 1,4-butanediamine).¹¹ Recently, it has been found that replacement of Se^{2-} with perselenide $(\text{Se}_2)^{2-}$ anions in the $[\text{InSe}_2]^-$ chains can occur, resulting in the formation of chains in which four and five-membered rings alternate, as exemplified by $[\text{C}_6\text{H}_{16}\text{N}_2][\text{In}_2\text{Se}_3(\text{Se}_2)]$, $\{[\text{M}(\text{phen})_3\text{In}_2\text{Se}_5\cdot\text{H}_2\text{O}]_n\}$ (where M = Ni, Fe; phen = 1,10-phenanthroline) and $[\text{Mn}(\text{en})_3][\text{In}_2\text{Se}_5]$.¹² Despite the ongoing research efforts on the solvothermal synthesis of new indium selenides, the number of reported phases has remained low. This may be related to the low selectivity with which a particular structure is crystallised with a specific structure-directing agent. For instance, we have found

that frameworks such as $[\text{NH}_4][\text{In}_{12}\text{Se}_{20}]$ or $[\text{In}_{33}\text{Se}_{56}]^-$ can be obtained using a wide variety of structure-directing agents. In an effort to identify structure-directing agents with selectivity towards novel selenides, we have explored the use of organic superbases, and in particular, of two distinctly different bicyclic amines, 1,8-diazabicyclo[5.4.0]undec-7-ene (DBU) and 1,4-diazabicyclo[2.2.2]octane (DABCO). This work, which is described here, has resulted in the synthesis and characterisation of five new indium selenides (1-5) of varying dimensionality, which exhibit a number of novel structural features, including the incorporation of $(\text{Se}_2)^{2-}$ anions and of highly unusual $[\text{Na}(\text{DABCO})_2]^+$ units.

Experimental

Materials and methods

Syntheses were carried out using 23 mL Teflon lined stainless steel autoclaves. The reagents were added individually to the Teflon liner and mixed for approximately 10 minutes, prior to sealing the reaction vessel. The sealed autoclaves were then heated to a set temperature for a defined period of time. After cooling to room temperature, the products were collected by vacuum filtration and washed with deionised water, methylated spirits and acetone.

Synthesis of $[\text{C}_9\text{H}_{17}\text{N}_2]_3[\text{In}_5\text{Se}_{8.07}(\text{Se}_2)_{0.93}]$ (1)

A mixture of In (0.1676 g, 1.46 mmol, 99+%, Aldrich), Se powder (0.2369 g, 3 mmol, 99.99%, Alfa Aesar), DBU (0.3 mL, 2.01 mmol, 98%), imidazole (0.2042 g, 3 mmol, $\geq 99\%$) and acetonitrile (3 mL, Fisher) was placed in a sealed autoclave. The vessel was heated to 200°C for 10 days. The product contained a small amount of a black powder and large yellow crystals. The yellow crystals were identified as 1 by single crystal X-ray diffraction. Elemental analysis: found: C = 17.55%, H = 2.69%, N = 4.38%; calc.: C = 17.84%, H = 2.83%, N = 4.62%

Synthesis of $[\text{C}_9\text{H}_{17}\text{N}_2]_3[\text{In}_5\text{Se}_{8.74}(\text{Se}_2)_{0.26}]$ (2)

This compound was synthesised using InCl_3 (0.3229 g, 1.46 mmol, 98%, Aldrich) with Se powder (0.2369 g, 3 mmol, 99.99%, Alfa Aesar) and DBU (1 mL, 6.7 mmol, 98%, Aldrich). The sealed vessel was heated at 200°C for 10 days. The collected product consisted of yellow rod-like crystals of 2. Elemental analysis: found: C = 18.39%, H = 2.95%, N = 4.67%; calc.: C = 18.37%, H = 2.91%, N = 4.76%

Synthesis of $[\text{C}_6\text{H}_{12}\text{N}_2]_4[\text{C}_6\text{H}_{14}\text{N}_2]_3[\text{In}_{10}\text{Se}_{15}(\text{Se}_2)_3]$ (3)

A mixture of In (0.1676 g, 1.46 mmol, 99.99%, Aldrich), Se powder (0.2369 g, 3 mmol, 99.99%, Alfa Aesar), DABCO (0.6731 g, 6 mmol, $\geq 99\%$, Aldrich) and dimethylformamide (DMF, 6 mL, Fisher), with the approximate molar composition 1.5: 3: 6: 78, was placed in a Teflon liner, sealed and heated at 140°C for 10 days. The product contained an abundance of small brown crystals, which were identified as 3 by single-

crystal diffraction, and a small amount of orange powder. Elemental analysis: found: C = 11.51%, H = 1.90%, N = 4.25%; calc.: C = 14.02%, H = 2.52%, N = 5.45%

Synthesis of $[\text{C}_6\text{H}_{14}\text{N}_2][(\text{C}_6\text{H}_{12}\text{N}_2)_2\text{NaIn}_5\text{Se}_9]$ (4)

This compound was prepared using In (0.1676 g, 1.46 mmol, 99.99%, Alfa Aesar), Se (0.2369 g, 3 mmol, 99.9%, Alfa Aesar), DABCO (0.6731 g, 6 mmol, $\geq 99\%$, Aldrich), 0.1 mL of 15 wt% NaOH solution and 6 mL of acetonitrile, loaded into a Teflon-lined stainless steel autoclave with the approximate molar composition of 1.46: 3: 6: 0.4: 115. The reaction was carried out at 140°C for 10 days. The product consisted of a small amount of black powder with an abundance of brown prism crystals of 4. Smaller yields of 4 were obtained when 1 mmol of a sodium source such as $\text{Na}(\text{NO}_3)$, $\text{Na}(\text{COOCH}_3)$, $\text{Na}_2(\text{C}_2\text{O}_4)$ or $\text{Na}_2(\text{CO}_3)$ were added to the reaction, instead of NaOH. Elemental analysis: found: C = 12.91%, H = 2.20%, N = 4.67%; calc.: C = 13.12%, H = 2.33%, N = 5.10%

Synthesis of $[\text{enH}_2][\text{NH}_4][\text{In}_7\text{Se}_{12}]$ (5)

This material was prepared using In powder (0.1676 g, 1.46 mmol, 99.99%, Aldrich), Se powder (0.2369 g, 3 mmol, 99.99%, Alfa Aesar), DABCO (0.6731 g, 6 mmol, $\geq 99\%$, Aldrich) and deionised water (3 mL), heated to 200°C for 14 days. The resulting product contained numerous yellow plates of 5, and a small amount of red needle-like crystals identified by single-crystal X-ray diffraction as the previously reported $[\text{NH}_4]_4[\text{In}_{12}\text{Se}_{20}]$.³ The presence of ammonium and ethylenediamine cations in the crystal structure of 5 suggested that DABCO decomposed under solvothermal conditions. A similar decomposition of DABCO has been reported in the hydrothermal preparation of uranium fluorides.¹³ Attempts were made to prepare 5 from the products of the decomposition of DABCO. For this purpose, ethylenediamine dihydrochloride (3 mmol, 99%, Aldrich) and ammonium chloride (3 mmol, 99.9%, Aldrich) were used, together with In powder (1.46 mmol), Se (3 mmol) and deionised water (3 mL) at 200°C for 10 days. This reaction gave a brownish powder where 5 was identified by powder X-ray diffraction, but no single crystals were observed. Elemental analysis for 5: found: C = 1.22%, H = 0.88%, N = 2.29%; calc.: C = 1.31%, H = 0.77%, N = 2.29%

Single-crystal diffraction

Single-crystal X-ray diffraction data for crystals of 1-4 were collected at 100 K, whilst data for 5 were collected at 293 K. For 3, the crystal used for data collection was particularly small, despite unsuccessful attempts to optimize the reaction conditions to grow larger crystals. The structures of 1-4 were solved using the charge-flipping method, Superflip,¹⁴ while that of 5 was solved using SHELX,¹⁵ which located the In and Se atoms. Organic molecules were generally found in the difference Fourier maps. Subsequent Fourier calculations and least squares refinements on F were carried out using the

CRYSTALS program¹⁶ for all structures. Hydrogens were not placed on the ammonium cation in 5 as they are likely to be disordered. Selected crystallographic information for these compounds is shown in Table 1. Data have been deposited with the Cambridge Crystallographic Data Centre as CCDC 1023692-1023696.

INSERT TABLE 1 HERE (see end of document)

Characterisation

Powder X-ray diffraction data were collected using a Bruker D8 Advance powder diffractometer, operating with germanium monochromated $\text{CuK}\alpha_1$ radiation ($\lambda = 1.5406 \text{ \AA}$) fitted with a Bruker LynxEye linear detector. Data were collected, on a ground portion of the reaction product, over the angular range $5 \leq 2\theta/^\circ \leq 85$ with a step size of 0.009° . Lattice parameters were determined using Topas.¹⁷ Analysis of powder X-ray diffraction data (ESI) indicates that 1-5 are the main products obtained. Elemental analysis on handpicked crystals was carried out on an Exeter CE-440 elemental analyser. Thermogravimetric analysis was performed using a DuPont Instruments 951 thermal analyser. Approximately 10 mg of finely ground crystals were heated under a flow of O_2 over the temperature range $30 \leq T/^\circ\text{C} \leq 1000$. Diffuse reflectance measurements were performed using a Perkin Elmer Lambda 35 UV-vis spectrometer. BaSO_4 powder was used as a reference (100% reflectance) and absorption data were calculated from the Kubelka-Munk function.¹⁸ Infrared measurements were carried out using a Perkin Elmer Spectrum 100 ATR spectrometer.


Results

Crystal structures of 1 and 2

Although 1 crystallises in the monoclinic space group $P2_1/c$, whilst 2 is triclinic ($P\bar{1}$), their crystal structures are closely related, and consist of anionic ribbons separated by protonated DBU cations. The ribbons found in 1 and 2 have the compositions $[\text{In}_5\text{Se}_{8.07}(\text{Se}_2)_{0.93}]^{3-}$ and $[\text{In}_5\text{Se}_{8.74}(\text{Se}_2)_{0.26}]^{3-}$ respectively, and differ only in the content and arrangement of disordered $(\text{Se}_2)^{2-}$ units. The simplest fragment of the anionic ribbon in 1 is shown in Figure 1(a). This repeating unit contains five crystallographically-independent tetrahedra linked by their edges and corners. In this unit, three tetrahedra containing In(1), In(4) and In(5) are linked by their corners forming a six-membered ring. The In(5) Se_4 tetrahedron is linked by an edge to an In(3) Se_4 tetrahedron, forming a four-membered ring. The linkage between In(4) Se_4 and In(2) Se_4 is more complex, due to the coexistence of disordered $(\text{Se}_2)^{2-}$ and Se^{2-} moieties. Depending on whether a Se^{2-} or a $(\text{Se}_2)^{2-}$ unit is present, the linkage between In(4) Se_4 and In(2) Se_4 creates a four- or a five-membered ring. In 1, the perselenide linkage shown in Figure 1(a) is dominant, with the fractional occupancy of the $(\text{Se}_2)^{2-}$ unit being 92.66(18)%, whilst the occupancy of the corresponding Se^{2-} is only 7.34(18)%. By contrast, in 2 (Figure 1(b)) four-membered rings are predominant, as reflected by a fractional occupancy for the perselenide $(\text{Se}_2)^{2-}$ moiety of

25.6(2)%, whilst the single Se^{2-} has an occupancy of 74.4(2)%. Compounds 1 and 2 also differ in the location of the perselenide moiety within the repeating unit. In 1, In(5) Se_4 and In(3) Se_4 always form a four-membered ring, while the ring formed by In(2) Se_4 and In(4) Se_4 can be a four- or a five-membered ring. By contrast, in 2 partial replacement of a Se^{2-} by a $(\text{Se}_2)^{2-}$ can occur in both four-membered rings. The Se-Se distance in the perselenide is 2.379(11) \AA for 1 and 2.356(7) for 2, similar to the values previously reported for indium selenides containing $(\text{Se}_2)^{2-}$ moieties.¹²

(a)

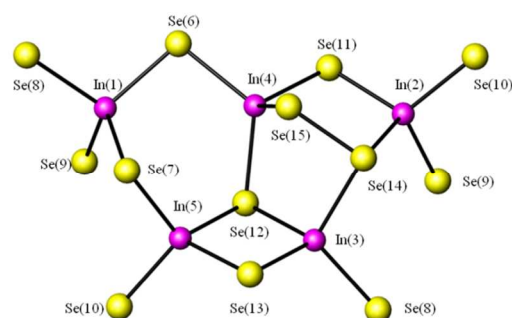

(b)

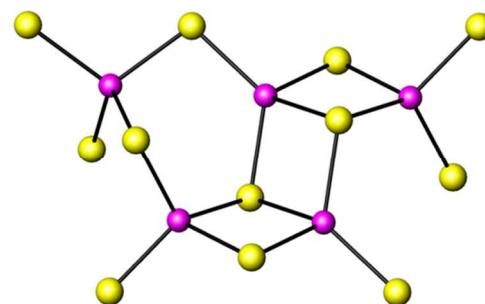


Figure 1. View of the building block for the $[\text{In}_5\text{Se}_{8+x}(\text{Se}_2)_{1-x}]^{3-}$ ribbons in (a) compound 1, and (b) compound 2. For clarity, the disordered Se^{2-} in 1, and the disordered $(\text{Se}_2)^{2-}$ in 2, have been omitted. Key: indium, large pink circles; selenium, large yellow circles.

In 1, each $[\text{In}_5\text{Se}_{11+x}(\text{Se}_2)_{1-x}]^{9-}$ repeating unit is linked to two other $[\text{In}_5\text{Se}_{11+x}(\text{Se}_2)_{1-x}]^{9-}$ blocks, which are rotated by 180° , via the terminal Se (8), Se(9) and Se(10) atoms, forming the one-dimensional ribbon shown in Figure 2(a). Compound 2 (Figure 2(b)) differs from 1 in the distribution of perselenide moieties along the ribbon. In 2, $[\text{In}_5\text{Se}_{12}]^{9-}$ units, which contain no $(\text{Se}_2)^{2-}$, alternate with $[\text{In}_5\text{Se}_{10+2x}(\text{Se}_2)_{2-2x}]^{9-}$ units. In both cases, the overall stoichiometry of the ribbon is given by the general formula $[\text{In}_5\text{Se}_{8+x}(\text{Se}_2)_{1-x}]^{3-}$. Charge balance is achieved through the incorporation of protonated organic amines into the crystal structure. As shown in Figure 3, the ribbons in 1 and 2 are aligned parallel to the c -axis, and separated by the protonated organic cations.

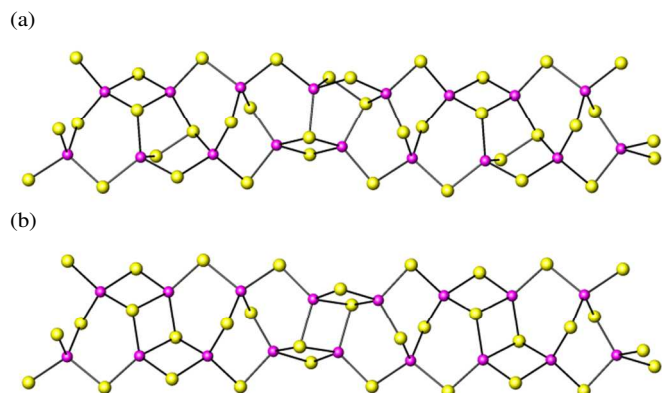


Figure 2. Anionic $[\text{In}_5\text{Se}_{8+x}(\text{Se}_2)_{1-x}]^{3-}$ ribbons found in 1, 2 and 4. (a) Ribbon found in 1 ($x=0.93$), showing the predominant five-membered perselenide rings. (b) Ribbon found in 2 ($x=0.26$) and 4 ($x=0$), showing the predominant four-membered rings. Key as for Figure 1.

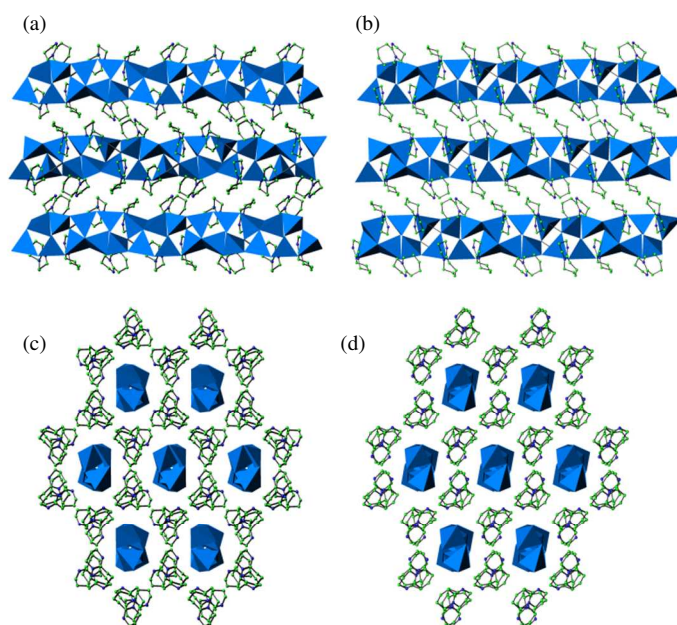


Figure 3. Polyhedral representation of the crystal structures of 1 and 2, viewed along $[100]$ for (a) 1 and (b) 2, and along $[001]$ for (c) 1 and (d) 2. Hydrogen atoms have been omitted for clarity. Key: InSe_4 , blue tetrahedra; carbon, small green circles; nitrogen, small blue circles.

Crystal structure of 3

Compound 3 crystallises in the monoclinic space group $P2_1/c$ and contains a complex one-dimensional ribbon with stoichiometry $[\text{In}_{10}\text{Se}_{15}(\text{Se}_2)_3]^{6-}$. The asymmetric unit of 3 (ESI) has ten crystallographically-independent indium atoms, all of which are tetrahedrally coordinated to selenium atoms. The InSe_4 tetrahedra are linked via vertex- and edge-sharing. This creates a number of six- $[\text{In}_3\text{Se}_3]$, five- $[\text{In}_2\text{Se}_3]$ and four- $[\text{In}_2\text{Se}_2]$ membered rings, which were also present in 1 and 2, as well as $[\text{In}_2\text{Se}_4]$ and $[\text{In}_4\text{Se}_4]$ rings, not found in 1 and 2. The

Se-Se distances in the perselenide $(\text{Se}_2)^{2-}$ units present in this material range from 2.411(2) to 2.438(2) Å, which are slightly longer than those reported for $(\text{Se}_2)^{2-}$ units in other indium selenides,¹² but within the range of Se-Se distances observed in polyselenides.¹⁹

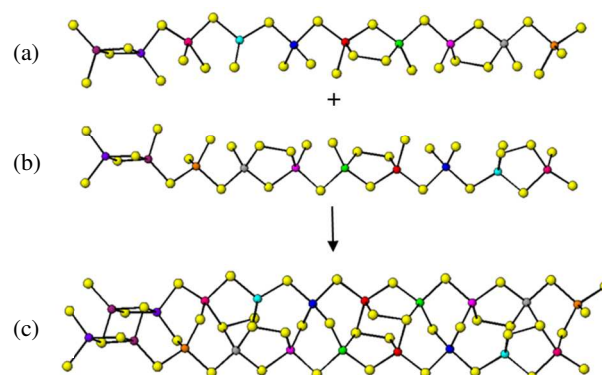


Figure 4. Two one-dimensional chains of InSe_4 tetrahedra (a) and (b) fuse in (c) to form the $[\text{In}_{10}\text{Se}_{15}(\text{Se}_2)_3]^{6-}$ ribbon found in 3. Each crystallographically independent indium atom along the chain is shown in a different colour, and selenium is shown in yellow.

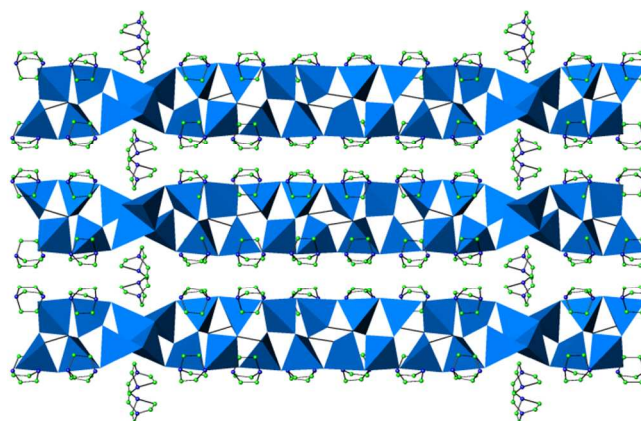


Figure 5. Polyhedral representation of the crystal structure of 3 along $[001]$. Key as for Figure 3.

The $[\text{In}_{10}\text{Se}_{15}(\text{Se}_2)_3]^{6-}$ ribbons in 3 can be described as consisting of two identical one-dimensional chains of InSe_4 tetrahedra, related by a rotation of 180° , and fused to form a ribbon (Figure 4). This ribbon exhibits twists where the tetrahedra are connected via edge-sharing linkages (Figure 5). In the crystal structure of 3, the ribbons are aligned parallel to the $[101]$ direction and interspaced by DABCO moieties, which surround the ribbons. At each twist in the ribbon, the DABCO moiety is rotated by $\sim 90^\circ$ with respect to the other DABCO molecules. This may be related to the presence of hydrogen-bonding interactions between the amine located at the twist and the ribbon, given the $\text{N}\cdots\text{Se}$ distance of 3.27(3) Å, which is similar in magnitude to previously reported hydrogen-bonding interactions in selenides.^{6,12(a),20} Charge balance requires protonation of some of the organic molecules, but the structural

study is unable to establish directly the degree of protonation of the amines. Given the significantly shorter N...Se distance (3.27(3) Å) found for the DABCO at the twist when compared to the remaining crystallographically independent amines (>4.1 Å), the former is likely to be protonated. There are also short N...N distances (ca. 2.7 Å) between neighbouring DABCO moieties, consistent with N-H...N bonding interactions.

Crystal structure of 4

Compound 4 is the first example of incorporation of a sodium complex into a solvothermally-prepared indium selenide. The crystal structure of this material contains one-dimensional ribbons, linked into a three-dimensional structure by $[\text{NaSe}_3(\text{DABCO})_2]^{5-}$ complexes. In 4, edge and corner linkages between InSe_4^{5-} tetrahedra result in the formation of a one-dimensional ribbon, with stoichiometry $[\text{In}_5\text{Se}_9]^{3-}$. This ribbon is closely related to those found in 1 and 2, although in this case, no perselenide (Se_2)²⁻ anions are present (Figure 2(b)).

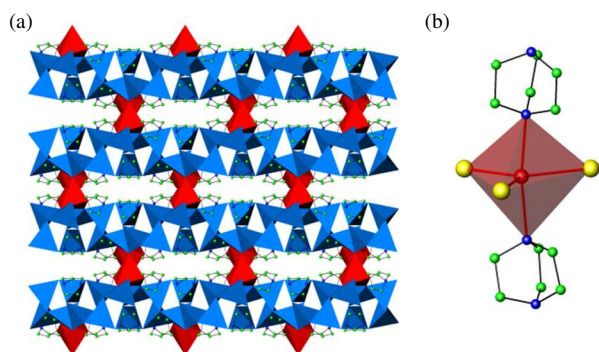


Figure 6. Polyhedral representation of (a) the crystal structure of 4 along the [001] direction, and (b) the $[\text{NaSe}_3(\text{DABCO})_2]^{5-}$ complex. Key: InSe_4 , blue tetrahedra; NaSe_3N_2 , red bipyramid; carbon, small green circles; nitrogen, small blue circles.

The ribbons are oriented along the [101] direction and linked into a three-dimensional network (Figure 6(a)) by trigonal bipyramidal complexes of $[\text{NaSe}_3(\text{DABCO})_2]^{5-}$. In this complex, sodium is bonded to three selenium atoms from three neighbouring ribbons, in the equatorial positions and two nitrogen atoms from two DABCO molecules, in the axial positions (Figure 6(b)). The Na-Se distances are 2.9681(13) and 2.973(3) Å, comparable to those in Na_2Se_2 ,²¹ and the Na-N distance is 2.516(3) Å, longer than the Na-N bonds in Na_3N .²² This might be a consequence of steric interactions between the ligands. This sodium complex is extremely unusual. The closest precedent is found in a small number of thiolates in which sodium is coordinated to N and S atoms with a coordination number of 5, but their geometry is better described as that of a distorted square planar pyramid.²³ To the best of our knowledge, examples containing selenium are not known.

To achieve charge balance, one diprotonated DABCO cation per formula unit is incorporated into the structure of 4. There are relatively short N...N distances between the DABCO cations and the $[\text{NaSe}_3(\text{DABCO})_2]^{5-}$ complexes, of 2.705(5) Å,

which imply the presence of hydrogen-bonding interactions. Although 4 exhibits a three-dimensional structure, when van der Waals' radii are taken into account there is no available porosity or free channels. This material hence consists of a dense framework.

Crystal structure of 5

Compound 5 is a rare example of a three-dimensional indium selenide. The asymmetric unit of 5 (ESI) contains seven crystallographically-independent indium atoms, all of which are tetrahedrally coordinated to selenium. The simplest secondary building block in 5 is shown in Figure 7(a). In this unit, tetrahedra containing In(2), In(4) and In(5) are corner-linked forming a chain. This is linked to another chain of corner-linked tetrahedra containing In(3), In(6) and In(7). The $\text{In}(1)\text{Se}_4$ tetrahedron caps this double chain by corner-linking to In(2), In(3) and In(7) Se_4 tetrahedra. These units of seven tetrahedra are linked into two-dimensional buckled layers (Figure 7(b)) by the terminal Se vertices. Rotation by 90° of the layers depicted in Figure 7(b), followed by their linkage through the corner of the capping tetrahedron, ($\text{In}(1)\text{Se}_4$), results in the formation a three-dimensional framework, illustrated in Figure 7(c).

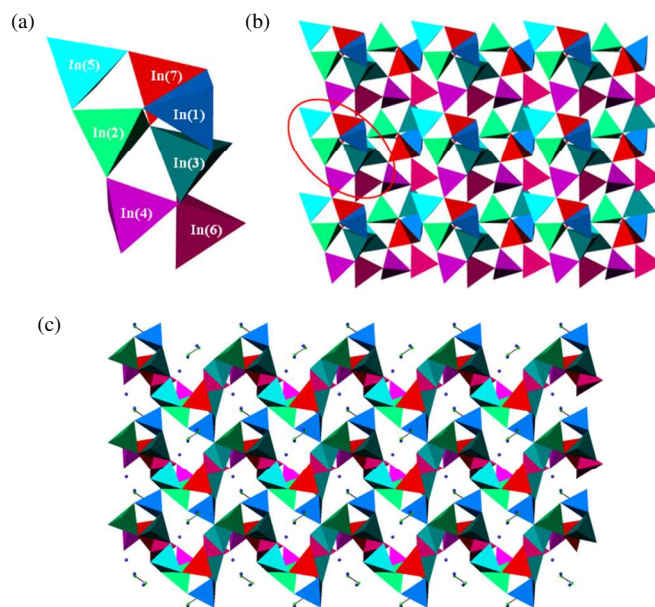


Figure 7. Polyhedral representation of (a) the secondary building block in 5; (b) the zig-zag layer in 5, with the secondary building block circled, and (c) view of the crystal structure of 5 along the [100] direction. Key: $\text{In}(1)\text{Se}_4$, blue; $\text{In}(2)\text{Se}_4$, green; $\text{In}(3)\text{Se}_4$, teal; $\text{In}(4)\text{Se}_4$, purple; $\text{In}(5)\text{Se}_4$, turquoise; $\text{In}(6)\text{Se}_4$, pink; $\text{In}(7)\text{Se}_4$, red; carbon, small green circles; nitrogen, small blue circles. Hydrogen atoms have been omitted for clarity.

For this anionic framework, the solvent accessible void space, calculated using the SOLV function in PLATON,²⁴ is only 18.9% of the unit cell volume. This void space consists of small cavities where protonated ethylenediamine and ammonium

cations reside. There is a number of N...Se distances indicative of hydrogen-bonding interactions between the framework and the organic moieties. Each of the $-\text{NH}_3^+$ groups of the enH_2^{2+} cation are involved in three H-bonding interactions with distances in the range 3.35(2) to 3.57(3) Å, with the NH_4^+ cation involved in four N-H...Se interactions of 3.34(1) to 3.59(1) Å which are comparable to interactions in previously reported indium and gallium selenides.^{6,12(a),20}

Characterisation

Powder X-ray diffraction data (ESI) collected on the bulk products of the reactions producing 1-5 indicate that 1-5 are the main products of the reactions, and the lattice parameters (ESI) determined for 1-5 using powder X-ray diffraction data are in good agreement with those determined by single-crystal diffraction.

Thermogravimetric analysis (ESI) was carried out on hand-picked crystals of 1-5 under an oxidizing atmosphere. Compounds were found to be stable up to 180-250°C. The weight loss occurs as a multistage process, with the overall weight change corresponding to the decomposition of the starting material into In_2O_3 . For 1, 3 and 5, a small increase in weight is observed between 300 and 400°C, suggesting that a selenate, selenite or oxyselenide may form in the initial stages of the decomposition process. The found weight losses, together with those calculated for the removal of the amine are as follows: 1 found: 61.2%; calc.: 61.8%; 2 found: 62.2%; calc.: 60.7%; 3 found: 59.8%; calc.: 61.5%; 4 found: 57.2%; calc.: 57.8%; 5 found: 48.3%; calc.: 46.9%.

FT-IR data (ESI) collected for 1 to 5 show bands consistent with the organic species identified within the structure by X-ray crystallography. Bands observed for 1 and 2 are consistent with the presence of DBUH^+ . For instance, the strong bands at 1685 to 1580 cm^{-1} correspond to the C-N stretch, that at $\sim 2900\text{cm}^{-1}$ can be assigned to C-H stretches, whilst the bands at 1632 and 1443 cm^{-1} are characteristic of $\nu(\text{C}=\text{N})$ and $\delta(\text{C}-\text{H})$ respectively. Bands at lower wavenumbers (1320 to 1000 cm^{-1}) are consistent with deformation and bends of C-N and C-C bonds. Bands in 3 and 4 are consistent with the presence of protonated and unprotonated DABCO, as established by comparison with the assignments reported by Guzonas and Irish.²⁵ FT-IR data for 5 are consistent with the presence of the $[\text{NH}_4]^+$ cation within the crystal structure. The band at $\sim 3000\text{cm}^{-1}$ can be assigned to the N-H symmetric stretching vibration, with the signal at 1600 cm^{-1} corresponding to N-H deformation of the $[\text{NH}_4]^+$ cations. The signal 1400 cm^{-1} can be assigned to an N-H bending mode.²⁶ Other peaks in the spectra are consistent with the presence of protonated ethylenediamine within the crystal structure ($\sim 1524\text{cm}^{-1}$ N-H def, 1478 cm^{-1} ν C-N).

Optical absorption properties

UV-Vis diffuse reflectance measurements (Figure 8) were carried out to estimate the optical band gap of compounds 1-5. The band gap values, which are given in Table 2, are consistent with the colour of the crystals (Figure 8). For antimony sulphides, the band gap variation has been related to the density

of metal centres within the crystal structures.²⁷ This correlation has been attributed to the weakening of the interactions between anion and cation orbitals with decreasing density, which has an effect on the energy levels at the top of the valence band. As shown in Table 2, this simple relationship between band gap and density of metal centres (given as number of In atoms per 1000 Å³) does not hold here. We have previously observed, when comparing the related chains $[\text{GaSe}_2]^-$ and $[\text{Ga}_2\text{Se}_3(\text{Se}_2)]^{2-}$, a marked reduction of the band gap when $(\text{Se}_2)^{2-}$ anions are present.²⁸ Similarly, the band gap of $[\text{DBUH}]_2[\text{Hg}_2\text{Sn}_2\text{Se}_6(\text{Se}_2)]$ is lower than that of the closely related $[\text{DBUH}]_2[\text{Hg}_2\text{Sn}_2\text{Se}_7]$.²⁹ This suggests that the perselenide anion contributes to energy levels close to the band gap, and hence may explain the larger band gap found for 5, when compared to those of the materials containing perselenides (1-3). The band gap variation between 4 and 5 does not follow either the expected trend of a smaller band gap with increasing framework density. This is perhaps not surprising, given that in these materials the connectivity between tetrahedra is very different and they also differ in the presence of Na.

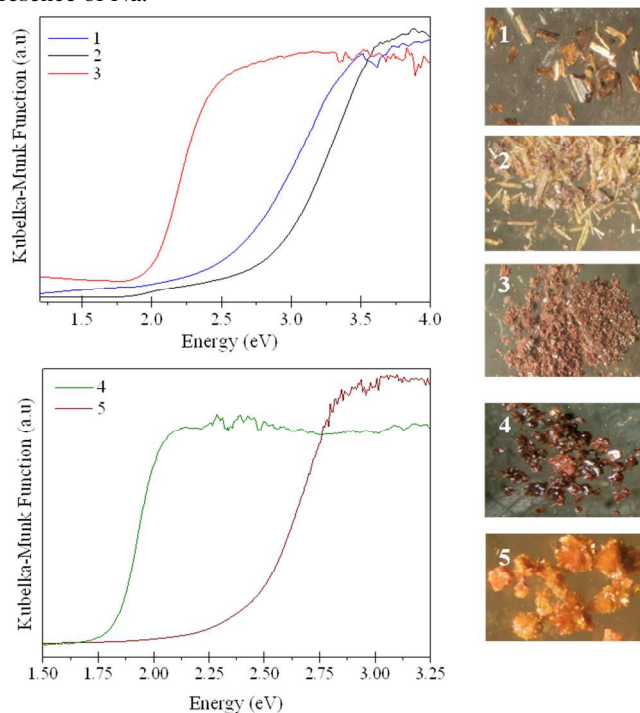


Figure 8. UV-Vis diffuse reflectance spectra for (a) compounds 1-3 and (b) 4 and 5 (left). Photographs of the crystals of 1-5 (right).

Table 2. Optical band gap and density of metal centres for compounds 1-5.

Compound	Band Gap / eV	In atoms/1000 Å ³
1	2.49(3)	4.3
2	2.83(4)	4.5
3	1.88(3)	4.9
4	1.79(1)	5.4
5	2.44(2)	9.6


Discussion

Synthetic considerations

The preparation, under mild solvothermal conditions, of compounds containing sulfur-sulfur bonds occurs only rarely. Despite the large number of main-group sulfides prepared by solvothermal synthesis,³⁰ examples containing S-S bonds remain scarce.³¹ By contrast, recent literature provides growing evidence of the relative ease of formation of compounds containing Se-Se bonds under solvothermal conditions. For example, $(\text{Se}_n)^{2-}$ anions have been found in a variety of chains, including $[\text{M}_2\text{Se}_3(\text{Se}_2)]^{2-}$ ($\text{M} = \text{Ga}, \text{In}$), $[\text{Ga}_2\text{Se}_2(\text{Se}_2)(\text{Se}_3)]^{2-}$ and $[\text{Ga}_2\text{Se}_2(\text{Se}_2)]^{2-}$,^{12,20,28} and in heterometallic ribbons such as $[\text{DBUH}]_2[\text{Hg}_2\text{Sn}_2\text{Se}_6(\text{Se}_2)]$ and $[\text{DBNH}]_4[\text{Cd}_3\text{Sn}_4\text{Se}_{11}(\text{Se}_2)_2]$ (where $\text{DBN} = 1,5\text{-diazabicyclo}[4.3.0]\text{non-5-ene}$),^{29,32} as well as the compounds 1-3 reported here. This contrasting behaviour may be related to the greater tendency shown by the heavier chalcogens to form chalcogen-rich phases, containing chalcogen-chalcogen bonds. Examination of the synthetic conditions suggests that the preparation of phases containing $(\text{Se}_n)^{2-}$ occurs more readily when more basic amines are used as solvents and/or structure-directing agents. For instance, we have observed that reactions using substituted pyridines as solvents, with pK_a values of ~ 5 to 7, have resulted in materials that do not contain perselenides,^{6,10} while reactions using primary amines (e.g. 1,4-diaminobutane, $\text{pK}_a \sim 10.8$)³³ or amidines, which are strongly basic, have produced perselenides.^{20,28,32} Of the amines used here, DBU ($\text{pK}_a \sim 24.3$)³⁴ is more strongly basic than DABCO ($\text{pK}_a \sim 8.9$),³⁵ which has a pK_a comparable to that of some alkyl amines. In both cases, materials containing $(\text{Se}_2)^{2-}$ have been obtained. Potential/pH diagrams for selenium in aqueous solutions at ambient conditions indicate that polyselenides are predominant species at high values of pH.³⁶ A similar trend seems to occur under solvothermal conditions. Further experimental data on selenides synthesised using different structure-directing agents will be useful to confirm the relationship between pK_a and the presence of $(\text{Se}_2)^{2-}$ anions.

With DBU as a structure-directing agent, compounds 1 and 2, which differ in their $(\text{Se}_2)^{2-}$ content, were obtained by varying the indium source and solvent, as well as adding imidazole, which is not incorporated in the final crystal structure. This suggests that other reaction parameters can influence the amount of $(\text{Se}_2)^{2-}$ anions incorporated into the crystal structure. It has been previously shown that the one-dimensional $[\text{DBUH}]_2[\text{Hg}_2\text{Sn}_2\text{Se}_6(\text{Se}_2)]$ transforms into $[\text{DBUH}]_2[\text{Hg}_2\text{Sn}_2\text{Se}_7]$ when increasing the reaction time.²⁹ Attempts to control the $(\text{Se}_2)^{2-}$ content in the $[\text{In}_5\text{Se}_{8+x}(\text{Se}_2)_{1-x}]^{3-}$ ribbons by varying the time were carried out, but these have not been successful so far. While DBU was found to be stable at the reaction temperatures investigated (115–200°C), DABCO only remained intact when low reaction temperatures were used. It was found that reactions using DABCO afforded a variety of structures of differing dimensionality, including the previously reported frameworks $[\text{In}_{33}\text{Se}_{56}]^{13-}$ and $[\text{In}_{10}\text{Se}_{18}]^{6-}$,

which were obtained at 170 and 185°C respectively (see ESI). A summary of the compounds obtained using DABCO is given in Scheme 1. As the temperature of the reaction is raised, an increase in the dimensionality of the products, together with an increase in the density of metal centres, is observed. At 140°C, the materials prepared, 3 and 4, contain one-dimensional ribbons, while at intermediate temperatures, the microporous frameworks $[\text{In}_{33}\text{Se}_{56}]^{13-}$ and $[\text{In}_{10}\text{Se}_{18}]^{6-}$, both of which have a porosity of ca. 50% of the available unit cell volume,^{9,7} are obtained. Compound 5, which was prepared at the highest temperature investigated, 200°C, consists of a dense three-dimensional framework with no accessible porosity. Similar findings have been reported for the solvothermal synthesis of cobalt succinates and for hybrid vanadium oxyfluorides, where increased condensation and density was found as reaction temperatures increased.³⁷ Although there are no systematic studies on the effect of temperature on the solvothermal synthesis of indium selenides, similar results have been found for other metal chalcogenides. In particular, the solvothermal synthesis, in the presence of ethylenediamine, of antimony sulfides containing transition-metal complexes has been extensively explored.³⁸ In this system, it has been shown that a change of only 25°C can result in the condensation of isolated $[\text{Sb}_2\text{S}_5]^{2-}$ anions into $[\text{SbS}_2]^-$ chains,^{38(a)} although changes in reagent concentration whilst maintaining a constant temperature can also result in markedly different products.^{38(b)} Similarly, for tin chalcogenides, marked changes in the structure dimensionality have been achieved at room temperature by varying the reactants and solvent concentrations.³⁹



Scheme 1. Products obtained at different temperatures when using DABCO as a structure-directing agent.

Structural chemistry

The anionic ribbons found in 1-4 are the first examples of ribbons in indium selenides. Two distinct ribbons, both of which constitute new structural types, have been identified in this work. Compounds 1, 2 and 4 contain anionic ribbons with the general formula $[\text{In}_5\text{Se}_{8+x}(\text{Se}_2)_{1-x}]^{3-}$, while 3 contains a $[\text{In}_{10}\text{Se}_{15}(\text{Se}_2)_3]^{6-}$ ribbon. In both cases, corner- and edge-sharing linkages of InSe_4^{5-} tetrahedra coexist in the ribbon, and this can lead to a long repeating sequence along the ribbon, as found in 3, where the distances between consecutive twists is ca. 36 Å. In the case of the $[\text{In}_5\text{Se}_{8+x}(\text{Se}_2)_{1-x}]^{3-}$ ribbons, partial substitution of Se^{2-} with $(\text{Se}_2)^{2-}$ occurs in the $[\text{In}_2\text{Se}_2]$ rings in 1 and 2, whilst 4 contains no perselenide. Although the complete replacement of Se^{2-} with a perselenide has been observed in simple indium selenide chains,¹² partial substitution had not been previously encountered. The existence of ribbons with x values of 0, 0.26 and 0.93 suggests that the synthesis of analogous ribbons with different perselenide contents should be possible, and this could be exploited to control the properties

(e.g. optical band gap) of these materials. Although there are no prior reports of indium selenide ribbons in the literature, anionic ribbons, with entirely different structural motifs to the compounds described here, have been found in the tin selenides [DBUH]₂[Hg₂Sn₂Se₆(Se₂)] and [DBUH]₂[Hg₂Sn₂Se₇]²⁹ as well as in the tellurides [HTMDP]₂[In₄Te₈] and [HDAP]₈[In₁₂Te₂₃] (where TMDP = 4,4'-trimethylenedipiperidine and DAP = 1,3,-diaminopropane).⁴⁰ The mercury tin selenides differ from the ribbons reported here in the absence of edge linkages between tetrahedra, while in the indium tellurides, a combination of corner- and edge-sharing also occur. Whilst [HTMDP]₂[In₄Te₈] does not contain (Te₂)²⁻ units, the structure of [HDAP]₈[In₁₂Te₂₃] consists of helical double chains of InTe₄⁵⁻ tetrahedra connected into a 3-dimensional network by [In₂Te₃] rings which contain a (Te₂)²⁻ anion.⁴⁰

In compound 4, the indium selenide ribbons are linked into a 3-dimensional network by highly unusual [Na(DABCO)₂]⁺ units. While Na⁺ ions can act as counteranions, as exemplified by the indium selenide framework ICF-21,² the incorporation of an alkali-metal complex as a bridging unit into a solvothermally-prepared chalcogenide is unprecedented. Transition-metal complexes have been shown to act as counteranions, pendants groups or linkers.⁴¹ By contrast, there are very few known examples of chalcogenides containing complexes of group 1 and 2 elements. These appear to be limited to the [Mg(en)₃]²⁺ complexes, which act as counteranions in [Mg(en)₃][Sb₄S₇] and [Mg(en)₃][In₂S₄],⁴² and the [Na₅(H₂O)₆]⁵⁺ clusters, which fill the cavities in the 3-dimensional frameworks of Na₅(M₄S)(MS₄)₃•6H₂O (M = Ga, In).⁴³ Compound 5 also exhibits a three-dimensional structure, which arises from corner linkage of InSe₄⁵⁻ tetrahedra. Only a small number of indium selenide frameworks are known,^{2,3,7,9,10} and 5 differs from previously reported examples in its lack of channels or accessible porosity. This material, which is obtained at temperatures at which DABCO decomposes, consists of a highly dense framework, containing only small cavities.

Conclusions

We have demonstrated that bicyclic amines can be used for the preparation of complex indium selenides, containing perselenide (Se₂)²⁻ anions, and identified amine pK_a as a significant parameter for the targeted synthesis of perselenides. In addition, the thermal stability of the amine under solvothermal conditions is important in order to produce new structural types. We have also shown that alkali-metal complexes can act as linkages in indium selenide frameworks, and identified a range of entirely new structural building blocks in these materials. These findings indicate that a wide range of complex indium selenides, containing (Se_n)²⁻ anions and/or alkali-metal complexes, should be accessible through mild solvothermal reactions.

Acknowledgements

SJE would like to thank Heriot-Watt University for a studentship. The authors would like to thank Christina Graham for elemental analysis data.

Notes and references

^a Institute of Chemical Sciences, Heriot Watt University, Edinburgh, EH14 4AS, UK.

^b Department of Chemistry, University of Reading, Whiteknights, Reading, RG6 6AD. E-mail: p.vaqueiro@reading.ac.uk

Electronic Supplementary Information (ESI) available: Local coordination diagrams, and powder X-ray diffraction patterns, thermogravimetric and FT-IR data for 1-5. CIF file deposition numbers CCDC: 1023692-1023696. See DOI: 10.1039/b000000x/

- (a) N. Zheng, X. Bu, H. Vu, P. Feng, *Angew. Chem. Int. Ed.* 2005, **44**, 5299; (b) Z. Zhang, J. Zhang, T. Wu, X. Bu, P. Feng, *J. Am. Chem. Soc.*, 2008, **130**, 15238.
- N. Zheng, X. Bu, P. Feng, *Nature*, 2003, **426**, 428.
- M. J. Manos, C. D. Malliakas, M. G. Kanatzidis, *Chem. Eur. J.*, 2007, **13**, 51.
- Q. Zhang, I. Chung, J. I. Jang, J. B. Ketterson, M. G. Kanatzidis, *Chem. Mater.*, 2009, **21**, 12.
- (a) P. Feng, X. Bu, N. Zheng, *Acc. Chem. Res.*, 2005, **38**, 293; (b) X. Bu, N. Zheng, P. Feng, *Chem. Eur. J.*, 2004, **10**, 3356; (c) L. Wang, T. Wu, X. Bu, X. Zhao, F. Zuo, P. Feng, *Inorg. Chem.*, 2013, **52**, 2259; (d) T. Wu, X. Bu, P. Liao, L. Wang, S.-T. Zheng, R. Ma, P. Feng, *J. Am. Chem. Soc.* 2012, **134**, 3619; (e) T. Wu, F. Zuo, L. Wang, X. Bu, S.-T. Zheng, R. Ma, P. Feng, *J. Am. Chem. Soc.*, 2011, **133**, 15886.
- S. J. Ewing, A. V. Powell, P. Vaqueiro, *Inorg. Chem.* 2012, **51**, 7404.
- C. Wang, X. Bu, N. Zheng, P. Feng, *Chem. Commun.*, 2002, 1344.
- S. J. Ewing, D. I. Woodward, A. V. Powell, P. Vaqueiro, *J. Solid State Chem.*, 2013, **204**, 159.
- C. Wang, X. Bu, N. Zheng, P. Feng, *Angew. Chem. Int. Ed.*, 2002, **41**, 1959.
- P. Vaqueiro, *Inorg. Chem.*, 2008, **47**, 20.
- K.-Z. Du, W.-B. Hu, B. Hu, X.-F. Guan, X.-Y. Huang, *Mat. Res. Bull.*, 2011, **46**, 1969.
- (a) S. J. Ewing, A. V. Powell, P. Vaqueiro, *J. Solid State Chem.*, 2011, **184**, 1800; (b) X. Zhang, Z.-X. Lei, W. Luo, W.-Q. Mu, X. Zhang, Q.-Y. Zhu, J. Dai, *Inorg. Chem.*, 2011, **50**, 10872; (c) H. G. Yao, M. Ji, S.-H. Ji, Y.L. An, *Z. Anorg. Allg. Chem.*, 2012, **638**, 683.
- C. L. Cahill, P. C. Burns, *Inorg. Chem.*, 2001, **40**, 1347.
- L. Palatinus, G. Chapuis, *J. Appl. Cryst.*, 2007, **40**, 786.
- G. M. Sheldrick, *Acta Cryst.*, 2008, **A64**, 112.
- P. W. Betteridge, J. R. Carruthers, R. I. Cooper, K. Prout, D. J. Watkin, *J. Appl. Cryst.*, 2003, **36**, 1487.
- TOPAS, Version 3, Bruker-AXS Inc, 1999, Madison, Wisconsin, USA.
- W. W. Wendlandt, H. G. Hecht, *Reflectance Spectroscopy*, Interscience publishers, New York, 1966.
- W. S. Sheldrick, H. G. Braunbeck, *Z. Naturforsch. B* 1989, **44**, 1397.
- W.-W. Xiong, J.-R. Li, M.-L. Feng, X.-Y. Huang, *CrystEngComm*, 2011, **13**, 6206.


- 21 H. Foeppel, E. Busmann, F. K. Frorath, *Z. Anorg. Allg. Chem.*, 1962, **314**, 12.
- 22 D. Fischer, M. Jansen, *Angew. Chem. Int. Ed.*, 2002, **41**, 1755.
- 23 (a) S. Chadwick, K. Ruhlandt-Senge, *Chem. Eur. J.*, 1998, **4**, 1768; (b) U. Englich, K. Ruhlandt-Senge, *Coord. Chem. Rev.*, 2000, **210**, 135.
- 24 A. L. Spek, *J. Appl. Cryst.*, 2003, **36**, 7.
- 25 D. A. Guzonas, D. E. Irish, *Can. J. Chem.*, 1988, **66**, 1249.
- 26 K. Nakamoto, *Infrared and Raman Spectra of Inorganic and Coordination Compounds, Part A* Wiley Interscience Publication, 5th Edition, USA, 1997, 189.
- 27 A. V. Powell, R. J. E. Lees, A. M. Chippindale, *J. Phys. Chem. Solids*, 2008, **69**, 1000.
- 28 S. J. Ewing, M. L. Romero, J. Hutchinson, A. V. Powell, P. Vaqueiro, *Z. Anorg. Allg. Chem.* 2012, **638**, 2526.
- 29 W.-W. Xiong, P.-Z. Li, T.-H. Zhou, A. I. Y. Tok, R. Xu, Y. Zhao, Q. Zhang, *Q. Inorg. Chem.*, 2013, **52**, 4148.
- 30 (a) W. S. Sheldrick, M. Wachhold, *Coord. Chem. Rev.*, 1998, **176**, 211; (b) A. V. Powell, *Int. J. Nanotechnol.*, 2011, **8**, 783.
- 31 (a) P. Vaqueiro, M. L. Romero, *J. Phys. Chem. Solids*, 2007, **68**, 1239; (b) N. Zheng, X. Bu, P. Feng, *J. Am. Chem. Soc.*, 2003, **125**, 1138; (c) Y.-H. Wang, J.-B. Jiang, P. Wang, X.-L. Sun, Q.-Y. Zhu, J. Dai, *CrystEngComm*, 2013, **15**, 6040; (d) K. M. Tan, Y. H. Ko, J. B. Parise, J. H. Park, A. Darovsky, *Chem. Mater.*, 1996, **8**, 2510.
- 32 W.-W. Xiong, K. Ye, L. Ye, Q. Zhang, *Inorg. Chem. Commun.*, 2013, **35**, 337.
- 33 CRC Handbook of Chemistry and Physics, 74th Edition, CRC Press, New York, 2003.
- 34 E.-I. Room, A. Kütt, I. Kaljurand, I. Koppel, I. Leito, I. A. Koppel, M. Mishima, K. Goto, M. Miyahara, *Chem. Eur. J.*, 2007, **13**, 7631.
- 35 R. L. Benoit, D. Lefebvre, M. Frechette, *Can. J. Chem.*, 1987, **65**, 996.
- 36 A. Olin, B. Nolang, E. G. Osadchii, L.-O. Ohman, E. Rosen, *Chemical Thermodynamics Series: Chemical Thermodynamics of Selenium 2005*, Volume 7, pp. 158-160. Ed. F. J. Mompean, J. Perrone, M. Illemassene, OECD Nuclear Energy Agency Data Bank.
- 37 (a) P. M. Forster, A. R. Burbank, C. Livage, G. Férey, A. K. Cheetham, *Chem. Commun.*, 2004, 368; (b) D. W. Aldous, N. F. Stephens, P. Lightfoot, *Dalton Trans.*, 2007, 4207.
- 38 (a) R. J. E. Lees, A. V. Powell, A. M. Chippindale, *Polyhedron*, 2005, **24**, 1941-1948; (b) H.-O. Stephan, M.G. Kanatzidis, *Inorg. Chem.* 1997, **36**, 6050-6057; (c) R. J. E. Lees, A. V. Powell, A. M. Chippindale, *J. Phys. Chem. Solids*, 2007, **68**, 1215-1219; (d) P. Vaqueiro, A. M. Chippindale, A. V. Powell, *Inorg. Chem.* 2004, **43**, 7963-7965; (e) L. Engelke, R. Stahler, M. Schur, C. Nather, W. Bensch, R. Pottgen, *Z. Naturforsch. B* 2004, **59**, 869-876; (f) M. Schur, H. Rijnberk, C. Nather, W. Bensch, *Polyhedron*, 1998, **18**, 101-107.
- 39 Yuan, M.; Dirmyer, M.; Badding, J.; Sen, A.; Dahlberg, M.; Schiffer, P. *Inorg. Chem.* **2007**, *46*, 7238-7240.
- 40 J. Heine, S. Santner, S. Dehnen, *Inorg. Chem.*, 2013, **52**, 4424.
- 41 (a) P. Vaqueiro, *Inorg. Chem.*, 2006, **45**, 4150; (b) Y.-H. Wang, M.-H. Zhang, Y.-M. Yan, G.-Q. Bian, Q.-Y. Zhu, J. Dai, *Inorg. Chem.* 2010, **49**, 9731; (c) J. Zhou, J. Dai, G.-Q. Bian, C.-Y. Li, *Coord. Chem. Rev.*, 2009, **253**, 1221.
- 42 (a) E. Quiroga-Gonzalez, C. Näther, W. Bensch, *Z. Naturforsch.* 2009, **64b**, 1312; (b) E. Quiroga-Gonzalez, L. Kienle, C. Näther, V. S. K. Chakravadhanula, H. Lühmann, W. Bensch, *J. Solid State Chem.*, 2010, **183**, 2805.
- 43 (a) N. Zheng, X. Bu, P. Feng, *J. Am. Chem. Soc.*, 2005, **127**, 5286; (b) J. Rumble, P. Vaqueiro, *Solid State Sci.*, 2011, **13**, 1137.

ARTICLE

Table 1. Crystallographic data for compounds 1-5.

Compound	1	2	3	4	5
Empirical formula	C ₂₇ H ₅₁ In ₅ N ₆ Se _{9.93}	C ₂₇ H ₅₁ In ₅ N ₆ Se _{9.26}	C ₄₂ H ₈₄ In ₁₀ N ₁₄ Se ₂₁	C ₁₈ H ₃₈ In ₅ N ₆ NaSe ₉	C ₂ H ₁₀ In ₇ N ₃ Se ₁₂
M _r	1817.65	1764.67	3603.59	1646.27	1837.38
Crystal Habit	Yellow block	Yellow needle	Red block	Red octahedron	Yellow block
Dimensions/ mm ³	0.07×0.08×0.10	0.04×0.05×0.08	0.04×0.04×0.06	0.05×0.05×0.09	0.05×0.05×0.08
Crystal System	Monoclinic	Triclinic	Monoclinic	Monoclinic	Monoclinic
Space group	<i>P</i> 2 ₁ / <i>c</i>	<i>P</i> $\bar{1}$	<i>P</i> 2 ₁ / <i>c</i>	<i>C</i> 2/ <i>c</i>	<i>P</i> 2 ₁
T/K	100	100	100	100	293
<i>a</i> /Å	11.1124(14)	10.9401(8)	35.936(3)	15.123(2)	10.3062(3)
<i>b</i> /Å	23.284(3)	12.9893(9)	21.7994(15)	20.189(2)	13.4581(4)
<i>c</i> /Å	18.304(2)	18.1462(12)	10.4921(7)	12.1666(16)	10.5966(3)
α /°	90	105.196(3)	90	90	90
β /°	101.943(5)	100.004(3)	91.201(3)	98.459(6)	96.145(2)
γ /°	90	109.565(3)	90	90	90
V/Å ³	4633.4(10)	2245.8(3)	8217.4(10)	3674.4(9)	1461.32(7)
Z	4	2	4	4	2
ρ_{cal} /g cm ⁻¹	2.606	2.609	2.903	2.976	4.153
Flack	-	-	-	-	0.079(12)
Number of parameters	261	261	504	178	193
R _{merg}	0.042	0.077	0.093	0.048	0.051
R(I>3.0 σ (I))	0.0389	0.0522	0.0690	0.0270	0.0327
R _w	0.0439	0.0572	0.0721	0.0289	0.0344

Table of Contents

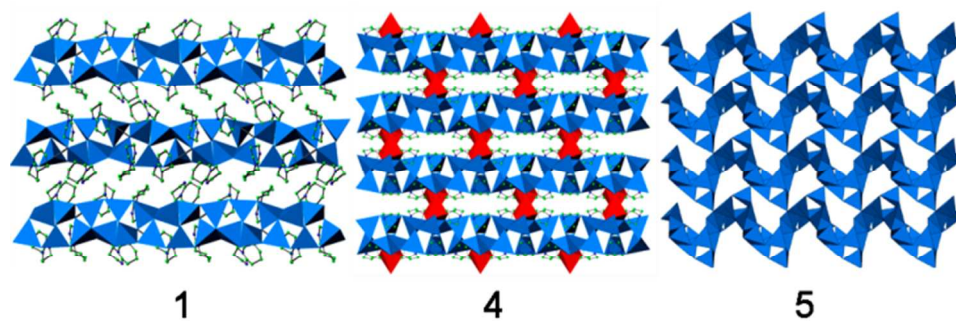

Synopsis: The use of bicyclic amines as structure-directing agents has resulted in the preparation of materials containing complex indium selenide ribbons (1-3), which can be linked into three-dimensional structures by unusual sodium complexes (4). Decomposition of the structure-directing agent leads to the formation of the dense three-dimensional framework found in 5