

# Organic & Biomolecular Chemistry

Accepted Manuscript



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

*Accepted Manuscripts* are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this *Accepted Manuscript* with the edited and formatted *Advance Article* as soon as it is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Cite this: DOI: 10.1039/c0xx00000x

www.rsc.org/xxxxxx

ARTICLE TYPE

## Tuning Viscoelastic Properties of Supramolecular Peptide Gels via Dynamic Covalent Crosslinking


Mohammad Aref Khalily<sup>a</sup>, Melis Goktas<sup>a</sup>, and Mustafa O. Guler<sup>a</sup>, \*

Received (in XXX, XXX) Xth XXXXXXXXXX 20XX, Accepted Xth XXXXXXXXXX 20XX  
DOI: 10.1039/b000000x

Dynamic covalent crosslinking approach is used to crosslink supramolecular peptide gels. This novel approach facilitates tuning viscoelastic properties of the gel and enhances mechanical stability (storage modulus exceeding  $10^5$  Pa) of the peptide gels.

Supramolecular peptide gels are a class of supramolecular polymers, which are capable of encapsulating large amount of water, up to 100 times of their dry weight. These soft materials are produced by molecular self assembly of naturally occurring short peptide sequences<sup>1</sup>. Beside their inherent biocompatibility, biodegradability and bio-functionality peptides can be straightforwardly designed with a desired sequence, function and molecular weight<sup>2</sup>. In soft materials research, versatile peptide gels have attracted a large amount attention and they have been explored comprehensively<sup>3</sup>. Supramolecular peptide gels have been exploited as scaffolds for wound healing, sustained release of drugs and biomolecules, cell culture media and tissue engineering<sup>3b, c, 4</sup>, template for nanofabrication<sup>5</sup>, catalysts for organic reactions<sup>6</sup>, and light harvesting device<sup>7</sup>. Despite versatility of peptide hydrogels, they suffer from low mechanical stability with storage moduli of 100-5000 Pa<sup>8</sup>. There has been extensive research to tune and enhance the mechanical stability of peptide gels. Light<sup>8</sup>, metal ions<sup>9</sup>, disulfide<sup>10</sup>, catalytic<sup>11</sup>, and enzymatic<sup>12</sup> crosslinking mechanisms are main approaches to improve the mechanical stability of peptide hydrogels.


Here, we utilized a novel dynamic imine covalent bonding approach to crosslink the supramolecular peptide hydrogels to tune and enhance their viscoelastic characteristics. This approach is quite simple and straightforward. The crosslinking takes place between amine and aldehyde groups in aqueous medium at room temperature and forming a dynamic covalent bond, imine<sup>13</sup>.

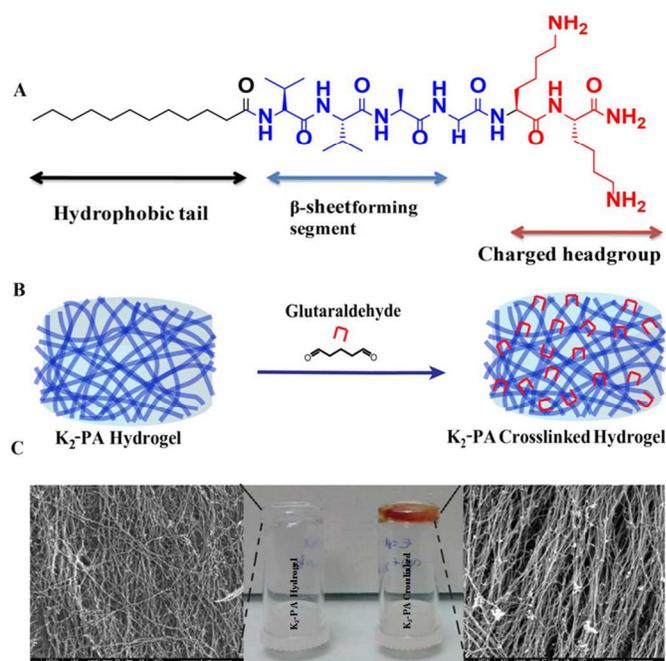

**Figure 1.** Schematic representation of peptide amphiphile chemical structure (A), peptide gel formation and glutaraldehyde crosslinking strategy (B), (C).

This novel crosslinking system has many advantages over other crosslinking strategies; it does not require any catalyst, enzyme, photocrosslinker, metal ions and any other crosslinking agent. Moreover, there is no need for purification of crosslinked peptide gels since water is the only side product from reaction of amine and aldehyde. The reversibility of imine bond is crucial for proper self-assembly of peptide molecules to conserve the nanofibrous morphology and self-healing properties.

In this study, we designed and synthesized a peptide amphiphile (P A) molecule (Lauryl-VVAGKK-Am) (Figure 1A). At pH > 7,

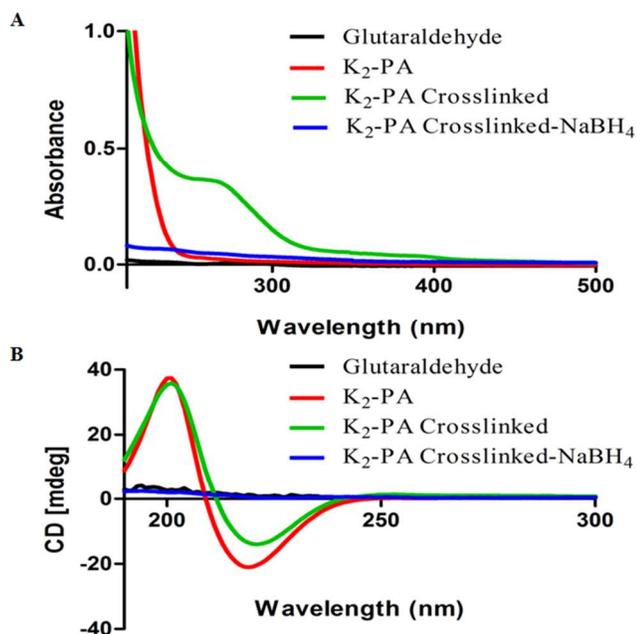


**Figure 2.** UV-Vis spectroscopy (A) and Circular Dichroism (B) analysis of peptide gels and crosslinked peptide gels at pH 7.5

the PA molecules self-assemble into nanofibers with a diameter of ca. 10 nm (Fig. 5B, and S5) directed by  $\beta$ -sheet structures. A three-dimensional network of the PA nanofibers forms a self-supporting gel at concentrations of 1 wt% (Fig. 1C and Fig. S3a) or even lower (0.1 wt%. Figure S11).

In this design, the lauryl group promotes hydrophobic interactions. Meanwhile,  $\beta$ -sheet forming amino acids (VVA) facilitates hydrogen-bonding. These two segments are required for self-assembly of peptide molecules in aqueous medium<sup>4</sup> (Figure 1C). Two lysine residues have significant roles in assisting solubility of the peptide molecules in water and then reacting with glutaraldehyde molecules to crosslink the peptide nanofibers (Figure 1B).

We investigated formation of imine bond and its affect on peptide self-assembly and  $\beta$ -sheet structure using UV-Vis spectroscopy and Circular Dichroism (CD). Although glutaraldehyde is widely used for crosslinking of biomaterials, its chemistry is not still well understood<sup>14</sup>. The reaction between amines and glutaraldehyde in aqueous solution is quite complex and many studies have been conducted to determine the products<sup>14</sup>. After peptide gel formation at pH 7.5, 10  $\mu$ L of glutaraldehyde (25% solution) was added and then imine formation was followed by UV-Vis spectroscopy. Interestingly, the crosslinked

supramolecular peptide gels showed absorbance at 265 nm

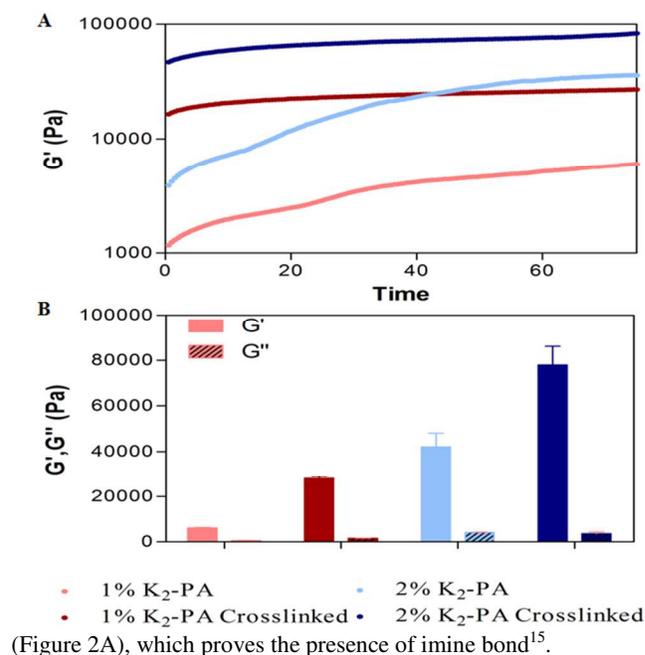


**Figure 3.** Rheological characterization of the gels. A) Gelation kinetics, B) Equilibrium moduli at pH 7.5.

We further investigated the effect of the crosslinking on peptide self-assembly by circular dichroism (CD). Dilute solution of peptide gels showed  $\beta$ -sheet structure (positive signal at 195 nm and negative signal at 220 nm) and glutaraldehyde crosslinking does not affect the  $\beta$ -sheet structure (Figure 2B). This could be due to the nature of dynamic and reversible imine bond formation in aqueous media, which does not disturb the peptide self-assembly. The imine can be reduced to amine by reductive amination using a reducing agent<sup>13</sup>. Therefore, NaBH<sub>4</sub> solution was added (2 eqv. with respect to glutaraldehyde) to crosslinked peptide hydrogels.

As the reducing agent was added into the gel, the gel collapsed immediately. The reduced peptide gels showed no absorbance at 265 nm (Figure 2A) and no  $\beta$ -sheet structure was observed (Figure 2B). Reduction of imines to amines locked the system by formation of covalent bonds instead of dynamic covalent bond, therefore, the peptide self-assembly is disturbed and the peptides lost their  $\beta$ -sheet structure and the gel formation was prevented.

We further investigated the degree of deprotonated side chain amines by zeta potential analysis because only deprotonated amines can react with glutaraldehyde. Therefore, zeta potentials were measured at different pH values by titration of peptide

solution with 0.1M NaOH (Figure S7). Although the peptide forms gel around pH 7.5 but its potential is around 15 mV

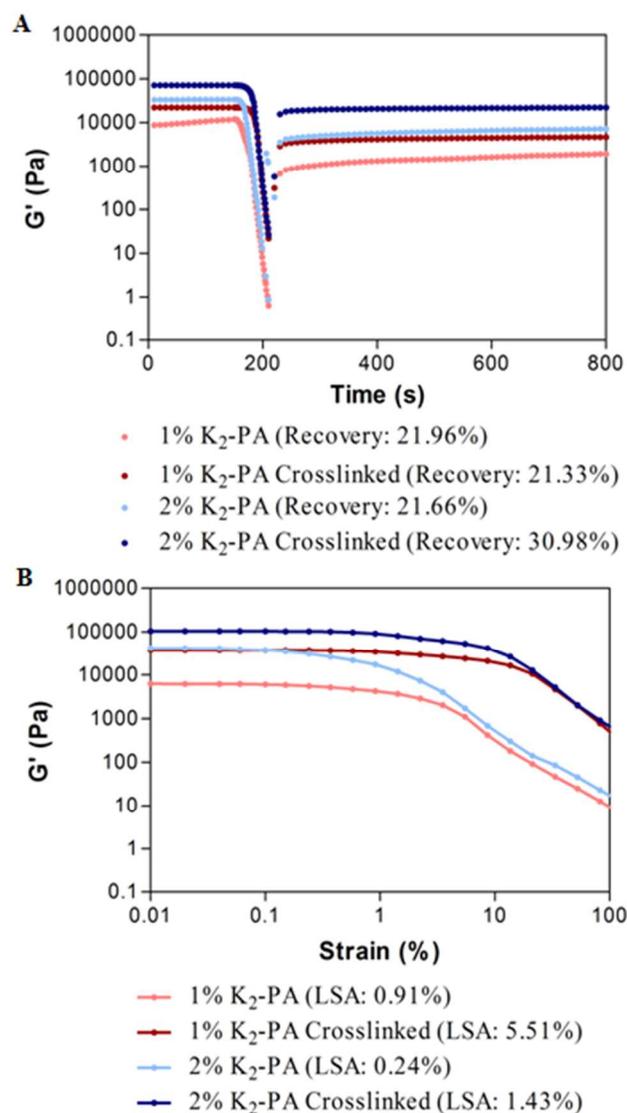


indicating that amines are not fully neutralized (Figure S7).

**Figure 4.** A) Self-healing of the gels and B) amplitude sweep test at pH 7.5.

The complete neutralization takes place when pH is above 8. Therefore, we investigated the gelation kinetics at minimum pH of gelation (7.5) and at pH 10 (Figure S8 and S9) to ensure the entire deprotonation of amines.

Gelation kinetics and viscoelastic properties are important materials characteristics indicating the potential use of a hydrogel. Oscillatory rheology was used to monitor the mechanical stiffness and elasticity of the gel systems. Gelation kinetics was determined by time-sweep test within the linear viscoelastic range. Within 75 min, storage moduli, the energy

stored during deformation, of all groups reached to a plateau demonstrating the complete gelation (Figure 3A, S8a). However, the storage moduli of noncovalently self-assembled peptide gels

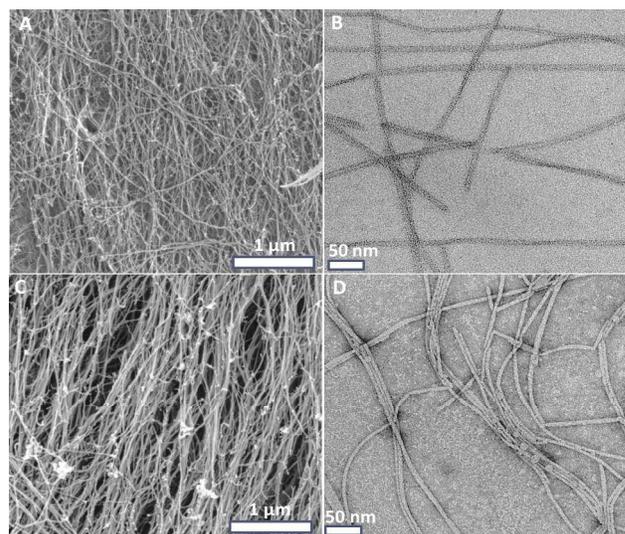

20 showed a greater ramp at pH 7.5 (Figure 3A) when compared to

**Figure 5.** SEM and TEM images of the peptide gels (A, B) and crosslinked peptide gels (C, D) at pH 7.5.

pH 10 (Figure S8a), which reached a stationary phase at the earlier periods. This result indicated that the self-assembly process was completed at an increased rate under basic conditions. In addition, covalent crosslinking through glutaraldehyde addition resulted in rapid completion of gelation process by locking the mobile PA molecules within the self-assembled system both at pH 7.5 and pH 10 (Figure S8a) when compared to regular PA gel systems.

For all of the groups, storage moduli ( $G'$ ) greater than loss moduli ( $G''$ ) and the energy loss during deformation showed the gel character of the resulting networks (Figure 3B, S8b). Storage modulus of glutaraldehyde crosslinked samples was significantly higher for all groups when compared to their self-assembled PA controls showing that the crosslinking resulted in formation of stiffer gels (Figure 3B, S8b). Another important point to elucidate is the effect of crosslinking on the mechanical properties ( $G'/G''$  ratio or loss (damping) factor). Gelation takes place when  $G'/G''$  value is below 1 and smaller damping factor refers to a more pronounced elastic character against viscous character.

Since the storage moduli of glutaraldehyde crosslinked samples were significantly higher than non-covalently self-assembled PA controls, their loss moduli was comparable. Covalent crosslinking

resulted in a smaller damping factor indicating the formation of stronger gels. Furthermore, the peptide formed stronger gels at pH 10 (Figure S10) than at pH 7.5 (Figure S10). The zeta potential analysis (Figure S7) at pH 7.5 indicated the presence of partially protonated amines. The positively charged amines cause repulsion among the peptide molecules therefore weakening the gel formation. In the case of glutaraldehyde crosslinking, at pH 7.5, the protonated amines lose their nucleophilicity therefore cannot attack the aldehyde. We can conclude that the degree of crosslinking is less at pH 7.5 than at pH 10 as result formation of a weaker gel.

To investigate the viscoelastic properties of the resulting gels, we performed amplitude sweep test showing the relationship between the storage modulus and strain amplitudes. Within the linear viscoelastic (LVE) range, gels maintained their storage moduli at constant values independent from increasing strain values. When a certain limit of LVE (limiting strain amplitude (LSA)) was exceeded, the gels showed a transition from linear to nonlinear viscoelastic behavior and the storage values started to decrease under increased strain values (Figure 4B, S9a). For all of the groups, limiting strain amplitude of glutaraldehyde crosslinked samples was approximately six times higher than that of self-assembled peptide nanofiber controls. This increase in LSA showed that compared to noncovalent networks, glutaraldehyde crosslinked PA gels can withstand six times higher shear strain. Covalent crosslinking supported the increased resistance to deformation and elasticity of the resulting networks.

To investigate the self-healing ability, in other words recovery after high shear loads, we performed thixotropic test under increasing strain amplitudes far beyond the linear viscoelastic range up to 1000%. At this range, all noncovalent interactions were expected to be broken to completely deform the network. When the shear load was removed, recovery of the noncovalent bonds was measured. The recovery of the glutaraldehyde crosslinked samples was comparable to their noncovalently self-assembled PA controls and no significant decrease was observed in the self-healing ability of the gels after covalent crosslinking (Figure 4A, S9b). After deformation, noncovalent interactions driving the self-assembly of PA molecules were similarly restored both for noncovalently self-assembled PA gels and glutaraldehyde crosslinked PA gels. Therefore, these results indicated that the glutaraldehyde crosslinking increased the mechanical stability of PA gels, supported the load bearing

capacity and elasticity of the resulting networks, and also as an additional advantage, and did not harm the self-healing ability of noncovalent interactions within the self-assembled network.

Interestingly, the dynamic crosslinking process did not affect the nanofiber morphology, porosity and fibrous structure of the peptide gels (Figure 5C, D and Figure S4, S5, S6). SEM (Figure 5A, C) and TEM (Figure 5B, D) images show no difference in width and length of the peptide nanofibers. Crosslinking at molecular level is observed by UV spectroscopy (Figure 2A) but we could not observe distinct morphological changes at the nanometer level. This could be due to dominant intrafibrillar crosslinking rather interfibrillar crosslinking. UV-vis, CD, SEM, TEM characterizations and self-healing ability of the crosslinked peptide gels prove the presence of a dynamic covalent imine bonding.

## Conclusion

In this work, we developed a novel supramolecular peptide nanostructure system, which could be crosslinked in a dynamic manner. This approach facilitates tuning and enhancing the viscoelastic characteristics of the self-assembled peptide gels. Beside improved mechanical stability, the peptide gels also conserved their porous, fibrous structures and self-healing characteristics. The viscoelastic properties of the peptide gels could further be tuned by addition of changing ratios of glutaraldehyde or addition of shorter or longer length dialdehydes.

## Notes and references

<sup>a</sup>*Institute of Materials Science and Nanotechnology, National Nanotechnology Research Center (UNAM), Bilkent University, Ankara, Turkey 06800, Tel: +90 312 290 3552, Fax: +90 312 266 4365, E-mail: moguler@unam.bilkent.edu.tr*



† Electronic Supplementary Information (ESI) available: [Experimental procedures and additional details are provided in the ESI]. See DOI: 10.1039/b000000x/

1. Cui, H.; Webber, M. J.; Stupp, S. I., Self-assembly of peptide amphiphiles: from molecules to nanostructures to biomaterials. *Biopolymers* **2010**, *94* (1), 1-18.
2. Ulijn, R. V.; Smith, A. M., Designing peptide based nanomaterials. *Chem Soc Rev* **2008**, *37* (4), 664-75.
3. (a) Dasgupta, A.; Mondal, J. H.; Das, D., Peptide hydrogels. *Rsc Adv* **2013**, *3* (24), 9117-9149; (b) Hosseinkhani, H.; Hong, P. D.; Yu, D. S., Self-Assembled Proteins and Peptides for Regenerative Medicine. *Chem*

- Rev **2013**, *113* (7), 4837-4861; (c) Jonker, A. M.; Lowik, D. W. P. M.; van Hest, J. C. M., Peptide- and Protein-Based Hydrogels. *Chem Mater* **2012**, *24* (5), 759-773; (d) Bhattacharjee, S.; Bhattacharya, S., Phthalate mediated hydrogelation of a pyrene based system: a novel scaffold for shape-persistent, self-healing luminescent soft material. *J Mater Chem A* **2014**, *2* (42), 17889-17898; (e) Moitra, P.; Kumar, K.; Kondaiah, P.; Bhattacharya, S., Efficacious Anticancer Drug Delivery Mediated by a pH-Sensitive Self-Assembly of a Conserved Tripeptide Derived from Tyrosine Kinase NGF Receptor. *Angew Chem Int Edit* **2014**, *53* (4), 1113-1117.
4. Zhao, X.; Pan, F.; Xu, H.; Yaseen, M.; Shan, H.; Hauser, C. A.; Zhang, S.; Lu, J. R., Molecular self-assembly and applications of designer peptide amphiphiles. *Chem Soc Rev* **2010**, *39* (9), 3480-98.
5. Khalily, M. A.; Ustahuseyin, O.; Garifullin, R.; Genc, R.; Guler, M. O., A supramolecular peptide nanofiber templated Pd nanocatalyst for efficient Suzuki coupling reactions under aqueous conditions. *Chem Commun* **2012**, *48* (92), 11358-11360.
6. Guler, M. O.; Stupp, S. I., A self-assembled nanofiber catalyst for ester hydrolysis. *J Am Chem Soc* **2007**, *129* (40), 12082-3.
7. Nalluri, S. K. M.; Berdugo, C.; Javid, N.; Frederix, P. W. J. M.; Ulijn, R. V., Biocatalytic Self-Assembly of Supramolecular Charge-Transfer Nanostructures Based on n-Type Semiconductor-Appended Peptides. *Angew Chem Int Edit* **2014**, *53* (23), 5882-5887.
8. Ding, Y.; Li, Y.; Qin, M.; Cao, Y.; Wang, W., Photo-Cross-Linking Approach to Engineering Small Tyrosine-Containing Peptide Hydrogels with Enhanced Mechanical Stability. *Langmuir* **2013**, *29* (43), 13299-13306.
9. Stendahl, J. C.; Rao, M. S.; Guler, M. O.; Stupp, S. I., Intermolecular forces in the self-assembly of peptide amphiphile nanofibers. *Adv Funct Mater* **2006**, *16* (4), 499-508.
10. Seow, W. Y.; Hauser, C. A. E., Tunable Mechanical Properties of Ultrasmall Peptide Hydrogels by Crosslinking and Functionalization to Achieve the 3D Distribution of Cells. *Adv Healthc Mater* **2013**, *2* (9), 1219-1223.
11. Boekhoven, J.; Poolman, J. M.; Maity, C.; Li, F.; van der Mee, L.; Minkenberg, C. B.; Mendes, E.; van Esch, J. H.; Eelkema, R., Catalytic control over supramolecular gel formation. *Nat Chem* **2013**, *5* (5), 433-437.
12. Li, Y.; Ding, Y.; Qin, M.; Cao, Y.; Wang, W., An enzyme-assisted nanoparticle crosslinking approach to enhance the mechanical strength of peptide-based supramolecular hydrogels. *Chem Commun* **2013**, *49* (77), 8653-8655.
13. Belowich, M. E.; Stoddart, J. F., Dynamic imine chemistry. *Chemical Society Reviews* **2012**, *41* (6), 2003-2024.
14. (a) Damink, L. H. H. O.; Dijkstra, P. J.; Vanluyn, M. J. A.; Vanwachem, P. B.; Nieuwenhuis, P.; Feijen, J., Glutaraldehyde as a Cross-Linking Agent for Collagen-Based Biomaterials. *J Mater Sci-Mater M* **1995**, *6* (8), 460-472; (b) Migneault, I.; Dartiguenave, C.; Bertrand, M. J.; Waldron, K. C., Glutaraldehyde: behavior in aqueous solution, reaction with proteins, and application to enzyme crosslinking. *Biotechniques* **2004**, *37* (5), 790-6, 798-802.
15. Bowes, J. H.; Cater, C. W., The interaction of aldehydes with collagen. *Biochim Biophys Acta* **1968**, *168* (2), 341-52.

5

Table of Contents Image

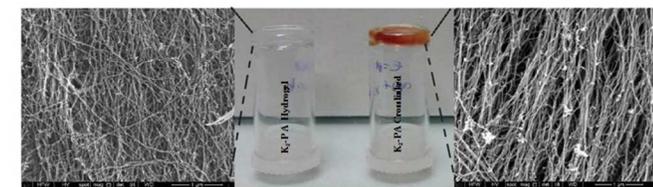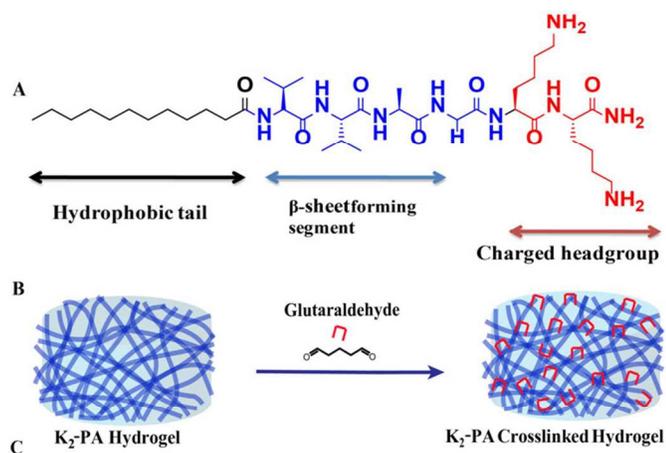

10