

RSC Advances




This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

Graphical Abstract

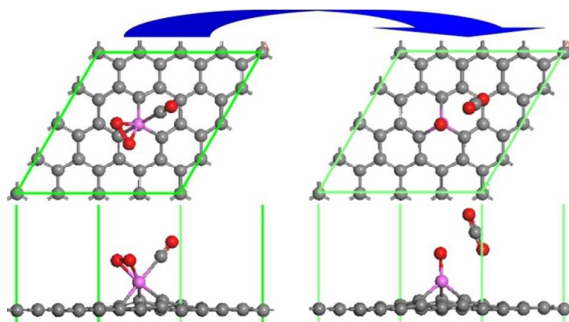

The energy barrier of the CO oxidation for the rate limiting step on Al-embedded graphene is only 0.32 eV.

Density Functional Theory Calculations on the CO Catalytic Oxidation on Al-Embedded Graphene

Q. G. Jiang,^{1,2} Z. M. Ao,^{3*} S. Li,² Z. Wen^{1*}

1 Key Laboratory of Automobile Materials (Jilin University), Ministry of Education, and School of Materials Science and Engineering, Jilin University, Changchun 130022, China

2 School of Materials Science and Engineering, The University of New South Wales, Sydney, NSW 2052, Australia

3 Centre for Clean Energy Technology, School of Chemistry and Forensic Science, University of Technology, Sydney, PO Box 123, Broadway, Sydney, NSW 2007, Australia

Abstract

The oxidation of CO molecules on Al-embedded graphene has been investigated by using the first principles calculations. Both Eley-Rideal (ER) and Langmuir-Hinshelwood (LH) oxidation mechanisms are considered. In the ER mechanism, O₂ molecule is first adsorbed and activated on Al-embedded graphene before a CO molecule approaches, the energy barrier for the primary step (CO + O₂ → OOCO) is 0.79 eV. In the LH mechanism, O₂ and CO molecules are firstly co-adsorbed on Al-embedded graphene, the energy barrier for the rate limiting step (CO + O₂ → OOCO) is only 0.32 eV, much lower than that of ER mechanism, which indicates that LH mechanism is more favourable for CO oxidation on Al-embedded graphene. Hirshfeld charge analysis shows that embedded Al atom would modify the charge distributions of co-adsorbed O₂ and CO molecules. The charge transfer from

* Corresponding authors: zhimin.ao@uts.edu.au; wenzi@jlu.edu.cn

O₂ to CO molecule through the embedded Al atom plays an important role for the CO oxidation along the LH mechanism. Our result shows that the low cost Al-embedded graphene is an efficient catalyst for CO oxidation at room temperature.

Key words: graphene, Al-embedded, CO, oxidation, first principles

1. Introduction

The oxidation of carbon monoxide (CO) has attracted great interests due to its importance in applications such as cleaning air and atmosphere purification for CO₂ lasers,^{1,2} as well as removing CO from hydrogen gas fuel to avoid electrode poisoning in fuel cells.³ Some noble metals, such as Au,⁴ Pt,⁵⁻⁷ Pd^{6,8} and Rh^{9,10} have been studied as catalysts for CO oxidation, and the typical energy barriers for the rate limiting step in CO oxidation reaction reported are 0.46 eV for Au(221),⁴ 0.79 eV⁶ (0.82 eV⁷) for Pt(111), 0.91 eV⁶ (0.93 eV⁸) for Pd(111), 1.17 eV⁶ (1.01 eV⁹) for Rh(111), and 1.00 eV for Rh(100).¹⁰ Supported noble metal clusters are exploited to further decrease the reaction barriers for CO oxidation.¹¹⁻¹⁵ However, these noble metal catalysts are costly and usually require high reaction temperature for efficient operation due to the high energy barriers, which is energy-consuming and may trigger explosion in the presence of hydrogen molecules. Therefore, developing low-cost catalysts for CO oxidation at room temperature is desirable, i.e. further reducing the energy barrier for the CO oxidation reaction using non-noble metals.

As a novel form of carbon, graphene¹⁶ is a promising matrix to support metal atoms to realize new catalysts due to its outstanding electrical,¹⁷ mechanical¹⁸ and thermal properties.¹⁹ Moreover, the large surface-to-volume ratio also benefits for graphene as a support for heterogeneous catalysts. However, the interaction between pristine graphene and CO molecule is rather weak due to the inert nature of the graphene sheet.²⁰ Theoretically, Au-, Fe-, Cu-, Pt- and Si-embedded graphenes were predicted to be highly active catalysts for CO oxidation,²¹⁻²⁵ where the energy barriers for the rate limiting step are 0.31 eV for Au-embedded,²¹ 0.58 eV for Fe-embedded,²² 0.54 eV for Cu-embedded,²³ 0.59 eV for Pt-embedded,²⁴ and 0.57 eV for Si-embedded graphene,²⁵ respectively. Among these embedded graphenes, the

Au-embedded graphene shows the best performance for CO oxidation. However, the adsorption energy of CO molecule ($E_{\text{ad_CO}} = -1.53$ eV) is larger than that of O₂ molecule ($E_{\text{ad_O}_2} = -1.34$ eV) on Au-embedded graphene,²¹ which indicates that CO molecule has priority to adsorb on the Au-embedded graphene and may prevent the oxidation reaction. Therefore, further exploiting efficient graphene-based catalyst for CO oxidation is necessary. It has been reported that the reaction energy barrier is proportional to the adsorption energy of adsorbed molecules.⁶ For example, the reaction mechanism for CO oxidation on Au- and Cu-embedded graphene is the same, and the co-adsorption energy of CO and O₂ molecules on Au-embedded graphene ($E_{\text{ad}} = -1.82$ eV)²¹ is much smaller than that on Cu-embedded graphene ($E_{\text{ad}} = -3.29$ eV),²³ corresponding to a smaller energy barrier for the rate limiting step on Au-embedded graphene. Our previous studies show that Al-embedded graphene is a highly active catalyst for H₂O dissociative adsorption²⁶ and is a promising sensor material for CO detection.²⁰ In addition, our calculated co-adsorption energy of CO and O₂ molecules on Al-embedded graphene ($E_{\text{ad}} = -1.95$ eV) is similar to that on Au-embedded graphene. Therefore, we expect that graphene embedded with the low-cost metal Al may be also highly active as a catalyst for the CO oxidation.

In this work, we will study the reaction mechanism of the CO oxidation on Al-embedded graphene through first principles calculations. The energy barriers for the reaction are discussed and the corresponding mechanisms are analyzed through understanding the electronic structures.

2. Calculation methods

The spin-unrestricted density functional theory (DFT) calculations are carried out by using Dmol³ package.²⁷ Exchange-correlation functions are taken as

generalized gradient approximation (GGA) with Perdew–Burke–Ernzerhof (PBE).²⁸ DFT semicore pseudopotentials (DSPPs) core treatment is implemented for relativistic effects, which replaces core electrons by a single effective potential. Double numerical plus polarization (DNP) is employed as the basis set. The convergence tolerance of energy of 10^{-5} Hartree is taken (1Hartree = 27.21 eV), and the maximal allowed force and displacement are 0.002 Hartree/Å and 0.005 Å, respectively. It was reported that the selection of exchange–correlation functional has evidential effect on the result of adsorption energies. However, the effect on the calculated reaction energy barriers is much smaller.²⁹ To investigate the minimum energy pathway for CO oxidation on graphene, linear synchronous transit/quadratic synchronous transit (LST/QST)³⁰ and nudged elastic band (NEB)³¹ tools in Dmol³ module are used, which have been well validated to determine the structure of the transition state and the minimum energy reaction pathway. In the simulation, three–dimensional periodic boundary conditions are taken. The simulation cell consists of a 4×4 graphene supercell with a vacuum width of 20 Å above the graphene layer to minimize the interlayer interaction. The k –point is set to $5 \times 5 \times 1$, and all atoms are allowed to relax according to previous reports.²⁶ After structure relaxations, the density of states (DOS) are calculated with a finer k –point grid of $15 \times 15 \times 1$. The DFT+D method within the Grimme scheme³² is used in all calculations to consider the van der Waals forces. The electron orbits of the free and adsorbed molecules are calculated with CASTEP code,³³ where the ultrasoft pseudopotentials, GGA–PBE functional, an energy cutoff of 340 eV and $5 \times 5 \times 1$ k –point meshes are used.

For one molecule (CO or O₂) adsorbed on graphene, the adsorption energy E_{ad} is determined by,

$$E_{\text{ad}} = E_{\text{molecule/graphene}} - (E_{\text{graphene}} + E_{\text{molecule}}) \quad (1a)$$

where $E_{\text{molecule/graphene}}$, E_{graphene} and E_{molecule} are total energies of the molecule/graphene system, the isolate graphene and a molecule in the same slab, respectively.

For two molecules (CO and O₂) co-adsorbed on graphene, the co-adsorption energy E_{ad} is determined by,

$$E_{\text{ad}} = E_{\text{molecules/graphene}} - (E_{\text{graphene}} + E_{\text{CO}} + E_{\text{O}_2}) \quad (1b)$$

where $E_{\text{molecules/graphene}}$, E_{graphene} , E_{CO} and E_{O_2} are total energies of the molecules/graphene system, the isolate graphene, CO and O₂ in the same slab, respectively.

3. Results and Discussion

After embedding Al into graphene, where one C atom is substituted by one Al atom, the structure of graphene is reconstructed and the relaxed structure is shown in Fig. 1a. Covalent Al–C bonds are formed in graphene. Al is moved out of the plane to get more space due to its relatively large atomic radius of 1.25 Å, while that of C is 0.7 Å. The distance between the Al atom and graphene is $h_{\text{Al}} = 1.51$ Å, which is consistent with the reported result of $h_{\text{Al}} = 1.43$ Å.³⁴ The C–Al bond length $l_{\text{C–Al}}$ is 1.85 Å, which is in agreement with the reported result of 1.85 Å^{34,35} (1.86 Å³⁶). The binding energy of the Al atom in graphene is –5.60 eV. The atomic charges obtained by Hirshfeld method near the dopant are also given in the configuration of IS in Fig. 1a, where the Al atom forms electron–deficiency position by transferring electrons (0.40e) to graphene. The strong interaction between the Al atom and C atoms can be further confirmed by the partial density of states (PDOS) (Fig. 1b), where significant overlap of the bands of the embedded Al atom and C atom is found. In addition, the Fermi level crosses the valence band, indicating the electron–deficiency character, which is consistent with the atomic charge distribution obtained by Hirshfeld method.

To determine the possibility of Al aggregation, which is a problem when the concentration of the metals atoms is high,³⁷ the diffusion of the Al atom to its neighbouring position on graphene is investigated (see Fig. 1a). It is found that the corresponding diffusion barrier for Al atom is 2.98 eV. Since a surface reaction at ambient temperature may occur only when the energy barrier is smaller than the critical barrier of $E_{\text{cbar}} = 0.91$ eV,³⁸ the Al atom here is rather stable. In addition, the binding energy of Al on graphene is -5.60 eV, which is stronger than the cohesive energy of Al element of -3.39 eV/atom.³⁹ Therefore, the Al dopant can disperse on graphene quite stably without clustering problem.

To investigate the oxidation of CO on Al-embedded graphene, the adsorptions of CO and O₂ on Al-embedded graphene are first calculated, respectively. Fig. 2a shows the most stable configuration of a CO molecule adsorbed on Al-embedded graphene. It shows that the CO molecule is on the top of the embedded Al atom and vertical to graphene surface. Chemical bond is formed between the C atom in CO and the Al atom, indicating chemical adsorption of the CO molecule on Al-embedded graphene, which also agrees with the reported result.²⁰ The corresponding adsorption energies and structure data of the most stable configurations for CO and O₂ adsorption on Al-embedded graphene are listed in Table 1. The adsorption energy of a CO molecule on Al-embedded graphene $E_{\text{ad}} = -0.83$ eV, and $\sim 0.15 e$ is transferred from the CO molecule to the Al-embedded graphene based on Hirshfeld analysis. Fig. 2b shows the PDOS and orbitals of a free CO molecule. All orbitals are labelled and the $2\pi^*$ anti-bond orbital is fully empty since it locates far above Fermi level, which is consistent with the literature results for CO molecule.⁵ The other three orbitals are fully occupied. In addition, the 5σ orbital with two electrons at the Fermi level state mainly locates on the C atom, indicating that CO always acts as a donor when its C

atom pointing to the graphene surface.⁴⁰ This agrees with the above Hirshfeld analysis result. Fig. 2c and 2d show PDOS and orbitals of the adsorbed CO molecule on Al-embedded graphene, respectively. Compared with the free CO molecule, the 5σ spin down peak is significantly depressed in the CO adsorbed on Al-embedded graphene due to the transferring of electrons from CO to Al atom. Because CO- $2\pi^*$ is close to the Fermi level, there is some electrons transferred from Al atom to CO- $2\pi^*$ state and CO- $2\pi^*$ state is partial filled as shown in Fig. 2c and 2d, which leads to the slight elongation of the C-O bond from 1.14 Å in free CO molecule to 1.15 Å.

For the O₂ adsorption on Al-embedded graphene, the O₂ molecule is adsorbed on Al atom much stronger with an E_{ad} of -1.57 eV and the O-O bond is slightly tilted with the graphene sheet (see IS in Fig. 3a and 3d). To assess the stability of O₂ molecule on graphene, we also studied the dissociative adsorption of an O₂ molecule on Al-embedded graphene as shown in Fig. 3a. After dissociative adsorption, one O atom adsorbs on Al atom while the other O atom co-binds with the Al atom and a neighbouring C atom at FS state as shown in Fig. 3a. After LST/QST and NEB calculations, the energy barrier for the dissociative adsorption of an O₂ molecule on the Al-embedded graphene is 1.66 eV > $E_{\text{bar}} = 0.91$ eV,³⁸ which indicates that the adsorbed O₂ molecule is stable on Al-embedded graphene without dissociation at room temperature. The possibility of CO dissociation on Al-embedded graphene is also considered. Our DFT calculations show that binding energy of C-O bond ($E_{\text{b}} = 11.57$ eV) is much stronger than that of O-O bond ($E_{\text{b}} = 6.36$ eV). Thus CO should be more difficult to be dissociated. As seen in Fig. 3b, all the orbitals of free O₂ molecule are labelled while the $2\pi^*$ anti-bond orbital is half filled, which is consistent with the literature results for O₂ molecule.⁴¹ When one O₂ molecule is adsorbed on

Al-embedded graphene, based on Hirshfeld analysis, there are about 0.31 e to be transferred from the Al-embedded graphene to O₂ molecule, which occupies the initial empty component of the O₂-2 π^* orbital. This can be confirmed by two new peaks presence for O₂-2 π^* orbital after its adsorption on the Al-embedded graphene (see Fig. 3c), which also leads to the elongation of the O-O bond from 1.23 Å in free O₂ molecule to 1.43 Å. The hybridization between the Al atom and O₂-2 π^* orbitals is observed near Fermi level from the PDOS (see Fig. 3c). The above results reveal that Al-embedded graphene has strong interactions with O₂ and CO (corresponding E_{ad} are -1.57 and -0.83 eV, respectively), but the adsorption of O₂ is much stronger. The adsorbed O₂ is efficiently activated, which facilitates the further oxidation of CO molecules.

Two mechanisms for CO oxidation have been established: Eley-Rideal (ER) mechanism and Langmuir-Hinshelwood (LH) mechanism.^{21-25,42,43} In the ER mechanism, the pre-adsorbed O₂ molecule is activated by charge transferring with the substrate and an intermediate product forms when a free CO molecule approaching. In the LH mechanism, O₂ and CO molecules co-adsorb on the embedded graphene before the reaction happening. Since O₂ has stronger adsorption energy (-1.57eV) than that of CO on Al-embedded graphene (-0.83 eV), the adsorption of O₂ on Al-embedded graphene has higher priority, and thus the ER mechanism seems to be more favourable. Although the adsorption energy difference between CO and O₂ is relatively large, the lower co-adsorption energy of CO and O₂ molecules (-1.95 eV) indicates that there is a certain probability of having O₂ and CO co-adsorbed on Al atom as discussed in literatures.^{21,23,24} Therefore, both mechanisms will be investigated in this work.

In order to determine the preferred mechanism for CO oxidation, the first reaction step of both ER and LH mechanisms is studied, respectively. If the ER mechanism is favourable, the physisorbed CO molecule will react with the pre-adsorbed O₂ molecule to form OOCO intermediate (shown as the TS in Fig. 4a). If the LH mechanism is favourable, the physisorbed CO molecule will co-adsorb on Al atom with O₂ molecule with a small energy barrier. The energy profile for the ER mechanism is shown in Fig. 4a. The configuration of physisorbed CO perpendicular to the graphene surface was selected as the initial state IS after considering all possible adsorption positions. When one CO molecule approaches the activated O₂, after overcoming an energy barrier of 0.79 eV, one O–Al bond is broken, the O with dangling bond would form a covalent bond with the C atom in the CO molecule (see TS in Fig. 4a). Then the C atom of the CO binds with one C atom closed to the Al dopant and a peroxo-type OOCO complex is formed over the Al atom (see FS in Fig. 4a). This process is exothermic and releases energy of 1.28 eV. Fig. 4b shows the energy profile for the CO molecule co-adsorbed on Al atom with O₂ molecule, where the CO molecule is tilted towards the Al atom at TS state. After overcoming a small energy barrier of 0.03 eV, the CO molecule co-adsorbs on Al atom at FS state as shown in Fig. 4b. This process is exothermic with releasing energy of 0.18 eV.

The energy barriers above are considered at zero Kelvin. To take into consideration the effect of temperature, free energy change (ΔG) between IS and TS is considered as the corrected energy barrier E'_{bar} and can be determined by $\Delta G = \Delta H - T\Delta S$, where ΔH is the change in enthalpy, T is the room temperature (298.15 K), and ΔS is the change in entropy. It is known that $\Delta H = (\Delta U + P\Delta V)$, $\Delta U = (\Delta E_{\text{tot}} + \Delta E_{\text{vib}} + \Delta E_{\text{trans}} + \Delta E_{\text{rot}})$ and $\Delta S = \Delta S_{\text{vib}} + \Delta S_{\text{trans}} + \Delta S_{\text{rot}}$, where ΔU is the change of internal energy, ΔE_{tot} is the total electronic energy change obtained from DFT calculations,

the subscript *vib*, *trans* and *rot* indicate the components from vibration, translation and rotation, respectively. All the above terms can be calculated with vibrational frequency calculations in Dmol³ code. The corrected energy barriers at room temperature for each step in Fig. 4 are: $E'_{\text{bar}} = 0.95$ eV in Fig. 4a, and $E'_{\text{bar}} = 0.16$ eV in Fig. 4b. This result is reasonable since the physisorbed CO molecule prefers to desorb from graphene at higher temperature, which makes the reaction more difficult to occur. Since a surface reaction at room temperature may occur only when $E_{\text{bar}} < E_{\text{cbar}} = 0.91$ eV,³⁸ the reaction for the co-adsorption of CO and O₂ molecules in Fig. 4b will happen at room temperature, the LH mechanism is thus focused in the following.

For CO oxidation with LH mechanism, there are several steps and also intermediate products (MS) for the oxidation procedure as reported.^{21,23,24} For each reaction step, e.g. from IS to MS in Fig. 5a, there is also a transition state, the corresponding atomic structures before (IS) and after oxidation (FS), and MS are given in Fig. 5a. The configuration of co-adsorbed CO and O₂ on the Al-embedded graphene is taken as the initial state (IS in Fig. 5a) before oxidation based on the discussion above, where CO and O₂ are tilted and parallel to the graphene surface, respectively. At TS state, one Al–O bond elongates from 1.86 to 2.38 Å and the new C–O bond is formed. After overcoming an energy barrier of 0.32 eV, OOCO complex (MS in Fig. 5a) is formed while one O–Al bond is broken. This reaction continues with the formation of one CO₂ molecule (MS2) after overcoming an energy barrier of 0.18 eV (see Fig. 5b), and the CO₂ molecule is physically adsorbed in MS2 structure with an adsorption energy of –0.16 eV. Since the energy released in this step (2.34 eV) can sufficiently surmount the adsorption energy, the desorption of the first produced CO₂ molecule would be efficient. Note that the OOCO configuration in MS remains

at TS2 with slight adjustments of bond length and bond angle. The remaining O atom will react with another CO to produce CO₂ after overcoming an energy barrier of 0.10 eV based on our calculation (see Fig. 5c), similar to the reported result on Au-embedded graphene.²¹ The energy released in this step (2.60 eV) can also overcome the adsorption energy of CO₂ (-0.40 eV) in FS structure and the desorption of the second CO₂ molecule would be efficient as well. The energy profile for the formation of the first CO₂ molecule is shown in Fig. 5d where the rate limiting energy barrier is quite low (0.32 eV) for the formation of OOCO complex. Therefore, CO molecules can be easily oxidized on Al-embedded graphene at room temperature, indicating that Al-embedded graphene is an excellent catalyst for the CO oxidation. The catalyst efficiency is the second highest among present catalysts except Au-embedded graphene (0.31 eV²¹).

The corrected energy barriers at room temperature for each step in Fig. 5 are: $E'_{\text{bar}} = 0.35$ eV for step1, $E'_{\text{bar}} = 0.12$ eV for step2, and $E'_{\text{bar}} = 0.19$ eV for step3. The energy barriers for step1 and step3 slightly increase at room temperature compared with those at zero Kelvin. The reaction time for each step in Fig. 5 at room temperature is estimated by the following equation,

$$\tau = \frac{1}{\nu e^{\left(\frac{-E_{\text{bar}}}{K_B T}\right)}} \quad (2)$$

where ν is in order of 10^{12} Hz, K_B is the Boltzmann constant and $T = 298.15$ K. $\tau_1 = 8.1 \times 10^{-7}$ s for step1, $\tau_2 = 1.1 \times 10^{-10}$ s for step2, and $\tau_3 = 1.6 \times 10^{-9}$ s for step3, respectively. Thus, the CO oxidation on Al-embedded graphene in LH mechanism possesses very fast reaction kinetics.

To gain more insight into the origin of the high activity of the Al-embedded graphene, the Hirshfeld charge transfer and PDOS near the adsorbates along the LH

reaction path are shown in Figs. 5 and 6, respectively. O_2 obtains 0.362 e while CO loses 0.163 e by Hirshfeld charge analysis for IS structure in Fig. 5a. The initial empty component of the $O_2-2\pi^*$ orbital is partially filled while the $CO-2\pi^*$ orbital is nearly empty (see Fig. 6a) due to the electron transformation during the adsorption. Therefore, there is a tendency of charge transfer from the electron–efficiency O_2 to the electron–inefficiency CO, which will facilitate the bond formation of O_2 and CO. At TS state, the Hirshfeld charge of O_2 molecule is 0.287 e while that of CO molecule is 0.094 e in Fig. 5a, which indicates that there is charge transfer from O_2 to CO. The $CO-2\pi^*$ orbital is more filled and splitted as shown in Fig. 6b. After overcoming the energy barrier, there is more charge transfer from O_2 to CO, where the Hirshfeld charge of O_2 molecule is 0.237 e while that of CO molecule is 0.049 e for MS structure in Fig. 5a. The $O_2-2\pi^*$ orbital is significantly depressed while the $CO-2\pi^*$ orbital is half filled in Fig. 6c. The above discussions show that the Al–embedded graphene mediate the charge distribution of O_2 and CO molecules, where the charge transfer from O_2 to CO plays a key role for the OOCO formation. Moreover, the states of C–O in CO molecule and O1–O2 (labelled in Fig. 5a) in O_2 molecule interact with each other, strengthening C–O2 bond while weakening O1–O2 bond, as indicated by the superposition of the C–O and O1–O2 states at TS2 (see Fig. 6d), which will facilitate the formation of CO_2 molecule.

4. Conclusion

The oxidation of CO molecule on Al–embedded graphene has been investigated by using the first principles method. It is found that the LH mechanism is preferred for CO oxidation on Al–embedded graphene, where the energy barrier for the rate limiting step is only 0.32 eV. This barrier is lower than almost all reported catalysts, except the Au–embedded graphene with barrier of 0.31 eV. The charge transfer from

O₂ to CO molecule through the embedded Al plays an important role for the CO oxidation along the LH mechanism. Our result indicates that Al-embedded graphene can be a low cost and efficient catalyst for CO oxidation.

Acknowledgements

We acknowledge supports by National Key Basic Research, Development Program (Grant No. 2010CB631001) and China Scholarship Council (No. 201206170088). ZA acknowledges the financial supports from the Chancellor's Postdoctoral Research Fellowship Program of the University of Technology, Sydney, and the Goldstar Award of the University of New South Wales (RG124422). SL would also like to thank the financial support from Australia Research Council (FT FT100100956).

References

1. A. A. Herzing, C. J. Kiely, A. F. Carley, P. Landon and G. J. Hutchings, *Science*, 2008, **321**, 1331.
2. X. W. Xie, Y. Li, Z. Q. Liu, M. Haruta and W. J. Shen, *Nature*, 2009, **458**, 746.
3. A. Hornes, A. B. Hungria, P. Bera, A. L. Camara, M. Fernandez–Garcia, A. Martinez–Arias, L. Barrio, M. Estrella, G. Zhou, J. J. Fonseca, J. C. Hanson and J. A. Rodriguez, *J. Am. Chem. Soc.*, 2010, **132**, 34.
4. Z. P. Liu, P. Hu and A. Alavi, *J. Am. Chem. Soc.*, 2002, **124**, 14770.
5. K. Bleakley and P. Hu, *J. Am. Chem. Soc.*, 1999, **121**, 7644.
6. X. Q. Gong, Z. P. Liu, R. Raval and P. Hu, *J. Am. Chem. Soc.*, 2004, **126**, 8.
7. C. Dupont, Y. Jugnet and D. Loffreda, *J. Am. Chem. Soc.*, 2006, **128**, 9129.
8. C. J. Zhang and P. Hu, *J. Am. Chem. Soc.*, 2001, **123**, 1166.
9. A. H. Zhang, J. Zhu and W. H. Duan, *J. Chem. Phys.*, 2006, **124**, 234703.
10. D. J. Liu, *J. Phys. Chem. C*, 2007, **111**, 14698.
11. Z. P. Liu, X. Q. Gong, J. Kohanoff, C. Sanchez and P. Hu, *Phys. Rev. Lett.*, 2003, **91**, 266102.
12. B. Huber, P. Koskinen, H. Häkkinen and M. Moseler, *Nat. Mater.*, 2006, **5**, 44.
13. D. Y. Tang and J. Zhang, *RSC Adv.*, 2013, **3**, 15225.
14. P. Ghosh, M. F. Camellone and S. Fabris, *J. Phys. Chem. Lett.*, 2013, **4**, 2256.
15. Y. G. Wang, Y. Yoon, V. A. Glezakou, J. Li and R. Rousseau, *J. Am. Chem. Soc.*, 2013, **135**, 10673.
16. K. S. Novoselov, A. K. Geim, S. V. Morozov, D. Jiang, Y. Zhang, S. V. Dubonos, I. V. Grigorieva and A. A. Firsov, *Science*, 2004, **306**, 666.
17. K. S. Novoselov, A. K. Geim, S. V. Morozov, D. Jiang, M. I. Katsnelson, I. V. Grigorieva, S. V. Dubonos and A. A. Firsov, *Nature*, 2005, **438**, 197.
18. C. G. Lee, X. D. Wei, J. W. Kysar and J. Hone, *Nature*, 2008, **321**, 385.
19. A. A. Balandin, S. Ghosh, W. Bao, I. Calizo, D. Teweldebrhan, F. Miao and C. N. Lau, *Nano Lett.* 2008, **8**, 902.
20. Z. M. Ao, J. Yang, S. Li and Q. Jiang, *Chem. Phys. Lett.*, 2008, **461**, 276.
21. Y. H. Lu, M. Zhou, C. Zhang and Y. P. Feng, *J. Phys. Chem. C*, 2009, **113**, 20156.
22. E. H. Song, Z. Wen and Q. Jiang, *J. Phys. Chem. C*, 2011, **115**, 3678.
23. Y. F. Li, Z. Zhou, G. T. Yu, W. Chen and Z. F. Chen, *J. Phys. Chem. C*, 2010,

- 114, 6250.
24. Y. N. Tang, Z. X. Yang and X. Q. Dai, *Phys. Chem. Chem. Phys.*, 2012, **14**, 16566.
 25. J. X. Zhao, Y. Chen and H. G. Fu, *Theor. Chem. Acc.*, 2012, **131**, 1.
 26. Q. G. Jiang, Z. M. Ao and Q. Jiang, *Phys. Chem. Chem. Phys.*, 2013, **15**, 10859.
 27. B. Delley, *J. Chem. Phys.*, 2000, **113**, 7756.
 28. J. P. Perdew, K. Burke and M. Ernzerhof, *Phys. Rev. Lett.*, 1996, **77**, 3865.
 29. A. Roldán, J. M. Ricart and F. Illas, *Theor. Chem. Acc.*, 2009, **123**, 119.
 30. T. A. Halgren and W. N. Lipscomb, *Chem. Phys. Lett.*, 1977, **49**, 225.
 31. G. Henkelman and H. Jonsson, *J. Chem. Phys.*, 2000, **113**, 9978.
 32. S. Grimme, *J. Comput. Chem.*, 2006, **27**, 1787.
 33. M. D. Segall, P. L. D. Lindan, M. J. Probert, C. J. Pickard, P. J. Hasnip, S. J. Clark and M. C. Payne, *J. Phys.: Condens. Matter*, 2002, **14**, 2717.
 34. J. Y. Dai, J. M. Yuan and P. Giannozzi, *Appl. Phys. Lett.*, 2009, **95**, 232105.
 35. J. Y. Dai and J. M. Yuan, *Phys. Rev. B*, 2010, **81**, 165414.
 36. P. A. Denis, *Chem. Phys. Lett.*, 2010, **492**, 251.
 37. Z. M. Ao and F. M. Peeters, *Phys. Rev. B*, 2010, **81**, 205406.
 38. D. C. Young, *Computational Chemistry: A Practical Guide for Applying Techniques to Real World Problems*; Wiley: New York, 2001.
 39. http://www.knowledgedoor.com/2/elements_handbook/cohesive_energy.html.
 40. O. Leenaerts, B. Partoens and F. M. Peeters, *Phys. Rev. B*, 2008, **77**, 125416.
 41. K. Honkala and K. Laasonen, *Phys. Rev. Lett.*, 2000, **84**, 705.
 42. L. M. Molina and B. Hammer, *J. Catal.*, 2005, **233**, 399.
 43. W. An, Y. Pei and X. C. Zeng, *Nano Lett.*, 2008, **8**, 195.

Table 1. The adsorption energy E_{ad} , the distance between the adsorbate and Al-embedded graphene h , bond length of adsorbate l , and Hirshfeld charge transfer Q from the graphene substrate to the adsorbate of the most stable configurations for CO and O₂ molecules on Al-embedded graphene. The bond length l of the free CO and O₂ molecules are also shown in the table.

	E_{ad} (eV)	h (Å)	l (Å)	Q (e)
Free CO	—	—	1.14	—
Adsorbed CO	-0.83	2.06	1.15	0.15
Free O ₂	—	—	1.23	—
Adsorbed O ₂	-1.57	1.86	1.43	-0.31

Captions

Fig. 1. (Color online) (a) The pathway of the embedded Al atom diffusion on graphene, where IS, TS and FS represent initial structure, transition structure and final structure, respectively. The grey and pink atoms are C and Al in this and following Fig.s. The atomic charge obtained by Hirshfeld analysis near the dopant is also given. (b) PDOS of Al atom and C atom on the Al-embedded graphene. The vertical lines indicate the Fermi level.

Fig. 2. (Color online) (a) The most stable structure of CO adsorbed on Al-embedded graphene. (b) PDOS and orbitals of the CO molecule, where the number of electrons for each orbital is also shown by arrows. (c) PDOS of CO molecule and the Al atom for the Al-embedded graphene with adsorbed CO. (d) Charge density of 4σ , 1π , 5σ and $2\pi^*$ orbitals of CO molecule on Al-embedded graphene. The vertical lines indicate the Fermi level.

Fig. 3. (Color online) (a) The reaction pathway for the dissociative adsorption of O_2 molecule on Al-embedded graphene. (b) PDOS and orbitals of the O_2 molecule, where the number of electrons for each orbital is also shown by arrows. (c) PDOS of O_2 molecule and Al atom for the Al-embedded graphene with adsorbed O_2 . (d) Charge density of 4σ , 5σ , 1π and $2\pi^*$ orbitals of O_2 molecule on Al-embedded graphene. The vertical lines indicate the Fermi level.

Fig. 4. (Color online) (a) The primary reaction step for the oxidation of CO molecule on Al-embedded graphene for ER mechanism. (b) The reaction pathway for the adsorption of CO molecule on Al-embedded graphene with pre-adsorbed O_2 molecule.

Fig. 5. (Color online) The reaction pathway of CO oxidation on Al-embedded graphene for LH mechanism: step1 (a), step2 (b) and step3 (c). The energy profile for

the formation of the first CO₂ molecule is shown in (d). The unit of E is eV, where E is the energy barrier. The Hirshfeld charge near the adsorbate is also shown.

Fig. 6. (Color online) PDOS of adsorbed CO, O₂ and Al atom for the IS (a), TS (b), MS(c) and TS2 (d). Black, red and pink curves represent PDOS of adsorbed CO, O₂ and Al atom, respectively. The orbitals of the adsorbed CO and O₂ molecules are roughly labelled. The vertical lines indicate the Fermi level.

Fig. 1.

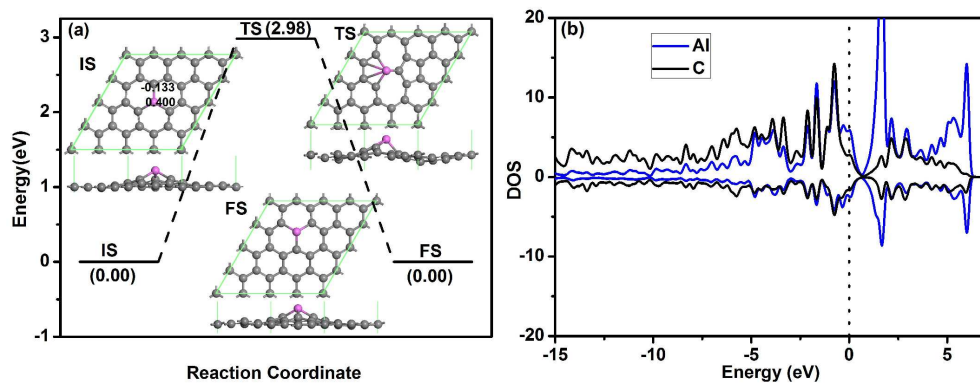


Fig. 2.

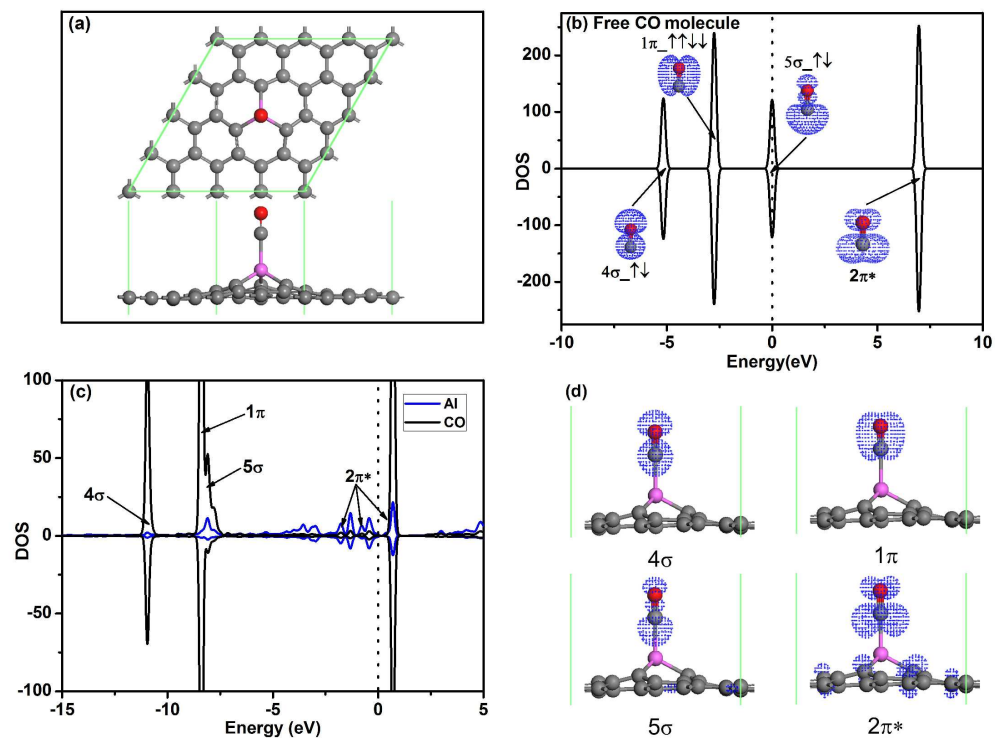


Fig. 3.

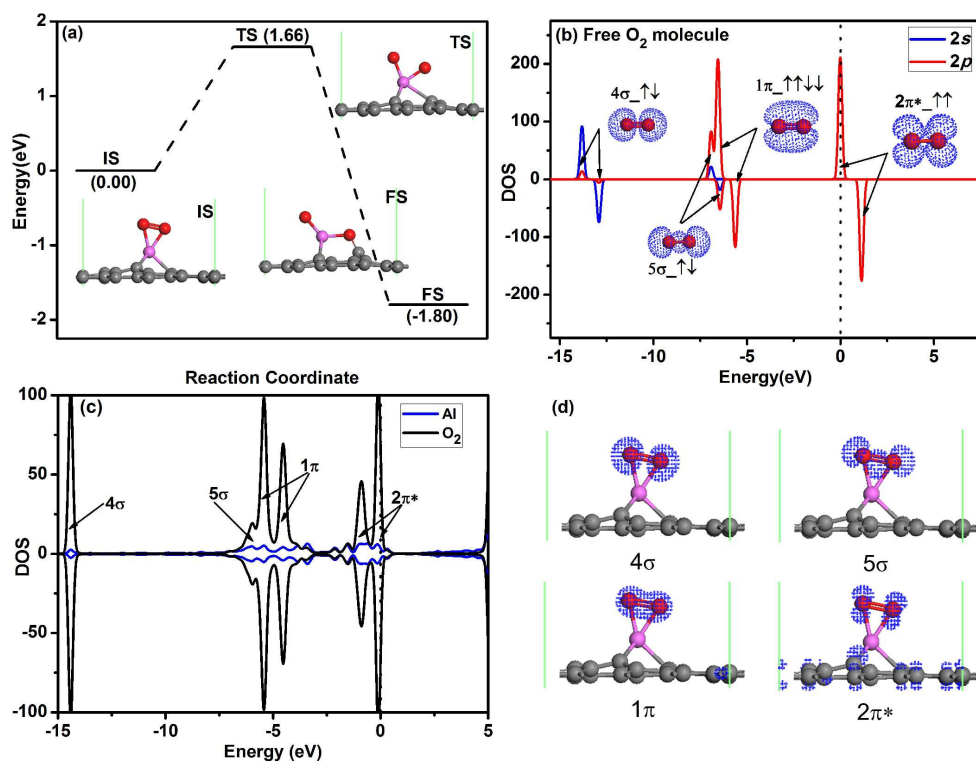


Fig. 4.

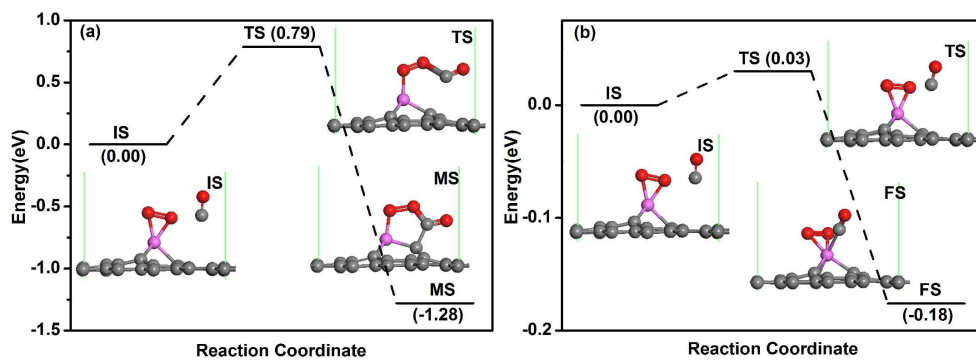


Fig. 5.

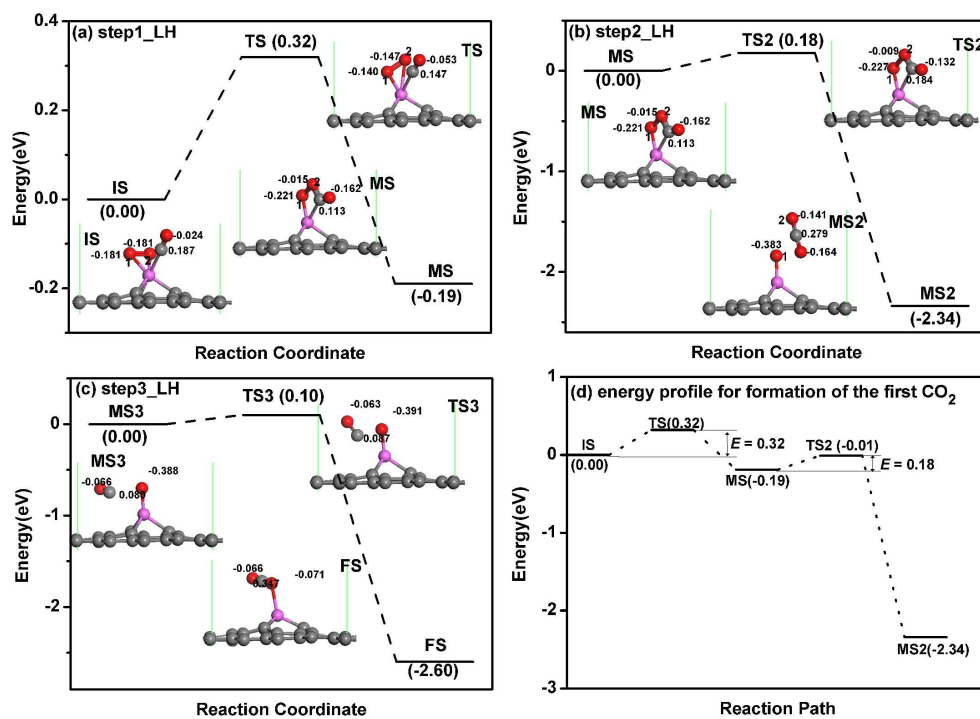


Fig. 6.

