

RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

COMMUNICATION

Formation of superconducting yttrium barium copper oxide using sulphur-containing templates†

Cite this: DOI: 10.1039/x0xx00000x

R. Boston,^{a, b} K. Awaya,^c T. Nakayama,^c W. Ogasawara^c and S. R Hall^{*a}Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

The formation of yttrium barium copper oxide (YBCO) via biotemplated routes is often plagued by unwanted stable intermediates, some of which arise from the template itself. Here we describe a method which allows sulphur-containing templates, such as proteins, to form YBCO which would have hitherto resulted in non-superconducting sulphated phases.

The rise of biotemplated syntheses for the creation of complex metal oxides has opened up a new field in oxide development and discovery. Biotemplates are natural polymers found in many forms including long chain polysaccharides, proteins and more complex structures such as DNA or viruses. The templating behaviour generally arises from the presence of suitable chelation sites which can uptake metal cations from solution, sequestering them for use in the creation of the final product. There are a large number of inorganic materials which can be made in this way and in general, providing suitable precursors and heating protocols can be found, the desired product can be synthesised. Biotemplated methods work extremely well for complex metal oxides, with many classes of ternary and quaternary functional oxides successfully synthesized, for example piezoelectrics,^{1,2} electrode materials³ and ferroelectrics⁴. While solid state routes also work very well for these types of materials, they tend to involve lengthy processing times, which make them impractical and expensive. The main advantage of biopolymer-mediated synthesis is the significantly shorter synthesis times required to produce such materials, and the additional levels of morphological control offered.

The high temperature superconductor (HTSC) yttrium barium copper oxide (YBCO) has been synthesized using biopolymers, with numerous novel morphologies developed purely as a result of the biopolymers used either through sacrificial templating methods,⁵ or through nanoscale crystal growth.⁶ There are a large number of templates which have been successfully employed to synthesise YBCO, including dextran,⁷ sodium alginate,⁸ and chitosan.⁹ The solid state techniques to create YBCO are plagued by the formation of recalcitrant phases, which are responsible for the long calcination times. In addition, the phase produced is generally poorly oxygenated, requiring additional annealing stages to create a good oxygen stoichiometry for superconducting properties. For YBa₂Cu₃O_{7- δ} (Y123), a value of $\delta \approx 0.1$ gives the highest transition temperature.¹⁰ Biotemplated methods generally give phase pure YBCO, and do not require an oxygen atmosphere or annealing step,^{5,7,11} and as such, represent a large improvement in both time and purity over the solid state methods.

Of all of these successful syntheses, however, there is one notable exception; the use of sulphur-containing templates such as κ -carrageenan. Previous work in this area concluded that the formation of YBCO was not possible due to the formation of highly stable barium sulphate (m.p. 1345 °C) during the early part of the calcination process.^{12,13} Theoretically, around half of the barium reacted with the sulphur groups in the κ -carrageenan, leading to a significant reduction in the amount of barium carbonate which is responsible for initiating Y123 phase formation. This suppression of BaCO₃ leads to the formation of other stable intermediates such as the non-superconducting “green phase” Y₂BaCuO₅ (Y211), Y₂Cu₂O₅, CuO and other barium deficient phases. As a result, it was concluded that sulphur-containing templates were not suitable for use with YBCO, effectively discounting many proteins (the amino acid cysteine contains a disulphide bridge) from being used for YBCO and other barium-containing complex oxides.

Megabalanus rosa cement protein (MRCP), produced by the *Megabalanus rosa*, or acorn barnacle, is one of a group of a relatively newly-isolated proteins, which are used by barnacles to adhere to rocks. Barnacles are well known for their ability to remain

^a School of Chemistry, Cantock's Close, University of Bristol, Bristol, BS8 1TS, UK.

^b Bristol Centre for Functional Nanomaterials, Centre for Nanoscience and Quantum Information, Tyndall Avenue, University of Bristol, Bristol, BS8 1FD, UK.

^c Nagaoka University of Technology, 1603 1 Kamitomioka, Nagaoka, Niigata 940 2188, Japan

† Electronic Supplementary Information (ESI) available: See DOI: 10.1039/c000000x/

securely attached to rocks and other surfaces in the ocean, and being commonly found around the coastal regions, they must be able to withstand the force of breaking waves and tides in order to survive. The crystal structure of the protein is not yet known, however the composition has been found using reverse HPLC and cloning¹⁴, and consists of a cysteine-rich, charged molecule, made up of 202 amino acids, the first 19 of which are thought to be used as a signal sequence, in the replication of the protein by the barnacle. The Cys residues are thought to be of great importance in maintaining exposed charged surfaces, which are reported to provide the interaction between barnacle and rock. These Cys residues could in theory provide as chelation sites for introduced metal cations, although as above, the sulphur content would appear to preclude the use of MRCP and other cysteine-rich proteins in the synthesis of barium-containing materials.¹³ Here we report the first successful synthesis of Y123 using sulphated templates (κ -carrageenan and MRCP) illustrating that sulphur-containing templates can be successfully employed for the synthesis of Y123 without the formation of BaSO₄ impurity phases. The use of a protein template may also offer the opportunity to create chosen crystal morphologies designed from the bottom up, through prodigious placement of particular chelating residues within the template molecule.

Stoichiometric quantities of yttrium, barium and copper nitrates (all Sigma Aldrich, UK) were dissolved in de-ionised water to form a solution with a 0.05: 0.1: 0.15 M ratio. Aliquots were then vigorously mixed with the chosen template (MRCP, or κ -carrageenan) and allowed to dry at 60 °C for 24 hours. Different ratios of template-to-precursor were used in order to investigate the formation of sulphated phases. Samples containing κ -carrageenan were prepared using template-to-precursor ratios of 10 g: 2 ml (which will be referred to as high ratio samples), as described previously,¹³ and 5 mg: 2 ml (low ratio samples). The samples prepared using MRCP used the low ratio, and the control sample was prepared as a 2 ml sample of precursor containing no templating agent. The dried films were then calcined in air at 920 °C for 2 h with a ramp rate of 10 °C/min. The resulting black powders were then analysed using powder X-ray diffraction (PXRD) (D8 Advance, Bruker, Germany), scanning electron microscopy (SEM) (JSM 6330F, JEOL, Japan) and high resolution transmission electron microscopy (HRTEM), including selected area electron diffraction (JEM 2010, JEOL, Japan). Elemental content was determined using energy dispersive X-ray analysis (EDXA) (Oxford Cryosystems, UK) fitted to the HRTEM and SEM. Magnetometry was performed using a superconducting interference device (SQUID) (Magnetic Property Measurement System Quantum Design, USA). Samples measured were powdered and placed inside a gelatine capsule.

As-prepared samples were examined using PXRD in order to determine the crystallochemical composition of the materials, as shown in Figure 1. In addition, selected area electron diffraction and EDXA were also performed in order to identify each phase within the sample directly. As has been shown previously,¹³ the sample containing a high ratio of κ -carrageenan-to-precursor (Figure 1a) produced almost no Y123 phase, with BaSO₄ (JCPDS card 01-076-0231) being the most prominent phase (Supplementary Information Figure S1a-c). BaSO₄ forms between 300 °C and 400 °C, (see Supplementary Information Figure S2) and due to its high melting point (1345 °C), remains solid in the reaction mixture at the final calcination temperature (920 °C), thus making the majority of the barium ions unavailable for the formation of Y123. In addition to this, yttrium- and copper-rich phases such as Y211 (JCPDS card 01-078-2214, Supporting Information Figure S1d-f), copper oxide (JCPDS card 01-074-1021, Supporting Information Figure S1g-i) and Y₂O₂S (JCPDS card 024-1421) were formed instead of the desired Y123 product, due to the unavailability of barium within the

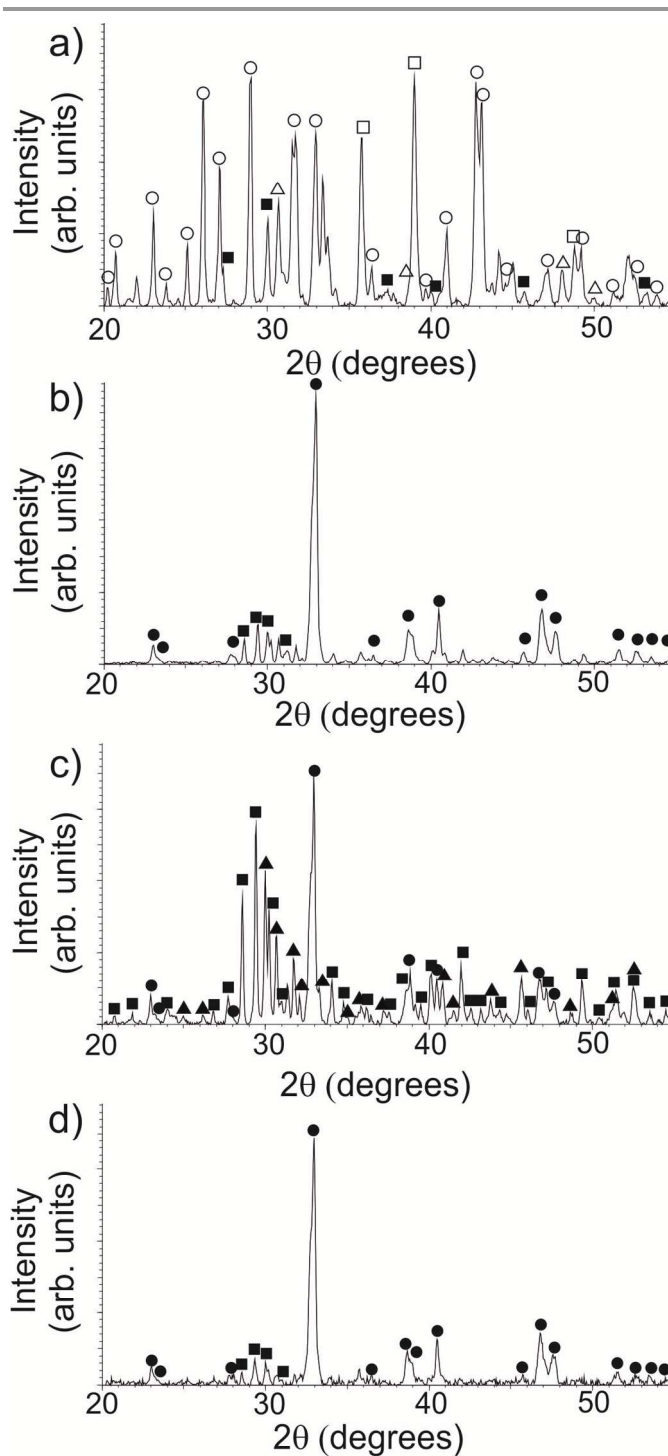


Figure 1. PXRD of the different samples: a) high-ratio κ -carrageenan; b) low-ratio κ -carrageenan; c) control sample containing no template; and d) MRCP-templated sample. Phases are marked as Y123 (●), BaCuO₂ (■), BaSO₄ (○), Y₂O₂S (Δ), CuO (□), and Y211 (▲).

system. We then reduced the mass of κ -carrageenan used, until arriving at a biopolymer:inorganic ratio where only a very low concentration of the barium ions are used in BaSO₄ formation, and as such the desired Y123 product was able to form (JCPDS card 01-079-0318, Supporting Information Figure S3). This can be observed as a marked difference between the PXRD patterns for the low-ratio templated sample (Figure 1b) and the high-ratio sample (Figure 1a).

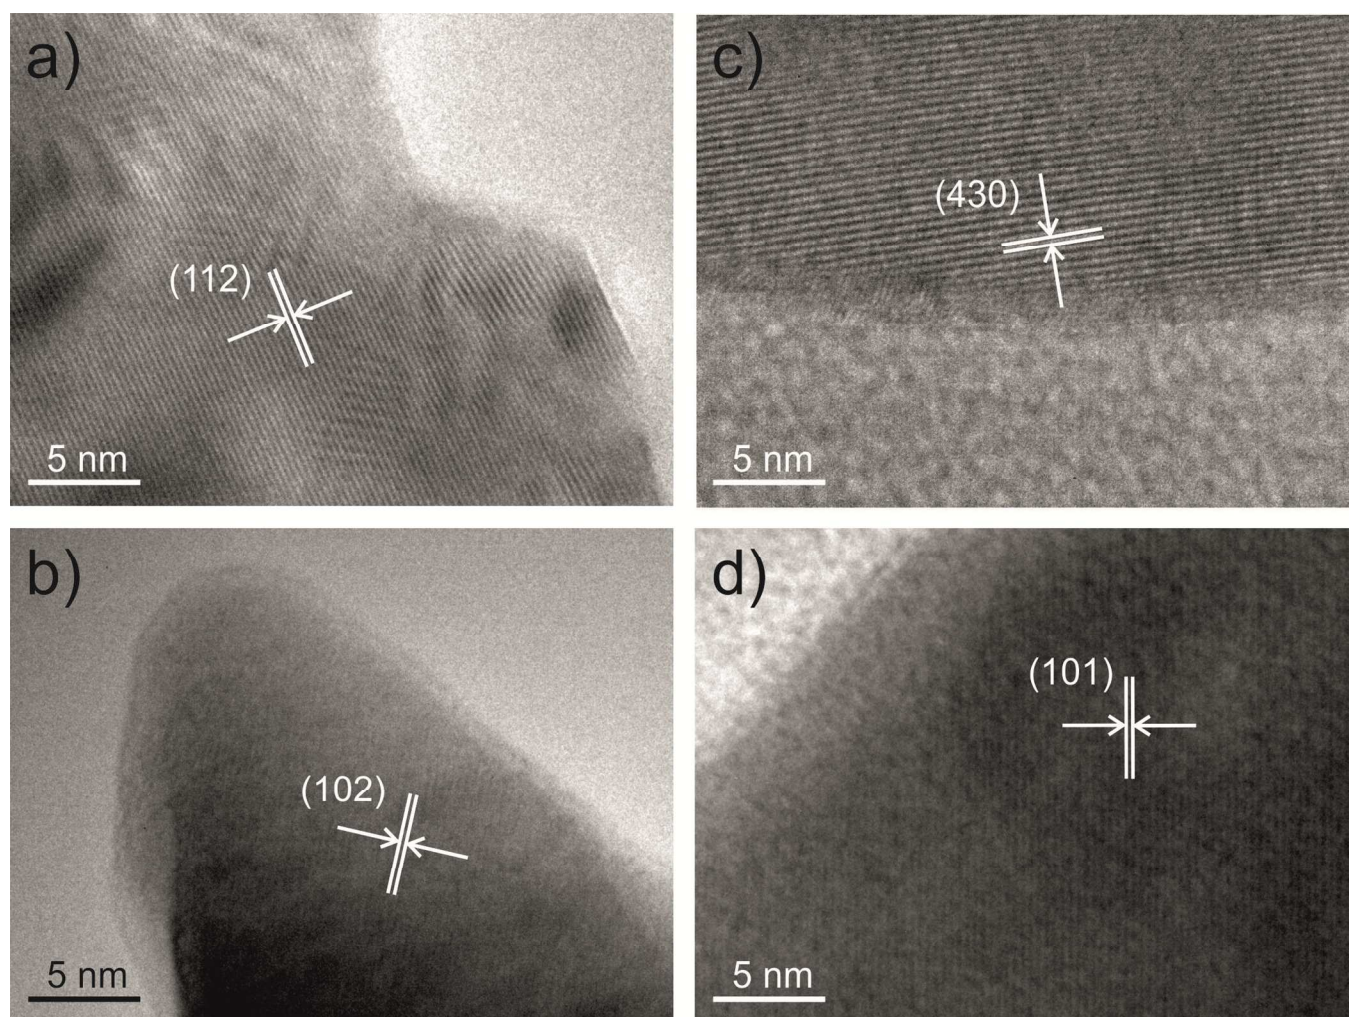


Figure 2. TEM micrographs of the major phase in each sample. a) the high-ratio sample with BaSO₄ lattice planes highlighted; b) the low-ratio sample with Y123 lattice planes highlighted; c) the control sample with BaCuO₂ lattice planes highlighted; and d) the MRCP-templated sample with Y123 lattice planes highlighted.

A control sample was also prepared using the same concentration of precursor ions but no template. Three major phases were observed: BaCuO₂ (JCPDS card 01-070-0441, Supporting Information Figure S4a-c), the non-superconducting Y211 (Supporting Information Figure S4d-f), and Y123 (Supporting Information Figure S4g-i). By introducing a low ratio of templating material, the formation of the Y123 phase is favoured over these intermediates suggesting that the chelating ability of the template is providing enough spatial separation of ions to reduce the likelihood of the formation of large-scale intermediate crystallites, as was observed in the control sample.

The phases of the different materials present were also confirmed using HRTEM and selected area electron diffraction. Figure 2 shows HRTEM micrographs of the major phase in each sample with lattice planes indicated corresponding to each material: BaSO₄ in the high ratio sample (Figure 2a), Y123 in the low-ratio sample (Figure 2b), BaCuO₂ in the control sample (Figure 2c) and Y123 in the sample templated using MRCP (Figure 2d).

The samples were examined using SEM in order to investigate crystallite morphology. The samples prepared with high ratios of κ-carrageenan resulted in a reticulated, blocky morphology, as observed previously¹³ (Figure 3a). Samples synthesised using a low ratio of κ-carrageenan also show this reticulated morphology (Figure

3b), indicating that the templating effect is effective at directing the crystallite growth in the same way as a sample synthesized using a high ratio of template-to-precursor. The morphological similarities between the samples prepared using high and low ratios of template-to-precursor suggests that the template is having the same effect on crystal morphology in both cases regardless of the phase forming. Conversely the control sample is crystallographically and compositionally inhomogeneous (Figure 3c). This is also evident in comparison between the particle sizes, which show that Y123 templated with both ratios of template produce crystallites with similar average sizes, as shown in Figure 4. Samples templated using both high and low ratios gave particles with an average largest dimension of $0.91 \pm 0.9 \mu\text{m}$ and $0.74 \pm 0.4 \mu\text{m}$ respectively, as opposed to the control sample which showed a smaller average size of $0.21 \pm 0.1 \mu\text{m}$. The inhomogeneous phase observed in the high-ratio κ-carrageenan templated samples and the control is indicative of the effect which the template is having on the morphology of the final product. The MRCP-templated sample has a similar particle size to the κ-carrageenan samples, which indicates that the protein is having a templating effect on the morphology of the product. The observation that a sulphur-containing polysaccharide can provide a templating effect at low ratios allows us to use a cysteine-rich

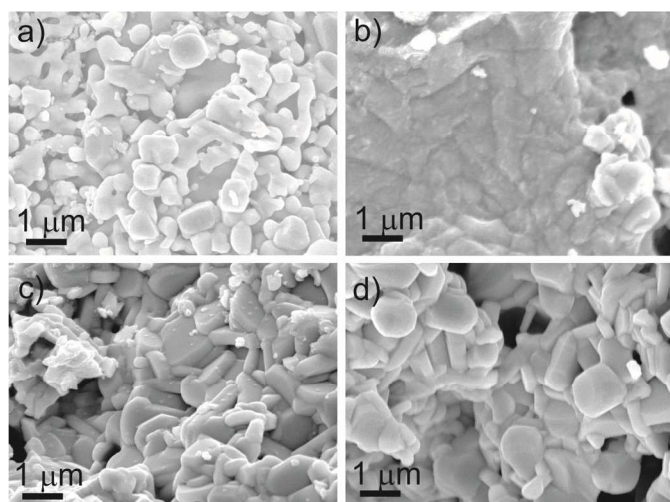


Figure 3. SEM micrographs showing the morphologies found using different templates. a) High ratio κ -carrageenan sample with similar reticulated blocky structure to b) low-ratio of κ -carrageenan sample. c) Crystallographically and morphologically inhomogeneous control sample. d) The sample templated using MRCP with similar structure to the κ -carrageenan samples.

protein as a biotemplate for the first time. MRCP was used to create Y123 without the formation of significant or detrimental quantities of impurity phases. The PXRD pattern (Figure 1d) indicates that the majority phase is Y123 (Supplementary Information Figure S5), similar to the low-ratio κ -carrageenan samples. Figure 2d shows a HRTEM image illustrating Y123 lattice planes.

The morphological structure of the crystallites was found to be reticulated and blocky, indicating a similar structure-directing effect on the Y123 phase (Figure 3d), as was observed in the low ratio κ -carrageenan. The average particle size for MRCP-templated YBCO was found to be $0.73 \pm 0.3 \mu\text{m}$, similar to the κ -carrageenan samples, and indicates that the template is having an effect on the size of crystallites formed.

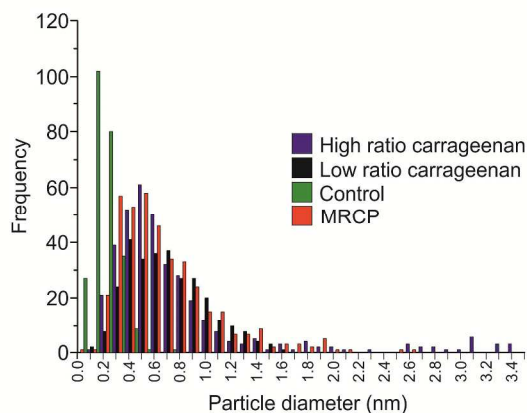


Figure 4. Histogram plots of crystallite size, measured using the longest dimension of the crystallites

SQUID magnetometry was performed on all samples in order to determine the superconducting transition temperature and volume susceptibility (Figure 5). All of the transitions are broad due to the samples being powdered and highly polycrystalline. The transition

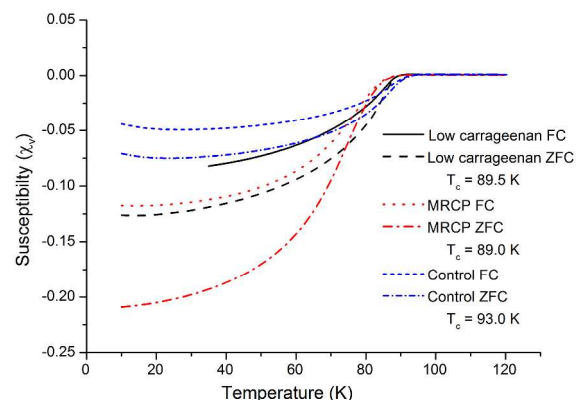


Figure 5. SQUID magnetometry of the control sample, and samples prepared using low ratios of κ -carrageenan and MRCP.

temperatures of the samples varied slightly, with the control sample giving the highest T_c of 93 K, followed by the low ratio κ -carrageenan-templated sample with a T_c of 89.5 K, and the MRCP-templated sample showing a transition at 89 K. Although the T_c of the MRCP sample is the lowest, under zero-field cooling the volume susceptibility, χ_v , was found to be the most negative, indicating, to a first approximation, that 21.0 % of the sample was in the superconducting state below the transition temperature. This is comparable to other Y123 samples synthesised using biotemplates,^{5,7} and also shows a significantly higher percentage than the low ratio κ -carrageenan-templated sample, of which approximately 12.5 % is superconducting. The lowest volume fraction was in the control sample, showing around 7.5 % of the material as superconducting phase, something which would be expected from the PXRD data which indicated a large number of impurity phases. This last result shows the general efficacy of biotemplates in the improved synthesis of YBCO.

In conclusion we have presented the first biotemplating of Y123 using sulphur-containing templates, including κ -carrageenan, which has previously been shown to be unsuitable for use in the synthesis of materials containing barium, due to the formation of barium sulphate. This synthesis method now allows for all the previously unusable sulphur-rich proteins to be considered as templates, and we have shown that they can be used to direct crystal size in the same way as has been observed in glucose-based templates. We have shown that this method is successful using the protein MRCP, which showed an increase in χ_v over similar κ -carrageenan-prepared samples. Proteins, therefore, provide a new source of templates for complex materials containing barium, and similar metals, and through bottom-up design of chelation sites, may provide a means of creating previously inaccessible morphologies in complex materials

Acknowledgements

We acknowledge the Electron and Scanning Probe Microscopy Facility at the University of Bristol for the use of SEMs and TEMs. RB and SRH acknowledge the Engineering and Physical Sciences Research Council (EPSRC), UK (grant EP/G036780/1), and the Bristol Centre for Functional Nanomaterials for project

funding, and Kei Kamino and Yosuke Shida for providing and purifying the MRCP.

References

- 1 K. Cung, B. J. Han, T. D. Nguyen, S. Mao, Y-W. Yeh, S. Xu, R. R. Naik, G. Poirier, N. Yao, P. K. Purohit and M. C. McAlpine, *Nano Lett.*, 2013, 13, 6197.
- 2 Z. Schnepp, J. Mitchells, S. Mann and S. R. Hall, *Chem. Commun.*, 2010, 46, 4887.
- 3 Y. Xia, W. Zhang, Z. Xiao, H. Huang, H. Zeng, X. Chen, F. Chen, Y. Gan and X. Tao, *J. Mater. Chem.*, 2012, 22, 9209.
- 4 B. Li, J. Zhou, R. Zong, M. Fu, Y. Bai, L. Li and Q. Li, *J. Am. Ceram. Soc.*, 2006, 89, 2298.
- 5 R. Boston, A. Carrington, D. Walsh and S. R. Hall, *CrystEngComm*, 2013, 15, 3763.
- 6 Z. Schnepp, S. C. Wimbush, S. Mann and S. R. Hall, *Adv. Mater.*, 2008, 20, 1782.
- 7 D. Walsh, S. C. Wimbush and S. R. Hall, *Chem. Mater.*, 2007, 19, 647.
- 8 Z. Schnepp, S. C. Wimbush, S. Mann and S. R. Hall, *CrystEngComm*, 2010, 12, 1410.
- 9 S. R. Hall, *Adv. Mater.*, 2006, 18, 487.
- 10 R. Liang, D. A. Bonn and W. N. Hardy, *Phys. Rev. B*, 2006, 73, 180505.
- 11 Z. Zhang, S. C. Wimbush, A. Kursumovic, H. Wang, J. H. Lee, H. Suo and J. L. MacManus-Driscoll, *CrystEngComm*, 2012, 14, 5765.
- 12 S. R. Hall, C. F. Hall, K. Hansberry, S. C. Wimbush, Y. Shida and W. Ogasawara, *Super. Sci. Tech.*, 2012, 25, 035009.
- 13 E. Smith, Z. Schnepp, S. C. Wimbush and S. R. Hall, *Physica C*, 2008, 468, 2283.
- 14 K. Kamino, *Biochem. J.*, 2001, 356, 503.

The formation of yttrium barium copper oxide (YBCO) via biotemplated routes is often plagued by unwanted stable intermediates, some of which arise from the template itself. Here we describe a method which allows sulphur-containing templates, such as proteins, to form superconducting YBCO which would have hitherto resulted in non-superconducting sulphated phases.



Protein from the acorn barnacle used to template high temperature superconductors
60x39mm (300 x 300 DPI)