

RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

ARTICLE

Water-Soluble Non-Polymeric Electrospun Cyclodextrin Nanofiber Template for the Synthesis of Metal Oxide Tubes by Atomic Layer Deposition

Cite this: DOI: 10.1039/x0xx00000x

Asli Celebioglu^{ab}, Sessa Vempati^{*a}, Cagla Ozgit-Akgun^{ab}, Necmi Biyikli^{ab} and Tamer Uyar^{*ab}

Received 00th January 2012,

Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

We report on the suitability of water-soluble non-polymeric electrospun cyclodextrin (CD) nanofiber template by using atomic layer deposition (ALD) to yield metal oxide tubes. To demonstrate this, water-soluble electrospun CD nanofibers were chosen as template to produce metal oxide tubes where we have tested two examples of ALD coatings, namely, Al₂O₃ and ZnO. After the ALD coating on CD nanofibers, simply the CD core is dissolved in water to yield metal oxide tubes. Morphological investigations suggested that Al₂O₃ is smoother in contrast to ZnO which has shown grainy structure. Structural characterization evidenced amorphous Al₂O₃ and highly crystalline ZnO. By given the applicability of Al₂O₃ and ZnO in various contexts the ionic states of Al, Zn and O are also investigated. After the washing step to remove CD core, Al₂O₃ developed some hydroxylation, while ZnO hosts various oxygen related functional groups.

Introduction

Nanostructures produced while combining industrially applicable techniques such as electrospinning and atomic layer deposition (ALD) are quite attractive as perused by various researchers for potential applications.¹⁻¹⁰ In fact ALD can yield coral,⁶ core-shell,^{4,5,11} hollow^{6,7,9} like complex nanostructures. Although various polymers are the subjects of electrospinning, the compatibility between the polymer and the ALD precursor is vital.² The foremost condition is the thermal stability of the polymer as ALD generally takes places at slightly elevated temperatures. The other factor is the chemical compatibility, see the ALD of Al₂O₃ on nylon-6 polymer,² ALD of ZnO on poly(propylene) fibers with Al₂O₃ base layer to inhibit the diffusion of diethylzinc (DEZn) into the polymer.¹ Despite of these limitations fibers of various polymers are explored by our group^{3,4,12} and other researchers in ALD.^{1,2,6,7,9,10} *Viz.* poly(propylene)/Al₂O₃/ZnO,¹ poly(acrylonitrile)/ZnO,^{3,10} polysulfone/ZnO,⁴ nylon 6,6/ZnO,¹² nylon-6/ZnO/Al₂O₃,² poly(vinyl alcohol) (PVA)/Al₂O₃,^{6,7} polyvinyl acetate/ZnO.⁹ Although electrospun polymeric nanofibers/ALD is established in the literature, the same combination with non-polymeric nanofibers is certainly novel and potential. In the context of electrospinning of non-polymeric systems, cyclodextrin (CD)¹³⁻¹⁶ are quite interesting apart from others.^{17,18} Hydrogen-bond-mediated aggregates of CD molecules help the electrospinning process where the aggregation is analogous to the polymeric chain entanglement. These CD aggregates are big enough to mimic the entanglement so that a continuous non-woven nanofibrous mat can be obtained.¹³⁻¹⁶ Hence

in this study we demonstrate the potential compatibility of CD nanofibers in ALD process while exploiting its fascinating properties. For instance, the intrinsic nature of CD helps in sustaining the fiber structure until ~150 °C, a typical temperature for an ALD process. This is in contrast to water-soluble polymers such as PEO which has melting point of ~65 °C or PVA with a glass transition temperature less than 100 °C. Hence the present combination is quite potential to produce metal oxide tubes for various applications, especially sensors.^{9,10} Basically, after the ALD process the core-shell fiber structure is either subjected to calcination^{9,7} or dissolution⁶ to remove the core-polymer yielding tube structure. Dissolution of the 'core' is quite interesting and energy efficient in contrast to the calcination, while on the other hand the latter strongly manipulates the crystalline property of the shell material. Hence it is always encouraging to increase the applicability of water processible materials by ever increasing environmental and cost related issues (green chemistry). Particularly, CD are non toxic materials and hence their release into the environment (after the washing step) does not cause any loading. When compared to the polymeric systems, the CD nanofibers have relatively higher and rapid solubility with small molecular size which enables a better removal from core-shell structure. Furthermore, prolonged exposure of metal oxide surfaces to solvents can influence the surface chemical characteristics. We do acknowledge that water-soluble polymers such as PVA⁶ fiber template has been used to obtain Al₂O₃ tubes via ALD process however, not many other reports are seen. This study is significant in terms of employing a non-polymeric template as well as

demonstrating the compatibility with ALD process to produce metal oxide tubes.

In this report we adopted this combination to produce core-shell structured cyclodextrin-metal oxide fibers and subsequently they were subjected to washing which removes the cyclodextrin core. Among various nanostructures, tubes have attracted a lot of attention due to their potential applicability. We have used methyl- β -cyclodextrin (M β CD) and hydroxypropyl- β -cyclodextrin (HP β CD) for the electrospinning since they have a very high solubility when compared to native β -CD. We use these electrospun CD nanofibers as templates to obtain Al₂O₃ and ZnO tubes by ALD coating where the core-shell structure is subjected to a simple dissolution of CD core.

Experimental

Materials

HP β CD (molar substitution \sim 0.6) and M β CD (molar substitution 1.6-1.9) were purchased from Wacker Chemie AG, Germany. N,N-dimethylformamide (DMF) was purchased from Riedel, Pestenal. Trimethylaluminum (TMAI) and DEZn were procured from Sigma Aldrich and HPLC-grade deionized water were used for the ALD process. All the materials were used without any purification.

Fabrication of metal oxide tubes

The process of obtaining metal oxide tubes consists of three steps. Initially CD nanofibers are produced (Step 1, electrospinning), followed by the deposition of metal oxide (Step 2, ALD process). Finally in Step 3, the core-shell nanofibers are subjected to washing, which removes the CD 'core'. Crucial points related to Step 1, 2 and 3 are discussed in the context of Figure 1.

Step 1: Clear and homogenous solutions of M β CD and HP β CD were prepared at 160% (w/v) and 120% (w/v) in DMF, respectively. Each of these solutions was taken in a syringe and a metallic needle of 0.45 mm inner diameter is attached as a tip. The syringe was placed horizontally on a syringe pump (SP 101IZ, WPI). A high voltage (Matsusada Precision, AU Series) terminal was connected to the tip while the counter electrode covered with an Al foil (substrate) was grounded. The electrospinning of the CD solutions was performed with the following parameters: applied voltage \sim 15 kV, tip-to-collector distance 10-15 cm and the solution flow rate was kept at 0.5 mL/h. The electrospinning apparatus was enclosed in a box at 25 °C and 30% relative humidity. These electrospun nanofibers of HP β CD or M β CD are used as substrates for subsequent deposition of Al₂O₃ or ZnO.

Step 2: In this step electrospun CD nanofibers were coated either with Al₂O₃ or ZnO at 80 °C in a Savannah S100 ALD reactor (Cambridge Nanotech Inc.) with N₂ as a carrier gas. Depositions were performed with exposure mode (a trademark of Ultratech/Cambridge Nanotech Inc.) in which dynamic vacuum is switched to static vacuum just before each precursor pulse by closing the valve between the reaction chamber and the pump. This allows the substrate to be exposed to precursor molecules for a certain

period of time (i.e., exposure time). This is followed by a purging period, where the chamber is switched back to dynamic vacuum for efficient evacuation/purging of excess precursor molecules and gaseous byproducts. 200 cycles Al₂O₃ or 400 cycles ZnO were deposited, where one ALD cycle consists of the following steps. Valve OFF/N₂ flow set to 10 sccm/TMAI or DEZn pulse (0.015 s)/exposure (60 s)/valve ON/N₂ flow set to 20 sccm/N₂ purge (60 s)/valve OFF/N₂ flow set to 10 sccm/H₂O pulse (0.015 s)/exposure (60 s)/valve ON/N₂ flow set to 20 sccm/N₂ purge (60 s).

Step 3: At this stage, we remove the CD core by washing the Al₂O₃ or ZnO coated core-shell nanofibers in water for 45 min with occasional manual shaking. These core-shell and tube structures were subjected to thorough characterization. For easy reference of various samples the following abbreviations are used in this report. 200 cycles of Al₂O₃ on M β CD nanofibers is referred as AM2, while 400 cycles of ZnO on HP β CD nanofibers is referred as ZH4. Samples subjected to washing are abbreviated as AM2_W or ZH4_W. Other samples follow similar nomenclature.

Characterization

A scanning electron microscope (SEM, FEI-Quanta 200 FEG) was employed to investigate the morphology and dimensions of the samples before and after the washing step. Nominal 5 nm Au/Pd was sputtered on the samples prior to the observation under SEM. Average fiber diameter (AFD) was estimated from SEM images with samplings well above the statistically acceptable limit. Metal oxide tubes were subjected to transmission electron microscopy (TEM, FEI-Tecnaï G2 F30) measurements where the sample was dispersed in ethanol and a tiny droplet was analyzed from a holey carbon coated TEM grid. X-ray diffraction (XRD) patterns were recorded in the range of $2\theta = 10-90^\circ$ using PANalytical X'Pert Pro Multi Purpose X-ray diffractometer with Cu K α radiation ($\lambda = 1.5418 \text{ \AA}$). The ionic states of the constituent elements at the surface of the samples (400 μm spot size) were investigated by X-ray photoelectron spectroscopy (XPS, ThermoScientific K-Alpha, Al K α radiation with $h\nu = 1486.6 \text{ eV}$) with a flood gun charge neutralizer. For the core-level spectra, the pass energy and step size were set to 30 eV and 0.1 eV, respectively. Valence band (VB) spectra were also recorded with a pass energy of 30 eV in energy steps of 0.2 eV. Spectral deconvolutions of the XPS data were performed through Advantage software while considering the chemistry of the sample. Origin 8.5 has been employed to deconvolute the XRD peaks with Lorentzian function. In the case of XRD, number of peaks and their angular location were the initial values while other parameters are set as free until convergence.

Results and discussion

As outlined in the introduction, electrospinning is a quite potential technique to produce polymeric and non-polymeric nanofibers (Figure 1, Step 1). When a polymer is subjected to electrospinning, the overlap and entanglement of the polymeric chains is essential for the electrospinning process. Analogous to this, CD molecules form 'aggregates' which fulfil the essential criteria of electrospinning process. These aggregates are accelerated in the electric field and

rapidly solidify while reaching the substrate in the form of nanofibers.¹³

Basically in an ALD process gaseous precursors are injected with a carrier gas into a chamber (containing the substrate) at a predetermined flow rate in a sequential manner. Precursor molecules are first adsorbed on the surface and then eventually chemisorbed by the reactive surface sites, forming a monomolecular layer of that precursor. In the case of Al_2O_3 , $-\text{CH}_3$ ligands in the TMAI interact with the surface as shown in Figure 1, Step 2 (top). Note that we did not show the O bridge bonds. The remnant methyl groups of TMAI react with the next pulse of H_2O . The sequence of reaction mechanism is shown on the image (Figure 1). Note that the $-\text{CH}_3$ ligands may interact with some other active functional groups if $-\text{OH}$ groups are not available. If not the growth process stops until the next pulse of precursor (H_2O) arrives. In the case of CD no pre-treatment is applied in the ALD process, as the CD molecules have sufficient density of $-\text{OH}$ groups. Each CD molecule consists of ~ 20 and ~ 9 $-\text{OH}$ groups for HP β CD and M β CD, respectively. However, if the reaction requires $-\text{OH}$ mediation and if the surface lacks it then a pre-treatment with water vapor is generally applied. Most importantly the chemisorption of TMAI has to take place as one monomolecular layer on the sample surface. The surface chemical functionality of CD is quite interesting when compared to polymers those were subjected to ALD processing, because of the surface $-\text{OH}$ groups. For ZnO deposition, DEZn also reacts similarly with the H_2O molecules as shown in Figure 1, Step 2 (bottom). Initially DEZn molecules arrive at the surface and form a surface bond with the $-\text{OH}$ groups. When H_2O is pulsed into the chamber the second ethyl group forms C_2H_6 gas leaving $-\text{OH}$ groups behind. The reaction mechanism is shown on the image (Figure 1, bottom of Step 2). The surface functional groups of CD can be considered as an additional advantage in the ALD process.

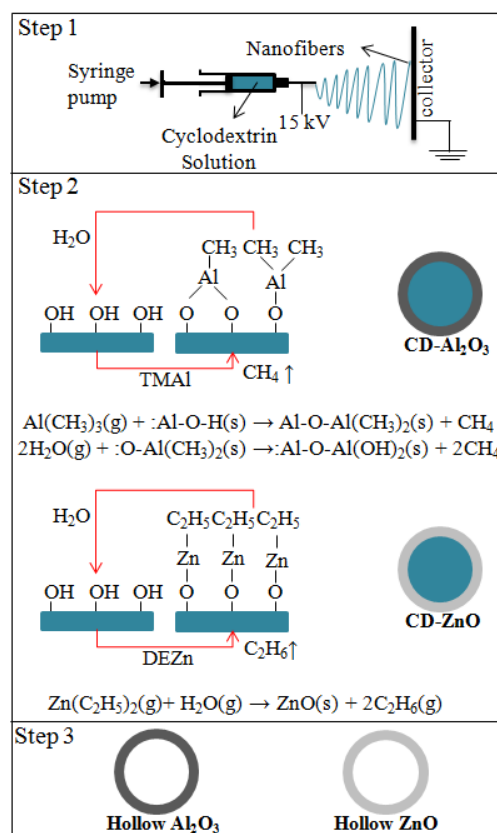


Figure 1. Schematic diagram showing the three step process to fabricate the metal oxide tubes and the mechanism involved in the ALD process.

The representative SEM images of pristine and ALD treated CD nanofibers (before and after washing step) are shown in Figure 2. It was observed that ALD process did not cause any disruption to the nanofiber morphology. It is interesting to note that the AFD decreases when the core-shell nanofibers are subjected to calcination to remove the polymeric core while the percentage shrinkage depends on the type and morphology of the polymer.⁵ On contrary, for the case of washing, we may not expect a change in the AFD. Severe morphological changes can occur when the nanofibers are subjected to thermal treatments.^{3,5} Once the 'core' is washed the resulting tube-like structure is apparent for all cases. In Figure 2b, d, and f the metal oxide coating is thin enough to be electron-transparent as the tubes from the bottom layers are explicit. In Figure 2d we show a selected region displaying their tube-like structures.

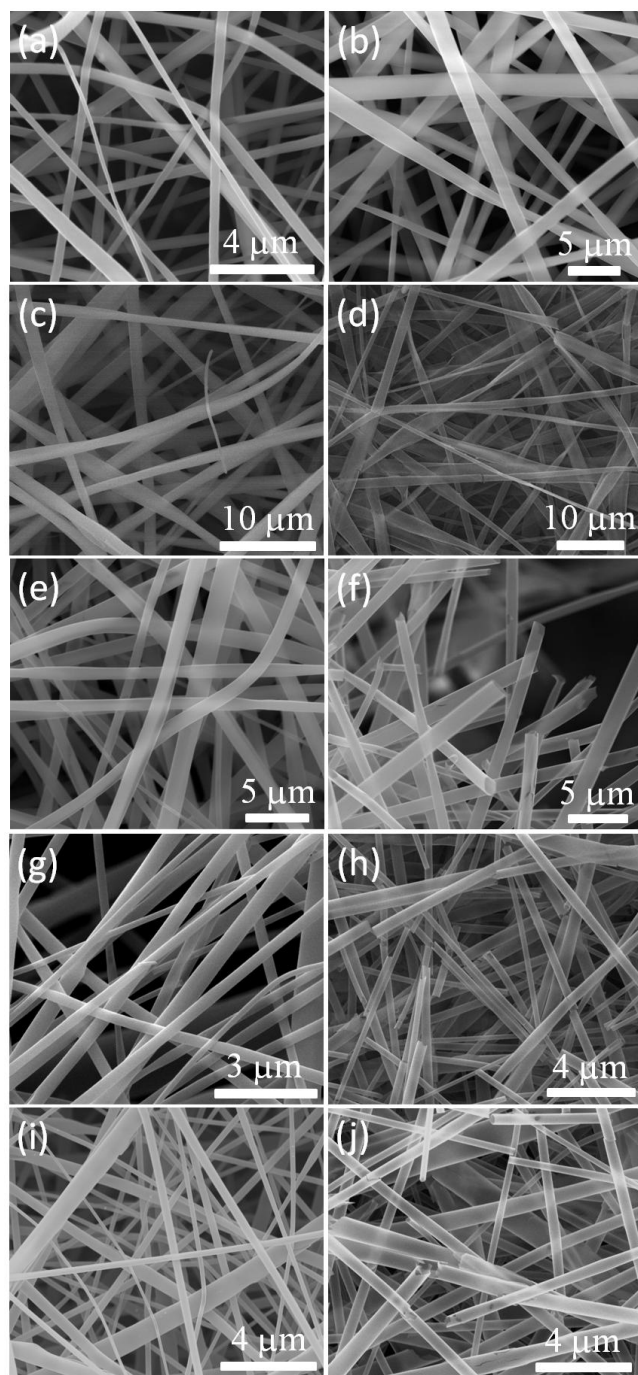


Figure 2. SEM images of samples before and after washing steps. (a) M β CD nanofibers, (b) HP β CD nanofibers (c) AM2, (d) AM2_W, (e) AH2, (f) AH2_W, (g) ZM2, (h) ZM2_W, (i) ZH4, and (j) ZH4_W.

We have analyzed the diameters of samples after Al₂O₃ or ZnO coating for both the types of CD nanofibers. The results are plotted in Figure 3 with Gaussian fittings. The center of the peak is numerically denoted on the corresponding graph. The process of fiber formation in electrospinning is quite complex and obtaining uniform morphology and diameter is a rather hard task.¹⁹⁻²² Similar to the case of polymeric fibers, the homogeneity and diameter of non-polymeric CD nanofibers highly depend on the used solvent types and concentration of the system.^{13,14} In our previous studies,^{13,14} the electrospinning parameters were optimized for both

CD types to produce nanofibers having bead-free morphology, thus we were able to obtain uniform tube structures in this study. However there is a variance at the diameter distributions and this is because of the intrinsic nature of the electrospinning process. On the other hand, after the washing step the structural integrity of the nanofibers was preserved yielding metal oxide tubes.

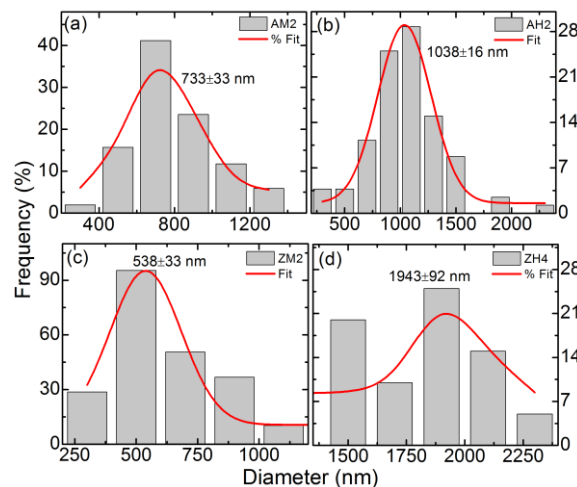


Figure 3. Diameter distribution and the AFD of samples from SEM images. (a) AM2, (b) AH2, (c) ZM2, and (d) ZH4. The center of Gaussian peak (i.e., average fiber diameter) is annotated on each of the distributions.

Local crystal structure and the thickness of the shell coating can be precisely estimated by recording TEM images on the samples. We have used tube-form of samples for such measurements and typical images are shown in Figure 4. 200 cycles of Al₂O₃ resulted in a thickness of 20 nm, 400 cycles of ZnO has developed a thickness of 40 nm. Samples AM2_W and AH2_W generally have a smoother morphology when compared to those of ZM4_W and ZH4_W samples. The smoother morphology is convincing as Al₂O₃ did not depict any grainy structure while in contrast ZnO has shown well developed grains. TEM image has shown smooth and uniform morphology. STEM (dark field) image is shown in Figure 4b for AH4_W sample, where we explicitly can see the tube-like structure. As expected ZM4_W and ZH4_W samples have shown well-developed crystal grains as seen in Figure 4c and d for hollow, respectively. The grain boundaries can host oxygen-related functional groups, which are detrimental in the optical properties,²³⁻²⁵ photocatalysis,³⁻⁵ photoresponse²³ etc. The electron diffraction pattern is shown for ZH4_W sample (inset of Figure 4d) with the corresponding reflections annotated. These circular rings seen in the pattern consists of a series of dots representing the well-developed single crystals assembled in various directions. The pattern is found to be consistent with the literature.^{24,25}

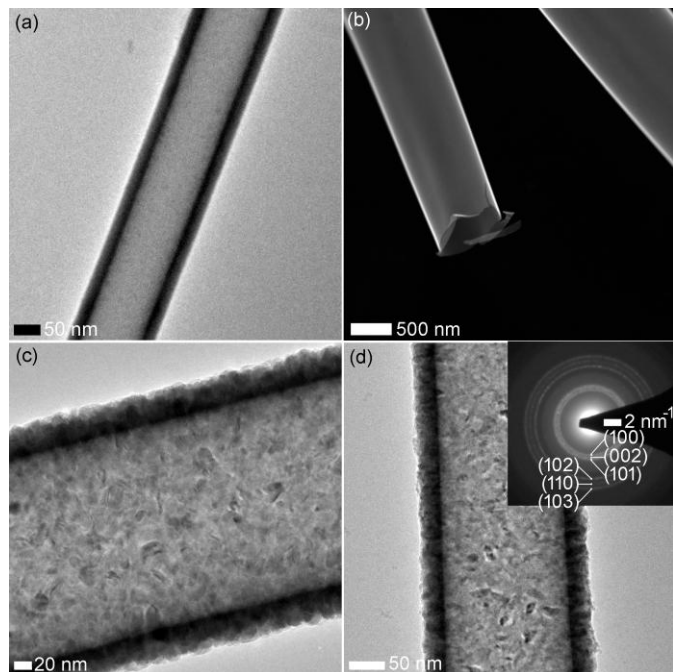


Figure 4. TEM of images of (a) AM2_W, (b) AH2_W, (c) ZM4_W, and (d) ZH4_W. The inset shows ED from ZH4.

XRD patterns from ZM2, ZH4 and their washed counterparts are shown in Figure 5. AH2, AM2 and their tube counterparts did not depict any clear diffraction peaks in the XRD analysis (not shown here). In contrast to Al₂O₃ case, explicit peaks were observed from ZnO and the corresponding reflections were annotated on Figure 5. We have compared the characteristics (Table 1 of ESI) of deconvoluted peaks (30–39°) for ZnO samples (ZM2, ZM2_W, ZH4, and ZH4_W) in terms of angular position and full width at half maximum (FWHM). Importantly, the values from Table 1 of ESI suggest that the washing away the 'core' did not induce any strain in the lattice. As mentioned in the introduction, thermal treatment can also be employed to remove the 'core'. In the case of calcination there can be a residual strain development, which is clearly not the case here. When the –OH groups of CD are randomly substituted with methoxy groups (MβCD) and hydroxypropyl (HPβCD), it results in amorphous material depicting a broad diffraction peak (2θ range not shown here) in contrast to pure β-CD which is a crystalline material.^{13,14}

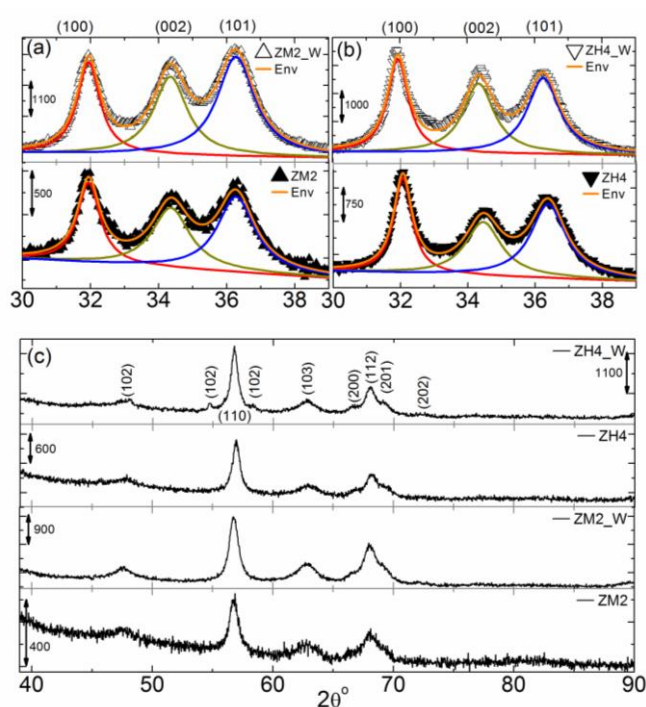


Figure 5. XRD patterns of ALD processed (ZnO) samples before and after washing steps. (a) ZM2, ZM2_W, (b) ZH4, ZH4_W within 30–39° and depicting the deconvolution of three reflections, viz (100), (002) and (101), and (c) 39–90° range is shown for the above samples.

Ionic state of elements on the surface can be identified rather precisely by analyzing XPS spectra. It is important in various contexts, for example Al₂O₃ can be used as an anticorrosive coating, where a clear understanding of the surface chemical functionalities is required.²⁶ While the surface characterization of the wide band gap material such as ZnO is of prime importance in the context of optical properties,^{23–25} photocatalysis,^{3–5} photoresponse²³ etc. XPS survey scan (not shown here) is performed on all samples and the results from metal oxide tubes are tabulated in Table 2 of ESI. Core level XPS spectra are analyzed on Al, Zn and O elements for all four cases before and after the washing step to infer any chemical changes occurred on the surface. Al2p spectra were shown in Figure 6a and b from Al₂O₃ samples of AM2, AH2 and their hollow counterparts, respectively. A significant signal-to-noise ratio is obtained despite of the relatively low ionization cross-section of Al.²⁷ The energetic values of Al2p doublet (2p_{3/2} and 2p_{1/2}) are not only in line with literature but also comparable across the Al₂O₃ coated samples.²⁸ However in the case of metal oxide tubes, a high energy component is seen for AM2_W (75.57 eV) and AH2_W (75.86 eV) cases which might be attributed to the surface bound hydroxyl groups on Al.²⁸ The surface groups arose from 'Step 3' during the fabrication of tubes. In the case of ZnO, ZM2 and ZH4 samples and their tube counterparts did not depict any differences in the Zn2p core-level spectra (Figure 1 of ESI). The spectral locations of the peaks are in line with literature.²⁵ Not observing any differences in Zn2p core-level spectra, of course, does not rule out the possibility of surface hydroxide formation or the presence of oxygen-related functional groups. We will see that this is the case in the context of O1s spectra from ZnO samples.

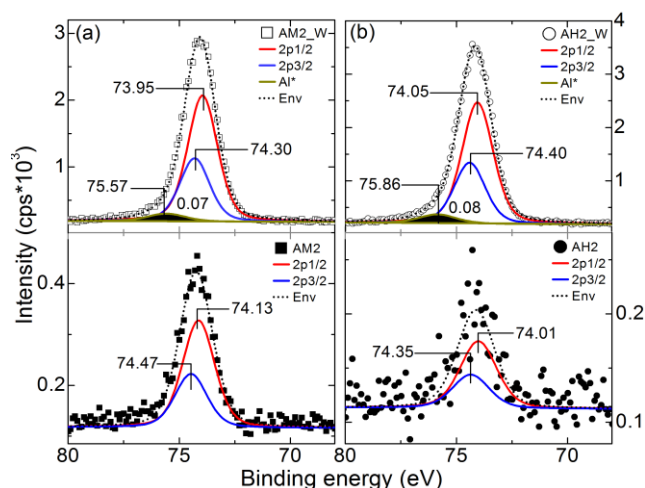


Figure 6. Al core level XPS spectra from Al_2O_3 coated samples before and after washing steps, (a) AM2, AM2_W and (b) AH2, AH2_W. The peak positions are annotated on the image in eV. The area ratio of the peak corresponding to hydroxyl bonded Al is annotated for washed samples.

In the following we discuss the O1s core level spectra for Al_2O_3 and ZnO coatings from core-shell and metal oxide tubes. O1s spectra were shown in Figure 7a and b from Al_2O_3 samples of AM2, AH2 and their tube counterparts, respectively. All the spectra were deconvoluted according to the chemistry of the material. The peak corresponding to lattice oxygen in each of the materials is shown as a shaded area in the plots. The spectra from AM2 and AH2 have shown major peaks centered at ~ 531 eV corresponding to the oxygen in Al_2O_3 ($\text{O}_{\text{Al}_2\text{O}_3}$) and are consistent with the literature.²⁸ The other minor peak appeared at ~ 529.5 eV for AM2 and AH2 samples, might be originated from contaminants while transporting the sample. The second peak on the higher binding energy (BE) side (~ 533 eV) is attributed to adsorbed H_2O ($\text{O}_{\text{H}_2\text{O}}$).^{4,5} Significant changes are observed for tube samples after ‘Step 3’, AM2_W and AH2_W where O1s spectra consist of four peaks (top parts of Figure 7a and b). Importantly the peaks at ~ 531 eV are from the $\text{O}_{\text{Al}_2\text{O}_3}$ (shaded). While the peaks at ~ 533 eV are from $\text{O}_{\text{H}_2\text{O}}$ and those at ~ 530 eV are from differential charging (Diff). Differential charging generally occurs on the surface because of the localized differences in the charge state.²⁸ Especially the mixture of Al_2O_3 and AlOOH phases perhaps enhance such possibility. Also because of the washing step, prominent peak appeared around 532 eV corresponds to O in OH of AlOOH for AM2_W and AH2_W samples.²⁸

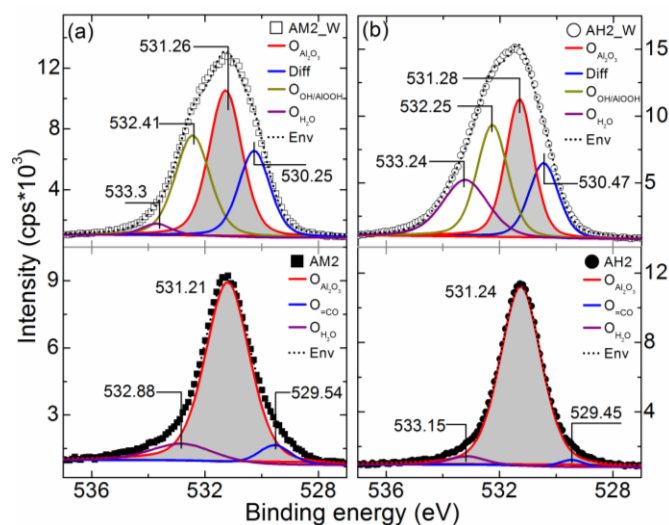


Figure 7. O1s core level XPS spectra from Al_2O_3 coated electrospun samples before and after washing steps, (a) AM2, AM2_W and (b) AH2, AH2_W. The peak positions are annotated on the plot in eV.

O1s spectra from ZM2, ZH4 and their tube counterparts are shown in Figure 8. All the spectra were deconvoluted into three peaks and the origin for each of them is discussed contextually. The peak corresponding to lattice oxygen from each of the materials is shaded in all cases. As mentioned earlier, the photocatalytic activity depends on the ionic state of the chemisorbed surface oxygen.³⁻⁵ O1s spectra were shown in Figure 8a and b from ZnO samples of ZM2, ZH4 and their tube counterparts, respectively. From Figure 8a, the shaded peak within the range of 530.57-530.61 eV in all samples is attributed to O^{2-} ions in the wurtzite structure which are supplemented by nearest neighbor Zn^{2+} in hexagonal configuration (O_{ZnO}). Apart from this, as prepared core-shell structures (ZM2 and ZH4) consist of two more peaks each on the higher BE side of O_{ZnO} . In the case of ZM2, 531.96 eV peak and 532.97 eV peak are attributed to chemisorbed oxygen, O_{Ch1} and O_{Ch2} respectively. ZH4 case, 532.03 and 533.35 eV peaks are ascribed to O_{Ch1} and O_{Ch2} respectively. Generally, the peak centered at 531.50 ± 0.1 eV is associated with O^{x-} ions ($x < 2$). The second high-energy minor peak at 532.50 ± 0.1 eV is typically ascribed to OH^- groups, chemisorbed oxygen or dissociated oxygen.³⁻⁵ This higher BE peak (532.50 ± 0.1 eV) is also attributed to oxygen in $-\text{CO}_3$ by some authors.^{27,29} It can be seen that the relative density of chemisorbed oxygen is higher for ZH4 than ZM2. The slight variation in the energy of the peak corresponding to non-native oxygen because what we see is an integral effect of various species. On the other hand, the grain boundaries (as seen in the TEM images) are obvious locations for such oxygen-related species to chemisorb. Since the sharing of an *electron* can be partial when combined with the above ions it has produced relatively broad binding energies peaked at ~ 531.9 eV.

Despite of the above discussed external oxygen content, the relative intensity of the peak corresponding to ZnO is the most prominent in all cases. The two non lattice origin peaks generally occur in connection to the oxygen vacancies (V_{O} s) in the ZnO lattice.^{3-5,25} In other words, the relative intensities of these components can be connected to the variations in the density of

V_{OS} /chemical functionalities. When the core-shell nanofibers subjected to washing step to convert into metal oxide tubes, significant changes have taken place, see ZM2_W in Figure 8a (top). ZM2_W has shown a component at 529.27 eV which is attributed to various contaminants. The second component \sim 531.81 eV from ZM2_W is attributed to chemisorbed oxygen satisfying the earlier given argument. Furthermore, the surface-Zn(OH)₂ component might be quite low when compared to the overall ZnO content. Note that the hydroxide formation is limited to the surface as we did not evidence any peaks corresponding to Zn(OH)₂ in the XRD pattern (range not shown here).

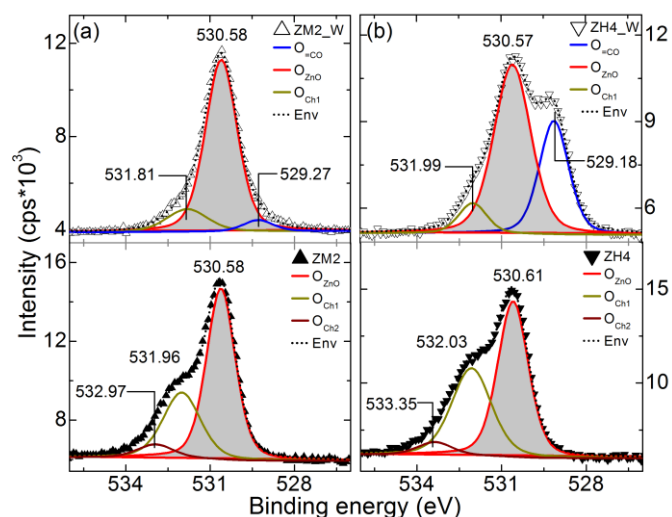


Figure 8. O1s core level XPS spectra from samples before and after washing steps, (a) ZM2, ZM2_W and (b) ZH4, ZH4_W. The peak positions are annotated on the plot in eV.

Density of occupied VB states is investigated in the case of Al₂O₃ tubes and core-shell nanofibers and significant changes were observed before and after washing. The changes are limited to the features below the edge while the edge is undisturbed. A very high band gap (O2p to Al3s transitions) of Al₂O₃ arises because of predominant ionic natured bonding.³⁰ Experimentally obtained VB density of states (DOS) is shown in Figure 9. The upper VB consists of two main features (enclosed with three peaks) within the given energy range. O2s arises below the VB maximum around -20 eV (range not shown here). The first feature is nonbonding orbitals of O2p form the top of the upper VB (Figure 9a). French³⁰ suggests that these bands are ‘flat’ in k-space and correspond to localized state in real space forming O²⁻ ion. Hence the VB is anionic in nature, in contrast empty Al antibonding orbitals corresponding to Al³⁺ form the cationic conduction band.³⁰ The second feature corresponds to mixed Al and O origin. These are hybridized Al-O bonding orbitals (*hAl-O*) represent the covalent bonding present in Al₂O₃. Furthermore, above 14 eV a clear difference is seen for AH2 and AH2_W samples, where the former has shown relatively higher DOS in contrast to the latter. It is also notable that AH2_W is more comparable to the Al₂O₃ spectrum of native or thermal oxide.³⁰ VB structure of ZnO is investigated and the results suggest that there are no changes in the VB edge before and after washing and MβCD to HPβCD nanofibers (spectra not shown here).

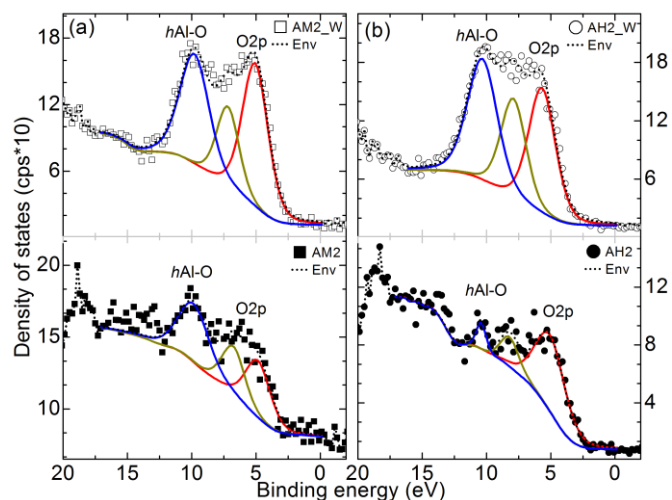


Figure 9. Valence band spectra from Al₂O₃ coated samples before and after washing steps, (a) AM2, AM2_W and (b) AH2, AH2_W.

We have attempted to obtain ZnO tubes with HPβCD nanofibers with 200 cycles of deposition. However after washing the tube structure is not sustained because of the following two reasons; 1. We have evidenced that HPβCD nanofibers are relatively thicker than MβCD nanofibers. 2. In the ALD process ZnO forms grain like structure. At higher diameter of core the grainy structure collapses due to the lack of mechanical robustness. Hence we have performed 400 cycles of deposition which has yielded well preserved ZH4_W sample. Note that this is not the case with Al₂O₃ which has formed amorphous structure and hence 200 cycles of deposition is good enough to sustain the structure. Hence the crystalline nature of the ALD product determines the integrity of the structure.

Conclusions

In this study we show that non-polymeric systems such as CD (MβCD and HPβCD) are well compatible in ALD process. This combination can produce core-shell nanofibers and subsequently metal oxide tubes. CD nanofibers are compatible at relatively higher temperatures which can have a better applicability in ALD processing. Exploiting the excellent water solubility of CD we have tested two metal oxide coatings *viz* Al₂O₃ and ZnO and thoroughly characterized the core-shell nanofibers and metal oxide tubes. By considering the deposition mechanism we note that the surface -OH groups of CD are beneficial to support a uniform coating. The surface morphology examination via SEM suggested smooth and consistent morphology within each of the samples. After washing the ‘core’ the tube-like structure is rather explicit under SEM. TEM images have evidenced smooth morphology for Al₂O₃ and grainy structure for ZnO. Electron diffraction confirmed the wurtzite structure of ZnO. XRD analyses of core-shell nanofibers and ZnO tubes corroborate no residual stress/strain development and wurtzite structure as well. XPS spectral analysis on Al₂O₃ and ZnO has confirmed the ionic state of Al and Zn. Core-level XPS on Al has shown a small fraction of hydroxylation. O1s from Al₂O₃ has shown significant variations within core-shell and tube samples. Noticeably

tube samples host AIOOH on the surface apart from other typical functional groups. O1s from ZnO is discussed elaborately as the grainy structure and intrinsic defects can host a variety of functional groups. Similar to the case of O1s from Al₂O₃, its VB structure also depicted notable differences which might arise from the formation of AIOOH on the surface because of the washing step.

Acknowledgements

A.C. thanks The Scientific and Technological Research Council of Turkey (TUBITAK) TUBITAK-BIDEB-2228 for PhD scholarship. S.V. thanks TUBITAK (TUBITAK-BIDEB 2221-Fellowships for Visiting Scientists and Scientists on Sabbatical) for the postdoctoral fellowship) for postdoctoral fellowship. N.B. thanks EU FP7-Marie Curie-IRG for funding NEMSmart (PIRG05-GA-2009-249196). T.U. thanks EU FP7-Marie Curie-IRG (NANOWEB, PIRG06-GA-2009-256428) and The Turkish Academy of Sciences– Outstanding Young Scientists Award Program (TUBA-GEBIP) for partial funding. Authors thank M. Guler for technical support for TEM analysis.

Notes and references

^a UNAM-National Nanotechnology Research Center, Bilkent University, Ankara, 06800, Turkey


^b Institute of Materials Science and Nanotechnology, Bilkent University, Ankara, 06800, Turkey

E-mail: svempati01@qub.ac.uk; uyar@unam.bilkent.edu.tr

† Electronic Supplementary Information (ESI) available: Output results of XRD peak deconvolution, results of XPS survey scan and Zn2p core-level XPS. See DOI: 10.1039/b000000x/

References

- W. J. Sweet, J. S. Jur and G. N. Parsons, *J. Appl. Phys.*, 2013, 113, 194303.
- C. J. Oldham, B. Gong, J. C. Spagnola, J. S. Jur, K. J. Senecal, T. A. Godfrey and G. N. Parsons, *J. Electrochem. Soc.*, 2011, 158, D549-D556.
- F. Kayaci, S. Vempati, C.O.-Akgun, N. Biyikli and T. Uyar, *Appl. Catal. B.*, 2014, 156-157, 173-183.
- F. Kayaci, S. Vempati, I. Donmez, N. Biyikli and T. Uyar, *Nanoscale*, 2014, 6, 10224–10234.
- F. Kayaci, S. Vempati, C. Ozgit, I. Donmez, N. Biyikli and T. Uyar, *Nanoscale*, 2014, 6, 5735.
- P. Heikkilä, T. Hirvikorpi, H. Hilden, J. Sievänen, L. Hyvärinen, A. Harlin and M. Vähä-Nissi, *J. Mater. Sci.*, 2012, 47, 3607-3612.
- Q. Peng, X.-Y. Sun, J. C. Spagnola, G. K. Hyde, R. J. Spontak and G. N. Parsons, *Nano Lett.*, 2007, 7, 719-722.
- Q. Peng, X.-Y. Sun, J. C. Spagnola, C. Saquing, S. A. Khan, R. J. Spontak and G. N. Parsons, *ACS Nano*, 2009, 3, 546-554.
- J. Y. Park, S.-W. Choi and S. S. Kim, *Nanotechnology*, 2010, 21, 475601.
- S. Cho, D.-H. Kim, B.-S. Lee, J. Jung, W.-R. Yu, S.-H. Hong and S. Lee, *Sensors and Actuators B*, 2012, 162, 300-306.
- E. Santala, M. Kemmel, M. Leskela and M. Ritala, *Nanotechnology*, 2009, 20, 035602.
- F. Kayaci, C. Ozgit-Akgun, N. Biyikli and T. Uyar, *RSC Adv.*, 2013, 3, 6817-6820.
- A. Celebioglu and T. Uyar, *Chem. Commun.*, 2010, 46, 6903-6905.
- A. Celebioglu and T. Uyar, *Nanoscale*, 2012, 4, 621-631.
- A. Celebioglu and T. Uyar, *J. Colloid. Interf. Sci.*, 2013, 404.
- A. Celebioglu and T. Uyar, *RSC Advances*, 2013, 3, 22891 - 22895.
- M. G. McKee, J. M. Layman, M. P. Cashion and T. E. Long, *Science*, 2006, 311, 353-355.
- X. Yan, M. Zhou, J. Chen, X. Chi, S. Dong, M. Zhang, X. Ding, Y. Yu, S. Shaod and F. Huang, *Chem. Commun.*, 2011, 47, 7086.
- S. Ramakrishna, K. Fujihara, W. Teo, T. Lim and Z. Ma, *An Introduction to Electrospinning and Nanofibers*, World Scientific Publishing Company, Singapore, 2005.
- J. H. Wendorff, S. Agarwal and A. Greiner, *Electrospinning: Materials, Processing, and Applications*, Wiley-VCH, Germany, 2012.
- J. V. Nygaard, T. Uyar, M. Chen, P. Cloetens, P. Kingshott and F. Besenbacher, *Nanoscale*, 2011, 3, 3594-3597.
- T. Uyar and F. Besenbacher, *Polymer*, 2008, 49, 5336-5343.
- S. Vempati, S. Chirakkara, J. Mitra, P. Dawson, K. K. Nanda and S. B. Krupanidhi, *Appl. Phys. Lett.*, 2012, 100, 162104.
- S. Vempati, J. Mitra and P. Dawson, *Nanoscale Res. Lett.*, 2012, 7, 470.
- S. Vempati, A. Shetty, P. Dawson, K. K. Nanda and S. B. Krupanidhi, *Thin Solid Films*, 2012, 524, 137.
- B. Díaz, E. Härkönen, J. Swiatowska, V. Maurice, A. Seyeux, P. Marcus and M. Ritala, *Corrosion Science*, 2011, 53, 2168-2175.
- M. Chen, X. Wang, Y. H. Yu, Z. L. Pei, X. D. Bai, C. Sun, R. F. Huang and L. S. Wen, *Appl. Surf. Sci.*, 2000, 158, 134-140.
- Handbooks of Monochromatic XPS Spectra: Commercially Pure Binary Oxides*, XPS International, California.
- S. Major, S. Kumar, M. Bhatnagar and K. L. Chopra, *Appl. Phys. Lett.*, 1986, 49, 394.
- R. H. French, *J. Am. Ceram. Soc.*, 1990, 73, 477-489.

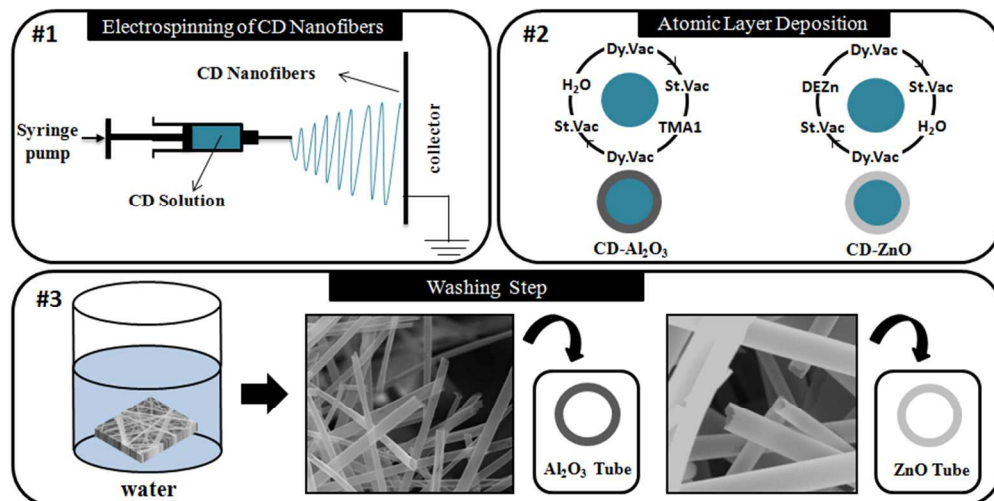

Graphical Abstract Image
78x39mm (300 x 300 DPI)