

RSC Advances



This is an *Accepted Manuscript*, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. This *Accepted Manuscript* will be replaced by the edited, formatted and paginated article as soon as this is available.

You can find more information about *Accepted Manuscripts* in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this *Accepted Manuscript* or any consequences arising from the use of any information it contains.

COMMUNICATION

3D interconnected SnO₂-coated Cu foam as a high-performance anode for lithium-ion battery applications

Cite this: DOI: 10.1039/x0xx00000x

Ji Hyun Um,^{ab} Hyeji Park,^c Yong-Hun Cho,^{*c} Matthew P. B. Glazer,^d David C. Dunand,^d Heeman Choe^c and Yung-Eun Sung^{*ab}Received 00th January 2012,
Accepted 00th January 2012

DOI: 10.1039/x0xx00000x

www.rsc.org/

A SnO₂-coated Cu foam with 3D interconnected scaffold was fabricated by a simple sol-gel method for use as a self-supporting anode for lithium-ion batteries. The binder- and carbon-free electrode integrated with current collector exhibits a high reversible capacity, excellent rate capability, and stable cycle retention by preserving its structural integrity.

Tin dioxide (SnO₂) has been regarded as a promising alternative to the currently used graphite anode for next generation lithium-ion batteries (LIBs) because of its relatively low cost, low toxicity, high natural abundance, and, most importantly, low discharge potential and high theoretical capacity of 781 mAh g⁻¹ from the maximum reaction to form Li_{4.4}Sn alloy.¹⁻³ However, the large amounts of Li ions inserted/extracted into/from Sn induce severe volume changes (up to approximately 300%), which causes a pulverization of Sn particles and a loss of electrical contact with current collector, eventually resulting in poor electrochemical performance.²⁻⁴

Substantial efforts have been devoted to addressing this issue, and two approaches have been extensively investigated: a unique nanostructuring of SnO₂ for short Li ion diffusion paths and void spaces to accommodate the severe volume changes^{4,5} and a nanocompositing with carbonaceous materials for enhanced electrical conductivity and structural stability resulted from the coating layer or matrix.^{4,6} However, the introduction of carbonaceous materials into SnO₂ has an inherent weakness with respect to gravimetric specific capacity calculated from the combination of SnO₂ and carbon. Since the theoretical capacity of graphite, based on a reversible intercalation reaction, is 372 mAh g⁻¹ (corresponding to LiC₆) which is considerably lower

than that of SnO₂. Although in case of graphene the theoretical capacity is 740 mAh g⁻¹ (corresponding to Li₂C₆) which is limited to the carbon composed predominantly of single layers.^{7,8} Therefore, the unique morphology controls of SnO₂ using several synthetic methods have been proposed to achieve prolonged cycle stability without a decrease in the gravimetric specific capacity. Many researches for the morphology controls of SnO₂ have been accomplished, including one-dimensional (1D) nanorods,⁹ nanotubes,¹⁰ or nanowires,^{11,12} two-dimensional (2D) nanosheets,^{13,14} and three-dimensional (3D) nanoarchitectures.¹⁵ Recently, the 3D scaffold architecture has attracted attention as a smart electrode prototype,^{16,17} and various architectures from simple periodic arrays of cylindrical nanopillars¹⁸ to complex arrangements such as inverse opal scaffold,¹⁹ foams,^{20,21} and long chains of particles^{22,23} have been conducted.

In this work, we report a facile synthesis of SnO₂-coated Cu foam (SnO₂/Cu foam) as a self-supporting anode for LIBs. Through the use of a simple sol-gel method, a SnO₂/Cu foam integrated with current collector, and free of binder and conducting agent was obtained. A 3D interconnected metallic scaffold coated with high capacity material is advantageous for alleviating the large volume changes of active material and for the easy transport of electrons and Li ions.^{4,15-17} The SnO₂/Cu foam exhibited a high reversible capacity of 621 mAh g⁻¹ at a rate of 1 C after 50 cycles, an excellent rate capability of 368 mAh g⁻¹ at 2 C, and a stable cycle performance, and its structural integrity was preserved after cycling.

The SnO₂/Cu foam was fabricated using a sol-gel method, and the synthesis process is shown in Fig. S1 (ESI†). The procedure for synthesizing the electrode is described in more detail in ESI†. Fig. 1 shows the surface morphology of commercially available

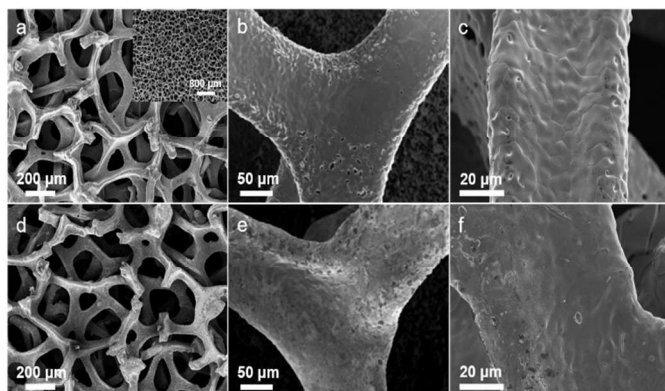


Fig. 1 FE-SEM images of Cu foam at pristine state (a)-(c) and after SnO₂ sol-gel coating (d)-(f). The inset shows the pristine Cu foam at low magnification.

Cu foam in the pristine state (Figs. 1a-c) and after SnO₂ sol-gel coating (Figs. 1d-f). In Fig. 1a, prior to coating with SnO₂, the Cu foam was a 3D interconnected scaffold composed of continuous struts with a width of less than approximately 100 μm and of interconnected pores with a diameter of 100–500 μm. This morphology character is also confirmed at lower magnification in the inset of Fig. 1a. The surface of the struts was further examined using higher magnification FE-SEM images (Figs. 1b and c), and the development of small pores and grains on the surface was observed. After SnO₂ coating, the 3D interconnected scaffold of the Cu foam was maintained as shown in Fig. 1d, and the surface morphology of the Cu foam was relatively smooth with covering the small pores and the grains (Figs. 1e and f). Figs. 2a-d present FE-SEM and EDX mapping images of the Cu foam after SnO₂ coating. The presence of Cu, Sn, and O was confirmed, and the distributions of Sn and O corresponded with that of Cu, which implies that the Cu foam served as a template for the deposition of SnO₂. To confirm the thickness of the SnO₂ deposited as a coating layer, the cross-sectional image of Fig. 2a obtained using FIB milling is presented in Fig. 2e. The inset shows a whole cross-sectional image of the SnO₂/Cu foam, and the magnified image indicates that the Cu foam was covered with a thin (approximately 200 nm) and uniform layer. This coating layer is presumed to be SnO₂ based on the EDX mapping (Fig. S2a, ESI†), and its thickness of approximately 200 nm was confirmed from the EDX line scan (Fig. S2b, ESI†). The XRD pattern in Fig. S3 (ESI†) confirms the presence of the SnO₂ because only peaks for tetragonal




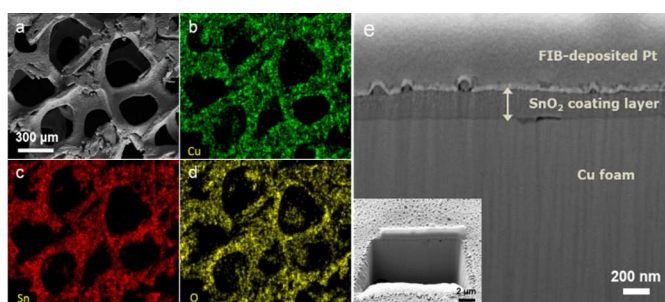


Fig. 2 FE-SEM images of SnO₂-coated Cu foam using EDX mapping (a)-(d) and using FIB milling (e). The inset shows the cross-sectional SnO₂-coated Cu foam at low magnification.

rutile SnO₂ (JCPDS 41-1445) and metallic Cu (JCPDS 04-0836) are observed with no additional peaks such as SnO and Cu₂O.²⁴⁻²⁶

The SnO₂ sol-gel concentration was initially investigated under the assumption that the Sn(II) molar concentration may or may not have an impact on the electrochemical performance. SnO₂/Cu foams were prepared from different Sn(II) molar concentrations of 3 M and 10 M, and these foams were referred to as SnO₂/Cu foam@3M and SnO₂/Cu foam@10M, respectively. To understand the reactive processes of the SnO₂/Cu foam@3M and SnO₂/Cu foam@10M, cyclic voltammetry (CV) measurement was conducted in the voltage range of 0.01–2 V at a scan rate of 0.1 mV s⁻¹ (Fig. S4, ESI†). The first five CV curves of SnO₂/Cu foam@3M and SnO₂/Cu foam@10M were in accord with the electrochemical behaviour of SnO₂-based materials.²⁷⁻²⁹ The first cathodic peak at 0.64 V of the SnO₂/Cu foam@3M is ascribed to the irreversible formation of a solid electrolyte interface (SEI) layer due to electrolyte decomposition and the reduction of SnO₂ to Sn as followed by eqn (1) and (2), respectively.



In addition, the cathodic peaks at 0.0–0.5 V indicate the formation of Li_xSn alloys as described by eqn (3), and the corresponding anodic peaks appeared at 0.2–1.0 V because of the extraction of Li ions from the Li_xSn alloys.³⁰ The anodic peak appeared at 1.42 V, which is attributed to the oxidation of Sn to SnO₂, and the first cathodic peak shifted to higher voltages by around 0.94 V during subsequent

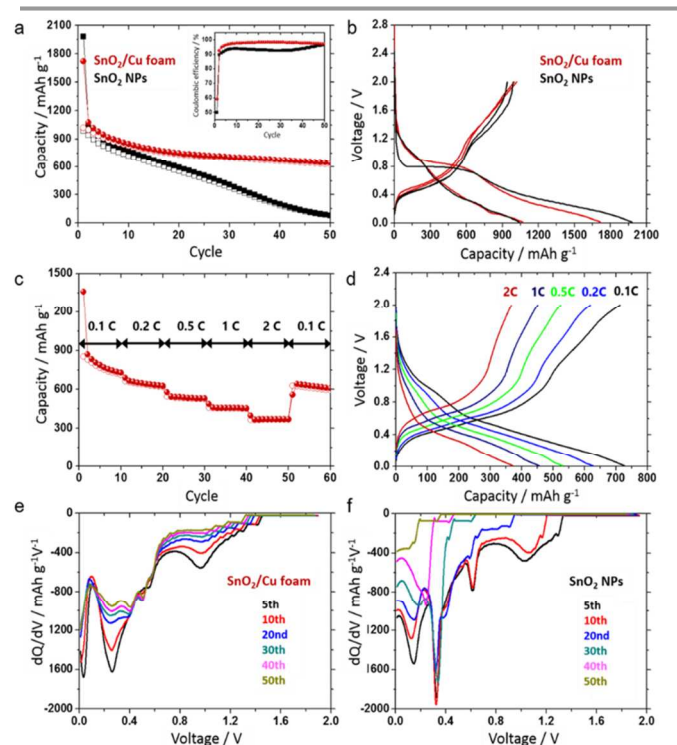


Fig. 3 (a) Cycle performance of SnO₂/Cu foam and SnO₂ NPs at 1 C for 50 cycles with the inset of coulombic efficiencies, (b) voltage profiles of SnO₂/Cu foam and SnO₂ NPs during the first two cycles at 1 C, (c) capacity and (d) voltage profiles of SnO₂/Cu foam cycled at various rates, and (e) dQ/dV profiles of SnO₂/Cu foam and (f) of SnO₂ NPs at 1 C at selected cycle.

cycles, which implies partial reversibility of the electrochemical reaction described by eqn (2).^{29,31} A battery performance test was carried out to examine the potential of SnO₂/Cu foam@3M and SnO₂/Cu foam@10M as anode for LIBs. Fig. S5a (ESI†) presents the first two voltage profiles of SnO₂/Cu foam@3M and SnO₂/Cu foam@10M in the voltage range of 0.01–2 V at a current density of 1 C (1 C = 781 mA g⁻¹), and these voltage profiles are consistent with the corresponding CV curves (Fig. S4, ESI†) and with the lithiation/delithiation process described in previous reports.^{22,31} The cycling performances of SnO₂/Cu foam@3M and SnO₂/Cu foam@10M at 1 C are shown in Fig. S5b (ESI†). Both electrodes exhibited stable capacity retention, and the capacity of SnO₂/Cu foam@10M was approximately 200 mAh g⁻¹ higher than that of SnO₂/Cu foam@3M throughout all of the cycles. Although the reason for the increase in capacity with increasing Sn(II) molar concentration is not yet clear, the 10 M Sn(II) solution was used in our investigation of high capacity electrode.

The electrochemical properties of the SnO₂/Cu foam were further examined by introducing a commercial SnO₂ powder electrode which was pasted on a Cu foil and referred to as SnO₂ NPs, as a control group. The cycling performances of the SnO₂/Cu foam and SnO₂ NPs at 1 C between 0.01 and 2 V are presented in Fig. 3a. Although the capacities of both SnO₂/Cu foam and SnO₂ NPs decreased in the early cycles, the SnO₂/Cu foam subsequently exhibited stable capacity retention and a reversible capacity as high as 621 mAh g⁻¹ after 50 discharge/charge cycles. The high Li ion storage of the SnO₂/Cu foam is fairly comparable to that of recently reported Sn-based anode materials (see the comparison in Table S1, ESI†). Additionally, the coulombic efficiencies of the SnO₂/Cu foam (inset of Fig. 3a) remained relatively stable, whereas those of the SnO₂ NPs were considerably lower and fairly unstable over all of the cycles. The commercially available Cu foam with 500 μm thickness was directly employed to an electrode. The thickness of Cu foam was thicker than the conventional Cu foil with 20 μm and also the previous 3D scaffold electrode with 160 μm,³² 59 μm,³³ and 10 μm¹⁹. The large difference of the electrode thickness in magnitude can be reduced by introducing a physically cutting or polishing step and a compression process under high pressure.^{32,33} The possibility to increase the volumetric energy density by reducing the thickness of Cu foam exists in our work. As shown in Fig. 3b, the first discharge and charge capacities of the SnO₂/Cu foam were 1720 and 1017 mAh g⁻¹, respectively, and those of the SnO₂ NPs were 1983 and 988 mAh g⁻¹, respectively, which indicates that the coulombic efficiency of the SnO₂/Cu foam was 10% higher than that of the SnO₂ NPs. Additionally, the second charge capacities of the SnO₂/Cu foam and SnO₂ NPs were 998 and 938 mAh g⁻¹, respectively. From a comparison of the first and second charge capacities, the rate of decrease in the capacity of the SnO₂ NPs is approximately 2.7 times faster than that of the SnO₂/Cu foam. The rate capability of the SnO₂/Cu foam cycled between 0.01 and 2 V was evaluated stepwise by increasing the C-rate from 0.1 C to 2 C and then returning to 0.1 C as shown in Fig. 3c. When cycled at 0.1 C, the first charge capacity of 852 mAh g⁻¹ decreased to 713 mAh g⁻¹ for the subsequent 10 cycles, and then the capacity became stable as the C-rate increased. At a significantly high rate of 2 C (1562 mA g⁻¹), the SnO₂/Cu foam delivered a high capacity of 368 mAh g⁻¹ with good

stability, which is comparable with recent reports on Sn-based materials,^{34,35} or even better.^{36–38} When the C-rate was reduced back to 0.1 C after 50 cycles, the SnO₂/Cu foam recovered a respectable amount of the first 0.1 C step capacity, demonstrating its excellent rate capability. Fig. 3d presents the last discharge/charge voltage profiles of each rate step shown in Fig. 3c. As the C-rate increased, the lithiation potential decreased and the delithiation potential increased, which is due to the kinetic effects of the material.³⁹ Moreover, the lithiation potential at a significantly high rate of 2 C exhibited a sloping profile between 0.01 and 0.3 V, corresponding to the formation of Li_xSn alloy.^{27–29,40} The differential capacity profiles (dQ/dV vs. voltage) of the SnO₂/Cu foam and SnO₂ NPs are shown in Figs. 3e and f. The distinct peaks between 0.0 and 0.7 V correspond to the lithiation steps for forming the Li_xSn alloys. For the SnO₂/Cu foam, the intensities corresponding to the Li_xSn peaks diminished with a slowly decreasing rate, and they retained a relatively large area after 50 cycles. This feature is also observed in the SnO₂/Cu foam prepared from a sol-gel concentration of 3 M (Fig. S6, ESI†). However, the intensities of the SnO₂ NPs rapidly decreased and nearly disappeared at the 50th cycle, which suggests that the insertion of Li ions into the SnO₂ NPs no longer occurs, which is in contrast to the SnO₂/Cu foam. The clearly stable Li ion storage of the SnO₂/Cu foam may be attributed to its 3D interconnected structure, effectively accommodating the large volume changes of Sn with repeated lithiation/delithiation processes, and thereby preventing the pulverization of Sn particles and the loss of its electrical connection.

To certify the stabilizing effect of the SnO₂/Cu foam, the cells of both SnO₂/Cu foam and SnO₂ NPs after 50 cycles at 1 C were disassembled and examined as shown in Fig. S7 (ESI†). The electrode morphology of the SnO₂/Cu foam retained its original architecture after cycling, whereas that of the SnO₂ NPs was quite different. In contrast to the SnO₂/Cu foam, the poor contact between SnO₂ nanoparticles and current collector in the SnO₂ NPs resulted in the rapid capacity fading. To further examine the surface and cross-sectional morphology of the SnO₂/Cu foam, the electrode after cycling was investigated using FE-SEM and FIB milling. As shown in Fig. 4a, the morphology of the SnO₂/Cu foam after cycling was similar to that before cycling (Fig. 1d). Moreover, the SnO₂ coating layer on the Cu foam was still present after 50 cycles, and its thickness increased to 480 nm, corresponding to an expansion ratio

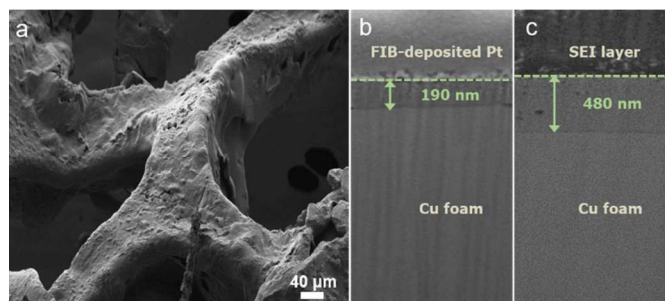


Fig. 4 (a) FE-SEM image of SnO₂/Cu foam after 50 cycles and (b) and (c) cross-sectional image of SnO₂/Cu foam before and after cycling, respectively.

of ~153% based on a comparison of the SnO₂ thickness before (Fig. 4b) and after (Fig. 4c) cycling. The presence of the stable SnO₂ coating layer on the Cu foam without severe separation from current collector maintained the electrical connection to the Cu foam, which provided the electrode with excellent cycling performance. As a further check for the stability of the anode, *In operando* X-ray diffraction was also performed on the SnO₂/Cu foam at 1 C (Fig. S8, ESI†), to monitor the evolution of strain in the Cu foam in response to (de)lithiation of the Sn during cycling. The elastic strain behaviour in Fig. S8 indicates that (de)lithiation-induced mismatch strains are created by load transfer from the expanding/contracting SnO₂ coating layer to the Cu foam, and increase/decrease (i) linearly with respect to the extent of (de)lithiation (and thus the amount of mismatch), (ii) reversibly during a full lithiation/delithiation cycle, and (iii) with good repeatability over 20 cycles. This is consistent with the Cu foam scaffold acting as a partial mechanical constraint for the lithiation of the SnO₂ coating layer, as observed also recently in an inverse-opal Ni scaffold coated with Si⁴¹. However, the Cu strains are low and within the elastic strain region for Cu, suggesting that the much larger mismatch due to (de)lithiation is mostly accommodated by expansion into the pores. The high repeatability between the various cycles in Fig. S9 indicates good mechanical (and thus also electrical) contact between the SnO₂ coating layer and the Cu foam current collector.

Conclusions

In summary, a SnO₂-coated Cu foam was obtained through a simple sol-gel synthesis, and was electrochemically investigated as an anode for LIBs. This electrode, which was integrated with current collector and without the addition of binder and conducting agent, delivered a high reversible capacity of 621 mAh g⁻¹ at 1 C after 50 cycles and an excellent rate performance of 368 mAh g⁻¹ at 2 C. The high Li ion storage and rate capability were attributed to the 3D continuous Cu foam scaffold and the interconnected porous structure for the facile transport of electrons and Li ions. From a comparison with the conventional SnO₂ nanoparticle electrode, the superiority of 3D scaffold architecture, particularly for the alleviating the severe volume changes of Sn, was demonstrated by preserving its original architecture. These results indicate that the SnO₂/Cu foam has promising applications as a self-supporting, binder- and carbon-free anode for advanced LIBs.

Acknowledgements

Y.-E. S. acknowledges the Institute for Basic Science (IBS) in Korea. This work was supported by Project Code (IBS-R006-G1). Y. H. C. acknowledges financial support from the Priority Research Center Program (2009-0093814) and the Basic Science Research Program (2013R1A1A2061636) through the National Research Foundation of Korea (NRF), which is funded by the Ministry of Education. M. P. B. G. acknowledges G. Halder (Advanced Photon Source) for assistance with *in operando* XRD data collection. This research used resources of the Advanced Photon Source, a U.S. Department of Energy (DOE) Office of Science User Facility operated for the DOE

Office of Science by Argonne National Laboratory under Contract No. DE-AC02-06CH11357.

Notes and references

^a School of Chemical & Biological Engineering, Seoul National University, Seoul 151-742, Republic of Korea.

^b Center for Nanoparticle Research, Institute for Basic Science (IBS), Seoul 151-742, Republic of Korea. E-mail: ysung@snu.ac.kr

^c School of Advanced Materials Engineering, Kookmin University, Seoul 136-702, Republic of Korea. E-mail: yhun00@kookmin.ac.kr

^d Department of Materials Science and Engineering, Northwestern University, Evanston, IL 60208, USA.

† Electronic Supplementary Information (ESI) available. See DOI: 10.1039/c000000x/

- 1 Y. Idota, T. Kubota, A. Matsufuji, Y. Maekawa and T. Miyasaka, *Science*, 1997, **276**, 1395.
- 2 I. A. Courtney and J. R. Dahn, *J. Electrochem. Soc.*, 1997, **144**, 2045.
- 3 T. Brousse, R. Retoux, U. Herterich and D. M. Schleich, *J. Electrochem. Soc.*, 1998, **145**, 1.
- 4 J. S. Chen and X. W. Lou, *Small*, 2013, **9**, 1877.
- 5 Z. Wang, L. Zhou and X. W. Lou, *Adv. Mater.*, 2012, **24**, 1903.
- 6 G. Cui, Y.-S. Hu, L. Zhi, D. Wu, I. Lieberwirth, J. Maier and K. Müllen, *Small*, 2007, **3**, 2066.
- 7 J. R. Dahn, T. Zheng, Y. Liu and J. S. Xue, *Science*, 1995, **270**, 590.
- 8 R. Mukherjee, A. V. Thomas, A. Krishnamurthy and N. Koratkar, *ACS Nano*, 2012, **6**, 7867.
- 9 J. Liu, Y. Li, X. Huang, R. Ding, Y. Hu, J. Jiang and L. Liao, *J. Mater. Chem.*, 2009, **19**, 1859.
- 10 J. Ye, H. Zhang, R. Yang, X. Li and L. Qi, *Small*, 2010, **6**, 296.
- 11 M.-S. Park, G.-X. Wang, Y.-M. Kang, D. Wexler, S.-X. Dou and H.-K. Liu, *Angew. Chem. Int. Ed.*, 2007, **46**, 750.
- 12 J. Y. Huang, L. Zhong, C. M. Wang, J. P. Sullivan, W. Xu, L. Q. Zhang, S. X. Mao, N. S. Hudak, X. H. Liu, A. Subramanian, H. Fan, L. Qi, A. Kushima and J. Li, *Science*, 2010, **330**, 1515.
- 13 S. Ding, J. S. Chen and X. W. Lou, *Adv. Funct. Mater.*, 2011, **21**, 4120.
- 14 H. B. Wu, J. S. Chen, X. W. Lou and H. H. Hng, *J. Phys. Chem. C*, 2011, **115**, 24605.
- 15 X. Li, A. Dhanabalan, L. Gu and C. Wang, *Adv. Energy Mater.*, 2012, **2**, 238.
- 16 H. Zhang, X. Yu and P. V. Braun, *Nat. Nanotechnol.*, 2011, **6**, 277.
- 17 X. Zhu, Z. Guo, P. Zhang, G. Du, R. Zeng, Z. Chen and H. Liu, *ChemPhysChem*, 2009, **10**, 3101.
- 18 L. Ji, Z. Tan, T. Kuykendall, E. J. An, Y. Fu, V. Battaglia and Y. Zhang, *Energy Environ. Sci.*, 2011, **4**, 3611.
- 19 H. Zhang and P. V. Braun, *Nano Lett.*, 2012, **12**, 2778.
- 20 Y. Fu, Z. Yang, X. Li, X. Wang, D. Liu, D. Hu, L. Qiao and D. He, *J. Mater. Chem. A*, 2013, **1**, 10002.
- 21 W. Ni, H. B. Wu, B. Wang, R. Xu and X. W. Lou, *Small*, 2012, **8**, 3432.
- 22 J. Lin, Z. Peng, C. Xiang, G. Ruan, Z. Yan, D. Natelson and J. M. Tour, *ACS Nano*, 2013, **7**, 6001.
- 23 Y. Yu, L. Gu, C. Wang, A. Dhanabalan, P. A. van Aken and J. Maier, *Angew. Chem. Int. Ed.*, 2009, **48**, 6485.

Journal Name

- 24 J. Y. Xiang, J. P. Tu, Y. F. Yuan, X. H. Huang, Y. Zhou and L. Zhang, *Electrochem. Commun.*, 2009, **11**, 262.
- 25 M. Bhagwat, P. Shah and V. Ramaswamy, *Mater. Lett.*, 2003, **57**, 1604.
- 26 Y.-Y. Zhu, S.-R. Wang, L.-J. Zhu, X.-L. Ge, X.-B. Li and Z.-Y. Luo, *Catal. Lett.*, 2010, **135**, 275.
- 27 J. Li, Y. Zhao, N. Wang and L. Guan, *Chem. Commun.*, 2011, **47**, 5238.
- 28 Y. Zhao, J. Li, N. Wang, C. Wu, G. Dong and L. Guan, *J. Phys. Chem. C*, 2012, **116**, 18612.
- 29 Y. Yang, X. Ji, F. Lu, Q. Chena and C. E. Banks, *Phys. Chem. Chem. Phys.*, 2013, **15**, 15098.
- 30 K. Kravchik, L. Protesescu, M. I. Bodnarchuk, F. Krumeich, M. Yarema, M. Walter, C. Guntlin and M. V. Kovalenko, *J. Am. Chem. Soc.*, 2013, **135**, 4199.
- 31 R. Demir-Cakan, Y.-S. Hu, M. Antonietti, J. Maier and M.-M. Titirici, *Chem. Mater.*, 2008, **20**, 1227.
- 32 H. Ji, L. Zhang, M. T. Pettes, H. Li, S. Chen, L. Shi, R. Piner and R. S. Ruoff, *Nano Lett.*, 2012, **12**, 2446.
- 33 J. Ji, H. Ji, L. L. Zhang, X. Zhao, X. Bai, X. Fan, F. Zhang and R. S. Ruoff, *Adv. Mater.*, 2013, **25**, 4673.
- 34 D. Wang, X. Li, J. Yang, J. Wang, D. Geng, R. Li, M. Cai, T.-K. Sham and X. Sun, *Phys. Chem. Chem. Phys.*, 2013, **15**, 3535.
- 35 B. Luo, B. Wang, M. Liang, J. Ning, X. Li and L. Zhi, *Adv. Mater.*, 2012, **24**, 1405.
- 36 H. Zhang, H. Song, X. Chen and J. Zhou, *J. Phys. Chem. C*, 2012, **116**, 22774.
- 37 C. Wang, Y. Li, Y.-S. Chui, Q.H. Wu, X. Chen and W. Zhang, *Nanoscale*, 2013, **5**, 10599.
- 38 B. Luo, B. Wang, X. Li, Y. Jia, M. Liang and L. Zhi, *Adv. Mater.*, 2012, **24**, 3538.
- 39 H. W. Lee, P. Muralidharan, R. Ruffo, C. M. Mari, Y. Cui and D. K. Kim, *Nano Lett.*, 2010, **10**, 3852.
- 40 H. Wu, G. Yu, L. Pan, N. Liu, M. T. McDowell, Z. Bao and Y. Cui, *Nat. Commun.*, 2014, **4**, 1943.
- 41 M. P. B. Glazer, J. Cho, J. Almer, J. Okasinski, P. V. Braun and D. C. Dunand, in preparation, 2014.

Graphical Abstract

A SnO₂-coated Cu foam with 3D interconnected scaffold was fabricated by a simple sol-gel method for use as a self-supporting anode for lithium-ion batteries. The binder- and carbon-free electrode integrated with current collector exhibits a high reversible capacity, excellent rate capability, and stable cycle retention by preserving its structural integrity.

